

Review on CO₂ Capture Using Amine-Functionalized Materials

Jannis Hack, Nobutaka Maeda,* and Daniel M. Meier*

Cite This: *ACS Omega* 2022, 7, 39520–39530


Read Online

ACCESS |

Metrics & More

Article Recommendations

ABSTRACT: CO₂ capture from industry sectors or directly from the atmosphere is drawing much attention on a global scale because of the drastic changes in the climate and ecosystem which pose a potential threat to human health and life on Earth. In the past decades, CO₂ capture technology relied on classical liquid amine scrubbing. Due to its high energy consumption and corrosive property, CO₂ capture using solid materials has recently come under the spotlight. A variety of porous solid materials were reported such as zeolites and metal–organic frameworks. However, amine-functionalized porous materials outperform all others in terms of CO₂ adsorption capacity and regeneration efficiency. This review provides a brief overview of CO₂ capture by various amines and mechanistic aspects for newcomers entering into this field. This review also covers a state-of-the-art regeneration method, visible/UV light-triggered CO₂ desorption at room temperature. In the last section, the current issues and future perspectives are summarized.

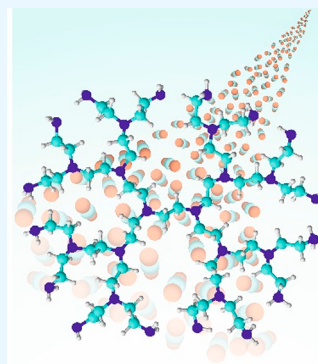

1. INTRODUCTION

Since the onset of the Industrial Revolution in the 18th century, the atmospheric concentration of carbon dioxide increased from ca. 280 ppm¹ to 417 ppm in 2022. The climate change and sea level rise of 1–3 mm per year arise from the record-high level of atmospheric CO₂ concentration. Besides, CO₂-induced ocean acidification is considered to have an impact on organisms and the ecosystem.^{2,3} Provided that no action is taken, the atmospheric CO₂ concentration is estimated to rise up to 450 ppm by 2050.⁴ Because of surging public concerns about potential environmental damage, carbon capture and storage/sequestration (CCS)⁵ or utilization (CCU)⁶ became one of the key research topics in the 21st century. CCS aims at geological storage of CO₂ in the deep underground. On the other hand, CCU is a concept in which captured CO₂ is utilized as a carbon source for chemical feedstocks such as fuels and fine chemicals. The scientific community and industry are gradually coming to a conclusion that CCS has limitations, taking into account the economic feasibility. Hence, industries are shifting toward exploration of CCU technologies.⁷ In any case, CO₂ capture is the very first step and thus the most critical technology to pave the way for facilitating the industrialization of CCS and CCU. In the industrial sector, pressure swing adsorption (PSA) and amine scrubbing have traditionally been applied for some decades.⁸ PSA, which has been the main technology in the last a few decades, separates hydrogen out of other gases, including CO₂. Since PSA aims at purification of H₂, the resulting concentration of CO₂ collected from off-gas is too low to utilize CO₂ for further chemical processes.⁸ On the other hand, amine scrubbing has been applied since 1930 and allows CO₂ collection with high purity (>99%).⁹ CO₂ is captured by using

monoethanolamine solution (20–30 wt % in water) and then released at 100–120 °C. Amine scrubbing produces a huge amount of degraded solvent as waste. Therefore, the current scrubbing technologies are energy intensive and therefore not very economical. To improve CO₂ capture technology, two major drawbacks of amine scrubbing need to be overcome: (1) energy-inefficient regeneration at high temperature and (2) waste management of the degraded solvent containing amines. In light of this, CO₂ capture using solid materials has recently come under the spotlight.¹⁰ CO₂ adsorption on solid materials occurs at solid–gas interfaces and thus requires no solvent, leading to the complete elimination of the solvent disposal process. Normally, CO₂ adsorption on solid materials is carried out at ambient temperature, followed by regeneration of the materials at 80–120 °C to release CO₂. Therefore, high energy input during the regeneration process is still inevitable. Solid adsorbent-based technology can be applied for two different capturing concepts. One is the direct air capture (DAC) which captures CO₂ directly from the atmosphere. The other is CO₂ capture from the off-gas of industrial sectors such as power plants and factories for fine chemical synthesis. DAC is considered to be a “negative emission technology” because already released CO₂ in the air (417 ppm) has to be captured. However, DAC is much less cost-effective compared to CO₂ capture from exhaust streams because of the low concentration

Received: May 31, 2022

Accepted: October 5, 2022

Published: October 28, 2022




Table 1. Summary of CO₂ Adsorption Performance of Different Adsorbents

Support	Absorbent	Amine loading [wt %]	Adsorption capacity [mmol/g]	Adsorption temperature [°C]	Desorption temperature [°C]	Adsorption conditions	Reference
SBA-15	functionalized by different aminosilanes	-	2.2 to 3.2	25	95 to 105	pure CO ₂ , static	Boukoussa et al. ³¹
SBA-15 and fumed silica	TEPA, impregnated	-	3.25 to 3.97	75	115	15% CO ₂ , no information about gas flow	Chao et al. ³²
β -zeolite	TEPA, impregnated	38.4	2.90	30	135	10% CO ₂ , 30 mL/min	Fischer et al. ¹²
protonated titanate nanotubes (PTNTs)	TEPA, impregnated	60	4.13	75	100	10% CO ₂ , 10 mL/min	Guo et al. ¹³
nanoporous titanium oxyhydrate	TEPA, impregnated	60	3.1	60	100	1% CO ₂ and 1% H ₂ O, 300 mL/min	Irani et al. ³³
carbon nanotubes (CNTs)	TEPA, impregnated	75	5.0	60	90	10% CO ₂ and 1% H ₂ O, 300 mL/min	Irani et al. ¹⁴
PMMA (HP2MG)	TEPA and modified TEPA, impregnated	-	2.58 to 4.30	25	100	pure CO ₂ , 200 mL/min	Jo et al. ¹⁵
silica gel	TEPA and PEI, impregnated	40	2.64 to 3.32	75	100	pure CO ₂ , 100 mL/min	Jung et al. ³⁴
PAN carbon fibers	TEPA and TETA, impregnated	50	4.30 to 5.44	25	90	10% CO ₂ , 30 mL/min	Kuang et al. ³⁵
mesoporous SiO ₂ (MCM-41)	EPA, DETA, TEPA, and PEHA, impregnated	40	1.19 to 2.34	35	100	10% CO ₂ , no information about gas flow	Liu et al. ¹⁷
TiO ₂	monoethanolamine, impregnated	40	1.09	45	90	1% CO ₂ , 300 mL/min	Sun et al. ³⁶
MR10 (LDPE)	BPEI, impregnated	50	2.64	25	70	different concentrations of CO ₂ , 3 mL/min	Wang et al. ²²
fumed silica	BPEI and IL, impregnated	30 and 10	-	25	50	5000 ppm of CO ₂ , 200 mL/min	Weisschar et al. ²³
nanosilica	LPEI, impregnated	different loadings	1.0 to 3.5	different temperatures	50–60	different concentrations of CO ₂ , 3 mL/min	Zhang et al. ²⁴
-	IRMOF-74-III-(CH ₂ NH ₂) ₂ , alkylamine functionality	-	1.2	25	120	pure CO ₂ , static	Flaig et al. ²⁹
-	N-containing polymer NUT-4, imine linker	-	6.9	25	25	10% CO ₂	Geng et al. ²⁷
-	N-doped copolymer	-	3.1	0	-	pure CO ₂ , static	Qi et al.

of CO₂ in the air and thus the associated thermodynamic barrier.⁴ On the other hand, CO₂ capture from industrial off-gas is considered as “zero emission technology” in order not to increase the current CO₂ level any further. Depending on emission sources, the CO₂ concentration differs in a wide range of 3–100%.¹¹ For example, the off-gas from coal-fired power plants contains 10–15% CO₂, whereas fermentation plants for ethanol production emit 98–99% CO₂.¹¹ Hence, CO₂ capture from these plants is thermodynamically favored and can be cost-effective. Public concerns about global warming and awareness of the importance of CO₂ removal make both “negative emission technology” and “zero emission technology” a high priority. Such an urgent demand has lately been extending the horizon of solid adsorbent materials with new concepts, and in the past decade we have witnessed tremendous advance in this field.¹⁰ Porous materials have been extensively explored, targeting high CO₂ adsorption capacity such as carbonaceous adsorbents, ionic liquids, zeolites, metal oxides, and metal–organic frameworks (MOFs). The overview of different adsorbents is summarized in a previously published review article.¹⁰

In this review, we outline properties, advantages, disadvantages, and future perspectives of amine-functionalized materials, foreseeing their potential for high CO₂ adsorption capacity, relatively low regeneration temperature, cost-effectiveness, and industrial applications. This article not only summarizes different amine-based materials but also sums up the effects

of impurities in off-gas streams and adsorption mechanisms and process engineering.

2. AMINE-FUNCTIONALIZED SOLID

Amine-functionalized solid adsorbents light a path for mitigating the issues encountered by liquid amine scrubbing, such as the loss of volatile amines by vaporization. The support materials with high surface area and porosity are functionalized with amines, such that the amines are well-dispersed as uniformly as possible. Hence, the functionalized materials possess the positive properties of both components (an amine and a support). The support materials are often functionalized in two different ways: wet impregnation or anchoring on the surface with covalent bonds. This chapter discusses what types of amines and solid support materials have already been explored. Table 1 lists adsorbent materials reported by different research groups in the last 15 years.

2.1. Type of Amines. As described in the Introduction, the monoethanolamine solution has been used as a main sorption component for amine scrubbing. Since monoethanolamine is not suitable for the functionalization of solids due to its high volatility and the small adsorption capacity of CO₂, longer-chain amines have often been employed in the past. A prime example in this respect is tetraethylenepentamine (TEPA), which contains five amine groups and thus has the theoretical capacity of chemisorption of up to five CO₂ molecules per one TEPA molecule. Because the past research mainly focused on

the adsorption capacity, the high adsorption capacity of TEPA attracted much attention.^{12–16} As a result, TEPA has become one of the most widely used amines for the functionalization of solid materials. Besides, other ethyleneamines, such as triethylenetetramine (TETA) and pentaethylenhexamine (PEHA), are also suitable for the functionalization as they have similar performance in CO₂ adsorption.¹⁷ Recently, the amine-containing polymer, i.e., polyethylenimine (PEI), has also come to the forefront of research. PEI has two different structures: branched polyethylenimine (BPEI) and linear polyethylenimine (LPEI).^{18–21} Due to the significantly lower price and availability in the market, BPEI was studied more extensively compared to LPEI. Both PEI types have adsorption capacity similar to or slightly lower than TEPA. However, the regeneration temperature of PEI is much lower, especially LPEI, compared to shorter ethyleneamines.^{21,22} Another exciting aspect of the use of PEI is the influence of the polymer size. Smaller PEI molecules are better suited for the impregnation of porous materials because they can diffuse more uniformly into the pores than large PEI molecules. Larger PEI molecules, on the other hand, are less soluble in water, resulting in better regeneration stability under humid conditions. This is an important factor considering long-term operations. As shown in Table 1, different adsorption temperatures 25–75 °C were chosen for each of the reports. The concept of such adsorption conditions was built upon the exploitation of the off-gas heat from industrial sectors. The source of CO₂ emission from the industrial sectors is normally higher than room temperature, e.g., coal and petroleum power plants (40–65 °C).¹¹ Therefore, the adsorption performance in this temperature range is important for industrial applications. Due to the climate change and global concerns about energy and the environment, the research direction is shifting toward how to lower the regeneration temperature without compromising the high adsorption capacity. Weissar et al. reported that a hybrid adsorbent of BPEI with ionic liquid released CO₂ even at 50 °C.²³ The zwitterions formed by the reaction of amines and CO₂ interact with counterion pairs of the ionic liquid, leading to the weakening of the C–N bond as shown in Figure 1.

Yogo et al. reported a different approach to improving both adsorption and desorption properties by chemical medication

of amino groups.²⁴ TEPA substituted with bulky alkyl groups was found to enhance the adsorption capacity and to lower the regeneration temperature. They achieved 88% efficiency in the desorption at 60 °C by sweeping an inert gas.

2.2. Support Materials. The choice of an appropriate support material is driven by several factors. Two important properties for the support material are the thermal stability and chemical inertness. Accordingly, the support material should not be decomposed at relatively high temperature and should not react with amines during functionalization so that the amines remain available for the chemisorption of CO₂. Table 1 shows the various support materials tested in recent years. It is worth noticing that all supports reported fulfill the two criteria mentioned above. However, additional properties must be considered to finely tune the adsorption and desorption performance. For example, additional decisive properties are specific surface area, porosity, and pore volume, whereby the adsorption performance is interrelated. The specific surface area plays an important role in impregnating amines onto the support material uniformly. Support materials with high surface area can impregnate a larger amount of amines, leading to higher adsorption capacity. Because BPEI is a highly viscous liquid, thick liquid BPEI layers are formed on support materials with low specific surface area. The thick liquid layers inhibit gas diffusion, resulting in the low efficiency for CO₂ adsorption. Furthermore, the porosity and the pore volume are important for the diffusion of gaseous molecules through the support material. Materials with high porosity and large pore volume are favored due to better mass transport through the support material. Such a property can enhance the adsorption capacity as well as rapid desorption of CO₂. Thus, the choice of support material drastically influences the performance of the adsorbents.²⁵ Furthermore, the number of acid sites on the surface also has an influence on the sorption properties of the amine. The beneficial effects of acidic sites of the support material can be attributed to the interaction between the acid sites and the amine groups. The presence of strong surface acidity contributes to the formation of protonated amine species on which CO₂ weakly adsorbs. This is beneficial to the repeated cycles of adsorption and desorption.²⁶ On one hand, the higher thermostability of the entire system and better distribution of the amine on the surface of the support material result in more efficient adsorption.²⁶

2.3. Functionalized Polymeric Adsorbents. There has been a new strategy to add the CO₂-capturing property to polymeric compounds such as porous polymers^{27,28} and metal–organic frameworks (MOFs)^{29,30} with amine-functionalized linkers. MOFs are classified as coordination polymers with a metal cation center and organic linker. Yagi and co-workers reported that IRMOF-74-III was functionalized with primary or secondary amines.³⁰ IRMOF-74-III-CH₃ without amine functionalization also adsorbed CO₂, but the adsorption capacity dropped by 80% under humid conditions. This behavior can be explained by the CO₂ adsorption to the open Mn sites where H₂O competitively coordinates. On the other hand, the moisture did not affect the performance of IRMOF-74-III-CH₂NH₂, indicating that the CO₂ uptake occurs with the amine linkers and that the open Mn sites are not available. The regeneration of IRMOF-74-III-CH₂NH₂ required 90 °C to remove CO₂. They extended the synthetic method toward functionalization by diamine and reported that IRMOF-74-III-(CH₂NH₂)₂ adsorbed 2.33 times more CO₂ than monoamine-

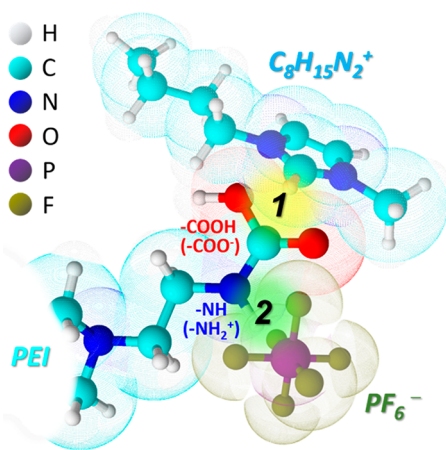


Figure 1. Proposed interaction of BPEI and ionic liquid. Copyright 2016 American Chemical Society. Reprinted with permission from ref 23.

functionalized IRMOF-74-III-CH₂NH₂.²⁹ The complete regeneration was achieved at 120 °C in a vacuum.

Recently, Sun and co-workers have proposed nitrogen-doped porous carbons (NPCs) for CO₂ capture.^{27,28} The NPCs were prepared through polymerization of 2,4,6-tris-(chloromethyl)mesitylene (TCM) and *p*-phenylenediamine (PD) to a polymer of NUT-4 (NUT stands for Nanjing Tech University). The obtained NUT-4 was further carbonized at elevated temperatures (400–700 °C) to obtain NPCs. The CO₂ adsorption capacity of 6.9 mmol/g was achieved with NPCs containing CO₂-philic N sites. The complete regeneration of the adsorbent was possible under mild condition (25 °C, 30 mmHg, 60 min).

3. MOISTURE EFFECT

Amine-functionalized solid materials are advantageous over porous adsorbents because of their high tolerance against moisture. In most of the cases, the presence of moisture even enhances the CO₂ adsorption capacity^{14,20,22,33,36–40} yet keeps the regeneration temperature in the same range.²³ The atmosphere contains 18–60% humidity on average over the year. The exhaust gas from power plants also contains moisture. Therefore, both DAC and CO₂ capture from industrial off-gas using amine-functionalized materials can greatly benefit from the enhancement effect of CO₂ adsorption by moisture. Figure 2 shows typical examples of reaction

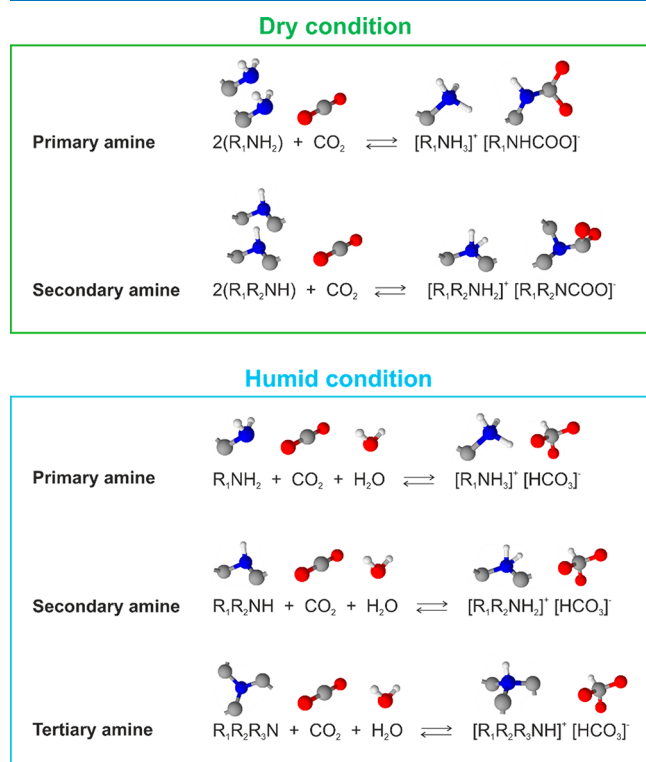


Figure 2. Examples of reaction schemes of CO₂ adsorption under dry and humid conditions.

schemes of amines with CO₂ under dry and humid conditions.¹⁴ Under dry conditions, two primary amines react with one CO₂ molecule to form an ammonium ion and carbamate ion. The secondary amines follow the same reaction path. Therefore, the maximum efficiency can only be 0.5 mol of CO₂ per mole of amine. Under humid conditions, both

primary and secondary amines react with CO₂ and H₂O to form ammonium ions and bicarbonate. Hence, the theoretical value of moles of CO₂ per mole of primary and secondary amines doubles to 1.0 under humid conditions. Likewise, under humid conditions, CO₂ and water react with tertiary amines by forming an ammonium ion and bicarbonate and by binding one mole of CO₂ per mole of tertiary amine. These reactions schemes are examples out of all the potential reaction paths, e.g., the formation of carbamic acid. The actual reaction appears to be more complicated than the schemes described in Figure 2.

According to the theoretical estimation, the presence of moisture should double the CO₂ adsorption capacity for primary and secondary amines. Thus, the enhancement effect of moisture depends on the type of amines used and relative humidity (RH). On PEI supported on resin²² or polymer,³⁹ CO₂ adsorption capacity increases proportionally with RH. With 100 RH % at a dew point of 25 °C, the CO₂ breakthrough period was twice as long as that of dry conditions.²³ The recyclability test was also conducted using a triamine-grafted mesoporous material.³⁸ Under dry conditions, CO₂ uptake dropped by 15% after 700 cycles because of the formation of a stable urea, whose reaction is not reversible. Under humid conditions, the same CO₂ adsorption capacity was kept over 700 cycles. H₂O was reported to react with urea to form carbamate, leading to the long-term durability of the adsorbent. Another striking feature of the moisture effect is that the desorption temperature was never influenced by the presence of moisture even though CO₂ uptake was doubled.²³ Normally, the desorption temperature increases for samples with higher loading amount of amine.⁴¹ A clear answer to this unique effect of the moisture was given by quantum chemical calculations.³⁷ As in Figure 3, a H₂O-stabilized zwitterion is formed during the CO₂ adsorption process, which helps CO₂ transport through PEI. Therefore, under humid conditions the diffusion barrier can be minimized.

4. TOLERANCE FOR IMPURITIES

In this section, the effects of SO₂, NO_x, CO, and O₂ on CO₂-capturing property are summarized. The performance of liquid amine scrubbing with monoethanolamine (MEA) is tremendously deteriorated by the presence of impurities such as SO₂ and O₂ in flue gas streams.⁴² Therefore, it is of vital importance to investigate the potential degradation of amine-functionalized materials under such conditions for industrial applications. Xu et al. investigated the effects of impurities in a flue gas on CO₂-capturing property using 50 wt % of BPEI (Mn = 600) finely dispersed in the pores of MCM-41.⁴³ They employed the actual off-gas from a natural gas-fired boiler containing 7.4–7.7% CO₂, 14.6% H₂O, ~4.45% O₂, 200–300 ppm of CO, 60–70 ppm of NO_x, and 73–74% N₂. N₂, O₂, and CO had little influence on CO₂ adsorption, while NO_x slightly decreased the amount of CO₂ adsorbed. However, CO₂ was captured 3000 times more than NO_x, demonstrating that BPEI/MCM-41 can efficiently separate CO₂ from the flue gas. Rezaei et al. reported single-component adsorption⁴⁴ and multicomponent adsorption⁴⁵ using SO₂, NO_x, and CO₂ with different amine types. They demonstrated that SO₂ greatly influenced CO₂ adsorption at 35 °C but had much less influence at 75 °C.⁴⁴ This phenomenon originates from the fact that SO₂ adsorption capacity decreases with an increase in temperature, while CO₂ adsorption capacity increases. The

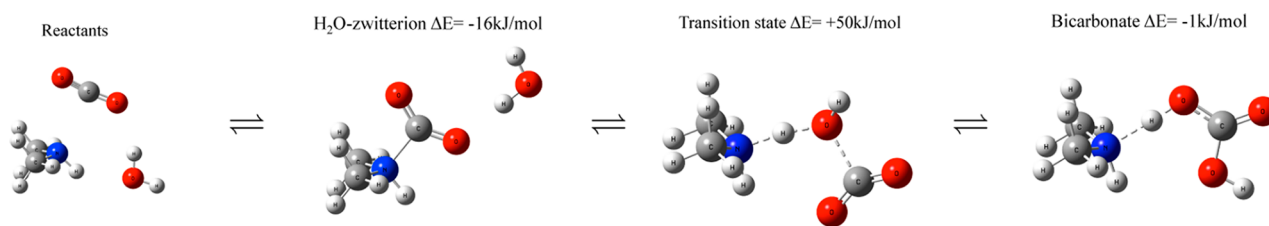


Figure 3. Water-assisted formation of bicarbonate via a zwitterion. Copyright 2016 American Chemical Society. Reprinted with permission from ref 37.

coadsorption experiments showed that the presence of SO₂ considerably deteriorates CO₂ adsorption performance.⁴⁵ Among all the amine types, secondary amine was less influenced by SO₂. Coadsorption with NO has no impact on CO₂ adsorption, whereas NO₂ slightly suppressed CO₂ adsorption capacity.⁴⁵

The degradation of amine-functionalized materials by oxygen was also extensively studied.^{46–51} Normally, the off-gas from power plants and some fine chemical factories contain a certain concentration of oxygen. Therefore, O₂ tolerance of the amine-based materials should be taken into account for industrial applications with long-term operation. The reason for the degradation by O₂ has never been clearly demonstrated. Heydari-Gorji et al. carried out infrared spectroscopic and NMR analysis of a triamine-grafted material (TRI).^{48,49} Upon the TRI deactivation, a new IR band emerged at 1665–1680 cm⁻¹, but only a minor change was confirmed by ¹³C NMR except for a weak peak at 158 ppm. What these changes indicate remain uncertain. However, they assumed that the possible formation of imine, carbamic acid, and nitrene cannot be ruled out. Further research is required to draw a solid conclusion on the oxidative degradation mechanism of TRI. Bali et al. thoroughly investigated the oxidative degradation of PEI and poly(allylamine) (PAA) on mesoporous alumina support employing infrared, Raman, and ¹³C NMR spectroscopy.⁴⁷ Their data clearly proved the formation of a C=O bond associated with deactivation of PEI. They concluded that undesirable formation of amides, acids, and imides leads to lower basicity of the nitrogen species in the polymer and thus low CO₂ adsorption capacity. According to their findings, PAA may serve as a better adsorbent with high oxidative stability. Ahmadalinezahad et al. also came to a similar conclusion by using 1D and 2D NMR techniques.⁴⁶ BPEI is the most unstable amine among the amines tested, and PAA and LPEI can be more resistant to the oxidative atmosphere.

5. MECHANISTIC STUDIES

The advance in spectroscopy, in situ techniques, and quantum mechanical modeling in the past decade promoted mechanistic investigations to unveil the underlying mechanism of CO₂ adsorption and desorption. Commonly used techniques in this field are infrared spectroscopy,^{23,52–60} nuclear magnetic resonance (NMR),^{61–66} and density functional theory (DFT).^{37,67–70} This chapter briefly summarizes what information can be gained by each technique and major findings related to CO₂ adsorption mechanisms.

NMR studies were mainly reported by the group of Jones and colleagues,^{61–66} exploiting ¹H NMR,⁶⁶ ¹³C NMR,^{64,65} ¹⁵N dynamic nuclear polarization (DNP) NMR,⁶⁴ rotational-echo double-resonance ¹⁵N(¹³C) and ¹³C(¹⁵N) (REDOR) NMR,⁶² and two-dimensional ¹³C–¹H heteronuclear correlation (HETCOR) NMR.^{61,63} ¹³C NMR is a powerful tool to

identify reaction pathways and surface species formed, such as carbamic acid, carbamate, bicarbonate, and urea. In particular, its combination with IR spectroscopy offers a firm understanding of molecular structure because the frequency difference between asymmetric and symmetric stretching vibrations of carboxylate ions provides insight into the molecular interaction.⁶⁴ REDOR NMR is useful to gain information about short- and long-range dipolar coupling between isolated pairs of heteronuclei. ¹⁵N(¹³C) REDOR NMR identified amide-like species such as carbamic acid and carbamate. Together with its counterpart, ¹³C(¹⁵N) REDOR NMR, REDOR NMR indicated that carbamate species are isolated from each other.⁶² 2D NMR with HETCOR sequence detects the correlation of two different nuclei (c.f., ¹³C and ¹H) via single-bond spin–spin coupling and thus unveils which proton is bonded to which carbon groups. Chen et al. reported that ¹³C and ¹H HETCOR NMR detected two distinct bicarbonate species at 100 K, which are coupled to different protons, respectively.⁶³ Their follow-up study evidenced that one bicarbonate species is coupled to H₂O molecules present on the walls of the mesoporous material, while another bicarbonate species is coordinated to H₂O molecules in the pores.⁶¹

DFT calculations contributed considerably to understanding what species is favorably formed and what reaction path is reasonable for the reaction of amines with CO₂.^{37,67–70} Early stage research was reported by Mebane et al. that the formation of a zwitterion was unstable in a polar environment of anhydrous PEI.⁶⁷ However, a dielectric medium under humid conditions stabilizes the zwitterion. They also proposed linear and ring topologies to be responsible for CO₂ diffusion in the bulk PEI under humid conditions.³⁷ DFT calculations in combination with adsorption isotherms demonstrated that CO₂ uptake caused the volume expansion of the amine layers and thus the decrease in the pore volume.⁶⁹ Therefore, sticky amines with high viscosity might increase the diffusion resistance and have a negative impact on CO₂ adsorption property.

In situ infrared spectroscopy is the most widely utilized technique to follow the reaction path in this field because the setup is relatively cheap and can be operated easily.^{23,52–60,64,71} Since there is an extensive review on IR spectroscopic studies published in 2019,⁵⁴ we only describe major findings briefly and update that what has been newly reported since then. A number of reports contributed to assign IR bands observed during CO₂ adsorption such as carbamic acid, carbamate-physisorbed CO₂, and ammonium ions. The detailed band assignment is given in a previous review article.⁵⁴ The most frequently used amine, TEPA, was also investigated by in situ IR spectroscopy. By increasing the thickness of TEPA layers, the interaction between amines was enhanced, forming zwitterions with NH and NH₂ groups.⁵⁹ This phenomenon

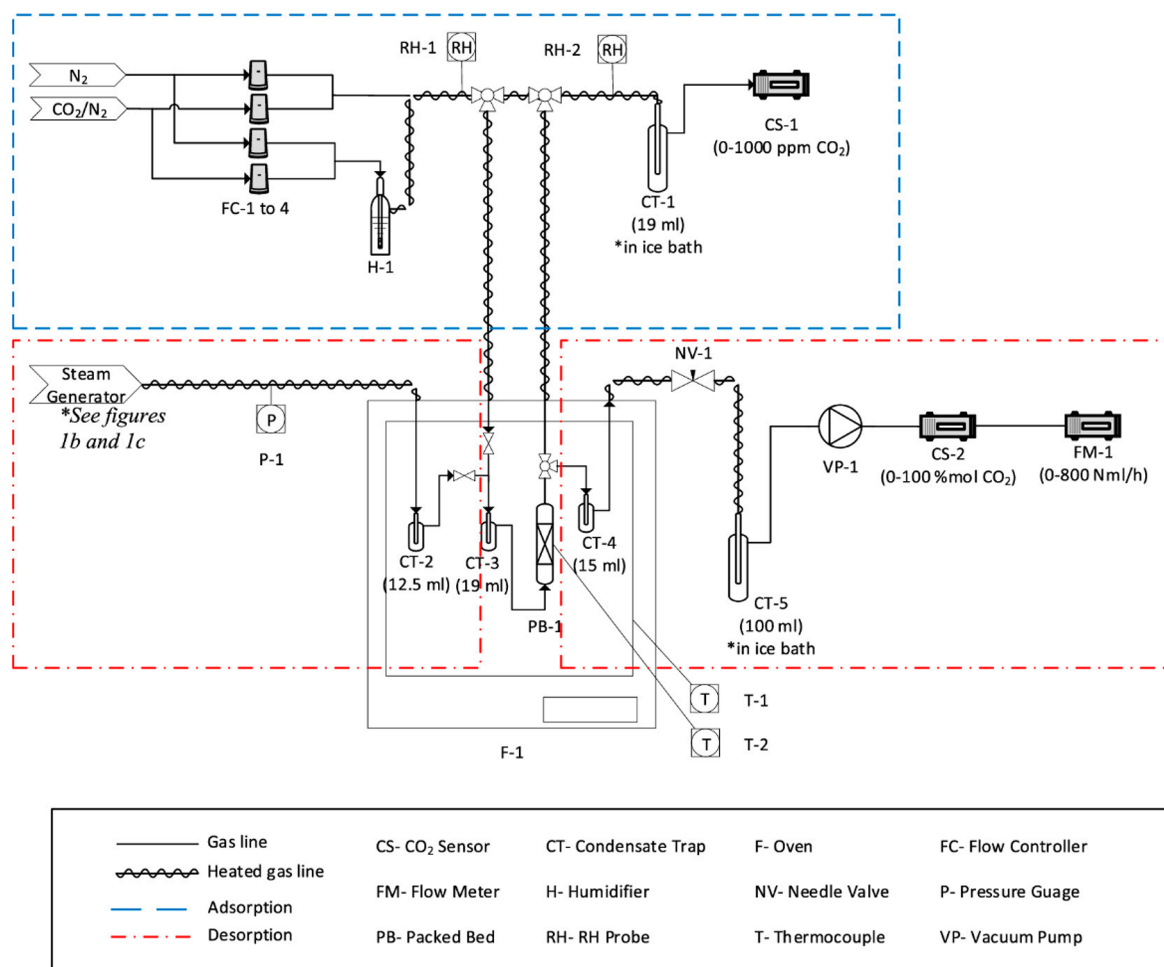


Figure 4. Water-assisted formation of bicarbonate via a zwitterion. Copyright 2016 American Chemical Society. Reprinted with permission from ref 72.

suppresses CO₂ gas diffusion in a thicker layer of liquid TEPA and leads to high-temperature desorption of CO₂ at 100 °C. The addition of polyethylene glycol (PEG) with low molecular weight TEPA was reported to increase the ratio of weakly adsorbed CO₂, whose band emerged at 2627 cm⁻¹ (NH₂—O).⁵⁷ PEI also possesses similar characteristics of IR bands.⁵⁶ IR spectroscopy together with thermogravimetric analysis (TGA) provided important information about BPEI behavior at different temperatures. Due to the high viscosity of liquid BPEI, adsorption capacity increased with temperature because of the reduction of the viscosity.⁵⁶ There are several reports on amine-grafted/-immobilized materials.^{52,53,58,60} The IR spectroscopic features and behavior were similar to that of TEPA and BPEI. Effects of NO₂ and SO₂ on CO₂ adsorption were also investigated by in situ IR spectroscopy.⁵⁵ Those acidic gases form NH—NO₂ and NH—SO₂ complexes assigned at 1650 cm⁻¹, leading to the deterioration of CO₂ adsorption performance. NO₂ has less influence on the amount of CO₂ adsorbed even at 200 ppm, but the presence of SO₂ leads to the considerable reduction of CO₂ adsorption above 50 ppm. Weissnar et al. have recently demonstrated that in situ IR spectroscopy could be a useful tool to monitor the weakening of the C—N bond of carbamic acid and carbamate.²³ Such an attempt would be beneficial for designing an adsorbent material with low-temperature regeneration.

6. REACTOR AND PROCESS DESIGN

6.1. Vacuum Swing Desorption. Temperature vacuum temperature swing desorption (TVSD) is considered to be useful because a high-level vacuum is not required.⁷² The process optimization is critical to not waste time, energy, and CO₂ gas during the desorption process so that the maximum efficiency for collecting pure CO₂ can be achieved. In the TVSD process, CO₂ is first chemisorbed on an adsorbent material at atmospheric conditions (typically 25 °C and 1 bar). After saturation of the material with CO₂, the chamber with the adsorbent is closed and evacuated by a vacuum pump, removing the excess gas at the beginning and weakly adsorbed CO₂. In order to desorb further CO₂, the adsorbent bed is heated to the desorption temperature.⁷³ Figure 4 displays the schematic diagram of a typical TVSD setup. There is also an attempt without any temperature swing, i.e., vacuum swing desorption (VSD), operated at 90 °C.⁷⁴ VSD can achieve 95% CO₂ purity and 90% recovery. Due to the high-temperature operation, the degradation of CO₂ adsorption capacity is expected with repeated cycles. Hence, the fabrication of thermally stable adsorbents must be taken into account.⁷⁴ Compared to VSD, TVSD is more efficient when higher CO₂ concentration is required. In some cases, >99% CO₂ can be achieved with 0.23 mmol/g/h of the desorption rate.⁷² Under humid conditions during the vacuum process, the desorption rate increased to 3.75 mmol/g/h, confirming the beneficial

kinetics assisted by steam. However, additional energy is required for the desorption of water if H₂O is coadsorbed with CO₂. The recyclability test revealed that 8% loss in CO₂ adsorption capacity was observed after 50 cycles (>1500 h).⁷² Gebald et al. also reported cyclic experiments using TVSD with amine-functionalized cellulose.⁷⁵ 100 cycles of adsorption and regeneration at 90 °C caused 2% loss of the N content. However, this report showed a high potential that TVSD can be well applied for DAC.

6.2. Steam-Stripping Regeneration. Instead of TVSD, steam-stripping regeneration combined with temperature swing desorption (TSD) has been explored to collect pure CO₂.^{76–82} In the regeneration process, a stream saturated with H₂O carries a mixture of CO₂ and H₂O, and then a concentrated CO₂ can be obtained by compression and condensation.⁸³ There is a report on studying how to minimize the energy consumption, employing superheated steam from low-pressure steam turbine and a heat exchanger.⁷⁶ This so-called “direct steam-stripping process” was found to lower the energy consumption by 23.2% compared to a conventional stripping method. The steam stripping can also be combined with vacuum swing adsorption, named steam-aided vacuum swing adsorption (SA-VSA).⁷⁷ Yogo et al. demonstrated highly efficient CO₂ capturing performance using a system with three columns: the first column for adsorption, the second column for rinsing, and the third column for desorption.⁷⁷ The SA-VSA process with an amine-impregnated mesoporous MSU-F silica can achieve >98% of CO₂ purity and >93% of recovery rate. They also estimated the required heat for the regeneration to be much lower than that of liquid amine scrubbing and other amine-based solid adsorbents.

A challenge for its industrial application is the H₂O tolerance of amines at elevated temperature. After steam treatment, the adsorption capacity drops to a certain degree.^{83,84} For long-term operations, the fabrication of robust amine-based adsorbents is desired. Sayari et al. reported that amine-grafted SBA-15 showed high hydrothermal stability, and its exposure to steam for 48 h caused no change in the adsorptive and structural properties.⁸⁵ A choice of support materials is also a key factor for the steam tolerance. Upon exposure to steam, alumina support is partially transformed into boehmite, but it does not alter the amine efficiency.⁸⁰ Therefore, γ -Al₂O₃ is considered to be a promising support material to impregnate PEI.

6.3. Reactor Design. The design of the adsorption–desorption chamber is also a crucial factor to achieve high efficiency with amine-functionalized solid materials. There are two flow-reactor types considered: (1) fixed-bed reactor⁸⁶ and (2) fluidized-bed reactor.⁸⁷ In the fixed-bed reactor, the solid adsorbent is placed such that its position always remains the same when a gas stream flows through the fixed bed.⁸⁶ On the contrary, in the fluidized bed reactor, the adsorbent powders are swirled up with a gas stream and fly around inside the chamber.⁸⁷ The advantage of the fixed-bed reactor is that the process engineering and reactor design are much simpler and cheaper than the fluidized-bed reactor. Furthermore, a significantly larger quantity of adsorbent can be used per unit of space, which results in better process efficiency. However, the fluidized-bed reactor benefits from high adsorption rate and uniform heat distribution because the adsorption process is exothermic.⁸⁷

6.4. Process Design and Cost Estimate. A techno-economic analysis (TEA) was considered to assess the

applicability of reactor systems with amine-functionalized solids for large-scale CO₂ capture from exhaust gases. This included four different reactor types (fixed bed, fluidized bed, moving bed, and rapid thermal swing) and was compared with the liquid amine scrubbing often used today. By integrating the adsorption/desorption and heating/cooling processes, TEA estimated a cost of the process by each reactor which falls into the range of 48.1–75.2 \$/t-CO₂ and a heating recovery of 45–58%. These results support the use and need for CO₂ capture for flue gas purification.⁸⁸ The lowest price of 48.1 \$/t-CO₂ can be achieved with the fixed-bed adsorption configuration. Considering the current cost of 62.8 \$/t-CO₂ with amine scrubbing using 30 wt % of MEA, CO₂ capture with amine-functionalized solid materials has a high potential to compete in the market.

Zhao et al. designed and evaluated a 200 kW_{th} pilot reactor for the energy balance of three different regeneration processes (thermal regeneration with CO₂ stream, vacuum regeneration, steam-stripping regeneration).⁸⁹ Amine-functionalized resin was selected to evaluate the efficiency and energy needs for each of the regeneration processes. The least energy is required for the thermal regeneration. Compared to the liquid amine scrubbing often used today, the energy consumption can be reduced by 30% or more. However, if the thermal regeneration is supported by an additional vacuum system, the energy consumption is higher than the thermal process itself but still much lower than the liquid amine scrubbing. In addition, the whole reactor is complicated and more expensive when the vacuum is applied. The steam-stripping regeneration requires the most energy, but the process can be greatly optimized when the steam condensation and heat recovery are taken into account.⁸⁹ The total annual cost also depends on the plant size. Mazzotti et al. performed a techno-economic assessment and found that the cost of commercially available adsorbent considered gas had much less impact on the process cost, but the size and shape of the adsorption system critically affect the investment cost.⁹⁰ The adsorption-based process can be competitive at the small scale (less than 100 tons of flue gas per day) and low recovery rate (less than 40%). However, the classical liquid amine scrubbing is still the most cost-effective at most of the plant sizes and recovery rates.

To perform a cost estimation for CO₂ capture and concentration (CCC) technology, a model was created to calculate the cost per ton of CO₂ captured for a 500 MW power plant. The absorbent used was zeolite 13X, which can also be replaced by an amine-functionalized material. Based on the calculations, a tremendous amount of energy can be saved when the concentration of CO₂ in the flue gas is high enough. Besides, the adsorption efficiency of the reactor can be increased by shortening the reactor length with the larger diameter. At an off-gas CO₂ concentration of 15%, the cost estimate was \$32.8 to \$34.4 per ton of CO₂ captured.⁹¹

7. LIGHT-TRIGGERED CO₂ ADSORPTION AND DESORPTION

In this section, a state-of-the-art CO₂ desorption method is described. In the past decade, photosensitive functional groups are applied for low-temperature regeneration of adsorbents by visible and/or UV light.^{92–94} This method allows CO₂ adsorption–desorption cycles to be operated under mild conditions (1 bar and room temperature). Lyndon et al. reported that a zinc-based MOF with 4,4′-dicarboxylate (AzDC) and *trans*-1,2-bis(4-pyridyl)ethylene (4,4′-BPE) as a

framework released CO₂ under UV light irradiation at 30–31 °C.⁹² In situ FT-IR spectroscopy detected the change in C–C–C and C–C–N bending modes, originating from *cis*–*trans* isomerization of Zn(AzDC)(4,4'-BPE)_{0.5} under UV irradiation. The desorption capacity was 42% under static irradiation conditions and 64% under dynamic measurements.

Sun and co-workers reported photosensitive MOFs functionalized with azobenzene for CO₂ adsorption–desorption by UV and visible lights.⁹³ Tetraethylenepentamine (TEPA) was impregnated onto an UiO-type MOF functionalized with azobenzene (U-azo). Azobenzene changes its form between *trans* and *cis* under visible and UV lights, respectively. Exploiting this phenomenon, CO₂ bound to TEPA is released by UV light irradiation. U-azo has the CO₂ adsorption capacity of 43.4 cm³/g (ca. 1.94 mmol/g), among which 45.6% of adsorbed CO₂ can be released. They also demonstrated that CO₂ can be selectively separated using this principle out of gas mixtures of CO₂/N₂ and CO₂/CH₄. They further developed a novel adsorbent which works only with visible light.⁹⁴ MCM-41 was functionalized with (3-aminopropyl)triethoxysilane (APTES) and Disperse Red 1 (DR1). Without irradiation, the photosensitive DR1 is in *trans* configuration, leading to CO₂ capture on amines. Under visible-light irradiation, DR1 transforms into *cis* configuration, inducing CO₂ desorption. The CO₂ adsorption capacity was 32.1 cm³/g (ca. 1.43 mmol/g), 40% of which can be reversibly adsorbed and desorbed upon visible-light irradiation.

8. SUMMARY

A great deal of research has been reported on CO₂ capture by amine-based solid materials. In the last two decades, we witnessed a tremendous advance in material synthesis, optimization, and mechanistic aspects. However, practical use in the industrial sector still needs to overcome the following issues:

- (1) Long-term thermal stability during the regeneration process
- (2) Oxidative degradation
- (3) Material fabrication with lower regeneration temperatures
- (4) Reactor engineering and process optimization

Especially, point 3, “material fabrication with lower regeneration temperatures”, can mitigate points 1 and 2 because thermal stability and oxygen resistance would be greatly improved when the regeneration is operated in a low-temperature range of 40–60 °C. The cost estimate clearly proved that CO₂ capture by amine-functionalized solid materials can reasonably be appointed to the position currently taken by the liquid amine scrubbing. The 2021 United Nations Climate Change Conference commonly referred to as the 26th United Nations Climate Change conference (COP26) set new goals for the increase in the global temperature level and CO₂ emissions. The decision made in COP26 will dramatically change and refine research directions of CCS and CCU technologies. Amine-functionalized solid materials will be one of the main contributing technologies for achieving these goals.

AUTHOR INFORMATION

Corresponding Authors

Nobutaka Maeda – Institute of Materials and Process Engineering (IMPE), School of Engineering (SoE), Zurich University of Applied Sciences (ZHAW), Winterthur CH-

8400, Switzerland; orcid.org/0000-0001-5549-4982;

Email: maeo@zhaw.ch

Daniel M. Meier – Institute of Materials and Process Engineering (IMPE), School of Engineering (SoE), Zurich University of Applied Sciences (ZHAW), Winterthur CH-8400, Switzerland; Email: meid@zhaw.ch

Author

Jannis Hack – Institute of Materials and Process Engineering (IMPE), School of Engineering (SoE), Zurich University of Applied Sciences (ZHAW), Winterthur CH-8400, Switzerland

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acsomega.2c03385>

Notes

The authors declare no competing financial interest.

REFERENCES

- (1) Zhao, X. Y.; Qian, J. L.; Wang, J.; He, Q. Y.; Wang, Z. L.; Chen, C. Z. Using a tree ring delta C-13 annual series to reconstruct atmospheric CO₂ concentration over the past 300 years. *Pedosphere* **2006**, *16* (3), 371–379.
- (2) Kawahata, H.; Fujita, K.; Iguchi, A.; Inoue, M.; Iwasaki, S.; Kuroyanagi, A.; Maeda, A.; Manaka, T.; Moriya, K.; Takagi, H.; Toyofuku, T.; Yoshimura, T.; Suzuki, A. Perspective on the response of marine calcifiers to global warming and ocean acidification: Behavior of corals and foraminifera in a high CO₂ world “hot house”. *Prog. Earth Planet. Sci.* **2019**, DOI: [10.1186/s40645-018-0239-9](https://doi.org/10.1186/s40645-018-0239-9).
- (3) Tresguerres, M.; Hamilton, T. J. Acid base physiology, neurobiology and behaviour in relation to CO₂-induced ocean acidification. *J. Exp. Biol.* **2017**, *220* (12), 2136–2148.
- (4) Keith, D. W. Why Capture CO₂ from the Atmosphere? *Science* **2009**, *325* (5948), 1654–1655.
- (5) Agaton, C. B. Application of real options in carbon capture and storage literature: Valuation techniques and research hotspots. *Sci. Total Environ.* **2021**, *795*, 148683.
- (6) Sabri, M. A.; Al Jitan, S.; Bahamon, D.; Vega, L. F.; Palmisano, G. Current and future perspectives on catalytic-based integrated carbon capture and utilization. *Sci. Total Environ.* **2021**, *790*, 148081.
- (7) Rafiee, A.; Khalilpour, K. R.; Milani, D. Chapter 8 - CO₂ Conversion and Utilization Pathways. In *Polygeneration with Polystorage for Chemical and Energy Hubs*; Khalilpour, K. R., Ed.; Academic Press: 2019; pp 213–245.
- (8) Robert, A. M. *Handbook of Petroleum Refining Processes*, 3rd ed.; McGraw-Hill Education: New York, 2004.
- (9) Rochelle, G. T. Amine Scrubbing for CO₂ Capture. *Science* **2009**, *325* (5948), 1652.
- (10) D'Alessandro, D. M.; Smit, B.; Long, J. R. Carbon Dioxide Capture: Prospects for New Materials. *Angew. Chem., Int. Ed.* **2010**, *49* (35), 6058–6082.
- (11) Bains, P.; Psarras, P.; Wilcox, J. CO₂ capture from the industry sector. *Prog. Energy Combust. Sci.* **2017**, *63*, 146–172.
- (12) Fisher, J. C.; Tanthana, J.; Chuang, S. S. C. Oxide-Supported Tetraethylenepentamine for CO₂ Capture. *Environ. Prog. Sustain. Energy* **2009**, *28* (4), 589–598.
- (13) Guo, L. P.; Hu, X.; Hu, G. S.; Chen, J.; Li, Z. M.; Dai, W.; Dacosta, H. F. M.; Fan, M. H. Tetraethylenepentamine modified protonated titanate nanotubes for CO₂ capture. *Fuel Process. Technol.* **2015**, *138*, 663–669.
- (14) Irani, M.; Jacobson, A. T.; Gasem, K. A. M.; Fan, M. H. Modified carbon nanotubes/tetraethylenepentamine for CO₂ capture. *Fuel* **2017**, *206*, 10–18.
- (15) Jo, D. H.; Jung, H.; Shin, D. K.; Lee, C. H.; Kim, S. H. Effect of amine structure on CO₂ adsorption over tetraethylenepentamine impregnated poly methyl methacrylate supports. *Sep. Purif. Technol.* **2014**, *125*, 187–193.

- (16) Xie, W. L.; Ji, X. Y.; Fan, T. T.; Feng, X.; Lu, X. H. CO₂ Uptake Behavior of Supported Tetraethylenepentamine Sorbents. *Energy Fuels* **2016**, *30* (6), 5083–5091.
- (17) Liu, Z. L.; Teng, Y.; Zhang, K.; Chen, H. G.; Yang, Y. P. CO₂ adsorption performance of different amine-based siliceous MCM-41 materials. *J. Energy Chem.* **2015**, *24* (3), 322–330.
- (18) Prud'homme, A.; Nabki, F. Comparison between Linear and Branched Polyethylenimine and Reduced Graphene Oxide Coatings as a Capture Layer for Micro Resonant CO₂ Gas Concentration Sensors. *Sensors* **2020**, *20* (7), 1824.
- (19) Rosu, C.; Pang, S. H.; Sujana, A. R.; Sakwa-Novak, M. A.; Ping, E. W.; Jones, C. W. Effect of Extended Aging and Oxidation on Linear Poly(propyleneimine)-Mesoporous Silica Composites for CO₂ Capture from Simulated Air and Flue Gas Streams. *ACS Appl. Mater. Interfaces* **2020**, *12* (34), 38085–38097.
- (20) Zhang, H.; Goeppert, A.; Olah, G. A.; Prakash, G. K. S. Remarkable effect of moisture on the CO₂ adsorption of nano-silica supported linear and branched polyethylenimine. *J. CO₂ Util.* **2017**, *19*, 91–99.
- (21) Zhang, H.; Goeppert, A.; Prakash, G. K. S.; Olah, G. Applicability of linear polyethylenimine supported on nano-silica for the adsorption of CO₂ from various sources including dry air. *RSC Adv.* **2015**, *5* (65), 52550–52562.
- (22) Wang, W.; Liu, F.; Zhang, Q.; Yu, G.; Deng, S. Efficient removal of CO₂ from indoor air using a polyethyleneimine-impregnated resin and its low-temperature regeneration. *Chem. Eng. J.* **2020**, *399*, 125734.
- (23) Weissnar, F.; Gau, A.; Hack, J.; Maeda, N.; Meier, D. M. Toward Carbon Dioxide Capture from the Atmosphere: Lowering the Regeneration Temperature of Polyethylenimine-Based Adsorbents by Ionic Liquid. *Energy Fuels* **2021**, *35* (10), 9059–9062.
- (24) Yamada, H.; Chowdhury, F. A.; Fujiki, J.; Yogo, K. Enhancement Mechanism of the CO₂ Adsorption–Desorption Efficiency of Silica-Supported Tetraethylenepentamine by Chemical Modification of Amino Groups. *ACS Sustain. Chem. Eng.* **2019**, *7* (10), 9574–9581.
- (25) Cogswell, C. F.; Xie, Z.; Wolek, A.; Wang, Y.; Stavola, A.; Finkenauer, M.; Gilmore, E.; Lanzillotti, M.; Choi, S. Pore structure–CO₂ adsorption property relations of supported amine materials with multi-pore networks. *J. Mater. Chem. A* **2017**, *5* (18), 8526–8536.
- (26) Liu, Y.; Liu, J.; Yao, W. Y.; Cen, W. L.; Wang, H. Q.; Weng, X. L.; Wu, Z. B. The effects of surface acidity on CO₂ adsorption over amine functionalized protonated titanate nanotubes. *RSC Adv.* **2013**, *3* (41), 18803–18810.
- (27) Geng, J. C.; Xue, D. M.; Liu, X. Q.; Shi, Y. Q.; Sun, L. B. N-Doped Porous Carbons for CO₂ Capture: Rational Choice of N-Containing Polymer with High Phenyl Density as Precursor. *AIChE J.* **2017**, *63* (5), 1648–1658.
- (28) Qi, S. C.; Wu, J. K.; Lu, J.; Yu, G. X.; Zhu, R. R.; Liu, Y.; Liu, X. Q.; Sun, L. B. Underlying mechanism of CO₂ adsorption onto conjugated azacyclo-copolymers: N-doped adsorbents capture CO₂ chiefly through acid-base interaction? *J. Mater. Chem. A* **2019**, *7* (30), 17842–17853.
- (29) Flaig, R. W.; Osborn Popp, T. M.; Fracaroli, A. M.; Kapustin, E. A.; Kalmutzki, M. J.; Altamimi, R. M.; Fathieh, F.; Reimer, J. A.; Yaghi, O. M. The Chemistry of CO₂ Capture in an Amine-Functionalized Metal–Organic Framework under Dry and Humid Conditions. *J. Am. Chem. Soc.* **2017**, *139* (35), 12125–12128.
- (30) Fracaroli, A. M.; Furukawa, H.; Suzuki, M.; Dodd, M.; Okajima, S.; Gándara, F.; Reimer, J. A.; Yaghi, O. M. Metal–Organic Frameworks with Precisely Designed Interior for Carbon Dioxide Capture in the Presence of Water. *J. Am. Chem. Soc.* **2014**, *136* (25), 8863–8866.
- (31) Boukoussa, B.; Hakiki, A.; Bouazizi, N.; Beltrao-Nunes, A. P.; Launay, F.; Pailleret, A.; Pillier, F.; Bengueddach, A.; Hamacha, R.; Azzouz, A. Mesoporous silica supported amine and amine-copper complex for CO₂ adsorption: Detailed reaction mechanism of hydrophilic character and CO₂ retention. *J. Mol. Struct.* **2019**, *1191*, 175–182.
- (32) Chao, K. J.; Klinthong, W.; Tan, C. S. CO₂ Adsorption Ability and Thermal Stability of Amines Supported on Mesoporous Silica SBA-15 and Fumed Silica. *J. Chin. Chem. Soc.* **2013**, *60* (7), 735–744.
- (33) Irani, M.; Gasem, K. A. M.; Dutcher, B.; Fan, M. H. CO₂ capture using nanoporous TiO(OH)₂/tetraethylenepentamine. *Fuel* **2016**, *183*, 601–608.
- (34) Jung, H.; Lee, C. H.; Jeon, S.; Jo, D. H.; Huh, J.; Kim, S. H. Effect of amine double-functionalization on CO₂ adsorption behaviors of silica gel-supported adsorbents. *Adsorption* **2016**, *22* (8), 1137–1146.
- (35) Kuang, Y.; He, H.; Chen, S.; Wu, J.; Liu, F. Adsorption behavior of CO₂ on amine-functionalized polyacrylonitrile fiber. *Adsorption* **2019**, *25* (4), 693–701.
- (36) Sun, Z. Y.; Fan, M. H.; Argyle, M. Supported Monoethanolamine for CO₂ Separation. *Ind. Eng. Chem. Res.* **2011**, *50* (19), 11343–11349.
- (37) Li, K. J.; Kress, J. D.; Mebane, D. S. The Mechanism of CO₂ Adsorption under Dry and Humid Conditions in Mesoporous Silica-Supported Amine Sorbents. *J. Phys. Chem. C* **2016**, *120* (41), 23683–23691.
- (38) Sayari, A.; Belmabkhout, Y. Stabilization of Amine-Containing CO₂ Adsorbents: Dramatic Effect of Water Vapor. *J. Am. Chem. Soc.* **2010**, *132* (18), 6312–6314.
- (39) Veneman, R.; Frigka, N.; Zhao, W. Y.; Li, Z. S.; Kersten, S.; Brilman, W. Adsorption of H₂O and CO₂ on supported amine sorbents. *Int. J. Greenh. Gas Control.* **2015**, *41*, 268–275.
- (40) Zhou, Z.; Balijepalli, S. K.; Nguyen-Sorenson, A. H. T.; Anderson, C. M.; Park, J. L.; Stowers, K. J. Steam-Stable Covalently Bonded Polyethylenimine Modified Multiwall Carbon Nanotubes for Carbon Dioxide Capture. *Energy Fuels* **2018**, *32* (11), 11701–11709.
- (41) Wang, X.; Song, C. Temperature-programmed desorption of CO₂ from polyethylenimine-loaded SBA-15 as molecular basket sorbents. *Catal. Today* **2012**, *194* (1), 44–52.
- (42) Uyanga, I. J.; Idem, R. O. Studies of SO₂- and O₂-Induced Degradation of Aqueous MEA during CO₂ Capture from Power Plant Flue Gas Streams. *Ind. Eng. Chem. Res.* **2007**, *46* (8), 2558–2566.
- (43) Xu, X.; Song, C.; Miller, B. G.; Scaroni, A. W. Adsorption separation of carbon dioxide from flue gas of natural gas-fired boiler by a novel nanoporous “molecular basket” adsorbent. *Fuel Process. Technol.* **2005**, *86* (14), 1457–1472.
- (44) Rezaei, F.; Jones, C. W. Stability of Supported Amine Adsorbents to SO₂ and NO_x in Postcombustion CO₂ Capture. 1. Single-Component Adsorption. *Ind. Eng. Chem. Res.* **2013**, *52* (34), 12192–12201.
- (45) Rezaei, F.; Jones, C. W. Stability of Supported Amine Adsorbents to SO₂ and NO_x in Postcombustion CO₂ Capture. 2. Multicomponent Adsorption. *Ind. Eng. Chem. Res.* **2014**, *53* (30), 12103–12110.
- (46) Ahmadalinezhad, A.; Sayari, A. Oxidative degradation of silica-supported polyethylenimine for CO₂ adsorption: insights into the nature of deactivated species. *Phys. Chem. Chem. Phys.* **2014**, *16* (4), 1529–1535.
- (47) Bali, S.; Chen, T. T.; Chaikittisilp, W.; Jones, C. W. Oxidative Stability of Amino Polymer-Alumina Hybrid Adsorbents for Carbon Dioxide Capture. *Energy Fuels* **2013**, *27* (3), 1547–1554.
- (48) Heydari-Gorji, A.; Belmabkhout, Y.; Sayari, A. Degradation of amine-supported CO₂ adsorbents in the presence of oxygen-containing gases. *Micropor. Mesopor. Mater.* **2011**, *145* (1–3), 146–149.
- (49) Heydari-Gorji, A.; Sayari, A. Thermal, Oxidative, and CO₂-Induced Degradation of Supported Polyethylenimine Adsorbents. *Ind. Eng. Chem. Res.* **2012**, *51* (19), 6887–6894.
- (50) Vu, Q. T.; Yamada, H.; Yogo, K. Oxidative Degradation of Tetraethylenepentamine-Impregnated Silica Sorbents for CO₂ Capture. *Energy Fuels* **2019**, *33* (4), 3370–3379.
- (51) Wang, M.; Yao, L.; Wang, J.; Zhang, Z.; Qiao, W.; Long, D.; Ling, L. Adsorption and regeneration study of polyethylenimine-impregnated millimeter-sized mesoporous carbon spheres for post-combustion CO₂ capture. *Appl. Ener.* **2016**, *168*, 282–290.

- (52) Bacsik, Z.; Hedin, N. Effects of carbon dioxide captured from ambient air on the infrared spectra of supported amines. *Vib. Spectrosc.* **2016**, *87*, 215–221.
- (53) Danon, A.; Stair, P. C.; Weitz, E. FTIR Study of CO₂ Adsorption on Amine-Grafted SBA-15: Elucidation of Adsorbed Species. *J. Phys. Chem. C* **2011**, *115* (23), 11540–11549.
- (54) Hedin, N.; Bacsik, Z. Perspectives on the adsorption of CO₂ on amine-modified silica studied by infrared spectroscopy. *Curr. Opin. Green Sustain.* **2019**, *16*, 13–19.
- (55) Pyo, S. W.; Maniangu, C.; Ko, Y. S. In-situ IR study on stability of amine-impregnated CO₂ adsorbents to acidic gases. *Catal. Today* **2020**, *352*, 198–203.
- (56) Chakravartula Srivatsa, S.; Bhattacharya, S. Amine-based CO₂ capture sorbents: A potential CO₂ hydrogenation catalyst. *J. CO₂ Util.* **2018**, *26*, 397–407.
- (57) Tanthana, J.; Chuang, S. S. C. In Situ Infrared Study of the Role of PEG in Stabilizing Silica-Supported Amines for CO₂ Capture. *ChemSusChem* **2010**, *3* (8), 957–964.
- (58) Tumuluri, U.; Isenberg, M.; Tan, C. S.; Chuang, S. S. C. In Situ Infrared Study of the Effect of Amine Density on the Nature of Adsorbed CO₂ on Amine-Functionalized Solid Sorbents. *Langmuir* **2014**, *30* (25), 7405–7413.
- (59) Wilfong, W. C.; Srikanth, C. S.; Chuang, S. S. C. In Situ ATR and DRIFTS Studies of the Nature of Adsorbed CO₂ on Tetraethylenepentamine Films. *ACS Appl. Mater. Interfaces* **2014**, *6* (16), 13617–13626.
- (60) Yu, J.; Chuang, S. S. C. The Structure of Adsorbed Species on Immobilized Amines in CO₂ Capture: An in Situ IR Study. *Energy Fuels* **2016**, *30* (9), 7579–7587.
- (61) Chen, C. H.; Sesti, E. L.; Lee, J. J.; Mentink-Vigier, F.; Sievers, C.; Jones, C. W.; Hayes, S. E. NMR Reveals Two Bicarbonate Environments in SBA15-Solid-Amine CO₂ Sorbents. *J. Phys. Chem. C* **2021**, *125* (30), 16759–16765.
- (62) Chen, C. H.; Shimon, D.; Lee, J. J.; Didas, S. A.; Mehta, A. K.; Sievers, C.; Jones, C. W.; Hayes, S. E. Spectroscopic Characterization of Adsorbed ¹³CO₂ on 3-Aminopropylsilyl-Modified SBA15 Mesoporous Silica. *Environ. Sci. Technol.* **2017**, *51* (11), 6553–6559.
- (63) Chen, C. H.; Shimon, D.; Lee, J. J.; Mentink-Vigier, F.; Hung, I.; Sievers, C.; Jones, C. W.; Hayes, S. E. The “Missing” Bicarbonate in CO₂ Chemisorption Reactions on Solid Amine Sorbents. *J. Am. Chem. Soc.* **2018**, *140* (28), 8648–8651.
- (64) Foo, G. S.; Lee, J. J.; Chen, C. H.; Hayes, S. E.; Sievers, C.; Jones, C. W. Elucidation of Surface Species through in Situ FTIR Spectroscopy of Carbon Dioxide Adsorption on Amine-Grafted SBA-15. *ChemSusChem* **2017**, *10* (1), 266–276.
- (65) Moore, J. K.; Sakwa-Novak, M. A.; Chaikittisilp, W.; Mehta, A. K.; Conradi, M. S.; Jones, C. W.; Hayes, S. E. Characterization of a Mixture of CO₂ Adsorption Products in Hyperbranched Aminosilica Adsorbents by ¹³C Solid-State NMR. *Environ. Sci. Technol.* **2015**, *49* (22), 13684–13691.
- (66) Park, S. J.; Lee, J. J.; Hoyt, C. B.; Kumar, D. R.; Jones, C. W. Silica supported poly(propylene guanidine) as a CO₂ sorbent in simulated flue gas and direct air capture. *Adsorption* **2020**, *26* (1), 89–101.
- (67) Mebane, D. S.; Kress, J. D.; Storlie, C. B.; Fauth, D. J.; Gray, M. L.; Li, K. J. Transport, Zwitterions, and the Role of Water for CO₂ Adsorption in Mesoporous Silica-Supported Amine Sorbents. *J. Phys. Chem. C* **2013**, *117* (50), 26617–26627.
- (68) Muller, K.; Lu, D. Y.; Senanayake, S. D.; Starr, D. E. Monoethanolamine Adsorption on TiO₂(110): Bonding, Structure, and Implications for Use as a Model Solid-Supported CO₂ Capture Material. *J. Phys. Chem. C* **2014**, *118* (3), 1576–1586.
- (69) Chen, Y.; Yuan, H. L.; Xia, H.; Jiang, W.; Yang, C.; Hu, G. S.; Lan, Y. Z.; Fan, M. H. The volume expansion effect of amine during CO₂ adsorption process: An experimental study combined with theoretical calculations. *J. Colloid Interface Sci.* **2020**, *572*, 190–197.
- (70) Lee, Z. R.; Quinn, L. D. J.; Jones, C. W.; Hayes, S. E.; Dixon, D. A. Predicting the Mechanism and Products of CO₂ Capture by Amines in the Presence of H₂O. *J. Phys. Chem. A* **2021**, *125* (45), 9802–9818.
- (71) Chen, C.-H.; Sesti, E. L.; Lee, J. J.; Mentink-Vigier, F.; Sievers, C.; Jones, C. W.; Hayes, S. E. NMR Reveals Two Bicarbonate Environments in SBA15-Solid-Amine CO₂ Sorbents. *J. Phys. Chem. C* **2021**, *125* (30), 16759–16765.
- (72) Wijesiri, R. P.; Knowles, G. P.; Yeasmin, H.; Hoadley, A. F. A.; Chaffee, A. L. Desorption Process for Capturing CO₂ from Air with Supported Amine Sorbent. *Ind. Eng. Chem. Res.* **2019**, *58* (34), 15606–15618.
- (73) Wurzbacher, J. A.; Gebald, C.; Brunner, S.; Steinfeld, A. Heat and mass transfer of temperature-vacuum swing desorption for CO₂ capture from air. *Chem. Eng. J.* **2016**, *283*, 1329–1338.
- (74) Krishnamurthy, S.; Boon, J.; Grande, C.; Lind, A.; Blom, R.; Boer, R.; Willemssen, H.; Scheemaker, G. Screening Supported Amine Sorbents in the Context of Post-combustion Carbon Capture by Vacuum Swing Adsorption. *Chem. Ing. Technol.* **2021**, *93* (6), 929–940.
- (75) Gebald, C.; Wurzbacher, J. A.; Tingaut, P.; Steinfeld, A. Stability of Amine-Functionalized Cellulose during Temperature-Vacuum-Swing Cycling for CO₂ Capture from Air. *Environ. Sci. Technol.* **2013**, *47* (17), 10063–10070.
- (76) Fang, M. X.; Xiang, Q. Y.; Wang, T.; Le Moullec, Y.; Lu, J. H.; Jiang, W. M.; Zhou, X. P.; Zhang, J. B.; Chen, G. F. Experimental Study on the Novel Direct Steam Stripping Process for Postcombustion CO₂ Capture. *Ind. Eng. Chem. Res.* **2014**, *53* (46), 18054–18062.
- (77) Fujiki, J.; Chowdhury, F. A.; Yamada, H.; Yogo, K. Highly efficient post-combustion CO₂ capture by low-temperature steam-aided vacuum swing adsorption using a novel polyamine-based solid sorbent. *Chem. Eng. J.* **2017**, *307*, 273–282.
- (78) Li, W.; Choi, S.; Drese, J. H.; Hornbostel, M.; Krishnan, G.; Eisenberger, P. M.; Jones, C. W. Steam-Stripping for Regeneration of Supported Amine-Based CO₂ Adsorbents. *ChemSusChem* **2010**, *3* (8), 899–903.
- (79) Plaza, M. G.; Rubiera, F.; Pevida, C. Evaluating the Feasibility of a TSA Process Based on Steam Stripping in Combination with Structured Carbon Adsorbents To Capture CO₂ from a Coal Power Plant. *Energy Fuels* **2017**, *31* (9), 9760–9775.
- (80) Sakwa-Novak, M. A.; Jones, C. W. Steam Induced Structural Changes of a Poly(ethylenimine) Impregnated gamma-Alumina Sorbent for CO₂ Extraction from Ambient Air. *ACS Appl. Mater. Interfaces* **2014**, *6* (12), 9245–9255.
- (81) Sandhu, N. K.; Pudasainee, D.; Sarkar, P.; Gupta, R. Steam Regeneration of Polyethylenimine-Impregnated Silica Sorbent for Postcombustion CO₂ Capture: A Multicyclic Study. *Ind. Eng. Chem. Res.* **2016**, *55* (7), 2210–2220.
- (82) Xiang, Q. Y.; Le Moullec, Y.; Fang, M. X.; Valle-Marcos, J. C.; Lu, J. H.; Jiang, W. M.; Zhou, X. P.; Chen, G. F.; Luo, Z. Y. In *Novel Solvent Regeneration Process through Direct Steam Stripping*, 12th International Conference on Greenhouse Gas Control Technologies (GHGT), Austin, TX, Oct 05–09, 2014; pp 1392–1398.
- (83) Chaikittisilp, W.; Kim, H. J.; Jones, C. W. Mesoporous Alumina-Supported Amines as Potential Steam-Stable Adsorbents for Capturing CO₂ from Simulated Flue Gas and Ambient Air. *Energy Fuels* **2011**, *25* (11), 5528–5537.
- (84) Fayaz, M.; Sayari, A. Long-Term Effect of Steam Exposure on CO₂ Capture Performance of Amine-Grafted Silica. *ACS Appl. Mater. Interfaces* **2017**, *9* (50), 43747–43754.
- (85) Jahandar Lashaki, M.; Ziaei-Azad, H.; Sayari, A. Insights into the Hydrothermal Stability of Triamine-Functionalized SBA-15 Silica for CO₂ Adsorption. *ChemSusChem* **2017**, *10* (20), 4037–4045.
- (86) Yu, Q.; Brilman, D. W. F. Design strategy for CO₂ adsorption from ambient air using a supported amine based sorbent in a fixed bed reactor. In *13th International Conference on Greenhouse Gas Control Technologies, Ghgt-13*; Dixon, T., Laloui, L., Twining, S., Eds.; 2017; Vol. 114, pp 6102–6114.

- (87) Esmaeili Rad, F.; Abbasian, J.; Arastoopour, H. Numerical simulation of CO₂ adsorption in a fluidized bed using solid-supported amine sorbent. *Can. J. Chem. Eng.* **2021**, 99 (7), 1595–1606.
- (88) Jung, W. H.; Lee, J. Economic evaluation for four different solid sorbent processes with heat integration for energy-efficient CO₂ capture based on PEI-silica sorbent. *Energy* **2022**, 238, 121864.
- (89) Zhao, W. Y.; Veneman, R.; Chen, D. G.; Li, Z. S.; Cai, N. S.; Brilmana, D. W. F. Post-Combustion CO₂ Capture Demonstration Using Supported Amine Sorbents: Design and Evaluation of 200 kW(th) Pilot. In *12th International Conference on Greenhouse Gas Control Technologies, Ghgt-12*; Dixon, T., Herzog, H., Twining, S., Eds.; 2014; Vol. 63, pp 2374–2383.
- (90) Zanco, S. E.; Pérez-Calvo, J.-F.; Gasós, A.; Cordiano, B.; Becattini, V.; Mazzotti, M. Postcombustion CO₂ Capture: A Comparative Techno-Economic Assessment of Three Technologies Using a Solvent, an Adsorbent, and a Membrane. *ACS Engineering Au* **2021**, 1 (1), 50–72.
- (91) Susarla, N.; Haghpanah, R.; Karimi, I. A.; Farooq, S.; Rajendran, A.; Tan, L. S. C.; Lim, J. S. T. Energy and cost estimates for capturing CO₂ from a dry flue gas using pressure/vacuum swing adsorption. *Chem. Eng. Res. Des.* **2015**, 102, 354–367.
- (92) Lyndon, R.; Konstas, K.; Ladewig, B. P.; Southon, P. D.; Kepert, P. C. J.; Hill, M. R. Dynamic Photo-Switching in Metal–Organic Frameworks as a Route to Low-Energy Carbon Dioxide Capture and Release. *Angew. Chem., Int. Ed.* **2013**, 52 (13), 3695–3698.
- (93) Jiang, Y.; Tan, P.; Qi, S.-C.; Liu, X.-Q.; Yan, J.-H.; Fan, F.; Sun, L.-B. Metal–Organic Frameworks with Target-Specific Active Sites Switched by Photoresponsive Motifs: Efficient Adsorbents for Tailorable CO₂ Capture. *Angew. Chem., Int. Ed.* **2019**, 58 (20), 6600–6604.
- (94) Wu, Q.-R.; Tan, P.; Gu, C.; Zhou, R.; Qi, S.-C.; Liu, X.-Q.; Jiang, Y.; Sun, L.-B. Smart adsorbents for CO₂ capture: Making strong adsorption sites respond to visible light. *Sci. China Mater.* **2021**, 64 (2), 383–392.