

# Structures and Magnetic Ordering in Layered Cr Oxide Arsenides $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ and $\text{Sr}_2\text{CrO}_3\text{CrAs}$

Bradley C. Sheath, Xiaoyu Xu, Pascal Manuel, Joke Hadermann, Maria Batuk, John O'Sullivan, Ruy S. Bonilla, and Simon J. Clarke\*



Cite This: *Inorg. Chem.* 2022, 61, 12373–12385



Read Online


ACCESS |

Metrics & More

Article Recommendations

Supporting Information

**ABSTRACT:** Two novel chromium oxide arsenide materials have been synthesized,  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  (i.e.,  $\text{Sr}_2\text{Cr}_3\text{As}_2\text{O}_3$ ) and  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  (i.e.,  $\text{Sr}_2\text{Cr}_2\text{AsO}_3$ ), both of which contain chromium ions in two distinct layers.  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  was targeted following electron microscopy measurements on a related phase. It crystallizes in the space group  $P4/mmm$  and accommodates distorted  $\text{CrO}_4\text{As}_2$  octahedra containing  $\text{Cr}^{2+}$  and distorted  $\text{CrO}_2\text{As}_4$  octahedra containing  $\text{Cr}^{3+}$ . In contrast,  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  incorporates  $\text{Cr}^{3+}$  in  $\text{CrO}_5$  square-pyramidal coordination in  $[\text{Sr}_2\text{CrO}_3]^+$  layers and  $\text{Cr}^{2+}$  ions in  $\text{CrAs}_4$  tetrahedra in  $[\text{CrAs}]^-$  layers and crystallizes in the space group  $P4/mmm$ . Powder neutron diffraction data reveal antiferromagnetic ordering in both compounds. In  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  the  $\text{Cr}^{2+}$  moments in the  $[\text{CrAs}]^-$  layers exhibit long-range ordering, while the  $\text{Cr}^{3+}$  moments in the  $[\text{Sr}_2\text{CrO}_3]^+$  layers only exhibit short-range ordering. However, in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ , both the  $\text{Cr}^{2+}$  moments in the  $\text{CrO}_4\text{As}_2$  environments and the  $\text{Cr}^{3+}$  moments in the  $\text{CrO}_2\text{As}_4$  polyhedra are long-range-ordered below 530(10) K. Above this temperature, only the  $\text{Cr}^{3+}$  moments are ordered with a Néel temperature slightly in excess of 600 K. A subtle structural change is evident in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  below the magnetic ordering transitions.

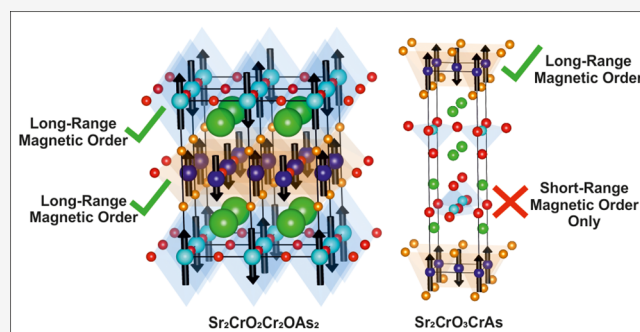


## INTRODUCTION


With increasing numbers of investigations into crystalline materials containing more than one anion over the last few decades, new phases are being discovered, and along with them come unexplored structures and properties. Research into these mixed-anion solids has been driven in recent years by the search for compounds that are high-temperature superconductors,<sup>1,2</sup> thermoelectrics,<sup>3</sup> fast-ion conductors,<sup>4</sup> and transparent conductors.<sup>5</sup> Another feature of interest is the nature of any long-range magnetic order present. In mixed-anion compounds such as the oxide arsenides described here and a related series of oxide chalcogenides,<sup>6–10</sup> the tendency of the different anions to segregate into different layers, due to their different sizes and electronegativities, can lead to the formation of multiple transition metal sublattices within the same structure. If these transition metals, situated in different coordination environments, are magnetic ions, then there is the prospect of novel and complex long-range magnetic order. A plethora of oxypnictide and oxychalcogenide compositions that contain very similar types of layers to the two title compounds have been investigated over the last decade, including  $\text{Ba}_2\text{Ti}_2\text{OAs}_2\text{Cr}_2\text{As}_2$ <sup>11</sup> with  $\text{TiO}_2\text{As}_4$  octahedra and  $\text{CrAs}_4$  tetrahedra,  $\text{BaTi}_2\text{OAs}_2$ <sup>12</sup> with  $\text{TiO}_2\text{As}_4$  octahedra, and  $\text{Sr}_2\text{CrO}_3\text{FeAs}$ <sup>13</sup> with  $\text{CrO}_5$  square-based pyramids.

We previously reported<sup>14</sup> that the compounds  $\text{Ae}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  ( $\text{Ae} = \text{Sr}, \text{Ba}$ ) adopt a structure containing alternating  $[\text{Ae}_2\text{CrO}_2]^{2+}$  layers (with  $\text{CrO}_2$  square sheets and the  $\text{Cr}^{2+}$  ions in distended  $\text{CrO}_4\text{As}_2$  octahedra) and anti-PbO  $[\text{Cr}_2\text{As}_2]^{2-}$  layers (with edge-sharing  $\text{CrAs}_4$  tetrahedra) as depicted in Figure 1 (left).  $\text{Cr}^{2+}$  stabilized under the relatively reducing reaction conditions is present on both Cr sublattices. The formula for this and the related compounds reported in this work are written so as to emphasize these different structural slabs. The compound  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  is an example of one with complex magnetic order. As described by Liu et al.<sup>15</sup> and by us (Xu et al.<sup>14</sup>), long-range antiferromagnetic order of the moments on the Cr ions on the  $[\text{Cr}_2\text{As}_2]^{2-}$  layer occurs below 590 K, and just below room temperature, the moments on the Cr ions on the oxide layer also start to order antiferromagnetically. The ordering of the oxide layer precipitates a reorientation of the moments in the arsenide layers even though the two Cr sublattices order with different

Received: May 23, 2022

Published: July 27, 2022



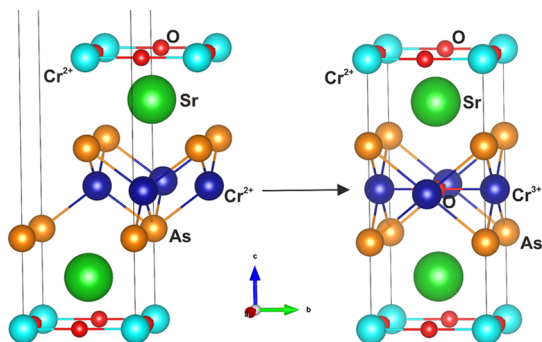

**Figure 1.** Crystal structures of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  (left)<sup>14,15,21</sup> and  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  (right). The structure of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  may formally be derived from oxidation of the  $[\text{Cr}_2\text{As}_2]^{2-}$  layers in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  and relative shifts of the  $[\text{Sr}_2\text{CrO}_2]^{2+}$  slabs.

propagation vectors. We concluded from the analysis of high-resolution neutron powder diffraction data that the magnetic structure was slightly incommensurate with the nuclear structure, which presumably enables communication between the two magnetic sublattices. Spin reorientations in related phases have been reported by Lawrence et al.<sup>16</sup> and by Xu.<sup>17</sup> We reported<sup>14</sup> that high-resolution transmission electron microscopy (TEM) measurements performed on  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  revealed the presence of stacking faults, which were presumed to arise from the oxidation of some  $[\text{Cr}_2\text{As}_2]^{2-}$  layers containing  $\text{Cr}^{2+}$  to  $[\text{Cr}_2\text{OAs}_2]^{2-}$  layers containing  $\text{Cr}^{3+}$ . This led us to target the title phase  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ , which is the fully oxidized analogue of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  where all  $[\text{Cr}_2\text{As}_2]^{2-}$  layers have been oxidized, accompanied by a relative shift of  $(\frac{1}{2} \frac{1}{2} 0)$  in the  $ab$  plane of neighboring  $[\text{Sr}_2\text{CrO}_2]^{2+}$  blocks as shown in Figure 1. The structure of this target phase, shown in Figure 1 (right), is analogous to that reported for the cation-defective  $\text{Ca}_2\text{Fe}_{2.6}\text{S}_2\text{O}_3$ ,<sup>18</sup> and the  $[\text{Cr}_2\text{OAs}_2]^{2-}$  blocks are the exact anti-type of the  $[\text{Sr}_2\text{CrO}_2]^{2+}$  (i.e.,  $[\text{O}_2\text{CrSr}_2]^{2+}$ ) blocks. Similar blocks  $M_2\text{OQ}_2$  ( $M$  = transition metal,  $Q$  = chalcogen or pnictogen) are known.<sup>19,20</sup>  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  with the  $\text{Sr}_2\text{GaO}_2\text{CuS}$  structure was also discovered as a minor phase in the original  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  sample,<sup>14</sup> and here, we report the crystal structure and magnetism of this material in the bulk form. Thicker oxide slabs are present in this compound compared to  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ , and the  $\text{Cr}^{3+}$  ions in the oxide layer are now in a square-pyramidal coordination of oxide anions rather than distorted  $\text{CrO}_4\text{As}_2$  octahedra.

## EXPERIMENTAL SECTION

**Synthesis.** One gram samples of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  and  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  were synthesized from  $\text{SrO}$ ,  $\text{Cr}_2\text{O}_3$  (Alfa Aesar, 99.6%),  $\text{Cr}$  (Alfa Aesar, 99.95%), and  $\text{As}$  (Alfa Aesar, 99%) in the ratios of 6:0.85:7.3:6 and 6:1:4:3, respectively. The mixture for  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  targeted a stoichiometry of  $\text{Sr}_2\text{Cr}_3\text{O}_{2.85}\text{As}_2$ , and the 5% oxygen deficiency was employed as it increased the phase purity of the sample as proposed by Jiang et al.<sup>21</sup> in their synthesis of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ .  $\text{SrO}$  had been previously prepared via thermal decomposition of  $\text{SrCO}_3$  (Alfa Aesar, 99.994%) by heating it at 830 °C for 16 h and then at 1100 °C for 4 h, all under dynamic vacuum.  $\text{Cr}_2\text{O}_3$  was also pre-dried in a furnace before use. The reagents were thoroughly ground together using an agate pestle and mortar until the mixtures appeared homogeneous. The powders were then pressed into pellets and sealed inside evacuated silica tubes. The  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  mixture was heated at 800 °C for 2 h (1 °C  $\text{min}^{-1}$  ramping rate) then at 1200 °C for 8 h (10 °C  $\text{min}^{-1}$  ramping rate) and then at 1200 °C for 2 h (10 °C  $\text{min}^{-1}$  ramping rate), with grinding and re-pelletizing between the two 1200 °C heating steps and quenching in ice water from both 1200 °C heating steps. The 800 °C heating step with slow ramping rate was used to ensure that the As reacted before reaching a high vapor pressure. The  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  target was quenched in ice water after having been heated at 1200 °C for 24 h (10 °C  $\text{min}^{-1}$  ramping rate).

**Diffraction.** An in-house Bruker D8 Advance Eco diffractometer (using  $\text{Cu K}\alpha$  radiation) was used to gather X-ray powder diffraction (XRPD) data in order to follow the reactions between heating steps. Data for detailed structural analysis were collected on beamline I11<sup>22</sup> at the Diamond Light Source using 30 min scans with 0.82 Å X-rays (calibrated precisely using a Si standard at the start of each beam time session) with the high-resolution multi-analyzer crystal (MAC) detector. A position-sensitive detector (PSD) was also used on beamline I11 to gather full diffraction patterns at 190 temperatures while cooling from 600 to 300 K in approximately 1 h. Neutron powder diffraction (NPD) was carried out on the WISH instrument<sup>23</sup> at the ISIS Facility, where approximately 0.8 g of each material was loaded into vanadium cans, and data were obtained at various temperatures between 7 and 543 K using a cryofurnace to cool down and warm up the samples. The XRPD and NPD data were analyzed by Rietveld refinement using the TOPAS Academic V5 software.<sup>24</sup>

**Transmission Electron Microscopy.** Electron diffraction (ED) patterns at room temperature and 100 K were acquired on a Philips CM20 transmission electron microscope operated at 200 kV. High-angle annular dark field (HAADF) and annular bright field (ABF) scanning transmission electron microscopy (STEM) images were acquired at room temperature using a FEI Titan 80-300 “cubed” microscope operated at 300 kV. Specimens for the TEM study were prepared by grinding the material under ethanol and depositing a few drops of the suspension onto a copper grid covered by a holey carbon layer. The specimens were prepared in air.

**Magnetometry.** A Quantum Design MPMS-3 SQUID magnetometer was employed to gather magnetometry data for the  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  sample, and a Quantum Design MPMS-XL SQUID magnetometer was used for the  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  sample. For measurements below 300 K, around 30 mg (accurately weighed) of sample was loaded into a gelatin capsule. This capsule was then secured in a plastic straw, and the straw was placed inside the instrument. Zero-field-cooled (ZFC) and field-cooled (FC) measurements were carried out in a field of 100 Oe. To take account of minuscule amounts of ferromagnetic impurities in the sample, data were also gathered as a function of temperature at 3 and 4 T in the region where the magnetization varied linearly with field, and the susceptibility of the sample was determined by subtraction. For measurements above 300 K, around 30 mg of sample was pressed in a pellet die to form a bar of material. Alumina cement was used to attach the sample to a heater stick on the MPMS-3 magnetometer, and copper foil was wrapped around the material to reduce radiative heat loss. Measurement of magnetization as a function of temperature (with a field of 100 Oe applied) gave the equivalent of a ZFC curve as the sample was warmed from 300 to 800 K, and a FC curve as the sample was then cooled back down from 800 to 300 K.


**High-Temperature Resistance.** Sintered  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  pellets were electrically characterized using the four-point probe technique as follows. Four aluminum contacts with thickness of 500 nm, length of 4 mm, and width of 1.5 mm were thermally evaporated on the sample surface spaced by 1.33 mm each. A current bias from  $-1$  mA to  $+1$  mA was applied across the outer two contacts, while the voltage was measured across the inner two contacts. Signal generation and measurement was carried out using a Keithley 2401 Source measuring unit controlled via a virtual instrument programmed in LabVIEW. Each current–voltage characteristic was acquired with 60 data points, and the mean resistance calculated from 5 current–voltage measurements. Current–voltage measurements were taken while the sample rested on an aluminum stage where the temperature was controlled via a PID controller from 300 to 770 K using a thermocouple in direct contact with the stage, next to the specimen. Measurements were acquired in temperature intervals of 20 K, and

the thermocouple reading was used to ensure the temperature of the stage was stable before data acquisition.

## RESULTS AND DISCUSSION

**Compositions and Crystal Structures.**  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ , a target identified from the nature of the stacking faults in some regions of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  samples,<sup>14</sup> was difficult to obtain with high purity. The purest sample reported here contains CrAs,  $\text{Sr}_2\text{CrO}_3\text{CrAs}$ , and As side phases, which proved difficult to avoid. Numerous attempts using a range of starting materials and heating profiles were attempted. Ultimately, the target phase was made with a fairly high purity (87% of the total mass) by heating to a very high temperature of 1200 °C (the limit for a single-walled silica ampoule), including a 5% oxygen deficiency in the reagent stoichiometry, and quenching in ice water. Even though an oxygen deficiency was used in the starting mixture, there was no evidence in the refinements of the room-temperature XRPD (Figure 4) and NPD (Figure S1) data that the final phase was oxygen-deficient. It is plausible that additional O arises due to reaction with the silica tubes; however, the impurities present are also consistent with a stoichiometric target phase given the slight off-stoichiometry of the reaction mixture.  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  crystallizes in the  $P4/mmm$  space group and is isostructural with the  $\text{Ca}_2\text{Fe}_{3-\delta}\text{O}_3(\text{S}_{1-x}\text{Se}_x)_2$  phases first reported by Zhang et al.<sup>18</sup> (structure shown in Figure 6). The alternating  $[\text{Sr}_2\text{CrO}_2]^{2+}$  and  $[\text{Cr}_2\text{OAs}_2]^{2-}$  slabs host distorted *trans*- $\text{CrO}_4\text{As}_2$  and *trans*- $\text{CrO}_2\text{As}_4$  octahedra, respectively. The  $\text{CrO}_4\text{As}_2$  octahedra are distended along the Cr–As bonds and are oxide-vertex sharing, whereas the  $\text{CrO}_2\text{As}_4$  octahedra are compressed along the Cr–O bonds and share  $\text{As}_2\text{O}$  faces.


$\text{Sr}_2\text{CrO}_3\text{CrAs}$ , which was identified as a minority phase in samples of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  by electron microscopy (Figures 2

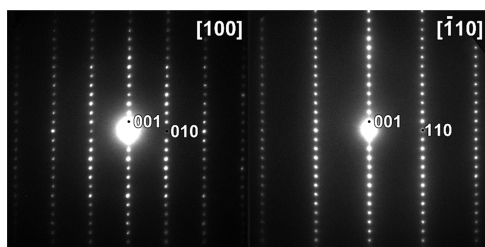

**Figure 2.** ED patterns taken from [100] and [110] zones of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  identified in a bulk sample of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ . The measurements were made at 100 K.

and 3), was synthesized successfully with only very minor amounts of unidentifiable side phases, as shown by the XRPD (Figures 4 and 5) and NPD (Figure S2) data at 300 K. It adopts the  $\text{Sr}_2\text{GaO}_3\text{CuS}$  structure type (Figure 7) with the  $P4/mmm$  space group.  $\text{Cr}^{2+}$  exists in the anti-PbO-type  $[\text{CrAs}]^-$  layers (tetrahedrally coordinated by As), whereas  $\text{Cr}^{3+}$  is present in the  $[\text{Sr}_2\text{CrO}_3]^+$  blocks (in a  $\text{CrO}_5$  square-pyramidal coordination). Low-temperature electron diffraction measurements of this phase did not reveal any structural changes down to 100 K (Figure 2).

**Structure Refinement.** The values in Table 1 and Figures 6 and 7 (refined from synchrotron XRPD data and WISH NPD data, respectively) detail the lattice parameters, atomic positions, and a selection of bond lengths and angles corresponding to both the  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  and  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  phases. A comparison between values refined from XRPD and

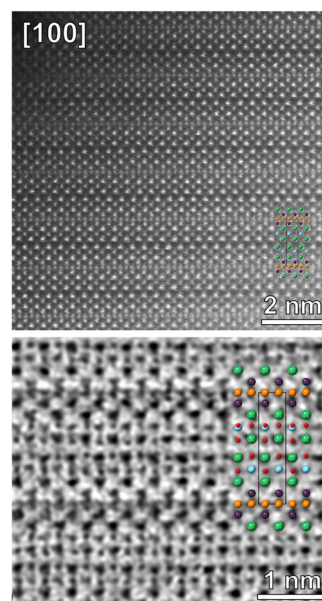


**Figure 3.** (Top) HAADF-STEM image of a well-ordered  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  structure identified in a bulk sample of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ ; (bottom) enlarged fragment of the ADF-STEM image with a  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  structure overlay. Atoms are Cr1: pale blue; Cr2: dark blue; Sr: green; As: orange; O: red. Unit cell is outlined with a black rectangle.


NPD measurements are given in the Supporting Information (Tables S1 and S2). Each site occupancy factor was allowed to freely refine in the early stages of the refinement, but there was no significant deviation from the ideal value of 1 by any atom, so these values were then fixed.

**Crystal Structures.**  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  is one of a wide variety of compositions that are known to adopt the  $\text{Sr}_2\text{GaO}_3\text{CuS}$ <sup>25</sup> structure. These include materials such as  $\text{Sr}_2\text{MnO}_3\text{CuS}$ ,<sup>26</sup>  $\text{Sr}_2\text{CrO}_3\text{CuS}$ ,<sup>27</sup> and  $\text{Ca}_2\text{FeO}_3\text{CuCh}$  ( $Ch = \text{S}, \text{Se}$ ).<sup>28</sup> Furthermore, in terms of the individual alternating blocks, the anti-PbO-type chromium arsenide layers found in this compound are well documented in the literature. For example, Park et al.<sup>29</sup> report on the nuclear and magnetic structures of  $\text{LaCrAsO}$ , containing alternating  $[\text{LaO}]^+$  and  $[\text{CrAs}]^-$  blocks where the chromium ions are in the +2 oxidation state. The Cr–As length refined from XRPD is given as 2.494(1) Å, and this is comparable to the value of 2.4927(5) Å found here for  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  (Table S2). This suggests that these chromium arsenide layers in  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  host the same  $\text{Cr}^{2+}$  species and that the oxide layer sitting between the  $[\text{CrAs}]^-$  layers has little effect on the nature of the Cr–As bonding. The  $\text{CrO}_5$  square-pyramidal environment in the  $[\text{Sr}_2\text{CrO}_3]^+$  block of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  is less common, but it is known in  $\text{Sr}_2\text{CrO}_3\text{CuSe}$ <sup>17</sup> where the axial Cr–O bond (aligned along the  $c$  axis) and basal Cr–O bonds (aligned roughly within the  $ab$  plane) have lengths of 1.999(15) and 1.9830(14) Å, respectively. There is significant deviation from this in the  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  compound, where the corresponding Cr–O distances are 1.868(5) and 1.9760(5) Å. This shows that the chromium oxide layer is not particularly rigid as the  $\text{CrO}_5$  square-pyramids are susceptible to significant changes in shape. However, the bond valence sums (calculated using the Cr–O bond lengths refined from XRPD data and using reference bond length data provided by Brown and Altermatt<sup>30</sup>) predict chromium oxidation states of +2.46(6) ( $\text{Sr}_2\text{CrO}_3\text{CuSe}$ ) and



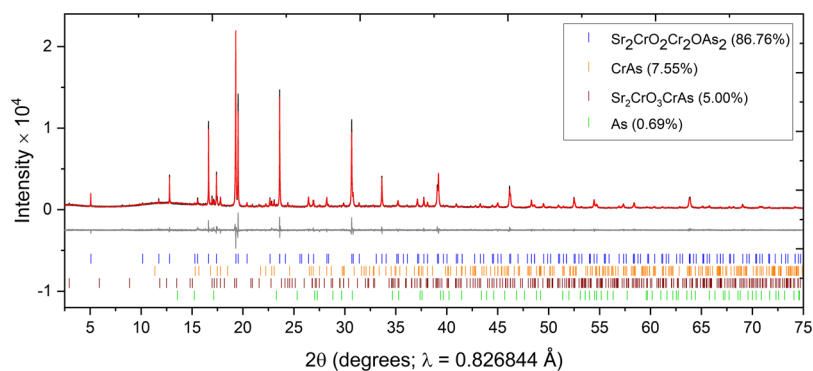

**Figure 4.** XRPD pattern of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  measured at 300 K on the MAC detector at I11 showing the observed (black), calculated (red), and difference (gray) curves.  $R_{\text{wp}}$ : 7.679%.

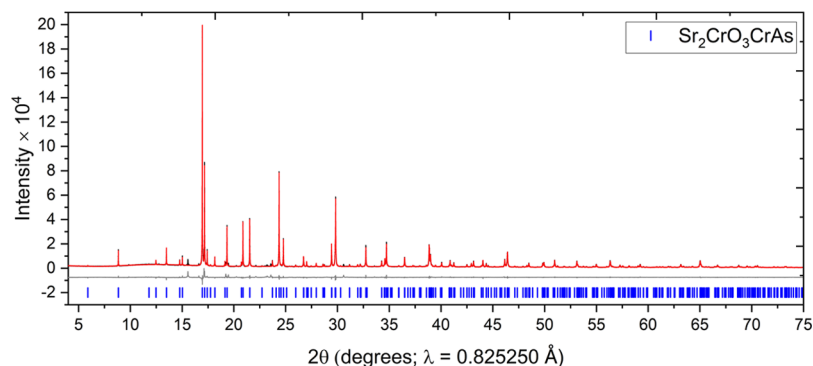


**Figure 5.** XRPD pattern of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  measured at 300 K on the MAC detector at I11 showing the observed (black), calculated (red), and difference (gray) curves.  $R_{\text{wp}}$ : 7.915%.


**Table 1.** Refinement Results from XRPD Patterns Collected at 300 K Using the MAC Detector at I11

		$\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$				$\text{Sr}_2\text{CrO}_3\text{CrAs}$			
diffractometer		I11 (MAC)				I11 (MAC)			
wavelength (Å)		0.826844				0.825250			
temperature (K)		300				300			
space group		$P4/mmm$				$P4/mmm$			
$a$ (Å)		4.040319(16)				3.909877(13)			
$c$ (Å)		9.33140(7)				16.05417(7)			
$V$ (Å <sup>3</sup> )		152.327(2)				245.422(2)			
		$\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$				$\text{Sr}_2\text{CrO}_3\text{CrAs}$			
atom	site	$x$	$y$	$z$	occupancy	$U_{11}$ (Å <sup>2</sup> )	$U_{22}$ (Å <sup>2</sup> )	$U_{33}$ (Å <sup>2</sup> )	
Sr	2h	0.5	0.5	0.17664(8) <sup>b</sup>	1	0.0024(2)	= $U_{11}$	0.0114(6)	
Cr1	1a	0	0	0	1	0.0000(4)	= $U_{11}$	0.0171(9)	
Cr2	2e	0.5	0	0.5	1	0.0002(3)	= $U_{11}$	0.0134(6)	
O1	2f	0.5	0	0	1	0.0063(8) <sup>a</sup>	= $U_{11}$	= $U_{11}$	
O2	1d	0.5	0.5	0.5	1	0.0063(8) <sup>a</sup>	= $U_{11}$	= $U_{11}$	
As	2g	0	0	0.32192(8)	1	0.0000(3)	= $U_{11}$	0.0125(7)	
		$\text{Sr}_2\text{CrO}_3\text{CrAs}$				$\text{Sr}_2\text{CrO}_3\text{CrAs}$			
atom	site	$x$	$y$	$z$	occupancy	$U_{11}$ (Å <sup>2</sup> )	$U_{22}$ (Å <sup>2</sup> )	$U_{33}$ (Å <sup>2</sup> )	
Sr1	2c	0.75	0.75	0.19950(5)	1	0.0053(4)	= $U_{11}$	0.0089(6)	
Sr2	2c	0.75	0.75	0.41633(5)	1	0.0063(4)	= $U_{11}$	0.0093(6)	
Cr1	2c	0.25	0.25	0.31312(8)	1	0.0039(5)	= $U_{11}$	0.0074(9)	
Cr2	2a	0.25	0.75	0	1	0.0081(5)	= $U_{11}$	0.0100(8)	
O1	4f	0.25	0.75	0.29518(19)	1	0.0130(10)	= $U_{11}$	= $U_{11}$	
O2	2c	0.25	0.25	0.4295(3)	1	0.0101(13)	= $U_{11}$	= $U_{11}$	
As	2c	0.25	0.25	0.09633(5)	1	0.0075(4)	= $U_{11}$	0.0077(6)	

<sup>a</sup>These oxygen displacement parameters were fixed at the same value, and they were refined isotropically. <sup>b</sup>The estimated standard deviations on the refined parameters produced in a Rietveld refinement give an indication of the data quality and may underestimate the true experimental uncertainty in a refined value.

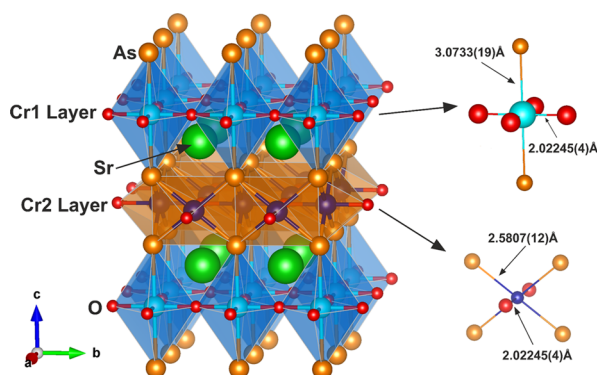

**Figure 6.** Structure of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ . The  $\text{CrO}_4\text{As}_2$  and  $\text{CrO}_2\text{As}_4$  distorted octahedra are shown by the blue and orange polyhedra, respectively. Ellipsoids with 99% displacement (right) are given using isotropic displacement parameters refined from room-temperature WISH NPD data (detailed in Table S1). Atoms are Cr1: pale blue; Cr2: dark blue; Sr: green; As: orange; O: red.

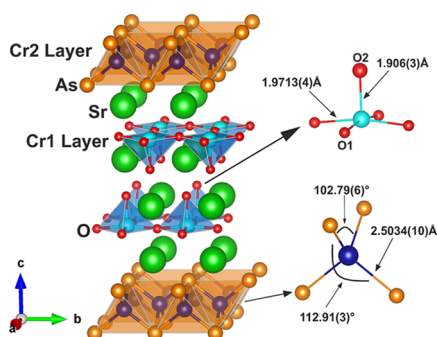


**Figure 7.** Structure of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$ . The  $\text{CrO}_5$  square-pyramids and  $\text{CrAs}_4$  tetrahedra are shown by the blue and orange polyhedra, respectively. Ellipsoids with 99% displacement (right) are given using isotropic displacement parameters refined from room-temperature WISH NPD data (detailed in Table S2). Atoms are Cr1: pale blue; Cr2: dark blue; Sr: green; As: orange; O: red.


+2.70(2) ( $\text{Sr}_2\text{CrO}_3\text{CrAs}$ ); therefore, it is highly probable that these two systems contain similar chromium species in the  $\text{CrO}_5$  environments.

$\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  adopts the lesser-explored structure type formally derived by oxygen insertion (Figure 1) from that of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ , the well-known structure of which was first reported for  $A_2\text{MnO}_2\text{Mn}_2\text{B}_2$  ( $A = \text{Sr}, \text{Ba}$ ;  $B = \text{As}, \text{Sb}, \text{Bi}$ ) by Brechtel et al.<sup>31</sup> Comparisons can be made by again focusing on each type of layer in the structure. We previously reported that the Cr–O distance within the  $\text{CrO}_2$  square-planar sheets of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  refined to a value of 2.00400(1) Å<sup>14</sup> (equal to half the basal lattice parameter), and in the case of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ , we find a similar value of 2.0202(1) Å for this Cr1–O distance. The formal oxidation of the  $\text{Cr}_2\text{As}_2$  layer to  $\text{Cr}_2\text{OAs}_2$  therefore seems to leave these  $\text{CrO}_2$  sheets unaffected, as would be expected due to the largely unchanged Cr1 environment.  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  is the first reported example of  $\text{Cr}_2\text{OAs}_2$  layers; however, some iron oxy-chalcogenides have been discovered with analogous  $\text{Fe}_2\text{OCh}_2$  ( $\text{Ch} = \text{S}, \text{Se}$ ) environments, such as  $A_2\text{F}_2\text{Fe}_2\text{OQ}_2$  ( $A = \text{Sr}, \text{Ba}$ ;  $Q = \text{S}, \text{Se}$ )<sup>32</sup> and  $\text{La}_2\text{O}_2\text{Fe}_2\text{OCh}_2$  ( $\text{Ch} = \text{S}, \text{Se}$ ).<sup>33–35</sup> Further examples where layers of this type host alternative 3d transition metals include the  $\text{Mn}_2\text{OSe}_2$  environments in  $A_2\text{O}_2\text{Mn}_2\text{OSe}_2$  ( $A = \text{La}, \text{Ce}, \text{Pr}$ ),<sup>19,36</sup> the  $\text{Co}_2\text{OSe}_2$  environments in  $\text{La}_2\text{O}_2\text{Co}_2\text{OSe}_2$ ,<sup>19,37</sup> and the  $\text{Ti}_2\text{OAs}_2$  environments in  $\text{Ba}_2\text{Ti}_2\text{OAs}_2\text{Cr}_2\text{As}_2$ ,<sup>11</sup>  $\text{BaTi}_2\text{OAs}_2$ ,<sup>12</sup> and  $\text{Ba}_2\text{Ti}_2\text{OAs}_2\text{Fe}_2\text{As}_2$ .<sup>20</sup>

**Magnetic Ordering in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ .** NPD data collected on the  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  sample at 10 K (Figure 8 and Figure S8) show a series of reflections where the intensities and  $d$ -spacings cannot be accounted for from scattering due to the nuclear model alone. These additional peaks only occur at long  $d$ -spacings, which is indicative of a magnetic origin. These peaks decrease in intensity as the sample is warmed (Figure 9) and can be explained by scattering from arrays of long-range ordered magnetic moments. The reflections labeled by black triangles in Figure 8 are positioned on top of nuclear peaks and are therefore accounted for by the  $k = (0\ 0\ 0)$  propagation vector. In contrast, the  $k$ -vector of the peaks denoted by a black square is  $k = (\frac{1}{2}\ \frac{1}{2}\ 0)$ , and these imply that the cell of the magnetic structure is a  $2a_{\text{nuc}} \times 2a_{\text{nuc}} \times c_{\text{nuc}}$  expansion of the nuclear unit cell and that the two Cr sublattices order independently with different propagation vectors. A number of much less intense magnetic Bragg reflections are highlighted by asterisks in Figure 8 and disappear on warming between 200 and 300 K.

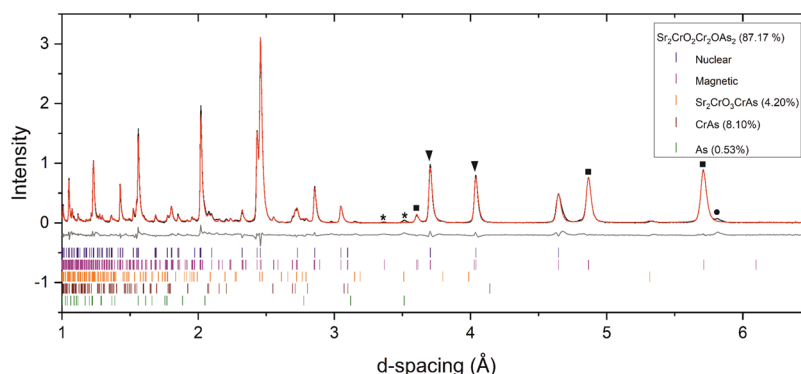


**Figure 8.** NPD pattern of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  (combination of banks 3 and 8 with average  $2\theta = 90^\circ$ ) measured at 10 K on the WISH instrument at ISIS showing the observed (black), calculated (red), and difference (gray) curves. The black triangles and black squares denote reflections with  $k = (0\ 0\ 0)$  and  $k = (\frac{1}{2}\ \frac{1}{2}\ 0)$ , respectively. The asterisks give examples of peaks that disappear before 300 K and are due to magnetic order in CrAs. The black circle highlights an unidentified impurity peak, which is presumably nuclear (not magnetic) in origin as it does not change intensity with varying temperature.  $R_{\text{wp}}: 5.751\%$ .

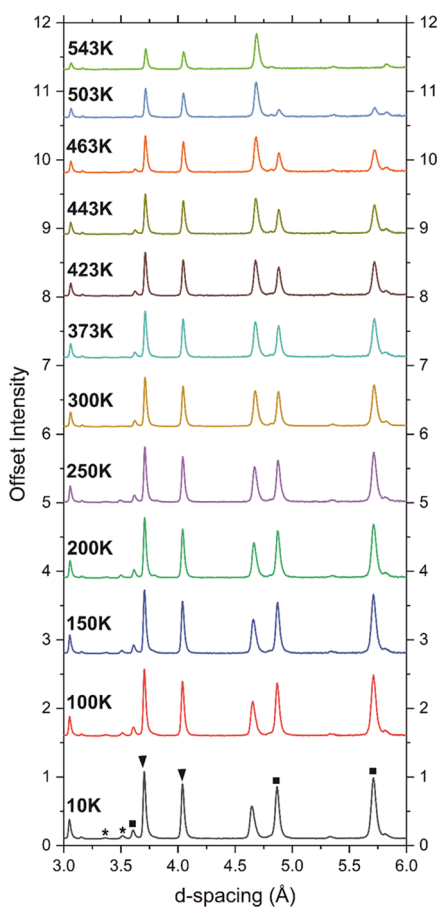

**Figure 9.** NPD patterns of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  (combination of banks 3 and 8 with average  $2\theta = 90^\circ$ ) at different temperatures measured on the WISH instrument at ISIS showing the evolution of the magnetic peaks. Magnetic Bragg peaks labeled with black squares disappear between 503 and 543 K, whereas those labeled with black triangles are still present at 543 K. Those highlighted by asterisks can be explained as the magnetic Bragg peaks of CrAs ( $T_N \approx 300$  K).

These can be attributed to the magnetic structure of the CrAs side phase evident in the XRPD pattern, which has a Néel temperature of approximately 300 K. The magnetic ordering transitions of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  are not detected in the high-temperature magnetometry data (Figures S3 and S4).

The ISODISTORT package<sup>38</sup> was used to deduce the magnetic modes available to this system, and then Rietveld refinement was carried out to assess the suitability of each mode to fit the NPD data. These modes are symmetry-adapted linear combinations of the Cr magnetic moments, which enable refinement of the magnetic structure with symmetry imposed. The most suitable model was one that describes the Cr1 layer moments using a single mode ( $mM3 + A2(a,0)$ ) and the Cr2 layer moments using a single mode ( $mF4 + B1(a,0)$ ) (these modes are depicted in Figure 10). The resulting model has all the Cr moments aligned along the  $c$  axis in antiferromagnetic arrangements, which is consistent with the absence of any intensity on reflections indexed perpendicular to the  $c$  axis (i.e., (001) reflections). Nearest neighbors in the Cr1 sublattice ( $\text{CrO}_2$  layers) are coupled antiferromagnetically, as is expected for  $\sigma$ - and  $\pi$ -type superexchange interactions between high spin  $d^4$ - $d^4$  ions in co-aligned distended octahedral coordination mediated by the  $2p$  orbitals of the  $\text{O}^{2-}$  anion. Reference 14 discusses the degree of distortion of

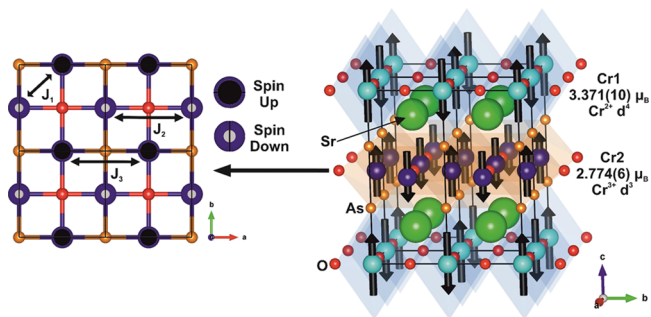

**Figure 10.** Model for the magnetic order on the Cr1 oxide-rich sublattice and Cr2 arsenide-rich sublattice of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  at 10 K. The major magnetic interactions in the Cr2 layer as considered for materials with analogous layers (examples including Ni et al.<sup>36</sup> Kabbour et al.<sup>32</sup> Free et al.<sup>19</sup> and Wang et al.<sup>40</sup>) are labeled  $J_1$  (Cr–Cr direct exchange),  $J_2$  ( $180^\circ$  Cr–O–Cr superexchange) and  $J_3$  ( $\sim 100^\circ$  Cr–As–Cr superexchange).


the  $\text{CrO}_4\text{As}_2$  octahedra in relation to the expected Jahn–Teller distortion for a  $\text{Cr}^{2+} d^4$  ion.

The model for the Cr2 sublattice ( $\text{Cr}_2\text{OAs}_2$  layers) in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  also has antiferromagnetic coupling of nearest neighbor  $\text{Cr}^{3+}$  moments. The main competing magnetic interactions are highlighted by Figure 10 (as previously described by Ni et al.<sup>36</sup>): the direct exchange between nearest neighbor  $\text{Cr}^{3+}$  centers ( $J_1$ ), the  $180^\circ$  superexchange mediated by  $\text{O}^{2-}$  ( $J_2$ ), and the approximately  $100^\circ$  superexchange mediated by  $\text{As}^{3-}$  ( $J_3$ ). It seems that this system is dominated by the direct exchange interaction ( $J_1$ ) between the  $d_{xz}$  and  $d_{yz}$  orbitals of neighboring Cr centers, which is antiferromagnetic in nature. This interaction acts between all the  $\text{Cr}^{3+}$  ions that are nearest neighbors, forming a checkerboard pattern of  $\text{Cr}^{3+}$  spins aligned along the  $c$  axis and alternating in their relative directions. The model suggests that this direct exchange is the strongest coupling mechanism, exceeding the strength of the superexchange interactions. The linear superexchange ( $J_2$ ) involving empty  $d_z^2$  orbitals is predicted to be an antiferromagnetic interaction by application of the Goodenough–Kanamori rules; however, here, the moments are ferromagnetically aligned along that pathway. The other superexchange interaction ( $J_3$ ) involving empty  $d_{xy}$  orbitals is predicted to be antiferromagnetic in nature, but again, here, moments connected by this interaction are aligned to be ferromagnetic. Stock and McCabe<sup>7</sup> summarize a number of long-range magnetic ordering schemes reported for layered materials comprising  $M_2\text{OSe}_2$  ( $M$  = transition metal) blocks. One observation of interest is that the magnetic structure for the Cr2 sublattice in the  $\text{Cr}_2\text{OAs}_2$  layers of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  is similar to that described for  $\text{La}_2\text{O}_2\text{Mn}_2\text{OSe}_2$ ,<sup>19,36</sup> containing  $\text{Mn}_2\text{OSe}_2$  layers similar to the  $\text{Cr}_2\text{OAs}_2$  layers considered here, where the  $d^5$  moments for  $\text{Mn}^{2+}$  ions are also directed perpendicular to the layers and order in a similar checkerboard manner. The magnetic structure of  $\text{La}_2\text{O}_2\text{Mn}_2\text{OSe}_2$  was also proposed to be a consequence of the antiferromagnetic nearest neighbor direct exchange interactions being dominant and frustrating the  $J_2$  and  $J_3$  superexchange interactions, resulting in ferromagnetic alignment of the moments along the perpendicular –Mn–O–Mn–O–Mn– chains.

The significantly larger refined long-range ordered moment per Cr ion in the Cr1 layer of  $3.371(10) \mu_B$  compared to the  $2.774(6) \mu_B$  per Cr in the Cr2 layer are consistent with the assignment of these as  $\text{Cr}^{2+} d^4$  and  $\text{Cr}^{3+} d^3$  cations respectively,

with the ordered moments reduced below the maximum expected spin-only values of 4 and 3  $\mu_B$  respectively by covalency. The Cr1 ( $\text{Cr}^{2+}$ ) moment is similar in direction and magnitude to the  $\text{Cr}^{2+}$  moment in the analogous layers in both  $\text{Ba}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  and  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ ,<sup>14,15</sup> where the  $\text{CrO}_2$  layers are also antiferromagnetic, therefore also supporting the assignment of the Cr1 oxidation state as  $\text{Cr}^{2+}$ . Furthermore, bond valence sums (calculated using bond length data provided by Brese and O'Keefe<sup>39</sup> and where the literature Cr–As bond length used was that for  $\text{Cr}^{\text{II}}$ –As in both cases as a known  $\text{Cr}^{\text{III}}$ –As bond length was not found) corroborate with this assignment as these give Cr1 an oxidation state of +2.090(2) and Cr2 an oxidation state of +2.980(8). The observed antiferromagnetism, the bond valence sums, and the sizes of the ordered moments are consistent with a lack of mixed valency on the Cr1 and Cr2 sites.


Figure 11 displays the refined value of the Cr moment in each layer in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  as the temperature is increased.

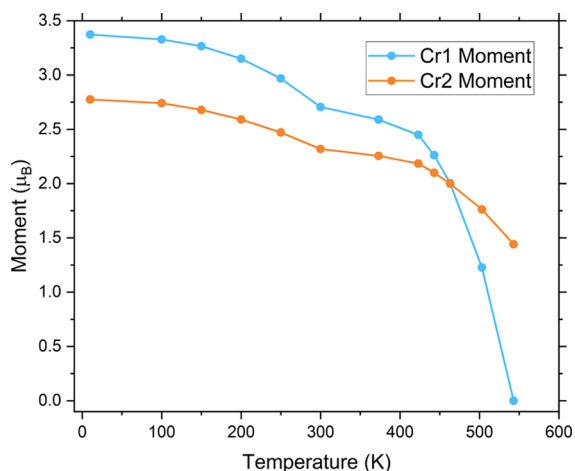

**Figure 11.** Value of the Cr1 and Cr2 moments (per Cr ion) in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  refined from NPD data collected at different temperatures on the WISH instrument at ISIS. The ESD obtained from the refinement on each value of the moment is smaller than the width of the corresponding data point. The apparent dip in the value of the moments at 300 K is due to the change in sample environment and poor temperature calibration close to room temperature for the high temperature sample environment.

Upon warming the sample, it is the Cr1 ( $\text{Cr}^{2+}$ ) moments that lose long-range order first and have the lower  $T_N$  of 530(10) K, with the  $T_N$  of the Cr2 ( $\text{Cr}^{3+}$ ) moments predicted to be approximately 600 K based on the evolution of the moment with temperature. The long-range ordering of the  $\text{Cr}^{3+}$  Cr2 moments in the  $\text{Cr}_2\text{OAs}_2$  layers occurs at a similar temperature to the  $\text{Cr}^{2+}$  moments in the  $[\text{Cr}_2\text{As}_2]^{2-}$  layers of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ <sup>14</sup> and with a similar magnitude of the long-range ordered moment. This is consistent with a stronger reduction of the ordered  $\text{Cr}^{2+}$  moment in the  $[\text{Cr}_2\text{As}_2]^{2-}$  layers in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  due to covalency, with evidence for some delocalization of electrons in that compound suggested by the fact that the compound is metallic.<sup>21</sup>

Whangbo et al.<sup>41</sup> describe a method by which the spin direction in a magnetically ordered system can be related to the ligand field of the magnetic ion (Figure 12) using spin-orbit coupling arguments. In the  $\text{CrO}_4\text{As}_2$  distorted octahedra (Cr1), the change in the magnetic quantum number between

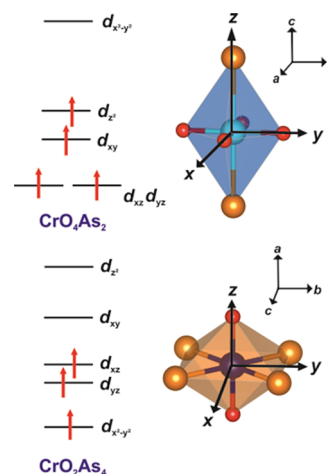


**Figure 12.** Ligand field splitting schemes for the  $\text{CrO}_4\text{As}_2$  and  $\text{CrO}_2\text{As}_4$  distorted octahedra. The  $x$ ,  $y$ , and  $z$  axes shown, which apply to these local coordinations, correspond to the  $a$ ,  $b$ , and  $c$  crystallographic axes respectively for the  $\text{CrO}_4\text{As}_2$  case and the  $c$ ,  $b$ , and  $a$  crystallographic axes respectively for the  $\text{CrO}_2\text{As}_4$  case. The ligand field splitting for the  $\text{CrO}_2\text{As}_4$  case is as described for analogous  $\text{CoO}_2\text{Se}_4$  octahedra in  $\text{La}_2\text{O}_2\text{Co}_2\text{OSe}_2$  by Wu *et al.*<sup>42</sup>


the HOMO and LUMO is given by  $|\Delta L_z| = 0$ , predicting that the moments order parallel to the principal axis (along the crystallographic  $c$ -direction, perpendicular to the layers). As for the  $\text{CrO}_2\text{As}_4$  environments (Cr2), this change in the magnetic quantum number between the HOMO and LUMO is given by  $|\Delta L_z| = 1$ , therefore predicting that the moments order perpendicular to the principal axis, which is defined in Figure 12 as parallel to the Cr2–O bonds, and thus, the moments are permitted to lie parallel to the crystallographic  $c$  axis and thus perpendicular to the layers as observed. It is reported that  $\text{La}_2\text{O}_2\text{Fe}_2\text{OSe}_2$ <sup>34</sup> and  $\text{La}_2\text{O}_2\text{Co}_2\text{OSe}_2$ <sup>19,37</sup> have transition metal moments oriented in the  $ab$  plane, whereas  $\text{La}_2\text{O}_2\text{Mn}_2\text{OSe}_2$ <sup>19,36</sup> contains moments directed along the  $c$  axis. The  $\text{FeO}_2\text{Se}_4$  and  $\text{CoO}_2\text{Se}_4$  coordination environments have  $|\Delta L_z| = 1$  and  $|\Delta L_z| = 0$ , respectively. Therefore, the Fe compound is predicted to contain moments perpendicular to  $z$  and the Co compound moments parallel to  $z$  (where  $z$  is parallel to the O–M–O direction of the  $\text{MO}_2\text{Se}_4$  octahedron as defined in Figure 12). This agrees with the models determined by experiment because moments perpendicular and parallel to  $z$  can both lie in the crystallographic  $ab$  plane. The  $\text{Mn}^{2+} d^5$  ion is predicted to have little spin direction preference. Overall, the transition metal moments in these  $M_2\text{OQ}_2$  ( $M$  = transition metal;  $Q$  = chalcogen or pnictogen) layers lie perpendicular to the crystallographic  $ab$  plane for  $\text{Cr}^{3+}$  ( $d^3$ ) and  $\text{Mn}^{2+}$  ( $d^5$ ) and lie within the  $ab$  plane for  $\text{Fe}^{2+}$  ( $d^6$ ) and  $\text{Co}^{2+}$  ( $d^7$ ).

**Magnetic Ordering in  $\text{Sr}_2\text{CrO}_3\text{CrAs}$ .** Variable-temperature NPD studies were also performed for  $\text{Sr}_2\text{CrO}_3\text{CrAs}$ . Reflections due to long range antiferromagnetic ordering are again observed, and these decrease in intensity until 478 K (Figure 13), at which temperature there are no longer any additional peaks than those arising from the nuclear model. Refinement of the  $m\Gamma_2^-$  ( $a,0$ ) mode, with  $k = (0\ 0\ 0)$ , gives the best-fitting model, and this consists of antiferromagnetically ordered  $\text{Cr}^{2+}$  moments in the  $[\text{CrAs}]^-$  layer aligned along the  $c$ -direction as depicted in Figure 14. In the 7 K refinement (Figure 15 and Figure S9), the long-range-ordered moment per  $\text{Cr}^{2+}$  ion is 2.12(3)  $\mu_B$ , which is lower than the predicted value of 4  $\mu_B$  for a  $d^4$  ion due to significant covalency in the



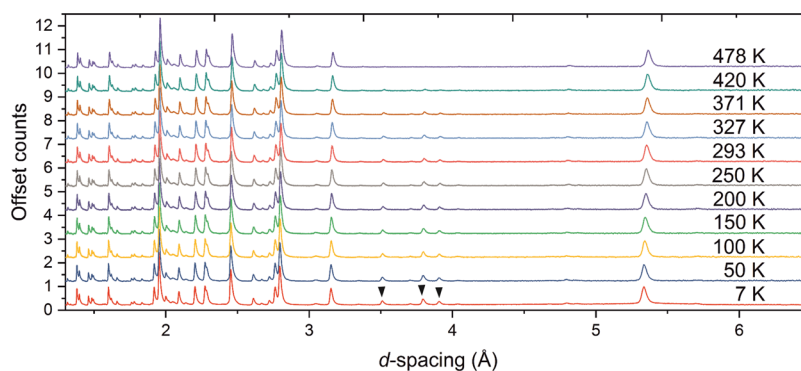

**Figure 13.** NPD patterns of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  (combination of banks 3 and 8 with average  $2\theta = 90^\circ$ ) at different temperatures measured on the WISH instrument at ISIS showing the evolution of the magnetic peaks. Magnetic Bragg peaks of the main phase are denoted by the black triangles.

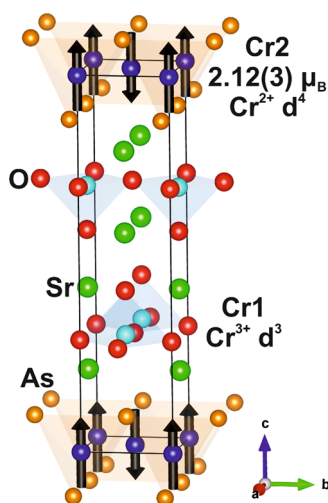


**Figure 14.** Model for the magnetic order in  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  at 7 K. The magnetic unit cell shown has the same  $a_{\text{nuc}} \times a_{\text{nuc}} \times c_{\text{nuc}}$  dimensions as the nuclear unit cell.

Cr–As bonds. It is comparable to the saturation value of  $2.298(8) \mu_{\text{B}}$  per Cr in the similar  $[\text{Cr}_2\text{As}_2]^{2-}$  layers of  $\text{Ba}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ .<sup>14</sup>

In the high  $d$ -spacing region of the NPD data, some very small peaks can be indexed as the magnetic reflections of a


$\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  impurity phase (Figure 16). Although this phase is not detected in the XRPD data, its presence is found due to the presence of these magnetic peaks at high  $d$ -spacing where reflections are generally fewer in number and more dispersed in  $d$ -spacing. The nuclear reflections of this impurity phase overlap with those of the main phase and are difficult to observe due to their relatively low intensities.

The orientation of the  $\text{Cr}^{2+}$  moments in the  $[\text{CrAs}]^-$  layer along the  $c$ -direction is replicated by magnetic ions in a number of related systems containing anti-PbO-type transition metal arsenide layers. Examples include the  $\text{Mn}^{2+}$  moments in  $\text{LaMnAsO}$ ,<sup>43</sup>  $\text{BaMn}_2\text{As}_2$ ,<sup>44</sup> and  $\text{Sr}_2\text{MnO}_2\text{Mn}_2\text{As}_2$ <sup>45</sup> and the  $\text{Cr}^{2+}$  moments in  $\text{LaCrAsO}$ ,<sup>29</sup>  $\text{BaCr}_2\text{As}_2$ ,<sup>46</sup> and  $\text{Ba}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ .<sup>14</sup> Other materials adopting the  $\text{Sr}_2\text{GaO}_3\text{CuS}$  structure type, such as  $\text{Sr}_2\text{CrO}_3\text{FeAs}$ <sup>47</sup> and  $\text{Sr}_2\text{CrO}_3\text{CuSe}$ ,<sup>17</sup> exhibit long-range antiferromagnetic ordering of the nearest-neighbor  $\text{Cr}^{3+}$  moments in the oxide layer. However, unlike these examples, the  $\text{Cr}^{3+}$  cations in the oxide layer of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  do not contribute to sharp magnetic Bragg peaks, and so the nature of the magnetic ordering must differ here. Instead, diffuse scattering can be seen around  $5.33 \text{ \AA}$   $d$ -spacing below 40 K—a position comparable to the main magnetic reflections observed for  $\text{Sr}_2\text{CrO}_3\text{FeAs}$ <sup>47</sup> (see Figure 17 and Figure S7). This could explain the broad signal observed in the magnetometry data (Figure S5). It may be the case that there exists some short-range order of the  $\text{Cr}^{3+}$

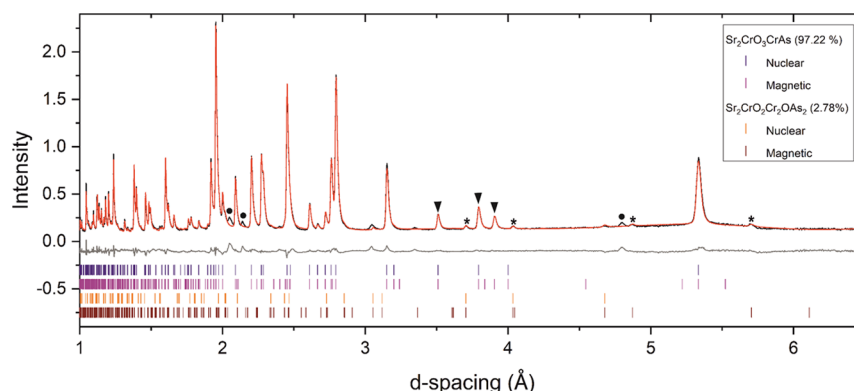


**Figure 15.** NPD pattern of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  (combination of banks 3 and 8 with average  $2\theta = 90^\circ$ ) measured at 7 K on the WISH instrument at ISIS showing the observed (black), calculated (red), and difference (gray) curves. The reflections labeled with a black triangle correspond to magnetic Bragg peaks arising from antiferromagnetic order in the arsenide layer. The asterisks denote magnetic peaks arising from the  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  impurity phase. The black circles highlight unidentified impurity peaks, which are presumably nuclear (not magnetic) in origin as their intensities do not change with varying temperature.  $R_{\text{wp}}$ : 4.620%.



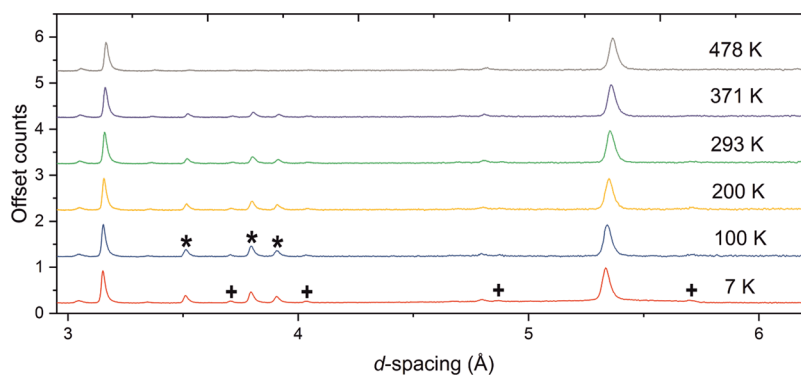

**Figure 16.** NPD patterns of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  (combination of banks 3 and 8 with average  $2\theta = 90^\circ$ ) at different temperatures measured on the WISH instrument at ISIS showing the magnetic Bragg peaks of the main phase  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  (\*) and the  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  side phase (+).

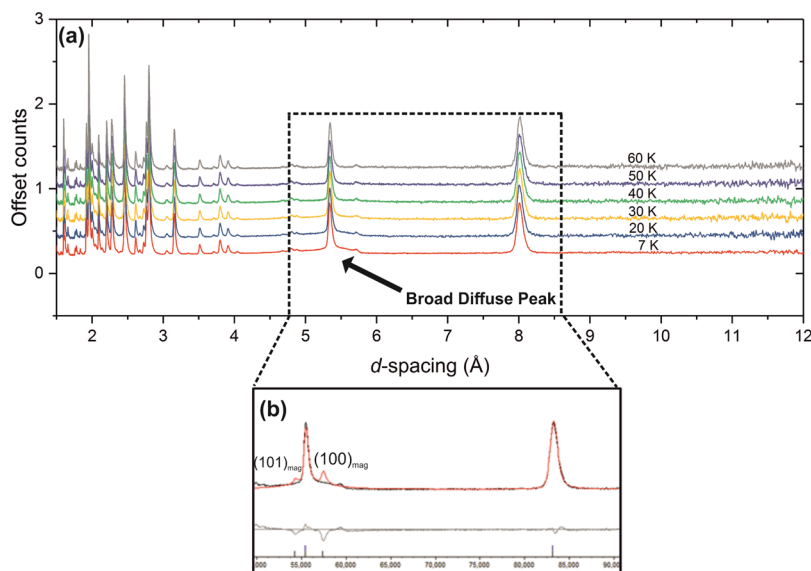


**Figure 17.** (a) NPD patterns of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  (combination of banks 3 and 8 with average  $2\theta = 90^\circ$ ) at low temperatures measured on the WISH instrument at ISIS and (b) simulated magnetic peaks (red) of  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  when the oxide layer contains moments aligned in a similar manner to  $\text{Sr}_2\text{CrO}_3\text{FeAs}$ ,<sup>47</sup> showing that the broad diffuse peak may arise due to short-range order of the  $\text{Cr}^{3+}$  oxide layer moments in the  $ab$  plane.

moments in the oxide layer, where the moments are antiferromagnetically aligned in the  $ab$  plane.

**Structural Distortion in  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$ .** Upon initial analysis of the variable-temperature synchrotron XRPD data for  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  it was noticeable that the lattice parameters did not decrease in a linear fashion as the sample was cooled from 600 to 300 K. Instead, below 400 K, the rate by which the lattice parameters diminish increases for lattice parameter  $a$  but decreases for lattice parameter  $c$  perpendicular to the layers (Figure 18a). However, the decrease in unit cell volume adopts a linear trend (Figure 18b). We note that this deviation is extremely subtle and only readily evident because the data were collected with high resolution in temperature. The possibility that this is an experimental artifact was considered; however, the agreement factors for the sequential refinements do not show any anomalies. This observation prompted further investigation into changes in bond lengths and bond valence sums (BVS). The trends shown by these values in the region from 500 K down to 400 K differ from the trends exhibited in the 600–500 and 400–300 K regions. As the temperature is decreased, the Cr1 octahedra ( $\text{CrO}_4\text{As}_2$ ) become marginally less distorted (Figure 18e) and the Cr2 octahedra ( $\text{CrO}_2\text{As}_4$ ) become marginally more distorted


(Figure 18g). In tandem with this structural change to the Cr polyhedra, the BVS value for Cr1 increases faster on cooling compared with the behavior in the 600–500 and 400–300 K regions, and the BVS for Cr2 becomes flat between these regions (Figure 18h). A plausible explanation could be that the  $\text{Cr}^{3+}$  ions in the Cr2 layers are being reduced by the  $\text{Cr}^{2+}$  in the Cr1 layers to a very small degree (of the order of  $0.02 e^-$  according to the trends in the BVS). The high temperature magnetometry data in Figure 18i supports the idea that the driving force behind this structural change is likely to be electronic in origin as it shows a transition in the magnetic susceptibility of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  between 500 and 400 K (i.e., exactly in the region of the structural change), which cannot be a signature of the magnetic ordering of the Cr2 and Cr1 layers as these have higher Néel temperatures of  $\sim 600$  and  $530(10)$  K, respectively, i.e., the subtle structural change occurs below the temperature of magnetic long range ordering on both sublattices and is so small that we would not expect to observe any modulation of the ordered moments. We cannot completely rule out that the transition in the magnetometry is due to an impurity (although the small  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  impurity observed does not have transitions in this range), but this would not account for the structural observation. The

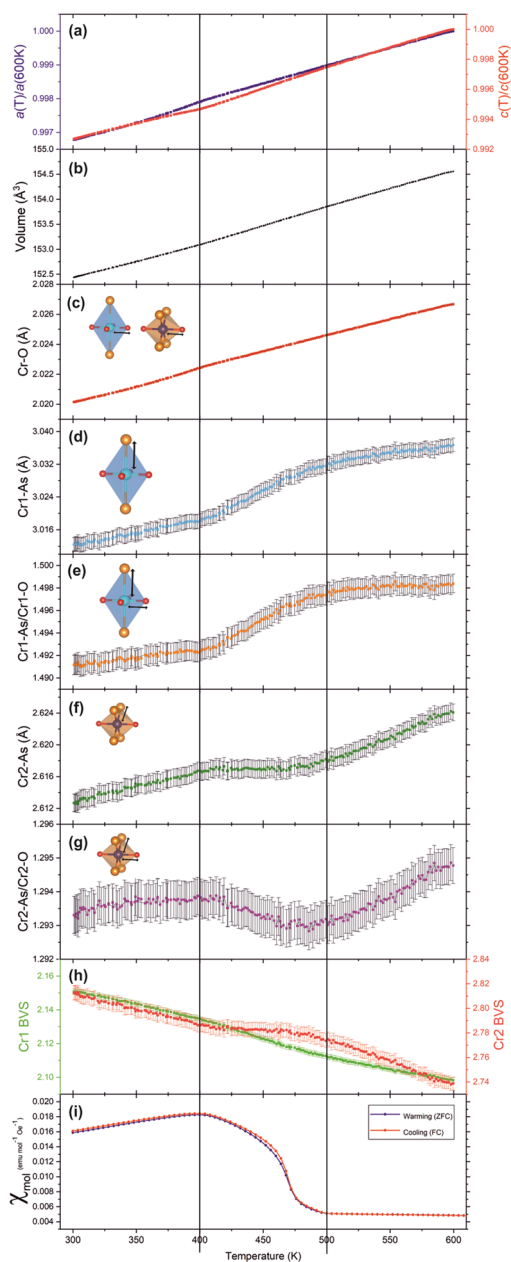

**Figure 18.** Refinement results of the variable-temperature XRPD data of  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  showing changes in (a) lattice parameters  $a$  and  $c$  normalized against their value at 600 K, (b) unit cell volume, (c) Cr–O distances (identical for Cr1–O and Cr2–O), (d) Cr1–As distance, (e) Cr1–As/Cr1–O bond length ratio, (f) Cr2–As distance, (g) Cr2–As/Cr2–O bond length ratio, and (h) Cr1 and Cr2 bond valence sum (BVS) (calculated using bond length data provided by Brese and O’Keefe<sup>39</sup> and where the literature Cr–As bond length used was that for  $\text{Cr}^{\text{II}}\text{–As}$  in both cases as a known  $\text{Cr}^{\text{III}}\text{–As}$  bond length was not found). High-temperature zero-field-cooled (ZFC) and field-cooled (FC) curves, measured in a field of 100 Oe, are given in (i).

nature of the structural distortion at each of the Cr sites is illustrated in Figure 19. Whether this structural change is due to a magnetostriction developing at the temperature where the ordered moments on the two independent Cr sublattices are both becoming saturated should also be considered.

High-temperature resistance experiments were attempted in this temperature range specifically to qualitatively test whether there was any observable electronic anomaly. The data suggest

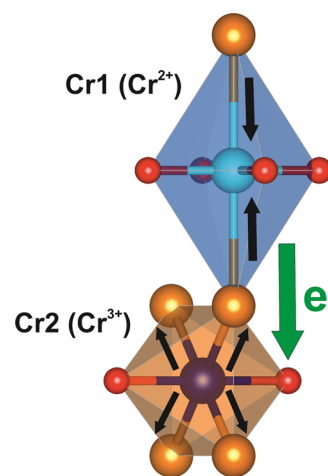

**Figure 19.** Schematic showing the small structural changes within the Cr polyhedra (as depicted by the black arrows) observed between 500 and 400 K as  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  is cooled. The changes in bond length (see Figure 18) are extremely small, and a possible driver for this transition would be a minuscule amount of electron transfer indicated by the green arrow (approx.  $0.02 e^-$ ).

metallic behavior for this compound, due to the low resistance values and increase of resistance with increasing temperature, but did not show any transition in the 400–500 K region (Figure S6). The most likely explanations for the lack of an obvious transition are the relatively low sensitivity of the experimental setup and the extremely subtle nature of the structural change observed in the material. It is possible that the impurities in the sample also affected these measurements. We propose that further measurements of the structure, magnetism, and transport properties on single-crystal samples, perhaps backed up by computation to suggest whether the proposed internal redox process is plausible, would be required to shed further light on this subtle structural change.

## CONCLUSIONS

Two new phases,  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  and  $\text{Sr}_2\text{CrO}_3\text{CrAs}$ , have been synthesized in the bulk form after initially being highlighted or suggested by electron microscopy examination of the related  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  compound.  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  crystallizes in the  $P4/mmm$  space group and comprises two unique Cr sublattices—one containing  $\text{Cr}^{2+}$  in a  $\text{CrO}_4\text{As}_2$  environment and the other  $\text{Cr}^{3+}$  in  $\text{CrO}_2\text{As}_4$  coordination.  $\text{Sr}_2\text{CrO}_3\text{CrAs}$  also has Cr in two distinct layers, and in this case,  $\text{CrO}_5$  square-pyramids host  $\text{Cr}^{3+}$  cations and  $\text{Cr}^{2+}$  is in a  $\text{CrAs}_4$  tetrahedral coordination. This material adopts a structure with space group  $P4/nmm$ . The challenge that arises due to the competition between the formation of these two materials and  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ —which only differ fairly slightly in their compositions (empirical formulae are  $\text{Sr}_2\text{Cr}_3\text{As}_2\text{O}_3$ ,  $\text{Sr}_2\text{Cr}_3\text{As}_2\text{O}_2$ , and  $\text{Sr}_2\text{Cr}_2\text{AsO}_3$ )—has been overcome through the use of synthetic optimization, and this has allowed sufficiently high levels of phase purity to be achieved for structural and magnetic analysis.

$\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{OAs}_2$  exhibits long-range magnetic ordering on both Cr sublattices. The  $\text{Cr}^{2+}$   $\text{CrO}_4\text{As}_2$  moments align parallel to the  $c$  axis via antiferromagnetic Cr–O–Cr  $180^\circ$  superexchange interactions, whereas the  $\text{Cr}^{3+}$   $\text{CrO}_2\text{As}_4$  moments are best described as forming a checkerboard arrangement of antiferromagnetically coupled nearest-neighbor Cr centers,

again with the moments directed along the *c*-direction. These observations can be rationalized by considering the various exchange interactions present and the preferential orientation of the moments with respect to the ligand field of the Cr centers. A Néel temperature of 530(10) K is evident for the three-dimensional long-range magnetic ordering on the Cr1 sublattice (CrO<sub>2</sub> planes). This is significantly higher than the three-dimensional long-range ordering temperature for the Cr<sup>2+</sup> moments in the similar layers in Sr<sub>2</sub>CrO<sub>2</sub>Cr<sub>2</sub>As<sub>2</sub> and Ba<sub>2</sub>CrO<sub>2</sub>Cr<sub>2</sub>As<sub>2</sub>,<sup>14,15</sup> presumably because in Sr<sub>2</sub>CrO<sub>2</sub>Cr<sub>2</sub>OAs<sub>2</sub>, adjacent layers of Cr1 moments are able to couple while in Sr<sub>2</sub>CrO<sub>2</sub>Cr<sub>2</sub>As<sub>2</sub> and Ba<sub>2</sub>CrO<sub>2</sub>Cr<sub>2</sub>As<sub>2</sub>—where adjacent layers are related by body centering—there is no net coupling between adjacent layers. The long-range-ordered moment on the Cr2 sublattice dissipates at around 600 K. There is no clear feature in the magnetometry measurements of these antiferromagnetic ordering transitions, as is quite commonly the case for strongly two-dimensional systems.<sup>48,49</sup> An electronic transition could be the driving force behind the very subtle structural distortions observed for the two Cr polyhedra between 500 and 400 K, accompanied by an anomaly in the magnetic susceptibility, but this subtle feature requires further investigation using single crystals.

In contrast, while NPD data show that the Cr<sup>2+</sup> moments in the arsenide layers of Sr<sub>2</sub>CrO<sub>3</sub>CrAs are antiferromagnetically ordered over a long length scale with a saturated moment of 2.12(3) μ<sub>B</sub>, diffuse scattering below 40 K is consistent with only short-range antiferromagnetic ordering of the Cr<sup>3+</sup> moments on the oxide layer in the *ab* plane. These moments do not appear to give rise to any sharp magnetic Bragg peaks.

## ■ ASSOCIATED CONTENT

### SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.inorgchem.2c01773>.

Further diffractograms, refinement parameters, and magnetometry and conductivity data (PDF)

## ■ AUTHOR INFORMATION

### Corresponding Author

Simon J. Clarke – Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, Oxford OX1 3QR, United Kingdom; [orcid.org/0000-0003-4599-8874](https://orcid.org/0000-0003-4599-8874); Email: [simon.clarke@chem.ox.ac.uk](mailto:simon.clarke@chem.ox.ac.uk)

### Authors

Bradley C. Sheath – Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, Oxford OX1 3QR, United Kingdom

Xiaoyu Xu – Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, Oxford OX1 3QR, United Kingdom

Pascal Manuel – ISIS Facility, STFC Rutherford Appleton Laboratory, Harwell Oxford, Didcot OX11 0QX, United Kingdom

Joke Hadermann – Electron Microscopy for Materials Science (EMAT), University of Antwerp, B-2020 Antwerp, Belgium; [orcid.org/0000-0002-1756-2566](https://orcid.org/0000-0002-1756-2566)

Maria Batuk – Electron Microscopy for Materials Science (EMAT), University of Antwerp, B-2020 Antwerp, Belgium; [orcid.org/0000-0003-1411-9785](https://orcid.org/0000-0003-1411-9785)

John O'Sullivan – Department of Materials, University of Oxford, Oxford OX1 3PH, United Kingdom; [orcid.org/0000-0002-4136-0067](https://orcid.org/0000-0002-4136-0067)

Ruy S. Bonilla – Department of Materials, University of Oxford, Oxford OX1 3PH, United Kingdom; [orcid.org/0000-0002-5395-5850](https://orcid.org/0000-0002-5395-5850)

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acs.inorgchem.2c01773>

## Author Contributions

B.C.S. synthesized and analyzed the data on Sr<sub>2</sub>CrO<sub>2</sub>Cr<sub>2</sub>OAs<sub>2</sub>. X.X. synthesized and analyzed the data on Sr<sub>2</sub>CrO<sub>3</sub>CrAs. P.M. performed the neutron diffraction measurements. M.B. and J.H. performed the electron microscopy measurements and interpreted the data. J.O.S. and R.S.B. performed the high-temperature resistance measurements. B.C.S. wrote the paper with input from the other authors. S.J.C. provided materials and initial concepts.

## Notes

The authors declare no competing financial interest.

## ■ ACKNOWLEDGMENTS

We thank the UK EPSRC (EP/T027991/1, EP/M020517/1, EP/R042594/1, and EP/P018874/1) for funding and for studentship support to B.C.S.; the ISIS pulsed neutron and muon source (RB1920123) and Diamond Light Source Ltd. (EE18786 and CY25166) for the award of beam time. We thank Dr. A. Baker and Dr. C. Murray for support on I11 and Dr. S. Cassidy for support with high temperature magnetometry measurements. M.B. is grateful to Dr. Dmitry Batuk for his help to unveil the Sr<sub>2</sub>CrO<sub>3</sub>CrAs structure from STEM data. R.S.B. was supported by the Royal Academy of Engineering under the Research Fellowship scheme.

## ■ REFERENCES

- (1) Jha, R.; Goto, Y.; Matsuda, T. D.; Aoki, Y.; Nagao, M.; Tanaka, I.; Mizuguchi, Y. Bulk Superconductivity in a Four-Layer-Type Bi-Based Compound La<sub>2</sub>O<sub>2</sub>Bi<sub>3</sub>Ag<sub>0.6</sub>Sn<sub>0.4</sub>S<sub>5.7</sub>Se<sub>0.3</sub>. *Sci. Rep.* **2019**, *9*, 1–9.
- (2) Watanabe, T.; Yanagi, H.; Kamiya, T.; Kamihara, Y.; Hiramatsu, H.; Hirano, M.; Hosono, H. Nickel-Based Oxyphosphide Superconductor with a Layered Crystal Structure, LaNiOP. *Inorg. Chem.* **2007**, *46*, 7719–7721.
- (3) Barreteau, C.; Pan, L.; Amzallag, E.; Zhao, L. D.; Bérardan, D.; Drago, N. Layered Oxychalcogenide in the Bi-Cu-O-Se System as Good Thermoelectric Materials. *Semicond. Sci. Technol.* **2014**, *29*, No. 064001.
- (4) Heerwig, A.; Merkle, R.; Maier, J.; Ruck, M. Cu<sub>2</sub>Bi<sub>12</sub>S<sub>21</sub>Cl<sub>16</sub>-A Mixed Conductor with Fast One-Dimensional Copper(I) Ion Transport. *J. Solid State Chem.* **2011**, *184*, 191–198.
- (5) Im, J.; Trimarchi, G.; Poeppelmeier, K.; Zunger, A. Incomplete Peierls-like Chain Dimerization as a Mechanism for Intrinsic Conductivity and Optical Transparency: A La-Cu-O-S Phase with Mixed-Anion Layers as a Case Study. *Phys. Rev. B* **2015**, *92*, No. 235139.
- (6) Clarke, S. J.; Adamson, P.; Herkelrath, S. J. C.; Rutt, O. J.; Parker, D. R.; Pitcher, M. J.; Smura, C. F. Structures, Physical Properties, and Chemistry of Layered Oxychalcogenides and Oxyphosphides. *Inorg. Chem.* **2008**, *47*, 8473–8486.
- (7) Stock, C.; McCabe, E. E. The Magnetic and Electronic Properties of Oxyselenides - Influence of Transition Metal Ions and Lanthanides. *Journal of Physics Condensed Matter.* **2016**, No. 453001.
- (8) Ainsworth, C. M.; Wang, C. H.; Johnston, H. E.; McCabe, E. E.; Tucker, M. G.; Brand, H. E. A.; Evans, J. S. O. Infinitely Adaptive Transition-Metal Ordering in Ln<sub>2</sub>O<sub>2</sub>MSe<sub>2</sub>-Type Oxychalcogenides. *Inorg. Chem.* **2015**, *54*, 7230–7238.



- (9) Hiramatsu, H.; Yanagi, H.; Kamiya, T.; Ueda, K.; Hirano, M.; Hosono, H. Crystal Structures, Optoelectronic Properties, and Electronic Structures of Layered Oxychalcogenides  $\text{MCuOCh}$  ( $M = \text{Bi, La}$ ;  $\text{Ch} = \text{S, Se, Te}$ ): Effects of Electronic Configurations of  $\text{M}^{3+}$  Ions. *Chem. Mater.* **2008**, *20*, 326–334.
- (10) Cario, L.; Popa, A. F.; Lafond, A.; Guillot-Deudon, C.; Kabbour, H.; Meerschaut, A.; Clarke, S. J.; Adamson, P. Cation Deficient Layered Ruddlesden-Popper-Related Oxysulfides  $\text{La}_2\text{LnMS}_2\text{O}_5$  ( $\text{Ln} = \text{La, Y}$ ;  $M = \text{Nb, Ta}$ ). *Inorg. Chem.* **2007**, *46*, 9584–9590.
- (11) Ablimit, A.; Sun, Y. L.; Jiang, H.; Bao, J. K.; Zhai, H. F.; Tang, Z. T.; Liu, Y.; Wang, Z. C.; Feng, C. M.; Cao, G. H. Synthesis, Crystal Structure and Physical Properties of a New Oxypnictide  $\text{Ba}_2\text{Tl}_2\text{Cr}_2\text{As}_4\text{O}$  Containing  $[\text{Tl}_2\text{As}_2\text{O}]^{2-}$  and  $[\text{Cr}_2\text{As}_2]^{2-}$  layers. *J. Alloys Compd.* **2017**, *694*, 1149–1153.
- (12) Wang, X. F.; Yan, Y. J.; Ying, J. J.; Li, Q. J.; Zhang, M.; Xu, N.; Chen, X. H. Structure and Physical Properties for a New Layered Pnictide-Oxide:  $\text{BaTi}_2\text{As}_2\text{O}$ . *J. Phys.: Condens. Matter* **2010**, *22*, No. 075702.
- (13) Tegel, M.; Hummel, F.; Su, Y.; Chatterji, T.; Brunelli, M.; Johrendt, D. Non-Stoichiometry and the Magnetic Structure of  $\text{Sr}_2\text{CrO}_3\text{FeAs}$ . *EPL* **2010**, *89*, 37006.
- (14) Xu, X.; Jones, M. A.; Cassidy, S. J.; Manuel, P.; Orlandi, F.; Batuk, M.; Hadermann, J.; Clarke, S. J. Magnetic Ordering in the Layered Cr(II) Oxide Arsenides  $\text{Sr}_2\text{CrO}_2\text{Cr}_2\text{As}_2$  and  $\text{Ba}_2\text{CrO}_2\text{Cr}_2\text{As}_2$ . *Inorg. Chem.* **2020**, *59*, 15898–15912.
- (15) Liu, J.; Wang, J.; Sheng, J.; Ye, F.; Taddei, K. M.; Fernandez-Baca, J. A.; Luo, W.; Sun, G. A.; Wang, Z. C.; Jiang, H.; Cao, G. H.; Bao, W. Neutron Diffraction Study on Magnetic Structures and Transitions in  $\text{Sr}_2\text{Cr}_3\text{As}_2\text{O}_2$ . *Phys. Rev. B* **2018**, *98*, No. 134416.
- (16) Lawrence, G. B.; Wildman, E. J.; Stenning, G. B. G.; Ritter, C.; Fauth, F.; McLaughlin, A. C. Electronic and Magnetic Properties of Cation Ordered  $\text{Sr}_2\text{Mn}_{2.23}\text{Cr}_{0.77}\text{As}_2\text{O}_2$ . *Inorg. Chem.* **2020**, *59*, 7553–7560.
- (17) Xu, X. *DPhil Thesis*, University of Oxford, 2019.
- (18) Zhang, H.; Wu, X.; Li, D.; Jin, S.; Chen, X.; Zhang, T.; Lin, Z.; Shen, S.; Yuan, D.; Chen, X.  $\text{Ca}_2\text{O}_3\text{Fe}_{2.6}\text{S}_2$ : An Antiferromagnetic Mott Insulator at Proximity to Bad Metal. *J. Phys.: Condens. Matter* **2016**, *28*, No. 145701.
- (19) Free, D. G.; Withers, N. D.; Hickey, P. J.; Evans, J. S. O. Synthesis, Structure and Properties of Several New Oxychalcogenide Materials with the General Formula  $\text{A}_2\text{O}_2\text{M}_2\text{OSe}_2$  ( $A = \text{La-Sm}$ ,  $M = \text{Fe, Mn}$ ). *Chem. Mater.* **2011**, *23*, 1625–1635.
- (20) Sun, Y. L.; Jiang, H.; Zhai, H. F.; Bao, J. K.; Jiao, W. H.; Tao, Q.; Shen, C. Y.; Zeng, Y. W.; Xu, Z. A.; Cao, G. H.  $\text{Ba}_2\text{Tl}_2\text{Fe}_2\text{As}_4\text{O}$ : A New Superconductor Containing  $\text{Fe}_2\text{As}_2$  Layers and  $\text{Tl}_2\text{O}$  Sheets. *J. Am. Chem. Soc.* **2012**, *134*, 12893–12896.
- (21) Jiang, H.; Bao, J. K.; Zhai, H. F.; Tang, Z. T.; Sun, Y. L.; Liu, Y.; Wang, Z. C.; Bai, H.; Xu, Z. A.; Cao, G. H. Physical Properties and Electronic Structure of  $\text{Sr}_2\text{Cr}_3\text{As}_2\text{O}_2$  Containing  $\text{CrO}_2$  and  $\text{Cr}_2\text{As}_2$  Square-Planar Lattices. *Phys. Rev. B* **2015**, *92*, No. 205107.
- (22) Thompson, S. P.; Parker, J. E.; Potter, J.; Hill, T. P.; Birt, A.; Cobb, T. M.; Yuan, F.; Tang, C. C. Beamline I11 at Diamond: A New Instrument for High Resolution Powder Diffraction. *Rev. Sci. Instrum.* **2009**, *80*, 879.
- (23) Chapon, L. C.; Manuel, P.; Radaelli, P. G.; Benson, C.; Perrott, L.; Ansell, S.; Rhodes, N. J.; Raspino, D.; Duxbury, D.; Spill, E.; Norris, J. Wish: The New Powder and Single Crystal Magnetic Diffractometer on the Second Target Station. *Neutron News*. **2011**, *22*, 22–25.
- (24) Coelho, A. A. TOPAS and TOPAS-Academic: An Optimization Program Integrating Computer Algebra and Crystallographic Objects Written in C++. *An. J. Appl. Crystallogr.* **2018**, *51*, 210–218.
- (25) Zhu, W. J.; Hor, P. H.  $\text{Sr}_2\text{CuGaO}_3\text{S}$ , a Rare Example of Square Pyramidal Gallium. *Inorg. Chem.* **1997**, *36*, 3576–3577.
- (26) Kamihara, Y.; Matoba, M.; Kyomen, T.; Itoh, M. Magnetic and Electronic Nature of Layered Manganese Oxysulfide  $\text{Sr}_2\text{CuMnO}_3\text{S}$ . *J. Appl. Phys.* **2002**, *91*, 8864–8866.
- (27) Zhu, W. J.; Hor, P. H. Crystal Structure of New Layered Oxysulfides:  $\text{Sr}_3\text{Cu}_2\text{Fe}_2\text{O}_5\text{S}_2$  and  $\text{Sr}_2\text{CuMO}_3\text{S}$  ( $M = \text{Cr, Fe, In}$ ). *J. Solid State Chem.* **1997**, *134*, 128–131.
- (28) Charkin, D. O.; Sadakov, A. V.; Omel'yanovskii, O. E.; Kazakov, S. M. Synthesis, Crystal Structure, and Properties of Novel Perovskite Oxychalcogenides,  $\text{Ca}_2\text{CuFeO}_3\text{Ch}$  ( $\text{Ch} = \text{S, Se}$ ). *Mater. Res. Bull.* **2010**, *45*, 2012–2016.
- (29) Park, S. W.; Mizoguchi, H.; Kodama, K.; Shamoto, S. I.; Otomo, T.; Matsuishi, S.; Kamiya, T.; Hosono, H. Magnetic Structure and Electromagnetic Properties of  $\text{LnCrAsO}$  with a  $\text{ZrCuSiAs}$ -Type Structure ( $\text{Ln} = \text{La, Ce, Pr, and Nd}$ ). *Inorg. Chem.* **2013**, *52*, 13363–13368.
- (30) Brown, I. D.; Altermatt, D. Bond-valence Parameters Obtained from a Systematic Analysis of the Inorganic Crystal Structure Database. *Acta Crystallogr. Sect. B* **1985**, *41*, 244–247.
- (31) Brechtel, E.; Cordier, G.; Schäfer, H. On Oxidpnictides: Preparation and Crystal Structure of  $\text{A}_2\text{Mn}_3\text{B}_2\text{O}_2$  with  $A = \text{Sr, Ba}$  and  $B = \text{As, Sb, Bi}$ . *Zeitschrift für Naturforsch. - Sect. B J. Chem. Sci.* **1979**, *34*, 777–780.
- (32) Kabbour, H.; Janod, E.; Corraze, B.; Danot, M.; Lee, C.; Whangbo, M. H.; Cario, L. Structure and Magnetic Properties of Oxychalcogenides  $\text{A}_2\text{F}_2\text{Fe}_2\text{OQ}_2$  ( $A = \text{Sr, Ba}$ ;  $Q = \text{S, Se}$ ) with  $\text{Fe}_2\text{O}$  Square Planar Layers Representing an Antiferromagnetic Checkerboard Spin Lattice. *J. Am. Chem. Soc.* **2008**, *130*, 8261–8270.
- (33) Zhu, J. X.; Yu, R.; Wang, H.; Zhao, L. L.; Jones, M. D.; Dai, J.; Abrahams, E.; Morosan, E.; Fang, M.; Si, Q. Band Narrowing and Mott Localization in Iron Oxychalcogenides  $\text{La}_2\text{O}_2\text{Fe}_2\text{O}(\text{Se, S})_2$ . *Phys. Rev. Lett.* **2010**, *104*, No. 216405.
- (34) Free, D. G.; Evans, J. S. O. Low-Temperature Nuclear and Magnetic Structures of  $\text{La}_2\text{O}_2\text{Fe}_2\text{OSe}_2$  from x-Ray and Neutron Diffraction Measurements. *Phys. Rev. B* **2010**, *81*, No. 214433.
- (35) Oogarah, R. K.; Suard, E.; McCabe, E. E. Magnetic Order and Phase Transition in the Iron Oxysulfide  $\text{La}_2\text{O}_2\text{Fe}_2\text{OS}_2$ . *J. Magn. Magn. Mater.* **2018**, *446*, 101–107.
- (36) Ni, N.; Climent-Pascual, E.; Jia, S.; Huang, Q.; Cava, R. J. Physical Properties and Magnetic Structure of the Layered Oxyselenide  $\text{La}_2\text{O}_3\text{Mn}_3\text{Se}_2$ . *Phys. Rev. B* **2010**, *82*, No. 214419.
- (37) Fuwa, Y.; Endo, T.; Wakeshima, M.; Hinatsu, Y.; Ohoyama, K. Orthogonal Spin Arrangement in Quasi-Two-Dimensional  $\text{La}_2\text{Co}_2\text{O}_3\text{Se}_2$ . *J. Am. Chem. Soc.* **2010**, *132*, 18020–18022.
- (38) Campbell, B. J.; Stokes, H. T.; Tanner, D. E.; Hatch, D. M. ISODISPLACE: A Web-Based Tool for Exploring Structural Distortions. *J. Appl. Crystallogr.* **2006**, *39*, 607–614.
- (39) Brese, N. E.; O'Keeffe, M. Bond-valence Parameters for Solids. *Acta Crystallogr., Sect. B: Struct. Sci.* **1991**, *47*, 192–197.
- (40) Wang, C.; Tan, M. Q.; Feng, C. M.; Ma, Z. F.; Jiang, S.; Xu, Z. A.; Cao, G. H.; Matsubayashi, K.; Uwatoko, Y.  $\text{La}_2\text{Co}_2\text{Se}_2\text{O}_3$ : A Quasi-Two-Dimensional Mott Insulator with Unusual Cobalt Spin State and Possible Orbital Ordering. *J. Am. Chem. Soc.* **2010**, *132*, 7069–7073.
- (41) Whangbo, M. H.; Gordon, E. E.; Xiang, H.; Koo, H. J.; Lee, C. Prediction of Spin Orientations in Terms of HOMO-LUMO Interactions Using Spin-Orbit Coupling as Perturbation. *Acc. Chem. Res.* **2015**, *48*, 3080–3087.
- (42) Wu, H. Electronic Structure, Spin State, and Magnetism of the Square-Lattice Mott Insulator  $\text{La}_2\text{Co}_2\text{Se}_2\text{O}_3$  from First Principles. *Phys. Rev. B* **2010**, *82*, No. 020410.
- (43) Emery, N.; Wildman, E. J.; Skakle, J. M. S.; Girit, G.; Smith, R. I.; McLaughlin, A. C. Giant Magnetoresistance in Oxypnictides ( $\text{La, Nd}$ )OMnAs. *Chem. Commun.* **2010**, *46*, 6777–6779.
- (44) Singh, Y.; Green, M. A.; Huang, Q.; Kreyssig, A.; McQueeney, R. J.; Johnston, D. C.; Goldman, A. I. Magnetic Order in  $\text{BaMn}_3\text{As}_2$  from Neutron Diffraction Measurements. *Phys. Rev. B* **2009**, *80*, No. 100403.
- (45) Nath, R.; Garlea, V. O.; Goldman, A. I.; Johnston, D. C. Synthesis, Structure, and Properties of Tetragonal  $\text{Sr}_2\text{M}_3\text{As}_2\text{O}_2$  ( $\text{M}_3 = \text{Mn}_3, \text{Mn}_2\text{Cu}$ , and  $\text{MnZn}_2$ ) Compounds Containing Alternating  $\text{CuO}_2$ -Type and  $\text{FeAs}$ -Type Layers. *Phys. Rev. B* **2010**, *81*, No. 224513.

(46) Filsinger, K. A.; Schnelle, W.; Adler, P.; Fecher, G. H.; Reehuis, M.; Hoser, A.; Hoffmann, J. U.; Werner, P.; Greenblatt, M.; Felser, C. Antiferromagnetic Structure and Electronic Properties of  $\text{BaCr}_2\text{As}_2$  and  $\text{BaCrFeAs}_2$ . *Phys. Rev. B* **2017**, *95*, No. 184414.

(47) Corkett, A. *DPhil Thesis*, University of Oxford, 2012.

(48) Herkelrath, S. J. C.; Blandy, J. N.; Clarke, S. J. Magnetic Ordering in the Layered OxyseLENides  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ . *J. Solid State Chem.* **2018**, *264*, 119–123.

(49) Blandy, J. N.; Parker, D. R.; Cassidy, S. J.; Woodruff, D. N.; Xu, X.; Clarke, S. J. Synthesis, Structure, and Compositional Tuning of the Layered Oxide Tellurides  $\text{Sr}_2\text{MnO}_2\text{Cu}_{2-x}\text{Te}_2$  and  $\text{Sr}_2\text{CoO}_2\text{Cu}_2\text{Te}_2$ . *Inorg. Chem.* **2019**, *58*, 8140–8150.