



Environmental Microbiology

Streptomyces lunalinharesii 235 prevents the formation of a sulfate-reducing bacterial biofilm



Juliana Pacheco da Rosa, Samyra Raquel Gonçalves Tibúrcio, Joana Montezano Marques, Lucy Seldin*, Rosalie Reed Rodrigues Coelho

Instituto de Microbiologia Paulo de Góes, Universidade Federal do Rio de Janeiro, Rio de Janeiro, RJ, Brazil

ARTICLE INFO

Article history:

Received 25 June 2015

Accepted 8 December 2015

Available online 19 April 2016

Associate Editor: Raquel Silva Peixoto

Keywords:

Streptomyces

Antimicrobial substance

Biofilm

Biocorrosion

Sulfate reducing bacteria

ABSTRACT

Streptomyces lunalinharesii strain 235 produces an antimicrobial substance that is active against sulfate reducing bacteria, the major bacterial group responsible for biofilm formation and biocorrosion in petroleum reservoirs. The use of this antimicrobial substance for sulfate reducing bacteria control is therefore a promising alternative to chemical biocides. In this study the antimicrobial substance did not interfere with the biofilm stability, but the sulfate reducing bacteria biofilm formation was six-fold smaller in carbon steel coupons treated with the antimicrobial substance when compared to the untreated control. A reduction in the most probable number counts of planktonic cells of sulfate reducing bacteria was observed after treatments with the sub-minimal inhibitory concentration, minimal inhibitory concentration, and supra-minimal inhibitory concentration of the antimicrobial substance. Additionally, when the treated coupons were analyzed by scanning electron microscopy, the biofilm formation was found to be substantially reduced when the supra-minimal inhibitory concentration of the antimicrobial substance was used. The coupons used for the biofilm formation had a small weight loss after antimicrobial substance treatment, but corrosion damage was not observed by scanning electron microscopy. The absence of the *dsrA* gene fragment in the scraped cell suspension after treatment with the supra-minimal inhibitory concentration of the antimicrobial substance suggests that *Desulfovibrio alaskensis* was not able to adhere to the coupons. This is the first report on an antimicrobial substance produced by *Streptomyces* active against sulfate reducing bacteria biofilm formation. The application of antimicrobial substance as a potential biocide for sulfate reducing bacteria growth control could be of great interest to the petroleum industry.

© 2016 Sociedade Brasileira de Microbiologia. Published by Elsevier Editora Ltda. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

* Corresponding author.

E-mail: lseldin@micro.ufrj.br (L. Seldin).

<http://dx.doi.org/10.1016/j.bjm.2016.04.013>

1517-8382/© 2016 Sociedade Brasileira de Microbiologia. Published by Elsevier Editora Ltda. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Introduction

Biofilms are microbial communities of surface-attached cells embedded in a self-produced extracellular polymeric matrix.¹ In the petroleum industry, the formation of biofilms on carbon steel causes many problems, such as pipe clogging, biofouling of the distribution systems and generating microbiologically influenced corrosion (or biocorrosion).^{2–4} Biocorrosion is an electrochemical process in which microorganisms initiate, facilitate, or accelerate a corrosion reaction on a metal surface.⁵ It is a well-documented phenomenon and produces a deterioration of petroleum product pipelines and storage tanks.⁶ Previous studies have emphasized the economic importance of undesirable microbial growth for the petroleum industry.^{7–9} It has been estimated that 40% of all internal pipeline corrosion in the petroleum industry can be attributed to biocorrosion.¹⁰ The main bacteria involved in these harmful processes in petroleum industries are the sulfate reducing bacteria (SRB).^{11,12} These bacteria may lead to the biodegradation of the metal surfaces of tanks and pipes through biofilm formation.¹³

In petroleum industries, biocides, such as chloride, glutaraldehyde and quaternary ammonium salts, are used for controlling and inhibiting SRB growth.¹⁴ However, the appearance of biocide-resistant bacteria and the difficulty of biocides in penetrating the biofilms present serious problems. In addition, the residual concentration, toxicity and persistence of biocides in industrial effluents are of high environmental concern.¹² For these reasons, alternative sources for SRB control are of great interest to the petroleum industry.^{15,16} One alternative method to control SRB growth with a reduced environmental impact is the use of antimicrobial substances produced by microorganisms.

Actinobacteria are biotechnologically valuable bacteria.^{17,18} The bioactive secondary metabolites produced by Actinobacteria are of clinical use and include antibiotics, antitumor agents, immunosuppressive agents and enzymes.^{19,20} Among the Actinobacteria, approximately 7600 compounds are produced by *Streptomyces* species.²¹ An antimicrobial substance (AMS) produced by strain 235 of *S. lunalinharesii*, which was originally isolated from a tropical Brazilian soil, was previously shown to inhibit the growth of *Desulfovibrio alaskensis* NCIMB 13491.²² This antimicrobial substance showed to be stable at a variety of temperatures and in a wide pH range.²² In this study, for the first time, the effects of the AMS produced by *S. lunalinharesii* strain 235 on the formation and stability of the *D. alaskensis* NCIMB 13491 biofilm on carbon steel surfaces and the consequences of AMS treatment on biocorrosion were evaluated.

Materials and methods

Bacterial strains and growth conditions

The Actinobacteria *Streptomyces lunalinharesii* strain 235 used in this study was originally isolated from soil of the Atlantic Forest (Rio de Janeiro, Brazil)²³ and was identified by our group.²² It was previously selected as a promising agent for the production of AMS against different microbial strains,^{23–25}

including aerobic and anaerobic bacteria involved in biocorrosion processes.²² This strain was grown in yeast extract-malt extract-agar (YMA)²⁶ under aerobic conditions at 28 °C for 7 days.

The sulfate reducing bacterium *Desulfovibrio alaskensis* NCIMB 13491 was isolated from a soured oil reservoir²⁷ and grown in Postgate C medium¹¹ at 30 °C for 3 days, in anaerobic conditions using sealed serum bottles (10 mL). The bottles were purged with a N₂ flux to achieve anaerobiosis.

Production of the antimicrobial substance (AMS)

Concentrated supernatant containing the AMS produced by strain 235 was obtained as described by Rosa et al.²² Briefly, a spore suspension (10⁸ spores/mL) was inoculated in 50 mL of liquid chemically defined medium containing glucose²⁸ at pH 7.0. After 7 days of incubation at 28 °C in stationary conditions, 5 mL of the culture was transferred into 2000 mL Erlenmeyer flasks containing 500 mL of the same liquid medium. After 7 days of incubation under the same conditions, the resulting supernatant was filtered through filter paper (Whatman n° 1), and the filtrate lyophilized (Free Zone 4.5) and resuspended in sterile Milli Q water (1.6 mL). The concentrated supernatant containing the AMS was used in the following experiments.

Short-term tests – the effect of AMS on the biofilm formation and stability

The short-term action of AMS on the *D. alaskensis* biofilm was evaluated during biofilm formation and after its formation, to evaluate its stability. The tests were conducted as described by Clark et al.²⁹ with some modifications. Petri dishes (5 cm) containing a single carbon steel coupon (10 mm × 10 mm × 2 mm) were filled with AMS (0.5 mL), a reducing solution (0.5 mL) containing sodium thioglycolate 0.0124%, ascorbic acid 0.01% and resazurin 0.4% (pH 7.5) and a cell suspension of *D. alaskensis* grown in Postgate C medium (10⁷ cells/mL, 1.0 mL). When testing the effect of AMS on the biofilm formation, AMS was introduced at the same time as the cell suspension, as described above. However, when testing the effect of AMS on the biofilm stability, the AMS was inoculated only after biofilm formation. In this case, Petri dishes containing the carbon steel coupon were filled solely with the cell suspension of *D. alaskensis* grown in Postgate C medium (10⁷ cells/mL, 2.0 mL) and incubated for 24 h. Afterwards, the cells were removed, and 1 mL of the reducing solution and 1 mL of AMS were added. Prior to beginning the experiments, the coupon surfaces were treated with a sandblasting technique, cleaned in 18% HCl, and neutralized by immersion in a sodium bicarbonate solution. Finally, the coupons were washed with distilled water, rinsed in acetone, and dried in an air stream.¹⁵ As an experimental control, Petri dishes containing the reducing solution and the cell suspension of *D. alaskensis* were used. After 7 days of incubation at 32 °C, the liquid mixture was removed and the coupons were rinsed 3 times in the reducing solution. The coupons were then submerged in a crystal violet dye (0.1%) for 10 min, rinsed 3 times in Milli Q water and destained in an ethanol/acetone solution (80:20, v/v) for 20 min. The destained solution was measured spectrophotometrically at OD₅₈₀. The original planktonic cell suspension was measured at OD₆₀₀,

and the ratio of OD₅₈₀ to OD₆₀₀ was calculated to determine relative biofilm formation and/or stability.

All inoculation and incubation procedures were conducted in an anaerobic chamber (Plas Labs, Lansing, MI, USA), and all experiments were performed in triplicate.

Long-term tests – evaluation of AMS treatment during biofilm formation and its effects on biocorrosion

Two long-term experiments were conducted. The first (Test 1) aimed to analyze the effect of AMS during *D. alaskensis* biofilm formation. The second (Test 2) evaluated the effects of AMS on the *D. alaskensis*-produced biocorrosion of a carbon steel coupon (10 mm × 10 mm × 2 mm). Prior to beginning the experiments, the coupon surfaces were sandblasted and cleaned as described by Nemati et al.¹⁵

The experiments were performed in sealed serum bottles (10 mL) containing a single carbon steel coupon, an SRB cell suspension (10⁷ cells/mL, 0.2 mL) and different amounts of AMS (0.05, 0.03, 0.01 g protein/mL, 1 mL) diluted in Postgate C medium, in order to obtain successive AMS dilutions (of 1/2, 1/4, 1/8). The AMS dilutions corresponded to the supra-MIC (Minimal Inhibitory Concentration) (2 × MIC), the MIC and the sub-MIC (0.5 × MIC) and were determined by our group.²² Serum bottles containing only Postgate C medium and serum bottles containing Postgate C medium and a cell suspension of SRB were used as the experimental controls. The experiments were performed in triplicate under anoxic conditions, incubated with stirring (50 rev/min) and maintained at 32 °C. After 30 days of incubation, the coupons were removed aseptically from each experiment inside a sterile laminar flow hood and used for imaging, cell counts and molecular analyses.

All inoculation and incubation procedures were conducted in an anaerobic chamber, and the experiments were performed in triplicate.

Scanning electronic microscopy (SEM) of the biofilms

To visualize biofilm formation by SEM (Test 1), the coupons were rinsed with a synthetic seawater solution (NaF 0.003%, SrCl₂·6H₂O 0.002%, H₃BO₃ 0.03%, KBr 0.1%, KCl 0.7%, CaCl₂ 1.113%, Na₂SO₄ 4%, MgCl₂·6H₂O 10.78%, NaCl 23.5%, NaSiO₃·9H₂O 0.02%, Na₂EDTA 0.01% and NaHCO₃ 0.2%, pH 7.5), fixed with 2.5% glutaraldehyde (w/v) in 0.1 M cacodylate buffer (pH 7.2) and kept for 24 h at 4 °C. Then, the coupons were rinsed three times with the same cacodylate buffer for 10 min, dehydrated in ethanol solutions of increasing concentration (30, 50, 70 and 90%) and washed three times in 100% ethanol for 10 min at each step. After this step, the coupons were chemically dried by immersion in a 50% HMDS solution (hexamethyldisilazane solvent – Sigma) for 3 min.³⁰ Finally, the samples were mounted on stubs, and coupon surfaces were sputter coated (Balzers SCD-040) with a 15 nm gold layer. The samples were then examined with a FEI QUANTA 250 microscope (FEI Company, Netherlands).

Corrosion tests

The surface corrosion (Test 2) and coupon weight loss were analyzed. To remove any adherent bacteria, the coupons were

scraped with a sterile wooden stick in sterile glass bottles with 9 mL of a reducing solution. For the weight loss test, the coupon surfaces were cleaned (washed in acid, neutralized with sodium bicarbonate, rinsed in water and acetone, and dried in an air stream) as described by Nemati et al.¹⁵ The determination of the exact weight of the coupons was carried out just before starting and after finishing the experiments. The coupon weight (in grams) was determined by using an electronic balance (Bioprecisa, model FA2104N). To calculate the weight loss resulting from corrosion, the weight of the coupon at the end of the experiments and after cleaning was subtracted from the original weight of the coupon. The corrosion rate (CR) of carbon steel coupons for each experiment (including the controls) was calculated and is expressed in mm/year,³¹ using 7.84 g/cm³ as the density of carbon steel. A two-sample t test was performed on the treated and control coupons.³² In addition, after the coupon surfaces were scraped and cleaned,¹⁵ they were gold coated and examined by SEM (FEI QUANTA 250 microscope) to observe their corrosion patterns. The images were acquired at a resolution of 7192 × 3090 pixels.

Most probable number

The most probable number (MPN) technique was performed as previously described.³³ To count the sulfate-reducing bacteria (SRB), an aliquot (1 mL) of the scraped cell suspension solution from the coupons (Test 2) described above was used as the initial inoculum. Decimal dilutions (up to 10⁻⁸) were prepared in a synthetic seawater solution. Aliquots (1 mL) from each dilution were then transferred to Postgate E medium¹¹ in triplicate and incubated at 32 °C. The MPN was determined using the MPN Reference Table.³⁴ This experiment was conducted under anaerobic conditions.

Molecular analysis

The scraped cell suspension from the coupons (Test 2) and the liquid phase were used to detect the dissimilatory sulfite reductase (DSR) gene. The presence of the *dsrA* gene indicates the presence of the reducing sulfate bacterium *D. alaskensis*. The dissimilatory sulfite reductase enzyme catalyzes the six-electron reduction of (bi)sulfite to sulfide, which is the central energy-conserving step of sulfate respiration.³⁵

Aliquots (3 mL) of the scraped cell suspension and of the liquid phase (2 mL) were filtered through a Millipore membrane (0.45 μm). The DNA extraction of filtrates was accomplished using a direct lyses method with a commercial Fast DNA Spin Kit for soil (Bio Systems, Q Bio Gene, USA), according to the manufacturer's instructions. The extracted DNA was visualized on 0.8% (w/v) agarose gels to assess the DNA integrity and stored at 4 °C prior to use in PCR reactions.

The DNA extracted from the filtrates was amplified using the primers DSR-1F (5'-AC[C/G]CACTGGAAGCAG-3') and DSR-R (5'-GTGGMRCCTGCAKRTTGG-3'),^{36,37} which are specific for the *dsrA* gene. The 25 μl reaction mixture contained 1 μl (10 ng) of DNA, 1 × Taq polymerase buffer (10 mmol Tris-HCl [pH 8.3], 10 mmol KCl), 0.2 mM of each dNTP, 100 nM of each primer, 2.5 mM MgCl₂, 1.25 U of Taq DNA polymerase (Promega, Madison, USA) and sterile Milli-Q water. The

amplification conditions were as follows: 1× (15 s, 94 °C), 30× (15 s, 94 °C; 20 s 54 °C; 54 s, 72 °C), and 1× (1 min, 72 °C). Positive (*D. alaskensis* strain NCIMB 13491) and negative controls (without DNA) were run in all amplifications. The PCR products were visualized by electrophoresis on 1.4% agarose gels stained with ethidium bromide (2 µg/mL).

Results

Short-term tests – the effect of AMS on biofilm formation and stability

After confirming the inhibitory activity of AMS against *D. alaskensis*, the action of AMS on the *D. alaskensis* biofilm was assessed by a short-term test. Quantification of the crystal violet dye retained in the biofilm cells revealed that biofilm formation was six fold smaller in the coupon treated with AMS (Ratio OD₅₈₀/OD₆₀₀ = 0.07) when compared to the untreated control (Ratio OD₅₈₀/OD₆₀₀ = 0.43) (Fig. 1A). However, it was observed that AMS had no effect on the biofilm stability of *D. alaskensis*, as it was observed that the coupon that was treated with AMS (Ratio OD₅₈₀/OD₆₀₀ = 0.16) retained even more dye than the coupon that received no treatment (Ratio OD₅₈₀/OD₆₀₀ = 0.11) (Fig. 1B).

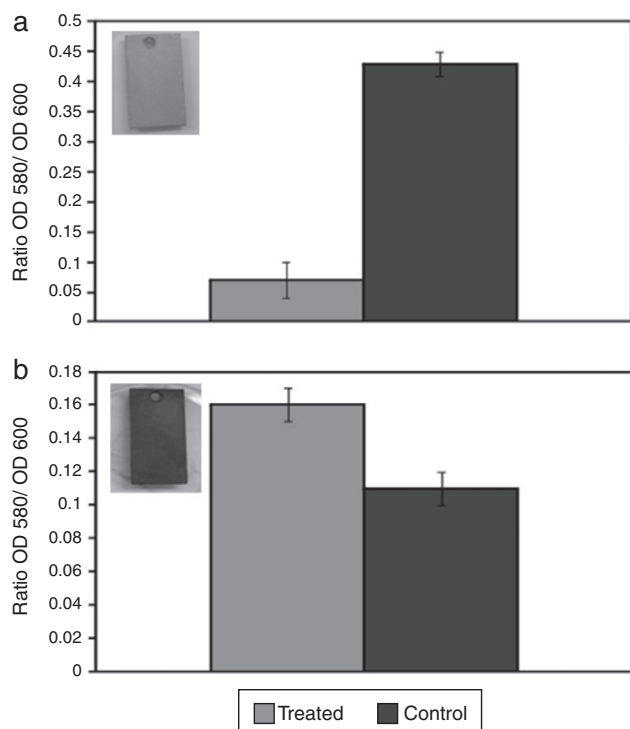


Fig. 1 – Quantification of the crystal violet dye retained in the biofilm formed by *D. alaskensis* cells on carbon steel coupons. The effect of the antimicrobial substance (AMS) on biofilm formation (A) and on biofilm stability (B) is shown. The values are expressed as a ratio of the optical densities of 580 and 600. The coupons treated with AMS are shown in the left of each graphic.

The coupons treated with AMS, obtained from both tests, were visually different. The coupon obtained from the first test remained clean without any blackish deposits (Fig. 1A, insert). However, the coupon obtained from the second test was covered in blackish deposits, suggesting iron sulfide formation and therefore the presence of *D. alaskensis* growth (Fig. 1B, insert).

Long-term tests – evaluation of the effects of AMS treatment during biofilm formation and on biocorrosion

Two experiments (Test 1 and Test 2) were carried out to evaluate the effects of AMS on *D. alaskensis* biofilm formation and on biocorrosion of the coupon surface. At the end of both experiments, the liquid phases of the experiments containing the 1/4 and 1/8 AMS dilutions and the control cells experiments were blackish, suggesting iron sulfide formation and therefore the presence of *D. alaskensis*. However, in the experiments containing the 1/2 dilution of AMS (0.05 g protein/mL) and the control without cells, the liquid phases maintained their yellowish color. The SEM comparison between the AMS-treated coupons, the blank coupons without cells (Fig. 2A) and the control cells with biofilm growth (Fig. 2B) shows that the biofilm was substantially reduced in the coupons treated with supra-MIC (1/2 of AMS) (Fig. 2C). However, the coupons treated with MIC (1/4 dilution of AMS) and sub-MIC (1/8 of AMS) (Fig. 2D and E, respectively) were not affected, and biofilms were subsequently formed.

Corrosion tests

Smaller corrosion rates (CR) were observed on the coupons treated with supra-MIC (the 1/2 dilution of AMS), MIC (the 1/4 dilution of AMS) and sub-MIC (the 1/8 dilution of AMS) (0.27, 0.28 and 0.21 mm/year, respectively) when compared with the control cell experiment (0.38 mm/year). However, these differences were not statistically significant ($p > 0.05$). Additionally, the corrosion damage on the carbon steel surface was not observed by scanning electron micrographs after treatment with AMS and on the control cells (data not shown).

Most probable number

The impact of AMS on the SRB cells present in the biofilms formed on the coupons from Test 2 were determined using the most probable number (MPN) estimation of the SRB cells (Fig. 3). Biofilm samples from the control cell coupons indicated that the SRB counts were approximately 10^3 cells/mL. The numbers of SRB cells decreased after treatment with AMS. After treatment with MIC and sub-MIC concentrations of AMS (the 1/4 and 1/8 dilutions of AMS, respectively) the SRB counts were approximately 10^2 cells/mL. In addition, after treatment with supra-MIC of AMS (dilution 1/2) SRB counts were not detectable.

Molecular analysis

A PCR using primers specific for the *dsrA* gene, encoding the dissimilatory sulfite reductase enzyme, was used to evaluate the effects of AMS on the *D. alaskensis* cells from the scraped

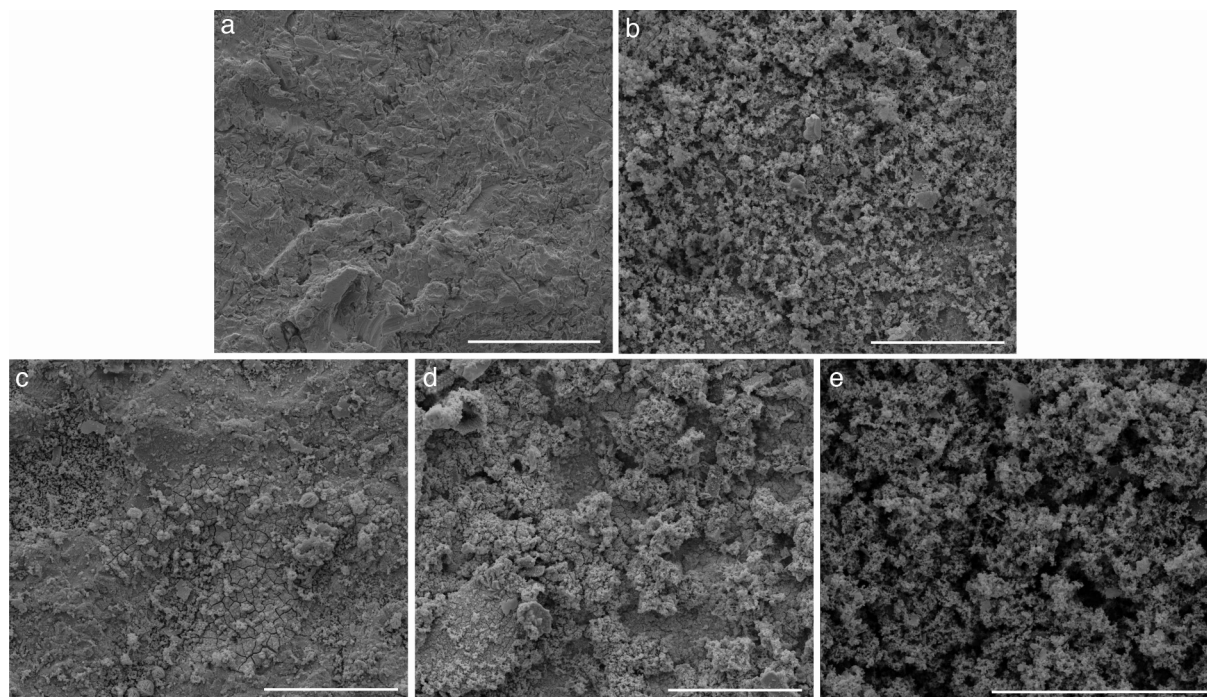


Fig. 2 – Scanning electronic microscopy (SEM) micrographs showing the coupons treated with different concentrations of the antimicrobial substance (AMS). Blank coupons – without biofilm formation (A); control – coupons not treated with AMS (B); coupons treated with supra-Minimal Inhibitory Concentration (MIC) of AMS (C); and coupons treated with MIC (D) and sub-MIC of AMS (E). Scale bars represent 100 μm .

cell suspension and the liquid phase (Test 2). According to Fig. 4a, in the liquid phase, a fragment with the expected size (approximately 200 bp) was observed after treatment with the supra-MIC, MIC and sub-MIC concentrations of AMS. However, in the scraped cell suspension (Fig. 4b), a fragment with the expected size was not detected after treatment with the supra-MIC of AMS. These results suggest that *D. alaskensis* could either be absent, or present at quantities below the PCR detection limit, after treatment with the lowest dilution (1/2) of AMS.

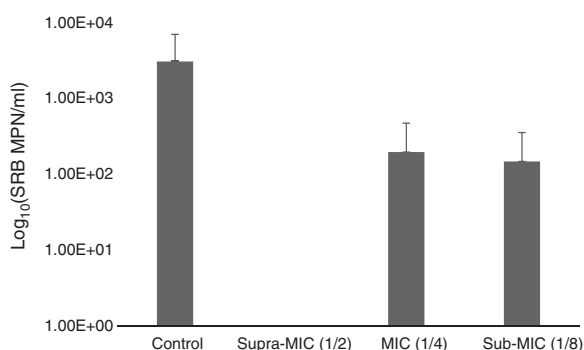


Fig. 3 – Most probable number (MPN) of sulfate reducing bacteria (SRB) after the treatment of the coupons with the Minimal Inhibitory Concentration (MIC – 1/4), supra-MIC (1/2) and sub-MIC (1/8) dilutions of AMS. The controls did not receive any treatment.

Discussion

The present study examined the effects of AMS produced by *S. lunalinharesii* strain 235 on the formation and stability of SRB biofilms and on the biocorrosion of carbon steel coupons caused by these bacteria. Biocides are traditionally used to control biofilm formation; however, the environmental impact and cost of using these compounds should be considered. *Streptomyces* are the prime producers of bioactive compounds for the biotechnology industry. Several clinically significant antibiotics, as well as other widely used drugs targeting common diseases, have been derived from this unique genus affiliated with the order Actinomycetales.³⁸ The AMS produced by *S. lunalinharesii* strain 235 has already been shown to inhibit the growth of SRB.²² However, further studies on this AMS had not yet been conducted. Several experiments in the present study have demonstrated that the AMS produced by *S. lunalinharesii* 235 is also able to affect the biofilms of SRB, a bacterial group involved in biofilm formation and pipe corrosion in the oil industry.

Since crystal violet staining was first described by Christensen et al.,³⁹ it has been modified to increase its accuracy and to allow biofilm biomass quantification.⁴⁰ Crystal violet is a basic dye which binds to negatively charged surface molecules and polysaccharides in the extracellular matrix.⁴¹ Crystal violet dye was used for the quantification of cells remaining in the SRB biofilm after AMS treatment in a seven-day experiment, and a reduction of about six fold was observed in the *D. alaskensis* cells. Consistent with this result, the

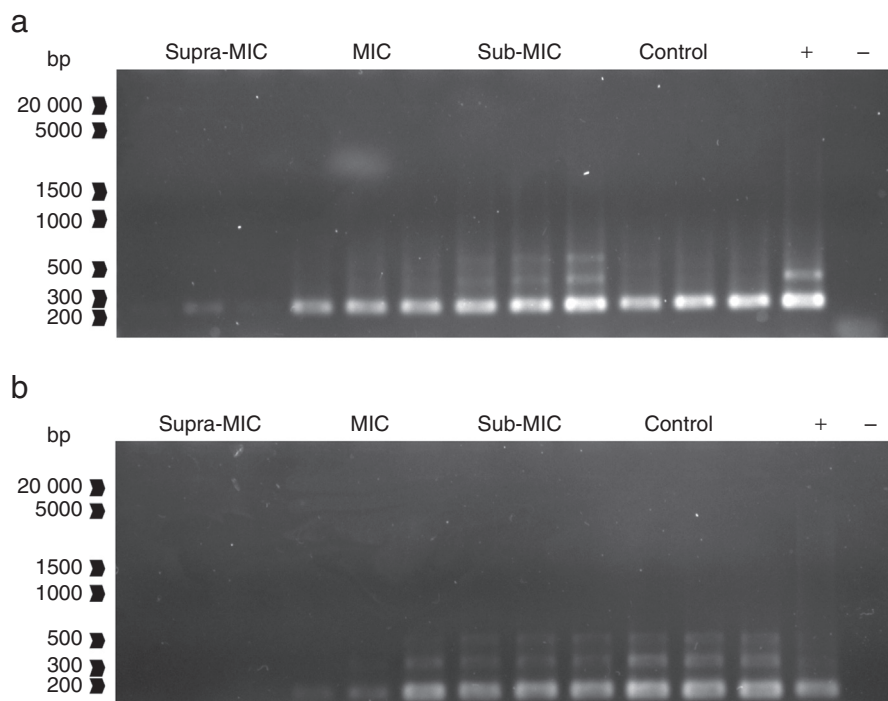


Fig. 4 – Agarose gel electrophoresis showing the PCR fragments (approximately 200 bp) obtained after the amplification with specific primers for the *dsrA* gene (encoding the dissimilatory sulfite reductase) of the scraped cell suspension (A) and the liquid phase (B) treated with Minimal Inhibitory Concentration (MIC), supra-MIC and sub-MIC dilutions of AMS as templates.

coupons remained clean and free of blackish deposits, suggesting the absence of ferrous sulfide production from the biocorrosive action of *D. alaskensis*. However, the AMS was not able to interfere with the stability of the biofilms because when treating biofilms that had already formed with AMS, no significant differences were observed. Using the same method, Clark et al.²⁹ observed that biofilm formation by *Desulfovibrio vulgaris* was inhibited approximately two fold after protease treatment. Korenblum et al.¹² also detected a reduction in the biofilm formation of *D. alaskensis* after treatment with a plant essential oil.

In another experiment, when *D. alaskensis* cells were incubated with different AMS dilutions for 30 days, the influence of AMS on the biofilm formation was again established. Scanning electron micrographs have shown biofilm formation on the coupons treated with MIC and sub-MIC concentrations of AMS; however, on the coupons treated with supra-MIC, the observed biofilm formation was substantially reduced, confirming that higher concentrations of AMS can inhibit biofilm formation to a significant degree. In addition, the most probable number counts of SRB were reduced after treatment with all three dilutions tested. In order to further verify this result, a more sensible molecular approach was used in the same experiment, and this approach also supported the efficiency of AMS in interfering with the biofilm formation of SRB on carbon steel coupons. After treatment with the lowest dilution (1/2) of AMS, the presence of a fragment with the expected size of the *dsrA* gene in the liquid phase and the absence of the same fragment in the scraped cell suspension suggested that *D. alaskensis* was unable to adhere to coupons treated with this dilution of AMS. Our study has revealed that in the

experimental conditions used here, the AMS produced by *S. lunalinharesii* was able to slightly reduce the weight loss of the coupons and thus the amount of biocorrosion. Moreover, corrosion damage was not observed using scanning electronic microscopy. The golden rule in order to avoid biocorrosion in all industrial systems is to keep the system clean.¹⁴ Thus, the use of AMS, produced by *S. lunalinharesii* strain 235, to control SRB biofilm formation would be incredibly useful for preventing metal surface corrosion. However, additional experiments will be necessary to allow for increased AMS production, so it can be detected without a supernatant concentration step.

Conflicts of interest

The authors declare no conflicts of interest.

Acknowledgements

This study was supported by grants from the Conselho Nacional de Desenvolvimento Científico e Tecnológico (CNPq), Coordenação de Aperfeiçoamento de Pessoal de Nível Superior (CAPES), Fundação de Amparo à Pesquisa do Estado do Rio de Janeiro (FAPERJ) and PETROBRAS. We thank Fernando Pereira de Almeida for the SEM images.

REFERENCES

1. Donlan RM, Costerton JW. Biofilms: survival mechanisms of clinical relevant microorganisms. *Clin Microbiol Rev.* 2002;15:167–193.

2. Flemming HC. Biofouling in water systems – cases, causes and countermeasures. *Appl Microbiol Biotechnol.* 2002;59:629–640.
3. Coetser SE, Cloete TE. Biofouling and biocorrosion in industrial water systems. *Crit Rev Microbiol.* 2005;31:213–232.
4. Videla HA, Herrera LK. Microbiologically influenced corrosion: looking to the future. *Int Microbiol.* 2005;8:169–180.
5. Rajasekar A, Anandkumar B, Maruthamuthu S, Ting Y-P, Rahman PKSM. Characterization of corrosive bacterial consortia isolated from petroleum-product-transporting pipelines. *Appl Microbiol Biotechnol.* 2010;85:1175–1188.
6. Benka-Coker MO, Metseagharun W, Ekundayo JA. Abundance of sulphate-reducing bacteria in Niger Delta oilfield waters. *Bioresour Technol.* 1995;54:151–154.
7. Costerton JW, Boivin J. Biofilms and biocorrosion. In: Flemming H-C, Geesey GG, eds. *Biofouling and Biocorrosion in Industrial Water Systems.* 1991:195–204. Heidelberg, Berlin.
8. Beech IB. Corrosion of technical materials in the presence of biofilms – current understanding and state-of-the-art methods of study. *Int Biodeter Biodegrad.* 2004;53:177–183.
9. Voordouw G. Production-related petroleum microbiology: progress and prospects. *Curr Opin Biotechnol.* 2011;22:401–405.
10. Graves JW, Sullivan EH. International corrosion in gas gathering systems and transmission lines. *Mater Prot.* 1966;5:33–37.
11. Postgate JR. *The Sulphate-reducing Bacteria.* 2nd ed. Cambridge, England: Cambridge University Press; 1984.
12. Korenblum E, Goulart FRV, Rodrigues IA, et al. Antimicrobial action and anti-corrosion effect against sulfate reducing bacteria by lemongrass (*Cymbopogon citratus*) essential oil and its major component, the citral. *AMB Express.* 2013;3:44.
13. Zuo R. Biofilms: strategies for metal corrosion inhibition employing microorganisms. *Appl Microbiol Biotechnol.* 2007;76:1245–1253.
14. Videla HA. Prevention and control of biocorrosion. *Int Biodeter Biodegrad.* 2002;49:259–270.
15. Nemati T, Jenneman GE, Voordouw G. Impact of nitrate-mediated microbial control of souring in oil reservoirs on the extend of corrosion. *Biotechnol Prog.* 2001;17:852–859.
16. Stewart P. Mechanisms of antibiotics resistance in bacterial biofilms. *Int J Med Microbiol.* 2002;292:107–113.
17. Balagurunathan R, Radhakrishnan M. Biotechnological, genetic engineering and nanotechnological potential of actinomycetes. In: Maheshwari DK, Dubey RC, Saravanamurthu R, eds. *Industrial Exploitation of Microorganisms.* 1st ed. 2010:302–436. New Delhi, India.
18. Satheeja SV, Jebakumar SRD. Phylogenetic analysis and antimicrobial activities of *Streptomyces* isolates from mangrove sediment. *J Basic Microbiol.* 2011;51:71–79.
19. Kekuda TRP, Shobha KS, Onkarappa R. Studies on antioxidant and antihelminthic activity of two *Streptomyces* species isolated from Western Ghat soils of Agumbe, Karnataka. *J Pharm Res.* 2010;3:26–29.
20. Ravikumar S, Inbaneson SJ, Uthiraselvam M, Priya SR, Ramu A, Banerjee MB. Diversity of endophytic actinomycetes from Karangkadu mangrove ecosystem and its antibacterial potential against bacterial pathogens. *J Pharm Res.* 2011;4:294–296.
21. Berdy J. Bioactive microbial metabolites. *J Antibiot (Tokyo).* 2005;58:1–26.
22. Rosa JP, Korenblum E, Franco-Cirigliano MN, et al. *Streptomyces lunalinharesii* strain 235 shows the potential to inhibit bacteria involved in biocorrosion process. *BioMed Res Int.* 2013;2013:1–10.
23. Coelho RRR, Lopes A, Semêdo LTAS, Cruz FS. Culture filtrates of actinomycetes isolated from tropical soils inhibit *Trypanosoma cruzi* replication in vitro. *Rev Microbiol.* 1995;26:307–313.
24. Semêdo LTAS, Linhares AA, Gomes RC, et al. Isolation and characterization of actinomycetes from Brazilian tropical soils. *Microbiol Res.* 2001;155:291–299.
25. Reis SA, Costa LV, Cavalcanti EDC, et al. Protein synthesis inhibitory activity in culture filtrates from new strains of *Streptomyces* isolated from Brazilian tropical soils. *Lett Appl Microbiol.* 2003;37:138–143.
26. Shirling EB, Gottlieb D. Methods for characterization of *Streptomyces* species. *Int J Syst Bacteriol.* 1966;16:313–340.
27. Feio MJ, Zinkevich V, Beech IB, et al. *Desulfovibrio alaskensis* sp. nov., a sulfate-reducing bacterium from a soured oil reservoir. *Int J Syst Evol Microbiol.* 2004;54:1747–1752.
28. von der Weid I, Alviano DS, Santos ALS, Soares RM, Alviano CS, Seldin L. Antimicrobial activity of *Paenibacillus peoriae* strain NRRL BD-62 against a broad spectrum of phytopathogenic bacteria and fungi. *J Appl Microbiol.* 2003;95:1143–1151.
29. Clark ME, Edelmann RE, Duley ML, Wall JD, Fields MW. Biofilm formation in *Desulfovibrio vulgaris* Hildenborough is dependent upon proteins filaments. *Environ Microbiol.* 2007;9:2844–2854.
30. Araujo JC, Téran FC, Oliveira RA, et al. Comparison of hexamethyldisilazane and critical point drying treatments for SEM analysis of anaerobic biofilms and granular sludge. *J Electron Microsc (Tokyo).* 2003;52:429–433.
31. ASTM G-4/95. Standard guide for conducting corrosion coupon tests in field applications. In: *Annual Book of American Society for Testing and Materials Standards 3.02.*; 2001:49–57. Philadelphia, PA, USA.
32. Motta VT, Wagner MB. *Bioestatística.* Caxias do Sul, RS/São Paulo, SP: Educ/Robe Editorial; 2003.
33. Coutinho CMLM, Magalhães FC, Araújo Jorge TC. Scanning electron microscope study of biofilm formation on different flow rates over metal surfaces using sulfate-reducing bacteria. *Biofouling.* 1993;7:19–27.
34. Taylor J. The estimation of members of bacteria by tenfold dilution serial. *J Appl Microbiol.* 1962;25:54–61.
35. Odom JM, Peck HD Jr. Hydrogenase, electron transfer proteins, and energy coupling in the sulfate-reducing bacteria *Desulfovibrio.* *Annu Rev Microbiol.* 1984;38:551–592.
36. Wagner M, Roger AJ, Flax JL, Brusseau GA, Stahl DA. Phylogeny of dissimilatory sulfite reductases supports an early origin of sulfate respiration. *J Bacteriol.* 1998;180:2975–2982.
37. Kondo J, Nedwell DB, Purdy KJ, Silva SQ. Detection and enumeration of sulphate-reducing bacteria in estuarine sediments by competitive PCR. *Geomicrobiol J.* 2004;21:145–157.
38. Medema MH, Breitling R, Takano E. Synthetic biology in *Streptomyces* bacteria. *Methods Enzymol.* 2011;497:485–502.
39. Christensen GD, Simpson WA, Younger JJ, et al. Adherence of coagulase-negative staphylococci to plastic tissue culture plates: a quantitative model for the adherence of staphylococci to medical devices. *J Clin Microbiol.* 1985;22:996–1006.
40. Stepanovic S, Vukovic D, Dakic I, Savic B, Svabic-Vlahovic M. A modified microtiter-plate test for quantification of staphylococcal biofilm formation. *J Microbiol Methods.* 2000;40:175–179.
41. Li X, Yan Z, Xu J. Quantitative variation of biofilms among strains in natural populations of *Candida albicans.* *Microbiology.* 2003;149:353–362.