

# SCIENTIFIC REPORTS



OPEN

## Antibacterial activity of a modified unfilled resin containing a novel polymerizable quaternary ammonium salt MAE-HB

Received: 12 May 2016  
Accepted: 04 September 2016  
Published: 23 September 2016


Li Huang<sup>1,\*</sup>, Fan Yu<sup>2,\*</sup>, Xiang Sun<sup>3,\*</sup>, Yan Dong<sup>2</sup>, Ping-ting Lin<sup>2</sup>, Hao-han Yu<sup>2</sup>, Yu-hong Xiao<sup>4</sup>, Zhi-guo Chai<sup>2</sup>, Xiao-dong Xing<sup>5</sup> & Ji-hua Chen<sup>2</sup>

Resins with strong and long-lasting antibacterial properties are critical for the prevention of secondary dental caries. In this study, we evaluated the antibacterial effect and the underlying mechanism of action of an unfilled resin incorporating 2-methacryloxyethyl hexadecyl methyl ammonium bromide (MAE-HB) against *Streptococcus mutans* UA159 (*S. mutans* UA159). MAE-HB was added into unfilled resin at 10 mass%, and unfilled resin without MAE-HB served as the control. Bacterial growth was inhibited on 10%-MAE-HB unfilled resin compared with the control at 1 d, 7 d, 30 d, or 180 d ( $P < 0.05$ ). The growth inhibitory effect was independent of the incubation time ( $P > 0.05$ ). No significant differences in the antibacterial activities of eluents from control versus 10%-MAE-HB unfilled resins were observed at any time point ( $P > 0.05$ ). The number of bacteria attached to 10%-MAE-HB unfilled resin was considerably lower than that to control. Fe-SEM and CLSM showed that 10%-MAE-HB unfilled resin disturbed the integrity of bacterial cells. Expression of the bacterial glucosyltransferases, *gtfB* and *gtfC*, was lower on 10%-MAE-HB unfilled resin compared to that on control ( $P < 0.05$ ). These data indicate that incorporation of MAE-HB confers unfilled resin with strong and long-lasting antibacterial effects against *S. mutans*.

Dental caries is one of the most prevalent infectious diseases in the world. Resins have been widely used for restoring decayed teeth mainly for their adhesive properties, better aesthetics, and reduced preparation size<sup>1–3</sup>. However, resin restorations are associated with higher failure rates owing to secondary caries<sup>2,4,5</sup>. The main shortcoming of resin-based materials is the potential for microleakage due to polymerization shrinkage, occlusal forces, and aging, thus enabling for bacterial invasion<sup>6</sup>. In addition, resins accumulate more dental plaque than other materials, which may increase the possibility of bacterial microleakage, leading to restoration failures and pulpal damage<sup>7,8</sup>. Therefore, resins with strong and long-lasting antibacterial properties are highly desirable.

Several approaches for endowing dental materials with antibacterial properties have been explored. Examples include modification of resins by addition of soluble antimicrobials such as fluoride, Ag, and chlorhexidine<sup>9,10</sup>. The addition of fluoride to resins has been applied widely owing to its beneficial effects in reducing demineralization, enhancing remineralization, and inhibiting microbial metabolism and plaque formation<sup>11</sup>. However, the release of fluoride may be not sufficient for a maximal antibacterial effect<sup>12</sup>. In the case of agent-releasing

<sup>1</sup>State Key Laboratory of Military Stomatology & National Clinical Research Centre for Oral Diseases & Shaanxi International Joint Research Center for Oral Diseases, Department of General Dentistry and Emergency, School of Stomatology, Fourth Military Medical University, Xi'an, Shaanxi, 710032, P. R. China. <sup>2</sup>State Key Laboratory of Military Stomatology & National Clinical Research Centre for Oral Diseases & Shaanxi key Laboratory of Stomatology, Department of Prosthodontics, School of Stomatology, Fourth Military Medical University, Xi'an, 710032, P. R. China. <sup>3</sup>State Key Laboratory of Military Stomatology & National Clinical Research Centre for Oral Diseases & Shaanxi Engineering Research Center for Dental Materials and Advanced Manufacture, Department of VIP Dental Care, School of Stomatology, Fourth Military Medical University, Xi'an, 710032, P. R. China. <sup>4</sup>Department of Stomatology, Kunming General Hospital of PLA, Kunming, 650032, P. R. China. <sup>5</sup>School of Chemical Engineering, Nanjing University of Science and Technology, Nanjing, 210094, P. R. China. \*These authors contributed equally to this work. Correspondence and requests for materials should be addressed to L.H. (email: 519huang@fmmu.edu.cn) or J.-h.C. (email: jhchen@fmmu.edu.cn)

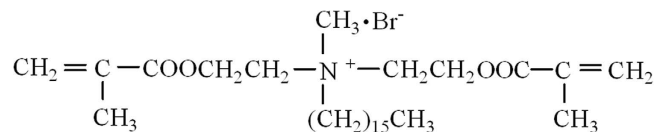

**Figure 1. Structure of the QAS monomer, MAE-HB.**

antibacterial resins, tight control of the release kinetics of the antimicrobials remains a challenge<sup>13</sup>, and the antibacterial activity of modified resins decreases with time<sup>14–16</sup>. Besides, the mechanical or physical properties of the parent resin may be compromised by the constant release of antibacterial agents. This is especially due to the porous surface that is formed during the release process, which may lead to poor wear resistance and increase the potential for staining and bacterial biofilm accumulation<sup>14</sup>. To overcome this issue, research groups have subsequently focused on the development of polymerizable antibacterial agents that are non-volatile.

12-Methacryloyloxy-dodecylpyridiniumbromide (MDPB) and methacryloxyethyl cetyl dimethyl ammonium chloride (DMAE-CB), which were developed by Imazato *et al.*<sup>17</sup> and by our research group<sup>18–20</sup>, can be chemically immobilized within resins. However, the amount of MDPB or DMAE-CB monomers incorporated into resin materials is limited<sup>19,21</sup>. This is because there is only one double bond in their molecular structures, and thus a limited amount of MDPB or DMAE-CB monomers can bind to the resin matrix during polymerization<sup>22</sup>.

To solve this problem, our group synthesized a novel polymerizable quaternary ammonium salt (QAS) monomer, MAE-HB, which has two double bonds<sup>22</sup>. MAE-HB exhibited strong bactericidal activities against *Streptococcus mutans*, *Actinomyces viscosus*, *Lactobacillus acidophilus*, *Staphylococcus aureus*, *Streptococcus sanguinis*, *Porphyromonas gingivalis*, *Prevotella melaninogenica*, and *Enterococcus faecalis*<sup>22</sup>. However, whether resins containing MAE-HB exhibit improved antibacterial activity compared to existing materials remains unclear. In this study, we added MAE-HB to an experimental light-curable unfilled dental resin, and investigated the antibacterial effects and the underlying mechanism of action of this composite.

## Methods

**Preparation of unfilled resins.** The structure of MAE-HB is presented in Fig. 1. The experimental light-curable unfilled resin consisted of 2,2-bis[4-(2-hydroxy-3-methacryloxypropoxy)phenyl] propane (Bis-GMA, Esstech, PA) and triethylene glycol dimethacrylate (TEGDMA, Esstech) with a mass ratio of 75:25. The photosensitizer camphorquinone (Esstech) was added at 0.5 wt%, and dimethylaminoethylmethacrylate (Sigma-Aldrich, St. Louis, MO) was added at 1 wt%. MAE-HB was added as an immobilized bactericide at 10 mass% (hereafter 10%-MAE-HB unfilled resin), and resin without MAE-HB (0%-MAE-HB unfilled resin) served as the control.

Unfilled resins were dropped into stainless steel moulds (10 mm in diameter and 3 mm in thickness). The top and bottom surfaces were covered with a polyester matrix and cured for 60 s with a light activation unit delivering 450 mW/cm<sup>2</sup> (Dentsply QHL71, Milford, DE). Then, the unfilled resins were sterilized with ethylene oxide gas, followed by degassing for 48 h.

**Bacterial strain and culture conditions.** *S. mutans* UA159 was cultured at 37 °C in brain heart infusion (BHI) broth (Difco, Detroit, MI) in an anaerobic atmosphere (90% N<sub>2</sub>, 5% CO<sub>2</sub>, and 5% H<sub>2</sub>). Then, the overnight culture was adjusted to 1 × 10<sup>5</sup> colony forming units (CFU)/ml for subsequent experiments.

**Antibacterial activity of immobilized MAE-HB.** The film contact method was used to evaluate the antibacterial activity of immobilized MAE-HB<sup>19</sup>. Unfilled resins were immersed in 2 ml distilled water at 37 °C for 1 d, 7 d, 30 d, or 180 d. The distilled water was changed daily. One hundred microliters of the bacterial suspension was dropped onto the specimen surface, which was then covered with a celluloid film and incubated at 37 °C for 24 h in an anaerobic atmosphere. Bacteria were collected by vortexing the specimen in 9.9 ml BHI for 2 min. The bacterial suspension was diluted 10-fold, and 100 μl of bacterial suspension was inoculated onto a BHI agar plate to quantify the number of CFU recovered. Five specimens were tested for each group.

**Antibacterial activity of released MAE-HB.** All specimens of 0%-MAE-DB and 10%-MAE-HB unfilled resin were immersed in 2 ml BHI at 37 °C for 1 d, 7 d, 30 d, or 180 d. The BHI was changed daily. The BHI at different immersion times was collected as the eluent and transferred to a 12-well plate. One hundred microliters of bacterial suspension was inoculated into the eluent and incubated at 37 °C for 24 h in an anaerobic atmosphere. Bacterial suspensions from each specimen were diluted 10-fold, and 100 μl was inoculated onto a BHI agar plate to quantify the number of CFU recovered. Five specimens were tested for each group.

**Fe-SEM observation.** All specimens of 0%-MAE-DB and 10%-MAE-HB unfilled resin were placed in a 24-well plate with 20 μl of bacterial suspension applied on the top. Two millilitres of BHI supplemented with 1% sucrose was added into each well after incubation at 37 °C for 1 h. After a further 4-h incubation, the specimens with biofilm were gently rinsed with distilled water and fixed in 2.5% glutaraldehyde in 0.1 mol/l cacodylate buffer at pH 7.2 for 4 h at room temperature. Specimens were then dehydrated in an ascending ethanol series with a critical-point drier. After being coated with gold using an ion sputter (JFC-1100E, JEOL, Japan), the central portion of the specimens was observed with Fe-SEM (S-4800, Hitachi, Tokyo, Japan).

Gene	Accession number	Forward primer sequences	Reverse primer sequences
<i>gtfB</i>	M17361	AGCAATGCAGCCAATCTACAAAT	ACGAACCTTGCCGTTATTGTCA
<i>gtfC</i>	M22054	CTCAACCAACCGCCACTGTT	GGTTTAAACGTCAAAATTAGCTGTATTAGC
<i>gtfD</i>	M29296	ACAGCAGACAGCAGCCAAGA	ACTGGGTTTGCTGCGTTTG
16S	X58303	CCTACGGGAGGCAGCAGTAG	CAACAGAGCTTTACGATCCGAAA

**Table 1.** Primer sequences used for qRT-PCR analysis.

**CLSM analysis of bacterial growth.** Specimens coated with *S. mutans* were prepared as described above and were analysed by CLSM<sup>23</sup>. After a 24-h incubation, the biofilm-coated disks were washed three times with sterile saline to remove loose bacteria, and the remaining bacteria were stained using the Live/Dead BacLight Bacterial Viability Kit (Cat. No. L7012, Molecular Probes, Eugene, OR, USA) with 15-min incubation in the dark at room temperature to allow stain development prior to image scanning. With this kit, live bacteria are stained by Syto 9 and produce green fluorescence, and bacteria with compromised membranes will be stained by propidium iodide and produce red fluorescence. The samples were rinsed gently with distilled water and observed by CLSM (FluoView FV1000, Olympus, Tokyo, Japan). Excitation with a 488-nm laser revealed the green fluorescence emission of live bacteria, and excitation with a 543-nm laser revealed the red fluorescence emission of bacteria with damaged membranes.

**Effects of MAE-HB unfilled resins on expression of glucosyltransferase B (*gtfB*), glucosyltransferase C (*gtfC*) and glucosyltransferase D (*gtfD*) in *S. mutans*.** Glucosyltransferase is mainly responsible for the synthesis of water-insoluble glucans, which promote the adhesion of *S. mutans* to teeth and dental materials<sup>24</sup>. Thus, we evaluated glucosyltransferase gene expression by real-time quantitative PCR<sup>25,26</sup>. Briefly, specimens were placed in a 6-well plate to generate biofilms for RNA analysis. One hundred microliters of *S. mutans* suspension was added to each well containing 5 ml BHI supplemented with 1% sucrose. After incubating in an anaerobic atmosphere at 37 °C for 24 h, the unfilled resins were rinsed with phosphate buffered saline (PBS: 0.01 M, pH 7.2) to remove unattached cells, and *S. mutans* attached to the surface of specimens was collected for RNA extraction<sup>27</sup>. For cDNA synthesis, RNA was reverse transcribed using a QuantScript RT Kit (Tiangen Biotech Co., Beijing, China). Real-time quantitative PCR was employed to determine gene expression in a ABI7500 Real-Time PCR System (Applied Biosystems, Foster City, CA) using SYBR Green RealMasterMix (Tiangen Biotech CO., Beijing, China) according to the manufacturer's instructions. The primers for real-time PCR are shown in Table 1. Gene expression was normalized to 16S rRNA. Five separate experiments were performed for each group.

**Statistical analysis.** The antibacterial activities of immobilized MAE-HB and released MAE-HB at different immersion times were compared by Kruskal–Wallis H test and Mann–Whitney U test. Real-time RT-PCR results were analysed using a two-sample t-test. Statistical analyses were performed with SPSS 14.0 software and significance level was set at  $P < 0.05$ .

## Results


**Antibacterial activity of immobilized MAE-HB.** The antibacterial activities of 0%- and 10%-MAE-HB unfilled resins at different immersion times are shown in Fig. 2A,B, respectively. Compared with the control group, bacterial growth was suppressed significantly on 10%-MAE-HB unfilled resins at 1 d, 7 d, 30 d, or 180 d ( $P < 0.05$ ). The time of incubation with the 10%-MAE-HB unfilled resins had no significant difference on antibacterial activity ( $P > 0.05$ ).

**Antibacterial activity of released MAE-HB.** The antibacterial activities of eluents from 0%- and 10%-MAE-HB unfilled resins are shown in Fig. 2C,D, respectively. No significant differences were found between the two groups at any time point ( $P > 0.05$ ).

**Fe-SEM observation.** The Fe-SEM observations show that, after anaerobic growth at 37 °C for 4 h, a significant amount of *S. mutans* accumulated on the surface of 0%-MAE-HB unfilled resin (Fig. 3A). In contrast, a small amount of *S. mutans* was found on the surface of 10%-MAE-HB unfilled resin (Fig. 3B). High magnification images revealed a normal morphology of *S. mutans* on 0%-MAE-HB unfilled resin (Fig. 3C), but a disturbed integrity of bacterial cells on 10%-MAE-HB unfilled resin (Fig. 3D).

**CLSM analysis of bacterial growth.** Representative live/dead staining CLSM images of the adherent biofilms on resin disks are shown in Fig. 4. The specimen of the 0%-MAE-HB unfilled resin was fully covered by primarily live bacteria (green), whereas the 10%-MAE-HB unfilled resin showed a lower density of cells and a greater proportion of dead bacteria (red).

**Effects of MAE-HB unfilled resins on expression of glucosyltransferase B (*gtfB*), glucosyltransferase C (*gtfC*) and glucosyltransferase D (*gtfD*) in *S. mutans*.** Figure 5 shows the expression of *gtfB*, *gtfC*, and *gtfD* in *S. mutans* biofilms attached to 0%- and 10%-MAE-HB unfilled resins. Both *gtfB* and *gtfC* expression on the 10%-MAE-HB unfilled resin was lower than that of the control group ( $P < 0.05$ ), while no significant difference was found with respect to *gtfD* expression ( $P > 0.05$ ).

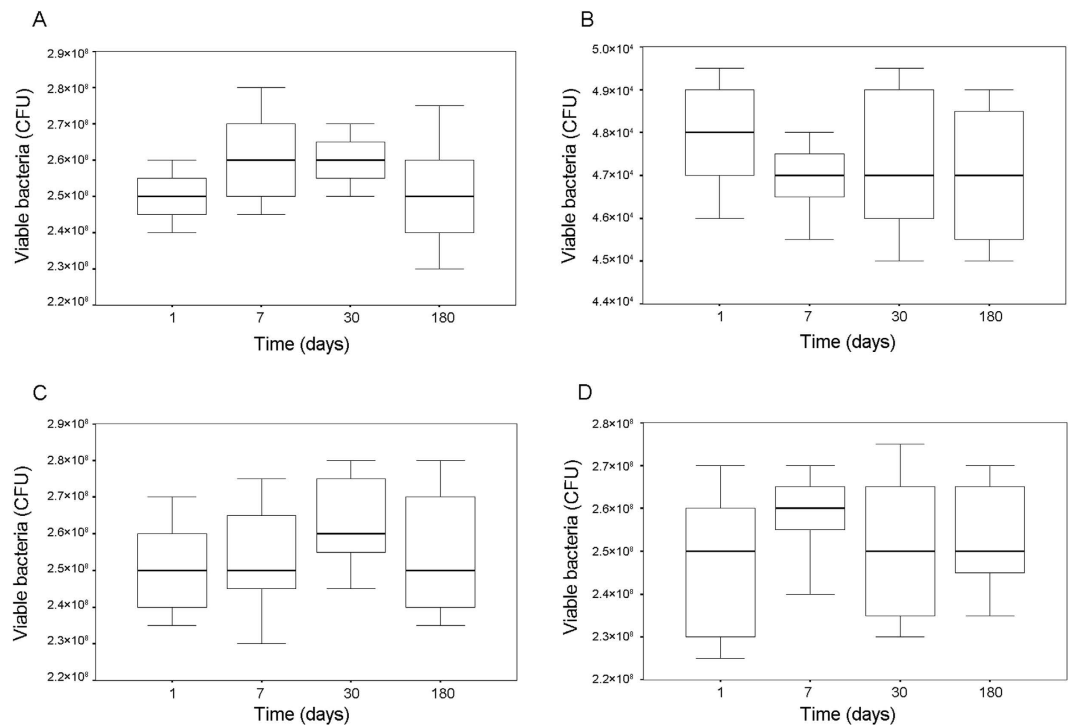

**Figure 2. Antibacterial activities of immobilized MAE-HB and released MAE-HB after different immersion times.** (A) The antibacterial activities of 0%-MAE-HB unfilled resins. (B) The antibacterial activities of 10%-MAE-HB unfilled resins. (C) The antibacterial activities of eluents from 0%-MAE-HB unfilled resins. (D) The antibacterial activities of eluents from 10%-MAE-HB unfilled resins.

## Discussion

Shrinkage of resins during the polymerization process is the main cause of secondary caries<sup>6</sup>. However, bacterial antigens and metabolic by-products can also diffuse through gaps between the resin and tooth, and may thereby lead to pulpal inflammation and infection<sup>28,29</sup>. Therefore, resins must be endowed with strong and long-lasting antibacterial properties in order to reduce the occurrence of secondary caries and protect pulp health.


Current antibacterial resin materials can be divided into agent-releasing and non-agent-releasing subtypes<sup>22</sup>. Soluble antimicrobials can easily be incorporated into resins to endow them with antibacterial activity. However, antibacterial agents are simply dispersed in resin matrix, and therefore their efficacy decreases with time. It is difficult to control the kinetics of release and, further exacerbating the problem, the release of soluble antimicrobials may exhibit unwanted side-effects against surrounding tissues and compromise the mechanical properties of composites<sup>15,28–30</sup>.

Non-agent-releasing antibacterial materials have been developed to overcome the disadvantages of agent-releasing antibacterial materials. A promising candidate is polymerizable QAS, which can polymerize with resin matrix, and exerts long-lasting antibacterial activity against a wide range of bacteria, fungi, and viruses<sup>17,22</sup>. Two typical examples of polymerizable QAS are MDPB, which was developed by Imazato *et al.*<sup>17</sup>, and DMAE-CB<sup>31</sup>, which was developed by our research group. These materials contain MDPB and DMAE-CB monomers that are chemically bound to the resin matrix, from where they exert stable antibacterial activity. However, there is only one double bond in the chemical structures of MDPB and DMAE-CB; thus only a small amount of MDPB and DMAE-CB can polymerize with the resin matrix, which limits their antibacterial activities<sup>19,21</sup>.


To increase the amount of polymerizable antibacterial monomer incorporated into resin materials, our research group developed the novel polymerizable QAS monomer, MAE-HB. The MAE-HB monomer contains two double bonds and can therefore polymerize with resin matrix more completely than previous substrates. MAE-HB exhibits strong bactericidal action against oral bacteria, and is rapidly bactericidal against *S. mutans*. At a concentration of 48.8 mg/ml ( $4 \times$  MBC), MAE-HB kills 99.99% of *S. mutans* within 1 min of incubation, and no viable bacteria are detected after 30 min<sup>22</sup>. Thus, MAE-HB is a good candidate for conferring antibacterial properties upon resin materials.

*S. mutans* is one of the major pathogens responsible for human dental caries, and is therefore often used for investigations into the antibacterial effects of modified unfilled resins<sup>19</sup>. Our current study indicates that 10%-MAE-HB unfilled resins have strong antibacterial effects against *S. mutans*, even after immersion in water for 180 days. In order to verify that the strong and long-lasting antibacterial effect was due to immobilized MAE-HB rather than released material, the eluent from 10%-MAE-HB unfilled resins was compared with that of control at all time points. The eluent had no antibacterial activity, and virtually no MAE-HB monomer was released from unfilled resins, even after immersion in water for 180 days. Thus, we infer that the quaternary ammonium group



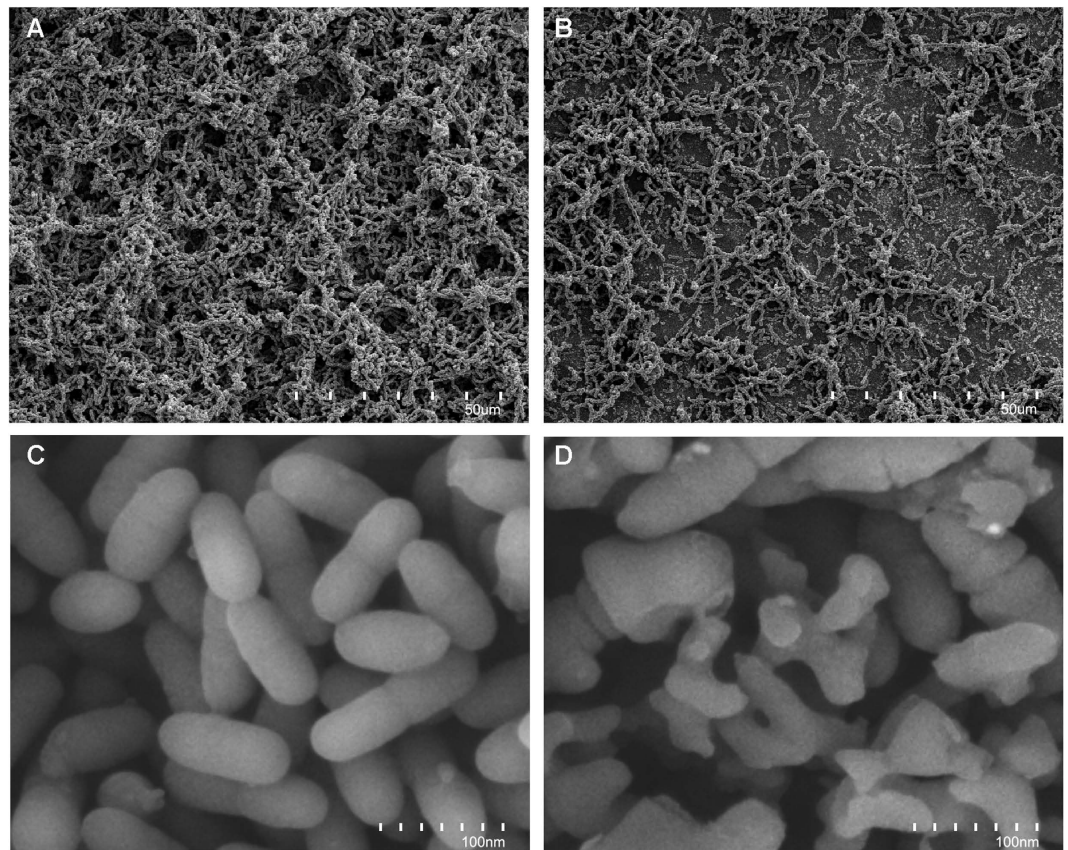


**Figure 3.** Fe-SEM images of *S. mutans* accumulation after anaerobic inoculation with (A) 0%- MAE-HB unfilled resin and (B) 10%-MAE-HB unfilled resin. Fe-SEM images of *S. mutans* morphology after anaerobic inoculation with (C) 0%- MAE-HB unfilled resin and (D) 10%-MAE-HB unfilled resin.

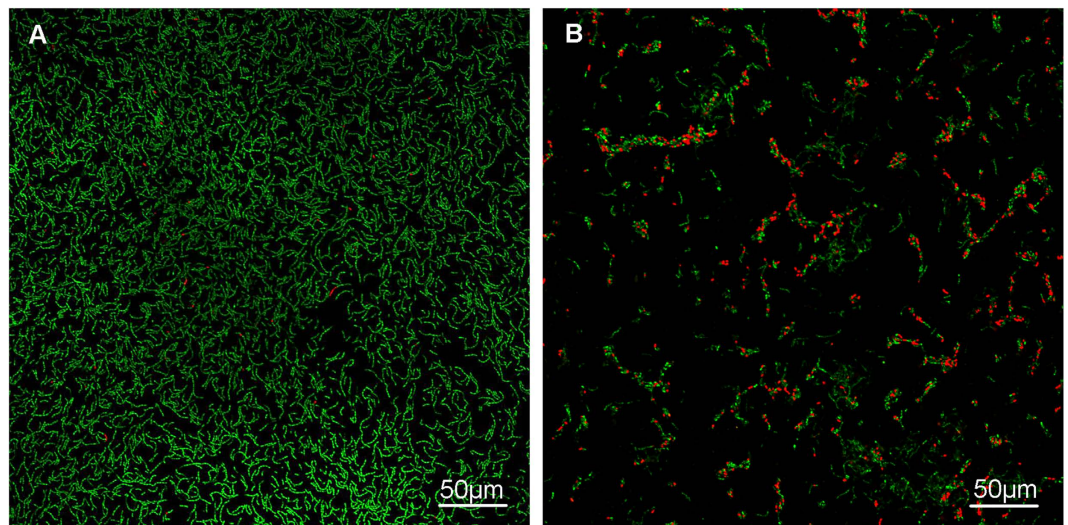

**Figure 4.** Representative confocal laser-scanning microscope (CLSM) images of live/dead-stained *S. mutans* after anaerobic inoculation with (A) 0%- MAE-HB unfilled resin and (B) 10%-MAE-HB unfilled resin. Live bacteria exhibited green fluorescence, and bacteria with compromised membranes exhibited red fluorescence. Scale bars, 50  $\mu\text{m}$ .

endowed the MAE-HB monomer with strong antibacterial activity, and that the dimethacrylate groups helped immobilize MAE-HB monomers in the resin matrix through covalent bonding after curing<sup>26</sup>.

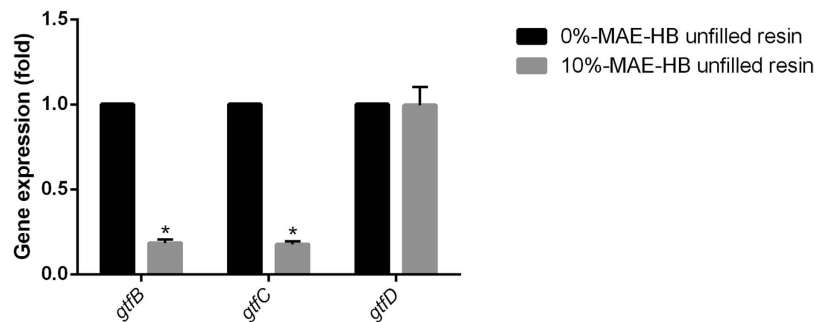

**Figure 5.** The expression of *gtfB*, *gtfC*, and *gtfD* by *S. mutans* on 0%- and 10%-MAE-HB unfilled resins. “\*” denotes statistical significance ( $P < 0.05$ ).

The Fe-SEM findings and CLSM findings were concordant, as they revealed that the death induced by the 10%-MAE-HB unfilled resin correlated with profound perturbations to bacterial morphology. Polymerizable QAS exhibits antibacterial activity due to its ability to adsorb negatively charged bacterial cells onto a positively charged quaternary amine  $N^+$ <sup>32–34</sup>. This process may contribute to the disruption of cell membranes, disturb the electric balance, and subsequently lead increased cell permeability, which ultimately may cause bacterial cell lysis<sup>32–36</sup>.

*S. mutans* produces glucosyltransferases, and subsequently synthesizes glucans *in situ*, which provides binding sites for cariogenic microorganisms, leading to dental plaque formation<sup>24,37</sup>. In addition, glucosyltransferases adsorbed to the surfaces of other oral microorganisms may convert them to glucan producers<sup>24</sup>. At least 3 *gtf* genes are involved in this process; *gtfB* encodes GTFB enzyme that synthesizes primarily insoluble glucan, *gtfC* encodes GTFC enzyme that produce a mixture of soluble and insoluble glucans, and *gtfD* encodes GTFD enzyme that forms predominantly soluble glucans<sup>37</sup>. Among them, the activities of GTFB and GTFC are the most important for building the biofilm structure<sup>38,39</sup> and water-insoluble glucans are the main composition of extracellular polysaccharides in dental biofilm, while GTFD serve as primers for GTFB and as a reserve source of energy and contribute in part at least to the low pH values observed in cariogenic plaque<sup>37,40–42</sup>. Decreased expression of *gtf* genes could reduce glucan synthesis, which would in turn reduce bacterial adhesion<sup>25</sup>.

In the present study, we found that *gtfBC* expression was significantly lower in the presence of 10%-MAE-HB unfilled resin, while *gtfD* expression was unaffected. Consistent with this, another QAS monomer, methacryloxyethyl cetyl dimethyl ammonium chloride (DMAE-CB), also has an inhibitory effect on the expression of these enzymes in *S. mutans* biofilms<sup>25</sup>. *gtf* gene expression can be influenced by a variety of reasons, such as carbohydrate availability and source, environmental pH, and growth phase/rate<sup>43–47</sup>. Thus we speculate that the suppression of *gtfBC* may be related to the chemical structure of QAS, and we suggest that the cationic moiety of MAE-HB could attract negatively charged exopolysaccharides of *S. mutans*. This may alter the physicochemical properties of the exopolysaccharide and the milieu for bacterial growth, which in turn could inhibit *gtfB* and *gtfC* expression<sup>25,37</sup>. Besides, previous studies have shown that the *gtfB* and *gtfC* genes are in an operon-like arrangement and may have a common promoter and appear to be coordinately expressed<sup>43</sup>. *gtfD* gene is located upstream of *gtfBC* loci, presents an independent promoter and may be regulated in a manner opposite that of *gtfB* and *gtfC*<sup>48,49</sup>. Thus we speculate that, *gtfB* and *gtfC* can be cotranscribed and be subjected to the same regulatory mechanisms when MAE-HB is present, as described in other studies<sup>48,50–52</sup>. Moreover, Ooshima *et al.*<sup>53</sup> found that when the level of bacterial adherence was associated with the ratio of 3 different GTFs. Taken together, the reduced *gtfBC* expression and unaltered *gtfD* expression by 10%-MAE-HB unfilled resin would alter the ratio of GTFs, hence disturbing glucan synthesis, preventing biofilm attachment and cariogenic bacteria accumulation.

In summary, this study indicates that the incorporation of MAE-HB endows unfilled resins with strong and long-lasting antibacterial effects against *S. mutans*, and could therefore play an important role in preventing the occurrence of secondary caries. This antibacterial effect was mainly caused by the positively charged quaternary amine  $N^+$  within MAE-HB. In addition, 10%-MAE-HB unfilled resin inhibits bacterial adhesion by modulating the expression of glucosyltransferases. This might facilitate the inhibition of caries via blockade of cariogenic biofilm accumulation. We suggest that MAE-HB is a promising candidate for incorporation in to dental resins with potent antibacterial activity.

## References

- Svanberg, M., Mjor, I. A. & Orstavik, D. Mutans streptococci in plaque from margins of amalgam, composite, and glass-ionomer restorations. *Journal of dental research* **69**, 861–864 (1990).
- Demarco, F. E., Correa, M. B., Cenci, M. S., Moraes, R. R. & Opdam, N. J. Longevity of posterior composite restorations: not only a matter of materials. *Dental materials: official publication of the Academy of Dental Materials* **28**, 87–101, doi: 10.1016/j.dental.2011.09.003 (2012).
- Da Rosa Rodolpho, P. A. *et al.* 22-Year clinical evaluation of the performance of two posterior composites with different filler characteristics. *Dental materials: official publication of the Academy of Dental Materials* **27**, 955–963, doi: 10.1016/j.dental.2011.06.001 (2011).
- Bernardo, M. *et al.* Survival and reasons for failure of amalgam versus composite posterior restorations placed in a randomized clinical trial. *Journal of the American Dental Association* **138**, 775–783 (2007).

5. Soncini, J. A., Maserejian, N. N., Trachtenberg, F., Tavares, M. & Hayes, C. The longevity of amalgam versus compomer/composite restorations in posterior primary and permanent teeth: findings From the New England Children's Amalgam Trial. *Journal of the American Dental Association* **138**, 763–772 (2007).
6. Jandt, K. D. & Sigusch, B. W. Future perspectives of resin-based dental materials. *Dental materials: official publication of the Academy of Dental Materials* **25**, 1001–1006, doi: 10.1016/j.dental.2009.02.009 (2009).
7. Cooper, P. R. *et al.* Inflammation-regeneration interplay in the dentine-pulp complex. *Journal of dentistry* **38**, 687–697, doi: 10.1016/j.jdent.2010.05.016 (2010).
8. Brunthaler, A., Konig, F., Lucas, T., Sperr, W. & Schedle, A. Longevity of direct resin composite restorations in posterior teeth. *Clinical oral investigations* **7**, 63–70, doi: 10.1007/s00784-003-0206-7 (2003).
9. Carey, C. M. Focus on Fluorides: Update on the Use of Fluoride for the Prevention of Dental Caries. *Journal of Evidence Based Dental Practice* **14**, 95–102 (2014).
10. Memarpour, M. & Shafiei, F. The effect of antibacterial agents on fissure sealant microleakage: a 6-month *in vitro* study. *Oral Health & Preventive Dentistry* **12**, 149–155 (2014).
11. Wiegand, A., Buchalla, W. & Attin, T. Review on fluoride-releasing restorative materials--fluoride release and uptake characteristics, antibacterial activity and influence on caries formation. *Dental Materials* **23**, 343–362 (2007).
12. Cury, J. A., Oliveira, B. H. D., Santos, A. P. P. D. & Tenuta, L. M. A. Are fluoride releasing dental materials clinically effective on caries control? *Dental Materials Official Publication of the Academy of Dental Materials* **32**, 323–333 (2016).
13. Itota, T., Carrick, T. E., Yoshiyama, M. & Mccabe, J. F. Fluoride release and recharge in giomer, compomer and resin composite. *Dental Materials Official Publication of the Academy of Dental Materials* **20**, 789–795 (2004).
14. Imazato, S. Antibacterial properties of resin composites and dentin bonding systems. *Dental materials: official publication of the Academy of Dental Materials* **19**, 449–457 (2003).
15. Leung, D. *et al.* Chlorhexidine-releasing methacrylate dental composite materials. *Biomaterials* **26**, 7145–7153, doi: 10.1016/j.biomaterials.2005.05.014 (2005).
16. Huang, Q. T. *et al.* Physical and chemical properties of an antimicrobial Bis-GMA free dental resin with quaternary ammonium dimethacrylate monomer. *Journal of the mechanical behavior of biomedical materials* **56**, 68–76, doi: 10.1016/j.jmbbm.2015.10.028 (2016).
17. Imazato, S. *et al.* Bactericidal activity and cytotoxicity of antibacterial monomer MDPB. *Biomaterials* **20**, 899–903 (1999).
18. Xiao, Y. H. *et al.* Antibacterial activity and bonding ability of an adhesive incorporating an antibacterial monomer DMAE-CB. *Journal of biomedical materials research Part B, Applied biomaterials* **90**, 813–817, doi: 10.1002/jbm.b.31350 (2009).
19. Li, F. *et al.* Effects of a dental adhesive incorporating antibacterial monomer on the growth, adherence and membrane integrity of *Streptococcus mutans*. *Journal of dentistry* **37**, 289–296, doi: 10.1016/j.jdent.2008.12.004 (2009).
20. Jiao, Y. *et al.* N-Acetyl Cysteine (NAC)-Directed Detoxification of Methacryloyloxyethyl Cetyl Ammonium Chloride (DMAE-CB). *PLoS one* **10**, e0135815, doi: 10.1371/journal.pone.0135815 (2015).
21. Ebi, N., Imazato, S., Noiri, Y. & Ebisu, S. Inhibitory effects of resin composite containing bactericide-immobilized filler on plaque accumulation. *Dental materials: official publication of the Academy of Dental Materials* **17**, 485–491 (2001).
22. Huang, L. *et al.* Antibacterial activity and cytotoxicity of two novel cross-linking antibacterial monomers on oral pathogens. *Archives of oral biology* **56**, 367–373, doi: 10.1016/j.archoralbio.2010.10.011 (2011).
23. Yang, Y. *et al.* *In vitro* antibacterial activity of a novel resin-based pulp capping material containing the quaternary ammonium salt MAE-DB and Portland cement. *PLoS one* **9**, e112549, doi: 10.1371/journal.pone.0112549 (2014).
24. Bowen, W. H. & Koo, H. Biology of *Streptococcus mutans*-derived glucosyltransferases: role in extracellular matrix formation of cariogenic biofilms. *Caries Research* **45**, 69–86 (2010).
25. Li, F. *et al.* Anti-biofilm effect of dental adhesive with cationic monomer. *Journal of dental research* **88**, 372–376, doi: 10.1177/0022034509334499 (2009).
26. Huang, L. *et al.* Antibacterial effect of a resin incorporating a novel polymerizable quaternary ammonium salt MAE-DB against *Streptococcus mutans*. *Journal of biomedical materials research Part B, Applied biomaterials* **100**, 1353–1358, doi: 10.1002/jbm.b.32703 (2012).
27. Cury, J. A. & Koo, H. Extraction and purification of total RNA from *Streptococcus mutans* biofilms. *Analytical biochemistry* **365**, 208–214, doi: 10.1016/j.ab.2007.03.021 (2007).
28. Chin-Lo, H. & Liewehr, F. R. Relationships between caries bacteria, host responses, and clinical signs and symptoms of pulpitis. *Journal of endodontics* **33**, 213–219 (2007).
29. Bergenholtz, G. Evidence for bacterial causation of adverse pulpal responses in resin-based dental restorations. *Critical reviews in oral biology and medicine: an official publication of the American Association of Oral Biologists* **11**, 467–480 (2000).
30. Jedrychowski, J. R., Caputo, A. A. & Kerper, S. Antibacterial and mechanical properties of restorative materials combined with chlorhexidines. *Journal of oral rehabilitation* **10**, 373–381 (1983).
31. Xiao, Y. H. *et al.* Antibacterial effects of three experimental quaternary ammonium salt (QAS) monomers on bacteria associated with oral infections. *Journal of oral science* **50**, 323–327 (2008).
32. Beyth, N., Yudovin-Farber, I., Ran, B., Domb, A. J. & Weiss, E. I. Antibacterial activity of dental composites containing quaternary ammonium polyethylenimine nanoparticles against *Streptococcus mutans*. *Biomaterials* **27**, 3995–4002 (2006).
33. Namba, N., Yoshida, Y. & Nagaoka, N. Antibacterial effect of bactericide immobilized in resin matrix. *Dental Materials Official Publication of the Academy of Dental Materials* **25**, 424–430 (2009).
34. Li, F., Weir, M. D. & Xu, H. H. K. Effects of quaternary ammonium chain length on antibacterial bonding agents. *Journal of dental research* **92**, 932–938 (2013).
35. Yoshimatsu, T. & Hiyama, K. Mechanism of the action of didecyltrimethylammonium chloride (DDAC) against *Escherichia coli* and morphological changes of the cells. *Biocontrol science* **12**, 93–99 (2007).
36. Sumitomo, T., Nagamune, H., Maeda, T. & Kourai, H. Correlation between the bacteriostatic action of a bis-quaternary ammonium compound and outer membrane proteins. *Biocontrol science* **11**, 115–124 (2006).
37. Kuramitsu, H. K. Virulence factors of *Streptococcus mutans*: role of molecular genetics. *Critical Reviews in Oral Biology & Medicine* **4**, 159–176 (1993).
38. Tamesada, M., Kawabata, S., Fujiwara, T. & Hamada, S. Synergistic Effects of Streptococcal Glucosyltransferases on Adhesive Biofilm Formation. *Journal of dental research* **83**, 874–879 (2004).
39. Kalesinskas, P., Kačergius, T., Ambrozaitis, A., Pečiulienė, V. & Ericson, D. Reducing dental plaque formation and caries development. A review of current methods and implications for novel pharmaceuticals. *Stomatologija/issued by public institution "Odontologijos studija" ... [et al.]* **16**, 44–52 (2014).
40. Bowen, W. H. & Koo, H. Biology of *Streptococcus mutans*-derived glucosyltransferases: role in extracellular matrix formation of cariogenic biofilms. *Caries Research* **45**, 69–86 (2011).
41. Leme, A. F. P., Koo, H., Bellato, C. M., Bedi, G. & Cury, J. A. The Role of Sucrose in Cariogenic Dental Biofilm Formation—New Insight. *Journal of dental research* **85**, 878–887 (2006).
42. Critchley, P., Wood, J. M., Saxton, C. A. & Leach, S. A. The polymerisation of dietary sugars by dental plaque. *Caries Research* **1**, 112–129 (1967).
43. Goodman, S. D. & Qian, G. Characterization of the *gtfB* and *gtfC* Promoters from *Streptococcus mutans* GS-5. *Plasmid* **43**, 85–98 (2000).



44. Li, Y. & Burne, R. A. Regulation of the *gtfBC* and *ftf* genes of *Streptococcus mutans* in biofilms in response to pH and carbohydrate. *Microbiology* **147**, 2841–2848 (2001).
45. Fujiwara, T., Hoshino, T., Ooshima, T. & Hamada, S. Differential and quantitative analyses of mRNA expression of glucosyltransferases from *Streptococcus mutans* MT8148. *Journal of dental research* **81**, 109–113 (2002).
46. Koo, H., Falsetta, M. L. & Klein, M. I. The Exopolysaccharide Matrix: A Virulence Determinant of Cariogenic Biofilm. *Journal of dental research* **92**, 1065–1073 (2013).
47. Shemesh, M. & Feldman, T. M. Differential expression profiles of *Streptococcus mutans* *ftf*, *gtf* and *vic R* genes in the presence of dietary carbohydrates at early and late exponential growth phases. *Carbohydrate Research* **341**, 2090–2097 (2006).
48. Wexler, D. L., Hudson, M. C. & Burne, R. A. *Streptococcus mutans* fructosyltransferase (*ftf*) and glucosyltransferase (*gtfBC*) operon fusion strains in continuous culture. *Infection & Immunity* **61**, 1259–1267 (1993).
49. Fujiwara, T. *et al.* Molecular analyses of glucosyltransferase genes among strains of *Streptococcus mutans*. *Fems Microbiology Letters* **161**, 331–336 (1998).
50. Ueda, S., Shiroza, T. & Kuramitsu, H. K. Sequence analysis of the *gtfC* gene from *Streptococcus mutans* GS-5. *Journal of Bacteriology* **69**, 101–109 (1988).
51. Hudson, M. C. & Rd, C. R. Regulation of expression of *Streptococcus mutans* genes important to virulence. *Infection & Immunity* **58**, 464–470 (1990).
52. Yoshida, A., Ansai, T., Takehara, T. & Kuramitsu, H. K. LuxS-based signaling affects *Streptococcus mutans* biofilm formation. *Applied & Environmental Microbiology* **71**, 2372–2380 (2005).
53. Ooshima, T. *et al.* Contributions of three glycosyltransferases to sucrose-dependent adherence of *Streptococcus mutans*. *Journal of dental research* **80**, 1672–1677 (2001).

## Acknowledgements

Supported by Grants 81130078, 81470773, 81371187 from National Natural Science Foundation of China, Grants 2016JM8086, 2016JQ8008 from Natural Science Foundation of Shaanxi Province and Program for Changjiang Scholars and Innovative Research Team in University (No. IRT13051).

## Author Contributions

L.H., F.Y. and X.S. performed the experiments and analytical part of the study and wrote the manuscript. Y.D., P.-t.L. and H.-h.Y. contributed to the specimen preparation. Y.-h.X., Z.-g.C. and X.-d.X. advised on the experimental design and edited the manuscript. J.-h.C. supervised the project and edited the manuscript. All authors reviewed the manuscript.

## Additional Information

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Huang, L. *et al.* Antibacterial activity of a modified unfilled resin containing a novel polymerizable quaternary ammonium salt MAE-HB. *Sci. Rep.* **6**, 33858; doi: 10.1038/srep33858 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016