

Poly[[diaquabis(μ -oxalato- $\kappa^4O^1,O^2;O^{1'}O^{2'}$)bis(μ_3 -5-oxidopyridin-1-ium-3-carboxylato- $\kappa^3O^3;O^{3'}O^{5'}$)-diholmium(III)] dihydrate]

Jun-Long Mi, Jing Huang and Hong-Ji Chen*

Department of Materials Science and Engineering, Jinan University, Guangzhou 510632, People's Republic of China

Correspondence e-mail: thjchen@jnu.edu.cn


Received 26 June 2012; accepted 20 July 2012

Key indicators: single-crystal X-ray study; $T = 173$ K; mean $\sigma(C-C) = 0.004$ Å; R factor = 0.016; wR factor = 0.038; data-to-parameter ratio = 12.0.

In the title compound, $\{[Ho_2(C_6H_4NO_3)_2(C_2O_4)_2(H_2O)_2] \cdot 2H_2O\}_n$, the Ho^{III} atom is coordinated by three O atoms from three 5-hydroxynicotinate ligands, four O atoms from two oxalate ligands, each lying on an inversion center, and one water molecule in a distorted square-antiprismatic geometry. The 5-hydroxynicotinate ligand is protonated at the N atom and deprotonated at the hydroxy group. The Ho^{III} atoms are bridged by the carboxylate and phenolate O atoms, forming a three-dimensional framework. N—H···O and O—H···O hydrogen bonds, as well as π – π interactions between the pyridine rings [centroid–centroid distance = 3.794 (2) Å], are observed.

Related literature

For background to the applications of compounds with metal-organic framework structures, see: Allendorf *et al.* (2009); Choi *et al.* (2008); Dang *et al.* (2010); Ishikawa *et al.* (2005); Lazare *et al.* (2010); Shimomura *et al.* (2010); Thallapally *et al.* (2010). For related structures, see: Zhang *et al.* (2012).

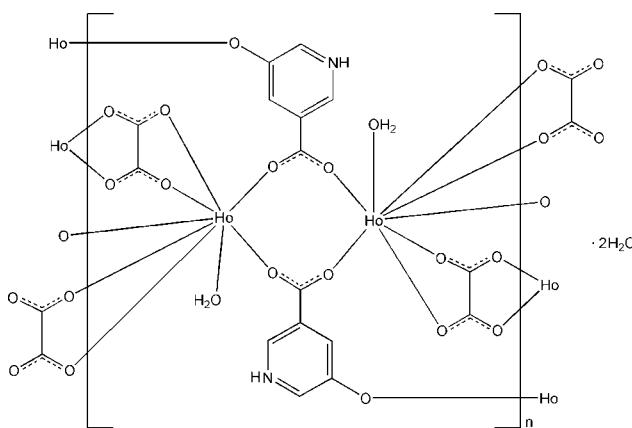

Experimental

Crystal data

$[Ho_2(C_6H_4NO_3)_2(C_2O_4)_2(H_2O)_2] \cdot 2H_2O$	$\beta = 96.862$ (3)°
$M_r = 854.16$	$\gamma = 95.770$ (3)°
Triclinic, $P\bar{1}$	$V = 545.8$ (2) Å ³
$a = 7.7786$ (16) Å	$Z = 1$
$b = 8.0562$ (17) Å	Mo $K\alpha$ radiation
$c = 9.505$ (2) Å	$\mu = 7.30$ mm ^{−1}
$\alpha = 110.912$ (3)°	$T = 173$ K
	$0.18 \times 0.16 \times 0.06$ mm

Data collection

Bruker APEXII CCD diffractometer	4550 measured reflections
Absorption correction: multi-scan (<i>SADABS</i> ; Sheldrick, 1996)	2295 independent reflections
$T_{\min} = 0.354$, $T_{\max} = 0.669$	2160 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.017$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.016$	H atoms treated by a mixture of independent and constrained refinement
$wR(F^2) = 0.038$	$\Delta\rho_{\max} = 0.57$ e Å ^{−3}
$S = 1.05$	$\Delta\rho_{\min} = -0.49$ e Å ^{−3}
2295 reflections	
192 parameters	
5 restraints	

Table 1
Hydrogen-bond geometry (Å, °).

$D\cdots H\cdots A$	$D\cdots H$	$H\cdots A$	$D\cdots A$	$D\cdots H\cdots A$
N1—H1···O7 ⁱ	0.90 (1)	1.83 (1)	2.727 (3)	171 (3)
O8—H7···O9 ⁱⁱ	0.85 (1)	1.95 (1)	2.787 (4)	171 (5)
O8—H8···O4 ⁱⁱⁱ	0.85 (1)	1.96 (1)	2.811 (3)	177 (6)
O9—H9···O3 ^{iv}	0.85 (1)	2.08 (1)	2.929 (4)	178 (6)
O9—H10···O1 ⁱⁱ	0.85 (1)	2.48 (6)	3.003 (4)	120 (5)

Symmetry codes: (i) $-x + 2, -y + 2, -z + 1$; (ii) $-x + 1, -y + 2, -z + 1$; (iii) $-x + 1, -y + 2, -z + 2$; (iv) $-x + 1, -y + 1, -z + 1$.

Data collection: *APEX2* (Bruker, 2007); cell refinement: *SAINT* (Bruker, 2007); data reduction: *SAINT*; program(s) used to solve structure: *SHELXTL* (Sheldrick, 2008); program(s) used to refine structure: *SHELXTL*; molecular graphics: *DIAMOND* (Brandenburg, 1999); software used to prepare material for publication: *SHELXTL*.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HY2567).

References

- Allendorf, M. D., Bauer, C. A., Bhakta, R. K. & Houk, R. J. T. (2009). *Chem. Soc. Rev.* **38**, 1330–1352.
- Brandenburg, K. (1999). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Bruker (2007). *APEX2* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Choi, H. J., Dinca, M. & Long, J. R. (2008). *J. Am. Chem. Soc.* **130**, 7848–7850.
- Dang, D. B., Wu, P. Y., He, C., Xie, Z. & Duan, C. Y. (2010). *J. Am. Chem. Soc.* **132**, 14321–14323.
- Ishikawa, N., Sugita, M. & Wernsdorfer, W. (2005). *Angew. Chem. Int. Ed.* **44**, 2931–2935.
- Lazare, S., Bazer-Bachi, D., Bonnier, F., Lecocq, V., Soyer, E., Quoineaud, A. A. & Bats, N. (2010). *J. Am. Chem. Soc.* **132**, 12365–12377.
- Sheldrick, G. M. (1996). *SADABS*. University of Göttingen, Germany.
- Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.

- Shimomura, S., Higuchi, M., Matsuda, R., Yoneda, K., Hijikata, Y., Kubota, Y., Mita, Y., Kim, J., Takata, M. & Kitagawa, S. (2010). *Nat. Chem.* **2**, 633–637.
- Thallapally, P. K., Fernandez, C. A., Motkuri, R. K., Nune, S. K., Liu, J. & Peden, C. H. F. (2010). *Dalton Trans.* **39**, 1692–1694.
- Zhang, J., Huang, J., Yang, J. & Chen, H.-J. (2012). *Inorg. Chem. Commun.* **17**, 163–168.

supplementary materials

Acta Cryst. (2012). E68, m1146–m1147 [doi:10.1107/S1600536812032916]

Poly[[diaqua $\text{bis}(\mu\text{-oxalato-}\kappa^4\text{O}^1,\text{O}^2:\text{O}^1,\text{O}^2)\text{bis}(\mu_3\text{-5-oxidopyridin-1-iun-3-carboxylato-}\kappa^3\text{O}^3:\text{O}^3:\text{O}^5)\text{diholmium(III)}]$] dihydrate]

Jun-Long Mi, Jing Huang and Hong-Ji Chen

Comment

Metal-organic frameworks (MOFs) remain nowadays one of the most studied topics in synthetic chemistry due to MOFs hold interesting structural features and properties. For example, they can be employed as effective heterogeneous catalysts (Dang *et al.*, 2010; Lazare *et al.*, 2010; Thallapally *et al.*, 2010), selective adsorption of gases (Choi *et al.*, 2008; Shimomura *et al.*, 2010), photoluminescent (Allendorf *et al.*, 2009) and magnetic properties (Ishikawa *et al.*, 2005).

The title compound is isostructural with its Dy(III) and Er(III) analogues (Zhang *et al.*, 2012). As shown in Fig. 1, the asymmetric unit is composed of one Ho^{III} atom, one phenoxyconicinate ligand, two halves of oxalate ligands, one coordinated and one solvent water molecules. The Ho^{III} atom is coordinated by eight O atoms, exhibiting a distorted square-antiprismatic geometry. One basal square face of the antiprism is defined by two carboxylate O atoms, one oxalate O atom and one aqua O atom; the other base is completed by the other three oxalate O atoms and one phenolate O atom. Adjacent Ho^{III} atoms are bonded to the carboxylate and phenolate O atoms of the phenoxyconicinate ligand, forming dinuclear subunits, which are further extended at a *syn-anti* conformation into infinite ladder-like chains. The metal atoms are also bridged by oxalate ligands in a side-by-side manner, forming one-dimensional zigzag chains. Both the ladder-like and zigzag chains are finally linked together through the metal atoms into a three-dimensional framework with one-dimensional microchannels (Fig. 2). The three-dimensional framework shows a topology of 3,5-connected {4².6⁵.8³}·{4².6}. N—H···O and O—H···O hydrogen bonds, as well as π—π interactions between the pyridine rings [centroid–centroid distance = 3.794 (2) Å] are found in the crystal.

Experimental


A mixture of holmium nitrate (0.4 mmol, 0.181 g), 5-hydroxynicotinic acid (0.8 mmol, 0.111 g), ammonium oxalate (0.8 mmol, 0.099 g) and 10 ml water was sealed in a 15 ml Teflon-lined autoclave. Colorless crystals suitable for X-ray crystallography analysis were obtained by heating the mixture at 453 K for 72 h and then cooled down to room temperature at a rate of 5 K h⁻¹ (yield: 41%). Analysis, calculated for C₁₆H₁₆Ho₂N₂O₁₈: C 22.50, H 1.89, N 3.28%; found: C 22.65, H 1.91, N 3.13%. IR (cm⁻¹, KBr): 3398 s, 3083 s, 2957 m, 2768 w, 2089 w, 1900 w, 1646 m, 1565 m, 1447 w, 1427 w, 1359 s, 1319 s, 1302 s, 1140 s, 1051 s, 1013 s, 963 s, 942 m, 894 w, 865 w, 823 w, 788 w, 672 m, 591 s, 545 s, 497 m, 450 w, 413 w.

Refinement


H atoms bonded to C atoms were positioned geometrically and refined as riding atoms, with C—H = 0.95 Å and U_{iso}(H) = 1.2U_{eq}(C). H atoms bonded to N and O atoms were located from a difference Fourier map and refined isotropically, with distance restraints of N—H = 0.90 (1) and O—H = 0.85 (1) Å.

Computing details


Data collection: *APEX2* (Bruker, 2007); cell refinement: *SAINT* (Bruker, 2007); data reduction: *SAINT* (Bruker, 2007); program(s) used to solve structure: *SHELXTL* (Sheldrick, 2008); program(s) used to refine structure: *SHELXTL* (Sheldrick, 2008); molecular graphics: *DIAMOND* (Brandenburg, 1999); software used to prepare material for publication: *SHELXTL* (Sheldrick, 2008).

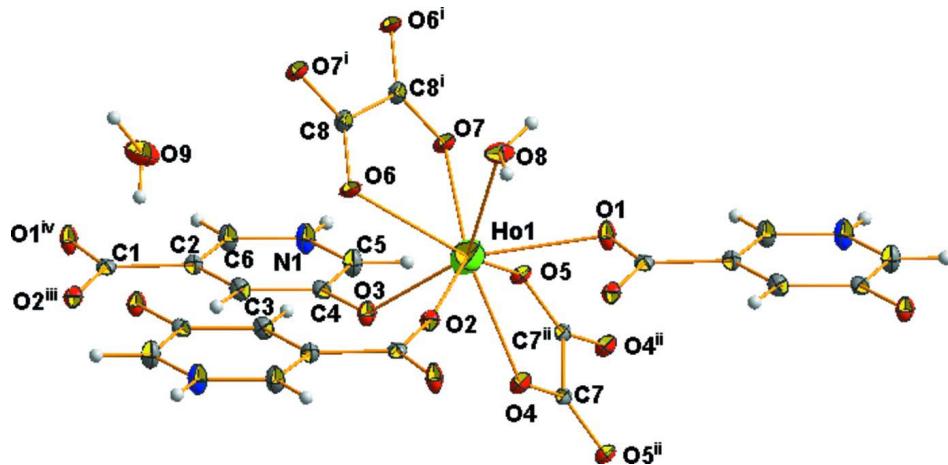**Figure 1**

The asymmetric unit of the title compound, showing displacement ellipsoids at the 50% probability level. [Symmetry codes: (i) $1-x, 2-y, 1-z$; (ii) $2-x, 2-y, 2-z$; (iii) $1-x, 1-y, 1-z$; (iv) $x, -1+y, -1+z$.]

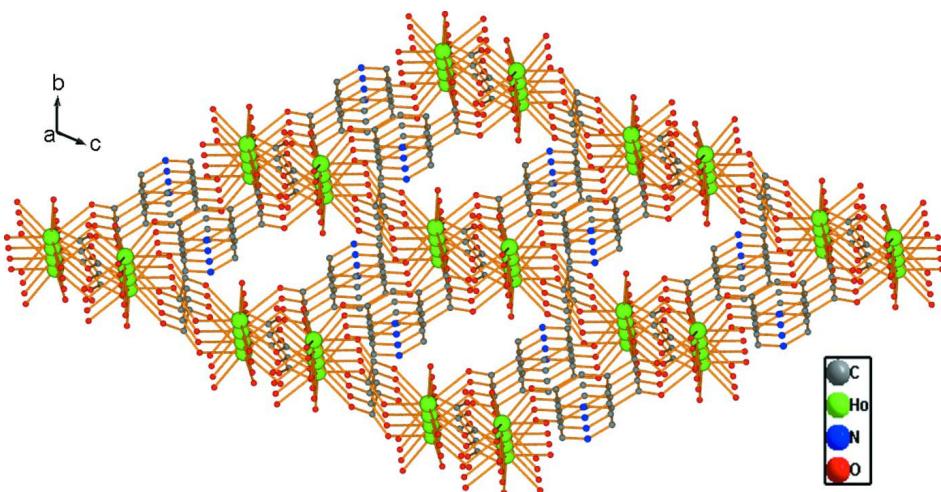**Figure 2**


The three-dimensional framework of the title compound. H atoms and solvent water molecules are omitted for clarity.

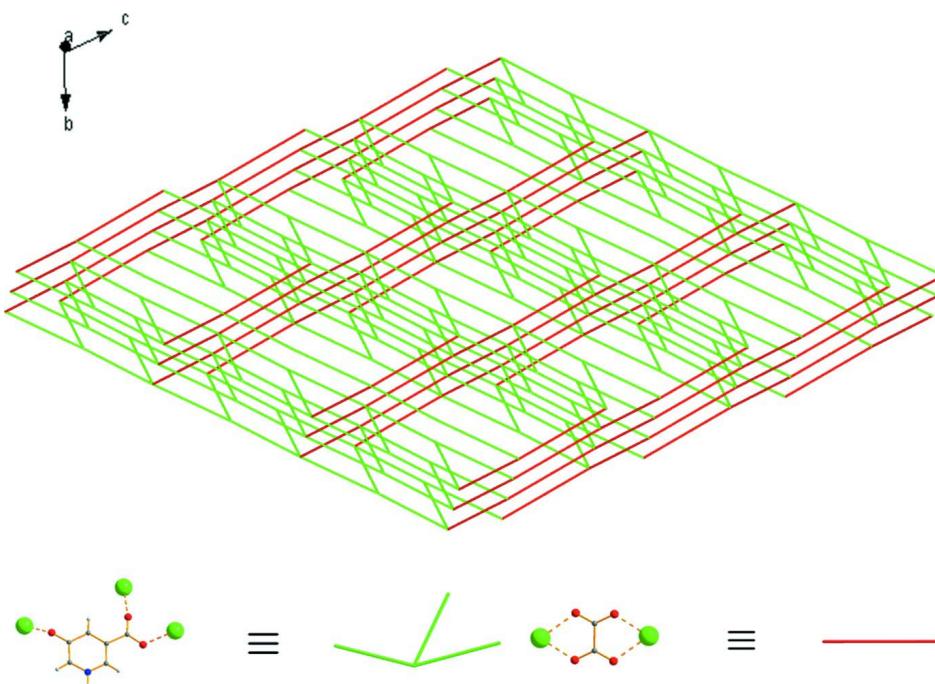**Figure 3**


A schematic view of the three-dimensional framework for the title compound.

Poly[[diaquabis(μ -oxalato- $\kappa^4O^1,O^2;O^{1'},O^{2'}$)bis(μ_3 -5- oxidopyridin-1-ium-3-carboxylato- $\kappa^3O^3;O^{3'};O^{5'}$)dholmium(III)] dihydrate]

Crystal data



$Z = 1$



$F(000) = 404$

Triclinic, $P\bar{1}$

$D_x = 2.599 \text{ Mg m}^{-3}$

Hall symbol: -P 1

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

$a = 7.7786 (16) \text{ \AA}$

Cell parameters from 4550 reflections

$b = 8.0562 (17) \text{ \AA}$

$\theta = 2.3\text{--}27.0^\circ$

$c = 9.505 (2) \text{ \AA}$

$\mu = 7.30 \text{ mm}^{-1}$

$\alpha = 110.912 (3)^\circ$

$T = 173 \text{ K}$

$\beta = 96.862 (3)^\circ$

Block, colorless

$\gamma = 95.770 (3)^\circ$

$0.18 \times 0.16 \times 0.06 \text{ mm}$

$V = 545.8 (2) \text{ \AA}^3$

Data collection

Bruker APEXII CCD

4550 measured reflections

diffractometer

2295 independent reflections

Radiation source: fine-focus sealed tube

2160 reflections with $I > 2\sigma(I)$

Graphite monochromator

$R_{\text{int}} = 0.017$

φ and ω scans

$\theta_{\max} = 27.0^\circ, \theta_{\min} = 2.3^\circ$

Absorption correction: multi-scan

$h = -9 \rightarrow 9$

(*SADABS*; Sheldrick, 1996)

$k = -10 \rightarrow 10$

$T_{\min} = 0.354, T_{\max} = 0.669$

$l = -12 \rightarrow 12$

*Refinement*Refinement on F^2

Least-squares matrix: full

$$R[F^2 > 2\sigma(F^2)] = 0.016$$

$$wR(F^2) = 0.038$$

$$S = 1.05$$

2295 reflections

192 parameters

5 restraints

Primary atom site location: structure-invariant direct methods

Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from neighbouring sites

H atoms treated by a mixture of independent and constrained refinement

$$w = 1/[\sigma^2(F_o^2) + (0.016P)^2 + 0.6363P]$$
$$\text{where } P = (F_o^2 + 2F_c^2)/3$$

$$(\Delta/\sigma)_{\text{max}} = 0.001$$

$$\Delta\rho_{\text{max}} = 0.57 \text{ e \AA}^{-3}$$

$$\Delta\rho_{\text{min}} = -0.49 \text{ e \AA}^{-3}$$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
C1	0.6934 (4)	1.2898 (4)	1.1270 (3)	0.0109 (5)
C2	0.7746 (4)	0.4547 (4)	0.2648 (3)	0.0123 (6)
C3	0.7041 (4)	0.5062 (4)	0.3987 (3)	0.0117 (6)
H3	0.5989	0.4387	0.4032	0.014*
C4	0.7864 (4)	0.6576 (4)	0.5285 (3)	0.0124 (6)
C5	0.9393 (4)	0.7518 (4)	0.5123 (3)	0.0158 (6)
H5	0.9999	0.8543	0.5962	0.019*
C6	0.9258 (4)	0.5562 (4)	0.2565 (4)	0.0162 (6)
H6	0.9743	0.5245	0.1651	0.019*
C7	0.9532 (4)	0.9560 (4)	1.0490 (3)	0.0106 (6)
C8	0.4187 (4)	0.9302 (4)	0.4887 (3)	0.0116 (6)
Ho1	0.647369 (16)	0.971506 (16)	0.803507 (14)	0.00854 (5)
N1	1.0014 (3)	0.6993 (4)	0.3802 (3)	0.0168 (5)
O1	0.7614 (3)	1.2593 (3)	1.0082 (2)	0.0162 (5)
O2	0.4346 (3)	0.8128 (3)	0.8643 (2)	0.0136 (4)
O3	0.7231 (3)	0.7072 (3)	0.6565 (2)	0.0150 (4)
O4	0.7922 (3)	0.8943 (3)	1.0004 (2)	0.0133 (4)
O5	0.9595 (3)	1.0464 (3)	0.8342 (2)	0.0123 (4)
O6	0.4182 (3)	0.8477 (3)	0.5761 (2)	0.0161 (4)
O7	0.7033 (3)	1.0868 (3)	0.6190 (2)	0.0135 (4)
O8	0.4335 (3)	1.1739 (3)	0.8101 (3)	0.0197 (5)
O9	0.3549 (5)	0.5133 (4)	0.1651 (4)	0.0462 (8)
H1	1.102 (3)	0.760 (4)	0.373 (4)	0.011 (8)*
H7	0.489 (6)	1.275 (4)	0.822 (6)	0.061 (17)*
H8	0.363 (6)	1.155 (7)	0.866 (5)	0.065 (17)*

H9	0.331 (8)	0.448 (7)	0.216 (6)	0.08 (2)*
H10	0.269 (6)	0.501 (9)	0.096 (5)	0.09 (2)*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
C1	0.0095 (13)	0.0105 (13)	0.0124 (14)	0.0018 (10)	0.0013 (10)	0.0039 (11)
C2	0.0128 (14)	0.0109 (14)	0.0113 (14)	0.0000 (11)	0.0015 (11)	0.0027 (11)
C3	0.0087 (14)	0.0118 (14)	0.0147 (14)	0.0008 (10)	0.0034 (11)	0.0046 (11)
C4	0.0136 (14)	0.0110 (14)	0.0126 (14)	0.0038 (11)	0.0029 (11)	0.0037 (11)
C5	0.0135 (15)	0.0159 (15)	0.0141 (15)	-0.0008 (11)	0.0017 (11)	0.0020 (12)
C6	0.0149 (15)	0.0161 (15)	0.0143 (15)	-0.0008 (12)	0.0039 (11)	0.0020 (12)
C7	0.0123 (14)	0.0095 (13)	0.0088 (13)	0.0042 (11)	0.0022 (10)	0.0012 (11)
C8	0.0096 (14)	0.0128 (14)	0.0115 (14)	0.0002 (11)	0.0017 (10)	0.0038 (11)
Ho1	0.00804 (7)	0.00981 (7)	0.00735 (7)	-0.00004 (5)	-0.00004 (4)	0.00353 (5)
N1	0.0126 (13)	0.0181 (13)	0.0151 (13)	-0.0051 (10)	0.0041 (10)	0.0022 (11)
O1	0.0163 (11)	0.0151 (11)	0.0127 (10)	-0.0024 (8)	0.0061 (8)	-0.0002 (9)
O2	0.0108 (10)	0.0137 (10)	0.0141 (10)	-0.0019 (8)	-0.0005 (8)	0.0045 (8)
O3	0.0173 (11)	0.0149 (10)	0.0106 (10)	0.0019 (8)	0.0050 (8)	0.0015 (8)
O4	0.0108 (10)	0.0185 (11)	0.0109 (10)	0.0007 (8)	0.0001 (8)	0.0069 (8)
O5	0.0105 (10)	0.0159 (10)	0.0101 (10)	0.0012 (8)	0.0004 (8)	0.0052 (8)
O6	0.0170 (11)	0.0165 (11)	0.0148 (11)	-0.0054 (8)	-0.0047 (8)	0.0103 (9)
O7	0.0108 (10)	0.0189 (11)	0.0115 (10)	-0.0019 (8)	-0.0010 (8)	0.0086 (8)
O8	0.0220 (13)	0.0232 (13)	0.0201 (12)	0.0096 (10)	0.0087 (9)	0.0122 (10)
O9	0.056 (2)	0.0259 (15)	0.055 (2)	0.0023 (14)	-0.0118 (17)	0.0206 (15)

Geometric parameters (\AA , ^\circ)

C1—O2 ⁱ	1.259 (4)	C8—O6	1.235 (4)
C1—O1	1.260 (4)	C8—O7 ^v	1.269 (3)
C1—C2 ⁱⁱ	1.507 (4)	C8—C8 ^v	1.545 (6)
C2—C3	1.388 (4)	Ho1—O2	2.245 (2)
C2—C6	1.390 (4)	Ho1—O3	2.271 (2)
C2—C1 ⁱⁱⁱ	1.507 (4)	Ho1—O7	2.322 (2)
C3—C4	1.414 (4)	Ho1—O4	2.372 (2)
C3—H3	0.9500	Ho1—O5	2.399 (2)
C4—O3	1.311 (4)	Ho1—O1	2.429 (2)
C4—C5	1.400 (4)	Ho1—O8	2.435 (2)
C5—N1	1.340 (4)	Ho1—O6	2.455 (2)
C5—H5	0.9500	N1—H1	0.90 (1)
C6—N1	1.337 (4)	O8—H7	0.85 (1)
C6—H6	0.9500	O8—H8	0.85 (1)
C7—O5 ^{iv}	1.237 (3)	O9—H9	0.85 (1)
C7—O4	1.266 (4)	O9—H10	0.85 (1)
C7—C7 ^{iv}	1.559 (6)		
O2 ⁱ —C1—O1	123.0 (3)	O4—Ho1—O5	68.67 (7)
O2 ⁱ —C1—C2 ⁱⁱ	119.6 (3)	O2—Ho1—O1	112.36 (7)
O1—C1—C2 ⁱⁱ	117.4 (3)	O3—Ho1—O1	143.48 (8)
C3—C2—C6	119.6 (3)	O7—Ho1—O1	91.68 (7)

C3—C2—C1 ⁱⁱⁱ	122.1 (3)	O4—Ho1—O1	75.80 (7)
C6—C2—C1 ⁱⁱⁱ	118.3 (3)	O5—Ho1—O1	67.35 (7)
C2—C3—C4	121.0 (3)	O2—Ho1—O8	83.88 (8)
C2—C3—H3	119.5	O3—Ho1—O8	142.95 (8)
C4—C3—H3	119.5	O7—Ho1—O8	75.53 (8)
O3—C4—C5	121.8 (3)	O4—Ho1—O8	130.78 (7)
O3—C4—C3	122.0 (3)	O5—Ho1—O8	126.55 (8)
C5—C4—C3	116.2 (3)	O1—Ho1—O8	71.62 (8)
N1—C5—C4	120.9 (3)	O2—Ho1—O6	74.25 (7)
N1—C5—H5	119.5	O3—Ho1—O6	74.55 (8)
C4—C5—H5	119.5	O7—Ho1—O6	68.06 (7)
N1—C6—C2	118.5 (3)	O4—Ho1—O6	141.48 (7)
N1—C6—H6	120.7	O5—Ho1—O6	132.12 (7)
C2—C6—H6	120.7	O1—Ho1—O6	138.53 (7)
O5 ^{iv} —C7—O4	126.2 (3)	O8—Ho1—O6	68.47 (8)
O5 ^{iv} —C7—C7 ^{iv}	118.1 (3)	C6—N1—C5	123.8 (3)
O4—C7—C7 ^{iv}	115.7 (3)	C6—N1—H1	117 (2)
O6—C8—O7 ^v	126.3 (3)	C5—N1—H1	119 (2)
O6—C8—C8 ^v	118.0 (3)	C1—O1—Ho1	115.09 (18)
O7 ^v —C8—C8 ^v	115.6 (3)	C1 ⁱ —O2—Ho1	169.7 (2)
O2—Ho1—O3	88.38 (8)	C4—O3—Ho1	132.61 (19)
O2—Ho1—O7	141.51 (7)	C7—O4—Ho1	118.19 (18)
O3—Ho1—O7	88.96 (8)	C7 ^{iv} —O5—Ho1	116.85 (18)
O2—Ho1—O4	75.56 (7)	C8—O6—Ho1	115.09 (18)
O3—Ho1—O4	81.26 (8)	C8 ^v —O7—Ho1	119.68 (18)
O7—Ho1—O4	141.63 (7)	Ho1—O8—H7	108 (4)
O2—Ho1—O5	143.17 (7)	Ho1—O8—H8	106 (4)
O3—Ho1—O5	78.02 (7)	H7—O8—H8	126 (5)
O7—Ho1—O5	73.02 (7)	H9—O9—H10	111 (6)

Symmetry codes: (i) $-x+1, -y+2, -z+2$; (ii) $x, y+1, z+1$; (iii) $x, y-1, z-1$; (iv) $-x+2, -y+2, -z+2$; (v) $-x+1, -y+2, -z+1$.

Hydrogen-bond geometry (\AA , $^\circ$)

$D\text{—H}\cdots A$	$D\text{—H}$	$H\cdots A$	$D\cdots A$	$D\text{—H}\cdots A$
N1—H1 \cdots O7 ^{vi}	0.90 (1)	1.83 (1)	2.727 (3)	171 (3)
O8—H7 \cdots O9 ^v	0.85 (1)	1.95 (1)	2.787 (4)	171 (5)
O8—H8 \cdots O4 ⁱ	0.85 (1)	1.96 (1)	2.811 (3)	177 (6)
O9—H9 \cdots O3 ^{vii}	0.85 (1)	2.08 (1)	2.929 (4)	178 (6)
O9—H10 \cdots O1 ^v	0.85 (1)	2.48 (6)	3.003 (4)	120 (5)

Symmetry codes: (i) $-x+1, -y+2, -z+2$; (v) $-x+1, -y+2, -z+1$; (vi) $-x+2, -y+2, -z+1$; (vii) $-x+1, -y+1, -z+1$.