


Cite this: *RSC Adv.*, 2019, 9, 30917

Rhodamine B derivative-modified up-conversion nanoparticle probes based on fluorescence resonance energy transfer (FRET) for the solid-based detection of copper ions†

Xiaoyan Liu,^{a,c} Nan Ding,^b Jun Wang,^c Honglan Chen,^c Xinwei Chen,^c Zhidong Wang^a and Xincun Peng^{*a}

Herein, a novel solid-based up-conversion fluorescence resonance energy transfer (FRET) sensor was developed using rhodamine B hydrazide, which provided a selective fluorescence response and suitable affinity towards Cu^{2+} ions over other biologically relevant metal ions because the Cu^{2+} ion could promote the hydrolysis of α -amino acid esters of rhodamine B hydrazide and yield the $\text{Cu} \cdot \alpha$ -amino acid chelate. This solid-based detection system is more convenient for the detection of Cu^{2+} based on color change and emission spectra instead of the complicated and tedious measurements than other up-conversion sensors and up-conversion luminescent nanoparticles used as an excitation source; moreover, the proposed system shows high selectivity, minimum photo-damage to living organisms, and high chemical stability.

Received 17th July 2019
Accepted 6th September 2019

DOI: 10.1039/c9ra05504e

rsc.li/rsc-advances

1. Introduction

Copper ion, as the third most abundant essential transition metal ion, plays a critical role in human health and environmental science, ranging from the diagnosis of life-threatening diseases to the analysis of environmental pollutants.^{1–3} However, when the Cu^{2+} ion is present at significantly high or low concentrations, it leads to serious human diseases;^{4,5} moreover, Cu^{2+} is non-degradable and can accumulate in the environment; hence, Cu^{2+} ion in excessive amounts will result in environmental pollution throughout the world due to its widespread use in industries, agriculture, household utensils, and water pipes. Therefore, the development of fast, convenient and reliable methods for the qualitative and quantitative detection of trace amounts of Cu^{2+} ions is of significant importance considering the biological and environmental implications of excess Cu^{2+} ions.

A number of studies have been conducted on Cu^{2+} detection;^{6,9,16–26} as is well-known, recently, fluorescent probes based on up-conversion nanoparticles (UCNP), focusing on converting the near-infrared (NIR) light to visible light, have attracted significant attention due to their potential use as bio-probes in detection and imaging.^{7,8,10–15} Compared to other methods, fluorescent probes based on UCNP present many intriguing advantages due to their unique anti-Stokes fluorescence properties including large penetration depth into tissues, high signal-to-noise ratio, minimum photo-damage to living organisms, high chemical stability and low toxicity.^{27,28} In addition, under NIR excitation, the auto-fluorescence from biological samples and scattering light becomes negligible.

To date, several sensors based on UC-FRET have been developed to detect DNA, metal ions, and small molecules,^{29,30} where the UCNPs (donor) transfer energy to other chromophores (acceptor), resulting in changes in the intensity of UC emission. However, it should be emphasized that the above-mentioned UCNP system sensors work in solutions. Liquid-based sensors are usually unstable and irreproducible and have weak up-conversion light (UCL) due to the interaction of UCNPs in solutions, which will unavoidably influence the detection limit and sensitivity. Therefore, it is significant to develop novel solid-state UC sensors with easy operation, stable performance and repeatable responses. For example, Song and co-workers developed solid-state UC biosensors for the detection of copper ions.¹¹ However, to the best of our knowledge, a Cu^{2+} fluorescent probe based on the solid-state UC-FRET with

^aEngineering Research Center of Nuclear Technology Application, Ministry of Education, Engineering Research Center of New Energy Technology and Equipment of Jiangxi Province, East China Institute of Technology, 418 Guanglan Avenue, Nanchang 330013, China. E-mail: xcpeng@ecit.cn

^bState Key Laboratory on Integrated Optoelectronics, College of Electronic Science and Engineering, Jilin University, 2699 Qianjin Street, Changchun 130012, China

^cInstitute for Electric Light Sources, School of Information Science and Technology, Engineering Research Center of Advanced Lighting Technology, Academy of Engineering and Technology, Fudan University, Shanghai 200433, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9ra05504e



rhodamine B hydrazide (referred to as RBH hereinafter) as the energy acceptor has not been reported to date.

In our study, we designed a novel solid-state fluorescent sensor based on the complex of the glass substrate/ $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ film and RBH for Cu^{2+} detection on the basis of color change and emission spectra, where the glass substrate/ $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ composite films served as the energy donor and RBH served as the energy acceptor. Fig. 1 illustrates the preparation process of the $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ core-shell structured probe and the principle of up-conversion FRET in the RBH-modified $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ sensor for Cu^{2+} detection. The rhodamine framework has been proven to be a classic mode for the construction of fluorescent probes because of its particular spiro-lactam structure and excellent photo-physical properties such as long absorption and emission wavelength, large absorption coefficient and good photostability.^{31–33} When the concentration of Cu^{2+} is up to a certain amount, the up-conversion FRET sensor changes from green to red.

2. Experimental

Rare-earth nitrates were purchased from the National Engineering Research Centre of Rare Earth Metallurgy and Function Materials, and other starting materials were bought from the Tianjin GuangFu Technology Development Co., Ltd and Beijing Chemical Plant. All of them were used directly without any further purification. Deionized water was used throughout the experiment.

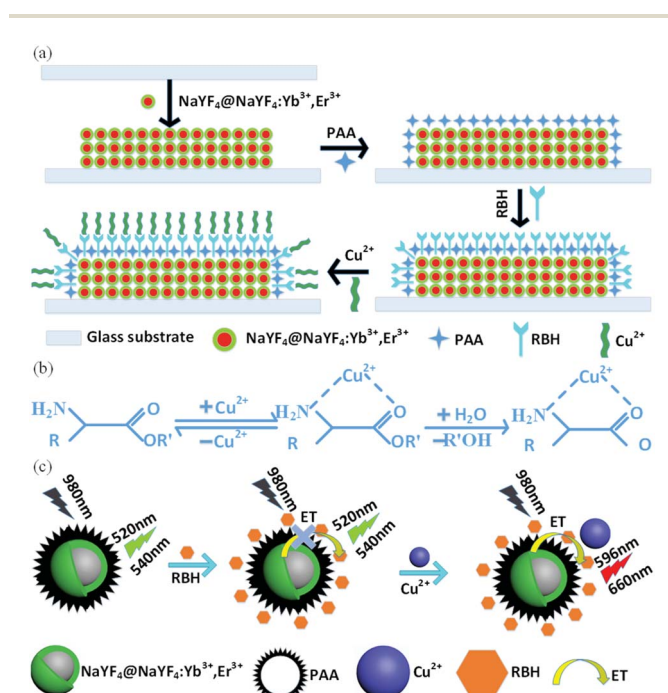


Fig. 1 (a) Schematic of the $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ film preparation process. (b) Reaction mechanism of RBH with Cu^{2+} ions. (c) Principle of up-conversion for Cu^{2+} detection using UCNPs as donors and RBH as acceptors in the $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ core-shell structured probe.

2.1 Synthesis of oleic-acid-coated NaYF_4

Oleic-acid-capped NaYF_4 was synthesized by a typical solvothermal method^{34–36} with slight modifications. The reaction temperature was controlled in the range of 285–330 °C to obtain NCNPs with different sizes. The as-prepared products were obtained and washed three times with absolute cyclohexane-ethanol (1 : 3 v/v), and the final products were dissolved in the cyclohexane solution for the following experiments.

The synthesis of NaYF_4 core nanoparticles was conducted as follows: $\text{YCl}_3 \cdot 6\text{H}_2\text{O}$ (1 mmol) was mixed with 6 mL oleic acid (OA) and 15 mL 1-octadecene (ODE) in a 50 mL three-necked bottle followed by heating to 160 °C to form a homogeneous solution; then, the mixture was cooled down to 40 °C. Following this, a 10 mL methanol solution containing NaOH (2.5 mmol) and NH_4F (4 mmol) was slowly added to the bottle, and the solution quickly became muddy. The mixed solution was stirred for 0.5 h, and it was ensured that all fluoride was consumed completely. Subsequently, the solution was slowly heated to evaporate methanol and then degassed at 120 °C for 0.5 h until it was clear. Then, the solution was heated to 300 °C and maintained at this temperature for 1.5 h under a nitrogen atmosphere and vigorous stirring. After the solution was naturally cooled down to room temperature, the resulting mixture was centrifugally separated and washed three times with cyclohexane-ethanol (1 : 3 v/v), and the product obtained was the NaYF_4 core, which was re-dispersed in cyclohexane.

2.2 Synthesis of oleic-acid-coated core-shell structured $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ UCNPs

$\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ (core/shell) nanoparticles were synthesized using similar procedures.^{37,38} The $\text{NaYF}_4\text{:Yb}^{3+},\text{Er}^{3+}$ shell precursor was first prepared by mixing $\text{YCl}_3 \cdot 6\text{H}_2\text{O}$ (0.78 mmol), $\text{YbCl}_3 \cdot 6\text{H}_2\text{O}$ (0.2 mmol) and $\text{ErCl}_3 \cdot 6\text{H}_2\text{O}$ (0.02 mmol) with 6 mL OA and 15 mL ODE in a 50 mL flask and subsequently heated at 160 °C for 0.5 h to form a homogeneous and clear solution before cooling to 40 °C. The NaYF_4 core nanoparticles in cyclohexane (5 mL) were added to the abovementioned solution, and the mixture was stirred for 0.5 h followed by heating to 80 °C to evaporate cyclohexane; after this, the temperature of the mixture was dropped to 40 °C, a 5 mL methanol solution of NH_4F (4 mmol) and NaOH (2.5 mmol) was injected into the bottle, and the mixed solution was stirred for 0.5 h. Then, the mixed solution was heated to 120 °C for 0.5 h to evaporate methanol under N_2 until a clear solution was obtained. Subsequently, the resulting mixture was heated to 310 °C under N_2 for 1.5 h, and then, the mixture was allowed to cool down to room temperature. The resulting nanoparticles were precipitated by adding ethanol, obtained by centrifugation at 9000 rpm, washed several times with cyclohexane-ethanol, and re-dispersed in cyclohexane. The final products were denoted as OA-UCNPs.

2.3 Synthesis of water-soluble PAA-modified UCNPs

Polyacrylic acid (PAA)-modified water-soluble UCNPs were synthesized *via* a previously reported ligand exchange method^{37,39} with slight modifications. Typically, 0.5 g PAA was added to 10 mL diethylene glycol (DEG) in a three-necked flask, and the mixture

was heated to 110 °C under vigorous stirring to form a clear solution. A cyclohexane solution containing 100 mg OA-UCNPs was added slowly and refluxed for 2.5 h at 150 °C under argon protection. The mixed solution was then heated to 240 °C for 0.5 h to get rid of cyclohexane. The resulting solution was cooled down to room temperature, and then, ethanol was added to form a precipitate. The PAA-UCNPs were recovered *via* centrifugation and washed three times with ethanol/water (1 : 1 v/v).

2.4 Synthesis of the RBH

At first, 1.92 g (4 mmol) rhodamine B was mixed with 30 mL absolute ethanol in a 100 mL three-necked bottle, and the mixture was stirred vigorously at room temperature to form a homogeneous purple-red solution; then, 6 mL hydrazine hydrate (80%) was added slowly to the abovementioned solution. After the addition, the stirred mixture was refluxed in an oil bath for 12 h at 85 °C. The solution changed from purple-red to light-orange and became transparent; it was then cooled down to room temperature. The solvent was removed by rotary evaporation to obtain the residual material, which was then dissolved in 60 mL of 1 mol L⁻¹ hydrochloric acid to develop a wine-red solution; subsequently, 70 mL of a 1 mol L⁻¹ NaOH solution was added dropwise to the abovementioned solution under constant stirring to obtain a white precipitate. The resulting precipitate was filtered and washed three times with deionized water. After drying the reaction mixture in a vacuum drying oven for 24 h at room temperature, a light-pink powder was obtained.

2.5 Characterization and measurements

The size and morphology of UCNPs were determined by transmission electron microscopy, which was carried out using the Hitachi H-800 transmission electron microscope (TEM) operating at an acceleration voltage of 200 kV. The crystalline structure of the samples was characterized by X-ray diffraction (XRD) using a monochromatized Cu target radiation source ($\lambda = 1.54 \text{ \AA}$). ¹H Nuclear magnetic resonance (NMR) spectra were obtained using the Bruker Avance III spectrometer.

Ultraviolet-visible (UV-Vis) absorption spectra of the resulting samples were obtained by the UV-1800 UV-visible spectrometer in the range from 200 nm to 1100 nm. The emission and excitation spectra of RBH were obtained using the SENS-9000 spectrometer. The UCL spectra were obtained using the Andor Shamrock SR-750 spectrometer. A photomultiplier (300–850 nm) combined with a monochromator and an infrared InGaAs detector (800–2200 nm) combined with a double-grating monochromator were used for signal collection from 400 nm to 2200 nm. A continuous 980 nm diode laser was used to pump the samples to investigate the steady-state spectra. The luminescence dynamics of the UCNPs were studied using a laser system consisting of a Nd:YAG pumping laser (1064 nm), a third-order harmonic-generator (355 nm) and a tunable optical parameter oscillator with a pulse duration of 10 ns, a repetition frequency of 10 Hz and a line width of 4–7 cm⁻¹.

3. Results and discussion

3.1 Structure and morphology of the NaYF₄@NaYF₄:Yb³⁺,Er³⁺ UCNPs

The core of the UCNP probe is the host matrix (NaYF₄ nanoparticle) without doped ions, and the emitter-doped Ln³⁺ ions are confined in the shell layer. In this structure of UCNPs, most emitting ions were positioned near the surface of the material and close to the external energy acceptors. Fig. 2(a)–(c) show the transmission electron microscopy (TEM) images of the as-synthesized nanoparticles, which clearly present the size evolution of the UCNPs. The size of the UCNPs gradually increases, *i.e.*, from the NaYF₄ core with an average diameter of ~30 nm (see Fig. 2(a)) to the NaYF₄@NaYF₄:Yb³⁺,Er³⁺ core-shell structure with the size of ~38 nm (see Fig. 2(c)). The X-ray diffraction patterns are shown in Fig. 2(d), which indicate that the obtained nanoparticles are in the hexagonal phase; moreover, these patterns are in good agreement with the standard cards (JCPDS 28-1192), suggesting high product crystallinity.

The hydrophobic UCNPs (with OA as ligands) were first transformed into water-dispersible materials using PAA molecules that replaced the original OA ligands through ligand exchange at the liquid-liquid interface;^{37,39} the successful loading of PAA was confirmed by dissolving the PAA-UCNPs in water to form a homogeneous solution, and their dissolution was the direct experimental evidence of the successful replacement of the OA ligand by the PAA molecules.

3.2 Photoluminescence spectra of RBH and UCNPs

Electrostatic interactions between positive and negative charges play a key role in the formation of the FRET probe. The strong attachment of the acceptor on the surface of the UCNP donor can occur by electrostatic interactions during simple mixing. In this study, we have selected an amine-tagged organic dye, RBH,

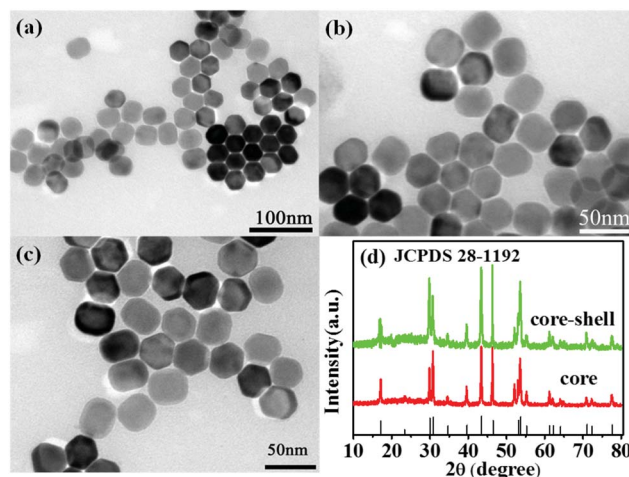


Fig. 2 Transmission electron microscopy (TEM) images of the as-synthesized nanoparticles. (a) TEM images of the oleate-capped NaYF₄ core, (b) oleate-capped NaYF₄@NaYF₄:Yb³⁺,Er³⁺ core-shell UCNPs and (c) PAA-modified core-shell UCNPs. (d) XRD patterns of the obtained core-shell nanocrystals.

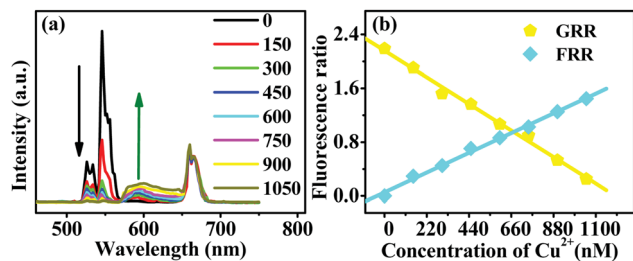


Fig. 6 (a) Fluorescence spectra of NaYF₄@NaYF₄:Yb³⁺,Er³⁺ with RBH in the presence of increasing concentrations of Cu²⁺ (0–1050 nM) upon 980 nm excitation. (b) Variation in both green-to-red emission ratio (GRR) of Er³⁺ and RBH fluorescence emission-to-red emission ratio (FRR) at different concentrations of Cu²⁺ ions.

responsible for the high selectivity of the sensor towards Cu²⁺ ions.^{40,43}

With an increase in the concentrations of Cu²⁺ ions, the fluorescence intensity of RBH increases gradually, whereas the intensity of the up-conversion emission at 520 nm and 540 nm decreases dramatically, as shown in Fig. 6, and the red emission of the UCNP at 660 nm remains nearly unchanged. Since RBH has no absorption for the red light of UCNP at 660 nm, the red emission intensity can thus be used as a reference. When the Cu²⁺ ion concentration is up to a significant amount (600 nM), the green emissions at 520 nm and 540 nm are nearly absent. Moreover, the red emission becomes dominant among the entire emission lines.

Fig. 6(b) exhibits the variation in both the green (²H_{11/2}–⁴I_{15/2} and ⁴S_{3/2}–⁴I_{15/2})-to-red (⁴F_{9/2}–⁴I_{15/2}) emission ratio (GRR) of Er³⁺ and RBH emission-to-red (⁴F_{9/2}–⁴I_{15/2}) emission ratio (FRR) at different concentrations of Cu²⁺ ions. The variation trend of the green-to-red emission ratio supports the UCNP emission/RBH absorption mechanism hypothesis. The changes in the fluorescence emission-to-red emission ratio also suggest the presence of resonant energy transfer; this indicates successful energy transfer between the UCNP donor and the RBH acceptor.⁹ Compared to the case reported in ref. 9, herein, when the concentration of the Cu²⁺ ion was up to 600 nM, the ratio of GRR was less than 1; these results indicated that the UC nano-probe visibly changed from green to red, similar to the case of pH indicator strips, and the solid sensor based on the color change for Cu²⁺ detection was realizable.

The corresponding images of the RBH-UCNP FRET probe in the absence and presence of Cu²⁺ are shown in Fig. S3.† It can be observed that in the absence of Cu²⁺ ions, the RBH-UCNP probe presents green emissions of Er³⁺ under 980 nm excitation. As the Cu²⁺ concentration increases, the intensity of the green up-conversion emissions gradually decreases until they are nearly absent. The red emission becomes dominant, and the RBH-UCNP probe presents a red color.

To further confirm the FRET process from the UCNP donors to the RBH acceptors, the luminescence decay dynamics for the ⁴S_{3/2}–⁴I_{15/2} transition of Er³⁺ with and without Cu²⁺ ions were measured and compared, as shown in Fig. S4.† It can be observed that under 980 nm excitation, the decay time of Er³⁺ with the Cu²⁺ ions is shorter than that without Cu²⁺ ions. The Er³⁺ lifetime decreases from 519 μs to

314 μs, which is an evidence for the FRET from Er³⁺ to RBH.^{9,12}

3.4 Fluorescence response characteristics of the probe for Cu²⁺ detection

An important feature of the probe is its high selectivity towards the Cu²⁺ ions over other competitive species such as Ag²⁺, Na⁺, Fe³⁺, Ba²⁺, Pb²⁺, Gd³⁺, Ca²⁺, Ni²⁺, Co²⁺, Mn²⁺, K⁺, and Zn²⁺. No obvious responses were observed in the absorption spectra of RBH upon the addition of the abovementioned species, as shown in Fig. 7(a). However, the addition of equivalent amount of Cu²⁺ ion induced a large absorption band centered at 540 nm accompanied by the remarkable change of the probe from colorless to magenta, as displayed in Fig. 7(b). This is because RBH possesses suitable affinity towards Cu²⁺ ions over other biologically relevant metal ions. The Cu²⁺ ion can promote the hydrolysis of the α-amino acid esters of RBH and yield the Cu·α-amino acid chelate; thus, the ring-opening of RBH occurs. The color of the solution to which Cu²⁺ was added changed significantly.³⁹ Note that the addition of the Fe³⁺ ions caused a slight change in the color of the solution. This might be due to the strong oxidizing property of the Fe³⁺ ions, which oxidized phenylhydrazine. The spirocyclic structure of RBH was destroyed, and the solution turned from colorless to light red.

To further estimate the selectivity of the solid-based FRET probe for copper detection, the integrated intensities of Ag²⁺, Na⁺, Fe³⁺, Ba²⁺, Pb²⁺, Gd³⁺, Ca²⁺, Ni²⁺, Co²⁺, Mn²⁺, K⁺, and Zn²⁺ were investigated in the presence of Cu²⁺ ions. As shown in Fig. 8, only Cu²⁺ ions led to a dramatic change in the fluorescence intensity, showing an obvious difference from the cases of other metal ions. There was no significant fluorescence intensity variation in the presence of other ions except for Cu²⁺ ions; this indicated the high selectivity of the proposed probe for the Cu²⁺ ions.

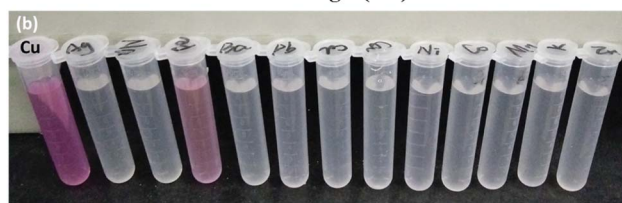
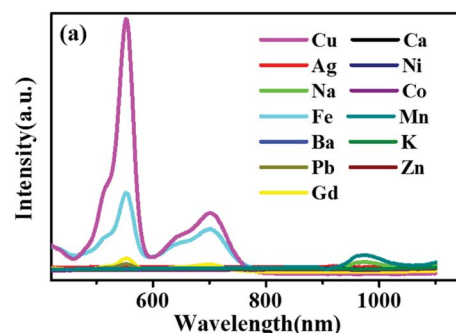


Fig. 7 (a) UV-Vis absorption spectra of RBH upon the addition of various metal ions (10 nM, in absolute ethyl alcohol) and (b) naked-eye detectable color changes.

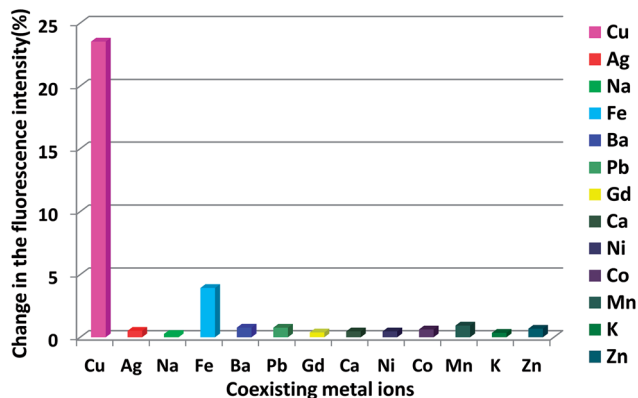


Fig. 8 Detection selectivity of the proposed UCNP probe for Cu²⁺ ions against other metal ions.

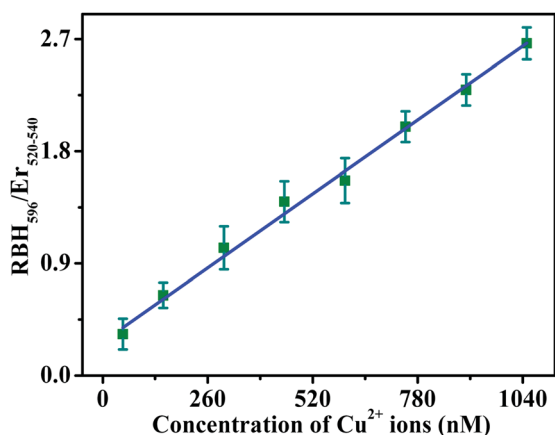


Fig. 9 Calibration curve of the integrated luminescence intensity ratio RBH₅₉₆/Er₅₂₀₋₅₄₀ versus the concentration of Cu²⁺ ions under 980 nm excitation for the FRET detection of Cu²⁺ ions.

The UCNPs utilize NIR excitation rather than ultraviolet (UV) excitation, thereby significantly minimizing background auto-fluorescence, photobleaching, and photodamage to biological specimens.²⁷ To study the anti-interference of the proposed UCNP-based sensor, the fluorescence characteristics with and without the serum were studied, as shown in Fig. S5.† It can be observed that the fluorescence intensity presents an insignificant change, which indicates that the serum does not significantly influence the Cu²⁺ detection. The abovementioned results suggest that the proposed UCNP-based sensor exhibits a good anti-interference performance.

Fig. 9 shows the curve of RBH₅₉₆/Er₅₂₀₋₅₄₀ as a function of the amount of Cu²⁺ ions. The signal of RBH₅₉₆/Er₅₂₀₋₅₄₀ increases steadily with an increase in the Cu²⁺ concentration. There is a good linear relationship between the fluorescence intensity ratio and the concentration of Cu²⁺ ions. *R*, defined as the correlation coefficient of the linear fit, is 0.9925 in the range of 50–1050 nM.

4. Conclusions

In summary, we presented a new FRET-based NIR solid state-based up-conversion nano-probe for copper ion detection,

which overcame the lack of NIR-excitable probes for Cu²⁺ ions. The proposed sensor has the advantages of a quick response towards Cu²⁺ ions, weak auto-fluorescence background, good selectivity, and ease of fabrication. Note that the solid-based UC sensor is more stable, convenient and applicable than the liquid-based UC sensor; thus, this system have further potential applications in Cu²⁺ detection in the sensor fields. Furthermore, we established a solid-based sensor with a promising prospect, which was used to detect the Cu²⁺ ions *via* color change and emission spectra. Thus, it is expected that the up-conversion solid-based sensor with the color change property may have potential applications in Cu²⁺ detection.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This study was supported by the Opening Foundation of Engineering Research Center of New Energy Technology of Jiangxi Province (no. JXNE2018-05), National Natural Science Foundation of China (no. 11875012), Young Scientists Fund of the National Natural Science Foundation of China (Grant no. 61204071), and Doctoral Research Start-Up Fund. We thank Prof. Hongwei Song and associate Prof. Wen Xu in Jilin University for offering us access to the fluorescence dynamic measurement using the Nd:YAG pumping laser and for helpful discussions.

References

- Y. Yang, Q. Zhao, W. Feng and F. Li, Luminescent upconversion for bioimaging, *Chem. Rev.*, 2012, **113**, 192–270.
- Z. Hu, J. Hu, Y. Cui, G. Wang, X. Zhang, K. Uvdal and H. Gao, A facile “click” reaction to fabricate a FRET-based ratiometric fluorescent Cu²⁺ probe, *J. Mater. Chem. B*, 2014, **2**, 4467–4472.
- L. Gao, L. Li, X. Wang, P. Wu, Y. Cao, B. Liang, X. Li, Y. Lin, Y. Lu and X. Guo, Graphene-DNAzyme junctions: a platform for direct metal ion detection with ultrahigh sensitivity, *Chem. Sci.*, 2015, **6**, 2469–2473.
- P. Verwilt, K. Sunwoo and J. S. Kim, The role of copper ions in pathophysiology and fluorescent sensors for the detection thereof, *Chem. Commun.*, 2015, **51**, 5556–5571.
- S. Hu, J. Song, F. Zhao, X. Meng and G. Wu, Highly sensitive and selective colorimetric naked-eye detection of Cu²⁺ in aqueous medium using a hydrazine chemosensor, *Sens. Actuators, B*, 2015, **215**, 241–248.
- C. Li, J. Liu, S. Alonso, F. Li and Y. Zhang, Upconversion nanoparticles for sensitive and in-depth detection of Cu²⁺ ions, *Nanoscale*, 2012, **4**, 6065–6071.
- J. Peng, W. Xu, C. L. Teoh, S. Han, B. Kim, A. Samanta, J. C. Er, L. Wang, L. Yuan, X. Liu and Y.-T. Chang, High-efficiency in vitro and in vivo detection of Zn²⁺ by dye-

- assembled upconversion nanoparticles, *J. Am. Chem. Soc.*, 2015, **137**, 2336–2342.
- 8 Z. Li, S. Lv, Y. Wang, S. Chen and Z. Liu, Construction of LRET-based nanoprobe using upconversion nanoparticles with confined emitters and bared surface as luminophore, *J. Am. Chem. Soc.*, 2015, **137**, 3421–3427.
- 9 J. Zhang, B. Li, L. M. Zhang and H. Jiang, An optical sensor for Cu(II) detection with upconverting luminescent nanoparticles as an excitation source, *Chem. Commun.*, 2012, **48**, 4860–4862.
- 10 F. Chen, W. Bu, S. Zhang, J. Liu, W. Fan, L. Zhou, W. Peng and J. Shi, Gd³⁺-ion-doped upconversion nanoprobe: relaxivity mechanism probing and sensitivity optimization, *Adv. Funct. Mater.*, 2013, **23**, 298–307.
- 11 S. Xu, W. Xu, Y. Wang, S. Zhang, Y. Zhu, L. Tao, L. Xia, P. Zhou and H. Song, NaYF₄:Yb, Tm nanocrystals and TiO₂ inverse opal composite films: a novel device for upconversion enhancement and solid-based sensing of avidin, *Nanoscale*, 2014, **6**, 5859–5870.
- 12 S. Xu, S. Xu, Y. Zhu, W. Xu, P. Zhou, C. Zhou, B. Dong and H. Song, A novel upconversion, fluorescence resonance energy transfer biosensor (FRET) for sensitive detection of lead ions in human serum, *Nanoscale*, 2014, **6**, 12573–12579.
- 13 X. Li, Y. Wu, Y. Liu, X. Zou, L. Yao, F. Li and W. Feng, Cyclometallated ruthenium complex-modified up-conversion nanophosphors for selective detection of Hg²⁺ ions in water, *Nanoscale*, 2014, **6**, 1020–1028.
- 14 F. Wang, D. Banerjee, Y. Liu, X. Chen and X. Liu, Up-conversion nanoparticles in biological labeling, imaging, and therapy, *Analyst*, 2010, **135**, 1839–1854.
- 15 Q. Liu, J. Peng, L. Sun and F. Li, High-efficiency upconversion luminescent sensing and bioimaging of Hg(II) by chromophoric ruthenium complex-assembled nanophosphors, *ACS Nano*, 2011, **5**, 8040–8048.
- 16 A. Salinas-Castillo, M. Ariza-Avidad, C. Pritz, M. Camprubí-Robles, B. Fernández, M. J. Ruedas-Rama, A. Megia-Fernández, A. Lapresta-Fernández, F. Santoyo-Gonzalez and A. Schrott-Fischer, Carbon dots for copper detection with down and upconversion fluorescent properties as excitation sources, *Chem. Commun.*, 2013, **49**, 1103–1105.
- 17 A. P. de Silva, H. Q. N. Gunaratne, T. Gunnlaugsson, A. J. M. Huxley, C. P. McCoy, J. T. Rademacher and T. E. Rice, Signaling recognition events with fluorescent sensors and switches, *Chem. Rev.*, 1997, **97**, 1515–1566.
- 18 S. Na, Z. Ying, C. Sinman, Y. Ronghua, C. Winghong, M. Tain and L. K. L. Feng, Copper ion-selective fluorescent sensor based on the inner filter effect using a spiropyran derivative, *Anal. Chem.*, 2005, **77**, 7294–7303.
- 19 F. Wang, Z. Gu, L. Wu, W. Wang, X. Xia and Q. Hao, Graphene quantum dots as a fluorescent sensing platform for highly efficient detection of copper(II) ions, *Sens. Actuators, B*, 2014, **190**, 516–522.
- 20 J. Wu, W. Liu, J. Ge, H. Zhang and P. Wang, New sensing mechanisms for design of fluorescent chemosensors emerging in recent years, *Chem. Soc. Rev.*, 2011, **40**, 3483–3495.
- 21 M. Taki, S. Iyoshi, A. Ojida, I. Hamachi and Y. Yamamoto, Development of highly sensitive fluorescent probes for detection of intracellular copper(I) in living systems, *J. Am. Chem. Soc.*, 2010, **132**, 5938–5939.
- 22 Z. Guo, W. Chen and X. Duan, Highly selective visual detection of Cu (II) utilizing intramolecular hydrogen bond-stabilized merocyanine in aqueous buffer solution, *Org. Lett.*, 2010, **12**, 2202–2205.
- 23 Y. Liu, Y. Zhao and Y. Zhang, One-step green synthesized fluorescent carbon nanodots from bamboo leaves for copper (II) copper(II) ion detection, *Sens. Actuators, B*, 2014, **196**, 647–652.
- 24 H. S. Jung, P. S. Kwon, J. W. Lee, J. I. Kim, C. S. Hong, J. W. Kim, S. Yan, J. Y. Lee, J. H. Lee, T. Joo and J. S. Kim, Coumarin-derived Cu²⁺-selective fluorescence sensor: synthesis, mechanisms, and applications in living cells, *J. Am. Chem. Soc.*, 2009, **131**, 2008–2012.
- 25 C. Zong, K. Ai, G. Zhang, H. Li and L. Lu, Dual-emission fluorescent silica nanoparticle-based probe for ultrasensitive detection of Cu²⁺, *Anal. Chem.*, 2011, **83**, 3126–3132.
- 26 Y. Su, B. Shi, S. Liao, Y. Qin, L. Zhang, M. Huang and S. Zhao, Facile preparation of fluorescent polydihydroxyphenylalanine nanoparticles for label-free detection of copper ions, *Sens. Actuators, B*, 2016, **225**, 334–339.
- 27 F. Wang and X. Liu, Recent advances in the chemistry of lanthanide-doped upconversion nanocrystals, *Chem. Soc. Rev.*, 2009, **38**, 976–989.
- 28 C. Wang, L. Chen and Z. Liu, Drug delivery with up-conversion nanoparticles for multi-functional targeted cancer cell imaging and therapy, *Biomaterials*, 2011, **32**, 1110–1120.
- 29 R. Deng, X. Xie, M. Vendrell, Y. Chang and X. Liu, Intracellular glutathione detection using MnO₂-nanosheet-modified upconversion nanoparticles, *J. Am. Chem. Soc.*, 2011, **133**, 20168–20171.
- 30 Y. Liu, M. Chen, T. Cao, Y. Sun, C. Li, Q. Liu, T. Yang, L. Yao, W. Feng and F. Li, A cyanine-modified nanosystem for in vivo up-conversion luminescence bioimaging of methylmercury, *J. Am. Chem. Soc.*, 2013, **135**, 9869–9876.
- 31 A. K. Mahapatra, S. K. Manna, D. Mandal and C. D. Mukhopadhyay, Highly sensitive and selective rhodamine-based “Off-On” reversible chemosensor for Tin (Sn⁴⁺) and imaging in living cells, *Inorg. Chem.*, 2013, **52**, 10825–10834.
- 32 S. Mandal, A. Banerjee, D. Ghosh, D. K. Mandal, D. A. Safin, M. G. Babashkina, K. Robeyns, M. P. Mitoraj, P. Kubisiak and Y. Garcia, An anion induced multi signaling probe for Hg²⁺ and its application for fish kidney and liver tissue imaging studies, *Dalton Trans.*, 2015, **44**, 13186–13195.
- 33 M. Li, X. Jiang, H. Wu, H. Lu, H. Li, H. Xu, S. Zang and T. C. Mak, A dual functional probe for “turn-on” fluorescence response of Pb²⁺ and colorimetric detection of Cu²⁺ based on a rhodamine derivative in aqueous media, *Dalton Trans.*, 2015, **44**, 17326–17334.
- 34 Z. Li and Y. Zhang, An efficient and user-friendly method for the synthesis of hexagonal-phase NaYF₄:Yb, Er/Tm

- nanocrystals with controllable shape and upconversion fluorescence, *Nanotechnology*, 2008, **19**, 345606.
- 35 Y. Dai, H. Xiao, J. Liu, Q. Yuan, P. A. Ma, D. Yang, C. Li, Z. Cheng, Z. Hou and P. Yang, In vivo multimodality imaging and cancer therapy by near-infrared light-triggered trans-platinum pro-drug-conjugated upconversion nanoparticles, *J. Am. Chem. Soc.*, 2013, **135**, 18920–18929.
- 36 B. Chen, B. Dong, J. Wang, S. Zhang, L. Xu, W. Yu and H. Song, Amphiphilic silane modified NaYF₄: Yb, Er loaded with Eu(TTA)₃(TPPO)₂ nanoparticles and their multi-functions: dual mode temperature sensing and cell imaging, *Nanoscale*, 2013, **5**, 8541–8549.
- 37 C. Liu, H. Wang, X. Li and D. Chen, Monodisperse, size-tunable and highly efficient β -NaYF₄:Yb, Er(Tm) up-conversion luminescent nanospheres: controllable synthesis and their surface modifications, *J. Mater. Chem.*, 2009, **19**, 3546–3553.
- 38 F. Wang, J. Wang and X. Liu, Direct evidence of a surface quenching effect on size-dependent luminescence of upconversion nanoparticles, *Angew. Chem., Int. Ed.*, 2010, **49**, 7456–7460.
- 39 L. Xiong, T. Yang, Y. Yang, C. Xu and F. Li, Long-term in vivo biodistribution imaging and toxicity of polyacrylic acid-coated upconversion nanophosphors, *Biomaterials*, 2010, **31**, 7078–7085.
- 40 V. Dujols, F. Ford and A. W. Czarnik, A long-wavelength fluorescent chemodosimeter selective for Cu(II) ion in water, *J. Am. Chem. Soc.*, 1997, **119**, 7386–7387.
- 41 Y. Qian, L. Cao, C. Jia, P. O. Boamah, Q. Yang, C. Liu, Y. Huang and Q. Zhang, A highly selective chemosensor for naked-eye sensing of nanomolar Cu(II) in an aqueous medium, *RSC Adv.*, 2015, **5**, 77965–77972.
- 42 T. Nguyen and M. B. Francis, Practical synthetic route to functionalized rhodamine dyes, *Org. Lett.*, 2003, **5**, 3245–3248.
- 43 R. Krämer, Fluorescent chemosensors for Cu²⁺ ions: fast, selective, and highly sensitive, *Angew. Chem., Int. Ed.*, 1998, **37**, 772–773.