



 Cite this: *RSC Adv.*, 2020, 10, 43447

# Microwave-assisted synthesis of an RGO/CdS/TiO<sub>2</sub> step-scheme with exposed TiO<sub>2</sub> {001} facets and enhanced visible photocatalytic activity†

 Zilun Ma,<sup>a</sup> Liyan Shi,<sup>a</sup> Wenwen Qu,<sup>a</sup> \*<sup>ab</sup> Qiong Hu,<sup>a</sup> Ruifang Chen,<sup>a</sup> Yijun Wang<sup>a</sup> and Zhen Chen<sup>a</sup>

Semiconductor-based heterojunction photocatalysts with a special active crystal surface act as an essential part in environmental remediation and renewable energy technologies. In this study, an RGO/CdS/TiO<sub>2</sub> step-scheme with high energy {001} TiO<sub>2</sub> facets was successfully fabricated *via* a microwave-assisted solvothermal method. The photocatalytic performance of as-prepared samples was assessed by degrading methylene blue under visible light irradiation. We found that the photocatalytic activity of the RGO/CdS/TiO<sub>2</sub> step-scheme heterojunction was related to the proportion of TiO<sub>2</sub>. A ternary sample with a TiO<sub>2</sub> content of 10 wt% exhibited superior photocatalytic performance, and approximately 99.7% of methylene blue was degraded during 50 min of visible illumination which was much higher than the percentages found for TiO<sub>2</sub>, CdS, RGO/TiO<sub>2</sub>, and RGO/CdS. The greatly improved photocatalytic performance is due to the exposure of the reactive {001} surface of TiO<sub>2</sub> and the formation of a CdS/TiO<sub>2</sub> heterojunction step-scheme, which effectively inhibits the recombination of charge carriers at the heterogeneous interfaces. Moreover, the incorporation of graphene further enhances the visible light harvesting and serves as an electron transport channel for rapidly separating photogenerated carriers. Based on the PL, XPS, photoelectrochemical properties and the free radical capturing experiment results, a possible photodegradation mechanism was proposed.

 Received 9th October 2020  
 Accepted 14th November 2020

DOI: 10.1039/d0ra08597a

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

With rapid economic and industrial development, environmental pollution and energy shortage have become two major problems for humanity.<sup>1–3</sup> Photocatalysis is a green technology that has great potential for use in environmental pollutant removal, the production of hydrogen *via* direct photolysis, and dye-sensitized solar cells.<sup>4–6</sup> Designing and synthesizing photocatalytic materials with superior performance is a hot topic due to their wide prospects for commercial applications. TiO<sub>2</sub> is a traditional semiconductor photocatalyst which has been widely applied in photocatalysis, solar cells, self-cleaning technologies and biosensors because of its excellent photocatalytic activity, high chemical stability, wide availability and environmental friendliness.<sup>7–10</sup> However, TiO<sub>2</sub> is subject to many limitations in photocatalytic performance such as weak absorption in the visible light region because of its wide band gap (3.2 eV) and it has low quantum efficiency because of the recombination

of photogenerated electron–hole pairs.<sup>11,12</sup> The photocatalytic properties of TiO<sub>2</sub> have been shown to be affected *via* its shape, size, morphology and specific surface area of TiO<sub>2</sub>.<sup>13,14</sup> In particular, the configuration of surface atoms and the extent of exposure of the reactive crystal plane determine the efficiency of the catalytic activities of TiO<sub>2</sub>.<sup>15,16</sup> Therefore, significant attention is being attracted toward controlling the surface structure of photocatalysts.

Microscale and nanoscale control of the morphology of TiO<sub>2</sub> crystal facets is considered to be an available approach to improve visible light adsorption and to achieve better separation of charge carriers. Both theoretical and experimental investigations have proved that the catalytic performance of anatase TiO<sub>2</sub> {001} surface is better than that of the thermodynamically steady {101} surface because of the higher surface energy of the {001} facet (0.90 J m<sup>−2</sup>) than that of the {101} facet (0.44 J m<sup>−2</sup>).<sup>17,18</sup> However, during the normal growth of TiO<sub>2</sub> crystals, the high energy {001} facet disappears quickly, and the crystal spontaneously forms a more thermodynamically stable {101} facet.<sup>19</sup> Some agents, such as hydrogen fluoride (HF) and an ammonium fluoride (NH<sub>4</sub>F), can be used to control the growth of the {001} plan.<sup>19</sup> Yang *et al.* first reported the anatase TiO<sub>2</sub> monocrystal with 47% exposed {001} surfaces using HF as a shape control agent. Subsequently, a battery of high energy TiO<sub>2</sub> surfaces with various morphologies have been successfully

<sup>a</sup>Faculty of Science, Kunming University of Science and Technology, Kunming 650500, China. E-mail: qwwen1977@126.com

<sup>b</sup>Key Laboratory of Unconventional Metallurgy Education Ministry, Kunming University of Science and Technology, Kunming 650093, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ra08597a



synthesized using fluorine-containing substances as a blocking agent. Research regarding the photocatalytic mechanism suggested that the higher surface energy of the {001} crystal plane is far more effective for the dissociative adsorption of the reactant molecules than the {101} plane, because of the low atomic coordination numbers of exposed atoms. Therefore, there are a large number of active unsaturated coordination Ti atoms and active surface oxygen atoms with wide bond angles of Ti–O–Ti in the {001} crystal plane.<sup>20–22</sup> In addition, density functional theory (DFT) calculations indicated that the {101} and {001} faces of anatase TiO<sub>2</sub> have different band edge positions and bandgaps, and these differences facilitate the transfer of photogenerated electrons from the {101} surface to the {001} surface.<sup>23</sup> Therefore, the recombination rate of photogenerated electron–hole pairs at the grain boundary of TiO<sub>2</sub> is reduced, which results in the improvement of the visible light photocatalytic performance of TiO<sub>2</sub>.<sup>24</sup>

Although the exposed {001} facets efficiently enhance the photocatalytic activity of TiO<sub>2</sub>, the poor visible light harvesting of TiO<sub>2</sub> still limited its application in photocatalysis. Many researches have centered around expanding the visible light response region and enhancing photocatalytic efficiency *via* loading catalysts on large-area materials, surface sensitization, metal and non-metal ion doping and semiconductor coupling.<sup>25–30</sup> Among these approaches, the formation of step-scheme (S-scheme) heterostructures *via* coupling TiO<sub>2</sub> with narrow-bandgap semiconductors is an excellent strategy for achieving high photocatalytic efficiency.<sup>31</sup> Construction of an S-type heterojunction usually requires two n-type semiconductor photocatalysts. At present, S-scheme heterojunction photocatalysts such as WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>,<sup>32</sup> TiO<sub>2</sub>/W<sub>18</sub>O<sub>49</sub>,<sup>33</sup> AgI/I-BiOAc<sup>34</sup> have been reported. CdS is recognized as one of the most promising n-type photocatalytic materials due to its negative conduction band edge position and narrow band gap (~2.4 eV).<sup>35–37</sup>

Nevertheless, in actual application, CdS nanoparticles still have drawbacks, such as photo corrosion and a tendency to agglomeration solution.<sup>38,39</sup> The large specific surface area of reduced graphene (RGO) can effectively disperse nanoparticles, reduce the agglomeration of active semiconductor components, and increase the effective active sites that of anchoring pollutants.<sup>40–43</sup> Moreover, the unique pore structure and electronic properties of RGO provide fast electron transport channels for materials, and these improve the forward migration index of photogenerated carriers and electrical conductivity.<sup>44–47</sup> Currently, there are many reports in the literature that studied the RGO/TiO<sub>2</sub> binary heterostructures with an exposed {001} plane of TiO<sub>2</sub>,<sup>48,49</sup> and it has been reported that introducing RGO greatly increases the photocatalytic performance of TiO<sub>2</sub>. However, there are few reports regarding the combination of the above modification methods to prepare an RGO/CdS/TiO<sub>2</sub> S-scheme with the exposed high energy {001} surface of TiO<sub>2</sub>. In addition, compared to the traditional synthesis method, microwave-assisted synthesis is a direct heating method that is based on *in situ* energy conversion, and this assists in rapid selection and internal heating of materials, furthers chemical reactions, and greatly reduces heating time.<sup>50</sup> We suggest that

this efficient hybrid system and microwave-assisted synthesis will afford a new and promising method for the further development of photocatalysis.

In this study, RGO/CdS/TiO<sub>2</sub> S-scheme heterojunction photocatalysts with an exposed high energy {001} facet of TiO<sub>2</sub> were synthesized *via* the microwave-assisted solvothermal method. The morphology and structure of the as-prepared samples were characterized by XRD, SEM, TEM-EDS, UV-Vis, FT-IR, photocurrent measurements and photocatalytic properties were researched *via* the visible-light catalytic degradation of methylene blue (MB). The influence of TiO<sub>2</sub> loading on the photocatalytic property of RGO/CdS/TiO<sub>2</sub> samples was also studied. As expected, the prepared composite nanomaterials showed enhanced photocatalytic activity when they are irradiated with visible light. In addition, according to PL, XPS and free radical capture experiments, the prepared RGO/CdS/TiO<sub>2</sub> photocatalyst conforms to the S-scheme photocatalytic enhancement mechanism.

## 2. Experimental

### 2.1. Materials and reagents

All reagents were of analytical purity and can be used without further processing. Thiourea was purchased from Chengdu Jinshan Chemical Reagent Co., Ltd. Ethanol, ethylene glycol, cadmium chloride, and urea were purchased from Tianjin Sailboat Chemical Reagent Technology Co., Ltd. Graphene was purchased from Shanghai Macklin Biochemical Co., Ltd. Ammonium fluoride was purchased from Tianjin Ruijinte Chemical Co., Ltd. Titanium sulphate was purchased from Sinopharm Chemical Reagent Co., Ltd.

### 2.2. Synthesis of RGO/CdS/TiO<sub>2</sub> heterojunction

The RGO/CdS/TiO<sub>2</sub> core–shell heterojunctions with exposed {001} facets of TiO<sub>2</sub> were compounded *via* a two-step, microwave-assisted solvothermal method.

**2.2.1. RGO/CdS.** First, 10 mg of GO and 342 mg of cadmium chloride were dispersed *via* sonication for 30 min in 10 mL of ethylene glycol to form a solution of GO nanosheets. Then, 342 mg of thiourea and 100 mg of urea were dissolved in another 10 mL of ethylene glycol, and the solution was added dropwise to the GO mixed solution *via* rate-controlled titration (5 mL/30 min) under sonication for 30 min. Next, the mixture was removed into a 35 mL microwave reaction tube that was put it into an automated focused microwave reaction system (DISCOVER CEM Co., microwave output power of 300 W and frequency of 2450 MHz) and microwave heated at 120 °C for 40 min. After reaction, the product was filtered with a microporous membrane and washed several times with deionized water and ethanol. Finally, the obtained sample was desiccated at 60 °C for 12 h in a vacuum oven, and the RGO/CdS (GC) composite was obtained. A weight content of 5 wt% GO in the RGO/CdS system showed the best photocatalytic activity compared to other GO contents, as reported in our previous work.<sup>51</sup>

**2.2.2. RGO/CdS/TiO<sub>2</sub>.** The RGO/CdS sample (0.4 g) and a certain amount of titanium sulfate were dissolved into 10 mL of ethanol using ultrasonication for 30 min. Then, 18.5 mg of ammonium fluoride was dissolved into 5 mL of deionized water, and the solution was injected into the RGO/CdS mixture *via* rate-controlled titration (5 mL/30 min) under ultrasonication for 30 min to form a uniform solution. The mixed solution was then put into the microwave reaction tube and treated at 120 °C for 4 h. Finally, the precipitate was filtered with a microporous membrane, washed several times with deionized water and absolute ethanol, collected *via* centrifugation, and desiccated at 60 °C for 12 h in vacuum to obtain RGO/CdS/TiO<sub>2</sub>. Scheme 1 shows the synthetic route for the RGO/CdS/TiO<sub>2</sub> photocatalysts. The as-prepared RGO/CdS/TiO<sub>2</sub> samples with 8 wt%, 10 wt%, 12 wt%, and 14 wt% TiO<sub>2</sub> are denoted as GCT-8, GCT-10, GCT-12, GCT-14, respectively, and the sample prepared with RGO/CdS is denoted as GC.

For comparison, TiO<sub>2</sub> and RGO/TiO<sub>2</sub> with exposed {001} facets were fabricated using a similar solvothermal procedure, and the products are denoted as TiO<sub>2</sub> and GT, respectively. In addition, non-high energy surface RGO/CdS/TiO<sub>2</sub> was prepared without adding ammonium fluoride, which is recorded as GCT-N.

### 2.3. Characterization

The structures and morphologies of the samples that were obtained *via* the experiments were characterized using a D/MAX-3B SEM. Microstructural information of the experimental samples was characterized using a JEM-2100 TEM. The surface element compositions and chemical states of the samples that were obtained *via* the experiment were characterized using a Thermo ESCALAB 250 XPS, and the phase structures of the samples were tested using a D/MAX-3B XRD. The functional group structure was determined using a Nicolet IS10 FTIR spectrometer. Light absorption characteristics of the samples were determined using a U-4100 UV-Vis spectrometer. Analytical structure and composition identification were determined using a Renishaw inVia Raman spectrometer, and the PL spectra of the samples were tested using a HITACHIF 4600. The light absorption performances of the catalytic samples were tested using a UV-2550 spectrophotometer. The electrochemical workstation (CHI660E, CH Instruments, China) was used to perform photoelectrochemical measurements under the irradiation of a 300 W xenon lamp. Apply a sample with an area of 1 cm<sup>2</sup> on the TFO conductive glass as a working electrode, the platinum and a saturated Ag/AgCl electrode were used as the counter and the reference electrodes, respectively. And Na<sub>2</sub>SO<sub>3</sub> solution was used as electrolyte. Electrochemical impedance spectroscopy (EIS) and transient photocurrent responses were

performed with 5 mV amplitude in a frequency range (1 Hz to 100 kHz) under open circuit potential conditions. The Brunauer–Emmett–Teller (BET) specific surface area of the sample obtained through nitrogen adsorption–desorption isotherms at 77 K by Autosorb-iQ.

### 2.4. Photocatalytic activity tests

Determination of photocatalytic performance of GCT nanocomposites by detecting degradation of MB aqueous solution under visible light irradiation. Firstly, 0.1 g of the as-prepared photocatalyst was suspended in 100 mL of 10 ppm MB aqueous solution, and a 30 min of dark-reaction with stirring would be implemented to achieve adsorption–desorption equilibrium. Then, the photocatalytic reaction was carried out in the PLS-LAX500ADJ photocatalytic reactor with a 300 W xenon lamp (with a light intensity of 496 mW cm<sup>-2</sup>) and a cut off filter ( $\lambda > 420$  nm). Aliquots (3 mL) of the as-prepared photocatalyst were removed at specific intervals of time and centrifuged to wipe off the catalyst powders. The concentration of the MB solution was analysed *via* used a spectrophotometer at a maximum absorption wavelength of 664 nm.

The photocatalytic degradation rate ( $D$ ) can be calculated as follows:

$$D = (1 - C/C_0) \times 100\% \quad (1)$$


where  $D$  is the photocatalytic degradation rate;  $C$  and  $C_0$  are the concentration at light reaction time  $t$  and the initial concentration, respectively.

In addition, radical capture experiments were carried out according to the above procedure of photocatalytic degradation test. Before the visible light irradiation, 2 mmol L<sup>-1</sup> benzoquinone (BQ) isopropanol (IPA), disodium edetate (EDTA-2Na) and silver nitrate (AgNO<sub>3</sub>) were added to the reaction system as scavengers for superoxide radicals ( $\cdot\text{O}_2^-$ ), hydroxyl radicals ( $\cdot\text{OH}$ ), photogenerated holes ( $h^+$ ) and photogenerated electrons ( $e^-$ ), respectively.

## 3. Results and discussion

### 3.1. XRD analysis

XRD is used to characterize the crystal structure of the GT and GCT samples with that has different contents of TiO<sub>2</sub> (Fig. 1). The diffraction peaks of GT appear at  $2\theta$  values of 25.3°, 37.8°, 48.1°, 53.9° and 55.1° can be assigned to the (101), (004), (200), (105), (211) and (116) crystal facets, respectively, of anatase-phase of TiO<sub>2</sub> (JCPDS no. 21-1272).<sup>52</sup> Anatase TiO<sub>2</sub> exposes (101), and their peak intensities are much higher than other diffraction peaks, which corresponds to the {001} high-energy facets of TiO<sub>2</sub>.<sup>53</sup> The crystallite size of TiO<sub>2</sub> is estimated using Scherrer's formula,<sup>54</sup> and the average size of TiO<sub>2</sub> for GT samples was 43.7 nm. Compared to the GT sample, GCT sample exhibited additional diffraction peaks located at  $2\theta$  values of 24.8°, 26.5°, 28.2°, 36.6°, 43.7°, 47.8°, and 51.8°, and these can be indexed to the (100), (002), (101), (102), (110), (103), and (112) crystal faces, respectively, of CdS (JCPDS no. 41-1049). The characteristic peaks of TiO<sub>2</sub> in the GCT sample is not obvious

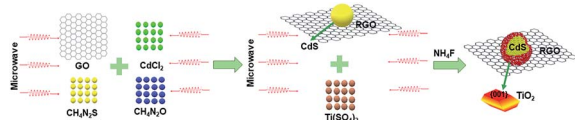

Scheme 1 Synthetic route of GCT photocatalysts.

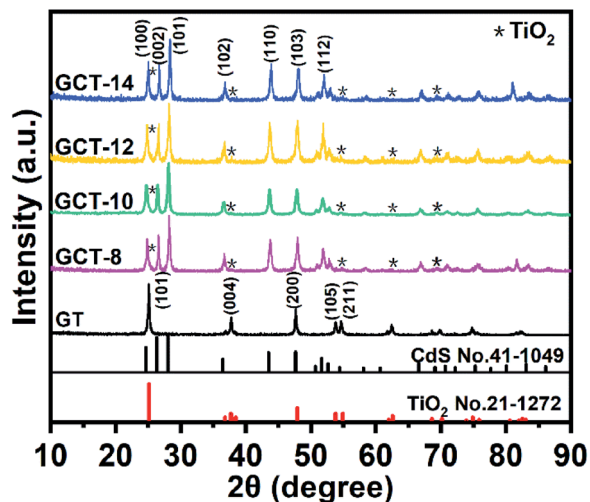


Fig. 1 XRD patterns of GT and GCT with different contents of  $\text{TiO}_2$  ( $\text{TiO}_2$  in samples are designated with asterisk \*).

because the proportion of  $\text{TiO}_2$  in the sample is low and the characteristic peaks of (101) surface of  $\text{TiO}_2$  largely overlap with the peak of (100) surface of CdS. Hence, it is difficult to observe the enhancement of intensity of (101) peaks of  $\text{TiO}_2$  with the increase of its proportion in XRD patterns. But when we compared with the standard card as well as the relative intensity of (100) vs. (002) peaks of GCT samples, we find that the relative intensity of (100) vs. (002) enhances with the increasing the proportion of  $\text{TiO}_2$ , which imply the enhancement of (101) facet of  $\text{TiO}_2$ . The enhanced intensity of the (101) facet represents the enhancement of the proportion of the exposed {001} facets. Notably, after solvothermal treatment, the characteristic diffraction peak of GO near  $12.2^\circ$  disappeared, which suggests that most of the GO was reduced. Furthermore, no typical RGO diffraction peaks appeared in the XRD patterns for GT and GCT because the weak RGO diffraction peak at  $23.0^\circ$  is overlapped by the stronger peak of CdS, which occurs at  $24.8^\circ$ .

### 3.2. SEM and TEM-EDS analysis

To visualize the morphologies of the GT, GC, and GCT-10 composites, we performed SEM and TEM-EDS characterization. Fig. 2(a), (b) and (c) show the SEM images of GT, GC, and GCT-10, respectively.  $\text{TiO}_2$ , CdS, and  $\text{TiO}_2/\text{CdS}$  nanoparticles in GT, GC, and GCT-10 grow in high density and are uniformly distributed on the gauze-like RGO sheet, which are subjected to hydrothermal treatment to increase the number of wrinkles. RGO not only supports CdS and  $\text{TiO}_2$  nanoparticles, but it also prevents their aggregation.<sup>55</sup> Fig. 2(d), (e), and (f) show TEM images of GT, GC, and GCT-10 samples, respectively, at the same magnification. In Fig. 2(d), nanocrystalline  $\text{TiO}_2$  is largely dispersed on RGO and is consisted of well-faceted nanocrystals with homogeneous particle size around 40 nm; this observation is consistent with the XRD results. Viewed from different perspectives, truncated rhombus, square and hexagon shapes can be seen in the TEM images, and these may be ascribed to the highly truncated octahedral bipyramidal structure that

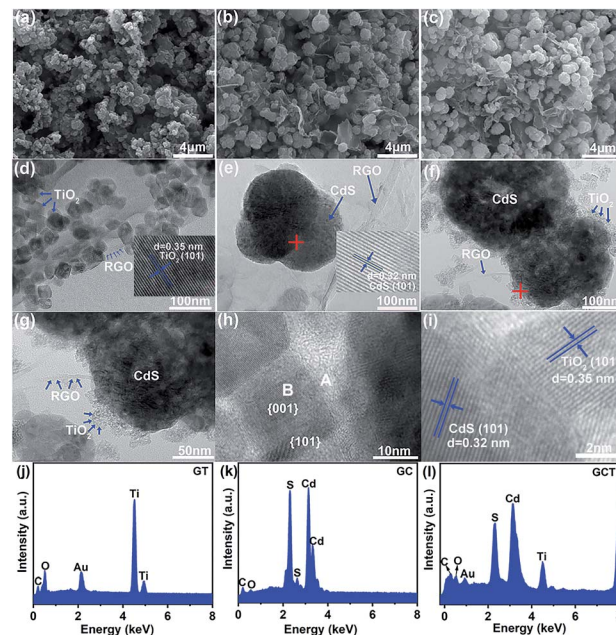


Fig. 2 SEM images of GT (a), GC (b) and GCT-10 (c). TEM images of GT (d), GC (e), and GCT-10 (f–i). EDS diagrams of GT (j), GC (k) and GCT-10 (l).

results when ammonium fluoride is used as a morphology control agent. The inset in Fig. 2(d) clearly shows lattice fringes of  $\text{TiO}_2$ . The lattice spacing is 0.35 nm and corresponds to the (101) plane of anatase  $\text{TiO}_2$  (JCPDS no. 21-1272). In the light of the symmetries of anatase  $\text{TiO}_2$ ,<sup>23</sup> the two thick and square surfaces in the crystal structure of the nanoparticles correspond to the {001} facet, and the other eight surfaces on the side of the truncated octahedral bipyramid correspond to the {101} facet. According to the combined XRD analysis with the SEM and TEM images, it can be concluded that the high energy {001} facets are successfully exposed in the GT sample. In the case of GC, CdS displays spherical nanoparticles that have diameters of approximately 200 nm. The lattice spacing of CdS in GC is 0.32 nm and corresponds to the (101) crystal plane of CdS (JCPDS no. 41-1049) (inset in Fig. 2(c)). Fig. 2(f)–(i) show the TEM images of the ternary GCT-10 composite. In Fig. 2(f) and (g), the morphology of GCT-10 sample is similar to that of the GC spherical nanoparticles, and the average size of the nanoparticles is 250–300 nm. The lamellar structure of multilayers of RGO stacked together exhibits a curly edge. In particular, the nanocrystalline  $\text{TiO}_2$  coated on the surface of CdS forms a core-shell structural heterojunction. The coated  $\text{TiO}_2$  shell protects the CdS nanoparticles from aggregation, photocorrosion, or effects of other reagents,<sup>56,57</sup> and this indicates improved photocatalytic activity. Further observation with high magnification TEM images (Fig. 2(h)) shows a truncated octahedral bipyramidal structure of  $\text{TiO}_2$  in GCT-10 sample which is similar to that in GT. The side length of the bipyramid is approximately 20 nm, which is smaller than that in GT because of the lower concentration of  $\text{TiO}_2$  in the GCT-10 composite. This observation further demonstrated that the high energy {001} facet of

TiO<sub>2</sub> was fabricated. The lattice fringes of the GCT-10 sample are obviously seen in the enlarged HRTEM image in Fig. 2(i). The lattice spacings of 0.35 nm and 0.32 nm corresponds to the anatase TiO<sub>2</sub> (101) and CdS (101) crystal facets, respectively, and these values indicate the intimate integration of TiO<sub>2</sub> and CdS. In addition, compared with GCT-10, GCT-N show different morphology of TiO<sub>2</sub>. The TEM images exhibit many spherical and irregular TiO<sub>2</sub> nanoparticles on the surface of CdS (Fig. S1(a) and (b) of ESI†). By analysis of the HRTEM image, we cannot observe any truncated octahedral bipyramidal structure, indicating no {001} facets TiO<sub>2</sub> are exposed. The measured lattice spacing of GCT-N is 0.35 nm, which can be attributed to the (101) plane of anatase TiO<sub>2</sub> (Fig. S1(c) of ESI†). Fig. 2(j), (k), (l) and S1(d)† show EDS diagrams of the GT, GC, GCT-10 and GCT-N samples, respectively. As shown, the samples contain five elements (C, Ti, O, Cd, and S), and this further confirms the presence of TiO<sub>2</sub>, CdS, and RGO in the heterostructures.

### 3.3. XPS analysis

XPS detections are performed to further investigate the chemical composition and elemental chemical states in the GC, GT, and GCT-10 samples. The full XPS spectrum of the GC, GT, and GCT-10 samples are shown in Fig. 3(a). The GCT-10 sample shows Ti 2p, Cd 3d, O 1s, S 2p and C 1s orbitals, and the corresponding binding energies are 459.2 eV, 530.3 eV, 530.0 eV,

161.7 eV and 284.4 eV, respectively. This indicates that TiO<sub>2</sub>, CdS, and graphene were successfully composited, which is in well accordance compliance with the XRD and EDS results. Fig. 3(b)–(f) show a comparison of high resolution XPS spectra of Ti 2p, Cd 3d, O 1s, S 2p, and C 1s for the GT, GC, and GCT-10 samples. The Ti 2p peaks of GT at 458.6 eV and 464.3 eV are attributed to Ti 2p<sub>3/2</sub> and Ti 2p<sub>1/2</sub>, respectively. GCT-10 shows a slight negative shift (0.3 eV) in the Ti 2p binding energy compared to that of GT. Meanwhile, the Cd 3d peaks of GC at 404.3 eV and 411.0 eV are corresponded to Cd 3d<sub>5/2</sub> and Cd 3d<sub>3/2</sub>, respectively (Fig. 3(c)). Two similar peaks at 405.3 eV and 412.0 eV are detected in GCT-10, which shift towards the higher energy region by 1.0 eV, compared to those of GC. Moreover, the characteristic peaks of the O 1s spectra of GT samples at 529.6 eV are associated with Ti–O. The corresponding O 1s peak of GCT-10 is located at 529.5 eV, which also slightly shifts toward lower binding energy by 0.1 eV. The corresponding binding energies of –OH in GT and GCT-10 are 531.1 eV and 531.4 eV, respectively. The other peak in the O 1s spectrum are located at 532.3 eV in the GT and GCT-10 samples and are attributed to C–O. The S 2p peaks of GC at 160.9 eV and 162.1 eV are attributed to S 2p<sub>3/2</sub> and S 2p<sub>1/2</sub>, respectively. Compared with GC, GCT-10 has moved forward 0.1 eV. Compared with the binary compounds, GCT-10 shows the decrease in the binding energies of Ti 2p and O 1s, suggesting an increase in electronic density on the TiO<sub>2</sub>. On the contrary, the increase in the binding energies of Cd 3d and S 2p suggest a decrease in electronic density on the CdS. The opposite shift of binding energy indicates the electrons migration pathway across the heterogeneous interface of TiO<sub>2</sub> and CdS. When TiO<sub>2</sub> is deposited on CdS, the close interfacial contact between TiO<sub>2</sub> and CdS makes it possible to transfer electrons from CdS to TiO<sub>2</sub> according to the more negative Fermi level and smaller work function of CdS than TiO<sub>2</sub> until the Fermi levels of TiO<sub>2</sub> and CdS are the same,<sup>58</sup> which is in well agreement with the S-scheme mechanism. In addition, Fig. 3(f) shows the C 1s of GO, GC, and GCT-10 samples. The binding energy at 284.4 eV, 286.2 eV and 532.3 eV is attributed to C–C, C–O and C=O of GCT samples, respectively. In the GC sample, the peak values of C–C, C–O and C=O are 284.6 eV, 286.2 eV and 288.3 eV, respectively. Compared with GO, the strength of the peak that corresponds to the oxygen-containing functional groups (C–O) in the GC and GCT composite is significantly less than that in GO (Fig. 3(f)). This indicates that most of the oxygen-containing functional groups are successfully removed and that GO is efficiently reduced to RGO after it is fabricated with CdS and TiO<sub>2</sub>. RGO serve as an electron acceptor and transport channel for fast separation and migration of photogenerated electrons generated from the catalysts, which enhances the conductivity of the sample. Therefore, the well-fabricated S-scheme TiO<sub>2</sub>/CdS heterostructure and the introduction of RGO is favourable for the GCT samples with enhanced photocatalytic activity.<sup>59</sup>

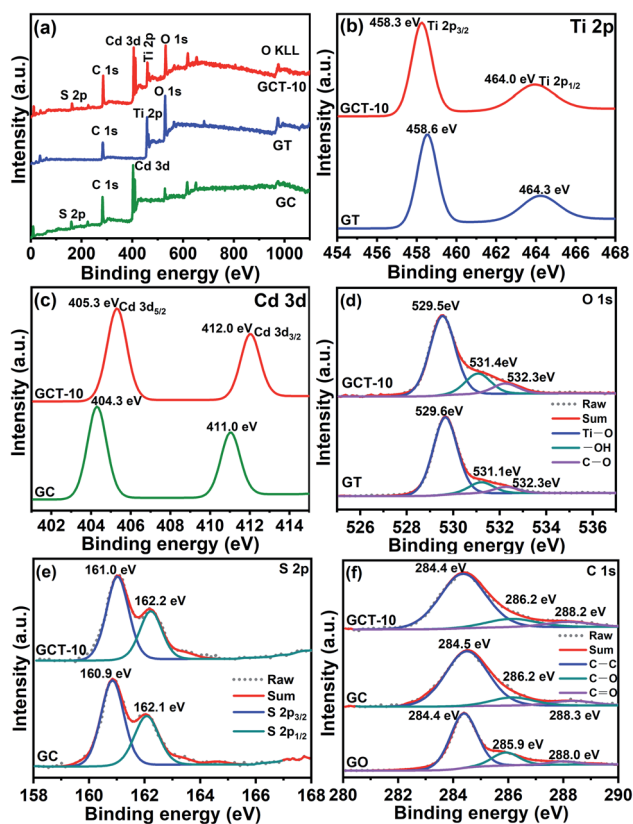


Fig. 3 XPS spectra of GC, GT, GCT-10 samples (a) and comparison of high-resolution XPS spectra of Ti 2p (b), Cd 3d (c), O 1s (d), S 2p (e) and C 1s (f) of GC, GT, and GCT-10.

### 3.4. Optical properties

**3.4.1. PL analysis.** PL spectroscopy is an effective technique to characterize the charge carrier trapping and transfer on the

catalyst surface. As seen in Fig. 4, both pure TiO<sub>2</sub> and CdS exhibit significant PL emission near 450 nm and 550 nm respectively, because of the faster recombination of photoinduced electron-hole pairs. The intensity of the PL emission peaks of GT and GC are much weaker than those of pure TiO<sub>2</sub> and CdS, respectively, indicating the efficient separation of the electron-hole pairs after the introducing of RGO. Remarkably, GCT exhibits the lowest PL intensity compared to that of GT and GC. This indicates that the formation of a TiO<sub>2</sub>/CdS heterojunction in the ternary sample can further impede the recombination of photogenerated charge carriers due to the presence of the built-in electric field between CdS and TiO<sub>2</sub> at the heterogeneous interface.

**3.4.2. Raman analysis.** We record the Raman spectra of GO, GT, GC, and GCT-10 (Fig. 5). The Raman peaks at 1353 cm<sup>-1</sup> and 1603 cm<sup>-1</sup> represent for the D-band and G-band of GO caused by sp<sup>2</sup> hybridization. The D-band is derived from the vibration of the crystalline carbon edge of graphite, which consists of disordered carbon. The G-band is originated from the in-plane stretching movement of the C-C bond, which is the basic vibration mode of GO. The D-band and G-band were observed in GC, GT, and GCT with  $I_D/I_G$  values of 0.85, 0.91, and 1.49 respectively, and they were all higher than the 0.80 of GO. The increased  $I_D/I_G$  values suggest a further reduction of GO during the synthetic reaction process. This result indicates that GO achieved deoxygenation and reduction, which is consistent with the C 1s XPS analysis.

**3.4.3. FT-IR analysis.** FT-IR spectra of GT, GC, and GCT samples with at different TiO<sub>2</sub> contents are shown in Fig. 6. The intensive vibration band is generated between 400 and 800 cm<sup>-1</sup>. Due to the bending vibration (515 cm<sup>-1</sup>) and tensile vibration (480 cm<sup>-1</sup>) of the Ti-O-Ti bond,<sup>60</sup> which suggests the interaction between TiO<sub>2</sub>-CdS (or TiO<sub>2</sub>) and RGO. The existence of the Ti-O-C bond (below 900 cm<sup>-1</sup>)<sup>61</sup> indicates that TiO<sub>2</sub> is not simply deposited on the surface of graphene during the preparation of the GT composite. Instead, it forms a chemical bond with graphene, and the chemical bond promotes the stability of TiO<sub>2</sub> in graphene. The absorption peaks at 1640 cm<sup>-1</sup> and 1050–1200 cm<sup>-1</sup> in GCT and GC correspond to the stretching

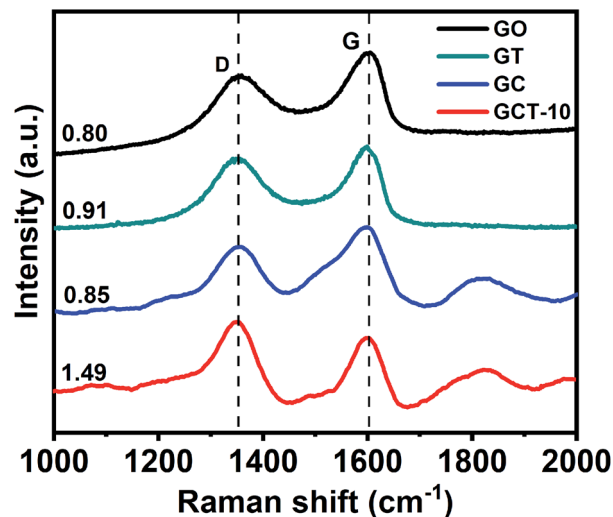


Fig. 5 Raman images of GO, GT, GC, and GCT-10.

vibration of Cd-S. With increasing TiO<sub>2</sub> content in the ternary composite, the peak intensity of the stretching vibration of Cd-S becomes gradually weaker. For each sample, the broad absorption peak near 3346 cm<sup>-1</sup> was assigned to the stretching vibration of the hydroxyl group (-OH). This indicates a strong interplay between the -OH groups on the surface of the composite, which is beneficial for preventing agglomeration of CdS nanoparticles and for improving the dispersion and stability of CdS on the surface of RGO. The characteristic peaks at 2900 cm<sup>-1</sup>, 1400 cm<sup>-1</sup>, 1057 cm<sup>-1</sup>, and 1570 cm<sup>-1</sup> correspond to the saturated C-H stretching vibration, methylene bending vibration, C-O-C stretching vibration, and graphene sp<sup>2</sup> hybrid carbon skeleton vibration.

**3.4.4. UV-vis DRS analysis.** Ultraviolet-visible diffuse reflectance spectroscopy (UV-vis DRS) was used to characterize the light absorption properties of the prepared catalyst samples.

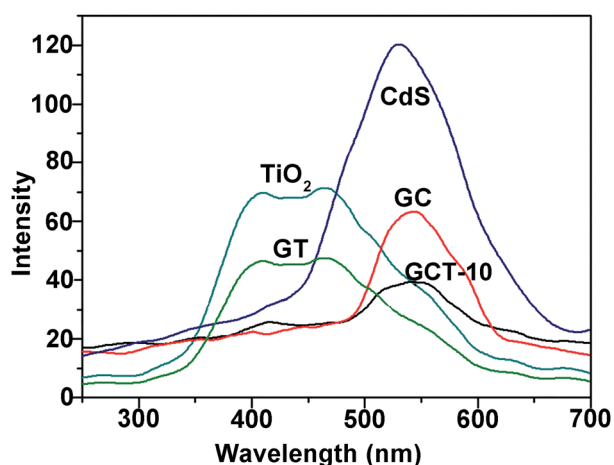


Fig. 4 PL spectra of TiO<sub>2</sub>, CdS, GT, GC, and GCT-10 samples.

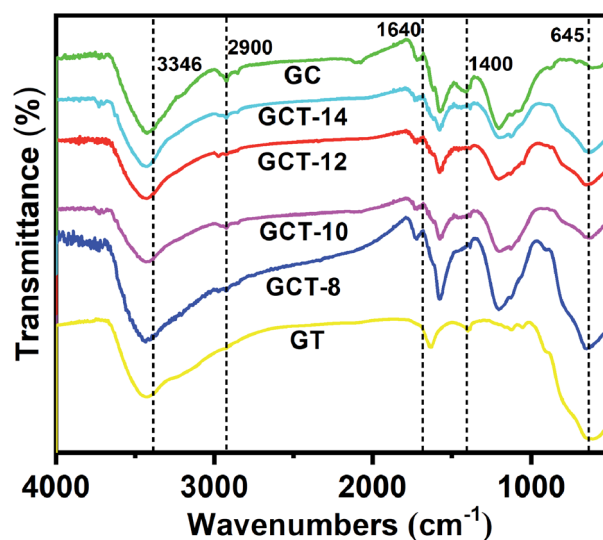


Fig. 6 FT-IR spectra of GC, GT, and GCT with different TiO<sub>2</sub> contents.

As shown in Fig. 7(a), GT has a powerful absorption band in the wavelength range of 350–400 nm, and this corresponds to the photo absorption edge of anatase TiO<sub>2</sub>. After the formation of the GCT heterojunction, the absorption edge of the ternary composite material showed an obviously red shift to the visible region of 450–550 nm, which corresponds to the photo absorption edge of CdS. Moreover, the presence of RGO in the binary and ternary systems greatly broadens the range of light absorption over the entire visible spectrum and enhances the absorption intensity, which is beneficial for effectively using solar energy.<sup>62</sup> Remarkably, the visible light absorption intensity of the ternary systems is strongly related to the loading amount of TiO<sub>2</sub>. In the visible light region of 500–800 nm, the GCT-10 sample (which has a TiO<sub>2</sub> content of 10 wt%) presents the strongest absorption intensity. When the TiO<sub>2</sub> content was further increased, the light absorption intensity decreased. A possible reason for this is that excess TiO<sub>2</sub> may shield CdS from visible light harvesting, and thus CdS cannot be efficiently stimulated by visible light. Additionally, the forbidden band width of the samples can be determined from the  $(\alpha h\nu)^2/(\alpha h\nu)^{1/2}-h\nu$  curve.<sup>63</sup> As shown in Fig. 7(b), the bandgap values of the obtained GCT-8, GCT-10, GCT-12, and GCT-14 samples are 2.23 eV, 2.06 eV, 2.19 eV, and 2.20 eV, respectively, and these are lower than that of GC (2.27 eV), GT (3.07 eV), TiO<sub>2</sub> (3.19 eV), and CdS (2.58 eV). The narrowing of the band width is beneficial for electron excitation *via* exposure to visible light irradiation, resulting in improved photocatalytic activity.

### 3.5. Photoelectrochemical properties

The interfacial charge-carrier separation and transfer efficiency of the GCT-10, GCT-N, GT and GC samples was investigated by photoelectrochemical measurements. Fig. 8(a) shows the transient photocurrent response of different samples under the same wavelength (420 nm) of light. It can be found that all samples will immediately detect a significant current in the light (ON), and will drop to almost zero in the dark (OFF) condition. After repeated ON/OFF cycles, the transient photocurrent response of GC, GT, GCT-N, and GCT can still be reproducible and stable. It is widely accepted that the reason for the generation of photocurrent is the diffusion of photo-generated electrons and the capture of photo-induced holes in the electrolyte.<sup>4,5,62</sup> Compared with GC, GT, GCT-N, GCT has the highest photocurrent response, suggesting more efficient

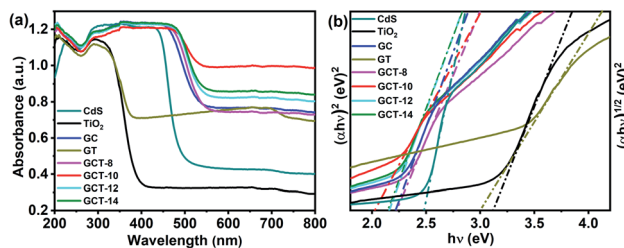


Fig. 7 UV-vis diffuse reflectance spectra (a) and the corresponding bandgap (b) of the blank, TiO<sub>2</sub>, CdS, GC, GT, and GCT samples with different TiO<sub>2</sub> contents.

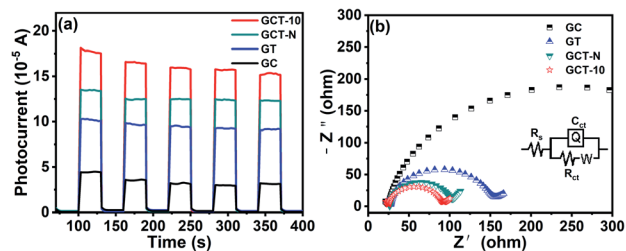


Fig. 8 Transient photocurrent response (a) and electrochemical impedance spectroscopy (EIS) Nyquist impedance plots (b) of TiO<sub>2</sub>, CdS, GT, GC, and GCT-10 samples.

separation and longer lifetimes for the photo-excited carries of GCT-10. Fig. 8(b) shows the experimental results of electrochemical impedance spectroscopy (EIS) Nyquist impedance plot, under the visible light irradiation.  $R_s$  represents the solution impedance,  $R_{ct}$  represents the charge transfer impedance, and  $C$  is the electric double layer capacitance.<sup>14,64,65</sup> The  $R_s$  of GC, GT, GCT-N and GCT-10 samples correspond to 24.10  $\Omega \text{ cm}^2$ , 26.78  $\Omega \text{ cm}^2$ , 25.96  $\Omega \text{ cm}^2$  and 24.43  $\Omega \text{ cm}^2$ , respectively. The similarity of  $R_s$  indicates that the photocurrent test is measured in the same environment. The  $R_{ct}$  of GC, GT, GCT-N and GCT-10 samples are 427.9  $\Omega \text{ cm}^2$ , 123.7  $\Omega \text{ cm}^2$ , and 71.85  $\Omega \text{ cm}^2$  are 65.43  $\Omega \text{ cm}^2$ . We can observe that the order of the impedance arc radius of the samples is GCT < GCT-N < GT < GC. Obviously, the impedance arc radiuses of ternary composites are smaller than those of the binary ones. GCT-10 shows the smallest impedance arc radius among these four samples, indicating the best electrical conductivity, which will prompt the effective migration of the photo-induced carries and reduced charge transfer resistance, thus the photocatalytic efficiency can be greatly enhanced.

### 3.6. Photocatalytic performance

Degradation of an MB aqueous solution exposed to visible-light irradiation was used to evaluate the photocatalytic activities of the GCT heterostructures with different amounts of TiO<sub>2</sub> loading were evaluated *via* the degradation of an MB aqueous solution exposed to visible light. MB is a cationic dye that is used in dyeing processes, and it is often use as a model for evaluating photocatalysts. Fig. 9(a) shows the relationship between  $C/C_0$  of MB degradation in different samples and irradiation time, where  $C$  is the concentration of MB at time  $t$  and  $C_0$  is the initial concentration of MB. Obviously, in the absence of photocatalyst, the self-degradation of MB is almost insignificant. For the 30 min reaction in the dark, each sample underwent little adsorption of MB, suggesting that adsorption-desorption equilibrium was established. The CdS, TiO<sub>2</sub>, GC, GT, and GCT samples showed approximately 5%, 19.5%, 24.6%, 32.2%, and 26.5% adsorption of MB molecules, respectively, and these values indicate that adsorption in the dark has negligible effect on the photocatalytic activities. However, under visible light irradiation, compared with those of TiO<sub>2</sub>, CdS, GC and GT, the MB degradation photocatalytic performance of the GCT-10 composites was greatly enhanced. Moreover, the

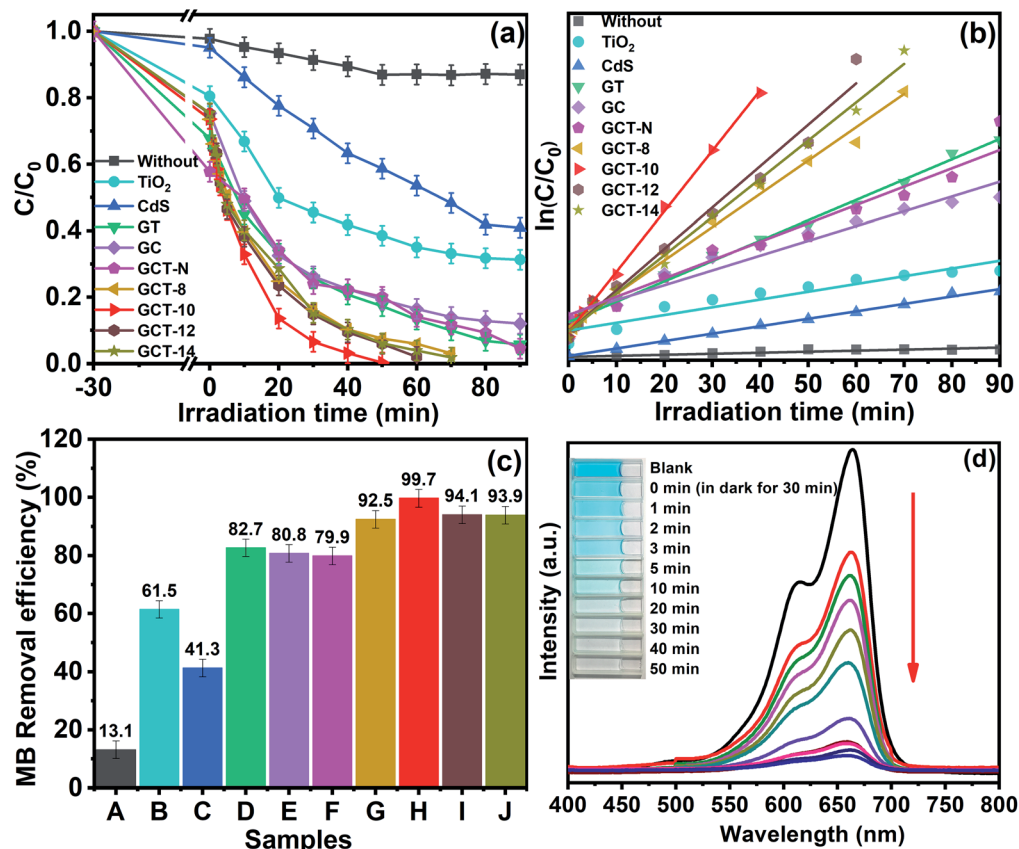


Fig. 9 Photocatalytic activity (a) and first order kinetics (b) of the without,  $\text{TiO}_2$ , CdS, GC, GT, GCT-N and GCT samples with different  $\text{TiO}_2$  content; degradation efficiency (c) of the without (A),  $\text{TiO}_2$  (B), CdS (C), GT (D), GC (E), GCT-N (F), GCT-8 (G), GCT-10 (H), GCT-12 (I) and GCT-14 (J) as-prepared samples for MB solution ( $10 \text{ mg L}^{-1}$ ) at 50 min; temporal evolution of the UV-vis spectra of MB solution in the presence of GCT-10 (d).

photocatalytic efficiency of the GCT samples are related to the proportion of  $\text{TiO}_2$  in the composites. GCT-10 (which has a  $\text{TiO}_2$  content of 10 wt%) exhibits the highest MB degradation rate (99.70%) at a reaction time of 50 min. Under the similar conditions, the MB degradation rates for CdS,  $\text{TiO}_2$ , GC, and GT only reach 41.3%, 61.5%, 80.8%, and 82.7%, respectively (Fig. 9(c)). The photocatalytic performance of the GCT composites is significantly improved due to the S-scheme heterostructure between  $\text{TiO}_2$  and CdS, and the good dispersity and electrical conductivity of RGO. By comparing the GCT-10 and GCT-N samples we can find that the MB degradation rates for GCT-N reached 79.9%, which is less about 20% than the GCT-10 sample under the same conditions. Obviously, the difference of photocatalytic activity between the two samples can be ascribed to the different morphology of  $\text{TiO}_2$ . The  $\text{TiO}_2$  with high energy {001} facet play a key role in determining the overall photocatalytic activity of GCT-10 composite through effectively accelerating the separation and transfer of carrier charges between the heterogeneous interface and promoting the dissociative adsorption of organic molecules on the reactive surface. The rate constant of MB degradation can be normalized to specific surface area to evaluate the contribution of surface area to the enhanced photocatalytic activity.<sup>66</sup> In order to calculate the surface area of the sample, we made an adsorption

equilibrium isotherm (Fig. S2(a) and (b)†). From the Table 1 we can see that the BET surface area of GCT samples slightly increase with the enhancement of  $\text{TiO}_2$  proportion, and the BET surface area of all ternary samples is in the range of 21–24  $\text{m}^2 \text{g}^{-1}$ , respectively. When dividing BET by  $k$  respectively, the normalized rate constants of MB photodegradation ( $k'$ ) are 0.0020, 0.0035, 0.0023, and 0.0021  $\text{min}^{-1} \text{m}^{-2}$ , respectively. The GCT-10 show the highest  $k'$ , indicating the superior photocatalytic performance for MB degradation. Apparently, the

Table 1 Kinetic parameters of without,  $\text{TiO}_2$ , CdS, GT, GC, GCT-N and GCT samples with different  $\text{TiO}_2$  content

$\text{TiO}_2$ content	$k/\text{min}^{-1}$	$R^2$	BET/ $\text{m}^2 \text{g}^{-1}$	$k'/\text{min}^{-1} \text{m}^{-2}$
Without	0.0013	0.8289	—	—
CdS	0.0023	0.8289	7.6	0.0003
$\text{TiO}_2$	0.0101	0.8894	60.0	0.0002
GC	0.0192	0.9910	5.8	0.0033
GT	0.0264	0.9922	62.6	0.0004
GCT-N	0.0238	0.9055	20.8	0.0011
GCT-8	0.0432	0.9922	21.9	0.0020
GCT-10	0.0785	0.9988	22.1	0.0035
GCT-12	0.0537	0.9828	23.1	0.0023
GCT-14	0.0496	0.9940	23.7	0.0021



contribution of surface area to the enhanced photocatalytic activity is not significant for GCT samples. Moreover, all GCT samples show much lower BET surface area compared to TiO<sub>2</sub> and GT, but exhibit higher photocatalytic activity. Hence, the major contribution of the enhanced photocatalytic performance may come from the synergistic effect of the CdS/TiO<sub>2</sub> heterojunction step-scheme, which is related to the loading capacity of TiO<sub>2</sub> on CdS. The decrease of photocatalytic property with the further increase of TiO<sub>2</sub> content can be ascribed to the excessive TiO<sub>2</sub> loading on CdS, which hampers visible light harvesting of CdS. Therefore, an appropriate amount of TiO<sub>2</sub> is important for improving the photocatalytic ability of the GCT composite. This result is in consistent with the UV-Vis DRS analysis.

The Langmuir–Hinshelwood model is chosen to quantify the reaction kinetics of MB degradation when MB is in the millimolar range. A pseudo-first-order kinetic equation is used:  $-\ln(C/C_0) = kt$ , where  $k$  and  $t$  are the reaction rate constant and irradiation time, respectively. Fig. 9(b) shows the linear photodegradation plot of  $-\ln(C/C_0) = kt$  for MB photodegradation. The values of the rate constant  $k$  and  $R$ -squared ( $R^2$ ) for each sample can be determined from a linear fitting. The adsorption part was not considered in the reaction kinetics. Table 1 lists the values of the kinetic parameters  $k$  and  $R$ -square ( $R^2$ ). As seen in the table, GCT-10 has the highest  $k$  value (0.0785 min<sup>-1</sup>), indicating the best photocatalytic performance, which is approximately 3, 3, 4, 8, and 34 times of degradation rate of GCT-N, GT, GC, TiO<sub>2</sub>, and CdS, respectively. This result further confirms the remarkably improved photocatalytic activity of the GCT photocatalysts. Fig. 8(d) shows the temporal evolution of the UV-vis spectra of MB solution in the presence of GCT-10 with visible light irradiation. A rapid decrease in MB absorption was observed at a maximum wavelength of 664 nm, and the colour of the suspension faded from blue to light blue and then to colourless, which suggests the complete degradation of MB. In addition, there was no apparent shift in the maximum absorption band of MB, which indicates that the degradation process is not accompanied by  $N$ -demethylation of MB to generate intermediates. MB degradation may be followed by hydroxyl radicals attacking the aromatic chromophore ring, which leads to cleavage of the MB structure.<sup>67</sup> It is noteworthy that the photocatalytic effect of the as-prepared GCT samples in our study that had high energy {001} facets of TiO<sub>2</sub> was superior to that of GCT samples without exposed {001} facets,<sup>61</sup> and this implied that fabrication of TiO<sub>2</sub>-based S-scheme heterojunctions with high energy {001} facets of TiO<sub>2</sub> is a beneficial strategy for enhancing photocatalytic performance.

In addition to photocatalytic properties, the stability of the catalyst is also an important factor in its effectiveness. Therefore, GCT-10 sample were subjected to photocatalytic cycling experiments to assess their photocatalytic stability. The result reveals that after five recycling runs for MB photodegradation, the degradation rates of GCT-10 samples decreased by only 11.89% (Fig. 10). Compared with the easily photo corrosion CdS photocatalysts reported in literature, GCT-10 is considerably stable during the photoinduced reaction process, which further suggests that the ternary GCT photocatalysts have great potential for environmental remediation.

### 3.7. Photodegradation mechanism

To understand the band position and the photocatalytic mechanism of GCT heterostructures, we calculated the valence band (VB) potential  $E_{VB}$  and the conduction band (CB) potential  $E_{CB}$  of TiO<sub>2</sub> and CdS using the following empirical equations:

$$E_{VB} = \chi - E_e + 0.5E_g \quad (2)$$

$$E_{CB} = E_{VB} - E_g \quad (3)$$

where  $E_{VB}$  and  $E_{CB}$  are the valence band (VB) potential and conduction band (CB) potential, respectively;  $E_e$  is the energy of free electrons on the hydrogen scale (*ca.* 4.5 eV);  $\chi$  is the electronegativity of the semiconductor, and  $E_g$  is the estimated band gap values of prepared TiO<sub>2</sub> (3.19 eV) with high energy {001} facet and CdS (2.58 eV) from the above UV-Vis analysis. The  $\chi$  values of TiO<sub>2</sub> and CdS are 5.81 eV and 5.18 eV, respectively.<sup>68</sup> The calculated  $E_{CB}$  and  $E_{VB}$  values of TiO<sub>2</sub> are -0.29 eV and 2.91 eV, respectively, and the calculated  $E_{CB}$  and  $E_{VB}$  values of CdS are -0.6 eV and 1.98 eV, respectively. During the photodegradation process, electrons that accumulate on CB of CdS reduce O<sub>2</sub> to form  $\cdot\text{O}^{2-}$  because the calculated ECB of CdS (-0.60 eV) is more negative than the redox potential of the O<sub>2</sub>/ $\cdot\text{O}^{2-}$  redox couple (-0.33 eV, *vs.* NHE).<sup>69</sup> At the same time, holes that accumulate on VB of TiO<sub>2</sub> oxidize OH<sup>-</sup> to produce  $\cdot\text{OH}$  because the calculated VB potential of TiO<sub>2</sub> (2.94 eV) is more positive to the redox potential of the OH<sup>-</sup>/ $\cdot\text{OH}$  redox couple (1.99 eV).<sup>70,71</sup> In addition, the holes themselves have strong oxidability and directly oxidize dyes into CO<sub>2</sub> and H<sub>2</sub>O. Therefore,  $\cdot\text{OH}$ ,  $\cdot\text{O}^{2-}$ , and  $\text{h}^+$ , which are the produced active species, can participate in the reaction to achieve degradation.

To prove the accuracy of the theoretical analysis, we did a capture experiment to detect the main active substances of GCT-10 in the MB decomposition process. EDTA-2Na, AgNO<sub>3</sub>, BQ, and IPA and were used as  $\text{h}^+$ ,  $\text{e}^-$ ,  $\cdot\text{O}^{2-}$  and  $\cdot\text{OH}$  scavengers, respectively. In Fig. 11(a), when EDTA-2Na was added, the degradation efficiency for MB decreased markedly, indicating  $\text{h}^+$  is the remarkable active species in the MB photodegradation


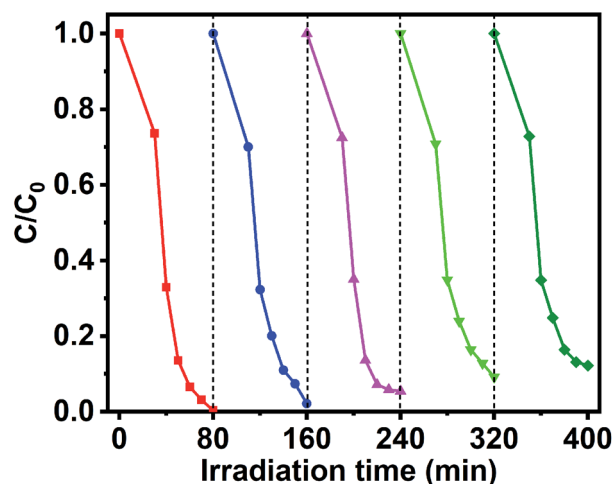


Fig. 10 Photocatalytic stability profile of GCT-10 sample.

process. Meanwhile, significant inhibition was noted when BQ and IPA were added into the reaction system, which suggest that  $\cdot\text{O}_2^-$  and  $\cdot\text{OH}$  play essential roles in the process of MB degradation. Comparatively, the decline of degradation efficiency after  $\text{AgNO}_3$  addition is less obvious than that for the other three scavengers, indicating that relatively fewer  $e^-$  were participated in the photocatalytic process. After EDTA-2Na, BQ, IPA and  $\text{AgNO}_3$  were added, the degradation efficiency for MB declined from 99.70% to 28.11%, 36.02%, 43.33% and 73.31%, respectively (Fig. 11(b)). Apparently,  $h^+$ ,  $\cdot\text{O}_2^-$ , and  $\cdot\text{OH}$  are the major active species for MB photodegradation, which are consistent with the calculated results.

Based on the band potential calculations and free radical capturing experiments, an S-scheme photocatalytic mechanism of the GCT heterogeneous photocatalyst is proposed and illustrated in Scheme 2. When  $\text{TiO}_2$  has an appropriate proportion of exposed  $\{001\}$  and  $\{101\}$  facets, the high active  $\{001\}$  facets and the efficient transfer of photogenerated electrons from the  $\{101\}$  to  $\{001\}$  planes will increase the photocatalytic activity of samples.<sup>23</sup> However, when  $\text{TiO}_2$  is loaded on CdS, a tight heterogeneous interface forms *via* the close contact between  $\text{TiO}_2$  and CdS. Since Fermi level of CdS is more negative than that of  $\text{TiO}_2$ ,<sup>52</sup> the electrons in CdS automatically flow to  $\text{TiO}_2$  through their interface until the Fermi levels are equal. Therefore, an internal electric field is generated at the interface, which is from CdS to  $\text{TiO}_2$ . When exposed to visible light, CdS and  $\text{TiO}_2$  in the GCT heterojunctions are first excited to generate electrons and holes. Relatively unused electrons in the CB of  $\text{TiO}_2$  and relatively unused holes in the VB of CdS are recombined and excluded annihilated at the interface. In contrast, the conducive holes in VB of  $\text{TiO}_2$  and conducive electrons in CB of CdS are retained because of the existence of the internal electric field. Simultaneously, RGO with a lower energy potential ( $-0.08$  eV vs. NHE)<sup>72</sup> in this system further leads to a fast charge transfer from CdS/ $\text{TiO}_2$  heterojunction to the RGO sheet through its unique  $\pi$ - $\pi$  conjugated structure. Therefore, efficient separation of photogenerated electrons and holes occurs at the ternary heterojunction, which can greatly reduce the recombination of the photoinduced charge carriers.

In brief, the promoted photocatalytic performance can be ascribed to the synergistic effect among high energy  $\{001\}$  facet  $\text{TiO}_2$ , S-type  $\text{TiO}_2/\text{CdS}$  heterojunction, and RGO. Particularly, the S-scheme heterojunction with exposed high energy  $\{001\}$  facet of  $\text{TiO}_2$  demonstrates a reasonable and efficient charge

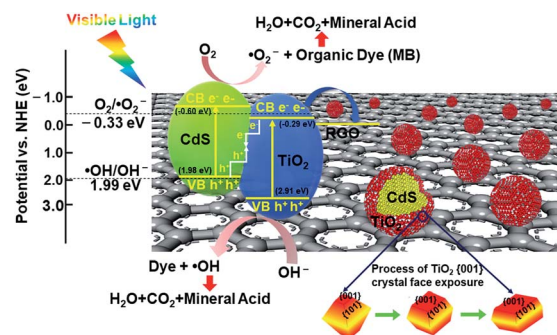

Scheme 2 Schematic illustration of enhancement mechanism of photocatalysis of GCT composite.

transfer and separation process and provide the photocatalyst with excellent redox capacity for the degradation of pollutants.

## 4. Conclusions

In summary, we report the successful fabrication of the RGO/CdS/ $\text{TiO}_2$  S-scheme photocatalyst using a facile solvothermal process with microwave irradiation. The morphology and structure characterizations demonstrate that  $\text{TiO}_2$  nanocrystals with successfully exposed high energy  $\{001\}$  facets grow on the surface of CdS spherical nanoparticles to form an S-scheme heterojunction. The nanoparticles are uniformly distributed on the support of the RGO. Most importantly, the photocatalytic performance of the ternary heterostructures is greatly enhanced compared to those of  $\text{TiO}_2$ , CdS, RGO/ $\text{TiO}_2$ , and RGO/CdS. For MB degradation under visible light, the RGO/CdS/ $\text{TiO}_2$  sample with 10 wt% of  $\text{TiO}_2$  achieved the highest degradation rate (99.70%) within 50 min, resulting in a rate that is 38.2%, 58.4%, 17.0%, and 18.9% higher than those of  $\text{TiO}_2$ , CdS, RGO/ $\text{TiO}_2$ , and RGO/CdS samples, respectively, under the same conditions. This remarkable enhancement depends on the synergistic effect among the individual constituents of the catalyst. Specifically, this enhancement results from the following: (i) exposure of high energy  $\{001\}$  facets of  $\text{TiO}_2$  greatly enhance the separation and transfer efficiency of charge carriers at the heterogeneous interfaces; (ii)  $\text{TiO}_2$  and CdS formed a step-scheme heterojunction that not only promotes the separation of useful electrons and holes, but also accelerates the recombination of relatively unnecessary electrons and holes. (iii) Introducing graphene promotes visible light utility and provides more reaction sites through large specific surface area. This work provided new insight for designing and fabricating photocatalysts through exposure of high energy facets, formation of S-scheme heterojunctions, and introduction of large surface supports. In addition, microwave-assisted synthesis is an energy-efficient and eco-friendly process, which has great potential for development of heterogeneous photocatalysts for environmental remediation.

## Conflicts of interest

There are no conflicts to declare.

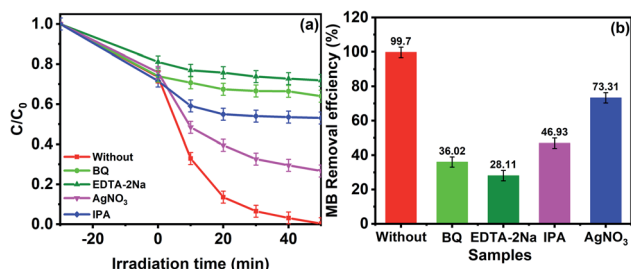


Fig. 11 Active species capture experiment during the photocatalytic degradation of MB by GCT-10 exposed to visible light.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (No. 51562018, U1402274). We are grateful to all of the contributing authors who have offered us help.

## References

- 1 D. Huang, S. Chen, G. Zeng, X. Gong, C. Zhou, M. Cheng, W. Xue, X. Yan and J. Li, *Coord. Chem. Rev.*, 2019, **385**, 44–80.
- 2 D. V. Markovskaya, A. V. Zhurenok, A. Y. Kurenkova, A. M. Kremneva, A. A. Saraev, S. M. Zharkov, E. A. Kozlova and V. V. Kaichev, *RSC Adv.*, 2020, **10**, 34137–34148.
- 3 Y. Liu, J. Chen, J. Zhang, Z. Tang, H. Li and J. Yuan, *RSC Adv.*, 2020, **10**, 30245–30253.
- 4 J. Jia, Q. Wang and Y. Wang, *J. Alloys Compd.*, 2019, **809**, 151791.
- 5 J. Low, B. Dai, T. Tong, C. Jiang and J. Yu, *Adv. Mater.*, 2019, **31**, 1–5.
- 6 Y. H. Chiu, T. F. M. Chang, C. Y. Chen, M. Sone and Y. J. Hsu, *Catalysts*, 2019, **9**, 430.
- 7 C. Zhang, Z. Xiao, T. Qin and Z. Yang, *J. Mol. Recognit.*, 2019, **32**, 1–7.
- 8 H. S. El-Sheshtawy, Z. ghubish, K. R. Shoueir and M. El-Kemary, *J. Alloys Compd.*, 2020, **842**, 155848.
- 9 M. Wang, Z. Cui, M. Yang, L. Lin, X. Chen, M. Wang and J. Han, *J. Colloid Interface Sci.*, 2019, **544**, 1–7.
- 10 J. Li, E.-H. Wu, J. Hou, P. Huang, Z. Xu, Y. Jiang, Q.-S. Liu and Y.-Q. Zhong, *RSC Adv.*, 2020, **10**, 34775–34780.
- 11 K. Xu, Z. Liu, S. Qi, Z. Yin, S. Deng, M. Zhang and Z. Sun, *RSC Adv.*, 2020, **10**, 34702–34711.
- 12 P. Y. Hsieh, J. Y. Wu, T. F. M. Chang, C. Y. Chen, M. Sone and Y. J. Hsu, *Arabian J. Chem.*, 2020, **13**, 8372–8387.
- 13 H. Zhao, S. Cui, L. Yang, G. Li, N. Li and X. Li, *J. Colloid Interface Sci.*, 2018, **512**, 47–54.
- 14 T. Lai, K. Katsumata and Y. Hsu, *Nanophotonics*, 2020.
- 15 S. Liu, J. Yu and M. Jaroniec, *Chem. Mater.*, 2011, **23**, 4085–4093.
- 16 Z. Ghasemi, V. Abdi and I. Sourinejad, *J. Alloys Compd.*, 2020, **841**, 155593.
- 17 L. Ye, J. Mao, J. Liu, Z. Jiang, T. Peng and L. Zan, *J. Mater. Chem. A*, 2013, **1**, 10532–10537.
- 18 H. G. Yang, C. H. Sun, S. Z. Qiao, J. Zou, G. Liu, S. C. Smith, H. M. Cheng and G. Q. Lu, *Nature*, 2008, **453**, 638–641.
- 19 W. J. Ong, L. L. Tan, S. P. Chai, S. T. Yong and A. R. Mohamed, *Nanoscale*, 2014, **6**, 1946–2008.
- 20 J. Wang, Z. Bian, J. Zhu and H. Li, *J. Mater. Chem. A*, 2013, **1**, 1296–1302.
- 21 J. Yu, L. Qi and M. Jaroniec, *J. Phys. Chem. C*, 2010, **114**, 13118–13125.
- 22 M. V. Sofianou, C. Trapalis, V. Psycharis, N. Boukos, T. Vaimakis, J. Yu and W. Wang, *Environ. Sci. Pollut. Res.*, 2012, **19**, 3719–3726.
- 23 J. Yu, J. Low, W. Xiao, P. Zhou and M. Jaroniec, *J. Am. Chem. Soc.*, 2014, **136**, 8839–8842.
- 24 Z. He, L. Jiang, D. Wang, J. Qiu, J. Chen and S. Song, *Ind. Eng. Chem. Res.*, 2015, **54**, 808–818.
- 25 L. L. Tan, W. J. Ong, S. P. Chai and A. R. Mohamed, *Appl. Catal., B*, 2015, **166–167**, 251–259.
- 26 J. Xiao, Y. Xie, H. Cao, F. Nawaz, S. Zhang and Y. Wang, *J. Photochem. Photobiol., A*, 2016, **315**, 59–66.
- 27 M. Zhang, Y. Xu, Z. Gong, J. Tao, Z. Sun, J. Lv, X. Chen, X. Jiang, G. He, P. Wang and F. Meng, *J. Alloys Compd.*, 2015, **649**, 190–195.
- 28 L. Luo, Y. Yang, A. Zhang, M. Wang, Y. Liu, L. Bian, F. Jiang and X. Pan, *Appl. Surf. Sci.*, 2015, **353**, 469–479.
- 29 M. Gao, L. Zhu, W. L. Ong, J. Wang and G. W. Ho, *Catal. Sci. Technol.*, 2015, **5**, 4703–4726.
- 30 J. Wang, M. Gao and G. W. Ho, *J. Mater. Chem. A*, 2014, **2**, 5703–5709.
- 31 B. Pant, N. A. M. Barakat, H. R. Pant, M. Park, P. S. Saud, J. W. Kim and H. Y. Kim, *J. Colloid Interface Sci.*, 2014, **434**, 159–166.
- 32 J. Fu, Q. Xu, J. Low, C. Jiang and J. Yu, *Appl. Catal., B*, 2019, **243**, 556–565.
- 33 R. Wang, J. Shen, W. Zhang, Q. Liu, M. Zhang, Zulfiqar and H. Tang, *Ceram. Int.*, 2020, **46**, 23–30.
- 34 X. Jia, Q. Han, M. Zheng and H. Bi, *Appl. Surf. Sci.*, 2019, **489**, 409–419.
- 35 V. U. Pandit, S. S. Arbuji, R. R. Hawaldar, P. V. Kshirsagar, A. J. Deshmukh, J. D. Ambekar, U. P. Mulik, S. W. Gosavi and B. B. Kale, *RSC Adv.*, 2015, **5**, 13715–13721.
- 36 Z. Yu, B. Yin, F. Qu and X. Wu, *Chem. Eng. J.*, 2014, **258**, 203–209.
- 37 M. J. Fang, C. W. Tsao and Y. J. Hsu, *J. Phys. D: Appl. Phys.*, 2020, **53**, 143001.
- 38 X. Ruan, H. Hu, H. Che, E. Jiang, X. Zhang, C. Liu and G. Che, *J. Colloid Interface Sci.*, 2019, **543**, 317–327.
- 39 Y. Xue, Z. Wu, X. He, Q. Li, X. Yang and L. Li, *J. Colloid Interface Sci.*, 2019, **548**, 293–302.
- 40 K. Tsai, P. Hsieh, T. Lai, C. Tsao, H. Pan, Y. Lin and Y. Hsu, *ACS Appl. Energy Mater.*, 2020, **3**, 5322–5332.
- 41 E. Mahmoudi, W. L. Ang, C. Y. Ng, L. Y. Ng, A. W. Mohammad and A. Benamor, *J. Colloid Interface Sci.*, 2019, **542**, 429–440.
- 42 H. Zhang, C. Zhai, H. Gao, N. Fu and M. Zhu, *J. Colloid Interface Sci.*, 2019, **547**, 102–110.
- 43 Y. Chen, K. Katsumata, Y. Chiu, K. Okada, N. Matsushita and Y. Hsu, *Appl. Catal., A*, 2015, **490**, 1–9.
- 44 K. Tsai and Y. Hsu, *Appl. Catal., B*, 2015, **164**, 271–278.
- 45 Y. Pu, H. Chou, W. Kuo and K. Wei, *Appl. Catal., B*, 2017, **204**, 21–32.
- 46 S. Chowdhury and R. Balasubramanian, *Appl. Catal., B*, 2014, **160–161**, 307–324.
- 47 W. Hu, Y. Chen, P. Hsieh, C. Tsao, Y. Chiu, T. M. Chang, C. Chen, M. Sone and Y. Hsu, *J. Taiwan Inst. Chem. Eng.*, 2020, **112**, 337–344.
- 48 B. Liu, Y. Huang, Y. Wen, L. Du, W. Zeng, Y. Shi, F. Zhang, G. Zhu, X. Xu and Y. Wang, *J. Mater. Chem.*, 2012, **22**, 7484–7491.
- 49 L. Gu, J. Wang, H. Cheng, Y. Zhao, L. Liu and X. Han, *ACS Appl. Mater. Interfaces*, 2013, **5**, 3085–3093.

- 50 J. h. Peng, Y. j. Zhao, Q. Ul Hassan, H. y. Li, Y. b. Liu, S. h. Ma, D. l. Mao, H. q. Li, L. c. Meng and M. Hojamberdiev, *Adv. Powder Technol.*, 2018, **29**, 1158–1166.
- 51 M. Yuan, L. Wang, W. Qu, L. Zhang, J. Zhang and Z. Chen, *Mater. Rep.*, 2019, **33**, 1602–1608.
- 52 A. Meng, B. Zhu, B. Zhong, L. Zhang and B. Cheng, *Appl. Surf. Sci.*, 2017, **422**, 518–527.
- 53 J. Wang, P. Zhang, X. Li, J. Zhu and H. Li, *Appl. Catal., B*, 2013, **134–135**, 198–204.
- 54 S. C. Pillai, J. M. Kelly, D. E. McCormack and R. Ramesh, *J. Mater. Chem.*, 2008, **18**, 3926–3932.
- 55 S. Dong, X. Ding, T. Guo, X. Yue, X. Han and J. Sun, *Chem. Eng. J.*, 2017, **316**, 778–789.
- 56 D. Ke, S. Liu, K. Dai, J. Zhou, L. Zhang and T. Peng, *J. Phys. Chem. C*, 2009, **113**, 16021–16026.
- 57 H. Zhu, R. Jiang, L. Xiao, L. Liu, C. Cao and G. Zeng, *Appl. Surf. Sci.*, 2013, **273**, 661–669.
- 58 M. Nasr, S. Balme, C. Eid, R. Habchi, P. Miele and M. Bechelany, *J. Phys. Chem. C*, 2017, **121**, 261–269.
- 59 X. Rong, F. Qiu, C. Zhang, L. Fu, Y. Wang and D. Yang, *Ceram. Int.*, 2015, **41**, 2502–2511.
- 60 Y. Ni, W. Wang, W. Huang, C. Lu and Z. Xu, *J. Colloid Interface Sci.*, 2014, **428**, 162–169.
- 61 B. Pant, M. Park, S. J. Park and H. Y. Kim, *Ceram. Int.*, 2016, **42**, 15247–15252.
- 62 S. Liu, M. Q. Yang and Y. J. Xu, *J. Mater. Chem. A*, 2014, **2**, 430–440.
- 63 C. Jia, X. Zhang, K. Matras-Postolek, B. Huang and P. Yang, *Carbon*, 2018, **139**, 415–426.
- 64 P. Y. Hsieh, Y. H. Chiu, T. H. Lai, M. J. Fang, Y. T. Wang and Y. J. Hsu, *ACS Appl. Mater. Interfaces*, 2019, **11**, 3006–3015.
- 65 Y. S. Chang, M. Choi, M. Baek, P. Y. Hsieh, K. Yong and Y. J. Hsu, *Appl. Catal., B*, 2018, **225**, 379–385.
- 66 K. H. Chen, Y. C. Pu, K. Der Chang, Y. F. Liang, C. M. Liu, J. W. Yeh, H. C. Shih and Y. J. Hsu, *J. Phys. Chem. C*, 2012, **116**, 19039–19045.
- 67 T. Zhang, T. Oyama, A. Aoshima, H. Hidaka, J. Zhao and N. Serpone, *J. Photochem. Photobiol., A*, 2001, **140**, 163–172.
- 68 M. A. Butler, *J. Electrochem. Soc.*, 1978, **125**, 228.
- 69 J. Guo, L. Shi, J. Zhao, Y. Wang, K. Tang, W. Zhang, C. Xie and X. Yuan, *Appl. Catal., B*, 2018, **224**, 692–704.
- 70 E. Gao, W. Wang, M. Shang and J. Xu, *Phys. Chem. Chem. Phys.*, 2011, **13**, 2887–2893.
- 71 Y. Huang, S. Kang, Y. Yang, H. Qin, Z. Ni, S. Yang and X. Li, *Appl. Catal., B*, 2016, **196**, 89–99.
- 72 Q. Xiang, J. Yu and M. Jaroniec, *J. Am. Chem. Soc.*, 2012, **134**, 6575–6578.