


 Cite this: *RSC Adv.*, 2020, 10, 719

The synthesis of calcium arsenate@iron arsenate coating materials and their application for arsenic-containing wastewater treatment†

 Yang Wang,^a Zhihao Rong,^a Xincun Tang ^{*a} and Shan Cao^{*b}

The current method of treating arsenic-containing wastewater is mainly to use a calcium method to synthesize stable calcium arsenate. It is easy to cause reverse dissolution by rain or other erosion, releasing arsenic into the natural world and polluting soil and groundwater. So, calcium arsenate is not an ideal material for removing and immobilizing arsenic. Iron arsenate (FeAsO₄) is much better than calcium arsenate because of its stability and acid resistance. In this study, calcium arsenate@iron arsenate coating materials were synthesized. From the results of the XRD and SEM analyses, it was shown that calcium arsenate was coated by an iron arsenate shell which consisted of nanoparticles. The stability of the coating materials was determined using the Toxicity Characteristic Leaching Procedure (TCLP). The results showed that the concentrations of As for CaHAsO₄ and Ca₃(AsO₄)₂ were 744 mg L⁻¹ and 302.2 mg L⁻¹, respectively. Arsenic was not detected through the TCLP tests for CaHAsO₄@FeAsO₄ and Ca₃(AsO₄)₂@FeAsO₄ coating materials, and the best coating condition was confirmed to be an Fe/As molar ratio of 4 : 1, pH of 4, and temperature of 50 °C. The stability of the materials showed a significant improvement. The results indicated that calcium arsenate materials could be converted to coating materials by using ferric salts. The coating materials had excellent stability in an aqueous solution. Thus, the coating was suitable for the removal and immobilization of arsenic in industrial applications. This work provided a new way to treat arsenic-containing wastewater, which was simple and economical. This method has potential for use in the field of wastewater treatment containing arsenic.

 Received 10th July 2019
 Accepted 16th December 2019

DOI: 10.1039/c9ra05278j

rsc.li/rsc-advances

1. Introduction

At present, the most common method for removing and immobilizing arsenic in industrial applications is the calcium arsenate (Ca₃(AsO₄)₂) precipitation method.^{1–3} The arsenic-containing wastewater is treated by using calcium oxide or calcium hydroxide to form a calcium arsenate precipitate.⁴ However, calcium arsenate is not stable, it easily reacts with carbon dioxide in the air and cannot exist stably in nature for very long.⁵ It is easy for reverse dissolution to occur from rain or other erosion, releasing arsenic into the natural world and polluting soil and groundwater.⁶ So calcium arsenate is not an ideal material for removing and immobilizing arsenic. The calcium arsenate can be stabilized using a treatment to make it more stable overall and resist external erosion.⁷ This is the best way to retain the economic advantages of calcium arsenate and avoid secondary pollution. Using iron arsenate (FeAsO₄) is

much better than using calcium arsenate because of its stability and acid resistance.^{8–10} It is also used to remove and immobilize arsenic.¹¹ However, the cost of the calcium salt to treat arsenic-containing wastewater is much lower than the iron salt. So most non-ferrous metal smelting companies choose the calcium arsenate method.¹² However, iron arsenate has obvious advantages in terms of the efficiency of arsenic removal and the safety of arsenic.¹³ The solubility of iron arsenate ($K_{sp} = 10^{-21}$ to 10^{-24}) is about 1 million times smaller than that of calcium arsenate ($K_{sp} = 10^{-18}$ to 10^{-21}) in water.^{14,15} Calcium arsenate can react with carbon dioxide to produce calcium carbonate and water-soluble arsenic acid, resulting in the re-dissolution of arsenic.¹⁶ In this study, the advantages and disadvantages of these two arsenates are considered. The calcium arsenate is stabilized using treatment with ferric chloride. In this research, the iron arsenate is synthesized and then calcium arsenate is coated with the synthesized iron arsenate. The iron–arsenic ratio is studied to achieve the best stabilization of calcium arsenate. Calcium hydrogen arsenate (CaHAsO₄) and calcium arsenate (Ca₃(AsO₄)₂) are the two most common calcium arsenate phases. In this research, they are synthesized and coated with iron arsenate. The Fe/As ratio, reaction time and pH are studied for the stabilization of the calcium arsenate. Furthermore, the stability of the synthesized samples was measured

^aCollege of Chemistry and Chemical Engineering, Central South University, Changsha 410083, China. E-mail: tangxincun@csu.edu.cn

^bSchool of Light Industry and Engineering, Qilu University of Technology, Shandong 250353, China. E-mail: cs1988@qlu.edu.cn

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9ra05278j



using the Toxicity Characteristic Leaching Procedure (TCLP), and its application properties were also evaluated.¹⁷

2. Material and methods

2.1 Reagents

Leaching liquid of smelting dust was used as the As(v) source. The components of the dust and leaching liquid are shown in Table 1. Analytical reagent grade calcium hydroxide (Ca(OH)₂) was used as the calcium source. Analytical reagent grade ferric chloride (FeCl₃) was used as the iron source. Analytical reagent grade nitric acid (HNO₃), and sodium hydroxide (NaOH) were used only for pH adjustment.

2.2 Calcium arsenate synthesis

A portion of arsenic-containing solution (800 mL) was taken and the pH value was adjusted to 5 using NaOH. Next, 0.75 mol of Ca(OH)₂ was dissolved ultrasonically in 200 mL of deionized water. To obtain a Ca(OH)₂ suspension, the pH value of the Ca(OH)₂ solution was adjusted to 5 using HNO₃. Then, the Ca(OH)₂ suspension was poured into the arsenic-containing solution, and the pH was adjusted to 5 with stirring. The reaction was maintained at 50 °C for 24 h. Finally, the product was washed, with suction, and dried at 60 °C. The product was named sample 1.

The synthesis process of sample 2 was same as for sample 1 except the reaction pH value was 10.

Sample 1 or sample 2 was dispersed in deionized water. A certain amount of FeCl₃ was added into the solution and then dissolved. The Fe/As molar ratios were 0.5 : 1, 1 : 1, 2 : 1, 3 : 1, 4 : 1, and 5 : 1. Then the pH of solution was adjusted to 4, 6, 7, 8, 10, or 12 using NaOH, and the reaction was left to occur for 12 h at room temperature, with stirring. Finally, the precipitations were washed with deionized water and dried at 60 °C. The products obtained were stabilized calcium arsenate@iron arsenate coated samples.

2.3 Characterization

The morphology of the synthesized products were observed using field emission scanning electron microscopy (FESEM, Hitachi S-4800, Japan). The X-ray diffraction (XRD) patterns were collected using a diffraction instrument with Cu K α radiation (Bruker D8, 40 kV, 40 mA).

2.4 Stability evaluation of the products

Leaching tests were conducted, to examine the leach ability of the precipitates, according to the Toxicity Characterization Leaching Procedure (TCLP) tests (EPA, 1994).¹⁷ Glacial acetic acid (HAc, 5.7 mL) and NaOH solution (64.3 mL, 1 mol L⁻¹) were

sequentially added to 500 mL of distilled water and then diluted to 1 L to give a pH of 4.93 \pm 0.05 to prepare the leaching agent.

The operating procedures of the leaching tests are briefly described here. The samples were each placed in PTFE bottles with extraction liquor at a liquid to solid (L/S) mass ratio of 20 : 1. The leaching tests were conducted for 16 \pm 2 h for the HAc solution. The temperature was maintained at 25 °C during the leaching tests. After leaching, the supernatant was collected using 0.8 μ m quantitative filter paper and the concentrations of arsenic and iron in the leaching solutions of the stability tests were determined using inductively coupled plasma optical emission spectroscopy (ICP-OES, PerkinElmer Optima 5300 DV, USA). The determination wavelength of As was 188.98 nm, and the detection limit of As was 0.01 mg L⁻¹.

3. Results and discussion

3.1 Characterization of samples

The synthesized samples were identified by XRD. Fig. 1(a) shows that CaHAsO₄ was synthesized successfully using the method of a previous report. As is known, the main peaks of scorodite (FeAsO₄·2H₂O) are located at approximately 30.1°, 27.8°, 16.9° and 10.9°, which can be indexed as the (221), (220), (101) and (020) lattice planes of scorodite (JCPDS no. 18-0288), respectively.¹⁸ The diffraction peak intensity was strong, and the CaHAsO₄ had excellent crystallinity. Fig. 1(b) shows that Ca₃(AsO₄)₂ was synthesized successfully by the method of the previous report. As is known, the main peaks of scorodite located at approximately 30.8° and 31.7°, can be indexed as the (020) and (021) lattice planes of Ca₃(AsO₄)₂ (JCPDS no. 01-0933).¹⁹ Sample 1 and sample 2 were the two most common calcium arsenate phases in the arsenic-containing wastewater treatment.

3.2 Analysis of calcium arsenate@iron arsenate coated samples

3.2.1 Stability analysis of CaHAsO₄@FeAsO₄. Fig. 2 shows the concentrations of arsenic found by TCLP test after sample 1 was treated by FeCl₃ to give it stability. Because of the design of the experiment, the products should be CaHAsO₄@FeAsO₄, and the synthesized CaHAsO₄ was coated by FeAsO₄. Fig. 2(a) shows the TCLP test results of the products which were reacted with different molar ratios of Fe/As at 25 °C. The concentration of arsenic was 744 mg L⁻¹ without stability treatment. This indicated that CaHAsO₄ was not stable in the solution. The concentrations of arsenic decreased when the Fe/As molar ratio was increased. The results indicated that the stability treatment by FeCl₃ obviously increased the stability of CaHAsO₄. The concentrations of arsenic were 1.075 mg L⁻¹ and 0.982 mg L⁻¹ when the Fe/As molar ratios were 4 : 1 and 5 : 1, respectively. These two results were below the standard value of TCLP (1.5 mg L⁻¹). 1.075 mg L⁻¹ and 0.982 mg L⁻¹ of the concentration were little difference. The reason for this was because the CaHAsO₄ could be completely coated when the Fe/As molar ratio was more than 4 : 1, and then the FeAsO₄ shell would prevent the continued reaction between the internal CaHAsO₄ and the FeCl₃ solution. However, it was more economical when

Table 1 Components of dust and leaching liquid

	As	K	Zn	Na	Pb
Dust (%)	46.8	0.9	0.7	0.4	14.7
Leaching liquid (g L ⁻¹)	20.1	0.5	0.1	0.2	—

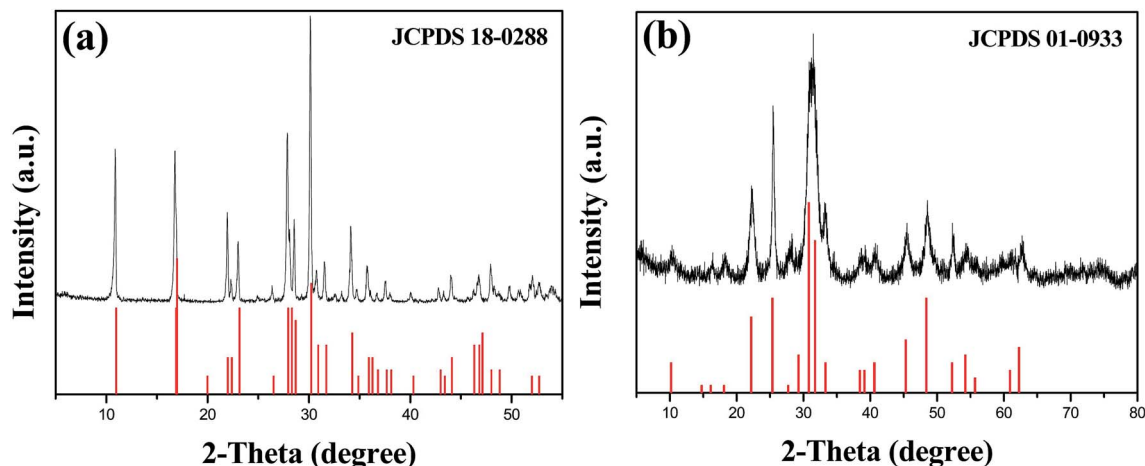


Fig. 1 The XRD patterns of (a) sample 1, (b) sample 2.

the Fe/As molar ratio was 4 : 1, so the best Fe/As molar ratio should be 4 : 1.

Fig. 2(b) shows the TCLP test results of products which were reacted at different pH values at 25 °C. The Fe/As molar ratio of the reaction was 4 : 1, and the reaction pH was 2. However, there was no precipitation because CaHAsO_4 and FeCl_3 were both dissolved completely when the pH was 2. The concentrations of arsenic obtained from the TCLP test increased when the pH value was 4 to 8. The reason for this was that CaHAsO_4 could react with Fe^{3+} and the FeAsO_4 shell formed when the solution was acidic. The concentrations of arsenic decreased when the pH value was 8 to 12. The reason for this was that Fe^{3+} would react with OH^- and form $\text{Fe}(\text{OH})_3$ preferentially when the solution was alkaline, and so FeAsO_4 could not form. So, the products were a $\text{CaHAsO}_4/\text{Fe}(\text{OH})_3$ mixture. The solution of TCLP test was acetic acid solution (HAc, $\text{pH} = 4.93 \pm 0.05$). The $\text{Fe}(\text{OH})_3$ reacted with H^+ preferentially in the TCLP test, this caused the pH value of the TCLP solution to increase. The newly produced Fe^{3+} ions reacted with CaHAsO_4 and formed FeAsO_4 , and this process made the materials more stable. The best pH of the stability treatment was 4, and the concentration of arsenic was 0.379 mg L^{-1} .

Fig. 2(c) shows the TCLP test results of the products which were reacted at $\text{pH} = 4$ at different temperatures. The Fe/As

molar ratio of the reaction was 4 : 1. The results indicated that the reaction rate increased as the temperature of the reaction increased. When the temperature was 50 °C, the CaHAsO_4 could be coated perfectly by FeAsO_4 . Arsenic was not detected by TCLP test.

3.2.2 Stability analysis of $\text{Ca}_3(\text{AsO}_4)_2@ \text{FeAsO}_4$. Fig. 3 shows the concentrations of arsenic obtained by the TCLP test after sample 2 was stability treated with FeCl_3 . Because of the design of the experiment, the products should be $\text{Ca}_3(\text{AsO}_4)_2@ \text{FeAsO}_4$, as a result of the synthesized $\text{Ca}_3(\text{AsO}_4)_2$ being coated by the FeAsO_4 . Fig. 3(a) shows the TCLP test results of products which were reacted with different Fe/As molar ratios at 25 °C. The concentration of arsenic was 302.2 mg L^{-1} without stability treatment. This indicated that $\text{Ca}_3(\text{AsO}_4)_2$ was not stable in the solution. This was the same as the results given in Section 3.2.1, and it indicated that the stability treatment could increase the stability of $\text{Ca}_3(\text{AsO}_4)_2$, and the best Fe/As molar ratio was 4 : 1.

Fig. 3(b) shows the TCLP test results of the products which were reacted at different pH values at 25 °C. The Fe/As molar ratio of reaction was 4 : 1 and the reaction pH was 2. However, there was no precipitation because $\text{Ca}_3(\text{AsO}_4)_2$ and FeCl_3 were both dissolved completely when the pH was 2. The concentrations of arsenic obtained from the TCLP test increased when the pH value was 4 to 8. The reason for this was same as for the

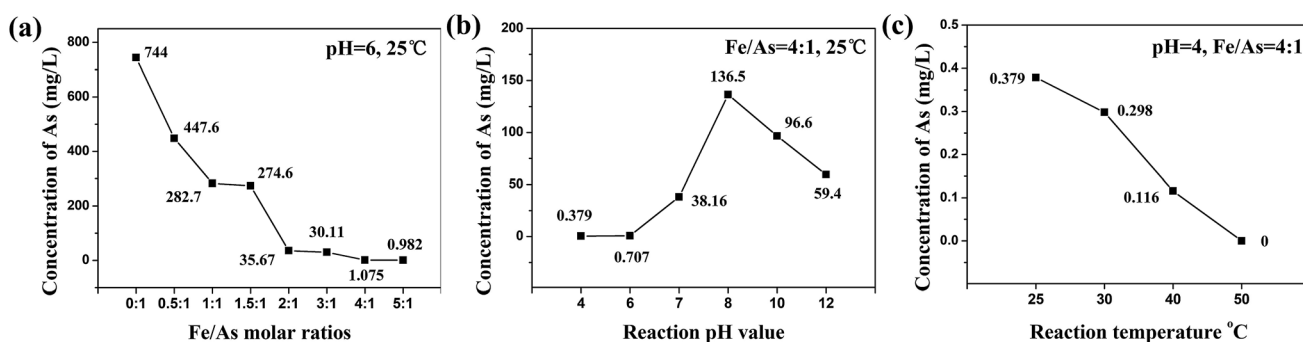


Fig. 2 Concentrations of arsenic obtained using the TCLP test after sample 1 was treated with FeCl_3 . (a) Different Fe/As molar ratios, (b) different reaction pH values, (c) different reaction temperatures.

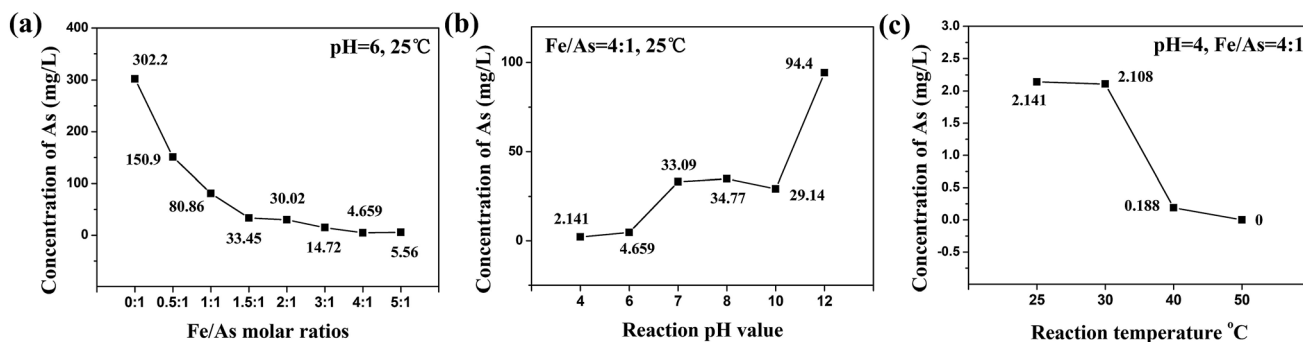


Fig. 3 Concentrations of arsenic obtained using the TCLP test after sample 2 was treated with FeCl_3 . (a) Different Fe/As molar ratios, (b) different reaction pH values, (c) different reaction temperatures.

CaHAsO_4 system given in Section 3.2.1. The best pH for the stability treatment was 4, and the concentration of arsenic obtained from the TCLP test was 2.141 mg L^{-1} .

Fig. 2(c) shows the TCLP test results of the products which were reacted at $\text{pH} = 4$ at different temperatures. The Fe/As molar ratio of reaction was 4 : 1. The results indicated that the reaction rate increased as the temperature of the reaction increased. When the temperature was $50 \text{ }^\circ\text{C}$, the $\text{Ca}_3(\text{AsO}_4)_2$ could be coated perfectly by the FeAsO_4 . Arsenic was not detected by the TCLP test.

3.3 Morphology of samples

Sample 3 was $\text{CaHAsO}_4@ \text{FeAsO}_4$ which was obtained by the FeCl_3 stability treatment of sample 1 (Fe/As = 4 : 1, $\text{pH} = 4$, $50 \text{ }^\circ\text{C}$). Sample 4 was $\text{Ca}_3(\text{AsO}_4)_2@ \text{FeAsO}_4$ which was obtained by the FeCl_3 stability treatment of sample 2 (Fe/As = 4 : 1, $\text{pH} = 4$, $50 \text{ }^\circ\text{C}$).

As shown in Fig. 4, the SEM images show the morphology of samples 1, 2, 3 and 4. Fig. 4(a) and (b) show that the synthesized CaHAsO_4 and $\text{Ca}_3(\text{AsO}_4)_2$ were both layered structures. The thickness of the layers was about 30 nm. This structure corresponded to previous reports of calcium arsenate.¹ The surface of the layers was smooth without particles. Sample 3 and sample 4 were the CaHAsO_4 and $\text{Ca}_3(\text{AsO}_4)_2$, respectively, which had been stability treated with FeCl_3 . As shown in Fig. 4(c) and (d), the layered structure remained, and the layer was coated by nanoparticles. According to the XRD and TCLP results, the particles were FeAsO_4 . The FeAsO_4 nanoparticles could prevent the internal calcium arsenate contacting with the solution, so the dissolution of calcium arsenate stopped. Fig. 4(d) shows the schematic diagram of the stability treatment process. The CaHAsO_4 or $\text{Ca}_3(\text{AsO}_4)_2$ dissolved into the aqueous solution, released Ca^{2+} and AsO_4^{3-} ions. The AsO_4^{3-} ions reacted with the Fe^{3+} ions and formed FeAsO_4 particles. These particles were

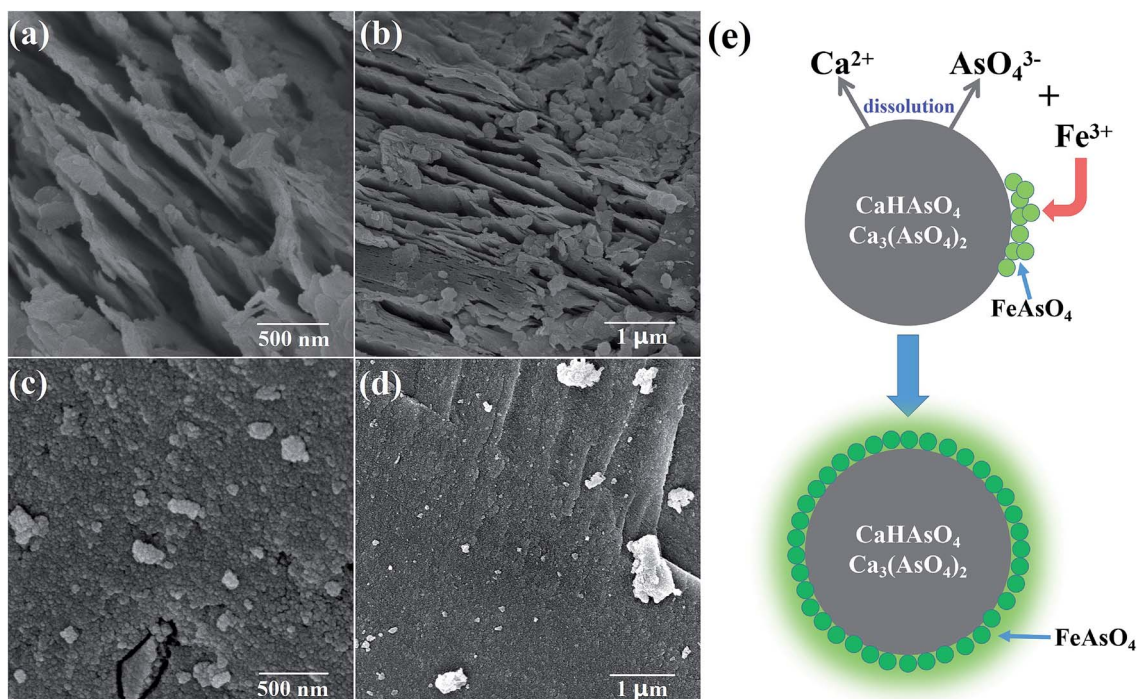


Fig. 4 The SEM images of (a) sample 1, (b) sample 2, (c) sample 3, (d) sample 4; (e) schematic diagram of the stability treatment process.

deposited on the surface of calcium arsenate until the calcium arsenate was coated completely. Because the solubility of FeAsO_4 was much less than the solubility of CaHAsO_4 or $\text{Ca}_3(\text{AsO}_4)_2$, the FeAsO_4 was insoluble material and could not react with H^+ and OH^- . The FeAsO_4 shell could protect the internal CaHAsO_4 and $\text{Ca}_3(\text{AsO}_4)_2$. They would not be corroded by the external solution. This structure was more stable after the stability treatment with FeCl_3 .

The XRD pattern is shown in Fig. S1 (ESI).† The EDS analysis results of sample 1 and 3 are shown in Fig. S2 and S3 (ESI).†

4. Conclusion

The leaching liquid of smelting dust was used as the As(v) source. Layered CaHAsO_4 and $\text{Ca}_3(\text{AsO}_4)_2$ were synthesized. The CaHAsO_4 and $\text{Ca}_3(\text{AsO}_4)_2$ were stability treated with FeCl_3 because the FeAsO_4 formed has a lower solubility and higher stability. From the XRD and SEM analyses, it can be seen that the $\text{CaHAsO}_4@FeAsO_4$ and $\text{Ca}_3(\text{AsO}_4)_2@FeAsO_4$ were synthesized successfully. The layered calcium arsenate was coated by a FeAsO_4 shell which consisted of nanoparticles. The stability of the coating materials was determined by the TCLP tests. The results showed that the concentrations of As for CaHAsO_4 and $\text{Ca}_3(\text{AsO}_4)_2$ were 744 mg L^{-1} and 302.2 mg L^{-1} , respectively. The concentration of As for $\text{CaHAsO}_4@FeAsO_4$ and $\text{Ca}_3(\text{AsO}_4)_2@FeAsO_4$ were both 0 mg L^{-1} , and the best coating conditions were confirmed as a Fe/As molar ratio of 4 : 1, a pH of 4, and a temperature of $50 \text{ }^\circ\text{C}$. The stability of the materials showed a significant improvement. The results indicated that calcium arsenate materials could be converted to coating materials by the ferric salts. The coating materials had excellent stability in aqueous solution. It was suitable for the removal and immobilization of arsenic in industrial applications. This work provided a new way to treat the arsenic-containing wastewater, which was simple and economical. This method has potential applications in the field of arsenic-containing wastewater treatment.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by National Natural Science Foundation of China (21476268, and 21808170) and Shandong Provincial Natural Science Foundation (ZR201807260006).

References

- 1 J. V. Bothe and P. W. Brown, *Environ. Sci. Technol.*, 1999, **33**, 3806–3811.
- 2 T. S. Choong, T. Chuah, Y. Robiah, F. G. Koay and I. Azni, *Desalination*, 2007, **217**, 139–166.
- 3 G. Ungureanu, S. Santos, R. Boaventura and C. Botelho, *J. Environ. Manag.*, 2015, **151**, 326–342.
- 4 C. Sullivan, M. Tyrer, C. R. Cheeseman and N. J. Graham, *Sci. Total Environ.*, 2010, **408**, 1770–1778.
- 5 Y. Zhu, X. Zhang, Q. Xie, D. Wang and G. Cheng, *Water Air Soil Pollut.*, 2006, **169**, 221–238.
- 6 E. O. Kartinen Jr and C. J. Martin, *Desalination*, 1995, **103**, 79–88.
- 7 J. Camacho, H.-Y. Wee, T. A. Kramer and R. Autenrieth, *J. Hazard Mater.*, 2009, **165**, 599–603.
- 8 K. Leetmaa, F. Guo, L. Becze, M. A. Gomez and G. P. Demopoulos, *J. Chem. Technol. Biotechnol.*, 2016, **91**, 408–415.
- 9 S. Vega-Hernandez, J. Weijma and C. J. Buisman, *J. Hazard Mater.*, 2019, **368**, 221–227.
- 10 P.-c. Ke and Z.-h. Liu, *Trans. Nonferrous Metals Soc. China*, 2019, **29**, 876–892.
- 11 Z. Yuan, D. Zhang, S. Wang, L. Xu, K. Wang, Y. Song, F. Xiao and Y. Jia, *Hydrometallurgy*, 2016, **164**, 228–237.
- 12 L. Yao, X. Min, H. Xu, Y. Ke, Y. Liang and K. Yang, *Int. J. Environ. Res. Public Health*, 2018, **15**, 1863.
- 13 M. Edwards, *J. Am. Water Work. Assoc.*, 1994, **86**, 64–78.
- 14 E. Woolson, J. Axley and P. Kearney, *Soil Sci. Soc. Am. J.*, 1973, **37**, 254–259.
- 15 J. Fei, J. Ma, J. Yang, Y. Liang, Y. Ke, L. Yao, Y. Li, D. Liu and X. Min, *Environ. Geochem. Health*, 2019, 1–12.
- 16 M. Stachowicz, T. Hiemstra and W. H. van Riemsdijk, *J. Colloid Interface Sci.*, 2008, **320**, 400–414.
- 17 *Test Methods for Evaluating Solid Waste Physical/Chemical Methods*, SW-846/Method 1311-Toxicity Characteristic Leaching Procedure, USEPA, 1992.
- 18 T. Nishimura and R. Robins, *Mineral Processing and Extractive Metallurgy Review*, 1998, **18**, 283–308.
- 19 Y. Fan, Q. Weng, Y. Zhuo, S. Dong, P. Hu and D. Li, *Materials*, 2019, **12**, 677.