

Enamel morphology after microabrasion with experimental compounds

NÚBIA I. P. PINI, RAFAELA COSTA¹, CARLOS E. S. BERTOLDO², FLAVIO H. B. AGUIAR, JOSÉ R. LOVADINO, DÉBORA ALVES NUNES LEITE LIMA

Abstract

Background: Enamel microabrasion is an esthetic treatment for removing superficial stains or defects of enamel. **Aim:** This study evaluated the roughness after enamel microabrasion using experimental microabrasive systems. **Materials and Methods:** One hundred and ten samples (5 × 5 mm) were obtained from bovine incisors and divided into 11 groups ($n = 10$) in accordance with the treatment: Microabrasion using 6.6% hydrochloric acid (HCl) or 35% phosphoric acid (H_3PO_4) associated with aluminum oxide (AlO_3) or pumice (Pum) with active application (using rubber cup coupled with a micro-motor of low rotation) or passive application (just placing the mixture on the enamel surface); just the use of acids in a passive application (negative control), and a group without treatment (positive control). Roughness analysis was performed before and after treatments. The statistical analysis used analysis of variance (PROC MIXED), Tukey-Kramer and Dunnet tests ($P < 0.05$). Representative specimens were evaluated using scanning electron microscopy (SEM). **Results:** There was no significant difference between the acids used ($P = 0.0510$) and the applications ($P = 0.8989$). All of the treated groups were statistically different from the positive control. When using passive application, the use of HCl + AlO_3 resulted in higher roughness when compared with HCl + Pum. Additionally, this treatment was statistically different from the passive application of H_3PO_4 (negative control) ($P < 0.05$). However, SEM analysis showed that the treatment with AlO_3 resulted in an enamel surface with a more polished aspect when compared with Pum. **Conclusion:** AlO_3 may be a suitable particle for use in microabrasive systems.

Keywords: Enamel, microabrasion, roughness

Introduction

Enamel microabrasion is a procedure used for removing a superficial layer of enamel that has some alteration of color and/or texture.^[1] This procedure is performed utilizing an association of an erosive agent (phosphoric acid (H_3PO_4) or hydrochloric acid (HCl)) and an abrasive agent (pumice (Pum) or silica particles).^[2-4] With the technique, a sub layer of enamel with normal characteristics is exposed. As the enamel wear is minimal, microabrasion is considered a safe and conservative procedure, when correctly prescribed.^[4-7]


Department of Restorative Dentistry, Piracicaba Dental School, State University of Campinas – FOP/Unicamp, ¹Clinical Practice, São Paulo, ²Restorative Dentistry, Clinical Practice, São Paulo, Brazil, São Paulo, Brazil

Correspondence: Assoc. Prof. Débora Alves Nunes Leite Lima, Department of Restorative Dentistry, Piracicaba Dental School, P. O. Box 52, University of Campinas – UNICAMP 13414-903, Piracicaba, SP, Brazil.
E-mail: deboralima@fop.unicamp.br

Recently, scientific studies have been performed to improve microabrasion and to know its effects on enamel.^[8-12] Initially, the acid used for microabrasion was 18% HCl; today, it is recognized that this concentration is considered erosive and toxic. Currently, the same acid is employed at a lower concentration and containing silica in commercial formulations.^[5-7] Another combination used for the microabrasion technique is 35% H_3PO_4 coupled with Pum, in equal parts.^[13] This mixture is advantageous because of its low cost and accessibility. However, it is subject to variations when the operator mixes the compounds.^[5,8]

The effects of microabrasion on enamel are related to the compounds, both erosive and abrasive, and to the mechanical pressure exerted when using microabrasion cups in slow-speed hand pieces.^[14-16] The common effects include increased roughness values, which are reestablished by saliva over a period between 7 and 15 days.^[8,9,11] In relation to the morphology, microscopic evaluations have shown that microabrasion causes alterations to the enamel surface, similar to the conditioning patterns caused by H_3PO_4 , to include exposure of the interprismatic spaces.^[17] Therefore, the enamel characteristics resulting from the technique are most likely related to the acid concentration and pH, in addition to the time and pressure of instrumentation and application.^[14,17] The abrasive is also relevant, as Pum is believed to present excessive abrasiveness and deep erosion when compared to other abrasive systems.^[18]

The aim of this study was to evaluate the effect of the acids (hydrochloric and phosphoric) in conjunction with

Access this article online	
Quick Response Code:	Website: www.contemplindent.org
	DOI: 10.4103/0976-237X.156038

different experimental abrasive mixtures on enamel morphology by means of roughness analysis and scanning electron microscopy (SEM).

Materials and Methods

Preparation of specimens

Bovine incisor teeth were selected and stored in a formaldehyde solution for at least 1-month. After the coronary portion was separated using a double-faced diamond disk (KG Sorensen, Ind. Com. Ltda.; Barueri, SP, Brazil), 110 enamel/dentin slabs ($5 \times 5 \times 3$ mm) were obtained using a precision saw (Isomet 1000; Buehler, Illinois, USA) and a high-concentration diamond disk ($4'' \times 012 \times \frac{1}{2}$, Buehler, Illinois, USA). The enamel surface of the blocks was flattened in a circular polishing machine (Aropol E, Arotec, Cotia; São Paulo, SP, Brazil), under water cooling, using the following: Silicon carbide papers of decreasing granulation (#300, #600 and #1200), felts, and diamond pastes of 1, 1/2 and 1/4 μm granulation greased with a specific oil (Arotec, Cotia; SP, Brazil). Between the polishing steps and after the final polishing, all slabs were cleaned for 15 min in an ultrasonic device (Marconi, Piracicaba, SP, Brazil) that contained distilled water.

Surface treatment

The following ingredients were used to fabricate the experimental microabrasive products:

- 6.6% hydrochloric acid (HCl – Drogral-Piracicaba, São Paulo/Brazil)
- 35% H_3PO_4 (H_3PO_4 – Ultradent Products – Utah, USA)
- Aluminum oxide (AlO_3 -NMartis – Colombo, Paraná/Brazil)
- Pumice (SS White LTDA, Rio de Janeiro, RJ/Brazil).

The specimens were randomly divided into 11 groups based on the acid and abrasive used and the application technique [Table 1].

All of the microabrasive products were formed using equal parts of each component as measured using a dosage spoon (0.240 g). The specific treatments were placed on the enamel surface with a syringe until the sample was covered; the amount required was 0.0200 g for the groups treated with acid and abrasive and 0.0150 g for the groups treated with acid only. The application of the acids in a passive form was performed to clearly identify the effects of the experimental mixtures on enamel, with these serving as negative controls. All of the surface treatments were performed with 10 applications for 10 s each. After each application, the enamel surface was rinsed and dried for 10 s using a dental sprayer and compressed air, respectively. The control group (positive) did not receive treatment.

Enamel roughness analysis

The enamel roughness regression analysis (Ra) was analyzed, using a profilometer roughness tester (Mitutoyo Surfite

211, São Paulo, SP, Brazil) before and after the microabrasive treatment. A diamond stylus was used to measure the surface roughness, using a cut-off of 0.25 mm and speed of 0.5 mm/s, under a constant load (5 N). The numeric values representing the roughness profile were computed and represented as Ra. Three readings were made in three different directions on the enamel surface, with the mean values of the measuring points calculated.

Scanning electron microscopy

For SEM analysis (JEOL.JSM 5600 LV, Tokyo, Japan), representative specimens from each group were placed on an acrylic stub under aluminum tape (3M Adhesives Ltd., St. Paul, MN, USA) and were sputter coated (Balzers – SCD 050 sputter coter, Germany) with a thin layer of gold, equivalent to 10^{-6} mm, and under vacuum, to increase the surface reflectance. Photomicrographs ($\times 4000$) of representative areas of the specimens were obtained.

Statistical analysis

The data obtained were submitted to statistical analysis using analysis of variance (PROC MIXED) for repeated measures, followed by Tukey's and Dunnett's tests. The significance level was 5%.

Results

Table 2 shows that all of the experimental groups presented an increase in the roughness values, with statistically significant differences when comparing the initial and final values. Additionally, there were no statistical differences between the acids used ($P = 0.0510$) or the application forms ($P = 0.8989$) with regards to roughness. However, the association between HCl and AlO_3 presented the highest mean value of surface roughness when applied in the passive form, which was statistically different from the association of Pum with the same acid and application. The comparison with negative controls showed a difference

Table 1: Groups of study

Acid	Abrasive	Application technique
6.6% HCl	AlO_3	Active
		Passive
	Pumice	Active
		Passive
35% H_3PO_4	AlO_3	Active
		Passive
	Pumice	Active
		Passive
HCl	-	Passive
H_3PO_4	-	Passive
Control	-	-

HCl: Hydrochloric acid; H_3PO_4 : Phosphoric acid; AlO_3 : Aluminum oxide

Table 2: Enamel roughness in micrometers, means (SD) in the analysis before and after treatments

Acid	Abrasive	Application	Analysis	
			Initial	Final
HCl	AlO ₃	Active	0.28 (0.01) B	0.49 (0.01) A ^d
		Passive	0.15 (0.04) B	0.57 (0.12) A ^{s,d,#}
	Pumice	Active	0.27 (0.05) B	0.47 (0.09) A ^d
		Passive	0.25 (0.08) B	0.41 (0.06) A ^d
H ₃ PO ₄	AlO ₃	Active	0.22 (0.11) B	0.40 (0.11) A ^d
		Passive	0.19 (0.05) B	0.49 (0.07) A ^d
	Pumice	Active	0.15 (0.09) B	0.37 (0.08) A ^d
		Passive	0.26 (0.06) B	0.46 (0.07) A ^d
HCl	-	Passive	0.28 (0.11) B	0.47 (0.17) A
H ₃ PO ₄	-	Passive	0.22 (0.08) B	0.43 (0.07) A
Control			0.20 (0.01) A	0.16 (0.02) A ^{s,#}

Different letters simply statistically significant differences, in rows ($P \leq 0.05$).

^sDiffer from Pum used in the same acid, application and time ($P \leq 0.05$);

There was not difference between the acids ($P = 0.0510$) and between

the application forms ($P = 0.8989$). ^dDiffer from HCl in the same

time ($P \leq 0.05$)/[#]Differ from H₃PO₄ in the same time ($P \leq 0.05$); ^dDiffer from

control group ($P \leq 0.05$). SD: Standard deviation; HCl: Hydrochloric acid;

H₃PO₄: Phosphoric acid; AlO₃: Aluminum oxide

between the association of HCl with AlO₃ (passive application) and H₃PO₄, showing the erosive power of the HCl and the inability of the AlO₃ to reduce the effects of HCl on enamel roughness. The control group (positive control) was statistically different from all of the experimental groups and the negative controls, proving the erosive action of the acids and the microabrasive mixtures on enamel roughness.

Scanning electron microscopy images showed different conditioning patterns for the different acids and microabrasive systems. Treatment with HCl in the microabrasive mixtures [Figure 1] did not present any specific conditioning pattern, with no evidence of the prism core (type I) or the prism periphery (type II), as found with the H₃PO₄ treatment, in which the type I [Figure 2] conditioning pattern was found. The combination of HCl with abrasive particles and active application [Figure 1a and c] resulted in a polished enamel surface, most noticeably with the association of HCl and AlO₃ [Figure 1a]. With the passive application [Figure 1b and d], HCl⁺ abrasives showed a tendency to exhibiting the demineralization characteristics as seen in Figure 3a. Treatment with H₃PO₄ and Pum [Figure 2c and d] presented the conditioning pattern type I, which was also found with the treatment using just H₃PO₄ [Figure 3b]. The association between H₃PO₄ and AlO₃ tended to present enamel conditioning without complete exposition of the prism cores, showing the action of this abrasive in reducing the erosive powder of the acid. Regarding the treatments with just the acids [Figure 3], H₃PO₄ exhibited more demineralization than HCl.

Discussion

Enamel microabrasion has become accepted as a conservative, nonrestorative method of improving the appearance of teeth with superficial defects or alteration of color.^[2,3,5,6,19] The technique is based on mild acid etching in combination with a rotary application of an abrasive medium.^[16] Studies have suggested the existence of an “abrosion effect,” whereby the erosive action of the acid coupled with an abrasive action to compact the mineralized tissue within the organic area. Through this process, the outer layer of prism-rich enamel is replaced with a densely compacted and prism-free region.^[5-7,20,21] However, the enamel surface after treatment presents with alterations in roughness and microhardness.^[8-11] The results on this present study demonstrated that all experimental microabrasive systems and acids caused an increase in superficial enamel roughness, as each experimental agent showed specific enamel conditioning when observed under SEM.

According to [Table 2], the roughness means increased after the microabrasion treatments (active application), and after the passive application of the microabrasive systems or acids, as related in other studies.^[8,9,11] These results in all experimental groups, including the passive application of the acids, may be explained due to the erosive action of the acids used.^[17,22] This action is responsible for enamel demineralization, as visualized in the SEM images. Although the microscopy analysis shows different conditioning patterns between the acids used, in which H₃PO₄ presents major evidence of demineralization with marked exposition of the prism cores,^[23] the absence of statistical differences for roughness in relation to the acids used ($P = 0.0510$) did not allow for defining which acid (35% H₃PO₄ or 6.6% HCl) had the greater erosive action on enamel.

In relation to the abrasive compounds used, AlO₃ in combination with both acids [Figures 1 and 2] resulted in a more polished and glossy enamel surface that was more likely to be similar to the surface found in the control group [Figure 4] when observed under SEM. This polished surface should be a result of the “abrosion effect,” as related by Croll (1997).^[20] This effect can be explained due to the effect of the polish conferred by the AlO₃, which has a constant grain size (60 μ) and is commonly used for finishing and polishing restorative materials and enamel surfaces.^[24]

As part of the microabrasion technique, it is important to perform a final polish using abrasive materials (felt disks and diamond paste) to finalize the esthetic appearance and minimize the surface roughness of the enamel,^[7,9,11] since greater surface roughness leads to greater plaque accumulation.^[25] Therefore, the technique using AlO₃ would obtain a polished enamel surface, which might reduce the clinical time for the technique, as it could eliminate the

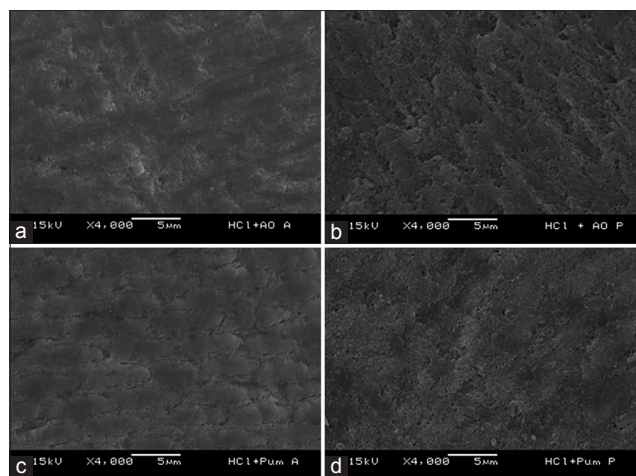


Figure 1: Scanning electron microscopy photomicrography for the groups treated with hydrochloric acid (HCl) in the microabrasive system treatment using the association between HCl and aluminum oxide (a and b) or Pumice (c and d) with passive active (a and c) or passive (b and d) modes of application

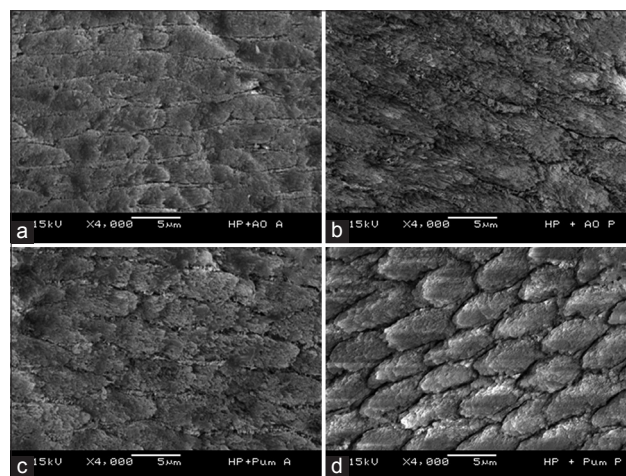


Figure 2: Scanning electron microscopy photomicrography for the groups treated with phosphoric acid (H₃PO₄) in the microabrasive system treatment using the association between H₃PO₄ and aluminum oxide (a and b) or Pumice (c and d) with passive active (a and c) or passive (b and d) modes of application

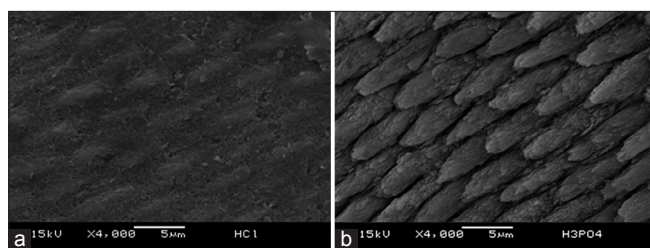


Figure 3: Scanning electron microscopy photomicrography for the groups treated with just the placement of the acids treatment hydrochloric acid (a) and phosphoric acid (b)

polishing stage. While the enamel roughness increased when using this abrasive, the literature is emphatic in demonstrating the remineralization effect of saliva in minimizing the roughness and microhardness alterations of enamel after microabrasion.^[8,9,11,26]

With both application modes, the SEM analysis showed that HCl, in a low concentration, combined with AlO₃ or Pum [Figure 1], resulted in an enamel surface that was less eroded when compared to surfaces treated with H₃PO₄. This may be explained due to the conditioning pattern observed with this acid, in which there was no marked exposition of the core or periphery of the prisms. Even though there were no statistically significant differences between the application forms of the microabrasives ($P = 0.8989$), the active application using special rubber cups in a slow-speed hand piece is well defined in the literature as being important for the microabrasion technique.^[14,15,27]

With regards to the passive application of the microabrasive mixtures containing AlO₃, as the roughness analysis for its use with HCl showed higher and statistically significant

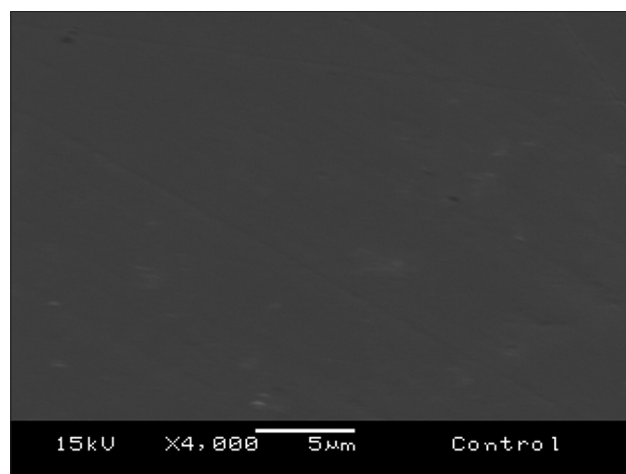


Figure 4: Scanning electron microscopy photomicrography for the control group. Control group without observation of any conditioning pattern

roughness means in relation to the Pum for the same acid and application form ($P < 0.05$), it can be suggested that the Pum, as an abrasive, may neutralize or reduce the erosive action of the acids better when compared to the AlO₃. However, regarding the SEM analysis, less invasive enamel surface conditioning was noted with the use of HCl when compared to the use of H₃PO₄, even considering that the AlO₃ may present a neutralizing action. Even so, the association between HCl and AlO₃ may be suitable for use, considering that the enamel roughness is corrected over time with exposure to saliva, as shown in *in vitro*^[9,11] or *in situ*^[8,26] studies. The improvement in roughness due to saliva is due to it containing a buffering capacity that may be improved by specific remineralizing agents, such as fluoride.^[28,29]

When considering the results obtained from this study with the clinical procedure of microabrasion, the passive application of the microabrasive systems, which resulted in an increase in the roughness values when compared to the control group, shows that the clinician should be careful in not overly exposing the enamel surface to the microabrasive compounds without mechanical application. This finding suggests that the use of mechanical application helps to guarantee the scattering and renewing of the acid on the enamel, without allowing the erosive substance to remain on the tooth surface for too long. This concern is especially important in the case of patients with fluorosis stains or remineralized white spots, which are common after finish orthodontic treatment.^[4,7] In these cases, the clinician should perform the procedure individually on each tooth, ensuring the renovation of the microabrasive mixture over the enamel surface to be treated, thereby reducing any extraneous erosive action, which is evident when the compounds are only placed on enamel.

The results of the present study, as well as those found in the literature, indicate that the microabrasive technique is a conservative esthetic procedure that may be safely indicated, although it causes alterations on the enamel surface. Therefore, it is important to study the technique, the microabrasive compounds and their effects on enamel, in order to reverse these effects and to obtain the most minimally invasive technique possible.

Conclusion

In conclusion, the results found in this study demonstrate that enamel microabrasion with different compounds results in an increase in the surface roughness of enamel. The association of HCl with AlO_3 resulted in an increase in surface roughness, when analyzed by SEM. The passive application of the microabrasive systems enamel was an important point to be evaluated, since the results showed the care that must be taken when using the technique, in order to avoid the extraneous erosive action of the acid on the enamel surface.

References

1. Croll TP. Enamel microabrasion: The technique. *Quintessence Int* 1989;20:395-400.
2. Sundfeld RH, Franco LM, Gonçalves RS, de Alexandre RS, Machado LS, Neto DS. Accomplishing esthetics using enamel microabrasion and bleaching – A case report. *Oper Dent* 2014;39:223-7.
3. Wang Y, Sa Y, Liang S, Jiang T. Minimally invasive treatment for esthetic management of severe dental fluorosis: A case report. *Oper Dent* 2013;38:358-62.
4. Benbachir N, Ardu S, Krejci I. Indications and limits of the microabrasion technique. *Quintessence Int* 2007;38:811-5.
5. Pini NI, Sundfeld-Neto D, Aguiar FH, Sundfeld RH, Martins LR, Lovadino JR, *et al.* Enamel microabrasion: An overview of clinical and scientific considerations. *World J Clin Cases* 2015;3:34-41.
6. Sundfeld RH, Sundfeld-Neto D, Machado LS, Franco LM, Fagundes TC, Briso AL. Microabrasion in tooth enamel discoloration defects: Three cases with long-term follow-ups. *J Appl Oral Sci* 2014;22:347-54.
7. Sundfeld RH, Croll TP, Briso AL, de Alexandre RS, Sundfeld Neto D. Considerations about enamel microabrasion after 18 years. *Am J Dent* 2007;20:67-72.
8. Pini NI, Lima DA, Sundfeld RH, Ambrosano GM, Aguiar FH, Lovadino JR. *In situ* assessment of the saliva effect on enamel morphology after microabrasion technique. *Braz J Oral Sci* 2014;13:187-92.
9. Bertoldo CE, Pini NI, Miranda DA, Catelan A, Ambrosano GM, Lima DA, *et al.* Physicochemical properties of enamel after microabrasion technique. *J Res Dent* 2014;2:176-88.
10. Rodrigues MC, Mondelli RF, Oliveira GU, Franco EB, Baseggio W, Wang L. Minimal alterations on the enamel surface by micro-abrasion: *In vitro* roughness and wear assessments. *J Appl Oral Sci* 2013;21:112-7.
11. Fragoso LS, Lima DA, de Alexandre RS, Bertoldo CE, Aguiar FH, Lovadino JR. Evaluation of physical properties of enamel after microabrasion, polishing, and storage in artificial saliva. *Biomed Mater* 2011;6:035001.
12. Meireles SS, Andre Dde A, Leida FL, Bocangel JS, Demarco FF. Surface roughness and enamel loss with two microabrasion techniques. *J Contemp Dent Pract* 2009;10:58-65.
13. Kamp AA. Removal of white spot lesions by controlled acid-pumice abrasion. *J Clin Orthod* 1989;23:690-3.
14. Paic M, Sener B, Schug J, Schmidlin PR. Effects of microabrasion on substance loss, surface roughness, and colorimetric changes on enamel *in vitro*. *Quintessence Int* 2008;39:517-22.
15. Zuanon AC, Santos-Pinto L, Azevedo ER, Lima LM. Primary tooth enamel loss after manual and mechanical microabrasion. *Pediatr Dent* 2008;30:420-3.
16. Schmidlin PR, Göhring TN, Schug J, Lutz F. Histological, morphological, profilometric and optical changes of human tooth enamel after microabrasion. *Am J Dent* 2003;16 Spec No: 4A-8A.
17. Tong LS, Pang MK, Mok NY, King NM, Wei SH. The effects of etching, micro-abrasion, and bleaching on surface enamel. *J Dent Res* 1993;72:67-71.
18. Honório HM, Rios D, Santos CF, Magalhães AC, Delbem AC, Buzalaf MA, *et al.* Cross-sectional microhardness of human enamel subjected to erosive, cariogenic or combined erosive/cariogenic challenges. *Caries Res* 2010;44:29-32.
19. Nahsan FP, da Silva LM, Baseggio W, Franco EB, Francisconi PA, Mondelli RF, *et al.* Conservative approach for a clinical resolution of enamel white spot lesions. *Quintessence Int* 2011;42:423-6.
20. Croll TP. Enamel Microabrasion. Chicago: Quintessence; 1991. p. 13-21.
21. Donly KJ, O'Neill M, Croll TP. Enamel microabrasion: A microscopic evaluation of the "abrosion effect". *Quintessence Int* 1992;23:175-9.
22. Torres-Rodríguez C, González-López S, Bolaños-Carmona V, Sánchez-Sánchez P, Rodríguez-Navarro A, Attin T. Demineralization effects of phosphoric acid on surface and subsurface bovine enamel bleached with in-office hydrogen peroxide. *J Adhes Dent* 2011;13:315-21.
23. Silverstone LM, Hicks MJ, Featherstone MJ. Dynamic factors affecting lesion initiation and progression in human dental enamel. II. Surface morphology of sound enamel and carieslike lesions of enamel. *Quintessence Int* 1988;19:773-85.
24. de Melo RM, Travassos AC, Neisser MP. Shear bond strengths of a ceramic system to alternative metal alloys. *J Prosthet Dent* 2005;93:64-9.
25. Segura A, Donly KJ, Wefel JS. The effects of microabrasion on demineralization inhibition of enamel surfaces. *Quintessence Int* 1997;28:463-6.

26. Grazziotin GB, Rios D, Honório HM, Silva SM, Lima JE. *In situ* investigation of the remineralizing effect of saliva and fluoride on enamel following prophylaxis using sodium bicarbonate. *Eur J Dent* 2011;5:40-6.
27. Dalzell DP, Howes RI, Hubler PM. Microabrasion: Effect of time, number of applications, and pressure on enamel loss. *Pediatr Dent* 1995;17:207-11.
28. Calvo AF, Tabchoury CP, Del Bel Cury AA, Tenuta LM, da Silva WJ, Cury JA. Effect of acidulated phosphate fluoride gel application time on enamel demineralization of deciduous and permanent teeth. *Caries Res* 2012;46:31-7.
29. Paes Leme AF, Dalcico R, Tabchoury CP, Del Bel Cury AA, Rosalen PL, Cury JA. *In situ* effect of frequent sucrose exposure

on enamel demineralization and on plaque composition after APF application and F dentifrice use. *J Dent Res* 2004;83:71-5.

How to cite this article: Pini NI, Costa R, Bertoldo CE, Aguiar FH, Lovadino JR, Lima DN. Enamel morphology after microabrasion with experimental compounds. *Contemp Clin Dent* 2015;6:170-5.

Source of Support: This study was supported by Conselho Nacional de Desenvolvimento Científico e Tecnológico (CNPq/Brazil). The authors would like to gratefully acknowledge the Drogal Pharmaceutics (Piracicaba/Brazil) for preparing the experimental acid used in this study.

Conflict of Interest: None declared.

Author Help: Reference checking facility

The manuscript system (www.journalonweb.com) allows the authors to check and verify the accuracy and style of references. The tool checks the references with PubMed as per a predefined style. Authors are encouraged to use this facility, before submitting articles to the journal.

- The style as well as bibliographic elements should be 100% accurate, to help get the references verified from the system. Even a single spelling error or addition of issue number/month of publication will lead to an error when verifying the reference.
- Example of a correct style
Sheahan P, O'leary G, Lee G, Fitzgibbon J. Cystic cervical metastases: Incidence and diagnosis using fine needle aspiration biopsy. *Otolaryngol Head Neck Surg* 2002;127:294-8.
- Only the references from journals indexed in PubMed will be checked.
- Enter each reference in new line, without a serial number.
- Add up to a maximum of 15 references at a time.
- If the reference is correct for its bibliographic elements and punctuations, it will be shown as CORRECT and a link to the correct article in PubMed will be given.
- If any of the bibliographic elements are missing, incorrect or extra (such as issue number), it will be shown as INCORRECT and link to possible articles in PubMed will be given.