


 Cite this: *RSC Adv.*, 2020, 10, 42860

Transformation of novel TiOF₂ nanoparticles to cluster TiO₂-{001/101} and its degradation of tetracycline hydrochloride under simulated sunlight

 Yue Jian,^{ac} Huayang Liu,^b Jiaming Zhu,^{ac} Yaqiong Zeng,^{ac} Zuohua Liu,^a Chentao Hou^{id}*^b and Shihua Pu^{*ac}

The anatase type cluster TiO₂-{001/101} was rapidly generated by a one-step hydrothermal method. The transformation process of coral-like TiOF₂ nanoparticles to cluster TiO₂-{001/101} was investigated for the first time, and the sensitization between cluster TiO₂-{001/101} and tetracycline hydrochloride (TCH) was also discussed. The degradation rate of TCH by cluster TiO₂-{001/101} under simulated sunlight was 92.3%, and the total removal rate was 1.76 times that of P25. Besides, cluster TiO₂-{001/101} settles more easily than P25 in deionized water. The study showed that cluster TiO₂-{001/101} derived from coral-like TiOF₂ nanoparticles had a strong adsorption effect on TCH, which was attributed to the oxygen vacancy (O_v) and {001} facets of cluster TiO₂-{001/101}. The strong adsorption effect promoted the sensitization between cluster TiO₂-{001/101} and TCH, and widened the visible light absorption range of cluster TiO₂-{001/101}. In addition, the fluorescence emission spectrum showed that cluster TiO₂-{001/101} had a lower luminous intensity, which was attributed to the heterojunction formed by {001} facets and {101} facets that reduces the recombination rate of carriers. It should be noted that cluster TiO₂-{001/101} still has good degradation performance for TCH after five cycles of degradation. This study provides a new idea for the synthesis of cluster TiO₂-{001/101} with high photocatalytic performance for the treatment of TCH wastewater.

 Received 5th October 2020
 Accepted 19th November 2020

DOI: 10.1039/d0ra08476j

rsc.li/rsc-advances

1. Introduction

Antibiotics are widely used around the world. TCH is a typical broad-spectrum tetracycline antibiotic, which is produced by actinomycetes and widely used as a growth promoter in the treatment of human diseases and animal feeding.¹ However, because the naphthol ring in the TCH structure can't be completely metabolized by humans and animals, a large amount of TCH absorbed is excreted into various water bodies through feces and urine.² Drinking water containing TCH for a long time will cause a series of diseases such as bacterial disorders, gastrointestinal reactions and mycoplasma pneumonia, and affect the growth of teeth and bones.³⁻⁵

In recent years, some methods have been used to treat TCH wastewater, such as microbial degradation,^{6,7} adsorption,^{8,9} electrochemical method,¹⁰ membrane separation method,^{11,12} photocatalytic degradation.¹³⁻¹⁶ Among these methods,

photocatalytic water purification technology is considered to be the most promising water treatment technology due to its economic, efficient and clean environment.¹⁷⁻²⁰

TiO₂ is widely used in environmental protection,¹⁸ biomedicine,²¹ solar cells²² and many other fields due to its advantages of simple control, low cost and non-toxic.²³ Especially in the photocatalytic treatment of pollutants showed excellent performance. However, it has a wide energy band gap (3.0–3.2 eV, which means it only reacts to UV) and a high carrier recombination rate, which hinders its application in sunlight.^{24,25} So far, many efforts have been made to make up for these shortcomings, such as metal doping,²⁶⁻²⁸ non-metal doping,²⁹⁻³¹ dye sensitization,³²⁻³⁴ and building heterogeneous semiconductor composite.³⁵⁻³⁸ Among these methods, the construction of semiconductor heterojunction seems to be an effective method to improve charge separation. However, the high-quality tight interface requirements required by heterojunction make the construction more difficult.³⁹ Although dye sensitization can improve the response of TiO₂ to visible light and enhance the photocatalytic activity. However, due to the weak binding force between organic dyes and TiO₂, if the dyes can not timely supplement the lost electrons in the system, the dyes will fall off from the TiO₂ and form competitive

^aChongqing Academy of Animal Sciences, Chongqing 402460, China. E-mail: pu88962@126.com

^bCollege of Geology and Environment, Xi'an University of Science and Technology, Xi'an 710054, China. E-mail: 807484470@qq.com

^cScientific Observation and Experiment Station of Livestock Equipment Engineering in Southwest, Ministry of Agriculture and Rural Affairs, Chongqing 402460, China



degradation with the target pollutants, which will reduce the degradation efficiency of the target pollutants.⁴⁰ Doping is the most commonly used method to enhance the photocatalytic activity of TiO₂ because of its simple method.^{41–44}

It is worth noting that fluorine (F) is a special anionic dopant. The existence of fluorine forms –Ti–F–Ti– and Ti³⁺ species to replace lattice oxygen to form O_{vs}.⁴⁵ The formation of Ti³⁺/O_{vs} is an effective and environmentally friendly strategy to improve visible light absorption and pollutant adsorption. Moreover, the existence of O_v can form an electron trap, which greatly reduces the composite rate of electrons and holes, thus effectively enhancing the photocatalytic activity of TiO₂.^{46,47} Furthermore, F, as an end-capping agent, promotes the growth of TiO₂-{001} facet.⁴⁸ For instance, Han *et al.*⁴⁹ using tetrabutyl titanate and hydrofluoric acid as precursors, the F–TiO₂ nanosheets with 89% TiO₂-{001} facets were obtained by hydrothermal treatment. Its photocatalytic activity is much higher than that of Degussa P25. Up to now, extensive experimental and theoretical studies have shown that the {001} facet with high surface energy has higher catalytic activity than the {101} facet with thermodynamic stability.^{50,51} This is because a low coordination number of exposed atoms and a high density of unsaturated Ti atoms on the {001} facet are in favor of the dissociation and adsorption of reactants.⁵² Lu *et al.*⁵³ demonstrated that the {001} facets of anatase TiO₂ nanocrystals exhibited much better photocatalytic activity than that of {101} facets of anatase TiO₂ nanocrystals toward photocatalytic oxidation of water and organic compounds with different functional groups (*e.g.*, –OH, –CHO, –COOH). Besides, Chen *et al.*⁵⁴ found that anatase TiO₂ microcrystals with highly exposed {001} facets have strong photocatalytic decomposition ability for gaseous styrene. Although the surface has very high surface energy, maximizing the percentage of exposed {001} area might not be a good direction. Khalil *et al.*⁵⁵ demonstrated that an appropriate proportion of exposed {001} and {101} facet, which forms a “surface heterojunction”. In the photocatalytic reactions, photogenerated electrons tend to transfer to the {101} facet with lower energy, and thus accumulating on the {101} facet, while photogenerated holes tend to accumulate on the {001} facet with high energy. This feature can effectively promote the separation of photogenerated electron–hole pairs, thereby improving their photocatalytic performance.⁵⁶ Therefore, it is necessary to explore how to synthesize TiO₂ with {001} and {101} facet.

In many methods of synthesizing TiO₂, solvothermal reaction conditions are relatively mild, and it can control the morphology of materials well.^{22,28,57} In the typical synthesis methods, tetrabutyl titanate was used as titanium source, ethanol as an inhibitor and hydrofluoric acid as end-capping agent. After hydrothermal treatment, TiO₂ nanosheets with {001} and {101} facets co-exposed could be synthesized. Interestingly, TiOF₂ is sometimes formed during the formation of TiO₂-{001}. In the previously reported X-ray diffraction characterization, it can be seen that TiOF₂ has two crystal forms, corresponding to no. 08-0060 and no. 01-0490 in JCPDS database.^{25,58} The TiOF₂ corresponding to JCPDS no. 08-0060 shows regular cubic morphology, while the TiOF₂ corresponding to

JCPDS no. 01-0490 shows irregular morphology of nanoparticles. Over the past ten years, some researchers have carried out extensive research on cubic TiOF₂. For instance, Zhang *et al.*⁵⁹ synthesized 3D hollow nanospheres with {001} main exposure facet using cubic TiOF₂ as a template, which improved the response of TiO₂ to visible light. Zhang *et al.*^{58,60,61} controlled the formation process of TiO₂-{001} nanosheets under different hydrofluoric acid dosage, reaction time and reaction temperature. It is found that cubic TiOF₂ is an important intermediate in the hydrothermal synthesis of TiO₂-{001} nanosheets. Shi *et al.*⁶² studied the transformation process of cubic TiOF₂ to TiO₂-{001/101} at different calcination temperatures and proposed the possible transformation mechanism of TiOF₂ to TiO₂-{001/101}. However, anatase TiO₂ nanosheets derived from cubic TiOF₂ are relatively large and easy to aggregate, which undoubtedly reduces the exposure area of TiO₂-{001} and leads to a low density of active sites, which inevitably increases the possibility of carrier recombination. Therefore, to further improve the photocatalytic activity of anatase TiO₂, it is necessary to synthesize small-sized TiO₂ with {001} and {101} facet co-exposed. Compared with cubic TiOF₂, few researchers pay attention to the TiOF₂ nanoparticles corresponding to JCPDS no. 01-0490. In our previous research,²⁵ this crystal type of TiOF₂ nanoparticles were successfully synthesized, and found that it can also transform into anatase TiO₂-{001} in hydrothermal reaction, and the obtained TiO₂/TiOF₂ hybrid has close interface contact and layered structure. Compared with cubic TiOF₂, this kind of TiOF₂ nanoparticles has a large number of mesoporous structures and smaller size. To enrich the research system of TiOF₂, it is necessary to explore the transition process of novel TiOF₂ in hydrothermal reaction. Moreover, this kind of TiOF₂ will be expected to transform into smaller TiO₂-{001/101} nanosheets under certain conditions.

In this study, the transition process of novel TiOF₂ nanoparticles to cluster TiO₂-{001/101} in the hydrothermal reaction was discussed for the first time. Under the irradiation of simulated sunlight, the degradation rate of TCH by TiO₂-{001/101} was 92.3%. Besides, the sedimentation performance of TiO₂-{001/101} was investigated and compared with that of Degussa P25. Furthermore, the sensitization between TCH and TiO₂-{001/101} was proposed for the first time, and the possible degradation pathway of TCH was discussed. This study provides an idea for the treatment of TCH wastewater.

2. Experimental

2.1. Chemicals

Tetrabutyl titanate (TBOT, A. R.), anhydrous ethanol (C₂H₅OH, A. R.), hydrofluoric acid (HF, A. R.) was purchased from Fuchen Chemical Reagent Factory, Tianjin, China. Degussa P25 (P25) was purchased from Beijing JiaHeng Technology Co., Ltd. Tetracycline hydrochloride (TCH) was provided by Aladdin Industrial Corporation (Shanghai, China), benzoquinone (BQ), methanol (MT), *tert*-butyl alcohol (*t*-BuOH) were purchased from Fuchen Chemical Reagent Factory, Tianjin, China. All reagents were used without further purification.

2.2. Synthesis of the photocatalysts

The experimental water is ultra-pure water. $\text{TiO}_2\text{-}\{001/101\}$ were synthesized by a one-step hydrothermal method. Add 30 mL anhydrous ethanol and 8 mL hydrofluoric acid into 100 mL polytetrafluoroethylene liner (Shanghai Qiuzuo Scientific Instrument Co., Ltd), stir for 10 min at 25 °C, and record the mixture as solution A. Take 30 mL tetrabutyl titanate, add it to solution A under stirring at the rate of 2 drops per second to form a white suspension, and stir the mixture at 25 °C for 2 h. Then, the polytetrafluoroethylene was placed in a high-pressure reactor (Shanghai Qiuzuo Scientific Instrument Co., Ltd) and reacted at 150 °C for 4 h. After the system is naturally cooled to room temperature, the solid products are collected by centrifugation and washed with ethanol and ultra-pure water three times. The samples were dried at 60 °C and named T-4h. The above steps remained unchanged and the reaction time varied between 0.5 h, 1 h and 3 h to study the transition process of novel TiOF_2 to $\text{TiO}_2\text{-}\{001/101\}$. These products were recorded as T-0.5h, T-1h, T-3h. Besides, we put the photocatalyst (30 mg) into 100 mL TCH (10 mg L^{-1}), stirred for 60 min under dark conditions, and then centrifuged and dried at 60 °C. The obtained samples were recorded as T-0.5h/TCH, T-1h/TCH, T-3h/TCH, T-4h/TCH and P25/TCH.

2.3. Characterization of the samples

The crystal structure of the samples was observed using X-ray diffraction (XRD; Bruker D8 Advance X-ray diffractometer) at 36 kV, 20 mA equipped with a Cu anode X-ray tube (Cu $K\alpha$ X-rays, $\lambda = 1.54056 \text{ \AA}$). SEM and EDS (JSM7500F, Japan) were used to record the surface morphology and element distribution of the samples. Transmission electron microscopy (TEM) images were achieved with a JEOL JEM-2100 high-resolution transmission electron microscope. The specific surface area (S_{BET}) and pore size analysis were performed by Brunauer-Emmett-Teller (BET) and Barrett-Joyner-Halenda (BJH) methods through a micromeritics JW-BK122W. The absorption characteristics of the samples were determined by UV-visible diffuse absorption spectroscopy (UV-Vis DRS, Shimadzu UV-2600, Japan). Fourier transform infrared spectrum (FT-IR) measurements, recorded in the range of $4000\text{--}400 \text{ cm}^{-1}$, were performed in KBr pellet by Nicolet IS5 Spectrometer, USA. The photoluminescence spectrum of the photocatalyst was measured by a fluorescence spectrometer (Shimadzu-RF-6000, Japan) with the excitation wavelength was 300 nm. The chemical valence states of the samples were analyzed by X-ray photoelectron spectroscopy (XPS, ThermoFisher K-Alpha). Electron paramagnetic resonance (EPR) was implemented by the BrukerA 300 spectrometer operating at room temperature.

2.4. Photocatalytic activity measurement

The photocatalytic activity of the catalyst was tested by the degradation of TCH. First, at the maximum absorption wavelength of 357 nm, the initial absorbance of TCH solution (10 mg L^{-1}) was measured by a UV-Vis spectrophotometer (Hitachi, UV-3900, Japan). After that, take 100 mL of TCH

solution (10 mg L^{-1}) in a measuring cylinder and put it into a 150 mL photocatalytic reaction tube (Ghx-1, Shanghai Qiaofeng Industrial Co., Ltd), weigh 30 mg of photocatalyst and add it into the TCH solution. The photocatalytic reaction tube was placed in the photocatalytic reactor (Ghx-1, Shanghai Qiaofeng Industrial Co., Ltd), and a 500 W xenon lamp (GXZ-500, Shanghai Jiguang Special Lighting Appliance actory) was used to simulate the degradation of TCH by sunlight. Before the xenon lamp is turned on, the solution is magnetically stirred in the dark for 60 min to ensure the adsorption balance, then turn on the xenon lamp to start the photodegradation test, take out 7 mL suspension every 10 min, and centrifugate at high speed to remove the catalyst, then analyze the remaining TCH concentration with UV-Vis spectrophotometer at the maximum absorption wavelength of 357 nm. After each photodegradation experiment, the sample was separated by a high-speed centrifuge (Tgl-16c, Shanghai Anting Scientific Instrument Factory), washed with distilled water, and ultimately dried at 60 °C for the next test. The initial concentration of TCH was changed from 10 mg L^{-1} to 20 mg L^{-1} , 30 mg L^{-1} and 40 mg L^{-1} to explore the effect of different TCH concentrations on photocatalytic degradation. The dosage of the photocatalyst was changed from 30 mg to 10 mg, 20 mg and 40 mg to explore the effect of photocatalyst dosage on the degradation of TCH. Different scavengers (BQ, MT and *t*-BuOH) were used to trap the active components ($\cdot\text{O}^{2-}$, h^+ , $\cdot\text{OH}$) in the photocatalytic process. This test is similar to the photocatalytic degradation test, except that a certain amount of scavenger was added to the TCH solution, and then photocatalyst was added.

2.5. Sedimentation experiment

The settling behavior of T-4h and P25 in deionized water were studied in glass cylinders (100 mL, diameter 2.8 cm, height 24 cm Fuchen Chemical Reagent Factory, Tianjin, China). T-4h suspension (1 g L^{-1}) was prepared with deionized water. The obtained T-4h suspension was homogenized by violent shaking

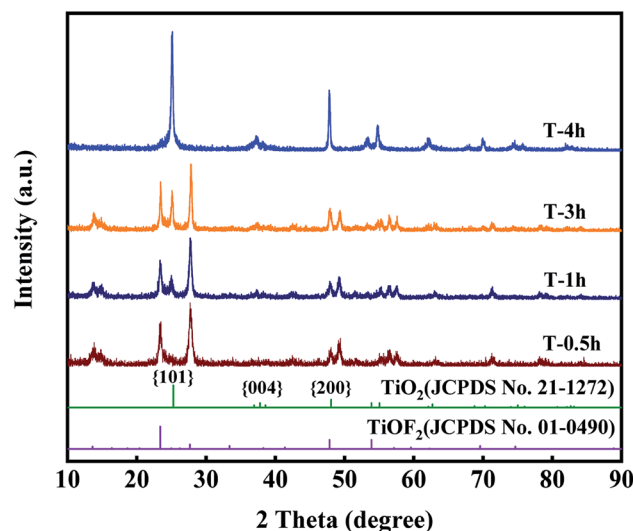


Fig. 1 XRD patterns of the prepared samples.

and then poured into the cylinder. The settlement behavior of T-4h was observed by standing for 2 h, 10 h, 24 h. The settlement behavior of P25 was studied under the same conditions.

3. Results and discussion

3.1. Crystal structure analysis

Fig. 1 clearly shows the crystal structure of the prepared samples. For T-0.5h, the diffraction peaks at $2\theta = 13.61^\circ, 23.39^\circ, 27.68^\circ, 47.8^\circ, 53.88^\circ, 59.6^\circ, 69.6^\circ, 74.7^\circ$ match with TiOF_2 (JCPDS no. 01-0490), indicating that the novel TiOF_2 was successfully prepared.²⁵

For T-4h, the diffraction peaks at $2\theta = 25^\circ, 37.76^\circ, 47.8^\circ, 54.86^\circ, 56.6^\circ, 70.3^\circ, 75^\circ, 82.22^\circ$ are attributed to the $\{101\}, \{004\}, \{200\}, \{105\}, \{211\}, \{220\}, \{215\}, \{224\}$ planes of anatase TiO_2 (JCPDS no. 21-1272), respectively.^{30,32,38} It can be seen that with the reaction time from 0.5 h to 4 h, the diffraction peak intensity of TiO_2 $\{101\}$ facet increases gradually, while the diffraction peak of TiOF_2 completely disappears at 4 h, which indicates that TiOF_2 has completely evolved into anatase TiO_2 . It should be noted that there is an obvious diffraction peak of $\{004\}$ facet in T-4h, which is often referred to as the existence of $\{001\}$ facet.^{25,39}




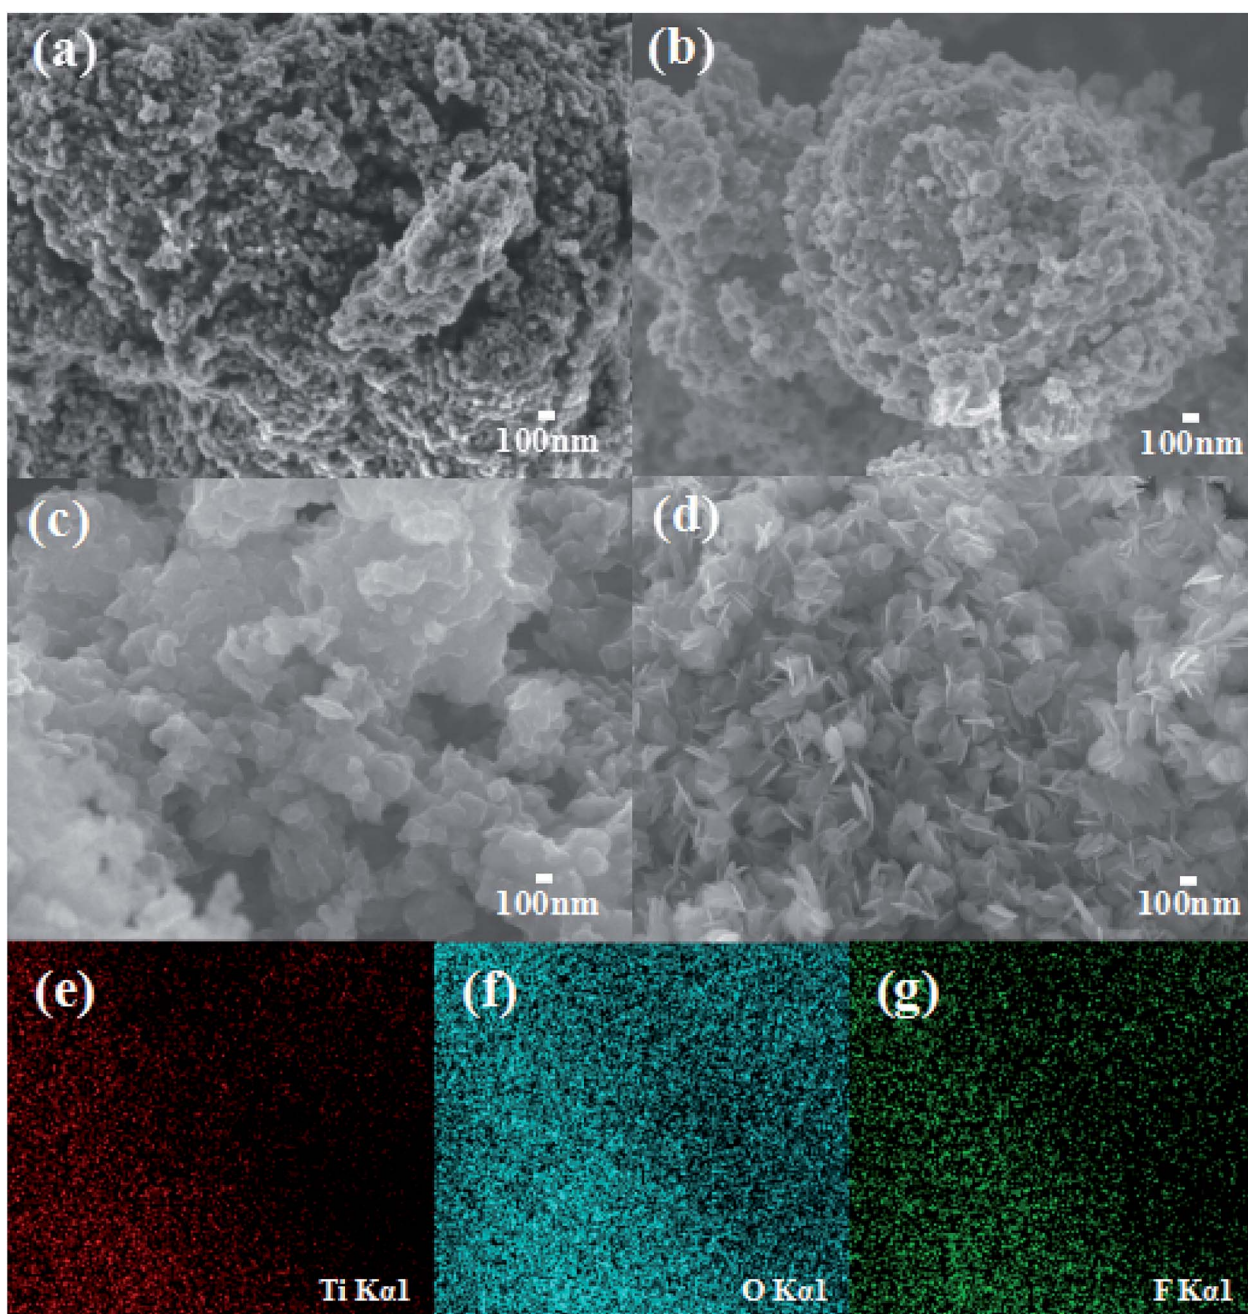


Fig. 2 The high-magnification FE-SEM images of (a) T-0.5h, (b) T-1h, (c) T-3h, (d) T-4h; the element mapping of (e) Ti, (f) O, (g) F in T-4h.

In summary, the chemical reactions of the formation of TiO_2 -{001/101} nanosheets can be proposed. The first step is the hydrolysis of TBOT. The reaction of TBOT to form $\text{Ti}(\text{OH})_4$ is shown in eqn (1).⁵⁴ Secondly, $\text{Ti}(\text{OH})_4$ can react with HF to produce TiOF_2 eqn (2).²⁵ Finally, with the hydrothermal reaction, TiOF_2 was hydrolyzed to anatase TiO_2 -{001/101}, as shown in eqn (3).⁴⁷



3.2. Morphology analysis of photocatalyst

Field emission scanning electron microscopy (FE-SEM) images of T-0.5h, T-1h, T-3h, T-4h are shown in Fig. 2. Fig. 2a shows the T-0.5h image. The novel of TiOF_2 shows coral-like structure

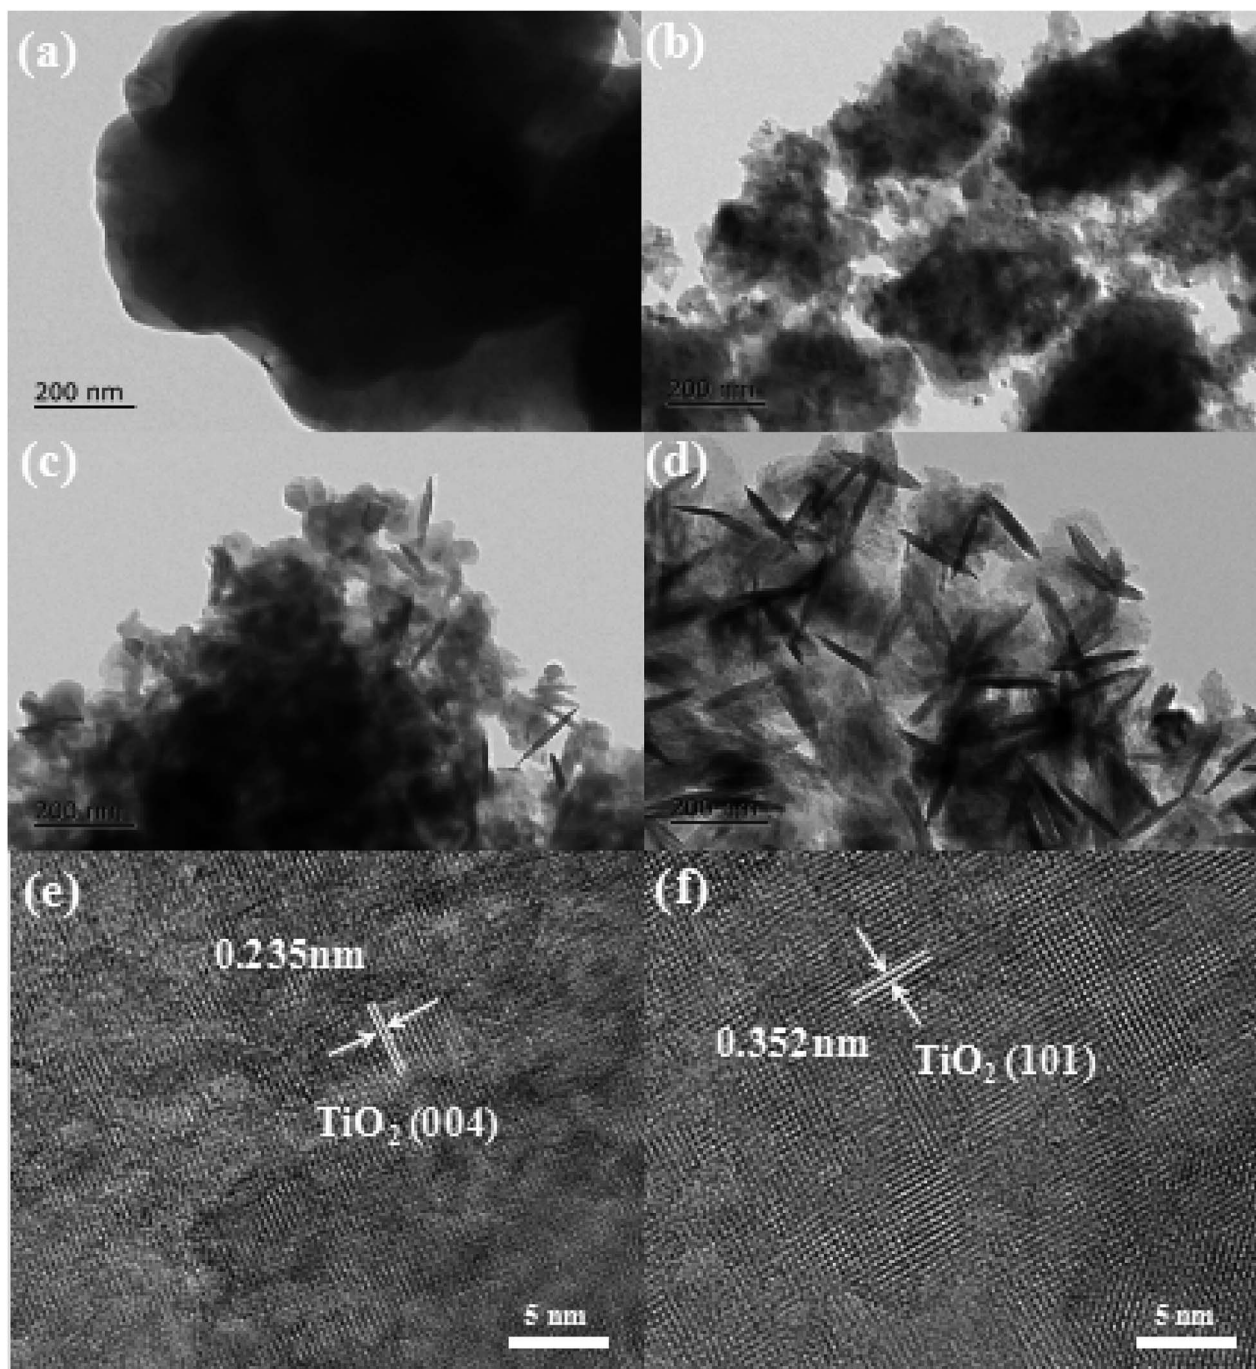


Fig. 3 TEM images of as-prepared samples (a) T-0.5h, (b) T-1h, (c) T-3h, (d) T-4h, and HRTEM images of (e and f) T-4h.

formed by the accumulation of spherical TiOF_2 nanoparticles, which is completely different from the cubic TiOF_2 that researchers have focused on before.^{58–61} The novel TiOF_2 has many macroporous structures, which is consistent with the pore size analysis. With the extension of reaction time, the spherical TiOF_2 nanoparticles tend to be flat, which may be due to the conversion of some TiOF_2 to TiO_2 (Fig. 2b). With the further hydrothermal reaction, it can be seen that the TiO_2 nanosheets derived from the surface of TiOF_2 are closely interlaced (Fig. 2c). By XRD analysis, most of the $\{101\}$ and a few $\{001\}$ facets of TiO_2 have been co-exposed, and a close interface contact is formed between the TiO_2 - $\{001/101\}$ and the untransformed TiOF_2 . When the reaction was further extended to 4 h, only TiO_2 - $\{001/101\}$ nanosheets were formed (Fig. 2d). TiO_2 nanosheets with an average diameter of about 200 nm are interlaced with each other to form clusters, which is conducive to the migration and transformation of electrons and holes between $\{001\}$ and $\{101\}$ facets. To further describe the element distribution of T-4h, elemental mapping analysis (Fig. 2e–g) of T-4h was performed. It is proved the existence of Ti, O, F elements and the mapping image matches well with the SEM image.

More morphological details on prepared samples were further obtained using transmission electron microscopy (TEM) images. It can be seen from Fig. 3a that the TiOF_2 nanoparticles are tightly packed together, which is consistent with the results observed by SEM. With the hydrothermal reaction, a small part of TiOF_2 was transformed into TiO_2 , showing a loose stacking structure (Fig. 3b). With further reaction, it can be seen that TiOF_2 nanoparticles are more dispersed, and more TiO_2 nanosheets with the size of 100–200 nm are closely linked with TiOF_2 (Fig. 3c). In Fig. 4d, it can be seen that the TiOF_2 nanoparticles have been completely transformed in TiO_2 nanosheets with $\{001\}$ and $\{101\}$ facets interlaced, with an average size of

200 nm. High-resolution TEM (HRTEM) image of T-4h (Fig. 3e) shows that the clear lattice fringes with a spacing of 0.352 nm correspond to the $\{101\}$ facets, indicating that $\{101\}$ facet is exposed on the surface of T-4h.⁴¹ The T-4h with a lattice spacing of 0.235 nm is indexed to the $\{004\}$ planed (Fig. 3f), demonstrating the exposure of $\{001\}$ facet on the surface of T-4h.^{45,49} Compared with the TiO_2 with $\{001\}$ facet exposure reported by most studies,^{48,54} the size of TiO_2 - $\{001/101\}$ derived from coral-like TiOF_2 is smaller. All the above results indicate that the coral-like TiOF_2 can be transformed into cluster TiO_2 - $\{001/101\}$.

3.3. BET specific surface area and pore structure

The specific surface area and pore size distribution of T-0.5h, T-1h, T-3h, T-4h were analyzed by nitrogen adsorption–desorption technology. As shown in Fig. 4, according to the classification of IUPAC, T-0.5h and T-1h show a typical IV type adsorption–desorption isotherm with H1 type hysteresis ring, which represents that the samples have a mesoporous structure with close-packed spherical particles and matches the image presented by SEM. T-3h, T-4h and P25 show a typical IV type adsorption–desorption isotherm with H3 type hysteresis ring, which represents that the samples have a mesoporous structure with cracks.²² Table 1 shows the specific surface area, pore volume and average pore size of all samples.

The specific surface areas of T-0.5h, T-1h, T-3h, T-4h are 33.44, 92.4, 31.75, 50.06 $\text{m}^2 \text{g}^{-1}$, respectively. The specific surface area of these samples is larger than that of P25 (21.98 $\text{m}^2 \text{g}^{-1}$). According to the corresponding BJH pore size distribution diagram (Fig. 4 inset), the average pore size of T-4h is 13.82 nm, which is well-matched with the size of TC (1.41 nm in length, 0.46 nm in width and 0.82 nm in height).

This is consistent with the strong removal rate of the dark reaction stage in the subsequent photocatalytic degradation experiment. Besides, these uniform and small pore mesopores are conducive to the absorption of light and multiple reflections inside the material and provide an effective transmission path for photogenerated carriers.³

3.4. FT-IR and EPR analysis

Fig. 5a shows the FT-IR spectra of photocatalysts prepared at different hydrothermal reaction times. The stretching and bending vibrations due to absorption by H_2O and the Ti-OH group on the sample surface are found at 3100–3500 cm^{-1} and 1628 cm^{-1} .^{25,47} T-0.5h, T-1h, T-3h have strong peaks at

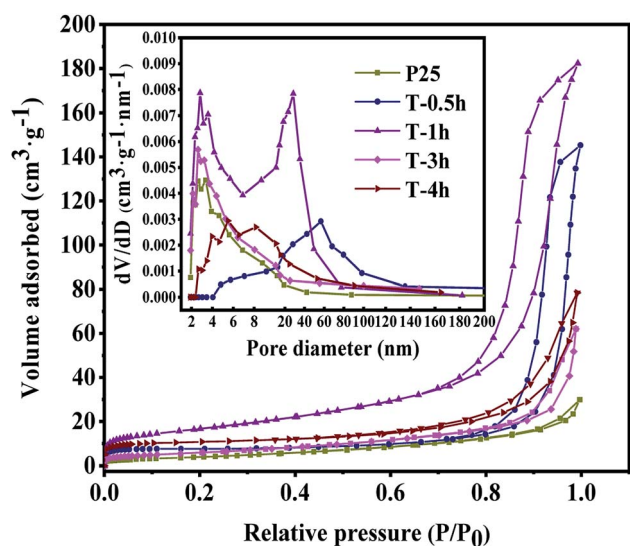


Fig. 4 Nitrogen adsorption and desorption isotherms of T-0.5h, T-1h, T-3h, T-4h and P25. The inset is the corresponding pore size distribution.

Table 1 Specific surface area, volume, mean pore size for the tested catalysts

Samples	Surface area ($\text{m}^2 \text{g}^{-1}$)	Pore volume ($\text{cm}^3 \text{g}^{-1}$)	Average pore size (nm)
T-0.5h	33.44	0.22477	37.39
T-1h	92.40	0.28203	18.88
T-3h	31.75	0.09572	17.78
T-4h	50.06	0.12127	13.82
P25	21.98	0.04630	12.67

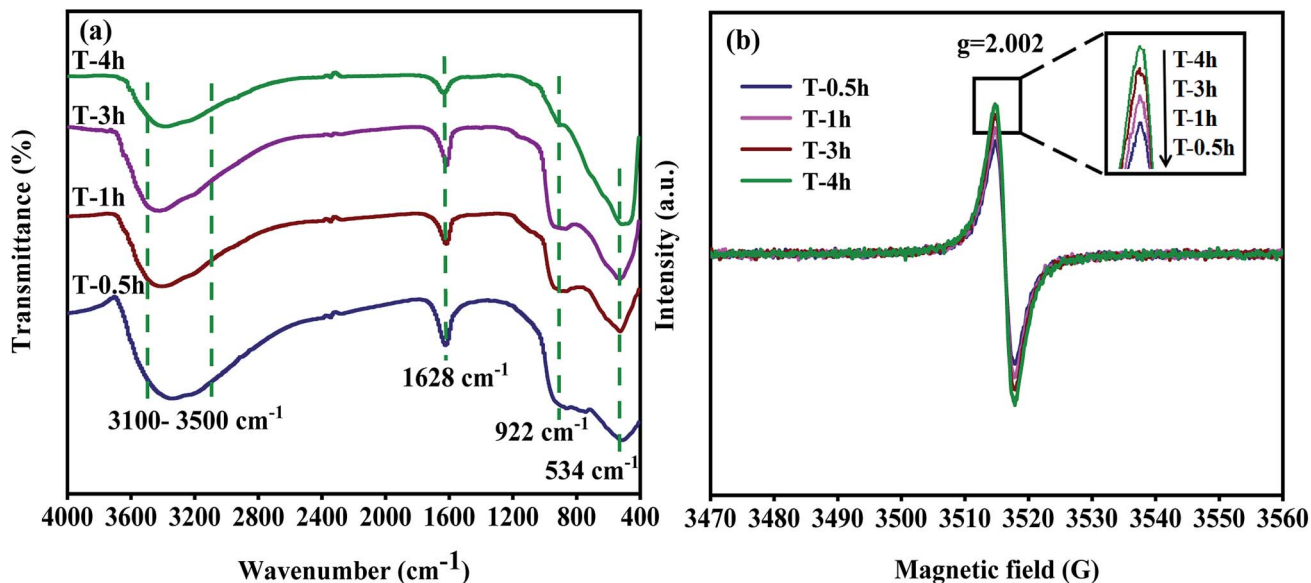


Fig. 5 FT-IR (a) and EPR (b) spectra of different samples.

922 cm^{-1} , which is attributed to Ti-F vibration in TiOF_2 . T-4h has an only a slight peak at 922 cm^{-1} , which can be attributed to the Ti-F vibration formed by adsorbed F and TiO_2 .⁵⁰ The peak at 534 cm^{-1} is attributed to Ti-O vibration or Ti-O-Ti vibration.⁵² It should be noted that the peak of T-4h shifts negatively from 534 cm^{-1} , which may be attributed to the formation of Ti^{3+} and O_v . The increased number of O_v in the lattice structure changes the number of Ti atom surrounding the O atom, and the electron cloud density around a Ti atom decreased.⁵⁹ This causes the stretching vibration absorption peak of a Ti-O bond to shift. Additional information on oxygen vacancy (O_v) was provided by EPR spectra collected at room temperature. As displayed in Fig. 5b, the signal at $g = 2.002$ corresponds to O_v .⁶³ It can be seen that all samples show the signal of O_v , and with the transformation of TiOF_2 to TiO_2 -{001/101}, the signal of O_v in T-4h is the strongest, which indicates that there is a lot of O_v in T-4h, which will effectively inhibit the recombination of electrons and holes, and improve the photocatalytic activity.

3.5. XPS analysis

The surface compositions and chemical states of pure T-0.5h, T-1h, T-3h and T-4h are displayed in Fig. 6. The survey spectra reveal signals of Ti, O, F, and C on all samples that match their respective signals from the individual spectra of TiOF_2 and TiO_2 (Fig. 6a), which is in accordance with the element mapping results. The existence of the peaks of element C at 284.8 eV can ascribe to surface adventitious reference carbon, which is unavoidable during the XPS measurement.²⁵

From the high-resolution XPS spectrum of $\text{Ti}2p$ in the samples (Fig. 6b). The binding energies of both $\text{Ti}2p_{3/2}$ (from 459.48 to 459.18 eV) and $\text{Ti}2p_{1/2}$ (from 465.28 to 464.88 eV) decreased slightly from TiOF_2 nanoparticles to cluster TiO_2 -{001/101}. This could be attributed to the decreased bond

strength of the Ti-O bond in TiO_2 compared with the Ti-F bond in TiOF_2 nanoparticles.⁵⁸ Through Gauss fitting, these peaks centered at 459.31 and 464.21 eV were ascribed to Ti^{3+} species, while peaks at 459.88 and 465.26 eV were ascribed to Ti^{4+} which indicate that the Ti^{3+} has formed in the reduction process.²⁵ The relative content of Ti^{3+} increases gradually with the increase of hydrothermal reaction time. The asymmetric O1s spectra were fitted to four different types of O, as shown in Fig. 6c. After Gauss fitting of all samples, the peak of the binding energy of each sample from small to large corresponds to lattice oxygen, hydroxyl oxygen, O_v and oxygen in adsorbed water, which can be considered as convincing evidence for the existence of O_v .^{58,63,64}

Fig. 6d shows the core-level F1s XPS spectra. The binding energy of F1s electrons shifted from 684.81 eV for T-0.5h to 684.76 eV for T-4h. The slight decrease in the F1s binding energy indicated the shifting of the Ti-F bond in the bulk TiOF_2 nanoparticles to the surface Ti-F bonds on the TiO_2 nanosheets.²

3.6. The optical absorption and PL analysis

Fig. 7a shows the light absorption performance of different photocatalysts and complexes after the adsorption of TCH. All samples show different absorption in the UV region without adsorption of TCH. The amount of light absorbed in the UV region increased in the order T-1h < P25 < T-0.5h < T-3h < T-4h. However, in the visible region, only T-0.5h shows visible light response, which is attributed to the narrow band gap energy of TiOF_2 (2.91 eV), as shown in Fig. 7b. Many researchers^{22,34} have studied the sensitization between TiO_2 and dyes, but only a few researchers focus on the sensitization between TiO_2 and antibiotics. Hasan *et al.*⁶⁵ believed that the LMCT effect formed between sulfonamides and TiO_2 , because sulfonamides did not absorb visible light. Interestingly, TCH has strong absorption in the visible and UV regions as shown in Fig. 7b, which is

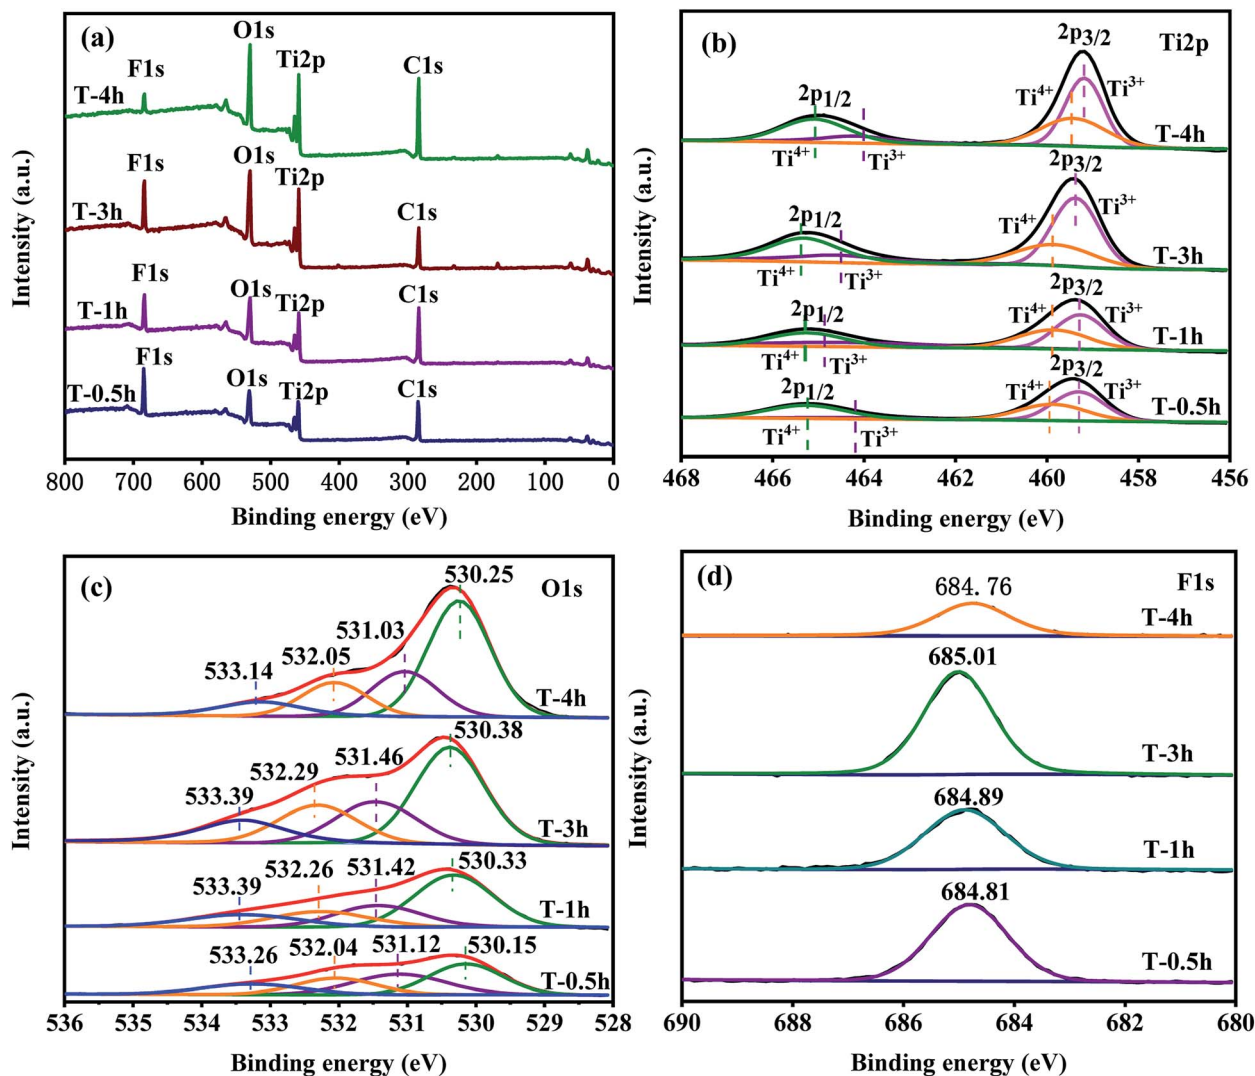


Fig. 6 (a) Survey XPS spectra of the samples; (b, c and d) high-resolution XPS data of Ti2p, O1s and F1s for samples respectively.

attributed to TCH molecule possesses a delocalized π bond connected with $-\text{OH}$ group, leading to a small energy gap between highest occupied molecular orbital (HOMO) and lowest unoccupied molecular orbital (LUMO) and thus availability for visible light absorption.⁶⁶ When the photocatalyst adsorbs TCH, it shows different degrees of absorption in the visible light region. Wu *et al.*⁶⁶ believed that the electron excited by visible light from HOMO to LUMO of TCH and further transferred to the conduction band of TiO_2 was a kind of sensitization. P25/TCH has only weak light absorption in the UV and visible light region. The amount of light absorbed in the visible light region increased in the order P25/TCH < T-4h/TCH < T-3h/TCH < T-1h/TCH < T-0.5h/TCH. The novel TiOF_2 seems to be more easily sensitized with TCH, showing the strongest absorption in the visible region, which may be attributed to the formation of intermolecular hydroxyl groups, which makes the π orbitals of TCH more easily form electronic coupling with the 3d orbitals of Ti^{4+} and Ti^{3+} , resulting in the formation of tight surface complexes between TCH and TiOF_2 . Although the T-0.5h/TCH has a strong response to visible light, T-0.5h does

not show the best photocatalytic activity in the degradation test of TCH, which shows that the response-ability of photocatalyst to visible light is not the only factor to evaluate the photocatalytic activity. The band gap energy (E_g) of T-0.5h, T-1h, T-3h, T-4h and P25 was calculated according to the Tauc curve. The results are shown in Fig. 7b. The band gap energies of T-0.5h, T-1h, T-3h, T-4h and P25 are 2.91 eV, 3.00 eV, 3.00 eV, 2.97 eV and 3.05 eV.

PL measurements are effective to examine the separation efficiency and recombination processes of photo-generated carriers because increased photo-generated electron-hole pair recombination results in stronger luminescence intensity. Three peaks were observed in the spectra.

Fig. 8 representatively shows the PL spectra of the T-0.5h, T-1h, T-3h, T-4h and P25 samples. Three peaks were observed in the spectra. The broad emission bands centered at 390 nm were ascribed to the interband transition of TiO_2 .⁵⁵ The two peaks at 454 and 469 nm are attributed to the O_v and two trapped electrons. The peak of O_v also appears in P25, which is attributed to the mixture of rutile and anatase phases, which increases the

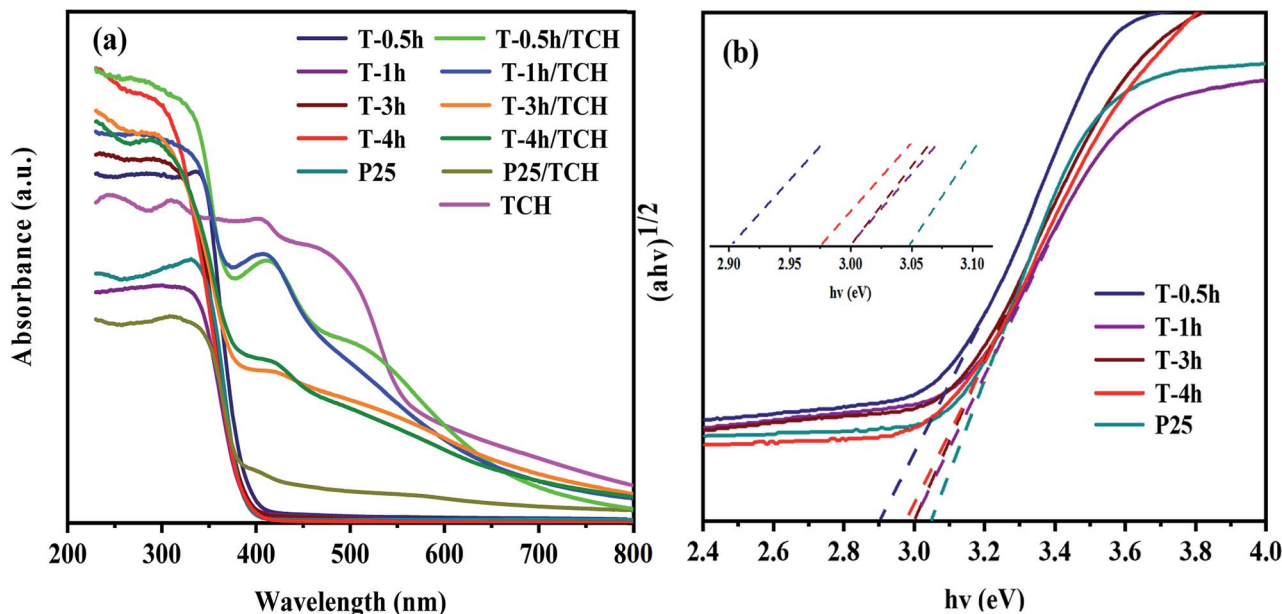


Fig. 7 (a) UV-Vis absorbance spectra of the samples and (b) the corresponding plots of $(\alpha hv)^{1/2}$ versus $h\nu$.

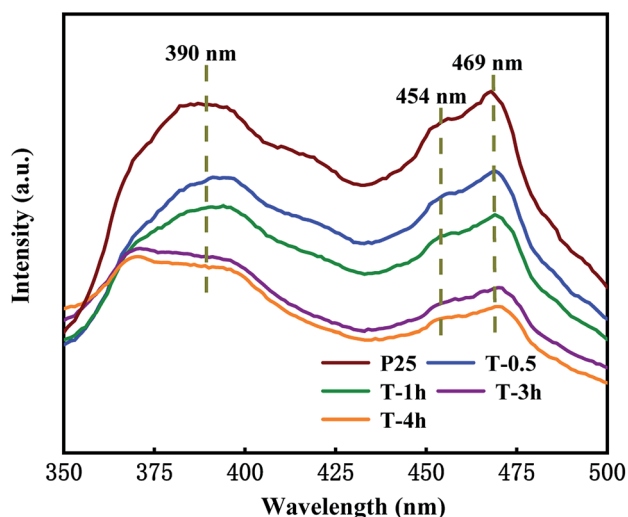


Fig. 8 The photoluminescence spectra with the excitation wavelength $\lambda_{\text{ex}} = 300$ nm for T-0.5h, T-1h, T-3h, T-4h and P25.

defect density in TiO_2 lattice.²⁵ It is worth noting that the luminescence intensity of T-3h is significantly lower than that of T-0.5h and T-1h, which can be attributed to the formation of suitable heterojunction between residual TiOF_2 and TiO_2 , which greatly reduces the recombination rate of electrons and holes. T-4h shows the lowest luminescence intensity, much lower than that of P25, this may be due to the surface heterojunction formed on $\{001\}$ and $\{101\}$ facets and the highest O_v concentration.^{56,59}

3.7. Photocatalytic activity

To study the photocatalytic performance of samples, TCH solution was used as a typical antibiotic pollutant in water to

simulate the solar photocatalytic degradation test. The results are shown in Fig. 9a. The photocatalysis system reacts in the dark for 60 minutes to reach the adsorption-desorption equilibrium before the sunlight. TCH has little self-degradation under sunlight. It can be seen that the samples of T-0.5h, T-1h, T-3h and T-4h have good adsorption properties. When the adsorption-desorption equilibrium was reached, the removal rates of TCH were 40%, 47%, 47% and 55%, respectively. T-4h sample has the strongest adsorption capacity for TCH. Large specific surface area, suitable pore structure and high exposure $\{001\}$ facets make TCH easy to adsorb on the surface of T-4h, which lays a foundation for the subsequent photocatalytic degradation. Although the adsorption capacity of T-0.5h for TCH is stronger than that of T-1h, the total removal rate (60%) is not higher than that of T-1h (62%). This shows that the adsorption performance of photocatalyst for TCH can not dominate its ability to degrade TCH. Surprisingly, the total degradation rate of TCH by T-4h reached 83.2% only after 10 min irradiation under simulated sunlight, and 92.3% after 60 min irradiation, which was much higher than that of P25 (52%).

The degradation kinetic model was studied and the photocatalytic properties of the samples were further analyzed. Fig. 9b shows that the linear relationship between degradation time (t) and $\ln(C_0/C)$ is almost a straight line, which proves that the degradation process of TCH conforms to pseudo-first-order reaction. The rate constants k of T-0.5h, T-1h, T-3h, T-4h and P25 were 0.00518, 0.00722, 0.01372, 0.02514 and 0.01123 min^{-1} , respectively. The results showed that the degradation rate of TCH by T-3h photocatalyst was significantly higher than that of T-0.5h and T-1h, which may be due to the appropriate ratio of residual TiOF_2 and TiO_2 in T-3h sample, and the synergistic effect of the two substances promoted the photodegradation.

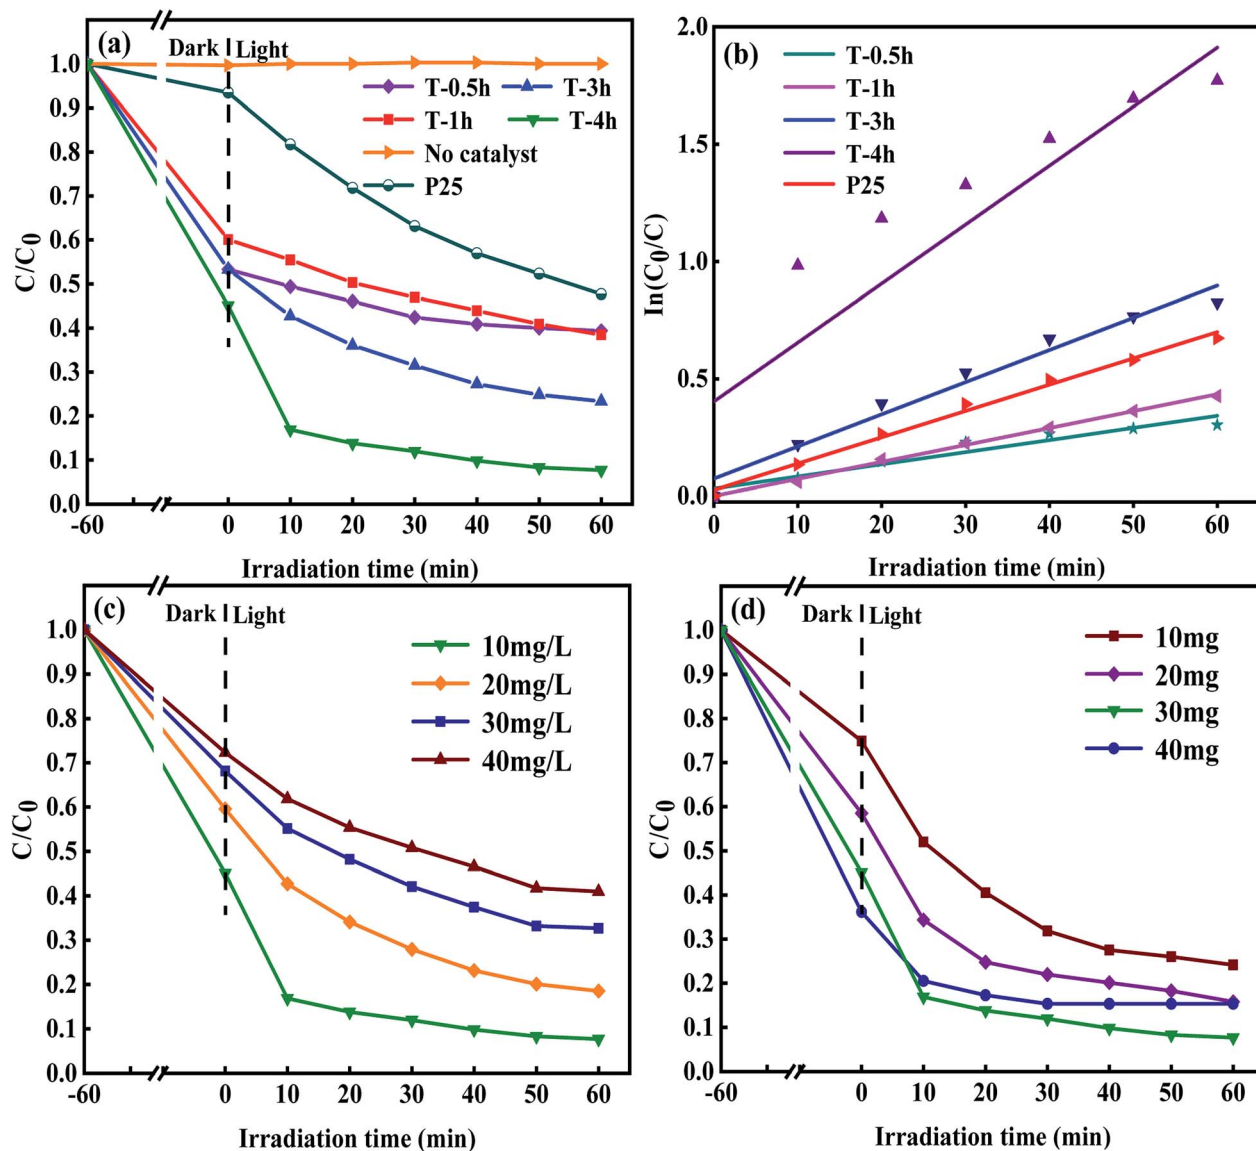


Fig. 9 (a) Photodegradation of TCH solution (10 mg L⁻¹, 100 mL) using different samples under simulated sunlight; (b) kinetic linear simulation curves of TCH solution photodegradation; (c) the effect of different concentration of TCH solution on the photocatalytic performance of T-4h (30 mg) under simulated sunlight; (d) the effect of different dosage of T-4h photocatalyst on degradation of TCH solution (10 mg L⁻¹, 100 mL) under simulated sunlight.

The maximum rate constant of T-4h was 2.24 times that of P25. Besides, the effects of different concentrations of TCH solution on the photocatalytic performance of the T-4h sample were studied (Fig. 9c). T-4h had the best degradation effect on the TCH solution of 10 mg L⁻¹. With the increase of TCH solution concentration, the photocatalytic performance of T-4h gradually decreased. It may be that the photocatalyst is not to provide enough active reaction sites to deal with so many TCH molecules. Fig. 9d shows the degradation curve of TCH solution with different T-4h dosage (0.1 g L⁻¹, 0.2 g L⁻¹, 0.3 g L⁻¹, 0.4 g L⁻¹). When the amount of catalyst is 0.3 g L⁻¹, the degradation effect of TCH is the best.

However, when the dosage of T-4h reached 0.4 g L⁻¹, the photocatalytic effect decreased which may be due to the

aggregation of excessive catalysts, which makes the solution turbid and leads to photon scattering, thus reducing the photocatalytic rate.¹⁶ The stability and reusability of photocatalyst are important factors affecting its practical application. Five consecutive cyclic photodegradation tests were carried out on sample T-4h, and the results are shown in Fig. 10a. After five cycles, the degradation rate of sample T-4h in simulated sunlight decreased from 92.3% to 84.5%, indicating that sample T-4h has a high reuse rate and photocatalytic performance.

As shown in Fig. 10b, after five cycles, the peak intensity of T-4h photocatalyst decreased, but the position of diffraction peak was the same as that before reaction, indicating that T-4h has high chemical stability.

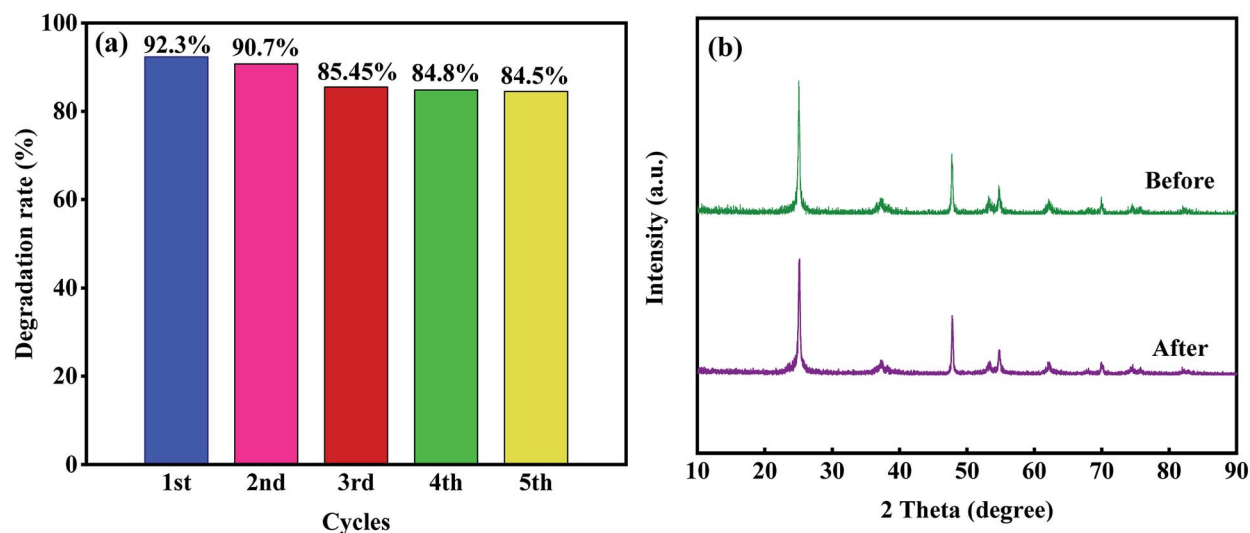


Fig. 10 (a) Photo stability tests over T-4h for TCH degradation; (b) XRD patterns of T-4h before and after five cycling runs; (c) effect of different scavengers on the degradation of TCH (10 mg L^{-1} , 100 mL) efficiencies over T-4h.

Besides, the settlement performance of T-4h and P25 were further studied. The digital images of P25 and T-4h suspensions in deionized water at pH 7.0 were taken at different sedimentation times, as shown in Fig. 11. P25 nanoparticles were well dispersed in water and settled very slowly. The supernatant was still very turbid after 24 h of sedimentation. The settling behavior of T-4h was distinctly different from that of P25. Most of the composites was settled in 4 h leaving a small fraction of T-4h suspended in the supernatant, which became clear after 24 h

of sedimentation. This shows that T-4h is more conducive to the practical application of wastewater treatment than P25.

3.8. Photocatalysis mechanism

In general, hydroxyl radicals ($\cdot\text{OH}$), superoxide radicals ($\cdot\text{O}_2^-$) and holes (h^+) can be found in the photocatalytic degradation process. For this reason, many scavengers, such as benzoquinone (BQ, $\cdot\text{O}_2^-$), *tert*-butyl alcohol (*t*-BuOH, $\cdot\text{OH}$), methanol (MT, h^+) and so on, were introduced to carry out free radical trapping experiments.

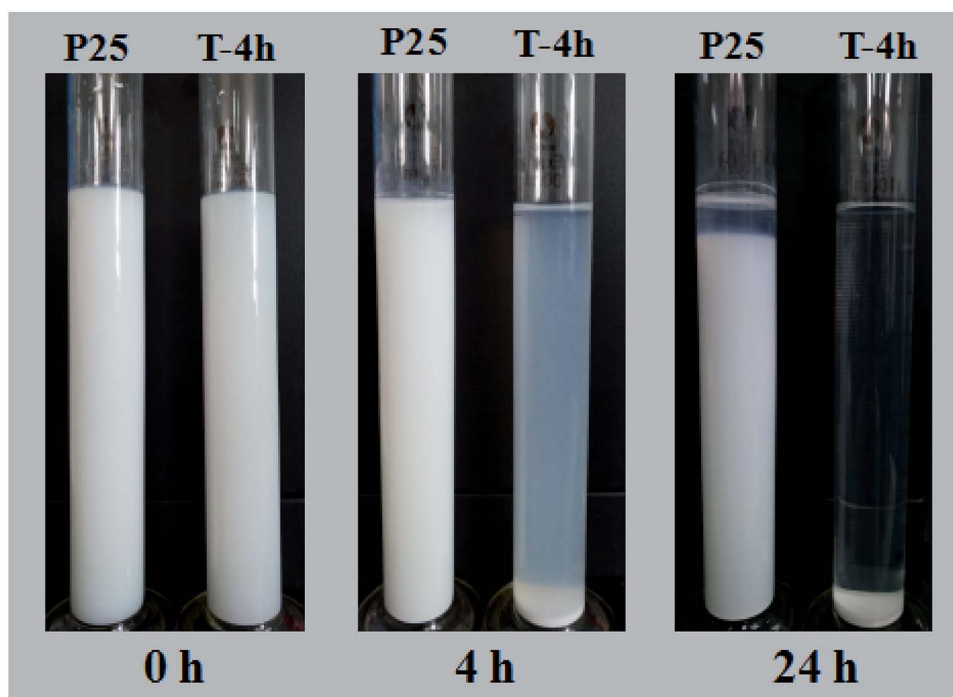


Fig. 11 Photographs of P25 suspension and T-4h suspension in deionized water at pH 7.0 at different settling times.

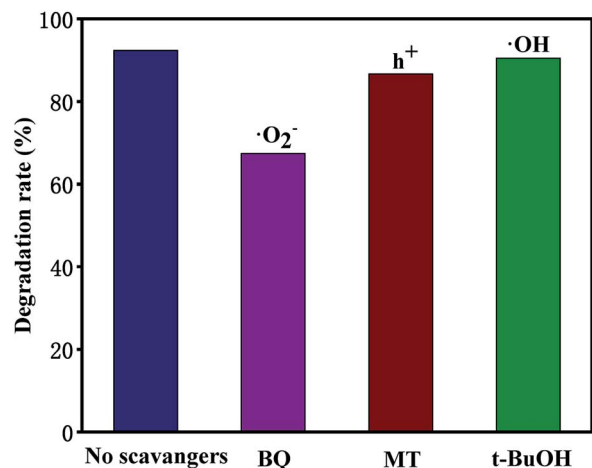


Fig. 12 Effect of different scavengers on the degradation of TCH (10 mg L^{-1} , 100 mL) efficiencies over T-4h.

It can be seen from Fig. 12 that under simulated sunlight irradiation, the introduction of BQ drastically decreased photodegradation efficiency of TCH from 92.3 to 67.4%, suggesting that $\cdot\text{O}_2^-$ played a key role in the photodegradation. When MT was added, the total degradation rate decreased by 5.65%, indicating that h^+ was the secondary substance affecting the photocatalytic degradation. After adding *t*-BuOH, the photocatalytic degradation was almost not inhibited, and the total removal rate decreased by 2%, indicating that $\cdot\text{OH}$ did not play a major role in the degradation. Based on the experimental results, the possible

mechanism of outstanding photocatalytic activity of T-4h was proposed (Fig. 13). Firstly, the $\{001\}$ facets of $\text{TiO}_2\text{-}\{001/101\}$ has a strong adsorption capacity for TCH.

Furthermore, the π orbital of TCH may form electronic coupling with the 3d orbital of Ti^{4+} , resulting in a surface complex between TCH and $\text{TiO}_2\text{-}\{001/101\}$.⁶⁷

TCH was degraded simultaneously in two pathways. In the first path, electrons are excited from the HOMO level of TCH to LUMO level under simulated sunlight, and then rapidly injected into the conduction band maximum (CBM) position of $\text{TiO}_2\text{-}\{001\}$ facets.³⁹ However, TCH lost its electrons and remained a stable product (TCH^+). Because the CBM of $\text{TiO}_2\text{-}\{001\}$ facets is more negative than that of $\text{TiO}_2\text{-}\{101\}$ facets. The electrons on CBM of $\text{TiO}_2\text{-}\{001\}$ facets can migrate to CBM of $\text{TiO}_2\text{-}\{101\}$ facets, and eventually react with O_2 adsorbed on the $\text{TiO}_2\text{-}\{101\}$ facet to form $\cdot\text{O}_2^-$ to oxidize TCH and TCH^+ .

In the second path, the doping of $\text{Ti}^{3+}/\text{O}_v$ can form new states at the bottom of the $\text{TiO}_2\text{-}\{001/101\}$ CBM. Under simulated sunlight irradiation, the $\{001\}$ and $\{101\}$ facets of TiO_2 produce electron-hole pairs respectively. The CBM and $\text{Ti}^{3+}/\text{O}_v$ state potentials of $\text{TiO}_2\text{-}\{001\}$ facets are negative than that of $\text{TiO}_2\text{-}\{101\}$ facets, respectively, allowing the holes of $\text{TiO}_2\text{-}\{101\}$ CBM partly transfer to that of $\text{TiO}_2\text{-}\{001\}$ CBM, and the electrons in $\text{Ti}^{3+}/\text{O}_v$ states of $\text{TiO}_2\text{-}\{001\}$ facets transfer to the $\text{Ti}^{3+}/\text{O}_v$ states of $\text{TiO}_2\text{-}\{101\}$ facets.⁶⁷ This process resulted in efficient space separation of photo-induced charge carriers to suppress recombination. Similar to the first pathway, electrons in the $\text{Ti}^{3+}/\text{O}_v$ states can interact with O_2 to form $\cdot\text{O}_2^-$ which can oxidize TCH and TCH^+ . The remaining holes can react with H_2O to form $\cdot\text{OH}$ and oxidize TCH with $\cdot\text{O}_2^-$.

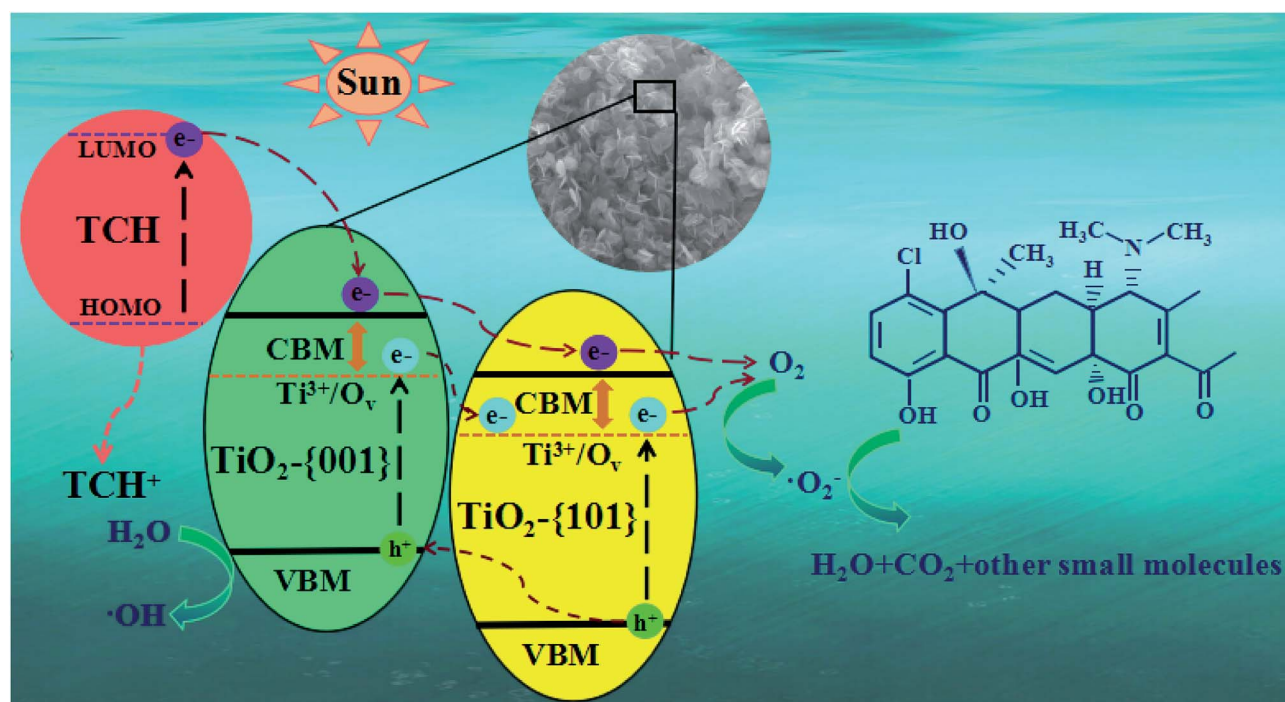


Fig. 13 Schematic illustration of the photocatalytic mechanism for TCH removal over the T-4h photocatalyst.

4. Conclusions

In summary, coral-like TiOF_2 can be synthesized by a one-step hydrothermal method, and with the extension of hydrothermal reaction time, cluster $\text{TiO}_2\{001/101\}$ with the smaller size can be obtained. The prepared cluster $\text{TiO}_2\{001/101\}$ exhibits excellent TCH degradation activity under simulated sunlight. The sensitization between TCH and cluster $\text{TiO}_2\{001/101\}$ can induce strong visible light absorption. It is worth noting that the photocatalyst has good stability, repeatability, and sedimentation, which is very important in practical application. This work opens up a new way to explore the TiOF_2 and provides a new idea for the degradation of TCH.

Conflicts of interest

There is no conflict of interests existing in the manuscript submission, and it is approved by all of the authors for publication. All the authors listed have approved the manuscript to be enclosed.

Acknowledgements

This work was supported by Special Project for Performance Guidance of Scientific Research Institution in Chongqing (19237), Chongqing Special Financial Funds Project (19511), the Earmarked Fund for Modern Agro-industry Technology Research System (CARS-35) and Scientific Observation and Experiment Station of Livestock Equipment Engineering in Southwest, Ministry of Agriculture and Rural Affairs.

References

- 1 D. Wan, L. Wu, Y. Liu, J. Chen, H. Zhao and S. Xiao, *Langmuir*, 2019, **35**, 3925–3936.
- 2 C. Lv, X. Lan, L. Wang, X. Dai, M. Zhang, J. Cui, S. Yuan, S. Wang and J. Shi, *Environ. Technol.*, 2019, **11**.
- 3 Q. Zhu, Y. Sun, F. Na, J. Wei, S. Xu, Y. Li and F. Guo, *Appl. Catal., B*, 2019, **254**, 541–550.
- 4 W. Yang, Y. Han, C. Li, L. Zhu, L. Shi, W. Tang, J. Wang, T. Yue and Z. Li, *Chem. Eng. J.*, 2019, **375**, 122076.
- 5 J. Miao, F. Wang, Y. Chen, Y. Zhu, Y. Zhou and S. Zhang, *Appl. Surf. Sci.*, 2019, **475**, 549–558.
- 6 Y. Ma, H. Xiong, Z. Zhao, Y. Yu, D. Zhou and S. Dong, *Chem. Eng. J.*, 2018, **351**, 967–975.
- 7 H. Xiong, D. Zou, D. Zhou, S. Dong, J. Wang and B. E. Rittmann, *Chem. Eng. J.*, 2017, **316**, 7–14.
- 8 L. Feng, X. Li, X. Chen, Y. Huang, K. Peng, Y. Huang, Y. Yan and Y. Chen, *Sci. Total Environ.*, 2020, **708**, 135071.
- 9 X. Chen, X. Jiang, C. Yin, B. Zhang and Q. Zhang, *J. Hazard. Mater.*, 2019, **367**, 194–204.
- 10 H. Song, L. Yan, J. Jiang, J. Ma, S. Pang, X. Zhai, W. Zhang and D. Li, *Chem. Eng. J.*, 2018, **344**, 12–20.
- 11 G. Yang, D. Bao, D. Zhang, C. Wang, L. Qu and H. Li, *Nanoscale Res. Lett.*, 2018, **13**, 146.
- 12 M. Liu, Y. Liu, D. Bao, G. Zhu, G. Yang, J. Geng and H. Li, *Sci. Rep.*, 2017, **7**, 43717.
- 13 Y. Wang, L. Rao, P. Wang, Z. Shi and L. Zhang, *Appl. Catal., B*, 2020, **262**, 118308.
- 14 C. Hou, J. Xie, H. Yang, S. Chen and H. Liu, *RSC Adv.*, 2019, **9**, 37911–37918.
- 15 J. Xu, C. Liu, J. Niu and M. Chen, *Sep. Purif. Technol.*, 2020, **230**, 115861.
- 16 W. Li, Q. Chen, X. Lei and S. Gong, *RSC Adv.*, 2019, **9**, 5100–5109.
- 17 Q. Zhang, J. Bai, G. Li and C. Li, *J. Solid State Chem.*, 2019, **270**, 129–134.
- 18 C. Hou, B. Hu and J. Zhu, *Catalysts*, 2018, **8**, 575.
- 19 Z. Yu, H. Moussa, B. Chouchene, M. Liu, R. Schneider, W. Wang, M. Moliere and H. Liao, *Nanotechnology*, 2019, **30**, 045707.
- 20 S. Zhong, C. Lv, M. Shen, L. Wu and C. Li, *J. Mater. Sci.: Mater. Electron.*, 2019, **30**, 4152–4163.
- 21 V. Madhubala, A. Pugazhendhi and K. Thirunavukarasu, *Process Biochem.*, 2019, **86**, 186–195.
- 22 V. M. Ramakrishnan, N. Muthukumarasamy, P. Balraju, S. Pitchaiya, D. Velauthapillai and A. Pugazhendhi, *Int. J. Hydrogen Energy*, 2020, **45**, 15441–15452.
- 23 M. Srinivasan, M. Venkatesan, V. Arumugam, G. Natesan, N. Saravanan, S. Murugesan, S. Ramachandran, R. Ayyasamy and A. Pugazhendhi, *Process Biochem.*, 2019, **80**, 197–202.
- 24 Y. Wang, L. Rao, P. Wang, Z. Shi and L. Zhang, *Appl. Catal., B*, 2020, **262**, 118308.
- 25 C. Hou and W. Liu, *R. Soc. Open Sci.*, 2018, **5**, 172005.
- 26 X. Wei, H. Cai, Q. Feng, Z. Liu, D. Ma, K. Chen and Y. Huang, *Mater. Lett.*, 2018, **228**, 379–383.
- 27 M. Malakootian, N. Olama and A. Nasiri, *Int. J. Environ. Sci. Technol.*, 2019, **16**, 4275–4284.
- 28 D. Hariharan, P. Thangamuniyandi, A. J. Christy, R. Vasantharaja, P. Selvakumar, S. Sagadevan, A. Pugazhendhi and L. C. Nehru, *J. Photochem. Photobiol., B*, 2020, **202**, 111636.
- 29 H. L. Shindume, Z. Zhao, N. Wang, H. Liu, A. Umar, J. Zhang, T. Wu and Z. Guo, *J. Nanosci. Nanotechnol.*, 2019, **19**, 839–849.
- 30 E. O. Oseghe and A. E. Ofomaja, *J. Environ. Manage.*, 2018, **223**, 860–867.
- 31 Y. Chen and K. Liu, *Chem. Eng. J.*, 2016, **302**, 682–696.
- 32 G. Guo, H. Guo, F. Wang, L. J. France, W. Yang, Z. Mei and Y. Yu, *Green Energy Environ.*, 2020, **5**, 114–120.
- 33 J. J. Murcia, E. G. Avila-Martinez, H. Rojas, J. Cubillos, S. Ivanova, A. Penkova and O. H. Laguna, *Nanomaterials*, 2019, **9**, 517.
- 34 V. M. Ramakrishnan, N. Muthukumarasamy, S. Pitchaiya, S. Agilan, A. Pugazhendhi and D. Velauthapillai, *Int. J. Energy Res.*, 2020, DOI: 10.1002/er.5806.
- 35 G. Liu, G. Wang, Z. Hu, Y. Su and L. Zhao, *Appl. Surf. Sci.*, 2019, **465**, 902–910.
- 36 A. Bathla, R. A. Rather, T. Poonia and B. Pal, *J. Nanosci. Nanotechnol.*, 2020, **20**, 3123–3130.
- 37 X. Du, X. Bai, L. Xu, L. Yang and P. Jin, *Chem. Eng. J.*, 2020, **384**, 123245.

- 38 T. An, J. Chen, X. Nie, G. Li, H. Zhang, X. Liu and H. Zhao, *ACS Appl. Mater. Interfaces*, 2012, **4**, 5988–5996.
- 39 S. Zhang, Z. Yin, L. Xie, J. Yi, W. Tang, T. Tang, J. Chen and S. Cao, *Ceram. Int.*, 2020, **46**, 8949–8957.
- 40 X. Zhang, Y. Chen, Q. Shang and Y. Guo, *Sci. Total Environ.*, 2020, **716**, 137144.
- 41 M. Sun, W. Kong, Y. Zhao, X. Liu, J. Xuan, Y. Liu, F. Jia, G. Yin, J. Wang and J. Zhang, *Nanomaterials*, 2019, **9**, 1603.
- 42 X. Gao, J. Tao, X. Xiao and J. Nan, *J. Photochem. Photobiol., A*, 2018, **364**, 202–207.
- 43 A. Kumar, M. Khan, L. Fang and I. M. C. Lo, *J. Hazard. Mater.*, 2019, **370**, 108–116.
- 44 V. M. Ramakrishnan, N. Muthukumarasamy, S. Pitchaiya, S. Agilan, D. Velauthapillai and A. Pugazhendhi, *Int. J. Energy Res.*, 2020, DOI: 10.1002/er.5882.
- 45 M. Bellardita, C. Garlisi, L. Y. Ozer, A. M. Venezia, J. Sa, F. Mamedov, L. Palmisano and G. Palmisano, *Appl. Surf. Sci.*, 2020, **510**, 145419.
- 46 B. G. Anitha and L. G. Devi, *Chem. Phys. Lett.*, 2020, **742**, 137138.
- 47 C. Zhang, L. Tian, L. Chen, X. Li, K. Lv and K. Deng, *Chin. J. Catal.*, 2018, **39**, 1373–1383.
- 48 H. Zhang, X. Liu, Y. B. Li, Y. Li and H. Zhao, *Sci. China: Chem.*, 2012, **56**, 402–417.
- 49 X. Han, Q. Kuang, M. Jin, Z. Xie and L. Zheng, *J. Am. Chem. Soc.*, 2009, **131**, 3152–3153.
- 50 Y. Zheng, X. Hu and P. Yang, *CrystEngComm*, 2018, **20**, 4485–4491.
- 51 L. Wang, J. Liu, Y. Min and K. Zhang, *Appl. Surf. Sci.*, 2019, **473**, 738–745.
- 52 X.-Y. Sun, X. Zhang, X. Sun, N.-X. Qian, M. Wang and Y.-Q. Ma, *Beilstein J. Nanotechnol.*, 2019, **10**, 2116–2127.
- 53 Y. Lu, Y. Zang, H. Zhang, Y. Zhang, G. Wang and H. Zhao, *Sci. Bull.*, 2016, **61**, 1003–1012.
- 54 J. Chen, G. Li, H. Zhang, P. Liu, H. Zhao and T. An, *Catal. Today*, 2014, **224**, 216–224.
- 55 M. Khalil, T. H. Rangkuti, F. Naumi, J. Gunlazuardi, T. A. Ivandini, G. T. M. Kadja and J. Y. Mulyana, *Inorg. Chem. Commun.*, 2020, **118**, 107992.
- 56 L.-Y. Zhang, J. You, Q.-W. Li, Z.-H. Dong, Y.-J. Zhong, Y.-L. Han and Y.-H. You, *Coatings*, 2020, **10**, 27.
- 57 V. M. Ramakrishnan, N. Muthukumarasamy, P. Balraju, S. Pitchalya, D. Velauthapillai and A. Pugazhendhi, *Int. J. Hydrogen Energy*, 2020, **45**, 15441–15452.
- 58 Y. Zhang, M. Shang, Y. Mi, T. Xia, P. Wallenmeyer, J. Murowchick, L. Dong, Q. Zhang and X. Chen, *ChemPlusChem*, 2014, **79**, 1159–1166.
- 59 C. Zhang, L. Tian, L. Chen, X. Li, K. Lv and K. Deng, *Chin. J. Catal.*, 2018, **39**, 1373–1383.
- 60 Y. Zhang, T. Xia, M. Shang, P. Wallenmeyer, D. Katelyn, A. Peterson, J. Murowchick, L. Dong and X. Chen, *RSC Adv.*, 2014, **4**, 16146–16152.
- 61 Y. Zhang, Q. Zhang, T. Xia, D. Zhu, Y. Chen and X. Chen, *ChemNanoMat*, 2015, **1**, 270–275.
- 62 T. Shi, Y. Duan, K. Lv, Z. Hu, Q. Li, M. Li and X. Li, *Front. Chem.*, 2018, **6**, 175.
- 63 Z. Liu, X. Liu, Q. Lu, Q. Wang and Z. Ma, *J. Taiwan Inst. Chem. Eng.*, 2019, **96**, 214–222.
- 64 J. Wu, X. Ma, L. Xu, B. Zhao and F. Chen, *Appl. Surf. Sci.*, 2019, **489**, 510–518.
- 65 N. Hasan, G. H. Moon, J. Park and J. Kim, *Sep. Purif. Technol.*, 2018, **203**, 242–250.
- 66 S. Wu, H. Hu, Y. Lin, J. Zhang and Y. Hu, *Chem. Eng. J.*, 2020, **382**, 122842.
- 67 M. Khalil, T. H. Rangkuti, F. Naumi, J. Gunlazuardi, T. A. Ivandini, G. T. M. Kadja and J. Y. Mulyana, *Inorg. Chem. Commun.*, 2020, **118**, 107992.