



Cite this: *RSC Adv.*, 2019, 9, 27042

Effectiveness of metal oxide catalysts for the degradation of 1,4-dioxane†

Kimberly N. Heck,^a Yehong Wang,^b Gang Wu,^c Feng Wang,^b Ah-Lim Tsai,^c David T. Adamson^d and Michael S. Wong^{d,*aefgh}

1,4-dioxane, commonly used as a solvent stabilizer and industrial solvent, is an environmental contaminant and probable carcinogen. In this study, we explored the concept of using metal oxides to activate H₂O₂ catalytically at neutral pH in the dark for 1,4-dioxane degradation. Based on batch kinetics measurements, materials that displayed the most suitable characteristics (high 1,4-dioxane degradation activity and high H₂O₂ consumption efficiency) were ZrO₂, WO_x/ZrO₂, and CuO. In contrast, materials like TiO₂, WO₃, and aluminosilicate zeolite Y exhibited both low 1,4-dioxane degradation and H₂O₂ consumption activities. Other materials (e.g., Fe₂O₃ and CeO₂) consumed H₂O₂ rapidly, however 1,4-dioxane degradation was negligible. The supported metal oxide WO_x/ZrO₂ was the most active for 1,4-dioxane degradation and had higher H₂O₂ consumption efficiency compared to ZrO₂. *In situ* acetonitrile poisoning and FTIR spectroscopy results indicate different surface acid sites for 1,4-dioxane and H₂O₂ adsorption and reaction. Electron paramagnetic resonance measurements indicate that H₂O₂ forms hydroxyl radicals ([•]OH) in the presence of CuO, and unusually, forms superoxide/peroxyl radicals ([•]O₂⁻) in the presence of WO_x/ZrO₂. The identified material properties suggest metal oxides/H₂O₂ as a potential advanced oxidation process in the treatment of 1,4-dioxane and other recalcitrant organic compounds.

Received 2nd July 2019
Accepted 14th August 2019

DOI: 10.1039/c9ra05007h

rsc.li/rsc-advances

1. Introduction

1,4-dioxane is an industrial solvent,¹ a byproduct present in personal-care products,¹ and a suspected carcinogen with US state maximum contaminant limits that are frequently below 1 ppb. Because it is used to stabilize chlorinated volatile organic compound (CVOC) solvents,^{1–5} 1,4-dioxane was found by Adamson *et al.* to co-occur at 76% of California sites containing trichloroethane, and at 68% of sites containing 1,1-dichloroethene.² Extrapolating this co-occurrence problem to the 15 000–25 000 US sites that are contaminated with CVOCs,⁶ 1,4-dioxane is likely widespread.

A number of advanced oxidation processes (AOPs) have been investigated for 1,4-dioxane remediation, including *ex situ* UV

oxidative processes (UV/H₂O₂, UV/ozone),⁷ photocatalysis,^{8–10} or sonolysis and photocatalysis.¹¹ A few studies looked at catalytic destruction of 1,4-dioxane, but most required the addition of high-energy resources such as UV light,^{12,13} ultrasonic waves,¹⁴ or electricity,^{15–17} which are not only costly from an energy perspective, but may also require the use of complicated reactor configurations and may not be suitable for universal treatment of 1,4-dioxane contamination (e.g. in chemical plumes).

“Dark” (non-photocatalytic) heterogeneous catalysis, which does not require additional energy sources, may be a more passive and more economically practical approach to treating 1,4-dioxane in water. Efforts have been made in the past to study the activation of chemical oxidants for AOP using materials as a heterogeneous form of Fenton's reagent, but few have focused much on 1,4-dioxane nor provided an experimental understanding of the surface chemistry.^{18,19} CuO has been investigated using ozone as oxidant, and implicated Lewis acid sites for the decomposition of ozone.²⁰ A Pd-based catalyst was reported effective for degrading 1,4-dioxane using peroxy-monosulfate, and suggested surface-bound radicals were responsible for degradation.²¹ Two studies discussed using H₂O₂; one a titanosilicate zeolite that was slightly active in water at 60 °C,²² and another concerning Fe(II)-containing clays that showed degradation activity on the order of several days.²³ Unexplored for 1,4-dioxane degradation and other contaminants are a number of materials reported to be able to

^aDepartment of Chemical and Biomolecular Engineering, Rice University, Houston, TX, 77005, USA. E-mail: mswong@rice.edu

^bDalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian, China

^cDivision of Hematology, Department of Internal Medicine, University of Texas-Medical School at Houston, Houston, TX, 77030, USA

^dGSI Environmental, Houston, TX, 77098, USA

^eDepartment of Chemistry, Houston, TX, 77005, USA

^fDepartment of Civil and Environmental Engineering, Houston, TX, 77005, USA

^gDepartment of Materials Science and Nano Engineering, Houston, TX, 77005, USA

^hCenter for Nano-Enabled Water Treatment, Rice University, Houston, TX, 77005, USA

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9ra05007h



nonphotocatalytically catalyze the dark dissociation of H_2O_2 , such as ZrO_2 ²⁴ and TiO_2 .²⁵ Furthermore, any materials properties of these unconventional H_2O_2 -active materials which allow them to degrade organics is unclear.

In this study, we screened commercially available relatively inexpensive metal oxide H_2O_2 -active catalysts to establish a set of basic data for the degradation of aqueous-phase 1,4-dioxane using H_2O_2 at mild ambient conditions and in the dark. A 1,4-dioxane degradation rate constant was measured for each material at room temperature and atmospheric pressure, and at near-neutral pH. H_2O_2 consumption activity (quantified as a rate constant) and consumption efficiency (quantified as moles of 1,4-dioxane degraded per mole H_2O_2 consumed) were also determined. To understand the essential surface properties that direct the degradation process, we further analyzed the materials using *in situ* Fourier-transform infrared (FTIR) analysis of acid sites using pyridine, acid site poisoning catalytic tests using acetonitrile, and electron paramagnetic resonance (EPR). Based on these results, we proposed a reaction mechanism to explain the observed material-dependency of 1,4-dioxane degradation.

2. Materials

CuO (>97%) and $\gamma\text{-Al}_2\text{O}_3$ (>97%) were used as received from Strem Chemicals. ZrO_2 and TiO_2 P25 were obtained from Evonik. Fe_2O_3 (hydrated, catalyst grade 30–50 mesh, crushed prior to characterization and kinetic experiments), WO_3 (nanopowder), Zeolite Y (hydrogen, 30 : 1 SiO_2 : Al_2O_3), CeO_2 (99.95%, nanopowder), dichloromethane (chromasolv, 99.9%), and 1,4-dioxane (>99.5%), H_2O_2 (30%), and TiOSO_4 (~15 wt% in dilute sulfuric acid) were used as received from Sigma Aldrich. A zirconia-supported tungsten oxide material (“ WO_x/ZrO_2 ”, 20 wt% WO_3 content) was obtained from MEI Chemicals and used as-received. Specific surface areas (SSA) of the metal oxide materials were evaluated on a Quantachrome Autosorb IIIB using five-point BET calculations on samples degassed at 350 °C overnight. 5-Tert-butoxycarbonyl-5-methyl-1-pyrrolidine-*N*-oxide (BMPO) was obtained from Enzo Life Sciences. Deionized water was used in all experiments.

3. Analytical methods

3.1 Catalytic activity testing

For kinetic experiments, 171 mL of deionized (DI) water, 0.4 μL of 1,4-dioxane ($[\text{1,4-dioxane}]_0 = 27 \mu\text{M}$, 2.3 ppm), and 0–600 μL of 30% H_2O_2 ($[\text{H}_2\text{O}_2]_0 = 0\text{--}30 \text{ mM}$) were added to a 250 mL Boston round bottle. After stirring, a ~2 mL aliquot was taken from the reactor for baseline measurements of H_2O_2 and 1,4-dioxane. The catalyst was added to the reactor, which was then sealed with a septum, covered in foil to shield from ambient light, and magnetically stirred at 600 RPM. The amount of added catalyst was chosen such that the total exposed oxide surface area in the reaction medium was the same between experiments (475 m^2 per L-fluid, Table S1†). Aliquots (~1.5 mL) of reaction fluid were filtered with a 0.2 μm syringe filter to remove solid catalyst prior to H_2O_2 and 1,4-dioxane

concentration measurements. Each reaction was repeated three times. No degradation was observed in experiments where only 1,4-dioxane and catalyst were present.

Because of order-of-magnitude differences in initial concentrations, the disappearance of H_2O_2 and 1,4-dioxane were both modeled as pseudo-first order processes, where the rate of disappearance of reactant X (either H_2O_2 or 1,4-dioxane), r_X , is given by

$$r_X = \frac{dX}{dt} = k_{\text{meas},X} C_X \quad (1)$$

where t is time, C_X is the concentration of reactant X, and $k_{\text{meas},X}$ is the measured pseudo-first order rate constant, which can be found from integrating eqn (1) to obtain

$$\ln\left(\frac{C_X}{C_{X,0}}\right) = -k_{\text{meas},X} t \quad (2)$$

where $C_{X,0}$ is the initial concentration of the reactant.

In order to better compare intrinsic catalytic activity, we report the pseudo-first order rate constant normalized by added catalyst surface area for each reagent for each catalyst, k_X , since only exposed catalyst sites should be active. k_X is given by

$$k_X = \frac{k_{\text{meas},X}}{C_{\text{cat}}} \quad (3)$$

where C_{cat} is the concentration of catalyst surface area in the reactor (units of $\text{m}^2 \text{ mL}^{-1}$), given by eqn (4)

$$C_{\text{cat}} = \frac{\text{SSA}_{\text{cat}} g_{\text{cat}}}{V_{\text{reactor}}} \quad (4)$$

where SSA_{cat} is the specific surface area of the catalyst (units $\text{m}^2 \text{ g}^{-1}$, as determined by BET, see Table S1†), g_{cat} is the grams catalyst added to the reactor (Table S1†), and V_{reactor} is the liquid reaction volume.

Selective site poisoning experiments were conducted using acetonitrile (which can chemisorb onto Lewis acid sites²⁶), in which the catalysts were premixed with 318 μL of 0.1 M acetonitrile stock solution (final [acetonitrile] in reactor = 186 μM).²⁷ Residual activity is defined as

$$\text{residual } k = \frac{k_{\text{no acetonitrile}}}{k_{\text{acetonitrile}}} \times 100\%. \quad (5)$$

3.2 H_2O_2 quantification

H_2O_2 remaining in the aliquots was quantified using titanium oxysulfate (TiOSO_4 , ~15 wt% in dilute H_2SO_4). TiOSO_4 reacts with H_2O_2 to form the yellow-colored product perititanic acid, quantifiable using UV-vis.²⁸ A standard curve was made using 0–80 μM H_2O_2 to verify that the response was linear at the maximum extinction (at $\lambda = 405 \text{ nm}$). Reaction samples were diluted up to 20 \times to verify that absorbance at $\lambda = 405 \text{ nm}$ was in the standard.

3.3 1,4-Dioxane quantification

The concentration of 1,4-dioxane was determined as detailed by Li *et al.*²⁹ Briefly, 0.5 mL of reaction aliquot and 0.5 mL of

dichloromethane (DCM) was added to an autosampler vial and vigorously shaken for at least 30 seconds to extract the 1,4-dioxane into the DCM phase. Following freezing at $-20\text{ }^{\circ}\text{C}$ for at least 1 hour, the liquid DCM was decanted from the vial and put into a fresh autosampler vial containing ~ 10 mg of sodium sulfate to sequester any residual water. These samples were then analyzed *via* GC-MS. A calibration curve was prepared using this method with 0–3200 ppb 1,4-dioxane in deionized water.

3.4 Determination of mass transfer resistances

To ensure the reported rate constants were kinetically limited, we evaluated external mass transfer resistances as we have done previously.^{30,31} We note that in this system, there is no gas phase reactants, therefore k_{g1} was neglected. Fig. S1,† prepared using CuO, one of the most active catalysts for H_2O_2 degradation, shows a linear increase in the measured rate constant with added catalyst, indicating there were no external mass transfer limitations in this range. The circled point corresponds to the SSA loading chosen for all other reactions.

To assess any internal mass transfer resistances, we determined the Weisz–Prater criterion (C_{WP}) for both the first-order degradation of H_2O_2 and 1,4-dioxane according to^{32,33}

$$C_{\text{WP}} = \frac{k' \rho_c R^2}{D_e} \quad (6)$$

where k' is the catalyst mass normalized rate constant ($\text{m}^3 \text{s}^{-1} \text{g}_{\text{cat}}^{-1}$), ρ_c is the catalyst density (g m^{-3}), R is the pellet radius (m, conservatively assumed to be 1 mm for all catalysts), and D_e is the effective diffusivity of H_2O_2 and 1,4-dioxane in the pores (assumed to be equivalent to H_2O_2 and 1,4-dioxane diffusivity in water, $5.0 \times 10^{-6} \text{ m}^2 \text{ h}^{-1}$ and $6.0 \times 10^{-8} \text{ m}^2 \text{ h}^{-1}$ respectively). As shown in Table S2,† the Weisz–Prater criterion was less than one for all materials, which implies that the catalysts' activities were not limited by internal diffusion.

3.5 EPR experiments

For the spin-trap experiments, 4 mM of CuO, WO_x/ZrO_2 , or ZrO_2 was added to a 83 mM H_2O_2 and 5–10 mM BMPO solution, then mixed for ~ 2 min. Transient radical species rapidly react with BMPO, forming stable adducts.^{34–37} 15 μL of the reaction mixture was sampled and sealed with Critoseal. EPR spectra of the spin trapped radicals were obtained using a Bruker EMX spectrometer at room temperature. EPR measurements were taken using a frequency of 9.30 GHz, power of 20 mW, modulation frequency of 100 kHz, modulation amplitude of 0.1 G, and time constant of 0.33 s. No radicals were detected in control solutions without metal oxide.

Freeze trapping was also attempted for direct detection of radicals. In these experiments, the 5 mm o.d. EPR tubes were rapidly frozen in an EtOH/dry ice bath before transferring into liquid N_2 . The measurements were conducted at 115 K using a frequency of 9.28 GHz; power of 1 mW; modulation frequency of 100 kHz, modulation amplitude of 2G, and time constant of 0.33 s.

3.6 Pyridine-FTIR

For the pyridine-FTIR experiments, the sample was pressed into a 13 mm diameter disk and analyzed in a homemade cell attached to a closed circulation system. Before pyridine adsorption, the cell was heated to $150\text{ }^{\circ}\text{C}$ for 30 min at low pressure ($<10^{-3}$ Pa) then allowed to cool to $25\text{ }^{\circ}\text{C}$. A spectrum was recorded as the background using a Bruker Tensor 27 FTIR spectrometer in transmittance mode. Gas-phase pyridine was then contacted with the sample for ~ 20 min, and then the chamber evacuated at $150\text{ }^{\circ}\text{C}$ for 30 min at low pressure ($<1.0 \times 10^{-3}$ Pa) to remove pyridine that was physically adsorbed before a FTIR spectrum of the chemisorbed pyridine was collected. Spectra were also taken after the sample was cooled to $25\text{ }^{\circ}\text{C}$.

For experiments looking at both pyridine and water, gas-phase water (~ 1 atm) was added to the cell after the pyridine step. The water atmosphere was maintained for ~ 20 min at $25\text{ }^{\circ}\text{C}$ and then desorbed at $25\text{ }^{\circ}\text{C}$ and $150\text{ }^{\circ}\text{C}$. The sample was brought to $25\text{ }^{\circ}\text{C}$, and an additional spectrum collected.

The Lewis acid site concentration is given by³⁸

$$C_{\text{Lewis}} = \frac{1.42 \times I \times R^2}{W} \quad (7)$$

where C_{Lewis} is Lewis acid site concentration ($\text{mmol g}_{\text{catalyst}}^{-1}$), R is the catalyst radius (cm), I is the integration of the Lewis band (cm^{-1}), W is the weight of disk (mg), and the factor 1.42 mol cm^{-1} is the extinction coefficient of pyridine adsorbed to an acid site.³⁸ The W used for the experiments for CuO, ZrO_2 , and WO_x/ZrO_2 were 4.17, 27.2, and 39.5 mg respectively, and the I were found to be 1.095, 4.173, and 17.317 cm^{-1} respectively.

4. Results and discussion

Fig. 1a shows the dark catalytic activities for H_2O_2 consumption alone (without 1,4-dioxane). CeO_2 , Fe_2O_3 , and CuO all have high reaction rate constants, which generally agree with reported values of these Fenton-like materials, *i.e.*, those that activate H_2O_2 *via* formal oxidation/reduction of the metal sites.^{25,39} The exception is CuO, which was slower than other reports (Table S3†), which may be due to differences in catalyst and H_2O_2 concentrations between studies. ZrO_2 and TiO_2 showed H_2O_2 degradation ability, in agreement with previous reports.^{24,25,39–41} SiO_2 and Al_2O_3 exhibited only trace activity (also in agreement with literature),²⁵ as was the case with zeolite Y. Monometallic WO_3 was also nearly inactive.

Fig. 1b shows catalytic activities for the H_2O_2 consumption in the presence of 1,4-dioxane, and catalytic activity for 1,4-dioxane degradation. We denote the “best” 1,4-dioxane degradation catalysts as those that quickly degrade 1,4-dioxane (high k_{diox}) while consuming low amounts of H_2O_2 (low $k_{\text{H}_2\text{O}_2}$), *i.e.*, those closest to the lower right hand side of the semi-log k -by- k plot. Catalytic activities for H_2O_2 consumption did not generally change in the presence of 1,4-dioxane (comparing Fig. 1a and b). Materials weakly active for H_2O_2 consumption (Al_2O_3 , SiO_2 , and WO_3) consumed H_2O_2 more rapidly, except for zeolite Y, which became less active; all these showed minimal 1,4-dioxane degradation ability.

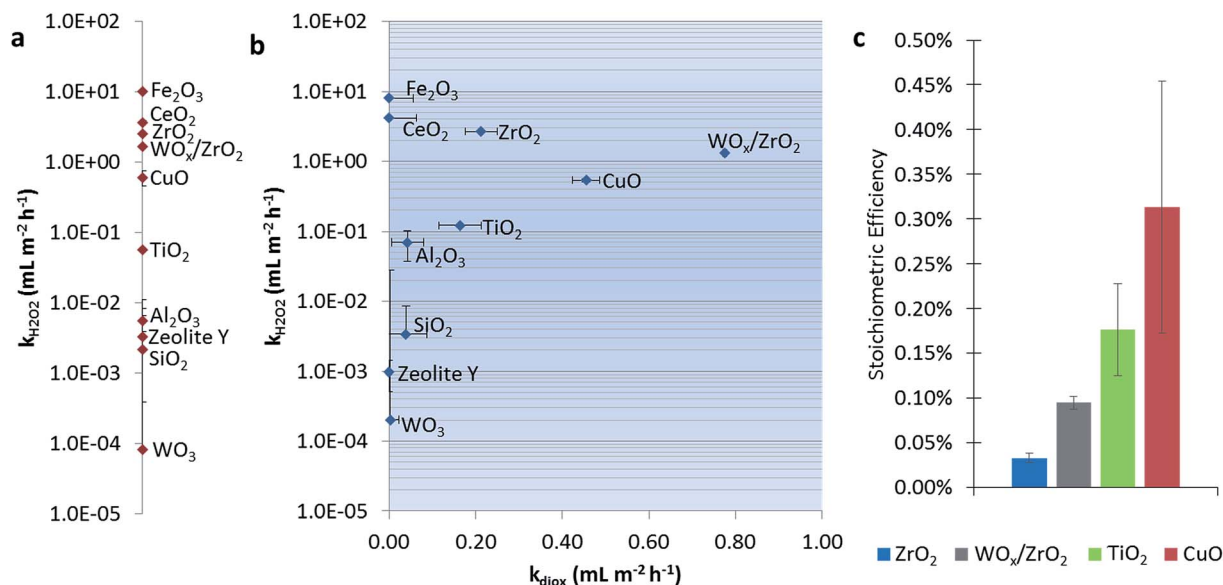


Fig. 1 Pseudo-first order rate constants normalized by catalyst surface area for H_2O_2 consumption ($[\text{H}_2\text{O}_2]_0 = 15 \text{ mM}$, $\text{pH} = 6.5$) in the (a) absence and (b) presence of 1,4-dioxane ($[\text{1,4-dioxane}]_0 = 27 \mu\text{M}$). Panel (b) shows the rate constant for H_2O_2 consumption plotted against the 1,4-dioxane degradation rate constant. (c) Stoichiometric efficiency (defined as moles 1,4-dioxane degraded per mole H_2O_2 consumed) calculated for catalysts active for 1,4-dioxane degradation at 10–12% conversion.

Catalysts most active for H_2O_2 consumption were not the most effective at degrading 1,4-dioxane; Fe_2O_3 and CeO_2 , the catalysts with the highest $k_{\text{H}_2\text{O}_2}$, were inactive for 1,4-dioxane, and could be due to the conversion of H_2O_2 to nonreactive species under these reaction conditions (neutral pH). Materials that had the highest k_{diox} values were (listed in order of decreasing activity) $\text{WO}_x/\text{ZrO}_2 \gg \text{CuO} > \text{ZrO}_2 \gg \text{TiO}_2$. Their H_2O_2 consumption activity was also less than those of Fe_2O_3 and CeO_2 .

We calculated the stoichiometric efficiency for the four catalysts most active for 1,4-dioxane degradation during the batch reactions (Fig. 1c). Under these conditions, CuO was the most H_2O_2 -efficient, followed by TiO_2 , WO_x/ZrO_2 , and ZrO_2 .

These values are on the same order of magnitude as those measured by Sedlak and co-workers for the degradation of phenol using H_2O_2 over a silica-Fe catalyst at neutral conditions (~ 0.20 – 0.30%).^{42,43} A direct comparison of these results to other materials is made with caution, as the initial reactant amount and reactant type (50–250 mM H_2O_2 and 0.5 mM phenol vs. 15 mM H_2O_2 and 27 μM 1,4-dioxane) differ.

To further understand the surface mechanism, we explored the effects of initial H_2O_2 concentrations (1.5–30 mM) using a Langmuir–Hinshelwood–Hougen–Watson (LHHW) bimolecular surface reaction model, which assumes the two reactants (H_2O_2 and 1,4-dioxane) compete to adsorb to the same catalytic sites. The rate of H_2O_2 consumption ($r'_{\text{H}_2\text{O}_2}$) increased before

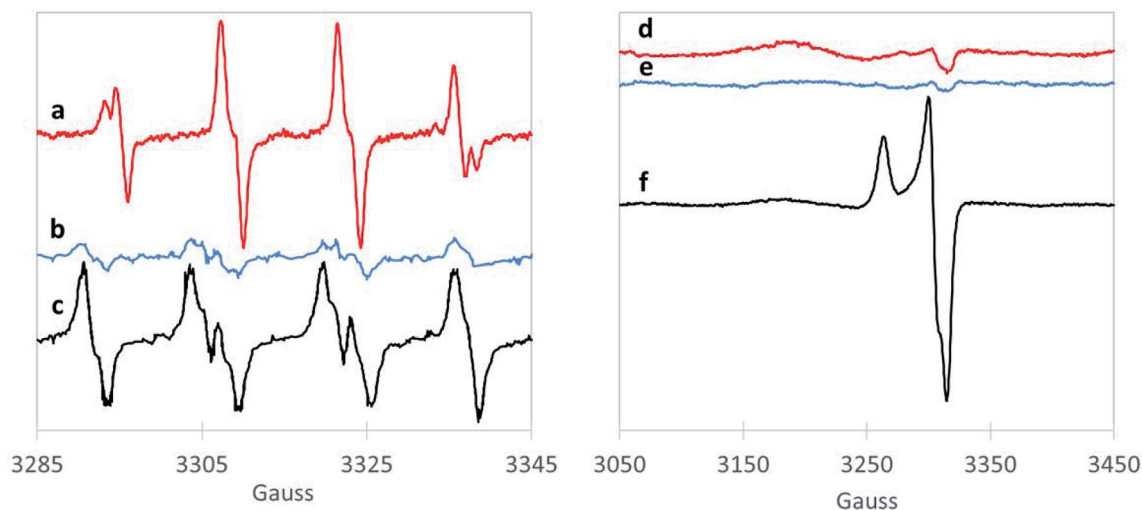


Fig. 2 BMPO-trapping of radical species in the H_2O_2 consumption with (a) CuO (red), (b) ZrO_2 (blue) and (c) WO_x/ZrO_2 (black). Spectra following freeze trapping over (d) CuO (red), (e) ZrO_2 (blue) and (f) WO_x/ZrO_2 (black). The small features at 3320 G for traces (d) and (e) are artifacts from the EPR sample cavity.

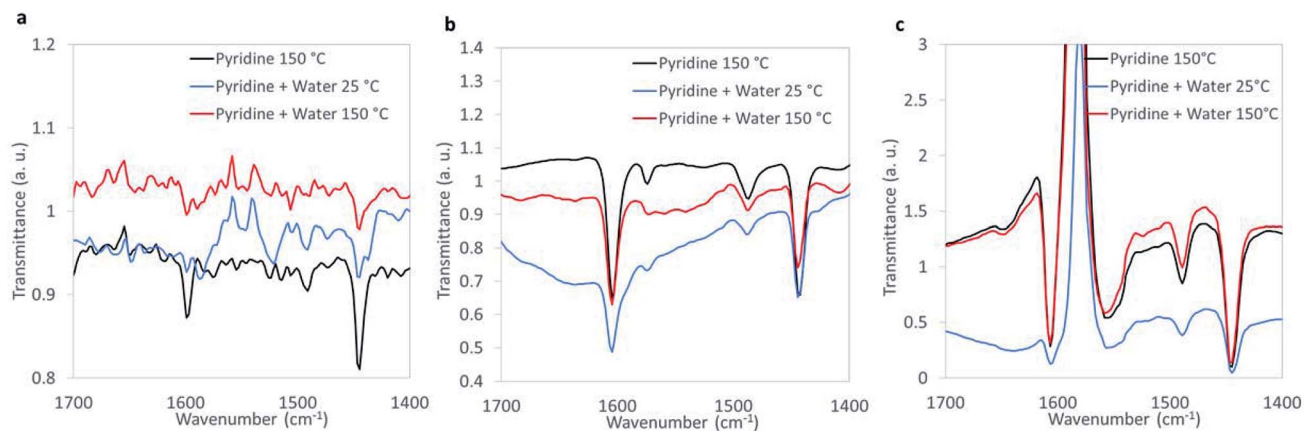


Fig. 3 FTIR spectra of chemisorbed pyridine under dehydrated and humid conditions for (a) CuO, (b) ZrO₂, and (c) WO_x/ZrO₂.

plateauing at high [H₂O₂]₀ for WO_x/ZrO₂, CuO, and ZrO₂, which was indicative of saturation coverage of the active sites at high H₂O₂ concentrations (Fig. S2a†). The 1,4-dioxane degradation rate ($r'_{1,4\text{-dioxane}}$), however, also increased and remained pseudo-first order with respect to [H₂O₂] (Fig. S2b†), which suggests that 1,4-dioxane adsorption (and subsequent reaction) sites are not blocked at high H₂O₂ concentrations, and implies that the adsorption and reaction occurs on sites different from those for H₂O₂ adsorption/reaction (for WO_x/ZrO₂, CuO, and ZrO₂).

We also examined the radicals formed from H₂O₂ activation by the 1,4-dioxane-active catalysts. Although EPR does not necessarily provide direct evidence of surface generation of radicals, it can reveal what radicals are generated in solution with the use of the spin-trap reagent. BMPO, the spin-trap reagent used here, rapidly reacts with otherwise transient radicals to form stable radical adducts with [•]OH and [•]O₂⁻ species. The hyperfine structures of the BMPO adduct are characteristic of those of BMPO/[•]OH (Fig. 2a), which fit well with two conformers with similar hyperfine splittings due to the nitrogen, the β hydrogen, and one of the γ hydrogen atoms,^{35,44}

indicating formation of [•]OH radical over CuO. The EPR signal did not change with the addition of superoxide dismutase (“SOD,” an enzyme which rapidly and selectively converts [•]O₂⁻ to O₂ or H₂O₂), confirming that CuO did not generate [•]O₂⁻ (Fig. S3†). This is in contrast to a recent study using ozone to degrade 1,4-dioxane over CuO, which formed primarily superoxide radical.²⁰ However, as hydroxyl radical is amongst the strongest oxidants (Table S4†), it is likely responsible for the high 1,4-dioxane degradation ability of CuO.

The spectra of BMPO-radical adducts were significantly different when ZrO₂ catalysts were exposed to H₂O₂ (Fig. 2b). The hyperfine structures of the EPR spectrum (Fig. 2b) indicates the formation of BMPO/[•]O₂⁻.³⁵ BMPO/[•]O₂⁻ adduct was also observed in the reaction of WO_x/ZrO₂ (Fig. 2c) and the spectrum fit well with two conformers with similar hyperfine splittings due to the nitrogen and the β hydrogen atoms (Fig. S4a and b†). Moreover, addition of SOD significantly decreased the amount of BMPO-trapped radical (Fig. S3†), corroborating that superoxide is the primary radical generated by ZrO₂ from H₂O₂. This observation is consistent with a previous work.⁴⁵

Superoxide radicals have a lower oxidation potential compared to H₂O₂^{46,47} (Table S3†), and are considered relatively unreactive.⁴⁸ It is surprising that this species (and not [•]OH) is generated by WO_x/ZrO₂, the most active catalyst tested for 1,4-dioxane degradation. This suggests some catalytically beneficial feature of ZrO₂-supported WO_x domains that is absent from ZrO₂ and from WO₃. Direct freeze-trapping EPR measurements, in which H₂O₂/metal oxide suspensions are frozen and analyzed for any generated radicals (without using a spin-trap reagent), showed signals for superoxide radicals for WO_x/ZrO₂ (Fig. 2f). The $g_{xy} = 2.007$ (3305 G) and $g_z = 2.088$ (broad peak centered at 3177 G) are typical of superoxide anion radicals in solution. The narrow peak at 3263 G ($g_z = 2.032$) and trough at 3315 G ($g_{xy} = 2.002$) are likely due to a WO_x/ZrO₂ surface-bound peroxy radical whose g values, particularly g_z , are perturbed due to its binding to the surface of the catalyst and much less spin-orbit coupling than that of free superoxide radical.⁴⁹ The EPR spectrum can be fit well with a combination of these two types of radicals (Fig. S4c†). No signals were detected in freeze-trapping of ZrO₂ and H₂O₂ even though [•]O₂⁻ was spin-trapped using


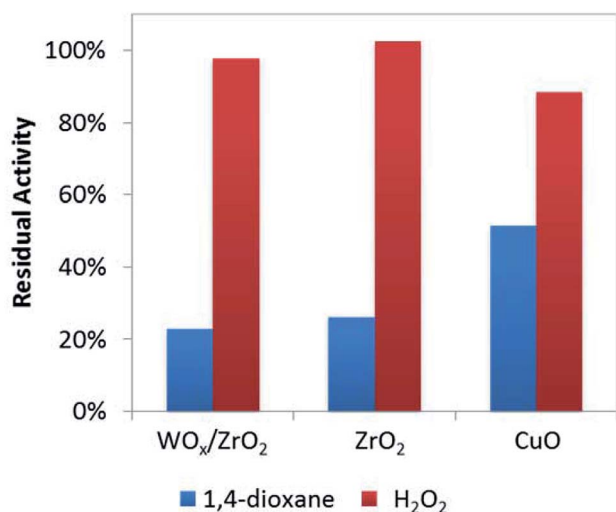


Fig. 4 Residual activity of catalysts for 1,4-dioxane and H₂O₂ degradation with the addition of 0.125 moles acetonitrile per mole surface site (186 μM acetonitrile).

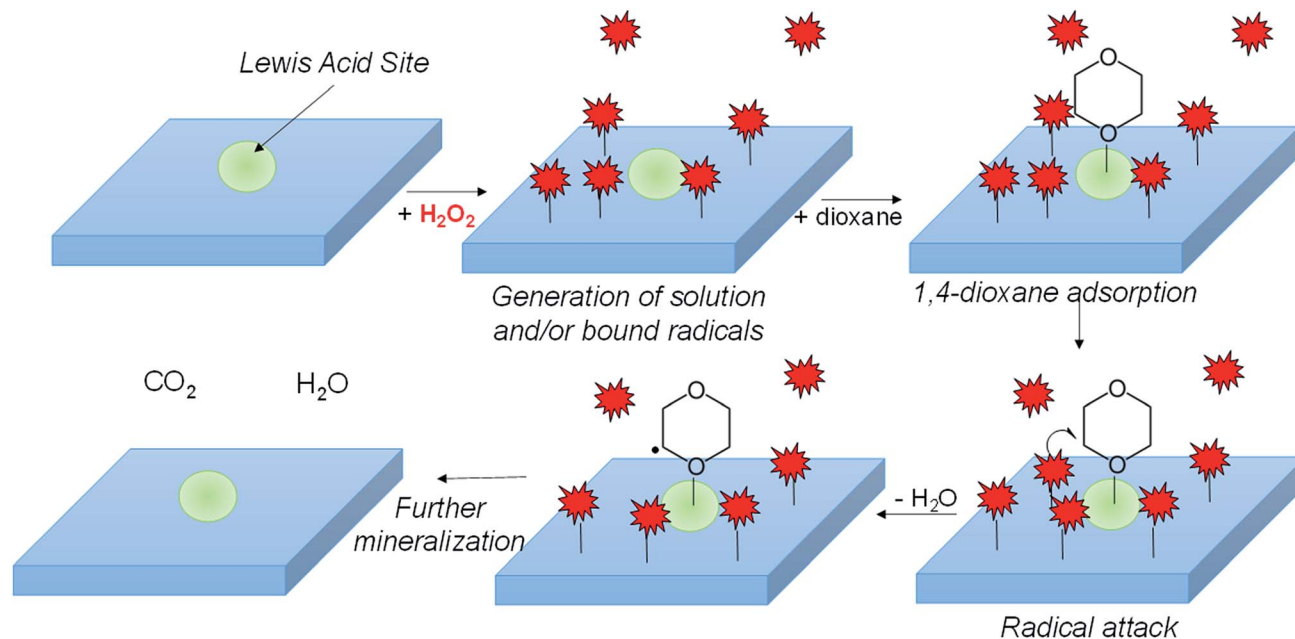

Scheme 1 Hypothesized general mechanism of 1,4-dioxane degradation over Lewis-acidic catalyst surfaces. 1,4-dioxane adsorbed to Lewis acid sites reacts with radicals generated from activation of H_2O_2 on surface.

BMPO in the same reaction, suggesting that WO_x/ZrO_2 can better stabilize $\cdot\text{O}_2^-$ radicals compared to ZrO_2 . In the CuO reaction with H_2O_2 , the formation of $\cdot\text{OH}$ was too transient to be directly freeze-trapped.

Recognizing that 1,4-dioxane was historically used as a CVOC stabilizer due to its ability to complex with AlCl_3 formed from CVOC storage inside aluminum-lined containers,^{50,51} we hypothesized that Lewis acid sites of the metal oxides are important for 1,4-dioxane degradation. We performed FTIR analysis of 1,4-dioxane-active materials using pyridine as probe molecule for surface acid sites under dry as well as humid conditions to simulate the aqueous-phase conditions of the oxidation reaction.

Characteristic peaks at $\sim 1445\text{ cm}^{-1}$ assigned to pyridine adsorbed on Lewis acid sites were observed on WO_x/ZrO_2 , ZrO_2 , and CuO (Fig. 3). The concentration of Lewis acid sites was quantified by integrating the area of the 1445 cm^{-1} peak, then normalizing by the amount of catalytic material and using an extinction coefficient previously determined by Emeis³⁸ (Table S5†). The metal oxides had similar Lewis acid site densities, which were lower than the theoretical metal site density of ~ 4 atoms per nm^{-2} (roughly 15–20%).^{52–54}

To help verify these Lewis acid sites participate in 1,4-dioxane oxidation catalysis, we co-added acetonitrile to the batch reactor tests (at amount equivalent to $\sim 12.5\%$ of theoretical metal site density, Fig. 4) and quantified the resulting rate constants. As a water-soluble Lewis base (less basic but easier to handle compared to pyridine), acetonitrile lowered 1,4-dioxane degradation substantially (by $\sim 75\text{--}80\%$) over ZrO_2 and WO_x/ZrO_2 , but did not affect H_2O_2 consumption much (by $<5\%$) (Fig. 4). The Lewis acid sites of ZrO_2 and WO_x/ZrO_2 are the likely adsorption sites for 1,4-dioxane (as poisoned by acetonitrile). Acetonitrile inhibited 1,4-dioxane degradation over CuO to

a lesser extent ($\sim 48\%$) and H_2O_2 consumption to a greater extent ($\sim 13\%$).

Humidification, which more closely resembles the aqueous reaction conditions, was introduced during FTIR analysis (Fig. 3). The introduction of water led to the appearance of Brønsted peaks (identified by characteristic pyridine IR peak at $\sim 1550\text{ cm}^{-1}$) on CuO but not ZrO_2 or WO_x/ZrO_2 . We suggest that CuO , when in water, contains Brønsted acid sites that may contribute 1,4-dioxane degradation, and that Brønsted acidity may not be an important characteristic for ZrO_2 or WO_x/ZrO_2 catalysis.

In combining the kinetic, EPR, FTIR, and surface poisoning results, we propose H_2O_2 dissociates onto metal surface sites into either surface adsorbed $\cdot\text{OH}$ or $\cdot\text{O}_2^-$ over the metal oxide surface, while Lewis-acidic sites (a minority of total sites) adsorb 1,4-dioxane (Scheme 1). The adsorbed radicals, or peroxy radicals, react with adsorbed 1,4-dioxane, which contributes to more efficient use of H_2O_2 and to higher 1,4-dioxane degradation activity.

5. Conclusions

In this work, we surveyed a number of H_2O_2 -active metal oxide materials, and evaluated their efficacy for the aqueous catalytic degradation of 1,4-dioxane at mild conditions (ambient temperature, neutral pH, in the dark). Of the materials screened, we found that WO_x/ZrO_2 had the highest 1,4-dioxane degradation rate, followed by CuO and ZrO_2 . A LHHW analysis indicated that H_2O_2 and 1,4-dioxane adsorb to distinct catalytic sites. EPR measurements indicate that CuO activates H_2O_2 into highly reactive hydroxyl radicals, while ZrO_2 and WO_x/ZrO_2 form solely less-active superoxide radicals. Pyridine-FTIR and selective poisoning experiments imply that 1,4-dioxane, a weak

Lewis base, selectively adsorbs to Lewis acid sites on the catalysts. We present a possible surface-reaction mechanism in which 1,4-dioxane adsorbs to catalyst sites and reacts with metal-oxide supported radical species. These materials show promise for treatment of 1,4-dioxane contaminated waters.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This study was supported by the Strategic Environmental Research and Development Program (SERDP) award ER-2307 and NIH NS094535 (A.-L. T.). Additional support for the collaboration came from the CAS/SAFEA International Partnership Program for Creative Research Teams. We thank C. Newell of GSI Environmental, D. Bryant of Geocleanse Intl., and S. Mahendra, M. Myers, and P. Gedalanga of UCLA for helpful discussions. K. N. H. did the kinetic studies and BET analysis, and Y. W. and F. W. did the FTIR analyses. EPR analyses were conducted by G. W. and A. T. All authors contributed toward the manuscript.

References

- 1 T. K. Mohr, *1,4-Dioxane and other Solvent Stabilizers*, San Jose, CA, June 14, 2001.
- 2 D. T. Adamson, S. Mahendra, K. L. Walker, S. R. Rauch, S. Sengupta and C. J. Newell, A Multisite Survey To Identify the Scale of the 1,4-Dioxane Problem at Contaminated Groundwater Sites, *Environ. Sci. Technol. Lett.*, 2014, **1**, 254–258.
- 3 R. H. Anderson, J. K. Anderson and P. A. Bower, Co-occurrence of 1,4-dioxane with trichloroethylene in chlorinated solvent groundwater plumes at US Air Force installations: Fact or fiction, *Integr. Environ. Assess. Manage.*, 2012, **8**, 731.
- 4 M. J. Zenker, R. C. Borden and M. A. Barlaz, Occurrence and treatment of 1,4-dioxane in aqueous environments, *Environ. Eng. Sci.*, 2003, **20**, 423.
- 5 T. Mohr, J. Stickney and W. Diguseppi, Environmental investigation and remediation: 1, 4-dioxane and other solvent stabilizers, *Environmental investigation and remediation: 1, 4-dioxane and other solvent stabilizers*, 2010.
- 6 T. Sale, C. Newell, H. Stroo, R. Hinchee and P. Johnson, *Regarding Management of Chlorinated Solvents in Soils and Groundwater*, 2008.
- 7 M. Otto and S. Nagaraja, Treatment technologies for 1,4-dioxane: Fundamentals and field applications, *Remediat. J.*, 2007, **17**, 81.
- 8 S. W. Lam, M. Hermawan, H. M. Coleman, K. Fisher and R. Amal, The role of copper(II) ions in the photocatalytic oxidation of 1,4-dioxane, *J. Mol. Catal. A: Chem.*, 2007, **278**, 152–159.
- 9 T. Vescovi, H. M. Coleman and R. Amal, The effect of pH on UV-based advanced oxidation technologies – 1,4-Dioxane degradation, *J. Hazard. Mater.*, 2010, **182**, 75–79.
- 10 H. Barndök, D. Hermosilla, C. Han, D. D. Dionysiou, C. Negro and Á. Blanco, Degradation of 1,4-dioxane from industrial wastewater by solar photocatalysis using immobilized NF-TiO₂ composite with monodisperse TiO₂ nanoparticles, *Appl. Catal., B*, 2016, **180**, 44–52.
- 11 A. Nakajima, M. Tanaka, Y. Kameshima and K. Okada, Sonophotocatalytic destruction of 1,4-dioxane in aqueous systems by HF-treated TiO₂ powder, *J. Photochem. Photobiol., A*, 2004, **167**, 75–79.
- 12 H.-S. Son, J.-K. Im and K.-D. Zoh, A Fenton-like degradation mechanism for 1,4-dioxane using zero-valent iron (Fe⁰) and UV light, *Water Res.*, 2009, **43**, 1457–1463.
- 13 H. Barndök, L. Blanco, D. Hermosilla and Á. Blanco, Heterogeneous photo-Fenton processes using zero valent iron microspheres for the treatment of wastewaters contaminated with 1,4-dioxane, *Chem. Eng. J.*, 2016, **284**, 112–121.
- 14 M. A. Beckett and I. Hua, Enhanced sonochemical decomposition of 1,4-dioxane by ferrous iron, *Water Res.*, 2003, **37**, 2372–2376.
- 15 J. R. Jasmann, T. Borch, T. C. Sale and J. Blotevogel, Advanced Electrochemical Oxidation of 1,4-Dioxane via Dark Catalysis by Novel Titanium Dioxide (TiO₂) Pellets, *Environ. Sci. Technol.*, 2016, **50**, 8817–8826.
- 16 J. De Clercq, E. Van de Steene, K. Verbeken and M. Verhaege, Electrochemical oxidation of 1, 4-dioxane at boron-doped diamond electrode, *J. Chem. Technol. Biotechnol.*, 2010, **85**, 1162–1167.
- 17 J. Y. Choi, Y.-J. Lee, J. Shin and J.-W. Yang, Anodic oxidation of 1, 4-dioxane on boron-doped diamond electrodes for wastewater treatment, *J. Hazard. Mater.*, 2010, **179**, 762–768.
- 18 A. D. Bokare and W. Choi, Review of iron-free Fenton-like systems for activating H₂O₂ in advanced oxidation processes, *J. Hazard. Mater.*, 2014, **275**, 121–135.
- 19 S. Wu, H. He, X. Li, C. Yang, G. Zeng, B. Wu, S. He and L. Lu, Insights into atrazine degradation by persulfate activation using composite of nanoscale zero-valent iron and graphene: Performances and mechanisms, *Chem. Eng. J.*, 2018, **341**, 126–136.
- 20 A. Basso, R. Landers, P. J. J. Alvarez, G. L. Puma and R. F. P. M. Moreira, Treatment of aqueous solutions of 1,4-dioxane by ozonation and catalytic ozonation with copper oxide (CuO) AU – Scaratti, Gidiane, *Environ. Technol.*, 2018, 1–13.
- 21 Y. Feng, P.-H. Lee, D. Wu and K. Shih, Surface-bound sulfate radical-dominated degradation of 1,4-dioxane by alumina-supported palladium (Pd/Al₂O₃) catalyzed peroxymonosulfate, *Water Res.*, 2017, **120**, 12–21.
- 22 W. Fan, Y. Kubota and T. Tatsumi, Oxidation of 1,4-Dioxane over Ti-MWW in the Presence of H₂O₂, *ChemSusChem*, 2008, **1**, 175–178.
- 23 Q. Zeng, H. Dong, X. Wang, T. Yu and W. Cui, Degradation of 1, 4-dioxane by hydroxyl radicals produced from clay minerals, *J. Hazard. Mater.*, 2017, **331**, 88–98.
- 24 C. M. Lousada and M. Jonsson, Kinetics, Mechanism, and Activation Energy of H₂O₂ Decomposition on the Surface of ZrO₂, *J. Phys. Chem. C*, 2010, **114**, 11202–11208.

- 25 A. Hiroki and J. A. LaVerne, Decomposition of Hydrogen Peroxide at Water–Ceramic Oxide Interfaces, *J. Phys. Chem. B*, 2005, **109**, 3364–3370.
- 26 J. W. Harris, M. J. Cordon, J. R. Di Iorio, J. C. Vega-Vila, F. H. Ribeiro and R. Gounder, Titration and quantification of open and closed Lewis acid sites in Sn-Beta zeolites that catalyze glucose isomerization, *J. Catal.*, 2016, **335**, 141–154.
- 27 I. E. Wachs, C. R. Brundle and J. C. A. Evans, *Characterization of Catalytic Materials*, 2009.
- 28 C. N. Satterfield and A. H. Bonnell, Interferences in Titanium Sulfate Method for Hydrogen Peroxide, *Anal. Chem.*, 1955, **27**, 1174–1175.
- 29 M. Li, P. Conlon, S. Fiorenza, R. J. Vitale and P. J. J. Alvarez, Rapid Analysis of 1,4-Dioxane in Groundwater by Frozen Micro-Extraction with Gas Chromatography/Mass Spectrometry, *Groundwater Monit. Rem.*, 2011, **31**, 70–76.
- 30 Y.-L. Fang, K. N. Heck, P. J. J. Alvarez and M. S. Wong, Kinetics Analysis of Palladium/Gold Nanoparticles as Colloidal Hydrodechlorination Catalysts, *ACS Catal.*, 2011, **1**, 128–138.
- 31 H. Qian, Z. Zhao, J. C. Velazquez, L. A. Pretzer, K. N. Heck and M. S. Wong, Supporting palladium metal on gold nanoparticles improves its catalysis for nitrite reduction, *Nanoscale*, 2014, **6**, 358–364.
- 32 P. B. Weisz and C. D. Prater, Interpretation of Measurements in Experimental Catalysis, in *Advances in Catalysis*, ed. W. G. Frankenburg, V. I. Komarewsky and E. K. Rideal, Academic Press, 1954, vol. 6, pp. 143–196.
- 33 N. Soultanidis, W. Zhou, A. C. Psarras, A. J. Gonzalez, E. F. Iliopoulou, C. J. Kiely, I. E. Wachs and M. S. Wong, Relating *n*-Pentane Isomerization Activity to the Tungsten Surface Density of WO_x/ZrO_2 , *J. Am. Chem. Soc.*, 2010, **132**, 13462–13471.
- 34 B. Gopalakrishnan, K. M. Nash, M. Velayutham and F. A. Villamena, Detection of nitric oxide and superoxide radical anion by electron paramagnetic resonance spectroscopy from cells using spin traps, *J. Visualized Exp.*, 2012, e2810.
- 35 H. Zhao, J. Joseph, H. Zhang, H. Karoui and B. Kalyanaraman, Synthesis and biochemical applications of a solid cyclic nitron spin trap: a relatively superior trap for detecting superoxide anions and glutathyl radicals, *Free Radical Biol. Med.*, 2001, **31**, 599–606.
- 36 H. Shi, G. Timmins, M. Monske, A. Burdick, B. Kalyanaraman, Y. Liu, J.-L. Clément, S. Burchiel and K. J. Liu, Evaluation of spin trapping agents and trapping conditions for detection of cell-generated reactive oxygen species, *Arch. Biochem. Biophys.*, 2005, **437**, 59–68.
- 37 D. Liu, Z. Xiu, F. Liu, G. Wu, D. Adamson, C. Newell, P. Vikesland, A.-L. Tsai and P. J. Alvarez, Perfluorooctanoic acid degradation in the presence of Fe(III) under natural sunlight, *J. Hazard. Mater.*, 2013, **262**, 456–463.
- 38 C. A. Emeis, Determination of Integrated Molar Extinction Coefficients for Infrared Absorption Bands of Pyridine Adsorbed on Solid Acid Catalysts, *J. Catal.*, 1993, **141**, 347–354.
- 39 C. M. Lousada, M. Yang, K. Nilsson and M. Jonsson, Catalytic decomposition of hydrogen peroxide on transition metal and lanthanide oxides, *J. Mol. Catal. A: Chem.*, 2013, **379**, 178–184.
- 40 C. M. Lousada, A. J. Johansson, T. Brinck and M. Jonsson, Mechanism of H_2O_2 Decomposition on Transition Metal Oxide Surfaces, *J. Phys. Chem. C*, 2012, **116**, 9533–9543.
- 41 C. M. Lousada, A. J. Johansson, T. Brinck and M. Jonsson, Reactivity of metal oxide clusters with hydrogen peroxide and water – a DFT study evaluating the performance of different exchange-correlation functionals, *Phys. Chem. Chem. Phys.*, 2013, **15**, 5539–5552.
- 42 A. L.-T. Pham, F. M. Doyle and D. L. Sedlak, Kinetics and efficiency of H_2O_2 activation by iron-containing minerals and aquifer materials, *Water Res.*, 2012, **46**, 6454–6462.
- 43 A. L.-T. Pham, C. Lee, F. M. Doyle and D. L. Sedlak, A Silica-Supported Iron Oxide Catalyst Capable of Activating Hydrogen Peroxide at Neutral pH Values, *Environ. Sci. Technol.*, 2009, **43**, 8930–8935.
- 44 P. Baldrian, V. Merhautová, J. Gabriel, F. Nerud, P. Stopka, M. Hrubý and M. J. Beneš, Decolorization of synthetic dyes by hydrogen peroxide with heterogeneous catalysis by mixed iron oxides, *Appl. Catal., B*, 2006, **66**, 258–264.
- 45 E. Giamello, P. Rumori, F. Geobaldo, B. Fubini and M. Paganini, The interaction between hydrogen peroxide and metal oxides: EPR investigations, *Appl. Magn. Reson.*, 1996, **10**, 173–192.
- 46 J. O. M. Bockris and L. F. Oldfield, The oxidation-reduction reactions of hydrogen peroxide at inert metal electrodes and mercury cathodes, *Trans. Faraday Soc.*, 1955, **51**, 249–259.
- 47 G. R. Buettner, The Pecking Order of Free Radicals and Antioxidants: Lipid Peroxidation, α -Tocopherol, and Ascorbate, *Arch. Biochem. Biophys.*, 1993, **300**, 535–543.
- 48 J. Nordberg and E. S. J. Arnér, Reactive oxygen species, antioxidants, and the mammalian thioredoxin system1, *Free Radical Biol. Med.*, 2001, **31**, 1287–1312.
- 49 D. M. Murphy and E. Giamello, EPR of Paramagnetic Centres on Solid Surfaces, *Electron Paramagn. Reson.*, 2002, **18**, 183–221.
- 50 W. L. Archer, A laboratory evaluation of 1,1,1-Trichloroethane-Metal-Inhibitor systems, *Mater. Corros.*, 1984, **35**, 60–69.
- 51 W. L. Archer, Aluminum-1, 1, 1-trichloroethane. Reactions and inhibition, *Ind. Eng. Chem. Prod. Res. Dev.*, 1982, **21**, 670–672.
- 52 T. Kim, A. Burrows, C. J. Kiely and I. E. Wachs, Molecular/electronic structure–surface acidity relationships of model-supported tungsten oxide catalysts, *J. Catal.*, 2007, **246**, 370–381.
- 53 I. E. Wachs, Raman and IR studies of surface metal oxide species on oxide supports: Supported metal oxide catalysts, *Catal. Today*, 1996, **27**, 437–455.
- 54 W. V. Knowles, M. O. Nutt and M. S. Wong, Supported metal oxides and the surface density metric, in *Handbook of Catalyst Synthesis: The Science and Engineering of Catalyst Preparation*, ed. Regalbuto J. R., Taylor & Francis, Boca Raton, FL, 2007, pp. 251–281.