

SCIENTIFIC REPORTS



OPEN

Co₃O₄ nanoparticles anchored on nitrogen-doped reduced graphene oxide as a multifunctional catalyst for H₂O₂ reduction, oxygen reduction and evolution reaction

Received: 30 September 2016

Accepted: 26 January 2017

Published: 08 March 2017

Tingting Zhang, Chuansheng He, Fengzhan Sun, Yongqi Ding, Manchao Wang, Lin Peng, Jiahui Wang & Yuqing Lin

This study describes a facile and effective route to synthesize hybrid material consisting of Co₃O₄ nanoparticles anchored on nitrogen-doped reduced graphene oxide (Co₃O₄/N-rGO) as a high-performance tri-functional catalyst for oxygen reduction reaction (ORR), oxygen evolution reaction (OER) and H₂O₂ sensing. Electrocatalytic activity of Co₃O₄/N-rGO to hydrogen peroxide reduction was tested by cyclic voltammetry (CV), linear sweep voltammetry (LSV) and chronoamperometry. Under a reduction potential at -0.6V to H₂O₂, this constructing H₂O₂ sensor exhibits a linear response ranging from 0.2 to 17.5 mM with a detection limit to be 0.1 mM. Although Co₃O₄/rGO or nitrogen-doped reduced graphene oxide (N-rGO) alone has little catalytic activity, the Co₃O₄/N-rGO exhibits high ORR activity. The Co₃O₄/N-rGO hybrid demonstrates satisfied catalytic activity with ORR peak potential to be -0.26V (vs. Ag/AgCl) and the number of electron transfer number is 3.4, but superior stability to Pt/C in alkaline solutions. The same hybrid is also highly active for OER with the onset potential, current density and Tafel slope to be better than Pt/C. The unusual catalytic activity of Co₃O₄/N-rGO for hydrogen peroxide reduction, ORR and OER may be ascribed to synergetic chemical coupling effects between Co₃O₄, nitrogen and graphene.

With the transition from traditional fossil fuels to clean and sustainable energy, lots of attentions have been paid on storage systems with environmental benignity, high efficiency and alternative energy conversion. Fuel cells have been considered as the most efficient and clean energy conversion device because fuels react with oxygen via mild electrochemical processes without combustion and the overall fuel-conversion efficiency is not limited by the Carnot cycle laws^{1,2}. Designing bifunctional catalysts with good oxygen reduction reaction (ORR) and oxygen evolution reaction (OER) activities would be highly beneficial to the development of metal-air batteries. However, developing catalysts for ORR and OER with high activity at low cost remain great challenges^{3,4}. Platinum-based materials are known to be the most active electrocatalysts for the ORR and the OER. However, the limited reserves of Pt, high cost, the activity deterioration with time and poor durability severely hinder the large-scale applications of Pt in ORR and OER⁵⁻⁸.

On the other hand, the determination of hydrogen peroxide (H₂O₂) has aroused more and more interests of researchers as its significance in the fields of applications in industry as well as biological reactions. Therefore, a rapid, accurate and reliable method to detect H₂O₂ is of highly demanded. Among various techniques for H₂O₂ detection, electrochemical H₂O₂ electrocatalysts are promising due to their high sensitivity, low cost, good selectivity, easy for automation and operational simplicity⁹⁻¹². Catalysts for hydrogen peroxide reduction, oxygen reduction and oxygen evolution reactions are vital in biological assay and renewable-energy technologies including fuel cells and water splitting.

Recently, transition metal oxides including manganese oxide, cobalt oxide, iron oxide and nickel oxide as promising materials have received considerable attention due to their low cost, high abundance and perfect

Department of Chemistry, Capital Normal University, Beijing, 100048, China. Correspondence and requests for materials should be addressed to Y.L. (email: linyuqing@cnu.edu.cn)

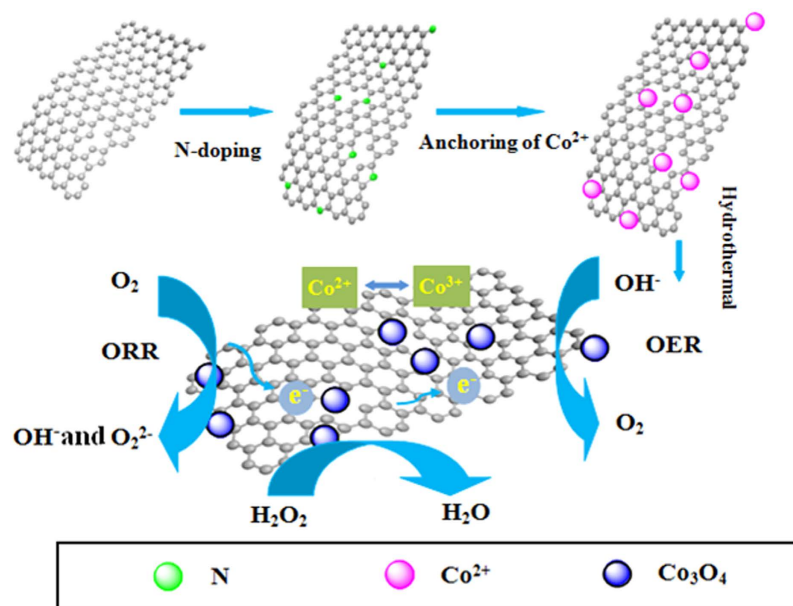


Figure 1. Schematic illustration of the synthesis of $\text{Co}_3\text{O}_4/\text{N-rGO}$.

catalytic activity for the ORR, OER and immobilizing enzymes for further applications in fabrication of hydrogen peroxide biosensor^{13–15}. Among them, Co_3O_4 with spinel crystal structure is beneficial to electron transportation between Co^{2+} and Co^{3+} ions, which has been extensively considered as an efficient electrocatalyst for OER and ORR^{16–18}. Previous studies reported that the efficiency of cobalt oxide as an OER catalyst could be ascribed to the increasing population of Co^{IV} centers at the oxide surface during electrochemical oxidation¹⁹. More interesting, Co_3O_4 , which exhibits catalase-like activity for the decomposition of H_2O_2 , can be applied to the detection of H_2O_2 in aqueous medium²⁰. However, these Co_3O_4 -based catalysts usually suffer from the poor electrical conductivity, short active site density and the dissolution or agglomeration during electrochemical processes. Co_3O_4 itself is a material with a little ORR, OER and H_2O_2 sensing activity and further studies exhibit that synergy between the carbon materials and Co_3O_4 can give a huge promotion of the electrocatalytic activity^{21,22}. Therefore, lots of researches have used conductive carbon nanomaterials such as carbon nanotubes (CNTs), carbon foam and graphene etc. To improve the conductivity of Co_3O_4 based hybrid catalysts as well as obtain uniformly dispersed Co_3O_4 nanoparticles and thus to improve the electrocatalyst activity.

Graphene, a two-dimensional layer framework of sp^2 -hybridized carbon with outstanding chemical and physical properties, has attracted a lot of attention in the last years^{21,23,24}. Graphene could be an attractive support for metal oxides to form a new class of nanocomposites for ORR due to their notable electronic conductivity and high surface area^{25,26}. Dai's group reported a hybrid material consisting of Co_3O_4 nanocrystals grown on reduced graphene oxide as a high-performance bi-functional catalyst for the ORR and OER²⁷. Wang etc. synthesized a novel multifunctional nano hybrid by chemically coupling ultrafine metal oxide nanoparticles to reduced graphene oxide (rGO) as an effective catalyst for oxygen reduction reaction²⁸. Anchoring Co_3O_4 nanocrystals on carbon-based supports could significantly improve their electrocatalytic activity contributed by the small crystalline size and conductive support²⁹. What's more, chemical doping with hetero atoms is an efficacious method to regulate electronic properties and surface chemistry of assembled graphene by the modulation of the carbon-carbon bonds^{30,31}. It has been also reported that nitrogen-doped graphene can promote the electrochemical reduction of H_2O_2 ³². As previous study, the introduction of the Co-N_4 complex onto the graphene basal plane facilitates the activation of O_2 dissociation and the desorption of H_2O during the ORR³³. Nitrogen-graphene can produce the synergistic support effect because the reactive intermediates such as hydrogen peroxide are known to decomposed by nitrogen doped carbon nanostructures. However, so far, few researches have reported catalyst which has three functions for H_2O_2 reduction, ORR and OER.

We report herein the synthesis of Co_3O_4 nanoparticles anchored on nitrogen-doped reduced graphene oxide ($\text{Co}_3\text{O}_4/\text{N-rGO}$) through a simple and scalable method as tri-functional catalysts for H_2O_2 reduction, ORR and the OER, as shown in Fig. 1. Co_3O_4 anchored uniformly into laminar nitrogen-doped reduced graphene oxide was confirmed by scanning electron microscopy (SEM). $\text{Co}_3\text{O}_4/\text{N-rGO}$ possesses a good electrocatalytic activity toward H_2O_2 reduction by enhancing the current response and decreasing H_2O_2 reduction over potential. The electrochemical results demonstrate that the $\text{Co}_3\text{O}_4/\text{N-rGO}$ can exhibit higher activity for both the ORR and the OER and better durability than a commercial carbon-supported Pt catalyst. The strong coupling between Co_3O_4 , nitrogen and reduced graphene oxide (rGO) is found to play an important role in the high electrocatalytic activities of the $\text{Co}_3\text{O}_4/\text{N-rGO}$. This synthesis route can be easily adopted for large-scale manufacturing due to its process simplicity and the accessibility of precursor materials.

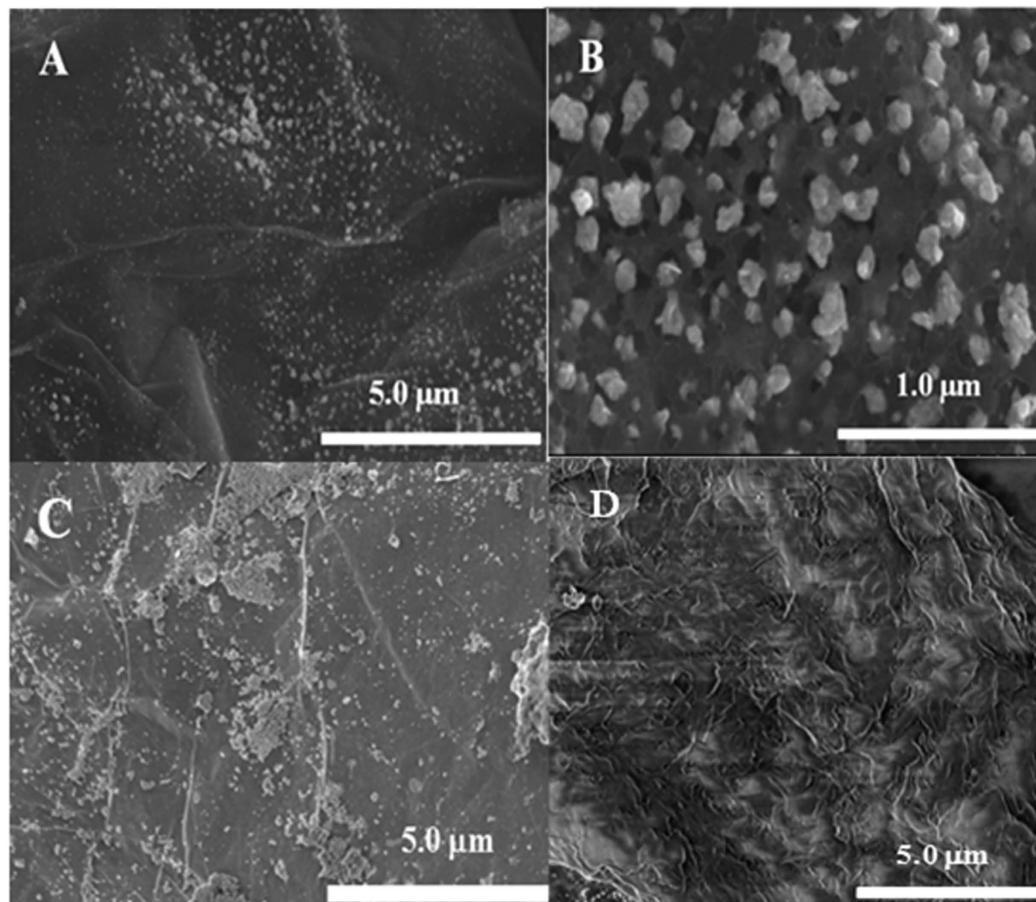


Figure 2. Scanning electron microscopy image of $\text{Co}_3\text{O}_4/\text{N-rGO}$ (A,B), $\text{Co}_3\text{O}_4/\text{rGO}$ (C) and N-rGO (D), respectively.

Results and Discussion

Characterization. Figure 2A and B illustrated field emission scanning electron microscopy (FE-SEM) images of $\text{Co}_3\text{O}_4/\text{N-rGO}$. We can clearly see from SEM images in Fig. 2B that Co_3O_4 nanoparticles are uniformly anchored on the rGO substrate with an approximate average diameter of 150 nm. This may be attributed that Co^{2+} ion was coordinated with negatively charged oxygen-containing functional groups on N-rGO sheets. During the hydrothermal process, Co^{2+} was oxidized into Co^{3+} by oxygen-containing groups, and crystallized to form Co_3O_4 nanoparticles anchored into N-rGO sheets³⁴. However, Fig. 2C demonstrate $\text{Co}_3\text{O}_4/\text{rGO}$ does not exhibit such a uniform morphology distribution of Co_3O_4 . In addition, we only found that a typical corrugated structure in Fig. 2D, suggesting there is no Co_3O_4 particles nucleate on N-rGO surface. The oxygen-containing functional groups of rGO were beneficial for the nucleation and anchoring of nanocrystals on the sheets to achieve covalent attachments, which help to shape the uniform formation of Co_3O_4 ^{35,36}. In addition, these uniform structures of Co_3O_4 particles anchored into N-rGO can also be ascribed to NH_3 together with oxygen-containing functional group coordinating with cobalt cations and thus reducing Co_3O_4 particles size and enhancing particles nucleation on N-rGO³⁷. XRD was performed to investigate the phase structure of $\text{Co}_3\text{O}_4/\text{N-rGO}$. As shown in Fig. 3A, the diffraction peaks of the pristine Co_3O_4 was consistent with the standard Co_3O_4 (JCPDS card: 42-1467).

The major diffraction peaks of $\text{Co}_3\text{O}_4/\text{N-rGO}$ were well in agreement with those of Co_3O_4 except for the broad (002) peak at approximately 25° , which can be ascribed to disordered stacked graphitic sheets³⁰. This manifest that the original GO has been reduced to rGO during the hydrothermal process, again confirming we have successfully incorporated Co_3O_4 into rGO³⁸. BET experiments was conducted to obtain specific surface area of as-prepared samples and the isotherms exhibit typical IV isotherms where the recorded BET surface area of $\text{Co}_3\text{O}_4/\text{N-rGO}$, N-rGO and Co_3O_4 are $103.9 \text{ m}^2/\text{g}$, $139.7 \text{ m}^2/\text{g}$, and $62.8 \text{ m}^2/\text{g}$, respectively. These results indicate the change of N-rGO structure after doping with Co_3O_4 .

Raman spectroscopy was carried out to extend the study for the carbon structures in $\text{Co}_3\text{O}_4/\text{N-rGO}$, N-rGO and $\text{Co}_3\text{O}_4/\text{GO}$ hybrid which are shown in Fig. 3B, where the peaks of Raman spectrum of Co_3O_4 anchored on the N-rGO and $\text{Co}_3\text{O}_4/\text{GO}$ hybrid at 193 , 470 and 680 cm^{-1} , can be attributed to the Eg, F2g and A1g modes of Co_3O_4 ³⁹. It is noted that there are two remarkable peaks around 1339 and 1591 cm^{-1} refer to the D-band (arising from the edge or defect sites of carbon) and G band (representing the sp^2 carbon) of the graphene domain, respectively⁴⁰.

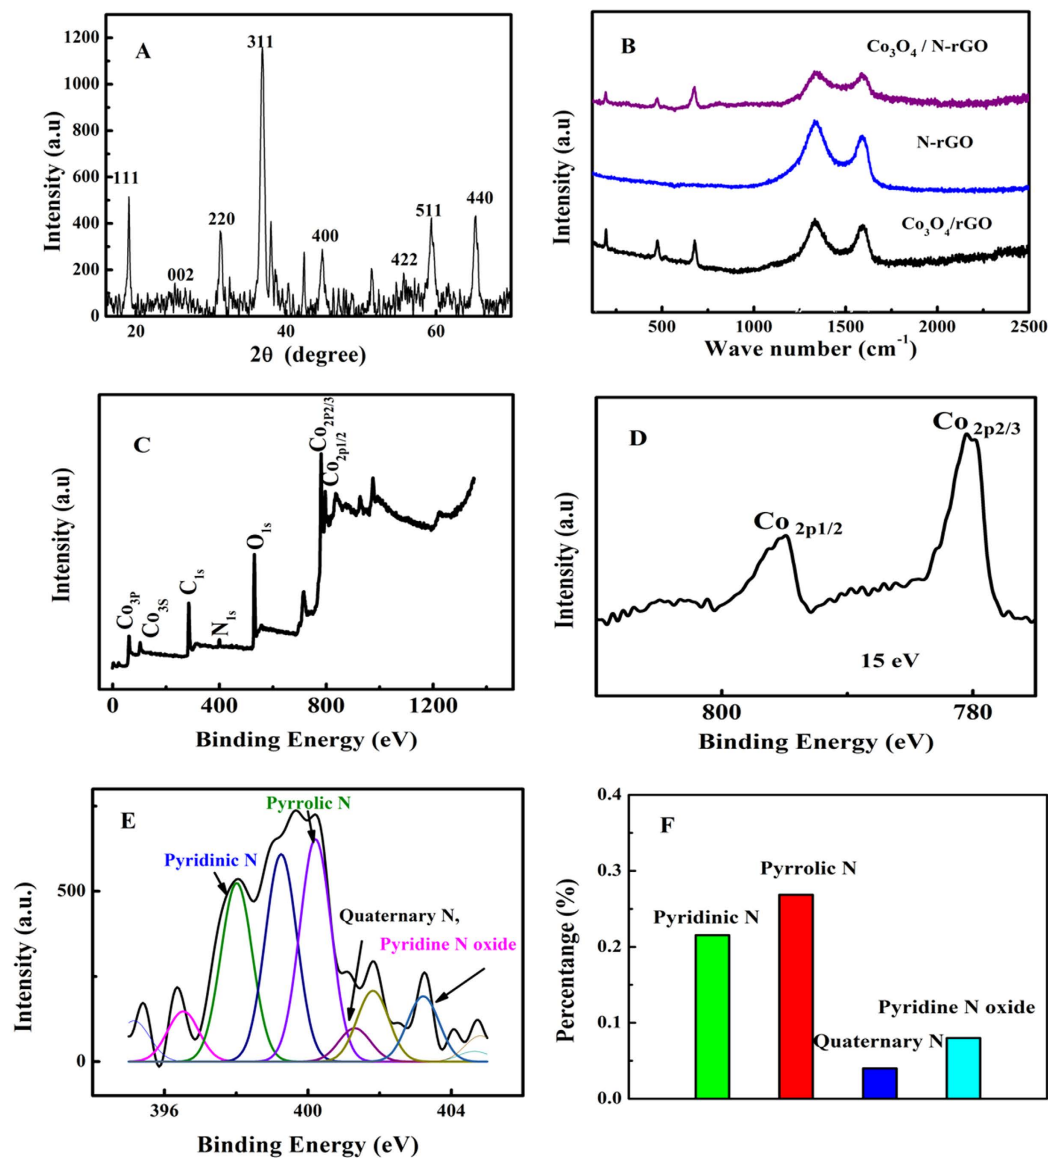


Figure 3. XRD spectrum of $\text{Co}_3\text{O}_4/\text{N-rGO}$ (A) and Raman spectra of $\text{Co}_3\text{O}_4/\text{N-rGO}$, N-rGO and $\text{Co}_3\text{O}_4/\text{rGO}$ (B); The XPS full spectrum of $\text{Co}_3\text{O}_4/\text{N-rGO}$ (C) and high resolution Co_{2p} spectra of $\text{Co}_3\text{O}_4/\text{N-rGO}$ (D); High-resolution N_{1s} XPS spectra of $\text{Co}_3\text{O}_4/\text{N-rGO}$ (E); The percentage of three nitrogen species in $\text{Co}_3\text{O}_4/\text{N-rGO}$ (E).

X-ray photoelectron spectroscopic (XPS) measurements were performed to determine the surface element constitution in $\text{Co}_3\text{O}_4/\text{N-rGO}$. The sharp peaks in Fig. 3C are corresponded to the characteristic peaks of C_{1s} , O_{1s} , N_{1s} and Co_{2p} , indicating the existence of carbon, oxygen, nitrogen and cobalt elements in the prepared sample. The XPS spectrum for Co_{2p} shown in Fig. 3D reveals two major peaks with binding energies at 780.1 and 795 eV, corresponding to $\text{Co}_{2p_{3/2}}$ and $\text{Co}_{2p_{1/2}}$, respectively, with a spin energy separation of 15 eV, which is attributed to the Co^{2+} oxidation state, indicating that a portion of Co^{3+} is reduced to Co^{2+} with generating oxygen vacancies¹⁷. These results again confirmed that Co_3O_4 nanoparticles have been anchored on N-rGO, Co^{2+} and Co^{3+} in the crystal structure of Co_3O_4 are being considered to be playing a vital role in improving catalytic performance of oxygen reduction reaction and oxygen evolution reaction³⁷. Furthermore, the main beautiful structure of Co_3O_4 is the peculiar cation distribution in the face centered cubic (FCC) crystal where the Co^{2+} ions reside on the $1/8^{\text{th}}$ of the tetrahedral A sites while the Co^{3+} ions occupy $1/2$ of the octahedral B sites¹¹, endow the system viable for electrocatalytic applications. The high-resolution N_{1s} XPS spectrum of $\text{Co}_3\text{O}_4/\text{N-rGO}$ was used primarily to determine the bonding configurations of N atoms in the composite, as seen in Fig. 3E. The peak deconvolution suggests four components were centered at about 398, 400, 401, and 403 eV, corresponding to pyridinic N, pyrrolic N, quaternary N, and oxidized N, respectively. N atom have the lone electron pairs which can hybridize with sp^2 carbon atoms to celebrate oxygen reduction reaction. The performance of ORR depends on the bonding configuration of N atoms in carbon materials. It has been reported that the onset potential of a nitrogen-doped

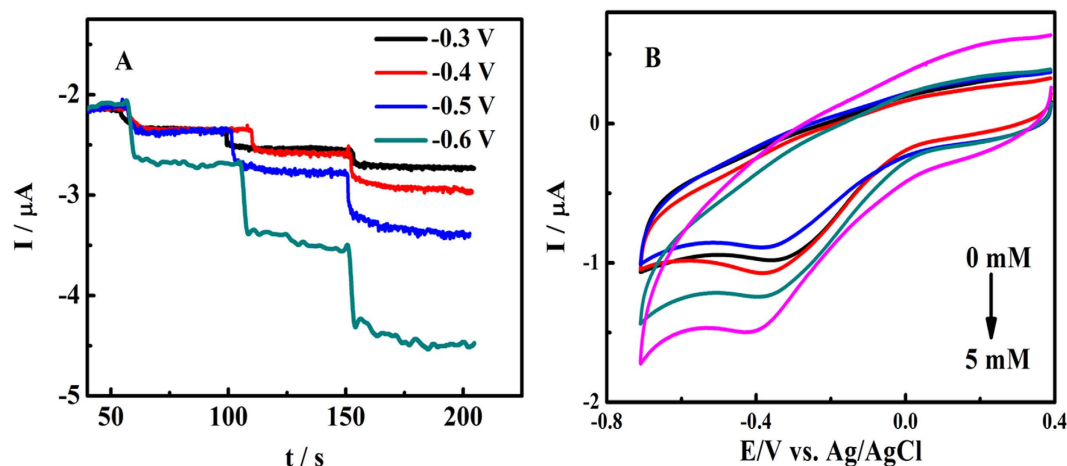


Figure 4. Cyclic voltammograms of (A) $\text{Co}_3\text{O}_4/\text{N-rGO}$, N-rGO and $\text{Co}_3\text{O}_4/\text{rGO}$ modified GC electrodes in 0.1 M PB solution (pH 7.0) containing 5 mM H_2O_2 and (B) $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode in 0.1 M PB solution (pH 7.0) containing different concentration of H_2O_2 (from the top: 0, 0.5, 1, 2 and 5 mM). Scan rate 50 mV s^{-1} .

catalyst has strong relation with pyridinic form nitrogen, but little effect by pyrrolic nitrogen and oxidized type nitrogen⁴¹.

Electrocatalytic activity of $\text{Co}_3\text{O}_4/\text{N-rGO}$ for H_2O_2 reduction. Though enzyme based electrochemical sensors have been widely developed to sensing H_2O_2 due to the advantages of high sensitivity and good selectivity, these sensors often suffer from unstable response due to the intrinsic nature of enzymes⁴². Therefore, it is necessary to develop a simple non-enzymatic strategy for sensing H_2O_2 with high sensitivity. To date, electrocatalysts for design H_2O_2 sensors with high sensitivity, good selectivity and easy regulation properties hold leading position among various sensors⁴². It has been proved that functional nano-structured transition-metal oxides exhibit good electrocatalytic activity toward the H_2O_2 reduction, which provides valuable strategy for the nonenzymatic determination of H_2O_2 ^{43,44}. Among various kinds of transition metal oxides, Co_3O_4 shows attracting electronic and electrocatalytic properties. Particularly, its normal spinel crystal structure is favorable for electron transportation between Co^{2+} and Co^{3+} ions and Co_3O_4 possess catalase-like activity, which is benefit to sensing H_2O_2 . Therefore, Co_3O_4 have been extensively explored as the sensing materials for developing enzyme-free H_2O_2 sensors. However, Co_3O_4 -based catalysts usually suffer from the poor electrical conductivity, low active site density and the dissolution or agglomeration during electrochemical processes^{45,46}. On the other hand, graphene has the ability to promote electron transfer rates and graphene-based modified electrode had much better electrocatalysis toward H_2O_2 ⁴⁷.

In our study, Co_3O_4 nanoparticles were incorporated into nitrogen doped graphene, leading to improved conductivity, enhanced catalytic activity and stability of the metal oxide nanocatalyst, and thus a better catalytic effect to H_2O_2 reduction due to the synergistic effect. To investigate the electrocatalytic characteristics to H_2O_2 reduction of $\text{Co}_3\text{O}_4/\text{N-rGO}$, voltammetric measurements were performed using the $\text{Co}_3\text{O}_4/\text{N-rGO}$, $\text{Co}_3\text{O}_4/\text{rGO}$ and N-rGO modified GC electrodes in the presence of 5 mM H_2O_2 at a scan rate of 0.05 V s^{-1} . Figure 4A exhibit that a distinct catalytic current peak at -0.40 V could be ascribed for $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode. Figure 4B reveals the CVs of $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC in the presence of different concentration of H_2O_2 in 0.1 M PB solution (pH 7.0) at the scan rate of 50 mV s^{-1} . It demonstrates that the reduction current gradually increases with the increase of H_2O_2 concentration (from the top: 0.5, 1, 2 and 5 mM), which manifest the $\text{Co}_3\text{O}_4/\text{N-rGO}$ material have improved electrocatalytic activity to H_2O_2 and pave a route for quantitative analysis.

It is a significant way for amperometric technique to test the sensing property of $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode. We studied the effect of the applied potential in order to improve the $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode performance towards non-enzymatic H_2O_2 sensing. We investigated applied potential on the amperometric response on the $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode towards sequential addition of 0.5 mM H_2O_2 by varying the potential between -0.6 V and -0.3 V . As shown in Fig. 5A and B, as amperometric response of the $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode has the optimal sensitivity, the applied potential at -0.6 V was selected. Figure 5A shows a typical current-time plot of the $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode on successive addition of H_2O_2 at an applied potential of -0.6 V . Catalytic currents showed linear response to H_2O_2 from 0.5 mM to 17.5 mM ($R^2 = 0.994$) with a detection limit ($S/N = 3$) to be 0.1 mM, which are comparable to or even better than those of the other metal-free or enzyme based H_2O_2 biosensors^{9,32,48}. To investigate the selectivity for H_2O_2 sensing, the amperometric responses of ascorbic acid (AA), dopamine (DA), uric acid (UA) and glucose (Glu) are investigated on the $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode. As shown in Fig. 5D, when the $\text{Co}_3\text{O}_4/\text{N-rGO}$ -modified GC electrode was polarized at -0.6 V , the addition of 0.2 mM AA, 0.02 mM DA, 0.2 mM UA and 5 mM Glu did not produce an observable current response while the addition of H_2O_2 induced obvious reduction currents response, indicating that the measurements of H_2O_2 are essentially interference-free from other relevant electroactive species. Therefore, the as-prepared the $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode is a good

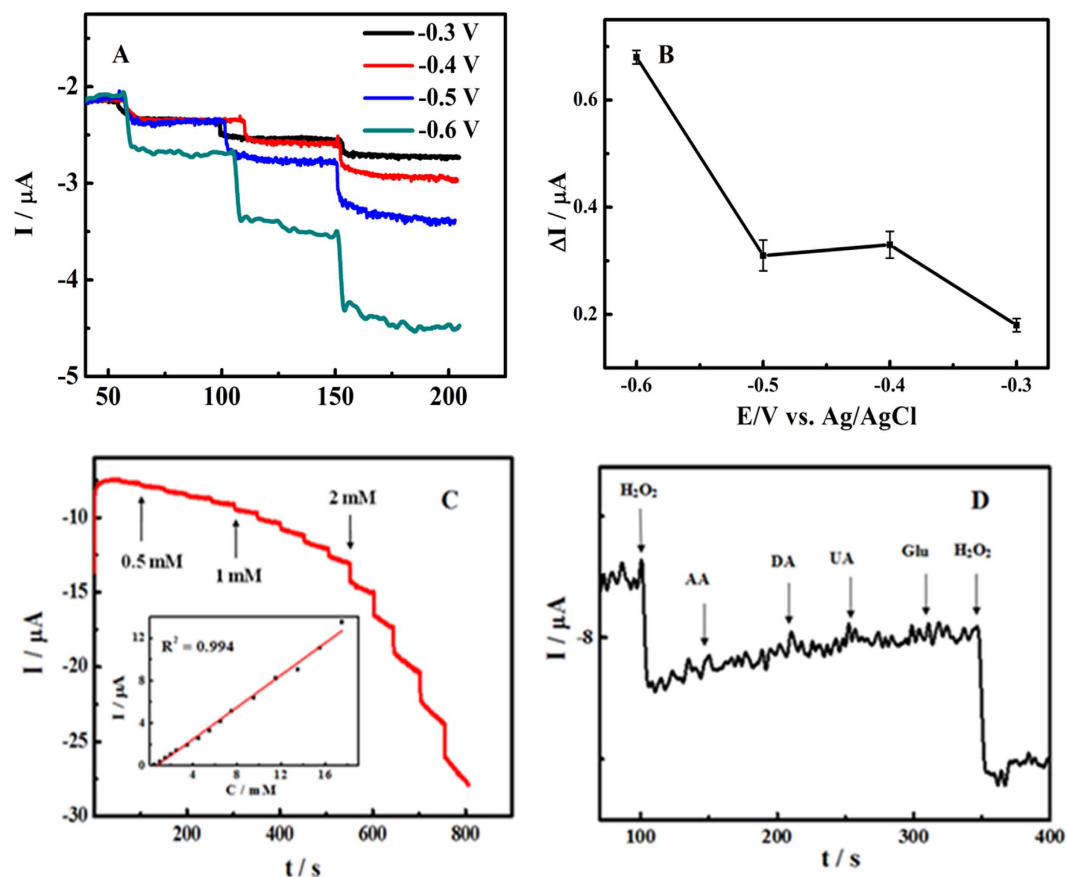


Figure 5. The effect of applied potential (A,B) to the amperometric response of sequential addition of 2 mM H_2O_2 on the $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode. Amperometric response of $\text{Co}_3\text{O}_4/\text{N-rGO}$ to successive addition of H_2O_2 . The inset is the plot of H_2O_2 peak current versus H_2O_2 concentration (C). Amperometric response of the $\text{Co}_3\text{O}_4/\text{N-rGO}$ exposed to H_2O_2 , AA, DA, UA and glucose. Applied potential: -0.6 V and supporting electrolyte: 0.1 M PB solution ($\text{pH } 7.0$) (D).

candidate for the fabrication of stable and specific amperometric sensor for the nonenzymatic detection of H_2O_2 . The excellent performance of H_2O_2 sensor can be ascribed to the well distributed and high loading amount of Co_3O_4 nanoparticles.

The performance of oxygen reduction reaction. To evaluate the ORR catalytic activity of $\text{Co}_3\text{O}_4/\text{N-rGO}$, N-rGO and $\text{Co}_3\text{O}_4/\text{rGO}$, CV measurements were performed in both O_2 and N_2 -saturated 0.1 M KOH solution. As shown in Fig. 6A, CV of N-rGO and $\text{Co}_3\text{O}_4/\text{rGO}$ in the O_2 -saturated electrolyte shows a reduction peak at -0.34 V and -0.33 V respectively, suggesting their electrochemical catalytic activity for ORR. As for $\text{Co}_3\text{O}_4/\text{N-rGO}$ composite modified electrode, a reduction peak at ca. -0.26 V is observed, which is more positive than those of N-rGO and $\text{Co}_3\text{O}_4/\text{rGO}$ while it also has a highest current density, suggesting a great improvement of catalytic activity, which is better than tri-functional carbon materials in previous study³². Previous have reported that the electrocatalytic activity of Co_3O_4 was mainly affected by structure⁴⁶. Co_3O_4 particles have a spinel structure and the direct Co-Co interactions across shared octahedral edges of its spinel framework can enhance the electronic conductivity which is beneficial to the ORR catalytic activity. On the other hand, the N-graphene also exhibited a much better electrocatalytic activity, long-term operation stability for oxygen reduction reaction²². Therefore, such an excellent electrocatalytic activity of the $\text{Co}_3\text{O}_4/\text{N-rGO}$ toward ORR can be ascribed to the synergetic chemical coupling effects of Co_3O_4 and N-graphene^{18,49,50}.

To investigate the oxygen reduction mechanism of $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrodes, the ORR was studied by RRDE technique via measurement of the yield of the generated intermediate H_2O_2 . The RRDE technique was applied to quantitatively determine the n value toward ORR and the H_2O_2 generation rate by setting the potential of the ring electrode at 0.4 V .

The electron transfer number n of ORR and HO_2^- intermediate production percentage ($\text{HO}_2^- \%$) were determined as

$$n = \frac{4 \times I_d}{I_d + I_r/N}$$

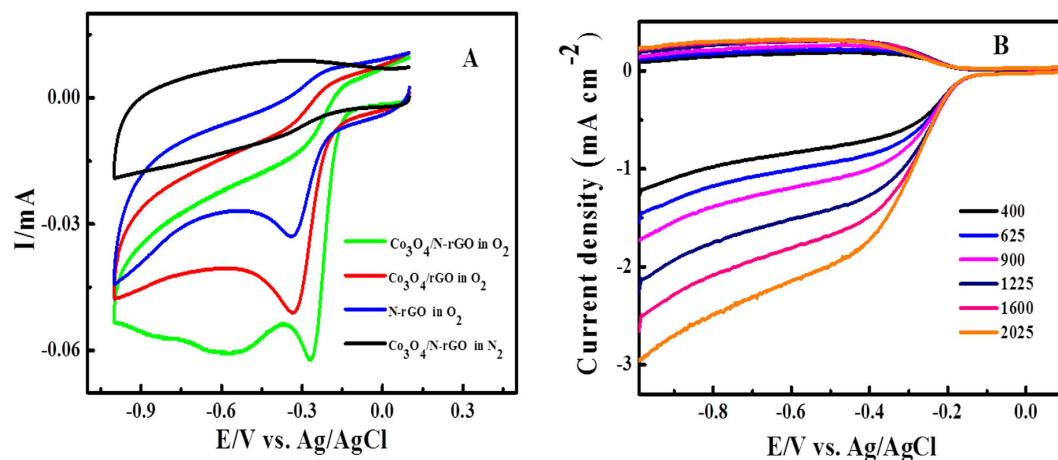


Figure 6. (A) Cyclic voltammograms of $\text{Co}_3\text{O}_4/\text{N-rGO}$, $\text{Co}_3\text{O}_4/\text{rGO}$, N-rGO modified GC electrodes in an O_2 -saturated and in N_2 -saturated 0.1 M KOH at a scan rate of 10 mV s^{-1} . (B) LSVs of $\text{Co}_3\text{O}_4/\text{N-rGO}$ on RRDE in 0.1 M KOH with various rotation rates at a scan rate of 5 mV s^{-1} .

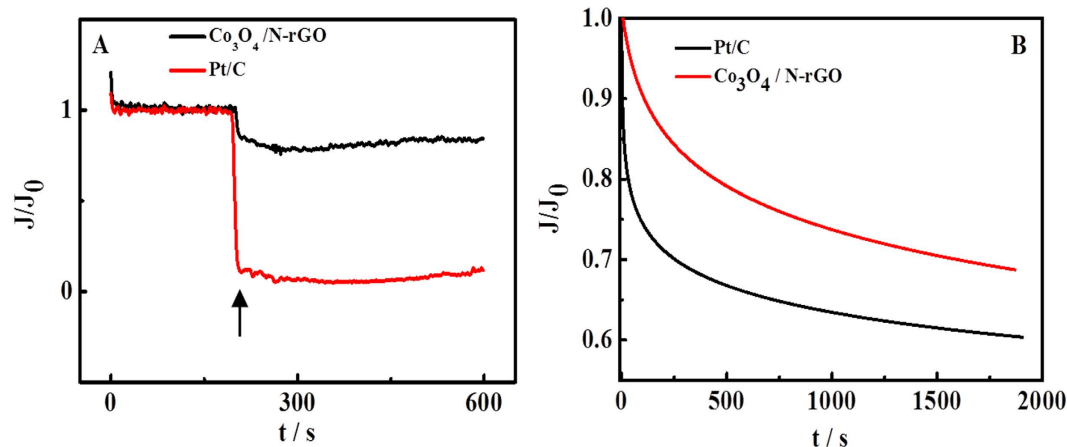


Figure 7. (A) Chronoamperometric responses of $\text{Co}_3\text{O}_4/\text{N-rGO}$ and Pt/C (20%) at -0.3 V in the O_2 -saturated 0.1 M KOH. The arrow indicates the addition of 3.0 M methanol into the O_2 -saturated electrochemical cell. (B) Chronoamperometric responses obtained at the Pt/C (20%) and $\text{Co}_3\text{O}_4/\text{N-rGO}$ at -0.3 V in O_2 -saturated 0.1 M KOH.

$$\text{HO}_2^- \% = 200 \times \frac{I_r/N}{I_d + I_r/N}$$

where I_d is the disk current, I_r is the ring current, and N is the current collection efficiency of the Pt ring, which was determined to be $0.4^{21,46}$. From the Fig. 6B, it was calculated $\text{H}_2\text{O}_2\%$ value for the $\text{Co}_3\text{O}_4/\text{N-rGO}$ during ORR process is about 63.5–32.2% at potentials ranging from -0.3 to -0.8 V . The calculated n value for the $\text{Co}_3\text{O}_4/\text{N-rGO}$ is about 2.9 to 3.4 from -0.3 to -0.8 V . These results reveal that the electrocatalytic process of $\text{Co}_3\text{O}_4/\text{N-rGO}$ is an improved four-electron pathway and a two-electron transfer pathway occurred simultaneously for ORR.

Methanol poisoning and stability are key issues challenging the cathode materials in current fuel cell techniques⁵¹. The effect of methanol poisoning and stability on the $\text{Co}_3\text{O}_4/\text{N-rGO}$ was investigated in Fig. 7A and B by current-time (i - t) chronoamperometry. As shown in Fig. 7A, when methanol was injected, a significant decrease (90.7%) in current was observed for the Pt/C electrode, whereas only a slight decrease (13.3%) was observed for the $\text{Co}_3\text{O}_4/\text{N-rGO}$, suggesting poor tolerance of Pt/C to methanol compared with the $\text{Co}_3\text{O}_4/\text{N-rGO}$ material. Figure 7B shows that the amperometric response of ORR on the $\text{Co}_3\text{O}_4/\text{N-rGO}$ which exhibits a very slow attenuation of relative current, after 2000 s i.e. a current loss of approximately 31.37%. In contrast, the Pt/C reveals degraded stability with a current loss (39.58%) after 2000 s, indicating the $\text{Co}_3\text{O}_4/\text{N-rGO}$ has a better stability than Pt/C .

The catalytic property of oxygen evolution reaction. Previous studies have reported Co_3O_4 particles deposited on stable supporting and conducting substrates can be used as effective electrode materials for both

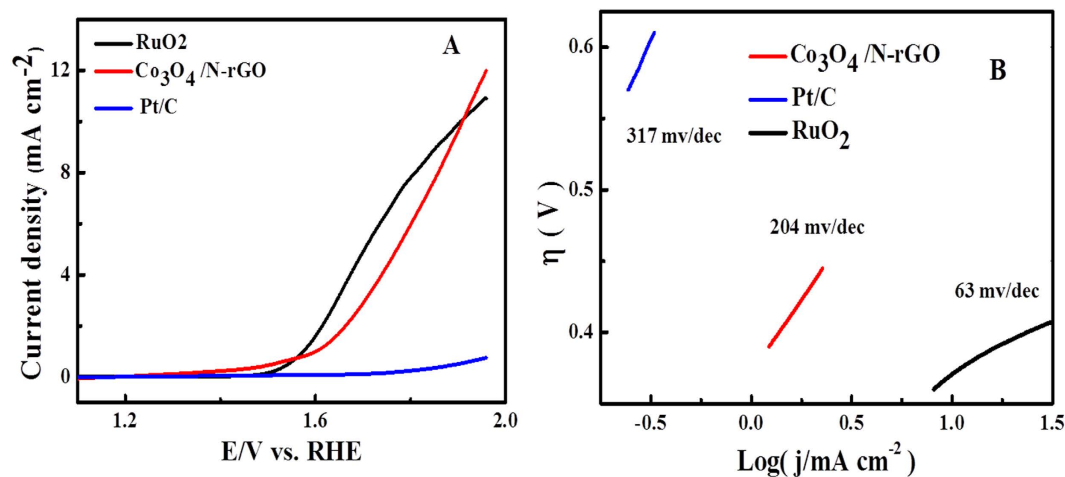


Figure 8. (A) The OER polarization curves of Co₃O₄/N-rGO catalyst and commercial Pt/C (20%) at a sweep rate of 5 mV s⁻¹ using RDE with a rotation speed of 1600 rpm and (B) corresponding Tafel plots.

the oxygen reduction (ORR) and evolution (OER) reactions via decreasing overpotential in fuel cells and water electrolyzers^{17,52}. The good catalytic performance of OER can be ascribed to the small crystalline size and the mixed valences Co²⁺ and Co³⁺ of Co₃O₄ as well with conductive support substrates¹⁷. Sun and his groups synthesize Co₃O₄ nanorod–multiwalled carbon nanotube hybrid with an onset potential of about 0.47 V vs. Ag/AgCl and Tafel slope of 65 mV/dec³⁷. In our work, a rotational disk electrode (RDE) tests were also carried out in alkaline solution to further evaluate the OER catalytic activity of the Co₃O₄/N-rGO. Figure 8A showed the typical linear sweep voltammograms using the RDE at an electrode rotating speed of 1600 rpm and a potential scanning rate of 5 mV s⁻¹. From the OER region, the Co₃O₄/N-rGO afforded a sharp onset potential at 1.54 V, which is worse than that of RuO₂ at 1.49 V and better than Pt/C. The OER over potential at current density of 10 mA cm⁻² is close to that of RuO₂, indicating the Co₃O₄/N-rGO has a good OER property. The Tafel slope is usually used to study the catalytic mechanism of electrocatalysis for OER. In Fig. 8B, The Tafel slope comparison showed that Co₃O₄/N-rGO has Tafel slope of 204 mV/dec which is much smaller than those for Pt/C (308 mV/dec) and is bigger than RuO₂ (63 mV/dec), suggesting Co₃O₄/N-rGO has an improved performance of OER.

Conclusions

In summary, this study describes a facile and effective route to synthesize hybrid material consisting of Co₃O₄ nanoparticles anchored on nitrogen-doped reduced graphene oxide (Co₃O₄/N-rGO) as a high-performance tri-functional catalyst for ORR, OER and H₂O₂ sensing. Owing to the synergetic chemical coupling effects between Co₃O₄ and graphene, the Co₃O₄/N-rGO exhibited excellent electrocatalytic activity with a direct reduction to H₂O₂ at -0.6 V and sensing ability towards H₂O₂. Although Co₃O₄/rGO or N-rGO alone has little catalytic activity, the Co₃O₄/N-rGO exhibits high ORR activity with ORR peak potential to be -0.26 V (vs. Ag/AgCl) and the number of electron transfer number is 3.4, excellent tolerance to methanol crossover and exceptionally good stability to Pt/C (20%) in alkaline solutions. Catalytic studies of Co₃O₄/N-rGO for OER display a better onset potential, overpotential under the current density of 10 mA cm⁻² and a smaller Tafel slope with Pt/C (20%). Due to the ease of synthesis and electrode fabrication, the method developed by this study could be used for large-scale synthesis of non-precious metal-based trifunctional metal catalyst for hydrogen peroxide reduction, ORR and OER.

Experimental

Chemicals and materials. Nafion perfluorinated resin solution (5 wt% in a mixture of lower aliphatic alcohols and water) and commercial platinum/carbon (Pt/C) 20 wt% (Pt loading: 20 wt%, Pt on carbon black) were obtained from Sigma-Aldrich. All other chemicals (analytical grade) were purchased from Beijing Chemical Reagent Company (Beijing, China) and used without further purification. Ultra-pure water was obtained with a Milli-Q plus water purification system (Milli-pore Co. Ltd., USA).

Materials characterization. Scanning electron microscopy (SEM) images were obtained on a Hitachi S-2600N scanning electron microscope. Elemental analysis data were obtained through Flash EA 1112. The X-ray photoelectronspectra (XPS) spectra were obtained using a VG Micro-tech ESCA 2000 using a monochromic 15 Al X-ray source. For rotating ring-disk electrode (RRDE) measurements, a bipotentiostat (CHI 832, Shanghai Chenhua Instrument Co. Ltd.) and a rotating ring-disk electrode with a rotating GC disk electrode and a platinum ring electrode (ALS RRDE-2) were used. The collection efficiency of the ring-disk electrode was evaluated with the Fe(CN)₆^{3-/4-} redox couple and was calculated to be 0.4. Electrochemical measurements were performed with a computer-controlled Electrochemical analyzer (CHI600E, Chenhua, China) in a two-compartment electrochemical cell with as-prepared material modified on a glassy carbon electrode (3 mm in diameter) as working electrode, a platinum wire as counter electrode, and a Ag/AgCl (3 M KCl) electrode as reference electrode. All electrochemical experiments were performed at room temperature.

Preparation of $\text{Co}_3\text{O}_4/\text{N-rGO}$, N-rGO and $\text{Co}_3\text{O}_4/\text{rGO}$ materials. 16.5 mg oxidized graphene oxide (GO) were redispersed in 50 mL anhydrous ethanol to form GO anhydrous ethanol suspension with concentration to be 0.33 mg/mL. The first step to prepare $\text{Co}_3\text{O}_4/\text{N-rGO}$ was performed by adding 3.6 ml of 0.2 M $\text{Co}(\text{Ac})_2$ aqueous solution to 72 ml of GO anhydrous ethanol suspension, followed by the addition of 1.8 ml of NH_4OH (30% solution) and 2.1 ml of water, consequently. The reaction was kept at 80 °C with stirring for 10 h. After that, the reaction mixture from the first step was transferred to a 100 mL autoclave for hydrothermal reaction at 180 °C for 12 h. $\text{Co}_3\text{O}_4/\text{GO}$ hybrid was made by the same steps without adding NH_4OH (30% solution) in the first step²⁶. N-rGO hybrid was also made by the same steps just as making $\text{Co}_3\text{O}_4/\text{N-rGO}$ preparation without adding $\text{Co}(\text{Ac})_2$ aqueous solution.

The fabrication of as-prepared materials modified electrodes. A rotating ring-disk electrode (RRDE) with a rotating glassy carbon (GC) disk electrode (4 mm diameter) and a platinum ring electrode (ALS RRDE-2), and a GC electrode with a diameter of 3 mm working electrode were used as working electrode in this study. Prior to the surface modification, the delectrode were polished with 1.0, 0.3, and 0.05 μm alumina slurries, and finally rinsed with Milli-Q water under an ultrasonic bath for 1 min. A $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode was prepared by casting the 4 μL of 2 mg/mL $\text{Co}_3\text{O}_4/\text{N-rGO}$ suspension on the disk electrode surface and drying in air to evaporate the solvent. Similarly, 4 μL of 2 mg/mL N-rGO solution and 4 μL of 2 mg/mL $\text{Co}_3\text{O}_4/\text{GO}$ suspension were dropped on GC electrodes, respectively and dried in air to evaporate the solvent for control experiment. Finally, 5 μL nafion (0.5%) solution (diluted 10 times with deionized water) was covered onto electrode surface and dried to form modified working electrode.

All of the electrochemistry experiments were performed at room temperature. The $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC electrode was pretreated by electrochemical oxidation in a phosphate buffered solution (pH = 6.8) at a potential of 1.7 V (vs. Ag/AgCl) for 300 s at room temperature, followed by potential sweeping from 0.0 V to 1.4 V in 0.5 M H_2SO_4 until a stable voltammogram was achieved, the purpose of electrochemical oxidation in phosphate buffered solution and H_2SO_4 is increased more oxygen containing functional group in carbon materials to increase the active site in oxygen reduction reaction. some Co_3O_4 nanoparticles may dissolve in H_2SO_4 thus leaves more active sites on grapheme. For linear sweep voltammetry (LSV) from 0.2 to -1.0 V, The $\text{Co}_3\text{O}_4/\text{N-rGO}$ modified GC was scanned at a scan rate of 10 $\text{mV}\cdot\text{s}^{-1}$ to measure the surface behavior of the ORR activity of the catalyst in O_2 -saturated 0.1 M KOH. For more quantitative measurements of the ORR activity, LSV was conducted on the catalyst-coated RRDE at a scan rate of 5 $\text{mV}\cdot\text{s}^{-1}$ in O_2 -saturated KOH solution at various rotation rates from 400 to 2025 $\text{r}\cdot\text{min}^{-1}$.

References

- Jiang, H. *et al.* Iron Carbide Nanoparticles Encapsulated in Mesoporous Fe-N-Doped Graphene-Like Carbon Hybrids as Efficient Bifunctional Oxygen Electrocatalysts. *ACS Appl Mater Interfaces* **7**, 21511–21520 (2015).
- Nishio, K. *et al.* Oxygen reduction and evolution reactions of air electrodes using a perovskite oxide as an electrocatalyst. *Journal of Power Sources* **278**, 645–651 (2015).
- Devoille, A. M. & Love, J. B. Double-pillared cobalt Pacman complexes: synthesis, structures and oxygen reduction catalysis. *Dalton Trans* **41**, 65–72 (2012).
- Kong, A. *et al.* From cage-in-cage MOF to N-doped and Co-nanoparticle-embedded carbon for oxygen reduction reaction. *Dalton Trans* **44**, 6748–6754 (2015).
- Daems, N., Sheng, X., Vankelecom, I. F. J. & Pescarmona, P. P. Metal-free doped carbon materials as electrocatalysts for the oxygen reduction reaction. *Journal of Materials Chemistry A* **2**, 4085–4110 (2014).
- Wang, Y. *et al.* One-step replication and enhanced catalytic activity for cathodic oxygen reduction of the mesostructured $\text{Co}_3\text{O}_4/\text{carbon}$ composites. *Dalton Trans* **43**, 4163–4168 (2014).
- Wang, Y.-J., Wilkinson, D. P. & Zhang, J. Synthesis of conductive rutile-phased $\text{Nb}_0.06\text{Ti}_0.94\text{O}_2$ and its supported Pt electrocatalysts (Pt/ $\text{Nb}_0.06\text{Ti}_0.94\text{O}_2$) for the oxygen reduction reaction. *Dalton Trans* **41**, 1187–1194 (2012).
- Chen, L. *et al.* One-step synthesis of sulfur doped graphene foam for oxygen reduction reactions. *Dalton Trans* **43**, 3420–3423 (2014).
- Wang, K., Liu, Q., Wu, X. Y., Guan, Q. M. & Li, H. N. Graphene enhanced electrochemiluminescence of CdS nanocrystal for H_2O_2 sensing. *Talanta* **82**, 372–376 (2010).
- Jia, L., Liu, J. & Wang, H. Preparation of poly(diallyldimethylammonium chloride)-functionalized graphene and its applications for H_2O_2 and glucose sensing. *Electrochimica Acta* **111**, 411–418 (2013).
- Wu, Q., Sheng, Q. & Zheng, J. Nonenzymatic amperometric sensing of hydrogen peroxide using a glassy carbon electrode modified with a sandwich-structured nanocomposite consisting of silver nanoparticles, Co_3O_4 and reduced graphene oxide. *Microchimica Acta* **183**, 1943–1951 (2016).
- Lin, Y., Li, L., Hu, L., Liu, K. & Xu, Y. Multifunctional poly(dopamine)-assisted synthesis of silver nano particles/carbon nanotubes nanocomposite: Toward electrochemical sensing of hydrogen peroxide with enhanced sensitivity. *Sensors and Actuators B: Chemical* **202**, 527–535 (2014).
- Li, X. *et al.* MOF derived Co_3O_4 nanoparticles embedded in N-doped mesoporous carbon layer/MWCNT hybrids: extraordinary bi-functional electrocatalysts for OER and ORR. *J. Mater. Chem. A* **3**, 17392–17402 (2015).
- Zhu, J. *et al.* Significantly enhanced oxygen reduction reaction performance of N-doped carbon by heterogeneous sulfur incorporation: synergistic effect between the two dopants in metal-free catalysts. *J. Mater. Chem. A* **4**, 7422–7429 (2016).
- Liu, H.-W. *et al.* Trap state passivation improved hot-carrier instability by zirconium-doping in hafnium oxide in a nanoscale n-metal-oxide semiconductor-field effect transistors with high-k/metal gate. *Applied Physics Letters* **108**, 173504 (2016).
- Aijaz, A. *et al.* $\text{Co}@\text{Co}_3\text{O}_4$ Encapsulated in Carbon Nanotube-Grafted Nitrogen-Doped Carbon Polyhedra as an Advanced Bifunctional Oxygen Electrode. *Angew Chem Int Ed Engl* **55**, 4087–4091 (2016).
- Xu, L. *et al.* Plasma-Engraved Co_3O_4 Nanosheets with Oxygen Vacancies and High Surface Area for the Oxygen Evolution Reaction. *Angew Chem Int Ed Engl* **55**, 5277–5281 (2016).
- Liu, S., Li, L., Ahn, H. S. & Manthiram, A. Delineating the roles of Co_3O_4 and N-doped carbon nanoweb (CNW) in bifunctional $\text{Co}_3\text{O}_4/\text{CNW}$ catalysts for oxygen reduction and oxygen evolution reactions. *Journal of Materials Chemistry A* **3**, 11615–11623 (2015).
- Yeo, B. S. & Bell, A. T. Enhanced activity of gold-supported cobalt oxide for the electrochemical evolution of oxygen. *J Am Chem Soc* **133**, 5587–5593 (2011).

20. Salimi, A., Hallaj, R., Soltanian, S. & Mamkhezri, H. Nanomolar detection of hydrogen peroxide on glassy carbon electrode modified with electrodeposited cobalt oxide nanoparticles. *Anal Chim Acta* **594**, 24–31 (2007).
21. Nguyen, T. T. *et al.* Facile synthesis of cobalt oxide/reduced graphene oxide composites for electrochemical capacitor and sensor applications. *Solid State Sciences* **53**, 71–77 (2016).
22. Zhang, Y. *et al.* Crystal plane-dependent electrocatalytic activity of Co₃O₄ toward oxygen evolution reaction. *Catalysis Communications* **67**, 78–82 (2015).
23. Xiao, J. *et al.* Core-shell Co@Co₃O₄ nanoparticle-embedded bamboo-like nitrogen-doped carbon nanotubes (BNCNTs) as a highly active electrocatalyst for the oxygen reduction reaction. *Nanoscale* **7**, 7056–7064 (2015).
24. Lu, H., Huang, Y., Yan, J., Fan, W. & Liu, T. Nitrogen-doped graphene/carbon nanotube/Co₃O₄ hybrids: one-step synthesis and superior electrocatalytic activity for the oxygen reduction reaction. *RSC Adv.* **5**, 94615–94622 (2015).
25. Chung, M. W., Choi, C. H., Lee, S. Y. & Woo, S. I. Dimensionality-dependent oxygen reduction activity on doped graphene: Is graphene a promising substrate for electrocatalysis? *Nano Energy* **11**, 526–532 (2015).
26. Jiang, L., Tang, Q., Liu, J. & Sun, G. Elucidation of oxygen reduction reaction pathway on carbon-supported manganese oxides. *Chinese Journal of Catalysis* **36**, 175–180 (2015).
27. Liang, Y. *et al.* Co₃O₄ nanocrystals on graphene as a synergistic catalyst for oxygen reduction reaction. *Nature Materials* **10**, 780–786 (2011).
28. Liu, S. *et al.* Nitrogen-rich carbon coupled multifunctional metal oxide/graphene nanohybrids for long-life lithium storage and efficient oxygen reduction. *Nano Energy* **12**, 578–587 (2015).
29. Wang, K. *et al.* N-doped carbon encapsulated Co₃O₄ nanoparticles as a synergistic catalyst for oxygen reduction reaction in acidic media. *International Journal of Hydrogen Energy* **40**, 3875–3882 (2015).
30. Li, M., Han, C., Zhang, Y., Bo, X. & Guo, L. Facile synthesis of ultrafine Co₃O₄ nanocrystals embedded carbon matrices with specific skeletal structures as efficient non-enzymatic glucose sensors. *Analytica Chimica Acta* **861**, 25–35 (2015).
31. Du, C., Huang, H., Feng, X., Wu, S. & Song, W. Confining MoS₂ nanodots in 3D porous nitrogen-doped graphene with amendable ORR performance. *J. Mater. Chem. A* **3**, 7616–7622 (2015).
32. Geng, D. *et al.* Non-noble metal oxygen reduction electrocatalysts based on carbon nanotubes with controlled nitrogen contents. *Journal of Power Sources* **196**, 1795–1801 (2011).
33. Cai, Z.-X., Song, X.-H., Chen, Y.-Y., Wang, Y.-R. & Chen, X. 3D nitrogen-doped graphene aerogel: A low-cost, facile prepared direct electrode for H₂O₂ sensing. *Sensors and Actuators B: Chemical* **222**, 567–573 (2016).
34. Li, F. *et al.* Atomic Mechanism of Electrocatalytically Active Co-N Complexes in Graphene Basal Plane for Oxygen Reduction Reaction. *ACS Appl Mater Interfaces* **7**, 27405–27413 (2015).
35. Liang, Y. *et al.* Oxygen reduction electrocatalyst based on strongly coupled cobalt oxide nanocrystals and carbon nanotubes. *J Am Chem Soc* **134**, 15849–15857 (2012).
36. Xiao, J. *et al.* Nitrogen-doped mesoporous graphene as a synergistic electrocatalyst matrix for high-performance oxygen reduction reaction. *ACS Appl Mater Interfaces* **6**, 17654–17660 (2014).
37. Zhang, Y. X., Guo, X., Zhai, X., Yan, Y. M. & Sun, K. N. Diethylenetriamine (DETA)-assisted anchoring of Co₃O₄ nanorods on carbon nanotubes as efficient electrocatalysts for the oxygen evolution reaction. *Journal of Materials Chemistry A* **3**, 1761–1768 (2015).
38. Wang, M., Jiang, X., Liu, J., Guo, H. & Liu, C. Highly sensitive H₂O₂ sensor based on Co₃O₄ hollow sphere prepared via a template-free method. *Electrochimica Acta* **182**, 613–620 (2015).
39. Wang, M. *et al.* Co₃O₄ nanorods decorated reduced graphene oxide composite for oxygen reduction reaction in alkaline electrolyte. *Electrochemistry Communications* **34**, 299–303 (2013).
40. Singh, S. K., Dhavale, V. M. & Kurungot, S. Surface-Tuned Co₃O₄ Nanoparticles Dispersed on Nitrogen-Doped Graphene as an Efficient Cathode Electrocatalyst for Mechanical Rechargeable Zinc–Air Battery Application. *ACS Applied Materials & Interfaces* **7**, 21138–21149 (2015).
41. Yang, L., Su, Y., Li, W. & Kan, X. Fe/N/C Electrocatalysts for Oxygen Reduction Reaction in PEM Fuel Cells Using Nitrogen-Rich Ligand as Precursor. *The Journal of Physical Chemistry C* **119**, 11311–11319 (2015).
42. Lin, Y. *et al.* A Facile Electrochemical Method for Simultaneous and On-Line Measurements of Glucose and Lactate in Brain Microdialysate with Prussian Blue as the Electrocatalyst for Reduction of Hydrogen Peroxide. *Analytical Chemistry* **79**, 9577–9583 (2007).
43. Zakaria, M. B. *et al.* Nanoporous Mn-based electrocatalysts through thermal conversion of cyano-bridged coordination polymers toward ultra-high efficiency hydrogen peroxide production. *Journal of Materials Chemistry A* **4**, 9266–9274 (2016).
44. Datta, K. J. *et al.* Micro-mesoporous iron oxides with record efficiency for the decomposition of hydrogen peroxide: morphology driven catalysis for the degradation of organic contaminants. *J. Mater. Chem. A* **4**, 596–604 (2016).
45. Sa, Y. J. & Kwon, K., Jae, Yeong Cheon, Kleitz, F. & Joo, a. S. H. Ordered mesoporous Co₃O₄ spinels as stable, bifunctional, noble metal-free oxygen electrocatalysts. *Journal of Materials Chemistry A* **1**, 9992–10001 (2013).
46. Ren, G. *et al.* A bio-inspired Co₃O₄-polypyrrole-graphene complex as an efficient oxygen reduction catalyst in one-step ballmilling. *Nano Research* **8**, 3461–3471 (2015).
47. Lin, Y., Hu, L., Li, L. & Wang, K. Facile synthesis of nickel hydroxide–graphene nanocomposites for insulin detection with enhanced electro-oxidation properties. *RSC Adv.* **4**, 46208–46213 (2014).
48. Li, S. J., Du, J. M., Zhang, J. P., Zhang, M. J. & Chen, J. A glassy carbon electrode modified with a film composed of cobalt oxide nanoparticles and graphene for electrochemical sensing of H₂O₂. *Microchim Acta* **181**, 631–638 (2014).
49. Qu, L., Liu, Y., Baek, J. & Dai, L. Nitrogen-Doped Graphene as Efficient Metal-Free Electrocatalyst for Oxygen Reduction in Fuel Cells. *ACS NANO* **4**, 1321–1326 (2010).
50. Wang, Z., Lei, H., Cao, R. & Zhang, M. Cobalt Corrole on Carbon Nanotube as a Synergistic Catalyst for Oxygen Reduction Reaction in Acid Media. *Electrochimica Acta* **171**, 81–88 (2015).
51. Zhang, X. X. *et al.* La₂O₃ Doped Carbonaceous Microspheres: A Novel Bifunctional Electrocatalyst for Oxygen Reduction and Evolution Reactions with Ultrahigh Mass Activity. *Journal of Physical Chemistry C* **118**, 20229–20237 (2014).
52. Kumar, K. *et al.* Effect of the Oxide–Carbon Heterointerface on the Activity of Co₃O₄/NrGO Nanocomposites toward ORR and OER. *The Journal of Physical Chemistry C* **120**, 7949–7958 (2016).

Acknowledgements

This work was financially supported by National Natural Science Foundation (21575090), Beijing Municipal Natural Science Foundation (2162009), Scientific Research Project of Beijing Educational Committee (KM201410028006), Youth Talent Project of the Beijing Municipal Commission of Education (CIT&TCD201504072), Scientific Research Base Development Program of the Beijing Municipal Commission of Education.

Author Contributions

T.Z. and Y.D. contributed to the experimental, data interpretation and wrote the manuscript. Y.L. conceived the study and experimental design. C.H. and F.S. contributed to the statistical analysis. M.W., L.P. and J.W. contributed to catalyst synthesis. All authors reviewed and approved of the final version of the manuscript.

Additional Information

Competing Interests: The authors declare no competing financial interests.

How to cite this article: Zhang, T. *et al.* Co₃O₄ nanoparticles anchored on nitrogen-doped reduced graphene oxide as a multifunctional catalyst for H₂O₂ reduction, oxygen reduction and evolution reaction. *Sci. Rep.* **7**, 43638; doi: 10.1038/srep43638 (2017).

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2017