

# SCIENTIFIC REPORTS



OPEN

## Prediction of a new ground state of superhard compound $B_6O$ at ambient conditions

Huafeng Dong<sup>1,2</sup>, Artem R. Oganov<sup>2,3,4,5</sup>, Qinggao Wang<sup>4,6</sup>, Sheng-Nan Wang<sup>2</sup>, Zhenhai Wang<sup>2,7</sup>, Jin Zhang<sup>2</sup>, M. Mahdi Davari Esfahani<sup>2</sup>, Xiang-Feng Zhou<sup>2,8</sup>, Fugen Wu<sup>1</sup> & Qiang Zhu<sup>2</sup>

Received: 21 April 2016

Accepted: 15 July 2016

Published: 08 August 2016

Boron suboxide  $B_6O$ , the hardest known oxide, has an  $R\bar{3}m$  crystal structure ( $\alpha$ - $B_6O$ ) that can be described as an oxygen-stuffed structure of  $\alpha$ -boron, or, equivalently, as a cubic close packing of  $B_{12}$  icosahedra with two oxygen atoms occupying all octahedral voids in it. Here we show a new ground state of this compound at ambient conditions,  $Cmcm$ - $B_6O$  ( $\beta$ - $B_6O$ ), which in all quantum-mechanical treatments that we tested comes out to be slightly but consistently more stable. Increasing pressure and temperature further stabilizes it with respect to the known  $\alpha$ - $B_6O$  structure.  $\beta$ - $B_6O$  also has a slightly higher hardness and may be synthesized using different experimental protocols. We suggest that  $\beta$ - $B_6O$  is present in mixture with  $\alpha$ - $B_6O$ , and its presence accounts for previously unexplained bands in the experimental Raman spectrum.

Superhard materials are used in many applications, from cutting, grinding and drilling tools to wear-resistant coatings<sup>1–3</sup>. However, most superhard materials<sup>4</sup>, such as diamond<sup>5</sup> and cubic-BN<sup>6</sup>, are synthesized at high pressure, which makes them expensive, but some (boron allotropes,  $B_6O$ ,  $B_4C$ ) are thermodynamically stable already at ambient conditions. The hardness of  $\alpha$ - $B_6O$ <sup>7</sup> was reported to be in the range 30–45 GPa<sup>8,9</sup>, making it the hardest known oxide<sup>9–11</sup>.

Objects with icosahedral symmetry ( $I_h$ ) bear a special fascination because of incompatibility of fivefold symmetry with crystalline periodicity. The discovery of multiply-twinned particles  $B_6O$ , an icosahedral packing of  $B_{12}$  icosahedra with  $I_h$  symmetry, had aroused interest<sup>7</sup>. Here we report the prediction of a new phase of  $B_6O$ , with space group  $Cmcm$ , which we name  $\beta$ - $B_6O$ . This structure is energetically almost degenerate with  $\alpha$ - $B_6O$  (and slightly more stable), is predicted to have a higher hardness, and actually corresponds to twinned  $\alpha$ - $B_6O$  structure.

### Results


**Discovery of  $\beta$ - $B_6O$  at ambient conditions.** Our variable-composition evolutionary searches expectedly find  $B_2O_3$  and  $B_6O$  to be the only stable compounds in the B-O system. Interestingly, there are also several compounds very close to stability -  $B_2O_7$  (this is a 2D-form of  $B_2O_3$  intercalated with oxygen molecules) and oxygen-deficient versions of  $B_6O$  with  $B_6O$ -like structures and compositions between B and  $B_6O$ . To our surprise,  $Cmcm$ - $B_6O$  ( $\beta$ - $B_6O$ , see Table 1 for structural parameters), instead of the well-known  $R\bar{3}m$ - $B_6O$  ( $\alpha$ - $B_6O$ )<sup>7,12–14</sup>, turned out to be the most stable structure at ambient pressure, as shown in Fig. 1; phonon calculations have confirmed its dynamical stability. Transmission electron microscopy recently confirmed its existence<sup>15</sup>. Structural parameters and some of the physical properties of  $\beta$ - $B_6O$  are shown in Table 1, in comparison with  $\alpha$ - $B_6O$  and two related forms of pure boron.

<sup>1</sup>School of Physics and Optoelectronic Engineering, Guangdong University of Technology, Guangzhou 510006, China.

<sup>2</sup>Department of Geosciences and Center for Materials by Design, Institute for Advanced Computational Science, State University of New York, Stony Brook, NY 11794, USA. <sup>3</sup>Skolkovo Institute of Science and Technology, Skolkovo Innovation Center, 3 Nobel St., Moscow 143026, Russia. <sup>4</sup>Moscow Institute of Physics and Technology, 9 Institutskiy Lane, Dolgoprudny city, Moscow Region 141700, Russian Federation. <sup>5</sup>Northwestern Polytechnical University, Xi'an 710072, China. <sup>6</sup>Department of Physics and Electrical Engineering, Anyang Normal University, Anyang, Henan Province 455000, China. <sup>7</sup>Peter Grünberg Research Center, Nanjing University of Posts and Telecommunications, Nanjing 210003, China. <sup>8</sup>School of Physics and Key Laboratory of Weak-Light Nonlinear Photonics, Nankai University, Tianjin 300071, China. Correspondence and requests for materials should be addressed to A.R.O. (email: artem.oganov@stonybrook.edu)

Phase	$\alpha$ -B	$Cmcm$ -B	$\alpha$ -B <sub>6</sub> O	$Cmcm$ -B <sub>6</sub> O
Space group	$R\bar{3}m$	$Cmcm$	$R\bar{3}m$	$Cmcm$
V, Å <sup>3</sup> /atom	7.248	7.262	7.387	7.384
Cell parameters	$a = b = c = 5.050$ Å, $\alpha = 58.04^\circ$	$a = 4.883$ Å, $b = 8.852$ Å, $c = 8.064$ Å $\alpha = \beta = \gamma = 90^\circ$	$a = b = c = 5.153$ Å, $\alpha = 63.10^\circ$	$a = 5.393$ Å, $b = 8.777$ Å, $c = 8.736$ Å $\alpha = \beta = \gamma = 90^\circ$
Atomic coordinates	B1(0.654, 0.010, 0.010) B2(0.630, 0.221, 0.221)	B1(0.000, 0.236, 0.568) B2(0.500, 0.937, 0.576) B3(0.823, 0.167, 0.750) B4(0.797, 0.831, 0.639) B5(0.682, 0.995, 0.750)	B1(0.998, 0.998, 0.667) B2(0.676, 0.201, 0.201) O(0.622, 0.622, 0.622)	B1(0.000, 0.756, 0.588) B2(0.000, 0.549, 0.584) B3(0.165, 0.824, 0.750) B4(0.238, 0.155, 0.649) B5(0.334, 0.987, 0.750) O(0.000, 0.840, 0.439)
$Hv_{(Chen)}$ , GPa	39	35	38	39
$Hv_{(Lyakhov)}$ , GPa	33.0	32.7	31.6	31.7
$B_0$ , GPa	212(214 <sup>a</sup> )	208	227(181 <sup>b</sup> )	226
G, GPa	201	189	208	209
DFT band gap, eV	1.457	1.772	1.854 <sup>c</sup>	1.805 <sup>c</sup>


**Table 1.** Calculated structural parameters, hardness, elastic moduli and band gap of  $\alpha$ -B,  $Cmcm$ -B,  $\alpha$ -B<sub>6</sub>O, and  $Cmcm$ -B<sub>6</sub>O phases at ambient pressure. <sup>a</sup>Theory, reference 40. <sup>b</sup>Experiment, reference 41. <sup>c</sup>See Supplementary Fig. S1 for detailed band structures.

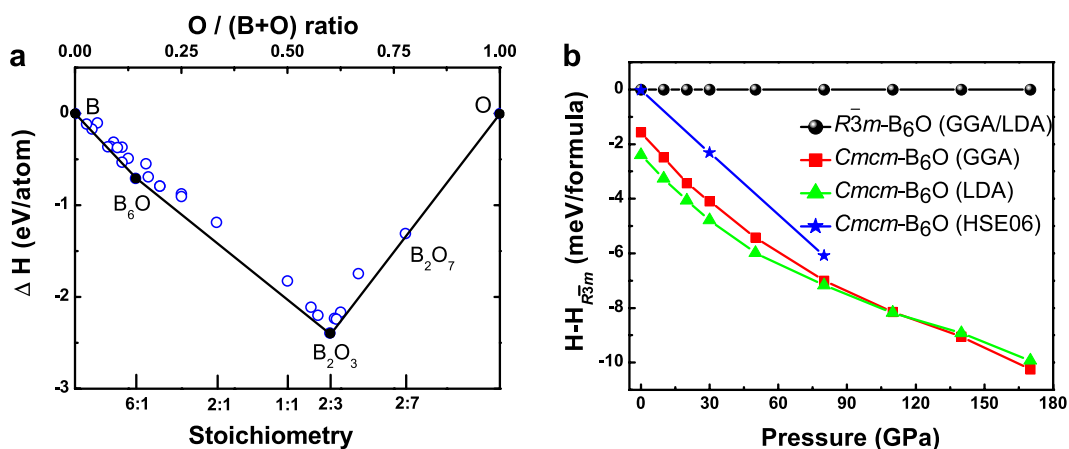


**Figure 1.** Stability of  $Cmcm$ -B<sub>6</sub>O. (a) Convex hull of the B-O system at ambient pressure. The solid (hollow) points represent the stable (metastable) structures. (b) Enthalpy difference between  $\beta$ -B<sub>6</sub>O and  $\alpha$ -B<sub>6</sub>O, including zero-point energy.

In order to further compare the stability of  $\beta$ -B<sub>6</sub>O and  $\alpha$ -B<sub>6</sub>O, we calculated their enthalpies as a function of pressure, as shown in Fig. 1b. We found that the enthalpy of  $\beta$ -B<sub>6</sub>O is lower than that of  $\alpha$ -B<sub>6</sub>O at ambient pressure, but the energy difference is only about 1.8 meV/formula within the GGA (and almost degenerate within the HSE06 hybrid functional). As pressure increases,  $\beta$ -B<sub>6</sub>O becomes progressively more favorable than  $\alpha$ -B<sub>6</sub>O, indicating that  $\beta$ -B<sub>6</sub>O might be more easily synthesized under pressure. The enthalpies of the two structures are so close that it makes us think: will the two structures coexist? what is their relationship? how to synthesize  $\beta$ -B<sub>6</sub>O? In order to answer these questions, we perform a detailed comparison of their structure, Raman spectra and phonon densities of states (PDOS).

**Comparison of crystal structures of  $\alpha$ -B<sub>6</sub>O and  $\beta$ -B<sub>6</sub>O.**  $\beta$ -B<sub>6</sub>O structure has hexagonal close packing of B<sub>12</sub> icosahedra (ABAB... stacking), while  $\alpha$ -B<sub>6</sub>O is based on the cubic close packing (ABCABC... stacking) of B<sub>12</sub> icosahedra, as shown in Fig. 2d,c. As is the case of hcp and fcc metals, twinning of  $\alpha$ -B<sub>6</sub>O can produce local  $\beta$ -B<sub>6</sub>O stackings. It may also be possible to obtain  $\beta$ -B<sub>6</sub>O-like stacking faults by deformation of  $\alpha$ -B<sub>6</sub>O, through plane slips. Most properties of these two phases are very similar: e.g. predicted volume per formula ( $V(\alpha$ -B<sub>6</sub>O) = 51.71 Å<sup>3</sup>/formula;  $V(Cmcm$ -B<sub>6</sub>O) = 51.69 Å<sup>3</sup>/formula), hardness ( $Hv(\alpha$ -B<sub>6</sub>O) = 38 GPa;  $Hv(Cmcm$ -B<sub>6</sub>O) = 39 GPa), elastic moduli (Table 1), DFT band gaps ( $\alpha$ -B<sub>6</sub>O has a 1.85 eV direct band gap, while  $Cmcm$ -B<sub>6</sub>O has a 1.81 eV indirect band gap).

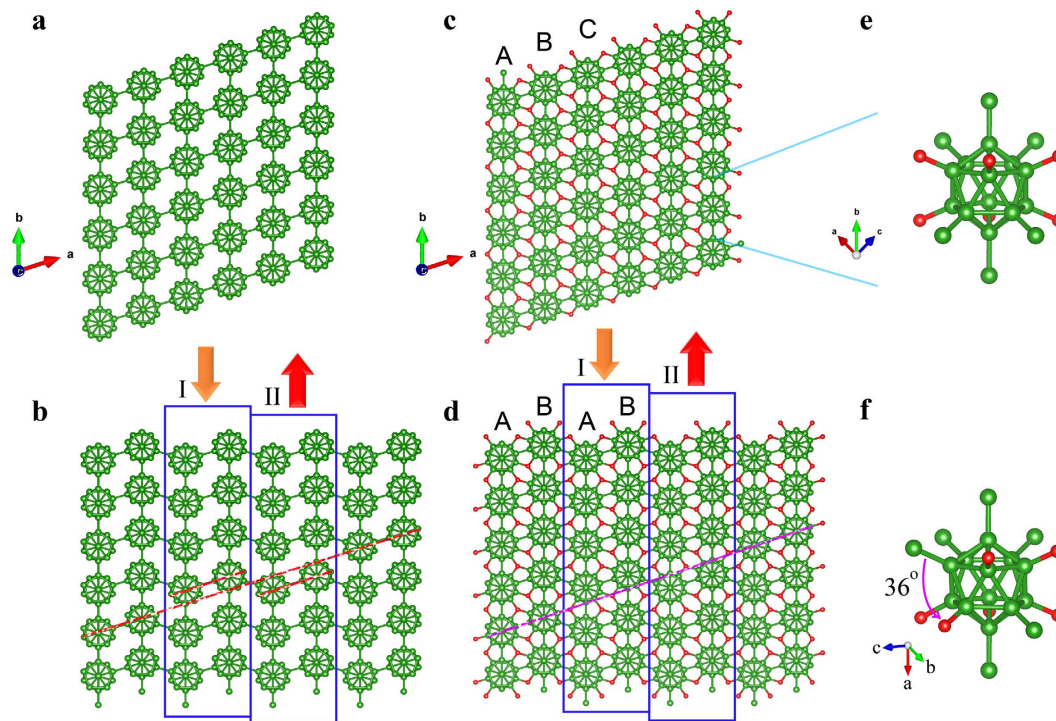


**Figure 2.** Crystal structures of (a)  $\alpha$ -B, (b)  $Cmc$ -B, (c)  $\alpha$ - $B_6O$ , (d)  $Cmc$ - $B_6O$ , and their local structures, (e,f)  $B_{12}$  icosahedra. Green (large) and red (small) spheres denote B and O atoms, respectively.

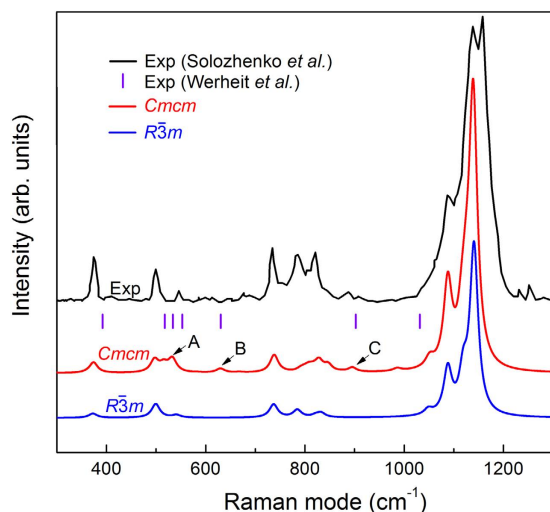

**Figure 3.** Raman spectra of  $B_6O$ : experimental spectrum of Solozhenko *et al.*<sup>12</sup>, Raman mode frequencies experimentally observed by Werheit and Kuhlmann<sup>21</sup>, and our calculated Raman spectra of  $Cmc$ - $B_6O$  and  $\alpha$ - $B_6O$ .

Another interesting aspect is that if we remove the oxygen atoms from  $\alpha$ - $B_6O$  and  $Cmc$ - $B_6O$ , they turn into  $\alpha$ -B<sup>16</sup> and  $Cmc$ -B, respectively (Fig. 2a,b).  $\alpha$ -B and  $Cmc$ -B are energetically nearly degenerate structures of boron at low pressure<sup>17</sup>, while  $Cmc$ -B is a newly predicted structure<sup>18,19</sup>. As shown in Fig. 2b, displacements of layers I and II can transform this structure into  $\alpha$ -B, and vice versa;  $Cmc$ - $B_6O$  and  $\alpha$ - $B_6O$  have a similar relationship (Fig. 2d). Furthermore, we found that the conversion of  $Cmc$ - $B_6O$  and  $\alpha$ - $B_6O$  will cause a deflection of B-O bond by  $36^\circ$ , as shown in their local structure (Fig. 2e,f).

However, it should be pointed out that it is not easy to change the stacking in covalent systems, though some examples are known – lonsdaleite (metastable “hexagonal diamond”) is formed in shocked cubic diamond. To obtain multiple polytypes, methods like physical vapor transport (PVT), also known as seeded sublimation growth, can be used: e.g., different polytypes of SiC were obtained using the PVT method<sup>20</sup>.

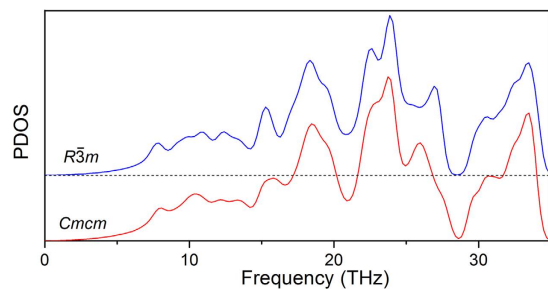

**Figure 4.** Phonon density of states of  $\alpha$ - $B_6O$  phase and  $Cmcm$ - $B_6O$  phase at ambient pressure. For clarity, the PDOS of  $\alpha$ - $B_6O$  was shifted.

**Comparison of Raman spectra.** As mentioned above,  $\beta$ - $B_6O$  and  $\alpha$ - $B_6O$  are energetically almost degenerate at zero pressure, structurally related and can coexist. To test the latter, we calculated their Raman spectra and compared with the experimental results<sup>12,13,21</sup>. In Fig. 3, the topmost curve is the Raman spectrum reported by Solozhenko *et al.*<sup>12</sup>; below it are the Raman frequencies reported by Werheit and Kuhlmann<sup>21</sup> and marked by vertical bars (|). The two curves below are our Raman spectra of  $\beta$ - $B_6O$  and  $\alpha$ - $B_6O$ . The experimental data correspond to normal isotopic abundance, and so do our calculations. Correspondingly, the atomic mass of boron in the calculations adopt the weighted average value, i.e. 10.811, which is based on the isotopic abundance of boron. As one could expect, the Raman spectra of  $\beta$ - $B_6O$  and  $\alpha$ - $B_6O$  are similar and match perfectly with the experimental spectra. For example, the Raman modes at 374, 499, 541, 737, 785, 833, 1088, 1119, 1141  $cm^{-1}$  are consistent with Solozhenko's results<sup>12</sup>. However, there are four Raman modes which are unique for  $\beta$ - $B_6O$ . The first two are computed to be at 516 and 533  $cm^{-1}$  (marked by letter A in Fig. 3), and Werheit and Kuhlmann indeed observed these two modes at 519 and 534  $cm^{-1}$ . The third mode is predicted to be at 630  $cm^{-1}$  (marked with letter B), and Werheit and Kuhlmann have indeed observed a Raman-active phonon at 627  $cm^{-1}$ . We note that  $\alpha$ - $B_6O$  does not have Raman-active modes between 570 and 700  $cm^{-1}$ , thus the one observed by Werheit and Kuhlmann at 627  $cm^{-1}$  cannot come from  $\alpha$ - $B_6O$ , but  $\beta$ - $B_6O$ . The fourth mode has the theoretical Raman frequency of 896  $cm^{-1}$  (marked with letter C), while  $\alpha$ - $B_6O$  has no Raman-active modes between 850 and 1000  $cm^{-1}$ . Thus, this mode is also unique to the  $\beta$ - $B_6O$  structure, and again seen in experiments: Solozhenko *et al.* observed Raman active phonon at 889  $cm^{-1}$ , and Werheit and Kuhlmann observed a Raman-active phonon at 902 (909)  $cm^{-1}$ . Moreover, Wang *et al.* also observed similar Raman spectra in their  $B_6O$  samples (see Fig. 1 in ref. 13). This analysis clearly shows that experimental samples contain  $\beta$ - $B_6O$ .

**Comparison of PDOSs and Gibbs free energy.** Comparing phonon densities of states (PDOSs) of  $\alpha$ - $B_6O$  and  $\beta$ - $B_6O$  at ambient pressure (Fig. 4), we once again see a great degree of similarity. In order to further confirm the stability of  $\beta$ - $B_6O$ , we have calculated the Gibbs free energy of  $\beta$ - $B_6O$  and  $\alpha$ - $B_6O$  as a function of temperature, shown in Supplementary Fig. S2. We conclude that  $\beta$ - $B_6O$  remains more stable than  $\alpha$ - $B_6O$  also when temperature is taken into account – and is even slightly stabilized by thermal effects.

Having found that  $\beta$ - $B_6O$  should be more stable than  $\alpha$ - $B_6O$ , and demonstrated that the two phases actually coexist in experimental samples, we ask a question: why is the synthetic compound mostly  $\alpha$ - $B_6O$ , instead of the more stable  $\beta$ - $B_6O$ ? While there can be no definitive answer at this point, we suggest that this may be because of the use of  $\alpha$ -rhombohedral-B ( $R\bar{3}m$ )<sup>9</sup> or  $\beta$ -rhombohedral-B ( $R\bar{3}m$ )<sup>22</sup> as a starting material (together with  $B_2O_3$ ) for synthesis of rhombohedral- $B_6O$ . Hubert *et al.*<sup>23</sup> used amorphous-B as the starting material, but they got not only  $B_6O$  but also  $B_6O$  twinning particles and some amorphous phases. And they observed a stacking of ABAB... around the planar defect, which is the same as  $\beta$ - $B_6O$  (We speculate it probably is  $\beta$ - $B_6O$ ). To obtain  $\beta$ -orthorhombic- $B_6O$ , one would need to crystallize it *from the melt* (preferably at high pressure, to increase its thermodynamic advantage over  $\alpha$ - $B_6O$ ), or use other phases of boron as precursors. Using  $Cmcm$ -B would be ideal, but this phase (just 11 meV/atom higher in energy than  $\alpha$ -B<sup>19</sup>) remains hypothetical, though likely to be eventually synthesized. Alternatively, the PVT method<sup>20</sup> could be used.

In summary, to our big surprise, *ab initio* structure prediction calculations discovered a new ground state for the widely studied superhard compound  $B_6O$  – our predicted  $\beta$ - $B_6O$  is more stable than experimentally known  $\alpha$ - $B_6O$ . The two phases are polytypes and have nearly the same densities ( $\beta$ - $B_6O$  is slightly denser), energies (slightly lower for  $\beta$ - $B_6O$ ), band gaps (slightly smaller and indirect, rather than direct, for  $\beta$ - $B_6O$ ), hardnesses ( $\beta$ - $B_6O$  is slightly harder) and phonon densities of states, but have important differences in Raman spectra. By comparing calculated and experimental Raman spectra, we demonstrated that the experimental samples are actually a mixture of  $\alpha$ - $B_6O$  and  $\beta$ - $B_6O$ . The discovery of  $\beta$ - $B_6O$  opens up new possibilities, in view of its greater stability, hardness and indirect band gap. Our findings also indicate possibilities of tuning the properties of  $B_6O$  by obtaining phase-pure samples (probably not obtained to date), and the possibility of metastable oxygen-deficient compounds based on  $\alpha$ - $B_6O$  or  $\beta$ - $B_6O$  – these can be obtained at high temperatures (where disordered oxygen vacancies will stabilize the structure) and low chemical potentials of oxygen.

## Methods

We used the *ab initio* evolutionary algorithm USPEX<sup>24–27</sup> to search for thermodynamically stable B-O compounds and their structures at ambient pressure. This methodology has shown its predictive power in many studies (e.g.,

ref. 17 and 27–29). All structures were relaxed; structure relaxations and total energy calculations were done using density functional theory (DFT) within the generalized gradient approximation (GGA)<sup>30</sup> as implemented in the VASP code<sup>31</sup>, with the projector-augmented wave method<sup>32</sup>. We used plane-wave kinetic energy cutoff of 600 eV, and sampled the Brillouin zone with uniform  $\Gamma$ -centered meshes of is  $2\pi \times 0.07 \text{ \AA}^{-1}$  resolution within structure search, and  $2\pi \times 0.04 \text{ \AA}^{-1}$  for subsequent highly precise relaxations and properties calculations. In order to confirm the relative stability of  $\alpha$ -B<sub>6</sub>O and  $\beta$ -B<sub>6</sub>O, we used local density approximation (LDA)<sup>33</sup> and HSE06 hybrid functional<sup>34</sup>. Phonon spectra was computed by PHONOPY<sup>35</sup> and VASP, and Raman spectra were calculated using the Fonari-Stauffer method<sup>36</sup>. Hardness was calculated with Chen model<sup>37</sup> and Lyakhov-Oganov model<sup>38</sup>. Elastic moduli were computed using Voigt-Reus-Hill averaging<sup>39</sup>.

## References

- Kaner, R. B., Gilman, J. J. & Tolbert, S. H. Designing Superhard Materials. *Science* **308**, 1268–1269 (2005).
- Kurakevych, O. O. Superhard phases of simple substances and binary compounds of the B-C-N-O system: from diamond to the latest results (a Review). *J. Superhard Mater.* **31**, 139–157 (2009).
- Wang, S. *et al.* Novel superhard B-C-O phases predicted from first principles. *Phys. Chem. Chem. Phys.* **18**, 1859–1863 (2016).
- Solozhenko, V. L. & Gregoryanz, E. Synthesis of superhard materials. *Mater. Today* **8**, 44–51 (2005).
- Bundy, F. P., Hall, H. T., Strong, H. M. & Wentorf, R. H. Man-Made Diamonds. *Nature* **176**, 51–55 (1955).
- Tian, Y. *et al.* Ultrahard nanotwinned cubic boron nitride. *Nature* **493**, 385–388 (2013).
- Hubert, H. *et al.* Icosahedral packing of B<sub>12</sub> icosahedra in boron suboxide (B<sub>6</sub>O). *Nature* **391**, 376–378 (1998).
- McMillan, P. F. New materials from high-pressure experiments. *Nat. Mater.* **1**, 19–25 (2002).
- He, D. W. *et al.* Boron suboxide: As hard as cubic boron nitride. *Appl. Phys. Lett.* **81**, 643–645 (2002).
- Mukhanov, V. A., Kurakevych, O. O. & Solozhenko, V. L. Thermodynamic model of hardness: Particular case of boron-rich solids. *J. Superhard Mater.* **32**, 167–176 (2010).
- Veprek, S., Zhang, R. F. & Argon, A. S. Mechanical properties and hardness of boron and boron-rich solids. *J. Superhard Mater.* **33**, 409–420 (2011).
- Solozhenko, V. L., Kurakevych, O. O. & Bouvier, P. First and second-order Raman scattering of B<sub>6</sub>O. *J. Raman Spectrosc.* **40**, 1078–1081 (2009).
- Wang, Z. W., Zhao, Y. S., Lazor, P., Annersten, H. & Saxena, S. K. *In situ* pressure Raman spectroscopy and mechanical stability of superhard boron suboxide. *Appl. Phys. Lett.* **86**, 041911 (2005).
- Kurakevych, O. O. & Solozhenko, V. L. Experimental study and critical review of structural, thermodynamic and mechanical properties of superhard refractory boron suboxide B<sub>6</sub>O. *J. Superhard Mater.* **33**, 421–428 (2011).
- An Q., Reddy K. M., Dong H., Chen M.-W., Oganov A. R. & Goddard W. A. Nanotwinned Boron Suboxide (B<sub>6</sub>O): New Ground State of B<sub>6</sub>O. *Nano Lett.* 10.1021/acs.nanolett.6b01204 (<http://dx.doi.org/10.1021/acs.nanolett.6b01204>) (2016).
- Decker, B. F. & Kasper, J. S. The crystal structure of a simple rhombohedral form of boron. *Acta Crystallogr. B* **12**, 503–506 (1959).
- Oganov, A. R. *et al.* Ionic high-pressure form of elemental boron. *Nature* **457**, 863–867 (2009).
- Zhu, Q., Oganov, A. R., Lyakhov, A. O. & Yu, X. Generalized evolutionary metadynamics for sampling the energy landscapes and its applications. *Phys. Rev. B* **92**, 024106 (2015).
- Pickard, C. J. & Needs, R. J. Ab initio random structure searching. *J. Phys.: Condens. Matter* **23**, 053201 (2011).
- Hofmann, D. *et al.* SiC-bulk growth by physical-vapor transport and its global modelling. *J. Cryst. Growth* **174**, 669–674 (1997).
- Werheit, H. & Kuhlmann, U. FTIR and FT Raman Spectra of B<sub>6</sub>O. *J. Solid State Chem.* **133**, 260–263 (1997).
- Solozhenko, V. L., Kurakevych, O. O., Turkevich, V. Z. & Turkevich, D. V. Phase Diagram of the B–B<sub>2</sub>O<sub>3</sub> System at 5 GPa: Experimental and Theoretical Studies. *J. Phys. Chem. B* **112**, 6683–6687 (2008).
- Hubert, H. *et al.* High-Pressure, High-Temperature Synthesis and Characterization of Boron Suboxide (B<sub>6</sub>O). *Chem. Mater.* **10**, 1530–1537 (1998).
- Oganov, A. R. & Glass, C. W. Crystal structure prediction using ab initio evolutionary techniques: Principles and applications. *J. Chem. Phys.* **124**, 244704 (2006).
- Oganov, A. R., Lyakhov, A. O. & Valle, M. How Evolutionary Crystal Structure Prediction Works—and Why. *Acc. Chem. Res.* **44**, 227–237 (2011).
- Lyakhov, A. O., Oganov, A. R., Stokes, H. T. & Zhu, Q. New developments in evolutionary structure prediction algorithm USPEX. *Comput. Phys. Commun.* **184**, 1172–1182 (2013).
- Zhu, Q., Oganov, A. R., Glass, C. W. & Stokes, H. T. Constrained evolutionary algorithm for structure prediction of molecular crystals: methodology and applications. *Acta Crystallogr. B* **68**, 215–226 (2012).
- Zhang, W. W. *et al.* Unexpected Stable Stoichiometries of Sodium Chlorides. *Science* **342**, 1502–1505 (2013).
- Dong, H., Oganov, A. R., Zhu, Q. & Qian, G.-R. The phase diagram and hardness of carbon nitrides. *Sci. Rep.* **5**, 9870 (2015).
- Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized Gradient Approximation Made Simple. *Phys. Rev. Lett.* **77**, 3865–3868 (1996).
- Kresse, G. & Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **47**, 558(R) (1993).
- Blöchl, P. E. Projector augmented-wave method. *Phys. Rev. B* **50**, 17953–17979 (1994).
- Perdew, J. P. & Zunger, A. Self-interaction correction to density-functional approximations for many-electron systems. *Phys. Rev. B* **23**, 5048–5079 (1981).
- Heyd, J., Scuseria, G. E. & Ernzerhof, M. Hybrid functionals based on a screened Coulomb potential. *J. Chem. Phys.* **124**, 219906 (2006).
- Togo, A., Oba, F. & Tanaka, I. First-principles calculations of the ferroelastic transition between rutile-type and CaCl<sub>2</sub>-type SiO<sub>2</sub> at high pressures. *Phys. Rev. B* **78**, 134106 (2008).
- Fonari, A. & Stauffer, S. [vasp\\_raman.py](https://github.com/raman-sc/VASP/) (<https://github.com/raman-sc/VASP/>, 2013).
- Chen, X.-Q., Niu, H., Li, D. & Li, Y. Modeling hardness of polycrystalline materials and bulk metallic glasses. *Intermetallics* **19**, 1275–1281 (2011).
- Lyakhov, A. O. & Oganov, A. R. Evolutionary search for superhard materials: Methodology and applications to forms of carbon and TiO<sub>2</sub>. *Phys. Rev. B* **84**, 092103 (2011).
- Hill R. The Elastic Behaviour of a Crystalline Aggregate. *Proc. Phys. Soc. London A* **65**, 349 (1952).
- Zhou, X. F., Tian, Y. & Wang, H. T. Large shear strength enhancement of gamma-boron by normal compression. *J. Superhard Mater.* **33**, 401–408 (2011).
- Kurakevych, O. O. & Solozhenko, V. L. Thermoelastic equation of state of boron suboxide B<sub>6</sub>O up to 6 GPa and 2700 K: Simplified Anderson-Grüneisen model and thermodynamic consistency. *J. Superhard Mater.* **36**, 270–278 (2014).

## Acknowledgments

H. F. D. and Q. G. W. gratefully acknowledges financial support from the National Natural Science Foundation of China (Grant No. 11547174 and No. 11504004) and the PhD Start-up Fund of Natural Science Foundation

of Guangdong Province, China (Grant No. 2016A030310352). A. R. O. thanks the Government of Russian Federation (grant No. 14.A12.31.0003), and Foreign Talents Introduction and Academic Exchange Program (No. B08040). Calculations were carried out in part at the Center for Functional Nanomaterials, Brookhaven National Laboratory, which is supported by the U.S. Department of Energy, Office of Basic Energy Sciences, under Contract No. DE-AC02-98CH10886. This work used the Extreme Science and Engineering Discovery Environment (XSEDE), which is supported by National Science Foundation grant number ACI-1053575.

### Author Contributions

H.F.D. performed all the calculations presented in this article with help from Q.Z. and X.F.Z. Research was designed by A.R.O., H.D. and A.R.O. wrote the first draft of the paper and A.R.O., Q.G.W., S.N.W., Z.H.W., J.Z., M.M.D.E., F.G.W. and Q.Z. contributed to revisions.

### Additional Information

**Supplementary information** accompanies this paper at <http://www.nature.com/srep>

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Dong, H. *et al.* Prediction of a new ground state of superhard compound B<sub>6</sub>O at ambient conditions. *Sci. Rep.* **6**, 31288; doi: 10.1038/srep31288 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016