



# Crystal structure of CdSO<sub>4</sub>(H<sub>2</sub>O): a redetermination

Chatphorn Theppitak<sup>a</sup> and Kittipong Chainok<sup>b\*</sup>

<sup>a</sup>Department of Chemistry, Faculty of Science, Naresuan University, Muang, Phitsanulok, 65000, Thailand, and <sup>b</sup>Department of Physics, Faculty of Science and Technology, Thammasat University, Khlong Luang, Pathum Thani, 12120, Thailand.  
\*Correspondence e-mail: kc@tu.ac.th

Received 31 August 2015; accepted 9 September 2015

Edited by M. Weil, Vienna University of Technology, Austria

The crystal structure of the title compound, cadmium sulfate monohydrate or poly[(μ<sub>2</sub>-aqua)(μ<sub>4</sub>-sulfato)cadmium], was redetermined based on modern CMOS (complementary metal oxide silicon) data. In comparison with the previous study [Bregeault & Herpin (1970). *Bull. Soc. Fr. Mineral. Cristallogr.* **93**, 37–42], all non-H atoms were refined with anisotropic displacement parameters and the hydrogen-bonding pattern unambiguously established due to location of the hydrogen atoms. In addition, a significant improvement in terms of precision and accuracy was achieved. In the crystal, the Cd<sup>2+</sup> cation is coordinated by four O atoms of four sulfate anions and two O atoms of water molecules, forming a distorted octahedral *trans*-[CdO<sub>6</sub>] polyhedron. Each sulfate anion bridges four Cd<sup>2+</sup> cations and each water molecule bridges two Cd<sup>2+</sup> cations, leading to the formation of a three-dimensional framework, with Cd···Cd separations in the range 4.0757 (2)–6.4462 (3) Å. O–H···O hydrogen-bonding interactions of medium strength between the coordinating water molecules and sulfate anions consolidate the crystal packing.

**Keywords:** crystal structure; redetermination; cadmium sulfate monohydrate; hydrothermal synthesis; hydrogen bonding.

**CCDC reference:** 1423357

## 1. Related literature

For the previous report on the structure of the title compound, see: Bregeault & Herpin (1970).

## 2. Experimental

### 2.1. Crystal data

CdSO<sub>4</sub>(H<sub>2</sub>O)

*M*<sub>r</sub> = 226.48

Monoclinic, *P*2<sub>1</sub>/*c*  
*a* = 7.6195 (3) Å  
*b* = 7.4517 (3) Å  
*c* = 8.1457 (3) Å  
*β* = 122.244 (1)°  
*V* = 391.17 (3) Å<sup>3</sup>

*Z* = 4  
Mo *Kα* radiation  
*μ* = 6.01 mm<sup>-1</sup>  
*T* = 296 K  
0.26 × 0.22 × 0.22 mm

### 2.2. Data collection

Bruker APEXII D8 QUEST CMOS diffractometer  
Absorption correction: multi-scan (*SADABS*; Bruker, 2014)  
*T*<sub>min</sub> = 0.701, *T*<sub>max</sub> = 0.746

17459 measured reflections  
1004 independent reflections  
958 reflections with *I* > 2σ(*I*)  
*R*<sub>int</sub> = 0.023

### 2.3. Refinement

*R*[*F*<sup>2</sup> > 2σ(*F*<sup>2</sup>)] = 0.012  
*wR*(*F*<sup>2</sup>) = 0.026  
*S* = 1.18  
1004 reflections  
72 parameters

2 restraints  
All H-atom parameters refined  
Δ*ρ*<sub>max</sub> = 0.29 e Å<sup>-3</sup>  
Δ*ρ*<sub>min</sub> = -0.33 e Å<sup>-3</sup>

**Table 1**

Hydrogen-bond geometry (Å, °).

<i>D</i> –H··· <i>A</i>	<i>D</i> –H	H··· <i>A</i>	<i>D</i> ··· <i>A</i>	<i>D</i> –H··· <i>A</i>
O5–H5A···O3 <sup>i</sup>	0.82 (2)	1.88 (2)	2.6958 (17)	170 (3)
O5–H5B···O2 <sup>ii</sup>	0.86 (2)	1.90 (2)	2.7530 (17)	173 (2)

Symmetry codes: (i)  $-x + 1, y - \frac{1}{2}, -z + \frac{1}{2}$ ; (ii)  $x, y - 1, z$ .

**Table 2**

Comparison of bond lengths (Å) in the current and the previous (Bregeault & Herpin, 1970) refinement of cadmium sulfate monohydrate.

For the previous refinement: *a* = 7.607, *b* = 7.541, *c* = 8.186 Å, *β* = 121.86° and reliability index *R* = 0.12.

Bond	Current refinement	Previous refinement
Cd1–O1 <sup>i</sup>	2.2417 (12)	2.21 (5)
Cd1–O2 <sup>ii</sup>	2.2530 (13)	2.27 (3)
Cd1–O3	2.2421 (12)	2.36 (5)
Cd1–O4 <sup>iii</sup>	2.3112 (12)	2.33 (3)
Cd1–O5 <sup>i</sup>	2.3210 (12)	2.24 (3)
Cd1–O5	2.4024 (12)	2.33 (3)
S1–O1	1.4703 (12)	1.50 (4)
S1–O2	1.4845 (12)	1.62 (6)
S1–O3	1.4831 (12)	1.45 (3)
S1–O4	1.4584 (12)	1.42 (4)

Symmetry codes: (i)  $x, -y + \frac{1}{2}, z + \frac{1}{2}$ ; (ii)  $-x, -y + 1, -z$ ; (iii)  $-x + 1, y - \frac{1}{2}, -z + \frac{1}{2}$ .

Data collection: *APEX2* (Bruker, 2014); cell refinement: *SAINTE* (Bruker, 2014); data reduction: *SAINTE*; method used to solve structure: coordinates taken from previous refinement; program(s) used to refine structure: *SHELXL2014* (Sheldrick, 2015); molecular graphics: *OLEX2* (Dolomanov *et al.*, 2009); software used to prepare material for publication: *OLEX2* and *pubCIF* (Westrip, 2010).

## Acknowledgements

The authors gratefully acknowledge the financial support provided by Thammasat University Research Fund under the TU Research Scholar.

---

Supporting information for this paper is available from the IUCr electronic archives (Reference: WM5211).

---

## References

Bregeault, J. M. & Herpin, P. (1970). *Bull. Soc. Fr. Mineral. Cristallogr.* **93**, 37–42.

Bruker (2014). *APEX2, SADABS and SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.

Dolomanov, O. V., Bourhis, L. J., Gildea, R. J., Howard, J. A. K. & Puschmann, H. (2009). *J. Appl. Cryst.* **42**, 339–341.

Sheldrick, G. M. (2015). *Acta Cryst.* **C71**, 3–8.

Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.

## supporting information

*Acta Cryst.* (2015). E71, i8–i9 [doi:10.1107/S2056989015016904]

## Crystal structure of $\text{CdSO}_4(\text{H}_2\text{O})$ : a redetermination


Chatphorn Theppitak and Kittipong Chainok

### S1. Synthesis and crystallization

The title compound was obtained serendipitously.  $\text{CdSO}_4 \cdot 8/3\text{H}_2\text{O}$  (0.256 g, 1 mmol) and 3,6-di-2-pyridyl-1,2,4,5-tetrazine (0.236 g, 1 mmol) dissolved in water (5 ml) were added to a 23 ml Teflon-lined autoclave and heated at 356 K for 5 days. The product was collected by filtration, washed with water and air-dried. Colourless block-shaped crystals of the title compound suitable for X-ray analysis were isolated.


### S2. Refinement

The same cell setting and atom numbering scheme as in the previous refinement (Bregeault & Herpin, 1970) were used. Starting coordinates for the atoms were also taken from the previous model. Hydrogen atoms of the water molecules were located from difference Fourier maps and were refined with an O—H distance restraint of 0.85 (2) Å.

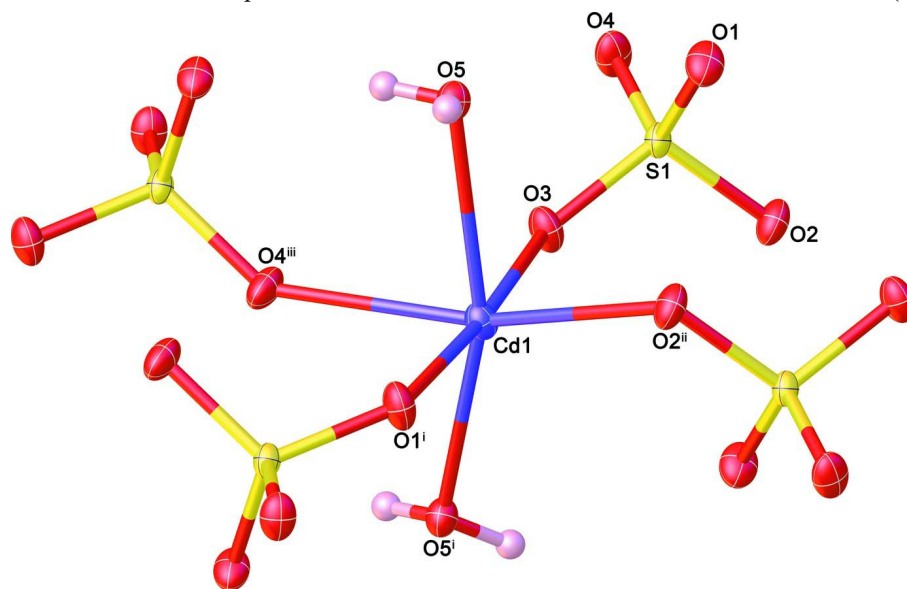

**Figure 1**

The coordination sphere around the  $\text{Cd}^{2+}$  cation with displacement ellipsoids drawn at the 50% probability level. [Symmetry codes: (i)  $x, 1/2 - y, 1/2 + z$ ; (ii)  $-x, 1 - y, -z$ ; (iii)  $1 - x, -1/2 + y, 1/2 - z$ ].

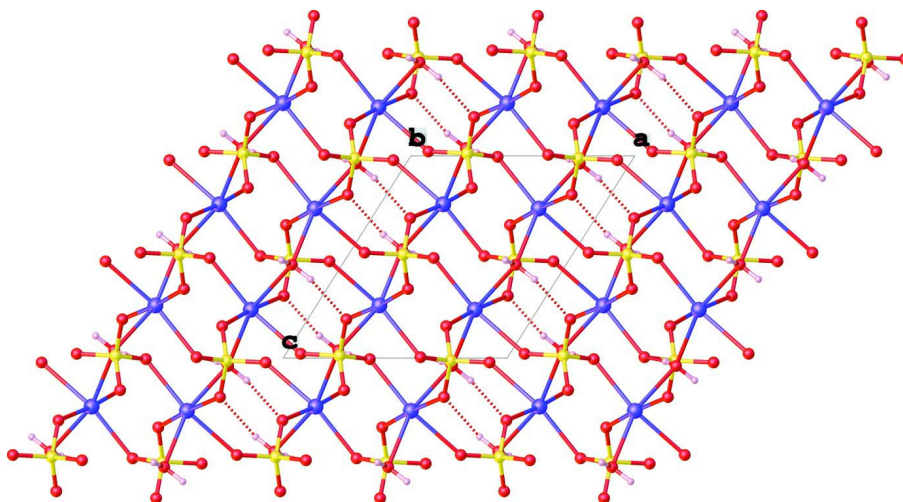**Figure 2**

The three-dimensional framework structure of the title compound in a view along the *b* axis. Dashed lines indicate intermolecular O—H...O hydrogen-bonding interactions.

### Poly[( $\mu_2$ -aqua)( $\mu_4$ -sulfato)cadmium]

#### Crystal data

CdSO<sub>4</sub>(H<sub>2</sub>O)

$M_r = 226.48$

Monoclinic,  $P2_1/c$

$a = 7.6195$  (3) Å

$b = 7.4517$  (3) Å

$c = 8.1457$  (3) Å

$\beta = 122.244$  (1)°

$V = 391.17$  (3) Å<sup>3</sup>

$Z = 4$

$F(000) = 424$

$D_x = 3.846$  Mg m<sup>-3</sup>

Mo  $K\alpha$  radiation,  $\lambda = 0.71073$  Å

Cell parameters from 9894 reflections

$\theta = 3.2$ – $30.5^\circ$

$\mu = 6.01$  mm<sup>-1</sup>

$T = 296$  K

Block, colourless

$0.26 \times 0.22 \times 0.22$  mm

#### Data collection

Bruker APEXII D8 QUEST CMOS  
diffractometer

Radiation source: microfocus sealed x-ray tube,  
Incoatec  $\mu$ us

GraphiteDouble Bounce Multilayer Mirror  
monochromator

Detector resolution: 10.5 pixels mm<sup>-1</sup>

$\omega$  and  $\varphi$  scans

Absorption correction: multi-scan  
(*SADABS*; Bruker, 2014)

$T_{\min} = 0.701$ ,  $T_{\max} = 0.746$

17459 measured reflections

1004 independent reflections

958 reflections with  $I > 2\sigma(I)$

$R_{\text{int}} = 0.023$

$\theta_{\max} = 28.7^\circ$ ,  $\theta_{\min} = 3.2^\circ$

$h = -10 \rightarrow 10$

$k = -10 \rightarrow 10$

$l = -10 \rightarrow 10$

#### Refinement

Refinement on  $F^2$

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.012$

$wR(F^2) = 0.026$

$S = 1.18$

1004 reflections

72 parameters

2 restraints

Primary atom site location: structure-invariant  
direct methods

Hydrogen site location: difference Fourier map

All H-atom parameters refined

$w = 1/[\sigma^2(F_o^2) + (0.0107P)^2 + 0.2955P]$

where  $P = (F_o^2 + 2F_c^2)/3$

$$(\Delta/\sigma)_{\max} = 0.001$$

$$\Delta\rho_{\max} = 0.28 \text{ e } \text{\AA}^{-3}$$

$$\Delta\rho_{\min} = -0.33 \text{ e } \text{\AA}^{-3}$$

*Special details*

**Experimental.** SADABS was used for absorption correction. wR2(int) was 0.0449 before and 0.0357 after correction. The Ratio of minimum to maximum transmission is 0.9396. The  $\lambda/2$  correction factor is 0.00150.

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

*Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )*

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Cd1	0.21887 (2)	0.26013 (2)	0.26053 (2)	0.01330 (5)
S1	0.25524 (6)	0.61729 (5)	0.01217 (5)	0.01018 (8)
O1	0.13754 (18)	0.50022 (16)	-0.15811 (17)	0.0183 (2)
O2	0.1103 (2)	0.75977 (15)	-0.00480 (19)	0.0169 (3)
O3	0.32756 (18)	0.51255 (16)	0.19211 (17)	0.0168 (2)
O4	0.43393 (18)	0.69973 (18)	0.02148 (18)	0.0184 (2)
O5	0.27603 (19)	0.09752 (16)	0.03844 (17)	0.0140 (2)
H5A	0.400 (3)	0.074 (4)	0.110 (3)	0.038 (7)*
H5B	0.216 (3)	-0.005 (2)	0.016 (3)	0.023 (6)*

*Atomic displacement parameters ( $\text{\AA}^2$ )*

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
Cd1	0.01176 (7)	0.01373 (7)	0.01200 (7)	-0.00165 (4)	0.00472 (5)	0.00087 (4)
S1	0.00809 (16)	0.00898 (17)	0.01063 (17)	0.00001 (13)	0.00310 (14)	0.00041 (13)
O1	0.0156 (6)	0.0170 (6)	0.0158 (6)	-0.0004 (5)	0.0041 (5)	-0.0054 (5)
O2	0.0122 (6)	0.0134 (6)	0.0206 (6)	0.0027 (4)	0.0058 (5)	-0.0018 (4)
O3	0.0155 (6)	0.0153 (6)	0.0147 (5)	-0.0019 (5)	0.0048 (5)	0.0046 (4)
O4	0.0101 (5)	0.0224 (6)	0.0198 (6)	-0.0022 (5)	0.0061 (5)	0.0047 (5)
O5	0.0120 (5)	0.0133 (5)	0.0145 (5)	-0.0008 (4)	0.0055 (5)	-0.0001 (4)

*Geometric parameters ( $\text{\AA}$ ,  $^\circ$ )*

Cd1—O1 <sup>i</sup>	2.2417 (12)	S1—O3	1.4831 (12)
Cd1—O2 <sup>ii</sup>	2.2530 (13)	S1—O4	1.4584 (12)
Cd1—O3	2.2421 (12)	O1—Cd1 <sup>iv</sup>	2.2417 (12)
Cd1—O4 <sup>iii</sup>	2.3112 (12)	O2—Cd1 <sup>ii</sup>	2.2530 (13)
Cd1—O5 <sup>i</sup>	2.3210 (12)	O4—Cd1 <sup>v</sup>	2.3112 (12)
Cd1—O5	2.4024 (12)	O5—Cd1 <sup>iv</sup>	2.3211 (12)
S1—O1	1.4703 (12)	O5—H5A	0.822 (17)
S1—O2	1.4845 (12)	O5—H5B	0.859 (16)
O1 <sup>i</sup> —Cd1—O2 <sup>ii</sup>	82.50 (4)	O1—S1—O3	109.76 (7)
O1 <sup>i</sup> —Cd1—O3	175.24 (4)	O3—S1—O2	109.52 (8)
O1 <sup>i</sup> —Cd1—O4 <sup>iii</sup>	89.31 (5)	O4—S1—O1	112.43 (8)

O1 <sup>i</sup> —Cd1—O5 <sup>i</sup>	92.57 (4)	O4—S1—O2	109.35 (7)
O1 <sup>i</sup> —Cd1—O5	88.62 (4)	O4—S1—O3	109.03 (7)
O2 <sup>ii</sup> —Cd1—O4 <sup>iii</sup>	161.94 (4)	S1—O1—Cd1 <sup>iv</sup>	131.81 (7)
O2 <sup>ii</sup> —Cd1—O5	80.22 (4)	S1—O2—Cd1 <sup>ii</sup>	116.42 (7)
O2 <sup>ii</sup> —Cd1—O5 <sup>i</sup>	117.97 (4)	S1—O3—Cd1	134.06 (7)
O3—Cd1—O2 <sup>ii</sup>	101.65 (4)	S1—O4—Cd1 <sup>v</sup>	140.91 (8)
O3—Cd1—O4 <sup>iii</sup>	86.05 (4)	Cd1 <sup>iv</sup> —O5—Cd1	119.27 (5)
O3—Cd1—O5	89.80 (4)	Cd1 <sup>iv</sup> —O5—H5A	109.7 (18)
O3—Cd1—O5 <sup>i</sup>	87.54 (4)	Cd1—O5—H5A	99.9 (18)
O4 <sup>iii</sup> —Cd1—O5 <sup>i</sup>	78.31 (4)	Cd1 <sup>iv</sup> —O5—H5B	113.3 (14)
O4 <sup>iii</sup> —Cd1—O5	83.53 (4)	Cd1—O5—H5B	108.6 (14)
O5 <sup>i</sup> —Cd1—O5	161.78 (6)	H5A—O5—H5B	104 (2)
O1—S1—O2	106.70 (7)		
O1—S1—O2—Cd1 <sup>ii</sup>	2.46 (10)	O3—S1—O1—Cd1 <sup>iv</sup>	-54.81 (11)
O1—S1—O3—Cd1	-23.82 (12)	O3—S1—O2—Cd1 <sup>ii</sup>	-116.29 (8)
O1—S1—O4—Cd1 <sup>v</sup>	-135.57 (12)	O3—S1—O4—Cd1 <sup>v</sup>	-13.61 (15)
O2—S1—O1—Cd1 <sup>iv</sup>	-173.39 (9)	O4—S1—O1—Cd1 <sup>iv</sup>	66.74 (12)
O2—S1—O3—Cd1	93.01 (11)	O4—S1—O2—Cd1 <sup>ii</sup>	124.30 (8)
O2—S1—O4—Cd1 <sup>v</sup>	106.10 (13)	O4—S1—O3—Cd1	-147.38 (10)

Symmetry codes: (i)  $x, -y+1/2, z+1/2$ ; (ii)  $-x, -y+1, -z$ ; (iii)  $-x+1, y-1/2, -z+1/2$ ; (iv)  $x, -y+1/2, z-1/2$ ; (v)  $-x+1, y+1/2, -z+1/2$ .

*Hydrogen-bond geometry* ( $\text{\AA}, ^\circ$ )

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O5—H5A $\cdots$ O3 <sup>iii</sup>	0.82 (2)	1.88 (2)	2.6958 (17)	170 (3)
O5—H5B $\cdots$ O2 <sup>vi</sup>	0.86 (2)	1.90 (2)	2.7530 (17)	173 (2)

Symmetry codes: (iii)  $-x+1, y-1/2, -z+1/2$ ; (vi)  $x, y-1, z$ .