

SCIENTIFIC REPORTS



OPEN

Light effect on Click reaction: Role of photonic quantum dot catalyst

Debkumar Nandi, Abu Taher, Rafique Ul Islam[†], Meenakshi Choudhary, Samarjeet Siwal & Kaushik Mallick

Received: 24 May 2016

Accepted: 17 August 2016

Published: 13 September 2016

Due to the light excitation, the valence band electron of the copper (I) sulfide quantum dot transfer to the conduction band and act as a scavenger of the terminal proton of the alkyne in the presence of organic azide with the formation of 1,4-disubstituted 1,2,3-triazoles, where the copper(I) species of Cu_2S act as a catalyst for the reaction. The above cycloaddition reaction between alkyne and azide is commonly known as the Click reaction. In this study, experiments were carried out under the exposure of ultra-violet and daylight and also dark environment. According to the original recommendation for the Click reaction, the role of the base was also considered for this experiment. We found that the effect of conduction band electron is more efficient than the recommended conventional base mediated reaction procedure.

Light induced catalytic organic transformation reaction is a new direction of research where the electronic property of the catalyst can play an important role with or without altering the mechanistic pathway and by eliminating one or more components (preferable hazardous) required for the reactions under normal condition.

Efforts have been made for the light induced metal oxide catalyzed organic transformation reactions where the conduction band electron has contribution for the reaction. The photocatalytic activity of these metal oxides is usually associated with non-selective free radical reaction processes. The photocatalytic oxidation of benzyl alcohol and its derivatives to the corresponding aldehydes proceeded at high conversion and selectivity on a TiO_2 photocatalyst under light irradiation in presence of oxygen atmosphere¹. The photocatalytic aerobic oxidation of benzyl amines to corresponding imines has also been reported on TiO_2 under UV-irradiation². Semiconductor Nb_2O_5 can also serve as a platform for the oxidation of alcohols through the light-induced formation of an excited electron in the conduction band and the positive hole in the valence band³.

The surface plasmon resonance effect of nanostructured materials also has substantial contribution on the light induced catalytic activity for various reactions. Unique optoelectronic and chemical properties of metal nanoparticles have drawn enormous attention of chemists, physicists and biologists for the fabrication of new generation devices. Some interesting reports on the Suzuki coupling reaction have been published based on the plasmonic effect of the gold nanoparticles at room temperature under visible light irradiation, where the role of gold is to increase the electron density of the catalytically active palladium to activate the aryl halides⁴⁻⁶. Similarly, photo induced charge transfer from graphitic carbon nitride to palladium is also reported for room temperature Suzuki coupling reaction⁷. The Suzuki reaction under ambient condition with equivalent amount of yield, as above, is also well documented in various reports⁸⁻¹⁰.

Motivated by the above reports, we have carried out the experiment to explore the photonic effect on the copper catalyzed azide-alkyne cycloaddition reactions^{11,12} for the preparation of 1,4-disubstituted regioisomeric 1,2,3-triazole compounds, also known as a Click reaction, which has a wide range of applications in organic synthesis, bio- and medicinal chemistry and materials science¹³. The Click reaction can be performed under an extremely wide variety of copper species¹⁴⁻¹⁹ in the presence of basic condition. In connection with our on-going research on the development of effective catalysts for organic transformations²⁰⁻²³, we have reported for both catalyst synthesis and cycloaddition reaction in a one-pot method²⁴ and Cu (I)-polyaminobenzoic acid catalyzed azide-alkyne cycloaddition reaction²⁵. Again, solvent-less microwave irradiation technique was also been reported for a 1,3-dipolar cycloaddition reaction between terminal alkynes and azides to synthesize 1,2,3-triazoles using polymer supported copper(I) composite, fabricated using a one-step chemical synthesis route under ambient condition²⁶. Protocols have also been reported for the photoinduced formation of Cu(I) using graphitic carbon nitride²⁷, fullerene²⁸ and bimetallic complex comprising a photosensitizer ruthenium

Department of Chemistry, University of Johannesburg, P.O. Box: 524, Auckland Park 2006, South Africa. [†]Present address: Department of Chemistry, Birla Institute of Technology, Mesra, Ranchi-835215, Jharkhand, India. Correspondence and requests for materials should be addressed to K.M. (email: kaushikm@uj.ac.za)

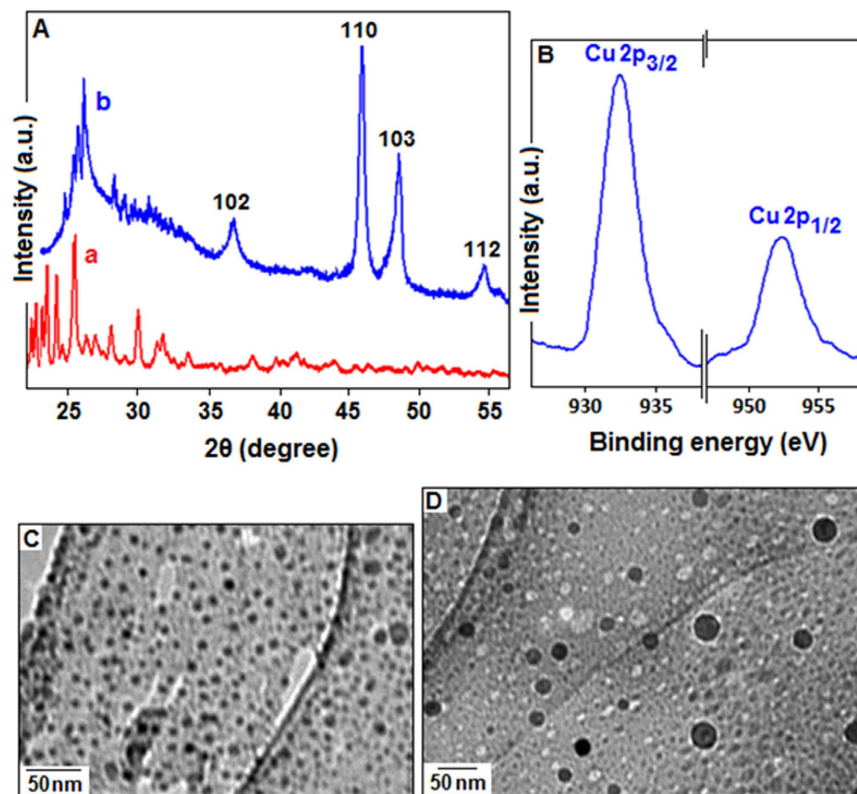


Figure 1. (A) The X-ray diffraction pattern of Cu(I)-polyaniline composite (a) and the polyaniline stabilized Cu_2S nanoparticles (b), where four broad peaks at 36.90° , 46.20° , 48.50° and 54.80° correspond to (102), (110), (103) and (112) lattice plane. (B) X-ray photoelectron spectroscopy for Cu2p shows the binding energies of the photoelectron peaks of Cu $2p_{3/2}$ and $2p_{1/2}$ are 932.5 eV and 952.5 eV, respectively, for the polymer stabilized Cu_2S . (C,D) TEM images, with two different magnification, of the polyaniline stabilized copper sulfide quantum dots.

unit²⁹ as a photocatalyst, from the Cu (II) precursor in the presence of amine as a base molecule for azide-alkyne cycloaddition reaction.

In this present communication, we report a convenient two step method for the synthesis of copper sulfide (Cu_2S) quantum dots where the first step involved the copper sulphate mediated synthesis of polyaniline with the formation of Cu(I)-polyaniline composite followed by the synthesis of Cu_2S nanoparticles by addition of thiourea, a source of sulfur, used for the synthesis of various metal sulfides³⁰. Copper(I) sulfide (Chalcocite) is a *p*-type semiconductor with a direct band gap of 1.8 eV and an indirect bandgap of 1.2 eV^{31–33} and has wide applications in solid-state electronics^{34–36}. In the literature, reports has been published for the synthesis of copper (I) sulfide by using different techniques^{37–42}.

The polyaniline stabilized Cu_2S nanoparticles, showed a high catalytic activity towards azide-alkyne 1, 3-dipolar cycloaddition reactions under ultra-violet (UV) irradiation condition. The following comparative studies were also performed under different photonic environment, such as, under daylight (DL) and daylight in presence of base (DLB) also under dark condition in absence of base (D) and dark condition in presence of base (DB), at room temperature.

Result

Mechanism of Cu_2S formation and characterization. Copper sulphate mediated synthesis of polyaniline is an example of ‘*in-situ* polymerization and composite formation’ (IPCF) technique, where the organic component (aniline) and the metal salt ($\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$) was chosen to facilitate such kind of reactions. The mechanism of the IPCF type of polymerization involve the release of electrons during the reaction between monomer and metal salt (oxidizing agent). In general, the released electrons reduce the metal ions, such as, gold, silver and palladium, with the formation of their corresponding nanoparticles^{43–45}. However, in the present experiment we found the reaction between aniline and copper sulphate evidences the formation of Cu(I) and polyaniline^{24,26}. Aniline has several amine as well as imine moieties which can act as a macro ligand⁴⁶, that coordinate with the Cu(I) species²⁴. The partial reduction of Cu(II) to Cu(I) species which is similar to the transformation from Cu(II) to Cu(I) species by terminal alkynes in the presence of tetramethylethylenediamine⁴⁷. The Cu(I)-polyaniline subsequently forms polyaniline stabilized Cu_2S quantum dots by the addition of thiourea.

The X-ray diffraction (XRD) patterns show (Fig. 1) the difference between Cu(I)-polyaniline and polyaniline stabilized Cu_2S . Figure 1(a) shows the X-ray diffraction of the Cu (I)-polyaniline composite and the pattern of the polyaniline generally depend on the length of the polymeric chains, oxidation states, synthetic routes, solvent


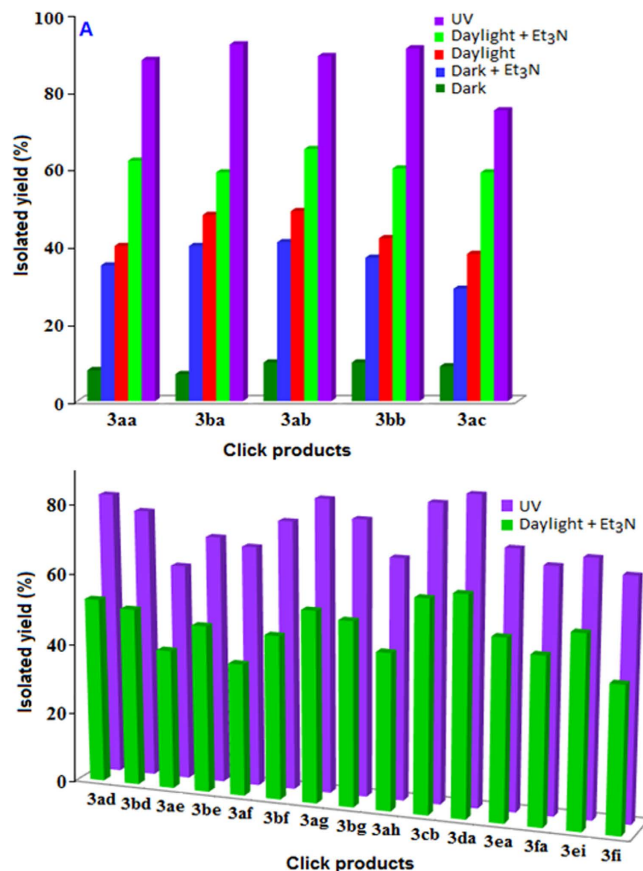


Figure 2. (A,B) Graphical representations show the azide-alkyne cycloaddition product (yield %) under different optical and basic condition.

used and oxidizing agent used for the synthesis. Figure 1(b) is the XRD for the polyaniline stabilized Cu₂S quantum dots where the pattern shows four broad peaks at 36.90°, 46.20°, 48.50° and 54.80° originating from (102), (110), (103) and (112) lattice plane, which are close to those reported for chalcocite Cu₂S⁴². X-ray photoelectron spectroscopy (XPS) analysis for the sample containing Cu₂S shows (Fig. 1B) the binding energies of the photoelectron peaks of Cu 2p_{3/2} and 2p_{1/2} are 932.5 eV and 952.5 eV, respectively, and is well consistent with the standard reference XPS spectrum of Cu 2p in Cu(I)⁴⁸. The transmission electron microscopy image showed the evidence for the formation of copper sulfide quantum dots (dark spots) with size distributions ranging from 10 to 40 nm (Fig. 1C,D). The synthesized material (polymer stabilized Cu₂S) was used as a catalyst for azide-alkyne cycloaddition reaction under different optical environment and the optimization study of the reaction was carried out as follows.

Optimization study for Click reaction. Optimization study has been shown in Figs 2A and 3. The reaction between azidomethyl benzene (**1a**) and ethynylbenzene (**2a**) yielding 1-benzyl-4-phenyl-1H-1,2,3-triazole (**3aa**) in presence of daylight was chosen as model reaction for the optimization study (Fig. 3, entry 1). Among the various solvents (CHCl₃, MeOH, MeOH:H₂O in different ratio, H₂O and THF) used for the reaction we found methanol appeared to be the best solvent yielding 40% of desired product at 120 min. In the next step, we have examined the effect of base on the performance of the reaction and tri-ethylamine (Et₃N) was recognized as optimized base for the above reaction as compared with other bases (K₂CO₃, Cs₂CO₃, KOH, N₂H₄·H₂O, di-ethyl ammine, di-isopropyl ammine) which resulted a yield of 62% of the product for the same period of time. Furthermore, we are interested to check the photonic effect on the reaction. We have performed the reaction under dark environment both in the absence and presence of base and obtained the product with the yield of 8 and 35%, respectively. Interestingly, when reaction was performed under UV-irradiation a yield of 88% product was obtained in the absence of base. A similar trend has also been observed for the **3ba**, **3ab**, **3bb**, **3ac** as represented graphically in Fig. 2A and in Fig. 3 (entries: 2–5) and discussed in the following section. It is pertinent to mention that a decrease of yield has been observed by addition of base under UV-irradiation for this reaction. In the absence of catalyst no coupled product was noticed.

Click reaction under different optical conditions. The cycloaddition reaction using polyaniline stabilized Cu₂S as catalyst in the presence and absence of Et₃N has been described below under different photonic conditions for other azide and alkyne molecules for the period of 120 min (Fig. 3: entries 2–5, Fig. 2A). In the presence of UV, azidomethyl benzene (**1a**) reacted with 1-ethynyl-4-methoxybenzene (**2b**)

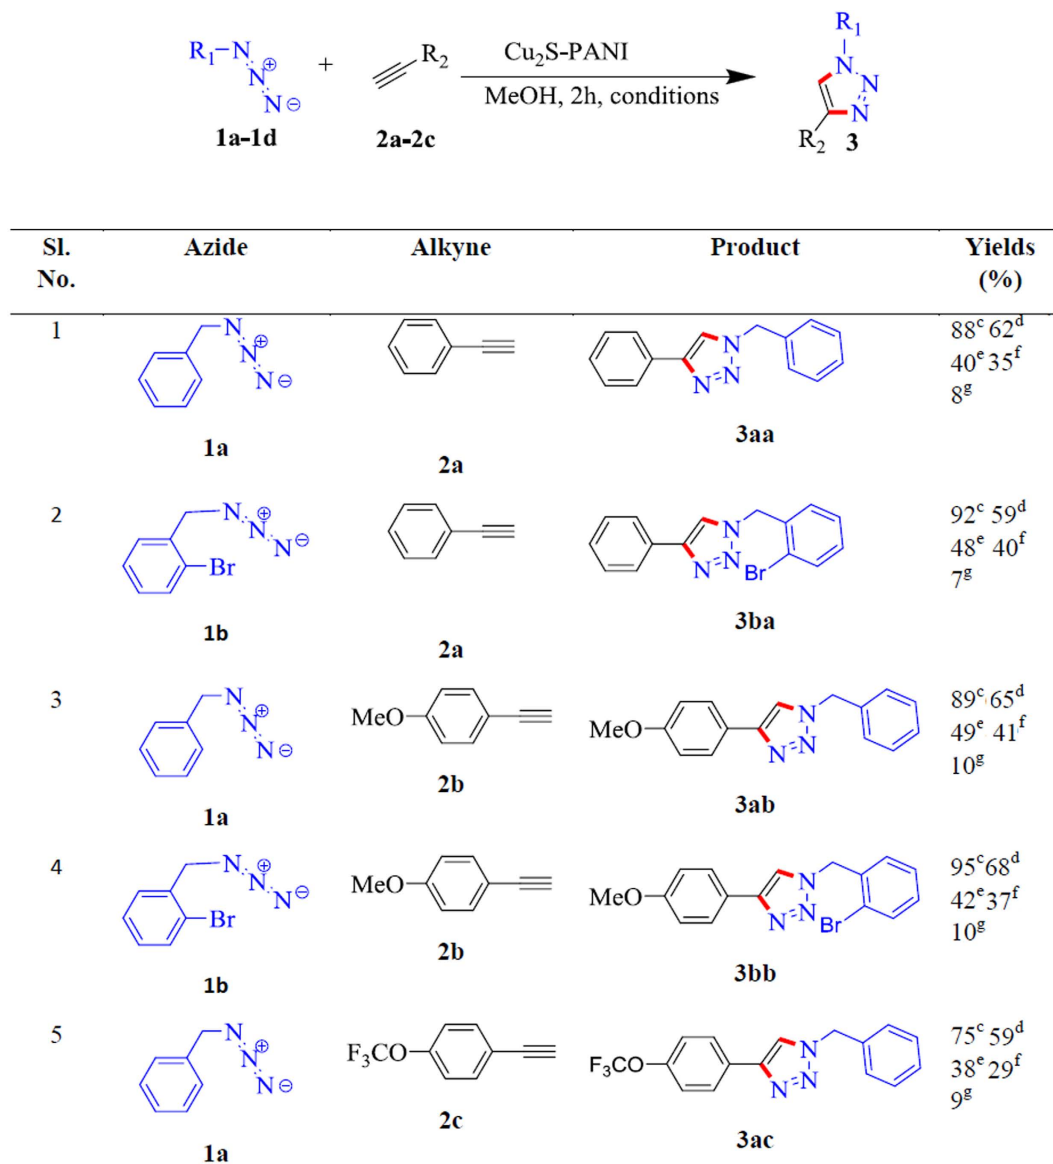

^aConditions: azide (1 mmol), alkyne (1 mmol), MeOH (4 mL), Cu₂S (5 mol% of Cu), 2h.
^bIsolated yields: depicted graphically in figure 1. c=UV, d = DLB (daylight in presence of base), e=DL (daylight without base), f=DB(dark condition in presence of the base) and g = D (dark condition).

Figure 3. Optimization of Photonic effect and effect of base on click products^{a,b}.

and 1-ethynyl-4-(trifluoromethoxy) benzene (**2c**) produced the cycloaddition products of 1-benzyl-4-(4-methoxyphenyl)-1H-1,2,3-triazole (**3ab**) and 1-benzyl-4-(4-(trifluoromethoxy) phenyl)-1H-1,2,3-triazole (**3ac**) with the yield of 89 and 75%, respectively. Under the DL condition, when the above reactions were performed in the presence and absence of base the product **3ab** with 65 and 49% of yields, respectively, and the product **3ac** with 59 and 38% of yields, respectively, were obtained. Again, when the above reactions were carried out under the dark condition both in the presence and absence of base the product **3ab** with 41 and 10% of yields, respectively, and **3ac** with 29 and 9% of yields, respectively, has been obtained. A similar effect has also been documented when 1-(azidomethyl)-2-bromobenzene (**1b**) reacted with ethynylbenzene (**2a**) and 1-ethynyl-4-methoxybenzene (**2b**), the formation of cycloaddition products 1-(2-bromobenzyl)-4-phenyl-1H-1,2,3-triazole (**3ba**) and 1-(2-bromobenzyl)-4-(4-methoxyphenyl)-1H-1,2,3-triazole (**3bb**) with the yield 92 and 95%, under UV exposure, followed by 59 and 68% of yields under DLB, respectively, were obtained. It is also important to mention that under DL 48 and 42% of yield of **3ba** and **3bb**, respectively, have been produced. Under the darkroom environment, 40 and 7% of **3ba** and 29 and 9% of **3ac** has been formed in the absence and presence of base, respectively. Based on the above studies, we found the maximum amount of products were formed under UV-irradiation followed by under DLB condition.

$$\text{R}_1\text{-N}_3 + \text{R}_2 \xrightarrow[\text{MeOH, 2h, conditions}]{\text{Cu}_2\text{S-PANI}} \text{R}_1\text{-N=N-R}_2$$

Sl. No.	Azide	Alkyne	Product	Yields (%)
6				81 ^c 53 ^d
7				77 ^c 51 ^d
8				62 ^c 40 ^d
9				62 ^c 40 ^d
10				69 ^c 53 ^d
11				77 ^c 47 ^d
12				84 ^c 55 ^d
13				79 ^c 53 ^d
14				69 ^c 45 ^d
15				85 ^c 61 ^d
16				88 ^c 61 ^d
17				74 ^c 52 ^d
18				70 ^c 48 ^d
19				73 ^c 55 ^d
20				69 ^c 42 ^d

^cReaction Conditions: azide (1 mmol), alkyne (1 mmol), MeOH (4 mL), Cu₂S (5mol% of Cu), 2h. ^dIsolated yields: depicted graphically in figure 2. ^c=UV; ^d=DLB (daylight + base).

Figure 4. Substrate scope and comparative studies of yields of the click products in day light with tri-ethyl ammine and under base free UV irradiation^{a,b}.

Versatility of the title reaction. We also have explored the versatility of the reaction for the structurally diverse azides and alkynes under two different conditions where the maximum yields were obtained and the results are summarized in Fig. 4 and also graphically (Fig. 2B). More than 75% of yield of thiophene substituted

triazole (**3ad** and **3bd**) product has been achieved due to the coupling between 3-ethynylthiophene and azide under UV irradiation whereas in the presence of base under daylight condition the maximum 53% of yield has been obtained for the same reaction (Fig. 4, entries: 6 and 7). For the reactions between azides with terminal alkyne group containing aliphatic alcohols (entries: 8, **3ae** and 9, **3be**), five (entries: 10, **3af** and 11, **3bf**) and six (entries: 12, **3ag** and 13, **3bg**) membered cyclic alcohols where UV-irradiation plays the superior role as compared with the base accompanied daylight condition for the formation of substituted triazole products. In the presence of UV, terminal alkyne derivatized unsaturated lactone (**2h**) with azide molecule (**1a**) also forms cycloaddition product, 4-((1-benzyl-1H-1,2,3-triazol-4-yl)methoxy)-6-methyl-2H-pyran-2-one (**3ah**), with the yield of 69% whereas the daylight mediated reaction under basic condition generate 45% of product (entry 14). Substituted ethynylbenzene with azidobenzene and ethynylbenzene with azidonaphthalene forms cycloaddition products of 4-(4-methoxyphenyl)-1-phenyl-1H-1,2,3-triazole (**3cb**) and 1-(naphthalen-1-yl)-4-phenyl-1H-1,2,3-triazole (**3da**), respectively, entries 15 and 16, where we have again observed the supremacy of the ultra-violet effect regarding the amount of product formation.


Examples with the sugar molecules. Azide-alkyne 1,3-dipolar cycloaddition reaction, serves as the most powerful tool for the creation of complex architecture at the molecular level. The unique properties of the carbohydrate moiety and the advantages of chemo- and regio-selective nature of the Click chemistry produce biologically relevant glycoconjugate type of molecules for various biological and pharmaceutical applications. In the current study we have synthesized glucose and galactose substituted azide molecule and we have found that the substituted azide molecule coupled with alkyne molecules to form β -D-glucopyranoside and β -D-galactopyranoside substituted 1,2,3-triazole moieties, respectively, under the exposure of the ultra-violet light in the presence of Cu_2S catalyst. A comparative study shows (Fig. 4, entries 17–20 and Fig. 2B, **3ea**, **3fa**, **3ei** and **3fi**) that the reaction under the UV exposure again showed the superior result than the reaction under daylight condition in the presence of triethyl amine. When 1-azido-2,3,4,6-tetra-O-acetyl- β -D-glucopyranose (**1e**) and 1-azido-2,3,4,6-tetra-O-acetyl- β -D-galactopyranose (**1f**) reacted with the alkyne molecule, ethynylbenzene (**2a**), the coupled product 4-Phenyl-1-(2,3,4,6-tetra-O-acetyl- β -D-glucopyranosyl)-1H-1,2,3-triazole (**3ea**), entry: 17, and 4-Phenyl-1-(2,3,4,6-tetra-O-acetyl- β -D-galactopyranosyl)-1H-1,2,3-triazole (**3fa**), entry: 18, obtained with the yield 90% and 70%, under UV and DLB conditions, respectively. A similar trend has also been found when 1-ethynyl-4-methylbenzene was used as alkyne molecule (entry: 19, **3ei**, and 20, **3fi**).
















Click reaction for single-step multicomponent system. In general, copper catalysed azide-alkyne cycloaddition reaction is a two component reaction system where the organic azides need to be synthesized in advance. Single-step reactions have many advantages in comparison with multi-step reactions, primarily due to environmental and economic considerations, and therefore the design of a single-step multicomponent reaction system has attracted lot of attention from the research groups in various areas of organic synthesis. For organic reactions the steps are not as efficient enough as enzymatic reactions. So, the strategy should be adopted carefully for the preparation of complex substances in which controlled formation of bonds occurs in a single step from the readily available precursors. For the current study, we also directed our attention to develop an efficient one-pot methodology that uses alkyl halides and sodium azide for direct cycloaddition with alkynes in the presence of Cu_2S catalyst under the UV-irradiation. The Cu_2S catalyst again performed well as a catalyst in methanol under the UV-irradiation to give the desired products (Fig. 5, entries 21–25, **5aj**, **5bj**, **5ak**, **5al** and **5am**, respectively) with the isolated yields ranging from 54 to 65% within 3 h. In presence of base under daylight condition, a longer time (5 h) required to achieve the equivalent amount of yield for the corresponding products.

Mechanistic discussion for the reaction. In general, Cu (I) catalyzed cycloaddition reaction, between azide and alkyne, happened under basic condition and illustrated in Fig. 6. Initially, a π -complex has formed between the Cu (I) and the alkyne molecule, results in the lowering of the pKa value of the terminal acetylene, [11, 12] which facilitate the proton abstraction mechanism from the C–H bond in the presence of a base, triethyl amine used as a base in this current study, Fig. 6(I), with the formation of copper-acetylidine complex followed by the addition of the azide molecule to form an intermediate complex. The intermediate complex subsequently forms the 1,2,3-triazole after the protonation and elimination of the catalyst.

In this study Cu_2S was used as the active catalyst and when the reaction was carried out under the exposure of UV-irradiation in absence of base the highest amount of cycloaddition was obtained. The photon energy from the ultraviolet source, deep UV (UV-C), is within the range of 6.53–4.43 eV (considering the wavelength between 190–280 nm) and which is the sufficient amount of energy to transfer an electrons from the valence band to the conduction band of Cu_2S quantum dot. The conduction band electron act as a scavenger of the terminal proton of the alkyne with the formation of copper-acetylidine complex, Fig. 6(II), and follows the similar mechanistic route as mentioned above. We also found that the daylight has a prominent effect on the reaction as the photon energy value of daylight is in between 3.26–1.59 eV (considering all the visible wavelength range from 380–780 nm). This photon energy is sufficient to facilitate the electron migration from the valence band to the conduction band and follow the Fig. 6(II). The difference in yield for the cycloaddition reaction between the ultra-violet and daylight condition can be justified as follows. As the photon energy of the UV-light is higher than the daylight so the higher population of electron would be available in the conduction band of Cu_2S for scavenging the terminal proton of the alkyne that consequently produce higher amount of cycloaddition product. The effect of daylight in presence of base shows the enhancement of the cycloaddition product than the daylight alone which is due to the combined effect of conduction band electron and lone pair electron of the base, both can participate the proton abstraction mechanism.

The Click reaction was also performed under darkroom environment in the presence and absence of base to find out the photonic effect on the reaction performance. Comparative study showed the daylight condition in



Sl. No.	Benzyl bromide	Alkyne	Product	Yields (%)
21	 4a	 2j	 5aj	58
22	 4b	 2j	 5bj	54
23	 4a	 2k	 5ak	61
24	 4a	 2l	 5al	65
25	 4a	 2m	 5am	63

^aReaction conditions: Benzyl bromide (1 mmol), NaN₃ (78 mg, 1.2 mmol), Alkyne (1 mmol), MeOH (4 mL), Cu₂S (5 mol% of Cu), 3h. ^bIsolated yields.

Figure 5. Substrate scope for multicomponent click products under UV irradiation^{a,b}.

absence of base performs slightly better than the presence of base under the dark condition, which again indicates the conduction band electron plays the dominant role for Cu₂S catalyzed cycloaddition reaction. In the absence of a base (under darkroom environment) the formation of little cycloaddition product (~10%) has also been noticed possible due to the presence of uncoordinated emeraldine form of polyaniline (emeraldine base) which act as the role of base to facilitate the reaction.

It is pertinent to mention that a decrease of yield has been observed by addition of base under UV-irradiation for this reaction and the mechanism of this event is included elsewhere in the manuscript. A decrease of product yield has been observed when the reaction was carried out under UV irradiation in presence of the base (triethyl amine) where the base can act as a hole-scavenger and also coordinate with the Cu(I) to form a complex⁴⁹. The formation of the new complex may limit the transfer mechanism of electron from valence band to conduction band which consequently has an adverse effect on the yield.

Conclusion

In this report, we have presented a 'two-step method' for the synthesis of polyaniline stabilized copper sulfide nanoparticles where the first step involved the formation of Cu (I)-polyaniline composite followed by the formation of polymer stabilized Cu₂S photonic quantum dots. In the presence of ultra-violet radiation (high photon energy) the conduction band electron of the copper sulfide involves in the azide-alkyne cycloaddition reaction and plays the crucial role by participating in the 'proton abstraction mechanism' by scavenging the terminal proton of the alkyne molecule. The similar kind of photonic effect is also possible due to the presence of daylight (low photon energy) as the copper sulfide is a low band gap semiconductor. Click reaction under UV-illumination condition has the potential advantage on the environmental point of view, where the use of hazardous base molecule

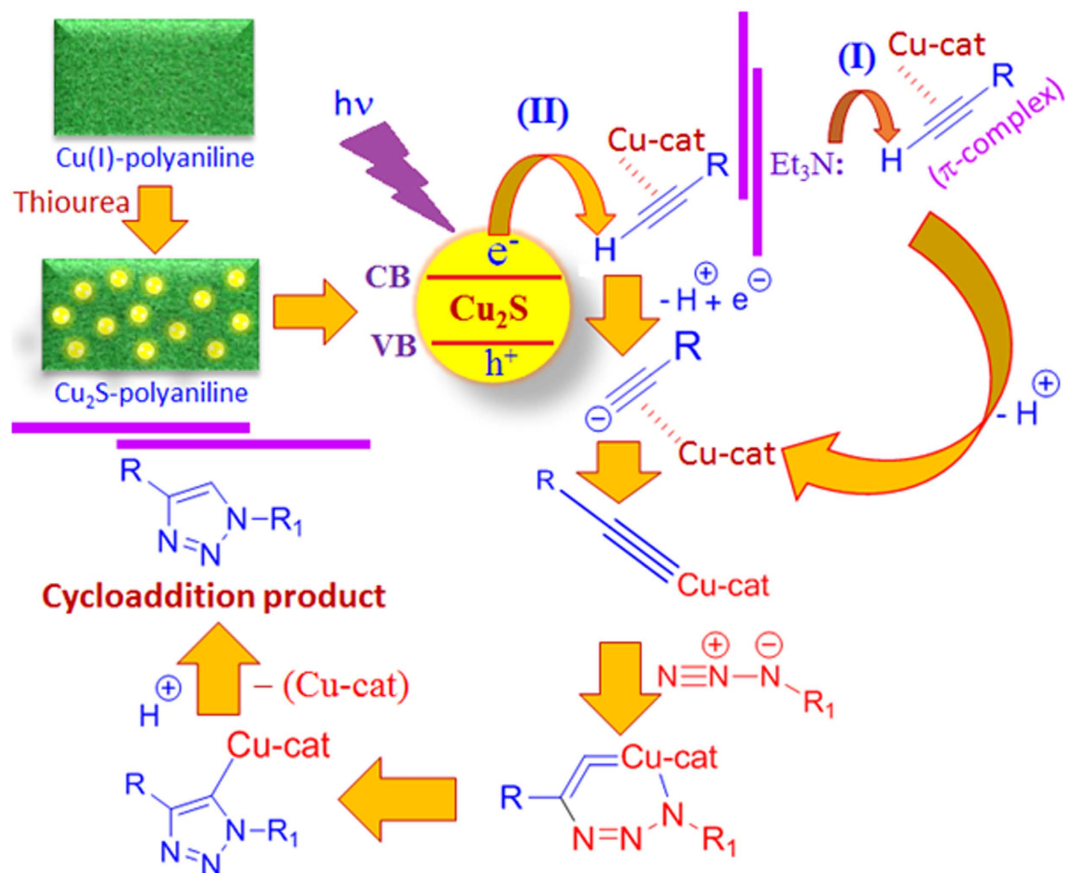


Figure 6. Schematic mechanism for the Cu₂S catalysed azide-alkyne cycloaddition reaction in presence of base, Et₃N, (I) and under UV or daylight irradiation (II) condition.

can be avoided. Another significant aspect for the UV-light mediated reaction is the rapid product formation. Photo-generated conduction band electron mediated reaction is faster than the conventional base molecule mediated reaction. It is also important to mention that many of the organic functional groups are base sensitive thus the use of base molecule in Click reaction may be an obstacle for achieving the targeted product. Present method has given an alternative route to those substrates for the targeted Click products and be beneficial for the reactions. The combined physical (photonic) and chemical (catalytic) properties of the Cu₂S has changed the original reaction mechanism of the Click reaction by creating an alternatives route in the presence of light energy.

Methods

Preparation of Cu₂S-polyaniline composite. In a typical experiment, 0.093 g of aniline (10⁻² mol dm⁻³) was dissolved in 10 mL methanol. To this solution, 0.250 g of CuSO₄ · 5H₂O in 10 mL of water (10⁻² mol dm⁻³) was added slowly under continuous stirring conditions. During the addition, the solution took on a green color, while at the end, a greenish precipitation was formed, indicates the formation of Cu (I)-polyaniline composite (24, 26), at the bottom of the conical flask. To this reaction mixture 5 mL of thiourea (10⁻¹ mol dm⁻³) was added and allowed to stir for 1 h. Entire reaction was performed under ambient condition. The dark brown precipitate material was allowed to settle for 30 min after which the colloidal solution was taken from the bottom of the conical flask and pipetted onto lacey, carbon-coated, nickel mesh grids for transmission electron microscopy (TEM) study. The remaining portion of the compound was dried under vacuum at 60 °C for XRD, XPS measurements and also applied as a catalyst for the azide-alkyne cycloaddition reaction.

General Procedure for the Click reaction. In a 25 mL round bottom flask, azide 1 (1 equivalent), alkyne 2 (1 equivalent), were taken in 4 ml methanol. To this reaction mixture the dried polyaniline stabilized Cu₂S catalyst (2 mg, 5 mol % of Cu) was added and stirred under the following conditions: (a) under UV light in the absence of base (b) under daylight with or without and Et₃N (1 equivalent) and (c) under dark environment with or without and Et₃N (1 equivalent) in 25 mL quartz reactor. The reaction mixture was stirred for 2 h and progress of the reaction was monitored using thin layer chromatography (TLC) technique. After completion, the reaction mixture was filtered and dried under residue pressure. The dried gummy mass was and diluted with 20 mL of distilled water; the solution was extracted with ethyl acetate. The organic layer was separated and dried over anhydrous MgSO₄. Combined organic layer was concentrated in vacuum to give the corresponding triazole which was further purified by recrystallization or by column chromatography technique.

Click reaction under luminescence condition. Philips UV-C (TUV T8) (germicidal) lamp has been used as the source of UV-light and a hand-held optical power meter (Newport) showed the optical intensity value was 40 mW/cm² adjacent to the quartz reaction chamber. The optical intensity was also measured during the daylight experiment and was found a value of 3.5 mW/cm² inside the fume hood.

General Procedure for one pot multicomponent click reaction. In a 25 mL quartz reactor, benzyl bromide **4** (1 equivalent), alkyne **2** (1 equivalent) and NaN₃ (78 mg, 1.2 equivalent) were taken in 4 ml methanol. To this reaction mixture Cu₂S catalyst (5 mol% of Cu) was added and stirred under UV light for 3 h. After completion, the reaction mixture was filtered and dried under residue pressure. The dried gummy mass was and diluted with 20 mL of distilled water; the solution was extracted with ethyl acetate. The organic layer was separated and dried over anhydrous MgSO₄. Combined organic layer was concentrated in vacuum to give the corresponding triazole which was further purified by recrystallization or by column chromatography technique. (NMR spectra for all the synthesized Click products are supplied in the supplementary information).

References

- Higashimoto, S. *et al.* Selective photocatalytic oxidation of benzyl alcohol and its derivatives into corresponding aldehydes by molecular oxygen on titanium dioxide under visible light irradiation. *J. Catal.* **266**, 279–285 (2009).
- Lang, X. J., Ji, H. W., Chen, C. C., Ma, W. H. & Zhao, J. C. Selective formation of imines by aerobic photocatalytic oxidation of amines on TiO₂. *Angew. Chem., Int. Ed.* **50**, 3934–3937 (2011).
- Shishido, T. *et al.* Mechanism of photo-oxidation of alcohol over Nb₂O₅. *J. Phys. Chem. C.* **113**, 18713–18718 (2009).
- Zhang, S. *et al.* Visible-light-activated Suzuki–Miyaura coupling reactions of aryl chlorides over the multifunctional Pd/Au/porous nanorods of CeO₂ catalysts. *ACS Catal.* **5**, 6481–6488 (2015).
- Wang, F. *et al.* Plasmonic harvesting of light energy for Suzuki coupling reactions. *J. Am. Chem. Soc.* **135**, 5588–5601 (2013).
- Sarina, S. *et al.* Enhancing catalytic performance of palladium in gold and Palladium alloy nanoparticles for organic synthesis reactions through visible light irradiation at ambient temperatures. *J. Am. Chem. Soc.* **135**, 5793–5801 (2013).
- Li, X. H., Baar, M., Blechert, S. & Antonietti, M. Facilitating room-temperature Suzuki coupling reaction with light: Mott-Schottky photocatalyst for C–C-coupling. *Sci. Rep.* **3**, 1743 (2013).
- Yang, J., Liu, S., Zheng, J. & Zhou, J. Room-temperature Suzuki–Miyaura coupling of heteroaryl chlorides and tosylates. *Euro. J. Org. Chem.* **2012**, 6248–6259 (2012).
- Li, S., Lin, Y., Cao, J. & Zhang, S. Guanidine/Pd(OAc)₂-catalyzed room temperature Suzuki cross-coupling reaction in aqueous media under aerobic conditions. *J. Org. Chem.* **72**, 4067–4072 (2007).
- Jawale, D. V. *et al.* Room temperature Suzuki coupling of aryl iodides, bromides, and chlorides using a heterogeneous carbon nanotube–palladium nanohybrid catalyst. *Catal. Sci. Technol.* **5**, 2388–2392 (2015).
- Tornøe, C. W., Christensen, C. & Meldal, M. J. Peptidotriazoles on solid phase: [1,2,3]-triazoles by regioselective copper(I)-catalyzed 1,3-dipolar cycloadditions of terminal alkynes to azides. *J. Org. Chem.* **67**, 3057–3064 (2002).
- Rostovtsev, V. V., Green, L. G., Fokin, V. V. & Sharpless, B. K. A stepwise Huisgen cycloaddition process: copper (I)-catalyzed regioselective “ligation” of azides and terminal alkynes. *Angew. Chem. Int. Ed.* **14**, 2708–2711 (2002).
- Meldal, M. & Tornøe, C. W. Cu-catalyzed azide-alkyne cycloaddition. *Chem. Rev.* **108**, 2952–3015 (2008).
- Lee, L. V. *et al.* Potent and highly selective inhibitor of human α -1,3-fucosyltransferase via Click chemistry. *J. Am. Chem. Soc.* **125**, 9588–9589 (2003).
- Siemsen, P., Livingston, R. C. & Diederich, F. Acetylenic coupling: A powerful tool in molecular construction. *Angew. Chem. Int. Ed.* **39**, 2632–2657 (2000).
- Bock, V. D., Hiemstra, H. & Van Maarseveen, J. H. CuI-catalyzed alkyne–azide “Click” cycloadditions from a mechanistic and synthetic perspective. *Eur. J. Org. Chem.* **1**, 51–68 (2006).
- DuránPachón, L., Van Maarseveen, J. H. & Rothenberg, G. Click chemistry: copper clusters catalyse the cycloaddition of azides with terminal alkynes. *Adv. Synth. Catal.* **347**, 811–815 (2005).
- Yamada, Y. M. A., Sarkar, S. M. & Uozumi, Y. Amphiphilic self-assembled polymeric copper catalyst to parts per million levels: Click chemistry. *J. Am. Chem. Soc.* **134**, 9285–9290 (2012).
- Sarkar, A., Mukherjee, T. & Kapoor, S. PVP-stabilized copper nanoparticles: a reusable catalyst for “Click” reaction between terminal alkynes and azides in nonaqueous solvents. *J. Phys. Chem. C* **112**, 3334–3340 (2008).
- Islam, R. *et al.* Conjugated polymer stabilized palladium nanoparticles as a versatile catalyst for Suzuki cross-coupling reactions for both aryl and heteroaryl bromide systems. *Catal. Sci. & Tech.* **1**, 308–315 (2011).
- Islam, R., Mahato, S., Shukla, S., Witcomb, M. & Mallick, K. Palladium-poly (3-aminoquinoline) hollow-sphere composite: Application in Sonogashira coupling reactions. *ChemCatChem* **5**, 2453–2461 (2013).
- Mahato, S., Islam, R., Acharya, C., Witcomb, M. & Mallick, K. Polymer-stabilized palladium nanoparticles for the chemoselective transfer hydrogenation of α , β -unsaturated carbonyls: Single-step bottom-up approach. *ChemCatChem* **6**, 1419–1426 (2014).
- Taher, A., Nandi, D., Choudhary, M. & Mallick, K. Suzuki coupling reaction in the presence of polymer immobilized palladium nanoparticles: a heterogeneous catalytic pathway. *New J. Chem.* **39**, 5589–5596 (2015).
- Islam, R., Taher, A., Choudhary, M., Siwal, S. & Mallick, K. Polymer immobilized Cu (I) formation and azide-alkyne cycloaddition: A one pot reaction. *Sci. Rep.* **5**, 9632 (2015).
- Islam, R., Taher, A., Choudhary, M., Witcomb, M. & Mallick, K. A polymer supported Cu (I) catalyst for the ‘Click reaction’ in aqueous media. *Dalton Trans.* **44**, 1341–1349 (2015).
- Taher, A., Nandi, D., Islam, R., Choudhary, M. & Mallick, K. Microwave assisted azide–alkyne cycloaddition reaction using polymer supported Cu(I) as a catalytic species: A solvent-less approach. *RSC Adv.* **5**, 47275–47283 (2015).
- Dadashi-Silab, S., Kiskan, B., Antonietti, M. & Yagci, Y. Mesoporous graphitic carbon nitride as a heterogeneous catalyst for photoinduced copper (I) catalyzed azide-alkyne cycloaddition. *RSC Adv.* **4**, 52170–52173 (2014).
- Taskin, O., Yilmaz, G. & Yagci, Y. Fullerene attached polymeric homogeneous/heterogeneous photo-activators for visible-light induced CuAAC Click reactions. *ACS Macro Lett.* **5**, 103–107 (2016).
- Kumar, P. *et al.* Visible light Assisted photocatalytic [3 + 2] Azide-Alkyne ‘Click’ reaction for the synthesis of 1,4-substituted 1,2,3-Triazoles using a novel bimetallic Ru–Mn complex. *ACS Sustainable Chem. Eng.* **4**, 69–75 (2016).
- Hendricks, M., Campos, M., Cleveland, G., Plante, I. & Owen, J. A tunable library of substituted thiourea precursors to metal sulfide nanocrystals. *Science* **348**, 1226–1230 (2015).
- Carbone, I. *et al.* Pulsed chemical vapor deposition of Cu₂S into a porous TiO₂ matrix. *J. Vac. Sci. Technol. A* **29**, 051505 (2011).
- Zhuang, Z., Peng, Q., Zhang, B. & Li, Y. Controllable synthesis of Cu₂S nanocrystals and their assembly into a super-lattice. *J. Am. Chem. Soc.* **130**, 10482–10483 (2008).
- Liu, G., Schulmeyer, T., Brötz, J., Klein, A. & Jaegermann, W. Interface properties and band alignment of Cu₂S/CdS thin film solar cells. *Thin Solid Films* **477**, 431–432 (2003).
- Chen, J. *et al.* Field emission from crystalline copper sulphide nanowire arrays. *Appl. Phys. Lett.* **80**, 3620 (2002).

35. Lee, H., Yoon, S. W., Kim, E. J. & Park, J. *In-situ* growth of copper sulfide nanocrystals on multi-walled carbon nanotubes and their application as novel solar cell and amperometric glucose sensor materials. *Nano Lett.* **7**, 778–784 (2007).
36. Chen, L. *et al.* Nonvolatile memory devices with Cu₂S and Cu-Pc bi-layered films. *Appl. Phys. Lett.* **91**, 073511 (2007).
37. Larsen, T. H., Sigman, M., Ghezelbash, A., Doty, R. C. & Korgel, B. A. Solvent-less synthesis of copper sulfide nanorods by thermolysis of a single source thiolate-derived precursor. *J. Am. Chem. Soc.* **125**, 5638–5639 (2003).
38. Mousavi-Kamazani, M., Zarghami, Z. & M. Salavati-Niasari, M. Facile and novel chemical synthesis, characterization, and formation mechanism of copper sulfide (Cu₂S, Cu₂S/CuS, CuS) nanostructures for increasing the efficiency of solar cells. *J. Phys. Chem. C.* **120**, 2096–2108 (2016).
39. Bulakhe, R. *et al.* Chemical synthesis of 3D copper sulfide with different morphologies for high performance supercapacitors application. *RSC Adv.* **6**, 14844–14851 (2016).
40. Liu, Z., Liang, J., Xu, D., Lu, J. & Qian, Y. A facile chemical route to semiconductor metal sulfide nanocrystal super-lattices. *Chem Commun.* **23**, 2724–2725 (2004).
41. Zhang, H. T., Wu, G. & Chen, X. H. Large-scale synthesis and self-assembly of monodisperse hexagon Cu₂S nanoplates. *Langmuir* **21**, 4281–4282 (2005).
42. Li, S. *et al.* Synthesis and assembly of monodisperse spherical Cu₂S nanocrystals. *J. Colloid Interface Sci.* **330**, 483–487 (2009).
43. Mallick, K., Witcomb, M., Dinsmore, A. & Scurrrell, M. Polymerization of aniline by auric acid: Formation of gold decorated polyaniline nanoballs. *Macromol Rapid Commun.* **26**, 232–235 (2005).
44. Choudhary, M., Siwal, S., Islam, R., Witcomb, M. & Mallick, K. Polymer stabilized silver nanoparticle: An efficient catalyst for proton-coupled electron transfer reaction and the electrochemical recognition of biomolecule. *Chem. Phys. Lett.* **608**, 145–151 (2014).
45. Mallick, K., Witcomb, M., Dinsmore, A. & Scurrrell, M. Fabrication of a metal nanoparticles and polymer nanofibers composite material by an *in-situ* chemical synthetic route. *Langmuir* **21**, 7964–7967 (2005).
46. Likhar, P. R. *et al.* Highly efficient and reusable polyaniline-supported palladium catalysts for open-air oxidative heck reactions under base- and ligand-free conditions. *Adv. Synth. Catal.* **350**, 1968–1974 (2008).
47. Zhang, G. *et al.* Direct observation of reduction of Cu(II) to Cu(I) by terminal alkynes. *J. Am. Chem. Soc.* **136**, 924–926 (2014).
48. Wagner, C. *et al.* NIST standard reference database 20, Version 3.4. (<http://srdata.nist.gov/xps>) (2003).
49. Yoke III, J., Weiss, J. F. & Tollin, G. Reactions of Triethylamine with Copper(I) and Copper(II) Halides. *Inorg. Chem.* **2**, 1210–1216 (1963).

Acknowledgements

The authors (D.K.N., A.T., R.U.I., M.C., S.S. and K.M.) acknowledge financial support from the University of Johannesburg. D.K.N. and S.S. acknowledge financial support from Global Excellence and Stature fellowship from the University of Johannesburg. M.C. and K.M. acknowledge financial support from the National Research Foundation (NRF), South Africa.

Author Contributions

D.K.N., A.T. and R.U.I. conceived the experiments and have equal contribution. M.C. and S.S. performed the characterization of the catalyst. K.M. designed and directed the study and also wrote the manuscript.

Additional Information

Supplementary information accompanies this paper at <http://www.nature.com/srep>

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Nandi, D. *et al.* Light effect on Click reaction: Role of photonic quantum dot catalyst. *Sci. Rep.* **6**, 33025; doi: 10.1038/srep33025 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016