

Article

New Antibacterial Silver(I) Coordination Polymers Based on a Flexible Ditopic Pyrazolyl-Type Ligand

Aurel Tăbăcaru ^{1,*}, Claudio Pettinari ², Mariana Bușilă ³ and Rodica Mihaela Dinică ^{1,*}

¹ Faculty of Sciences and Environment, Department of Chemistry, Physics and Environment, “Dunarea de Jos” University of Galati, 111 Domneasca Street, 800201 Galați, Romania

² School of Pharmacy, University of Camerino, Via Madonna delle Carceri 9, 62032 Camerino MC, Italy; claudio.pettinari@unicam.it

³ Department of Materials Science and Engineering, Faculty of Engineering, “Dunarea de Jos” University of Galati, 111 Domneasca Street, 800201 Galați, Romania; mariana.ibanescu@ugal.ro

* Correspondence: aurel.tabacaru@ugal.ro (A.T.); rodinica@ugal.ro (R.M.D.)

Received: 1 October 2019; Accepted: 10 October 2019; Published: 15 October 2019



Abstract: In the last two decades, a tremendous amount of attention has been directed towards the design of antibacterial silver(I)-based materials, including coordination polymers (CPs) built up with a great variety of oxygen and nitrogen-containing ligands. Herein, a family of six new silver(I)-based CPs, having the general stoichiometric formula $[Ag(H_2DMPMB)(X)]$ ($X = NO_3$, **1**; CF_3CO_2 , **2**; CF_3SO_3 , **3**; BF_4 , **4**; ClO_4 , **5**; and PF_6 , **6**) and incorporating the flexible ditopic pyrazolyl-type ligand 4,4'-bis((3,5-dimethyl-1H-pyrazol-4-yl)methyl)biphenyl (H_2DMPMB), has been prepared by the chemical precipitation method involving the reaction of silver(I) salts with H_2DMPMB in the 1:1 molar ratio, in alcohols, or acetonitrile at room temperature for two-hours. The new silver(I)-based polymeric materials were characterized by means of Fourier transform infrared spectroscopy (FTIR), elemental analysis (EA), and thermogravimetric analysis (TGA), allowing for the proposition that their structures comprise one-dimensional chains, with the silver(I) ions mostly assuming a T-shaped stereochemistry completed by the exo-bidentate ligands and counter-anions. The obtained silver(I) CPs showed a remarkable light insensitivity and stability in the air, are insoluble in water and in most common organic solvents, and possess appreciable thermal stabilities spanning the range 250–350 °C. The antibacterial activity of the obtained silver(I) CPs was tested against the Gram-negative bacteria *Escherichia coli* (*E. coli*) and Gram-positive bacteria *Staphylococcus aureus* (*S. aureus*) using the Tetrazolium/Formazan test (TTC), by measuring the bacterial viability at different time intervals. The complete reduction of both bacterial strains occurred after 24 h of exposure to all silver(I) CPs, the bacterial viability values for *S. aureus* reaching 8% for compounds **3**, **5**, and **6** after only two-hours.

Keywords: silver; coordination polymers; nitrogen ligands; thermal stability; antibacterial activity

1. Introduction


Coordination polymers (CPs) [1–4], and the subset of metal-organic frameworks (MOFs) [5–7], represent the vast class of inorganic–organic hybrid materials, which are made of metal ions or metal-based clusters and polydentate ligands connected through coordination bonds, which develop into 1-D, 2-D, and 3-D infinite structures. CPs and MOFs have gained a special place in fields of industrial, technological, economical, and environmental interest thanks to the great variety of functional properties so far achieved, ranging from gas storage and separation [8] to heterogeneous catalysis [9], luminescence [10], sensing [11], magnetism [12], conductivity [13], and biomedicine [14]. For their successful construction, the most typically used organic ligands have been rationally chosen

from the class of poly(carboxylates) [15,16], poly(azolates) [17–19], pyrazines and bipyridines [15,16,20], and phosphonates [21].

Special attention has also been offered, over the past two decades, to the synthesis of silver(I)-based CPs, which were found to show fascinating structural motifs [22–25] and interesting properties, ranging from photoluminescence [26,27] to electrical conductivity [28,29], magnetism [30,31], guest exchange and sorption [32,33], and catalysis [34,35]. The successful preparation of such polymeric materials has taken the judicious management of various factors into consideration, such as the reaction conditions [36], the silver-to-ligand ratio [37], the stereochemistry of silver ion coupled with the ligands functionality [38], and the nature of counter-anions [39].

In the last decade, silver(I)-based CPs, built up either with rigid or flexible nitrogen and oxygen-donor ligands, have gained popularity due to their potential as antibacterial agents, which unlike the soluble silver(I) complexes [40], have arisen to minimize the problem of reducing, as much as possible, the amount of silver(I) ions released into the environment, thus relying on their higher stabilities and very low solubilities. The pioneering works by Nomiya et al. have reported positive results of antimicrobial and antifungal activities of the azolyl-based silver(I) CPs [Ag(im)] [41], [Ag(1,2,3-tz)(PPh₃)₂] and [Ag(1,2,4-tz)(PPh₃)₂] [42], [Ag(tetz)(PPh₃)₂] [43] (im = 1,3-imidazole, 1,2,3-tz = 1,2,3-triazolate, 1,2,4-tz = 1,2,4-triazolate, tetz = 1,2,3,4-tetrazolate, PPh₃ = triphenylphosphine). These first results have then stimulated the preparation and characterization of new, other types of silver(I) CPs with promising results regarding the antibacterial activity against a wide spectrum of Gram-negative and Gram-positive pathogenic microorganisms. In this context, various prototypes of silver(I) CPs have been tested in the form of powders [44–49], polymer-based composites [50–54], and surface coatings [55–59], exhibiting remarkable biocidal effects, either in suspension or by contact.

In the past few years, we have shown that the flexible ditopic pyrazolyl-type ligand 4,4'-bis((3,5-dimethyl-1H-pyrazol-4-yl)methyl)biphenyl (H₂DMPMB, Scheme 1) [60], and its shorter analogue 1,4-bis((3,5-dimethyl-1H-pyrazol-4-yl)methyl)benzene (H₂BDMPX) [61], were able to generate cobalt(II)-, zinc(II)-, cadmium(II)-, and copper(I)-containing CPs displaying high thermal stabilities, coupled with either pro-porous properties or photoluminescence. Herein, we sought to further explore the coordinative potentiality of the flexible ligand H₂DMPMB towards the preparation of new antibacterial silver(I)-based CPs with different counter-anions, which are remarkably light-insensitive and highly insoluble.

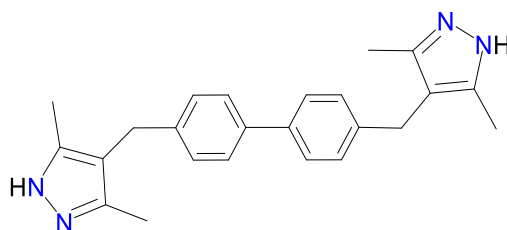

Scheme 1. Structure of 4,4'-bis((3,5-dimethyl-1H-pyrazol-4-yl)methyl)biphenyl (H₂DMPMB).

The present paper is, therefore, aimed at synthesizing, through a simple chemical precipitation and high-yielding method, a family of six new silver(I)-based CPs incorporating the flexible ligand H₂DMPMB with the general stoichiometric formula [Ag(H₂DMPMB)(X)] (X = NO₃, **1**; CF₃CO₂, **2**; CF₃SO₃, **3**; BF₄, **4**; ClO₄, **5**; and PF₆, **6**). Only two examples of silver nitrate and perchlorate complexes with the ethyl homologues of the flexible H₂DMPMB ligand were reported a few years ago [62]. Recently, two photoluminescent silver nitrate 1D coordination polymers with the bitopic ligand 1,1,2,2-tetra(pyrazol-1-yl)ethane were structurally characterized [63]. While Fourier transform infrared spectra (FTIR) were exhaustively analyzed to propose the structure of all the obtained silver(I) polymeric compounds, thermogravimetric analysis (TGA) revealed their appreciable thermal stabilities, lying in the range 250–350 °C. The antibacterial activity of the obtained silver(I) CPs against the Gram-negative bacteria *Escherichia coli* (*E. coli*) and Gram-positive bacteria *Staphylococcus aureus*

(*S. aureus*) was tested using the Tetrazolium/Formazan test (TTC), by measuring the bacterial viability at different time intervals.

2. Materials and Methods

2.1. General

- All reagents and solvents were purchased from Sigma-Aldrich (Darmstadt, Germany) and Alfa Aesar (Kandel, Germany), and were used as received.
- The ligand 4,4'-bis((3,5-dimethyl-1H-pyrazol-4-yl)methyl)biphenyl (H₂DMPMB) was synthesized according to an optimized method previously reported in the literature [60].
- FTIR spectra were recorded from 4000 to 650 cm⁻¹ with a Perkin-Elmer Spectrum 100 instrument (Perkin-Elmer, Shelton, CT, USA) by total reflectance on a ZnSe crystal. In the following, the IR bands are classified as very weak (vw), weak (w), medium (m), strong (s), and very strong (vs).
- Elemental analyses (C, H, N, and S) were performed in-house with Fisons Instruments 1108 CHNS-O Elemental Analyzer (Thermo Scientific, Waltham, MA, USA). Before performing the analytical characterization, all samples were dried in vacuo (50 °C, ~10⁻⁴ bar) until a constant weight was reached.
- Thermogravimetric analyses (TGA) were carried out from 30 to 700 °C in a N₂ stream with a Perkin-Elmer STA 6000 simultaneous thermal analyzer (Perkin-Elmer, Shelton, CT, USA) with the heating rate of 7 °C/min.

2.2. Syntheses

[Ag(H₂DMPMB)(NO₃)] (1). H₂DMPMB (0.093 g, 0.25 mmol) was dissolved in 30 mL of methanol under gentle warming (45 °C). Then, AgNO₃ (0.085 g, 0.5 mmol) was added. The resulting white suspension was left under stirring at room temperature for 2 h, obtaining a white precipitate that was filtered off, washed twice with methanol, and dried under a vacuum. Yield: 75%. **1** is insoluble in chlorinated solvents, alcohols, acetone, acetonitrile, dimethylformamide, dimethylsulfoxide, and water. IR (cm⁻¹): 3199(mbr) ν(N-H); 3100-3000(vw) ν(C-H_{aromatic}), 3000-2900(w) ν(CH₃, CH₂), 1748(w), 1582(w), 1528(w), 1499(w) ν(C=C+C=N), 1387(vs) ν_{asym}(NO₃), 1347(vs) ν_{asym}(NO₃), 1210(w), 1006(w), 905(w), and 754(vs). Elemental analysis calcd. for C₂₄H₂₆AgN₅O₃ (FW = 540.36 g/mol): C, 53.34; H, 4.85; N, 12.96%. Found: C, 53.03; H, 4.67; N, 12.38%.

[Ag(H₂DMPMB)(CF₃CO₂)] (2). H₂DMPMB (0.093 g, 0.25 mmol) was dissolved in 30 mL of ethanol under gentle warming (45 °C). Then, AgCF₃CO₂ (0.111 g, 0.5 mmol) was added. The resulting white suspension was left under stirring at room temperature for 4 h, obtaining a white precipitate that was filtered off, washed twice with ethanol, and dried under a vacuum. Yield: 75%. **2** is insoluble in chlorinated solvents, alcohols, acetone, acetonitrile, dimethylformamide, dimethylsulfoxide, and water. IR (cm⁻¹): 3186(mbr), ν(N-H), 3092(vw), 3028(vw) ν(C-H_{aromatic}), 2921(vw) ν(CH₃, CH₂), 1668(vs) ν(C=O), 1579(vw), 1528(vw), 1494(m) ν(C=C+C=N), 1431(m), 1201-1140(vs) ν(CF₃CO₂), 1058(m), 1005(m), 905(m), 806(m), 719(s). Elemental analysis calc. for C₂₆H₂₆AgF₃N₄O₂ (FW = 591.38 g/mol): C, 52.81; H, 4.43; and N, 9.47%. Found: C, 52.35; H, 4.25; N, 9.08%.

[Ag(H₂DMPMB)(CF₃SO₃)] (3). H₂DMPMB (0.093 g, 0.25 mmol) was dissolved in 30 mL of ethanol under gentle warming (45 °C). Then, AgCF₃SO₃ (0.129 g, 0.5 mmol) was added. The resulting white suspension was left under stirring at room temperature for 4 h, obtaining a white precipitate that was filtered off, washed twice with ethanol, and dried under a vacuum. Yield: 70%. **3** is insoluble in chlorinated solvents, alcohols, acetone, acetonitrile, dimethylformamide, dimethylsulfoxide, and water. IR (cm⁻¹): 3233(mbr), ν(N-H), 3024(vw) ν(C-H_{aromatic}), 2923(vw) ν(CH₃, CH₂), 1586(w), 1526(vw), 1498(w) ν(C=C+C=N), 1240(vs), 1224(vs), 1162(vs), 1029(vs) ν(CF₃SO₃), 905(w), 839(w), and 759(m). Elemental analysis calcd. for C₂₅H₂₆AgF₃N₄O₃S (FW = 627.43 g/mol): C, 47.86; H, 4.18; N, 8.93; S, 5.11%. Found: C, 47.85; H, 3.92; N, 8.34; S, 4.91%.

[Ag(H₂DMPMB)(BF₄)] (4). H₂DMPMB (0.093 g, 0.25 mmol) was dissolved in 30 mL of acetonitrile under gentle warming (45 °C). Then, (MeCN)₄AgBF₄ (0.179 g, 0.5 mmol) was added. The resulting white suspension was left under stirring at room temperature for 4 h, obtaining a white precipitate that was filtered off, washed twice with acetonitrile, and dried under a vacuum. Yield: 80%. **4** is insoluble in chlorinated solvents, alcohols, acetone, acetonitrile, dimethylformamide, dimethylsulfoxide, and water. IR (cm⁻¹): 3316(mbr) ν(N–H), 3025(vw) ν(C–H_{aromatic}), 2923(vw) ν(CH₃, CH₂), 1587(w), 1526(vw), 1494(w) ν(C=C+C=N), 1057(vs), 1005(vs) ν(BF₄), 904(w), 845(m), 799(w), 768(m), and 692(mbr). Elemental analysis calcd. for C₂₄H₂₆AgBF₄N₄ (FW = 565.17 g/mol): C, 51.00; H, 4.64; N, 9.91%. Found: C, 50.86; H, 4.45; N, 9.36%.

[Ag(H₂DMPMB)(ClO₄)] (5). H₂DMPMB (0.093 g, 0.25 mmol) was dissolved in 30 mL of ethanol under gently warming (45 °C). Then, AgClO₄ (0.104 g, 0.5 mmol) was added. The resulting white suspension was left under stirring at room temperature for 2 h, obtaining a white precipitate that was filtered off, washed twice with ethanol, and dried under a vacuum. Yield: 85%. **5** is insoluble in chlorinated solvents, alcohols, acetone, acetonitrile, dimethylformamide, dimethylsulfoxide, and water. IR (cm⁻¹): 3267(mbr) ν(N–H), 3025(vw) ν(C–H_{aromatic}), 2923(vw) ν(CH₃, CH₂), 1587(w), 1525(vw), 1495(w) ν(C=C+C=N), 1075(vs), 1040(vs) ν(ClO₄), 845(m), 769(m), and 687(mbr). Elemental analysis calcd. for C₂₄H₂₆AgClN₄O₄ (FW = 577.82 g/mol): C, 49.89; H, 4.54; N, 9.70%. Found: C, 49.52; H, 4.46; N, 9.51%.

[Ag(H₂DMPMB)(PF₆)] (6). H₂DMPMB (0.093 g, 0.25 mmol) was dissolved in 30 mL of ethanol under gently warming (45 °C). Then, AgPF₆ (0.125 g, 0.5 mmol) was added. The resulting white suspension was left under stirring at room temperature for 3 h, obtaining a white precipitate that was filtered off, washed twice with ethanol, and dried under a vacuum. Yield: 90%. **6** is insoluble in chlorinated solvents, alcohols, acetone, acetonitrile, dimethylformamide, dimethylsulfoxide, and water. IR (cm⁻¹): 3410(mbr) ν(N–H), 3027(vw) ν(C–H_{aromatic}), 2926(vw) ν(CH₃, CH₂), 1585(w), 1525(vw), 1495(w) ν(C=C+C=N), 828(vs) ν(PF₆), 768(m), and 667(mbr). Elemental analysis calcd. for C₂₄H₂₆AgF₆N₄P (FW = 623.33 g/mol): C, 46.25; H, 4.20; N, 8.99%. Found: C, 46.22; H, 3.98; N, 8.50%.

2.3. Bacteria Strain and Growth Conditions

The pathogenic bacteria, *Escherichia coli* ATCC 25922 and *Staphylococcus aureus* ATCC 25923 (clinical isolates), used as test microorganisms for the antibacterial activity study, were collected from the Microbial Culture Collection (Sf. Andrei Hospital of Galati, Romania). The cultivation medium for *E. coli* and *S. aureus* was Brain Heart Infusion Broth (BHI, Merck, Darmstadt, Germany). Bacterial culture for antibacterial activity was prepared by picking the colony in BHI agar plates and incubated for 24 h, followed by suspension in an appropriate medium (9 mL). The culture was grown aerobically for 20 h at 37 °C. For antibacterial assay, 1 mL of bacterial culture was diluted in 9 mL BHI medium to 10⁶ CFU/mL.

2.4. Antibacterial Activity

TTC (2,3,5-triphenyl tetrazolium chloride, Merck) was prepared by dissolving the powder in sterile water (5 mg/mL) at room temperature. In the presence of bacteria, TTC was reduced to red formazan, which was directly proportional to the activity and viability of the bacterial cells [64]. The TTC test was evaluated as a qualitative antibacterial method. For the susceptibility test using TTC, 1 mL of silver(I) CPs (suspended in sterile water, 5 mg/mL), 1 mL of AgNO₃ used as positive control (dissolved in sterile water, 5 mg/mL), and 100 µL of bacteria suspension (10⁶ CFU/mL) was added into 40 mL of BHI broth. The control sample contained only bacterial suspension and BHI broth. All flasks were incubated with shaking at 37 °C at 200× g for 4 h. Then, 1 mL from each flask containing the treated and control cultures was transferred to sterile Eppendorf tubes, and 100 µL of TTC was then introduced. All tubes were incubated at 37 °C for 20 min. The samples were centrifuged at 4000× g for 3 min, followed by decantation of the supernatants. The resulting formazan crystals were resuspended in ethanol (70%) and centrifuged again. The red formazan solution obtained at the

end was measured by a microplate reader (Tecan Infinite 200PRO, Tecan Trading AG, Männendorf, Switzerland) at 480 nm. All experiments were done in triplicate and the relative cell viability (%) was represented by a percentage relative to the untreated control cells.

3. Results and Discussion

3.1. Synthesis and FTIR Spectroscopy

Compounds **1–6**, having the general stoichiometric formula $[\text{Ag}(\text{H}_2\text{DMPMB})(\text{X})]$ ($\text{X} = \text{NO}_3$, **1**; CF_3CO_2 , **2**; CF_3SO_3 , **3**; BF_4 , **4**; ClO_4 , **5**; and PF_6 , **6**), hypothesized with the help of elemental analyses, have been obtained from the room temperature reaction carried out in a 2:1 molar ratio of two equivalents of silver(I) salts and one equivalent of H_2DMPMB , in alcohol for compounds **1–3**, **5**, and **6**, and acetonitrile for compound **4**. Their stoichiometry was found to be independent of the amount of silver(I) salts or ligand used in the syntheses, since the 1:1 molar ratio was always obtained, which was also observed in other bis(pyrazolyl)-based silver(I) compounds, such as $[\text{Ag}(\text{H}_2\text{BPZ})(\text{X})]$ ($\text{X} = \text{NO}_3$, ClO_4 , BF_4 , PF_6 , CH_3SO_3 , CF_3SO_3 ; $\text{H}_2\text{BPZ} = 4,4'$ -bipyrazole) [54], $[\text{Ag}(\text{H}_2\text{Me}_4\text{BPZ})(\text{NO}_3)] \cdot \text{CH}_3\text{OH}$ [65], and $[\text{Ag}(\text{H}_2\text{Me}_4\text{BPZ})(\text{X})]$ ($\text{X} = \text{ClO}_4$, CF_3SO_3 , $\text{C}_2\text{F}_5\text{CO}_2$; $\text{H}_2\text{Me}_4\text{BPZ} = 3,3',5,5'$ -tetramethyl-4,4'-bipyrazole) [66].

All compounds were in the form of white powders, and were remarkably light insensitive and air stable, even after twelve months, thus relying on the strength of silver-ligand bonds that may be imparted to the inertness of the overall structure. In fact, no change of their aspect was noticed, and both elemental analyses and FTIR spectra were preserved. Their polymeric nature was indicated by the observed insolubility, both in water and in most common organic solvents, along with the occurrence of high thermal decomposition temperatures revealed by the thermogravimetric analysis (Section 3.2). A preliminary powder X-ray diffraction analysis showed the amorphous nature of the obtained silver(I) CPs, and therefore, their molecular structures are yet to be revealed. Nevertheless, a deeper analysis of their FTIR spectra allowed the proposition of a structural characterization for the obtained H_2DMPMB -based silver(I) CPs, as will be shown in the following lines.

FTIR spectroscopy was employed in order to reveal both the changes in the absorption bands of the ligand upon coordination to silver(I) ions and the binding modes of the counterions. The FTIR spectrum of the free H_2DMPMB ligand is given in Figure 1, while the FTIR spectra of silver(I) CPs **1–6** are given in Figures 2 and 3. The infrared spectrum of the free ligand showed a strong and broad band in the region $2500\text{--}3200\text{ cm}^{-1}$, which was specific to the intermolecular hydrogen bond interactions mediated by the N-H functions of the pyrazolyl rings. Upon coordination to silver(I) ions, the infrared pattern of the ligand was significantly changed, indicating the success of the synthetic methodology adopted for obtaining the new silver(I) CPs.

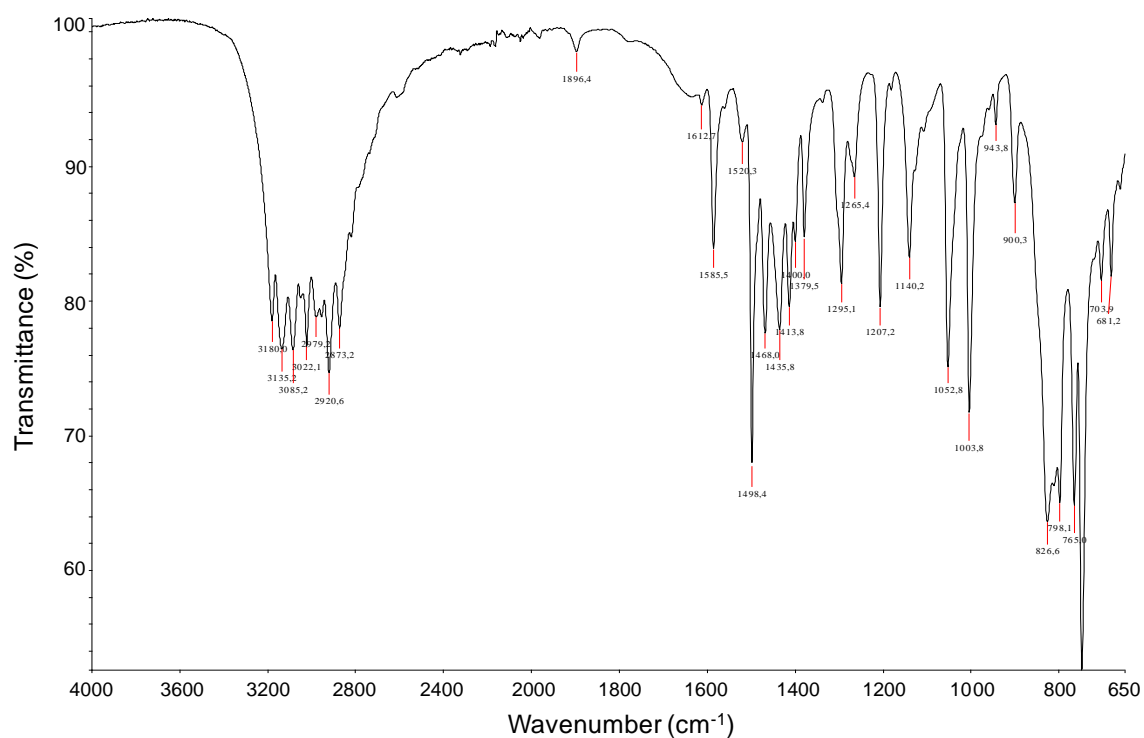


Figure 1. Fourier transform infrared spectroscopy (FTIR) spectrum of the free H₂DMPMB ligand.

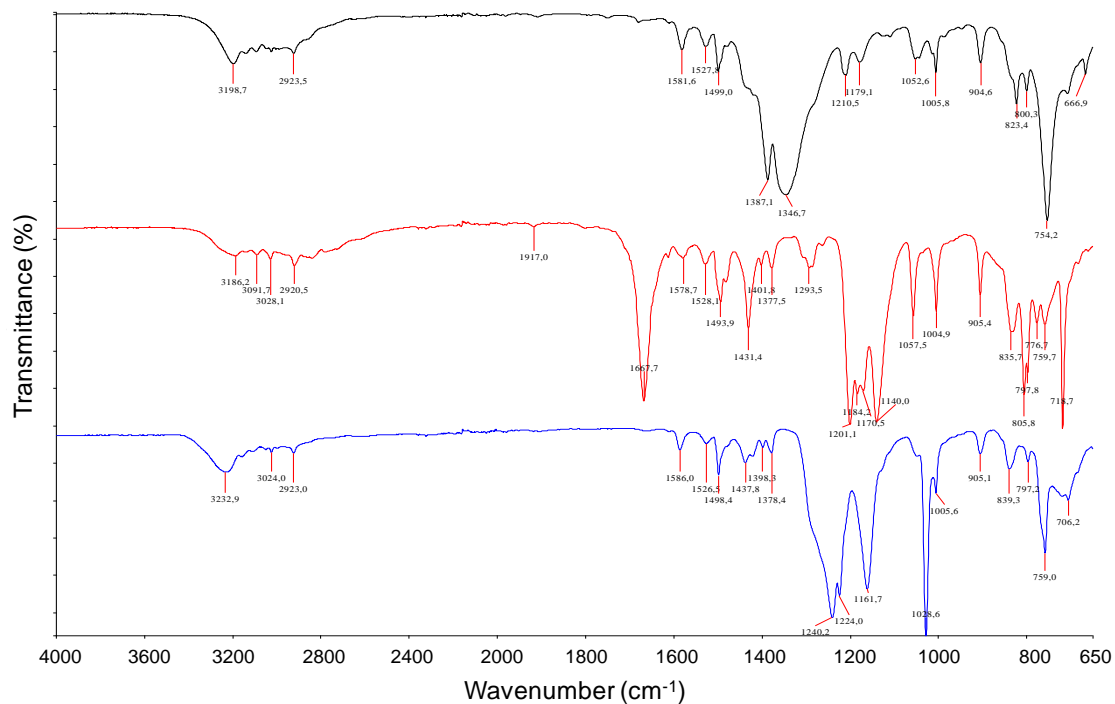


Figure 2. FTIR spectra of silver(I) CPs 1 (black), 2 (red), and 3 (blue).

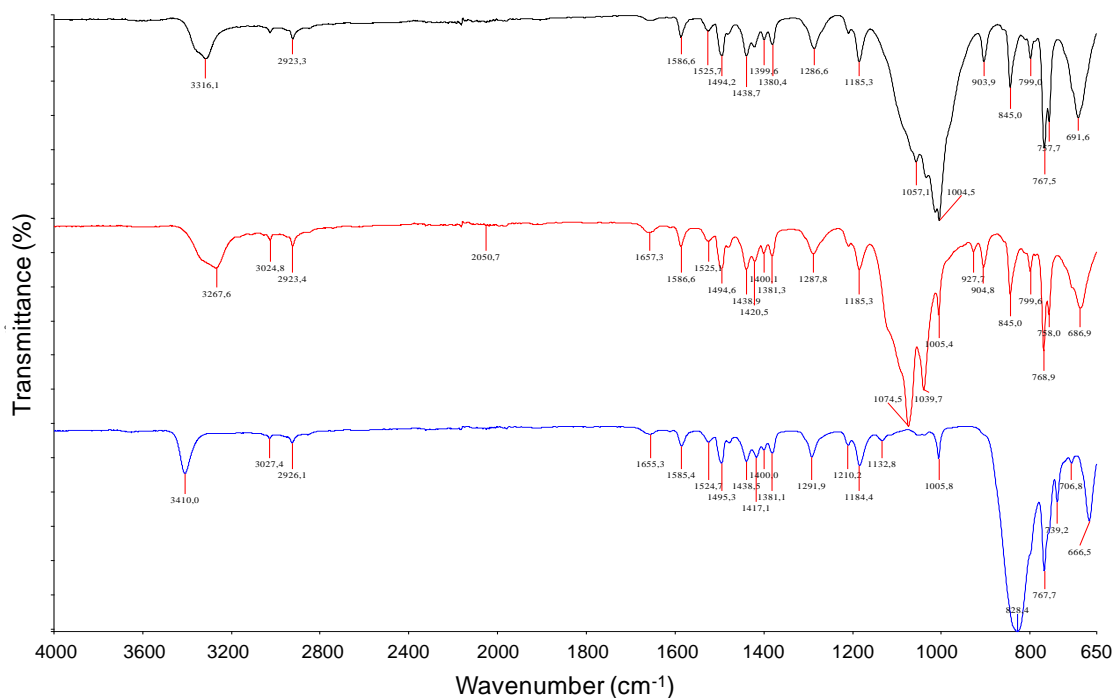


Figure 3. FTIR spectra of silver(I) CPs 4 (black), 5 (red), and 6 (blue).

The infrared spectra of all silver(I) CPs were generally consistent with the proposed formulations, and present all of the required absorption bands for both the ligand and the counterions. The presence of absorption bands, with a generally medium intensity in the range of 3180–3410 cm^{-1} , was specific for the stretching vibrations of the N–H function, confirming that the ligand maintained its neutrality in all compounds. The weak absorption bands located in the range 1579–1587 cm^{-1} were due to the so-called “breathing” of the neutral pyrazolyl rings [67], which was significantly reduced compared to the free ligand, as a consequence of coordination, and in consideration of the influence manifested by the different anions.

A deeper analysis of the infrared spectra of all synthesized silver(I) CPs was also performed in order to obtain clues about the possible interactions in which the anions are involved within the corresponding structures. As such, in the IR spectrum of **1**, the asymmetric stretching modes of the nitrate anion were denounced by the slightly split bands at 1387 and 1347 cm^{-1} . Moreover, the single, very weak band, almost indistinguishable from noise, in the overtone region at 1748 cm^{-1} , suggested that the nitrate anion was in a non-coordinated form [68]. Such a suggestion was further strengthened by the absence of the band associated with symmetric stretching nitrate vibrations near 1049 cm^{-1} [69]. The broad band present in the region 2700–3400 cm^{-1} was indicative of the hydrogen bond interactions between the nitrate anion and the N–H function of the ligand, spreading along adjacent linear chains formed by the $[\text{Ag}(\text{H}_2\text{DMPMB})]^+$ units. However, although the nitrate anion was not directly bound to the silver(I) ion, weak Ag–O interactions could be considered so that the silver(I) ion assumes a T-shaped stereochemistry (Figure 4), as was already observed in the silver(I) CPs $[\text{Ag}(\text{H}_2\text{BPZ})(\text{NO}_3)]$ [54] and $[\text{Ag}(\text{Me}_4\text{BPZ})(\text{NO}_3)] \cdot \text{CH}_3\text{OH}$ [65], and in the silver(I) complexes $\text{AgNO}_3 \cdot \text{tz}_2(\text{CH}_2) \cdot \text{ER}_3 \cdot \text{MeCN}$ ($\text{tz}_2(\text{CH}_2)$ = bis(1,2,4-triazol-1-yl)methane; E = P, As, Sb; MeCN = acetonitrile) [70].

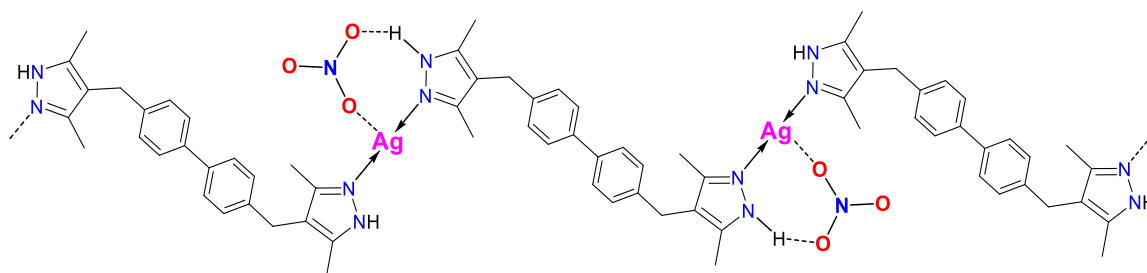


Figure 4. Proposed polymeric structure of $[\text{Ag}(\text{H}_2\text{DMPMB})(\text{NO}_3)]$ (**1**), evidencing the T-shaped stereochemistry of silver(I) ions assured by the nitrate anions and the neutral ligands coordinated in a bridging exo-bidentate mode.

The IR spectra of **2** showed a strong band at 1668 cm^{-1} and a medium one at 1431 cm^{-1} that were characteristic of the carboxylate asymmetric (ν_a) and symmetric stretching (ν_s), respectively. The difference $\Delta\nu = \nu_a - \nu_s = 237\text{ cm}^{-1}$ likely indicates a unidentate coordination of trifluoroacetate anion [71], thus conferring to the silver(I) ions a T-shaped stereochemistry, as was also observed in the silver(I) CP $[\text{Ag}(\text{Me}_4\text{BPZ})(\text{C}_2\text{F}_5\text{CO}_2)]$ [66] and the binaphthylbis(amidopyridyl)-based silver(I) CP $[\text{Ag}(\text{C}_{20}\text{H}_{12}\{\text{NHC}(\text{O})\text{-}3\text{-C}_5\text{H}_4\text{N}\}_2)(\text{CF}_3\text{CO}_2)]$ [72]. The broad band located in the region $2700\text{--}3400\text{ cm}^{-1}$ was also found in the IR spectrum of **2**, which was indicative of the hydrogen bond interactions between the trifluoroacetate anion and the N–H function of the ligand (Figure 5). Strong absorption bands present in the range $1140\text{--}1201\text{ cm}^{-1}$ were assignable to different vibration modes of the C–F bonds, while the sharp band at 719 cm^{-1} could be attributed to the C–O vibration [73]. The IR spectra of **3** shows two very strong and broad absorption bands in the $1200\text{--}1300\text{ cm}^{-1}$ region, due to asymmetric and symmetric vibrations of the SO_3 group from the unidentate trifluoromethanesulfonate group, along with the strong and broad absorption at 1162 cm^{-1} due to the C–F vibrations, and a sharp absorption at 1029 cm^{-1} , which was assignable to the S–O vibration [74,75]. The structure of **3** would therefore be made up of linear chains formed by $[\text{Ag}(\text{H}_2\text{DMPMB})]^+$ units, in which the silver(I) ions assume a T-shaped stereochemistry assured by the exo-bidentate ligands and the trifluoromethanesulfonate anions, as was also observed in the silver(I) CPs $[\text{Ag}(\text{H}_2\text{BPZ})(\text{CF}_3\text{SO}_3)]$ [54] and $[\text{Ag}(\text{Me}_4\text{BPZ})(\text{CF}_3\text{SO}_3)]$ [66] (Figure 6).

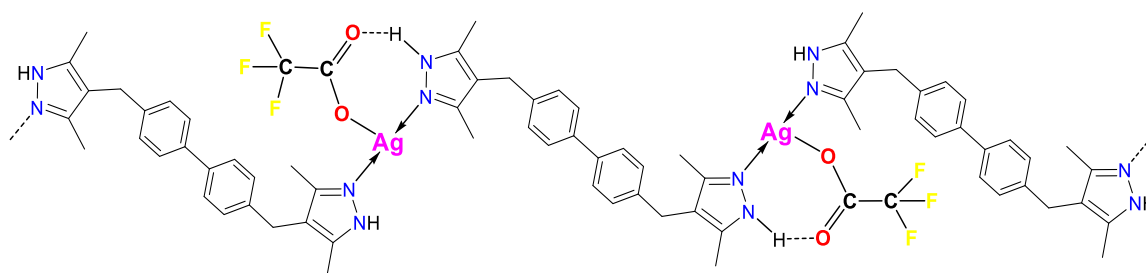


Figure 5. Proposed polymeric structure of $[\text{Ag}(\text{H}_2\text{DMPMB})(\text{CF}_3\text{CO}_2)]$ (**2**), evidencing the T-shaped stereochemistry of silver(I) ions assured by the trifluoroacetate anions and the neutral ligands coordinated in a bridging exo-bidentate mode.

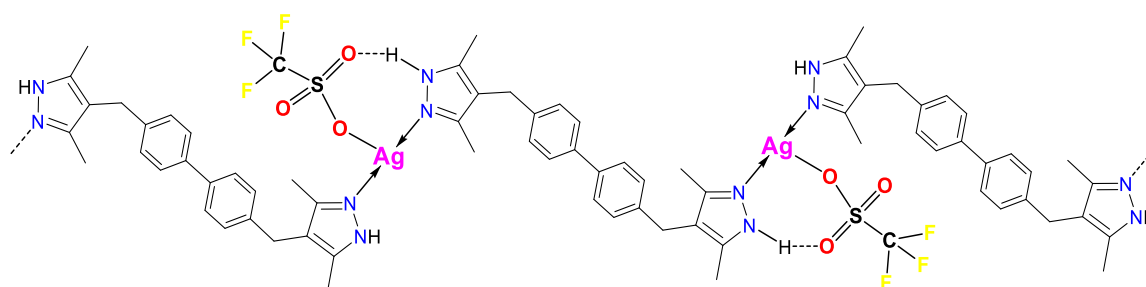


Figure 6. Proposed polymeric structure of $[\text{Ag}(\text{H}_2\text{DMPMB})(\text{CF}_3\text{SO}_3)]$ (**3**), evidencing the T-shaped stereochemistry of silver(I) ions assured by the trifluoromethanesulfonate anions and the neutral ligands coordinated in a bridging exo-bidentate mode.

In the IR spectrum of **4**, the fine splitting of the very strong and broad band in the region $1000\text{--}1100\text{ cm}^{-1}$, together with the medium sharp band at 768 cm^{-1} and the medium broad band at 692 cm^{-1} , were assigned to the weakly coordinating tetrafluoroborate group (Figure 7) [76], which could be involved in long interactions with the silver(I) ions to complete a T-shaped stereochemistry, as was also observed in the silver(I) CP $[\text{Ag}(\text{H}_2\text{BPZ})(\text{BF}_4)]$ [54]. The IR spectrum of **5** showed two strong broad bands at 1040 and 1075 cm^{-1} , along with the medium sharp band at 769 cm^{-1} and a medium broad band at 687 cm^{-1} , which were attributed to the coordinated perchlorate group (Figure 8) [76], thus completing a T-shaped stereochemistry of the silver(I) ions, as was also observed in the silver(I) CPs $[\text{Ag}(\text{H}_2\text{BPZ})(\text{ClO}_4)]$ [54] and $[\text{Ag}(\text{Me}_4\text{BPZ})(\text{ClO}_4)]$ [66]. Finally, in the IR spectrum of **6**, the very strong, broad absorption band located at 828 cm^{-1} , together with the medium sharp band at 768 cm^{-1} and the medium broad band at 667 cm^{-1} could be assigned to the weakly coordinating hexafluorophosphate anions, which are in fact situated between the cationic sheets instead of being in direct interaction with the silver(I) ions (Figure 9) [77].

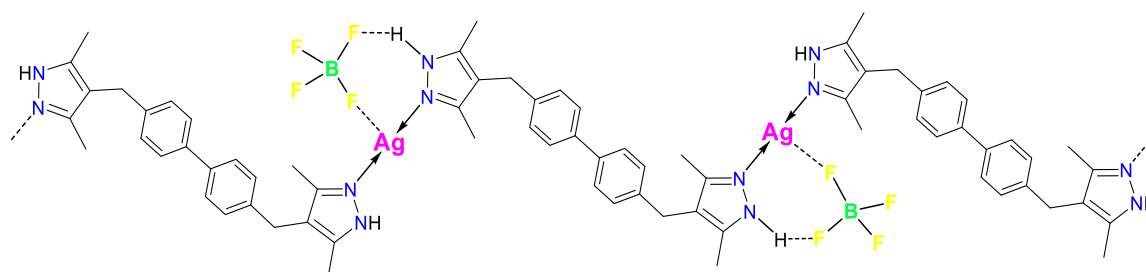


Figure 7. Proposed polymeric structure of $[\text{Ag}(\text{H}_2\text{DMPMB})(\text{BF}_4)]$ (**4**), evidencing the T-shaped stereochemistry of silver(I) ions assured by the tetrafluoroborate anions and the neutral ligands coordinated in a bridging exo-bidentate mode.

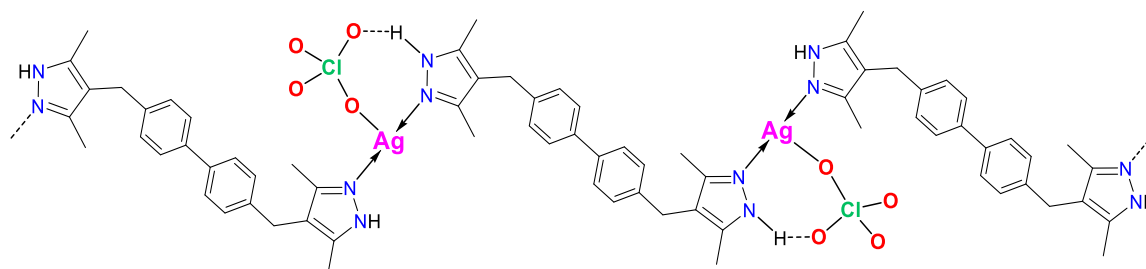


Figure 8. Proposed polymeric structure of $[\text{Ag}(\text{H}_2\text{DMPMB})(\text{ClO}_4)]$ (**5**), evidencing the T-shaped stereochemistry of silver(I) ions assured by the perchlorate anions and the neutral ligands coordinated in a bridging exo-bidentate mode.

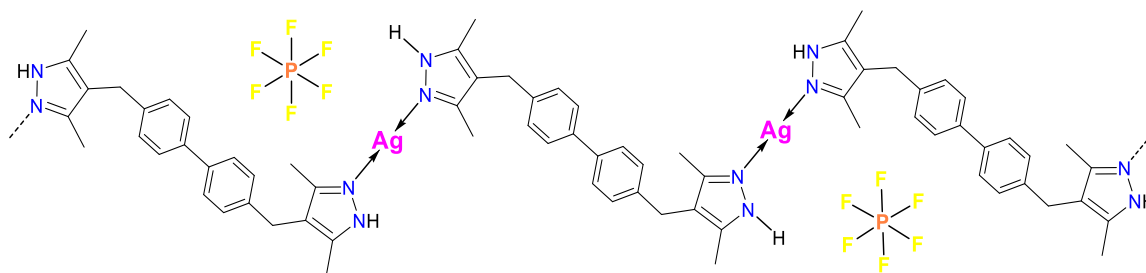


Figure 9. Proposed polymeric structure of $[Ag(H_2DMPMB)(PF_6)]$ (**6**), evidencing the digonal stereochemistry of silver(I) ions assured by the neutral ligands coordinated in a bridging exo-bidentate mode.

3.2. Thermogravimetric Analysis

The thermogravimetric analyses (TGA) of silver(I) polymeric species **1–6** were performed in order to investigate their thermal behavior upon heating from 30 to 700 °C, under nitrogen, and the resulting TGA curves were collectively gathered in Figure 10. Compound **1** showed an appreciable thermal stability, resistant up to 275 °C, after which a weight loss of about 12% in the range 275–325 °C was recorded, corresponding to the removal of one nitric acid molecule, which was the result of the proton transfer from one pyrazolyl moiety (theoretical weight loss: 11.66%). This loss was immediately followed by a progressive decomposition of the remaining species.

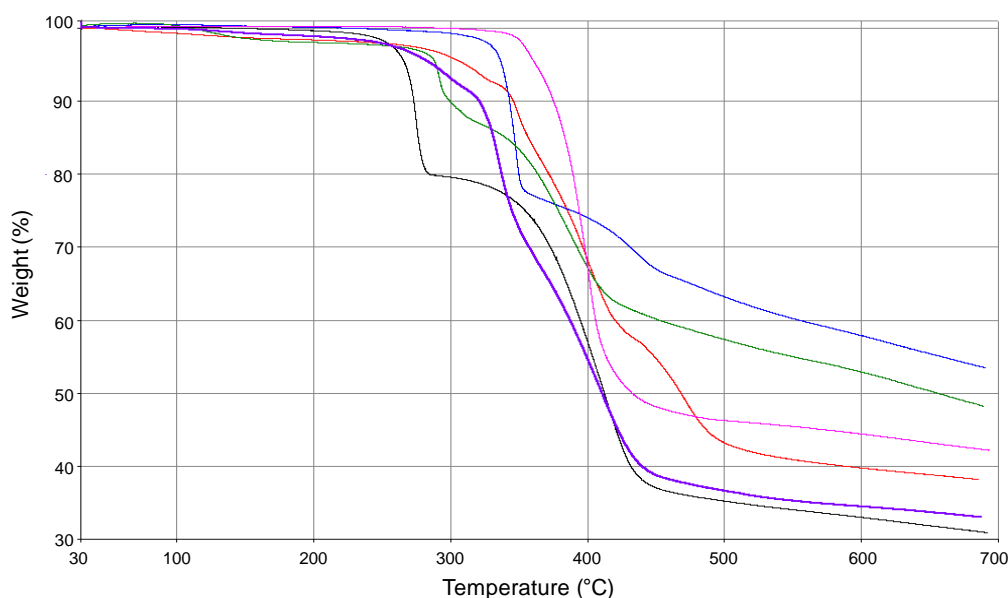


Figure 10. Thermogravimetric analysis (TGA) curves of silver(I) CPs **1** (green), **2** (black), **3** (fuchsia), **4** (red), **5** (blue), and **6** (purple).

Compound **2** was thermally stable up to 250 °C, which then underwent a weight loss of about 20% until 300 °C, which is in a good agreement with the expected theoretical weight loss of 19.28%, corresponding to the evolution of one trifluoroacetic acid molecule, which was the result of the proton transfer from the organic ligand. This event was further continued by a progressive decomposition of the remaining species.

Compounds **3** and **5** displayed the highest thermal stabilities, which were resistant up to 350 and 325 °C, respectively, overcoming the values reported for, e.g., the 3-D supramolecular isomer α - $[Ag_2(Me_4BPZ)]$ [78] and the neutral CP $[Ag_2(DMPMB)]$ [60], which were both resistant up to 300 °C, or the 1-D CP $[Ag(pz)]$ (pz = pyrazole), which was stable up to 270 °C [79]. Such remarkable results may be ascribed to the stronger electron-withdrawing effect of both trifluoromethanesulfonate and

perchlorate anions, imparting more inertness to the Ag-N coordinative bonds, and thus to the overall polymeric structures. Compounds **4** and **6** showed the lowest thermal stability, which, although still significant, peaked up to 250 °C, followed then by a progressive decomposition.

In all cases, at the end of the heating process, black residues, possibly containing a mixture of carbonaceous species and metallic silver/silver(I) oxide, were recovered. Other than the effect of the anions upon the thermal robustness of the obtained silver(I) polymeric species, the dependency of such property on the ligand itself should not be neglected.

3.3. Antibacterial Activity

The assessment of antibacterial activity of all prepared silver(I) CPs against Gram-negative bacteria *E. coli* and Gram-positive bacteria *S. aureus* was performed by using the Tetrazolium/Formazan test (TTC) as a qualitative assay, by measuring the bacterial viability at different time intervals (2, 4, 6, and 24 h). The tetrazolium salts are known for their ability to form, within the bacterial culture medium, highly colored products called formazans [80].

From the point of view of the mechanism of antibacterial action, it was shown that, from within the silver-based topical antibacterial agents, the silver(I) ions are those that manifest the bactericidal effects. More exactly, the silver(I) ions prevented the performance of the function of bacterial cells by direct interaction with the bacterial enzymes and DNA, thus interrupting the cell division and replication [81]. On the other hand, the silver(I) ions are involved in the interaction with the negatively charged peptidoglycan from the bacterial cell wall, thus affecting the cell breathing, which finally leads to cell death through the release, into the surrounding environment, their fluid and electrolyte content [82,83].

Figure 11 shows the bacterial viability of the two bacterial strains, *S. aureus* and *E. coli*, in the presence of silver(I) CPs **1–6**, and silver(I) nitrate (AgNO_3) used as a standard antibacterial agent, after 2, 4, and 6 h. The TTC test indicated, as expected in the presence of an antibacterial agent, the bacterial reduction in time with respect to the control (untreated cells). In the case of *S. aureus*, after 2 h, the values of bacterial viability significantly decreased to 8–19%, and after 6 h the values went down to 1–4%.

A markedly different behavior was appreciated against *E. coli*, that is, all six silver(I) CPs were less effective in the first period of exposure with a slower action rate compared to *S. aureus*. As such, after 2 h, the values of bacterial viability decreased to 37% (**1**), 60–64% (**2**, **4**, and **6**), and 79–81% (**3** and **5**). The decreasing trend was maintained after 4 h, and after 6 h, the values decreased to 2% (**1**), 21–22% (**2**, **4**, and **6**), 37% (**3**), and 42% (**5**). After 24 h of exposure, a complete bacterial reduction was observed. However, no neat influence of the counter-anions upon the bactericidal effect of the related silver(I) CPs could also be noticed.

For the standard AgNO_3 , the bactericidal effect against *S. aureus* was strong during the first 2 h of exposure (8%), while the bacterial reduction was complete after only 6 h, compared to *E. coli*, where the bacterial reduction was only 62% after 2 h and 5% after 6 h of exposure. Thus, a difference in the rate of action as a function of the bacteria types could be appreciated. It can be observed that the bactericidal effect of the standard AgNO_3 was comparable with that of our silver(I) CPs. However, the high insolubility of these CPs would bring the advantage of applying them for much longer time intervals, compared to the highly soluble AgNO_3 (2160 g/L at 20 °C), which underwent faster silver(I) ions release into the environment, thus leading to an increased level of toxicity [52–54].

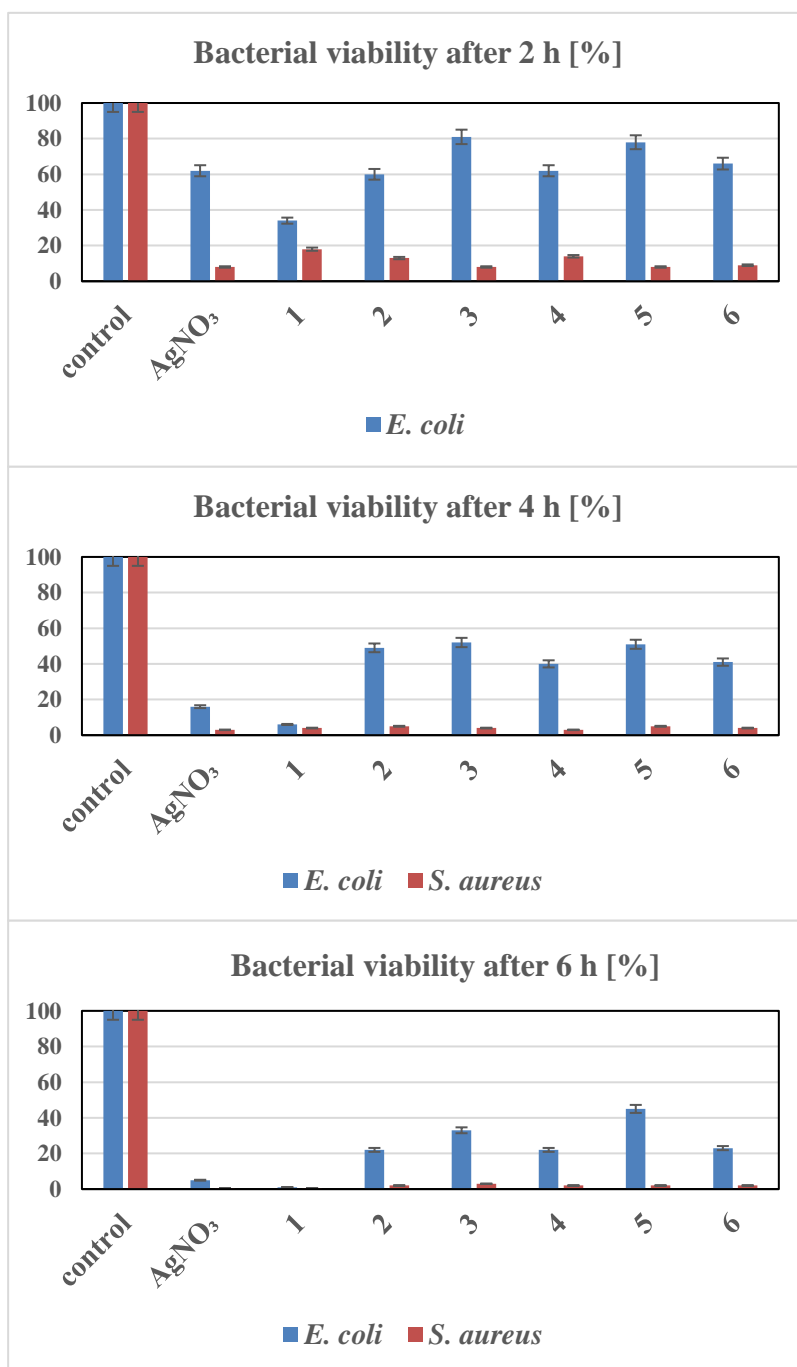


Figure 11. Bacterial viability of *S. aureus* and *E. coli* in the presence of silver(I) CPs 1–6 and standard AgNO₃.

4. Conclusions

Coupling the flexible ditopic ligand 4,4'-bis((3,5-dimethyl-1H-pyrazol-4-yl)methyl)biphenyl (H₂DMPMB) to different silver(I) salts afforded the preparation of six new, light insensitive, air stable, and highly insoluble silver(I) coordination polymers (CPs) with the general formula [Ag(H₂DMPMB)(X)] (X = NO₃, 1; CF₃CO₂, 2; CF₃SO₃, 3; BF₄, 4; ClO₄, 5; and PF₆, 6). The obtained silver(I) CPs demonstrated important antibacterial performances against *E. coli* and *S. aureus*, for which a complete reduction of both bacterial strains occurred after 24 h of exposure to all silver(I) CPs, the bacterial viability value for *S. aureus* reached 8% for compounds 3, 5, and 6 after only 2 h. The high

insolubility displayed by the new silver(I) CPs presents the advantage, if clinical applications are sought, of reapplying them for much longer time intervals, compared to the highly soluble silver(I) nitrate used as a standard antibacterial agent. The results thus highlight the quality of the new silver(I) CPs as interesting platforms to explore new antibacterial agents. The antibacterial properties proven by our silver(I) CPs, on the inhibition of antibiotic-resistant strains, such as *E. coli* and *S. aureus*, are promising tools that we hope offer a more powerful solution to the worldwide problem that has become a worrying issue: The multiplication of highly multidrug-resistant bacteria in clinical medicine. Future studies will be devoted to the application of these silver(I) CPs into antimicrobial cellulose papers for food packaging protection.

Author Contributions: Conceptualization, A.T., C.P. and R.M.D.; methodology, A.T., C.P., M.B. and R.M.D.; investigation, A.T., M.B. and R.M.D.; resources, C.P. and R.M.D.; writing—original draft preparation, A.T. and M.B.; writing—review and editing, A.T., C.P. and R.M.D.; visualization, C.P. and R.M.D.; supervision, C.P. and R.M.D.; project administration, A.T. and R.M.D.; funding acquisition, A.T. and R.M.D.

Funding: This work was supported by a grant of Ministry of Research and Innovation, CNCS—UEFISCDI, project number PN-III-P1-1.1-PD-2016-0409, within PNCDI III.

Acknowledgments: University of Camerino (UNICAM) is gratefully acknowledged for the assistance with the necessary scientific instruments.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Patel, V. *Synthesis, Characterization and Application of Coordination Polymers*; Lambert Academic Publishing: Saarbrücken, Germany, 2015.
2. Batten, S.R.; Neville, S.M.; Turner, D.R. *Coordination Polymers: Design, Analysis and Application*; Springer: New York, NY, USA, 2010.
3. Hong, M.-C.; Chen, L. *Design and Construction of Coordination Polymers*; John Wiley & Sons Inc.: Hoboken, NJ, USA, 2009.
4. Morsali, A.; Hashemi, L. *Main Group Metal Coordination Polymers: Structures and Nanostructures*; John Wiley & Sons Inc.: Hoboken, NJ, USA, 2017.
5. MacGillivray, L.R.; Lukehart, C.M. *Metal-Organic Framework Materials*; John Wiley & Sons Inc.: Weinheim, Germany, 2014.
6. Kaskel, S. *The Chemistry of Metal-Organic Frameworks: Synthesis, Characterization, and Applications*; John Wiley & Sons Inc.: Weinheim, Germany, 2016.
7. Seyyedi, B. *Metal–Organic Frameworks: A New Class of Crystalline Porous Materials*; Lambert Academic Publishing: Saarbrücken, Germany, 2014.
8. Li, H.; Wang, K.; Sun, Y.; Lollar, C.T.; Li, J.; Zhou, H.-C. Recent advances in gas storage and separation using metal-organic frameworks. *Mater. Today* **2018**, *21*, 108–121. [[CrossRef](#)]
9. Rogge, S.M.J.; Bavykina, A.; Hajek, J.; Garcia, H.; Olivos-Suarez, A.I.; Sepúlveda-Escribano, A.; Vimont, A.; Clet, G.; Bazin, P.; Kapteijn, F.; et al. Metal-organic frameworks and covalent organic frameworks as single-site catalysts. *Chem. Soc. Rev.* **2017**, *46*, 3134–3184. [[CrossRef](#)] [[PubMed](#)]
10. Heine, J.; Müller-Buschbaum, K. Engineering metal-based luminescence in coordination polymers and metal-organic frameworks. *Chem. Soc. Rev.* **2013**, *42*, 9232–9242. [[CrossRef](#)]
11. Zhang, X.; Wang, W.; Hu, Z.; Wang, G.; Uvdal, K. Coordination polymers for energy transfer: Preparations, properties, sensing applications, and perspectives. *Coord. Chem. Rev.* **2015**, *284*, 206–235. [[CrossRef](#)]
12. Mínguez Espallargas, G.; Coronado, E. Magnetic functionalities in MOFs: From the framework to the pore. *Chem. Soc. Rev.* **2018**, *47*, 533–557. [[CrossRef](#)] [[PubMed](#)]
13. Sun, L.; Campbell, M.G.; Dinca, M. Electrically conductive porous metal-organic frameworks. *Angew. Chem. Int. Ed.* **2016**, *55*, 3566–3579. [[CrossRef](#)] [[PubMed](#)]
14. Wu, M.-X.; Yang, Y.-W. Metal-organic framework (MOF)-based drug/cargo delivery and cancer therapy. *Adv. Mater.* **2017**, *29*, 1606134. [[CrossRef](#)]
15. Janiak, C.; Vieth, J.K. MOFs, MILs and more: Concepts, properties and applications for porous coordination networks (PCNs). *New J. Chem.* **2010**, *34*, 2366–2388. [[CrossRef](#)]

16. Robin, A.Y.; Fromm, K.M. Coordination polymer networks with O- and N-donors: What they are, why and how they are made. *Coord. Chem. Rev.* **2006**, *250*, 2127–2157. [[CrossRef](#)]
17. Tabacaru, A.; Pettinari, C.; Galli, S. Coordination polymers and metal-organic frameworks built up with poly(tetrazolate) ligands. *Coord. Chem. Rev.* **2018**, *372*, 1–30. [[CrossRef](#)]
18. Pettinari, C.; Tabacaru, A.; Galli, S. Coordination polymers and metal-organic frameworks based on poly(pyrazole)-containing ligands. *Coord. Chem. Rev.* **2016**, *307*, 1–31. [[CrossRef](#)]
19. Liao, P.-Q.; He, C.-T.; Zhou, D.-D.; Zhang, J.-P.; Chen, X.-M. Porous metal azolate frameworks. In *The Chemistry of Metal-Organic Frameworks: Synthesis, Characterization, and Applications*; Kaskel, S., Ed.; Wiley: Weinheim, Germany, 2016; Volume 1, pp. 309–343.
20. Biradha, K.; Sarkar, M.; Rajput, L. Crystal engineering of coordination polymers using 4,4'-bipyridine as a bond between transition metal atoms. *Chem. Commun.* **2006**, 4169–4179. [[CrossRef](#)] [[PubMed](#)]
21. Gagnon, K.J.; Perry, H.P.; Clearfield, A. Conventional and unconventional metal-organic frameworks based on phosphonate ligands: MOFs and UMOFs. *Chem. Rev.* **2012**, *112*, 1034–1054. [[CrossRef](#)] [[PubMed](#)]
22. Su, C.-Y.; Chen, C.-L.; Zhang, J.-Y.; Kang, B.-S. Silver(I) coordination polymers. In *Design and Construction of Coordination Polymers*; Hong, M.-C., Chen, L., Eds.; John Wiley & Sons, Inc.: Hoboken, NJ, USA, 2009; pp. 111–144.
23. Steel, P.J.; Fitchett, C.M. Metallosupramolecular silver(I) assemblies based on pyrazine and related ligands. *Coord. Chem. Rev.* **2008**, *252*, 990–1006. [[CrossRef](#)]
24. Mak, T.C.; Zhao, X.-L. Silver: Inorganic and coordination chemistry. In *Encyclopedia of Inorganic and Bioinorganic Chemistry*; King, R.B., Ed.; John Wiley & Sons, Inc.: Chichester, UK, 2005; pp. 5187–5197.
25. Khlobystov, A.N.; Blake, A.J.; Champness, N.R.; Lemenovskii, D.A.; Majouga, A.G.; Zyk, N.V.; Schröder, M. Supramolecular design of one-dimensional coordination polymers based on silver(I) complexes of aromatic nitrogen-donor ligands. *Coord. Chem. Rev.* **2001**, *222*, 155–192. [[CrossRef](#)]
26. Yan, J.; Wilbraham, L.; Basa, P.N.; Schüttel, M.; Macdonald, J.C.; Ciofini, I.; Coudert, F.-X.; Burdette, S.C. Emissive azobenzenes delivered on a silver coordination polymer. *Inorg. Chem.* **2018**, *57*, 15009–15022. [[CrossRef](#)]
27. Huang, R.-W.; Wei, Y.-S.; Dong, X.-Y.; Wu, X.-H.; Du, C.-X.; Zang, S.-Q.; Mak, T.C. Hypersensitive dual-function luminescence switching of a silver-chalcogenolate cluster based metal-organic framework. *Nat. Chem.* **2017**, *9*, 689. [[CrossRef](#)]
28. Rana, A.; Jana, S.K.; Pal, T.; Puschmann, H.; Zangrando, E.; Dalai, S. Electrical conductivity and luminescence properties of two silver(I) coordination polymers with heterocyclic nitrogen ligands. *J. Solid State Chem.* **2014**, *216*, 49–55. [[CrossRef](#)]
29. Zheng, X.-F.; Zhu, L.-G. Synthesis, structures and conductivity properties of silver 3-sulfobenzoate coordination polymers. *Inorg. Chim. Acta* **2011**, *365*, 419–429. [[CrossRef](#)]
30. Yamada, S.; Ishida, T.; Nogami, T. Supramolecular triangular and linear arrays of metal-radical solids using pirazolato-silver(I) motifs. *Dalton Trans.* **2004**, 898–903. [[CrossRef](#)]
31. Rigamonti, L.; Vaccari, M.; Roncaglia, F.; Baschieri, C.; Forni, A. New silver(I) coordination polymer with Fe₄ single-molecule magnets as long spacer. *Magnetochemistry* **2018**, *4*, 43. [[CrossRef](#)]
32. May, L.J.; Shimizu, G.K.H. Highly selective intercalation of primary amines in a continuous layer Ag coordination network. *Chem. Mater.* **2005**, *17*, 217–220. [[CrossRef](#)]
33. Yang, G.; Raptis, R.G. A robust, porous, cationic silver(I) 3,5-diphenyl-1,2,4-triazolate framework with a uninodal 4⁹.6⁶ net. *Chem. Commun.* **2004**, 2058–2059. [[CrossRef](#)] [[PubMed](#)]
34. Zhou, Z.; He, C.; Yang, L.; Wang, Y.; Liu, T.; Duan, C. Alkyne activation by a porous silver coordination polymer for heterogeneous catalysis of carbon dioxide cycloaddition. *ACS Catal.* **2017**, *7*, 2248–2256. [[CrossRef](#)]
35. Wang, C.C.; Jing, H.P.; Wang, P. Three silver-based complexes constructed from organic carboxylic acid and 4,4'-bipyridine-like ligands: Syntheses, structures and photocatalytic properties. *J. Mol. Struct.* **2014**, *1074*, 92–99. [[CrossRef](#)]
36. Blake, A.J.; Champness, N.R.; Cooke, P.A.; Nicolson, J.E.B. Synthesis of a chiral adamantoid network – the role of solvent in the construction of new coordination networks with silver(I). *Chem. Commun.* **2000**, 665–666. [[CrossRef](#)]

37. Feazell, R.P.; Carson, C.R.; Klausmeyer, K.K. Silver(I) 3-aminomethylpyridine complexes, Part 1: Effect of ligand ration, π -stacking, and temperature with a noninteracting anion. *Inorg. Chem.* **2006**, *45*, 2627–2634. [[CrossRef](#)]
38. Marchetti, F.; Pettinari, R.; Di Nicola, C.; Pettinari, C.; Paul, A.; Crispini, A.; Giorno, E.; Lelj, F.; Stoia, S.; Amati, M. Effect of methyl groups in a pyrimidine-based flexible ligand on the formation of silver(I) coordination networks. *New J. Chem.* **2018**, *42*, 13998–14008. [[CrossRef](#)]
39. Patra, G.K.; Goldberg, I.; De, S.; Datta, D. Effect of the size of discrete anions on the nuclearity of a complexation. *CrystEngComm* **2007**, *9*, 828–832. [[CrossRef](#)]
40. Medici, S.; Peana, M.; Crisponi, G.; Nurchi, V.M.; Lachowicz, J.I.; Remelli, M.; Zoroddu, M.A. Silver coordination compounds: A new horizon in medicine. *Coord. Chem. Rev.* **2016**, *327*, 349–359. [[CrossRef](#)]
41. Nomyia, K.; Tsuda, K.; Sudoh, T.; Oda, M. Ag(I)-N bond-containing compound showing wide spectra in effective antimicrobial activities: Polymeric silver(I) imidazolate. *J. Inorg. Biochem.* **1997**, *68*, 39–44. [[CrossRef](#)]
42. Nomiya, K.; Tsuda, K.; Kasuga, N.C. Synthesis and X-ray characterization of helical polymer complexes [Ag(1,2,3-L)(PPh₃)₂]_n and [Ag(1,2,4-L)(PPh₃)₂]_n (HL = triazole) and their antimicrobial activities. *J. Chem. Soc. Dalton Trans.* **1998**, 1653–1659. [[CrossRef](#)]
43. Nomiya, K.; Noguchi, R.; Oda, M. Complexes with tetrazole (Htetz) and triphenylphosphine ligands, and their antimicrobial activities. A helical polymer of silver (I) complex [Ag(tetz)(PPh₃)₂]_n and a monomeric gold (I) complex [Au(tetz)(PPh₃)]. *Inorg. Chim. Acta* **2000**, *298*, 24–32. [[CrossRef](#)]
44. Rogovoy, M.I.; Berezin, A.S.; Kozlova, Y.N.; Samsonenko, D.G.; Artem'ev, A.V. A layered Ag(I)-based coordination polymer showing sky-blue luminescence and antibacterial activity. *Inorg. Chem. Commun.* **2019**, *108*, 107513. [[CrossRef](#)]
45. Liu, A.; Wang, C.C.; Wang, C.Z.; Fu, H.-F.; Peng, W.; Cao, Y.-L.; Chu, H.-Y.; Du, A.-F. Selective adsorption activities toward organic dyes and antibacterial performance of silver based coordination polymers. *J. Colloid Interface Sci.* **2018**, *512*, 730–739. [[CrossRef](#)]
46. Marchetti, F.; Palmucci, J.; Pettinari, C.; Pettinari, R.; Scuri, S.; Grappasonni, I.; Cocchioni, M.; Amati, M.; Lelj, F.; Crispini, A. Linkage isomerism in silver acylpyrazolonato complexes and correlation with their antibacterial activity. *Inorg. Chem.* **2016**, *55*, 5453–5466. [[CrossRef](#)]
47. Alisir, S.H.; Demir, S.; Sariboga, B.; Buyukgungor, O. A disparate 3-D silver(I) coordination polymer of pyridine-3,5-dicarboxylate and pyrimidine with strong intermetallic interactions: X-ray crystallography, photoluminescence and antimicrobial activity. *J. Coord. Chem.* **2015**, *68*, 155–168. [[CrossRef](#)]
48. Lu, X.; Ye, J.; Sun, Y.; Bogale, R.F.; Zhao, L.; Tian, P.; Ning, G. Ligand effects on the structural dimensionality and antibacterial activities of silver-based coordination polymers. *Dalton Trans.* **2014**, *43*, 10104–10113. [[CrossRef](#)]
49. Jaros, S.W.; Smoleński, P.; Guedes da Silva, M.F.C.; Florek, M.; Król, J.; Staroniewicz, Z.; Pombeiro, A.J.L.; Kirillov, A.M. New silver BioMOFs driven by 1,3,5-triaza-7-phosphaadamantane-7-sulfide (PTALS): Synthesis, topological analysis and antimicrobial activity. *CrystEngComm* **2013**, *15*, 8060–8064. [[CrossRef](#)]
50. Lotlikar, S.R.; Gallaway, E.; Grant, T.; Popis, S.; Whited, M.; Guragain, M.; Rogers, R.; Hamilton, S.; Gerasimchuk, N.G.; Patrauchan, M.A. Polymeric composites with silver(I) cyanoximates inhibit biofilm formation of Gram-positive and Gram-negative bacteria. *Polymers* **2019**, *11*, 1018. [[CrossRef](#)]
51. Girard, J.; Joset, N.; Crochet, A.; Tan, M.; Holzheu, A.; Brunetto, P.S.; From, K.M. Synthesis of new polyether ether ketone derivatives with silver binding site and coordination compounds of their monomers with different silver salts. *Polymers* **2016**, *8*, 208. [[CrossRef](#)] [[PubMed](#)]
52. Marchetti, F.; Palmucci, J.; Pettinari, C.; Pettinari, R.; Marangoni, M.; Ferraro, S.; Giovannetti, R.; Scuri, S.; Grappasonni, I.; Cocchioni, M.; et al. Preparation of polyethylene composites containing silver(I) acylpyrazolonato additives and SAR investigation of their antibacterial activity. *ACS Appl. Mater. Interfaces* **2016**, *8*, 29676–29687. [[CrossRef](#)] [[PubMed](#)]
53. Marchetti, F.; Palmucci, J.; Pettinari, C.; Pettinari, R.; Condello, F.; Ferraro, S.; Marangoni, M.; Crispini, A.; Scuri, S.; Grappasonni, I.; et al. Novel composite plastics containing silver(I) acylpyrazolonato additives display potent antimicrobial activity by contact. *Chem. Eur. J.* **2015**, *21*, 836–850. [[CrossRef](#)] [[PubMed](#)]
54. Tabacaru, A.; Pettinari, C.; Marchetti, F.; Di Nicola, C.; Domasevitch, K.V.; Galli, S.; Masciocchi, N.; Scuri, S.; Grappasonni, I.; Cocchioni, M. Antibacterial action of 4,4'-bipyrazolyl-based silver(I) coordination polymers embedded in PE disks. *Inorg. Chem.* **2012**, *51*, 9775–9788. [[CrossRef](#)] [[PubMed](#)]

55. Brunetto, P.S.; Slenters, T.V.; Fromm, K.M. *In vitro* biocompatibility of new silver(I) coordination compound coated-surfaces for dental implant applications. *Materials* **2011**, *4*, 355–367. [[CrossRef](#)] [[PubMed](#)]
56. Slenters, T.V.; Sagué, J.L.; Brunetto, P.S.; Zuber, S.; Fleury, A.; Mirolo, L.; Robin, A.Y.; Meuwly, M.; Gordon, O.; Landmann, R.; et al. Of chains and rings: Synthetic strategies and theoretical investigations for tuning the structure of silver coordination compounds and their applications. *Materials* **2010**, *3*, 3407–3429. [[CrossRef](#)]
57. Gordon, O.; Slenters, T.V.; Brunetto, P.S.; Villaruz, A.E.; Sturdevant, D.E.; Otto, M.; Landmann, R.; Fromm, K.M. Silver coordination polymers for prevention of implant infection: Thiol interaction, impact on respiratory chain enzymes, and hydroxyl radical induction. *Antimicrob. Agents Chemother.* **2010**, *54*, 4208–4218. [[CrossRef](#)]
58. Brunetto, P.S.; Fromm, K.M. Antimicrobial coatings for implant surfaces. *Chimia* **2008**, *62*, 249–252. [[CrossRef](#)]
59. Slenters, T.V.; Hauser-Gerspach, I.; Daniels, A.U.; Fromm, K.M. Silver coordination compounds as light-stable, nano-structured and anti-bacterial coatings for dental implant and restorative materials. *J. Mater. Chem.* **2008**, *18*, 5359–5362. [[CrossRef](#)]
60. Tabacaru, A.; Pettinari, C.; Marchetti, F.; Galli, S.; Masciocchi, N. Bis(pyrazolato)-based metal-organic frameworks fabricated with 4,4'-bis((3,5-dimethyl-1H-pyrazol-4-yl)methyl)biphenyl and late transition metals. *Cryst. Growth Des.* **2014**, *14*, 3142–3152. [[CrossRef](#)]
61. Tabacaru, A.; Pettinari, C.; Masciocchi, N.; Galli, S.; Marchetti, F.; Angjellari, M. Pro-porous coordination polymers of the 1,4-bis((3,5-dimethyl-1Hpyrazol-4-yl)-methyl)benzene ligand with late transition metals. *Inorg. Chem.* **2011**, *50*, 11506–11513. [[CrossRef](#)] [[PubMed](#)]
62. Duan, P.-C.; Huang, Z.-D.; Zhang, F.-F.; Yang, G. Synthesis and crystal structure of copper(II) and silver(I) complexes of a biphenyl-bridged bipyrazolyl ligand. *Transition Met. Chem.* **2012**, *37*, 595–600. [[CrossRef](#)]
63. Semitut, E.; Komarov, V.; Sukhikh, T.; Filatov, E.; Potapov, A. Synthesis, crystal structure and thermal stability of 1D linear silver(I) coordination polymers with 1,1,2,2-tetra(pyrazol-1-yl)ethane. *Crystals* **2016**, *6*, 138. [[CrossRef](#)]
64. Moussa, S.H.; Tayel, A.A.; Al-Hassan, A.A.; Farouk, A. Tetrazolium/formazan test as an efficient method to determine fungal chitosan antimicrobial activity. *J. Mycol.* **2013**, *2013*, 753692. [[CrossRef](#)]
65. Boldog, I.; Rusanov, E.B.; Chernega, A.N.; Sieler, J.; Domasevitch, K.V. One- and two-dimensional coordination polymers of 3,3',5,5'-tetramethyl-4,4'-bipyrazolyl, a new perspective crystal engineering module. *Polyhedron* **2001**, *20*, 887–897. [[CrossRef](#)]
66. Domasevitch, K.V.; Boldog, I.; Rusanov, E.B.; Hunger, J.; Blaurock, S.; Schöder, M.; Sieler, J. Helical bipyrazole networks conditioned by hydrothermal crystallization. *Z. Anorg. Allg. Chem.* **2005**, *631*, 1095–1100. [[CrossRef](#)]
67. Banditelli, G.; Bandini, A.L.; Bonati, F.; Minghetti, G. Carbonylrhodium(I) derivatives of 3,5-dimethyl- and 3,5-bis(trifluoromethyl)pyrazole. *J. Organomet. Chem.* **1981**, *218*, 229–239. [[CrossRef](#)]
68. Lever, A.B.P.; Mantovani, E.; Ramaswamy, B.S. Infrared combination frequencies in coordination complexes containing nitrate groups in various coordination environments. A probe for the metal–nitrate interaction. *Can. J. Chem.* **1971**, *49*, 1957–1964. [[CrossRef](#)]
69. Nakamoto, K. *Infrared and Raman Spectra of Inorganic and Coordination Compounds, Part A*, sixth ed.; Wiley: Hoboken, NJ, USA, 2009.
70. Effendy; Marchetti, F.; Pettinari, C.; Pettinari, R.; Ricciutelli, M.; Skelton, B.W.; White, A.H. (Bis(1,2,4-triazol-1-yl)methane)silver(I) phosphino complexes: Structures and spectroscopic properties of mixed-ligand coordination polymers. *Inorg. Chem.* **2004**, *43*, 2157–2165. [[CrossRef](#)]
71. Nakamoto, K. *Infrared and Raman Spectra of Inorganic and Coordination Compounds, Part B*, sixth ed.; Wiley: Hoboken, NJ, USA, 2009.
72. Burchell, T.J.; Puddephatt, R.J. Homochiral and heterochiral coordination polymers and networks of silver(I). *Inorg. Chem.* **2006**, *45*, 650–659. [[CrossRef](#)]
73. Christe, K.O.; Naumann, D. Vibrational spectra of trifluoroacetates. *Spectrochim. Acta A* **1973**, *29*, 2017–2024. [[CrossRef](#)]
74. Miles, M.G.; Doyle, G.; Cooney, R.P.; Tobias, R.S. Raman and infrared spectra and normal coordinates of the trifluoromethanesulfonate and trichloromethanesulfonate anions. *Spectrochim. Acta A* **1969**, *25*, 1515–1526. [[CrossRef](#)]
75. Bala, R.; Sharma, R.P.; Bond, A.D. Second-sphere coordination in hexaamminecobalt(III) salt with organic sulphonate anions: Synthesis, characterization and X-ray crystal structure of [Co(NH₃)₆](CH₃SO₃)₃. *J. Mol. Struct.* **2007**, *830*, 198–203. [[CrossRef](#)]

76. Rosenthal, M.R. The myth of the non-coordinating anion. *J. Chem. Educ.* **1973**, *50*, 331–334. [[CrossRef](#)]
77. Awaleh, M.P.; Badia, A.; Brisse, F. Coordination networks with flexible ligands based on silver(I) salts: Complexes of 1,3-bis(phenylthio)propane with silver(I) salts of PF_6^- , CF_3COO^- , $\text{CF}_3\text{CF}_2\text{COO}^-$, $\text{CF}_3\text{CF}_2\text{CF}_2\text{COO}^-$, $p\text{-TsO}^-$, and CF_3SO_3^- . *Inorg. Chem.* **2005**, *44*, 7833–7845. [[CrossRef](#)]
78. Zhang, J.-P.; Kitagawa, S. Supramolecular isomerism, framework flexibility, unsaturated metal center, and porous property of Ag(I)/Cu(I) 3,3',5,5'-tetramethyl-4,4'-bipyrazolate. *J. Am. Chem. Soc.* **2008**, *130*, 907–917. [[CrossRef](#)]
79. Masciocchi, N.; Moret, M.; Cairati, P.; Sironi, A.; Ardizzioia, G.A.; La Monica, G. The multiphase nature of the Cu(pz) and Ag(pz) (Hpz = pyrazole) systems: Selective synthesis and ab-initio X-ray powder diffraction structural characterization of copper(I) and silver(I) pyrazolates. *J. Am. Chem. Soc.* **1994**, *116*, 7668–7676. [[CrossRef](#)]
80. Abate, G.; Aseffa, A.; Selassie, A.; Goshu, S.; Fekade, B.; WoldeMeskal, D.; Miörner, H. Direct colorimetric assay for rapid detection of rifampin-resistant Mycobacterium tuberculosis. *J. Clin. Microbiol.* **2004**, *42*, 871–873. [[CrossRef](#)]
81. Thompson, N.C. Silver. In *Comprehensive Inorganic Chemistry*; Bailey, J.C., Ed.; Pergamon Press: Oxford, UK, 1973; Volume 3, pp. 79–128.
82. Nawaz, M.; Han, M.Y.; Kim, T.; Manzoor, U.; Amin, M.T. Silver disinfection of Pseudomonas aeruginosa and E. coli in rooftop harvested rainwater for potable purposes. *Sci. Total Environ.* **2012**, *431*, 20–25. [[CrossRef](#)]
83. Jung, W.K.; Koo, H.C.; Kim, K.W.; Shin, S.; Kim, S.H.; Park, Y.H. Antibacterial activity and mechanism of action of the silver ion in Staphylococcus aureus and Escherichia coli. *Appl. Environ. Microbiol.* **2008**, *74*, 2171–2178. [[CrossRef](#)]



© 2019 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).