

CRYSTALLOGRAPHIC
COMMUNICATIONSOPEN  ACCESS

ISSN 2056-9890

Crystal structure of (2*E*)-1-(5-bromothiophen-2-yl)-3-(2-chlorophenyl)prop-2-en-1-one

B. R. Anitha,^a M. Vinduvahini,^b A. J. Ravi^a and
H. C. Devarajegowda^{a*}

^aDepartment of Physics, Yuvaraja's College (Constituent College), University of Mysore, Mysore 570 005, Karnataka, India, and ^bDepartment of Physics, Sri D Devaraja Urs Govt. First Grade College, Hunsur 571 105, Mysore District, Karnataka, India. *Correspondence e-mail: devarajegowda@yahoo.com

Received 7 November 2015; accepted 7 November 2015

Edited by E. R. T. Tiekink, University of Malaya, Malaysia


In the title compound, C₁₃H₈BrClOS, the thienyl ring is not coplanar with the benzene ring, their planes forming a dihedral angle of 13.2 (4)°. In the crystal, molecules stack along the *a* axis, with the interplanar separation between thienyl rings and between benzene rings being 3.925 (6) Å. The sample is an inversion twin.

Keywords: crystal structure; chalcone; π – π interactions.

CCDC reference: 1435865

1. Related literature

For general background to chalcones, see: Lin *et al.* (2001); Horng *et al.* (2003); López *et al.* (2001); Liu *et al.* (2003). For related crystal structures, see: Liang *et al.* (2011); Alex *et al.* (1993); Li & Su (1993).

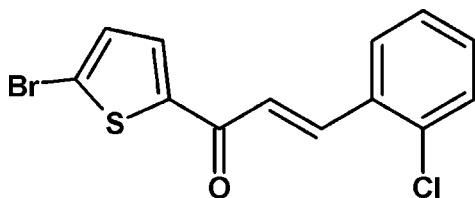

2. Experimental

2.1. Crystal data

C₁₃H₈BrClOS

*M*_r = 327.61

Orthorhombic, *Pc*2₁*b*
a = 3.9247 (19) Å
b = 11.549 (6) Å
c = 28.111 (14) Å
V = 1274.1 (11) Å³

Z = 4
Mo *K*α radiation
 μ = 3.58 mm⁻¹
T = 293 K
0.24 × 0.20 × 0.12 mm

2.2. Data collection

Bruker SMART CCD area-detector diffractometer
Absorption correction: ψ scan (*SADABS*; Sheldrick, 2007)
*T*_{min} = 0.770, *T*_{max} = 1.000

12995 measured reflections
3007 independent reflections
2096 reflections with *I* > 2σ(*I*)
*R*_{int} = 0.065

2.3. Refinement

R[*F*² > 2σ(*F*²)] = 0.062
wR(*F*²) = 0.137
S = 1.10
3007 reflections
155 parameters
1 restraint
H-atom parameters constrained

$\Delta\rho_{\max}$ = 0.79 e Å⁻³
 $\Delta\rho_{\min}$ = -0.33 e Å⁻³
Absolute structure: refined as an inversion twin
Absolute structure parameter: 0.15 (3)

Data collection: *SMART* (Bruker, 2001); cell refinement: *SAINTE* (Bruker, 2001); data reduction: *SAINTE*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL2014* (Sheldrick, 2015); molecular graphics: *ORTEP-3 for Windows* (Farrugia, 2012); software used to prepare material for publication: *SHELXL2014*.

Acknowledgements

The authors thank Professor T. N. Guru Row, SSCU, IISc, Bangalore, for support in the X-ray data collection.

Supporting information for this paper is available from the IUCr electronic archives (Reference: TK5406).

References

- Alex, G., Srinivasan, S., Krishnasamy, V., Suresh, R. V., Iyer, R. & Iyer, P. R. (1993). *Acta Cryst.* **C49**, 70–72.
Bruker (2001). *SMART* and *SAINTE*. Bruker AXS Inc., Madison, Wisconsin, USA.
Farrugia, L. J. (2012). *J. Appl. Cryst.* **45**, 849–854.
Horng, H. K., Lo, T. T., Kun, L. Y., Cheng, T. L., Jih, P. W. & Chun, N. L. (2003). *Bioorg. Med. Chem.* **1**, 105–111.
Li, Z. & Su, G. (1993). *Acta Cryst.* **C49**, 1075–1077.
Liang, Y.-S., Mu, S., Wang, J.-Y. & Liu, D.-K. (2011). *Acta Cryst.* **E67**, o830.
Lin, C., Hsieh, H., Ko, H., Hsu, M., Lin, H., Chang, Y., Chung, M., Kang, J., Wang, J. & Teng, C. (2001). *Drug Dev. Res.* **53**, 9–14.
Liu, M., Wilairat, P., Croft, S. L., Tan, A. L. & Go, M. L. (2003). *Bioorg. Med. Chem.* **11**, 2729–2738.
López, S. N., Castelli, M. V., Zacchino, S. A., Domínguez, J. N., Lobo, G., Charris-Charris, J., Cortés, J. C., Ribas, J. C., Devia, C., Rodríguez, A. M. & Enriz, R. D. (2001). *Bioorg. Med. Chem.* **9**, 1999–2013.
Sheldrick, G. M. (2007). *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
Sheldrick, G. M. (2015). *Acta Cryst.* **C71**, 3–8.

supporting information

Acta Cryst. (2015). E71, o930 [doi:10.1107/S2056989015021155]

Crystal structure of (2*E*)-1-(5-bromothiophen-2-yl)-3-(2-chlorophenyl)prop-2-en-1-one

B. R. Anitha, M. Vinduvahini, A. J. Ravi and H. C. Devarajewoda

S1. Comment

Chalcones are alpha,beta unsaturated ketones, widely distributed in nature and are extensively studied for their biological activity (Lin *et al.*, 2001; Horng *et al.*, 2003; López *et al.*, 2001; Liu *et al.*, 2003). We report here the crystal structure of a bromo derivative of hetero aryl chalcone which has shown aldose reductase inhibition in the virtual screening study conducted by us.

The asymmetric unit of (2*E*)-1-(5-bromo-2-thienyl)-3-(2-chlorophenyl) prop-2-en-1-one, C₁₃H₈Br Cl O S, contains just one molecule (Fig. 1). The five-membered thiophene ring (S2,C5–C8) is not coplanar with the benzene ring (C12–C17); the dihedral angle between the two planes is 13.2 (4)°. Bond lengths and angles are in good agreement with those observed in related crystal structures (Liang *et al.*, 2011; Alex *et al.*, 1993; Li *et al.*, 1993).

S2. Experimental

A mixture of 2-acetyl-5-bromothiophene (0.01 mol) and 2-chlorobenzaldehyde (0.01 mol) were stirred in ethanol (30 ml) and then an aqueous solution of potassium hydroxide (40%,15 ml) was added. The mixture was kept over night at room temperature, poured into crushed ice and acidified with dilute hydrochloric acid. The precipitated chalcone was filtered and crystallized from ethanol.

S3. Refinement

All H atoms were positioned at calculated positions with C—H = 0.93 Å, and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. The sample was refined as an inversion twin.

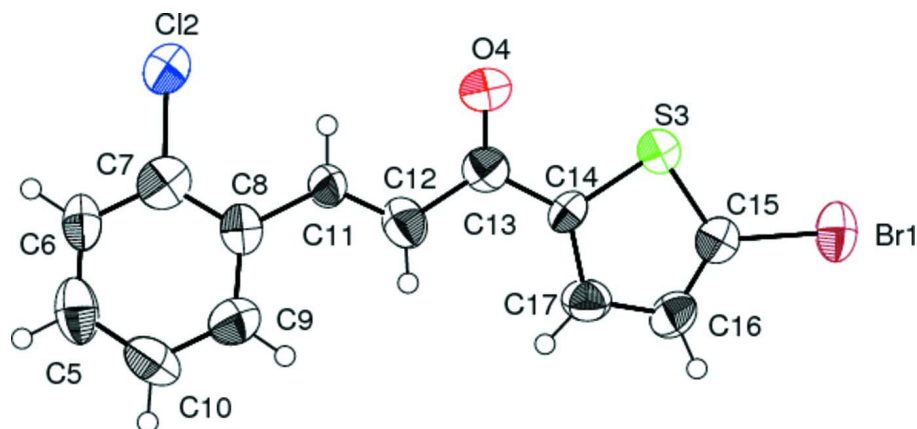


Figure 1

The molecular structure of the title compound, with displacement ellipsoids drawn at the 50% probability level.

(2E)-1-(5-Bromothiophen-2-yl)-3-(2-chlorophenyl)prop-2-en-1-one*Crystal data*C₁₃H₈BrClOSM_r = 327.61Orthorhombic, *Pc2₁b*

a = 3.9247 (19) Å

b = 11.549 (6) Å

c = 28.111 (14) Å

V = 1274.1 (11) Å³

Z = 4

F(000) = 648

D_x = 1.708 Mg m⁻³

Melting point: 342 K

Mo Kα radiation, λ = 0.71073 Å

Cell parameters from 3007 reflections

θ = 2.3–28.0°

μ = 3.58 mm⁻¹

T = 293 K

Prism, colourless

0.24 × 0.20 × 0.12 mm

*Data collection*Bruker SMART CCD area-detector
diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

ω and φ scans

Absorption correction: ψ scan

(SADABS; Sheldrick, 2007)

T_{min} = 0.770, T_{max} = 1.000

12995 measured reflections

3007 independent reflections

2096 reflections with I > 2σ(I)

R_{int} = 0.065θ_{max} = 28.0°, θ_{min} = 2.3°

h = -5→5

k = -15→14

l = -37→36

*Refinement*Refinement on F²

Least-squares matrix: full

R[F² > 2σ(F²)] = 0.062wR(F²) = 0.137

S = 1.10

3007 reflections

155 parameters

1 restraint

Hydrogen site location: inferred from
neighbouring sites

H-atom parameters constrained

w = 1/[σ²(F_o²) + (0.0565P)² + 0.585P]where P = (F_o² + 2F_c²)/3(Δ/σ)_{max} < 0.001Δρ_{max} = 0.79 e Å⁻³Δρ_{min} = -0.33 e Å⁻³

Absolute structure: refined as an inversion twin

Absolute structure parameter: 0.15 (3)

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refined as a 2-component inversion twin.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (Å²)

	x	y	z	U _{iso} */U _{eq}
Br1	0.8042 (2)	0.11487 (13)	0.17078 (3)	0.0615 (4)
S2	0.5184 (8)	0.2199 (2)	0.07773 (9)	0.0516 (7)
Cl2	-0.0696 (11)	0.3138 (3)	-0.17931 (10)	0.0789 (10)
O4	0.200 (2)	0.2992 (7)	-0.0100 (3)	0.072 (2)

C5	0.617 (2)	0.1001 (11)	0.1095 (3)	0.045 (2)
C6	0.541 (3)	0.0007 (10)	0.0881 (4)	0.056 (3)
H6	0.5781	-0.0720	0.1014	0.068*
C7	0.399 (3)	0.0198 (10)	0.0433 (4)	0.055 (3)
H7	0.3336	-0.0393	0.0228	0.066*
C8	0.367 (2)	0.1372 (9)	0.0325 (3)	0.040 (2)
C9	0.224 (2)	0.1930 (9)	-0.0097 (4)	0.047 (2)
C10	0.115 (2)	0.1212 (13)	-0.0502 (3)	0.056 (2)
H10	0.1262	0.0410	-0.0477	0.067*
C11	0.004 (3)	0.1676 (9)	-0.0897 (3)	0.050 (3)
H11	-0.0011	0.2481	-0.0904	0.060*
C12	-0.1123 (19)	0.1090 (13)	-0.1328 (3)	0.047 (2)
C13	-0.161 (2)	0.1657 (10)	-0.1751 (4)	0.056 (3)
C14	-0.284 (2)	0.1127 (16)	-0.2156 (3)	0.059 (2)
H14	-0.3209	0.1551	-0.2433	0.071*
C15	-0.351 (3)	-0.0028 (14)	-0.2143 (4)	0.071 (3)
H15	-0.4279	-0.0402	-0.2415	0.085*
C16	-0.305 (3)	-0.0644 (12)	-0.1730 (4)	0.070 (3)
H16	-0.3591	-0.1428	-0.1723	0.084*
C17	-0.179 (3)	-0.0115 (10)	-0.1326 (4)	0.065 (3)
H17	-0.1375	-0.0550	-0.1053	0.077*

Atomic displacement parameters (Å²)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Br1	0.0533 (5)	0.0886 (8)	0.0426 (5)	0.0105 (8)	-0.0063 (4)	-0.0005 (9)
S2	0.0619 (19)	0.0474 (14)	0.0454 (14)	0.0001 (14)	-0.0050 (14)	-0.0022 (12)
Cl2	0.114 (3)	0.0636 (19)	0.0588 (18)	-0.0100 (19)	-0.0207 (17)	0.0143 (15)
O4	0.105 (6)	0.045 (5)	0.067 (5)	-0.003 (4)	-0.014 (4)	0.005 (4)
C5	0.043 (4)	0.049 (6)	0.043 (4)	0.002 (6)	0.003 (3)	0.003 (5)
C6	0.060 (7)	0.050 (7)	0.060 (7)	0.013 (6)	-0.009 (6)	0.012 (5)
C7	0.063 (7)	0.040 (6)	0.063 (7)	0.004 (5)	-0.004 (5)	-0.002 (5)
C8	0.038 (5)	0.046 (7)	0.036 (4)	0.002 (4)	0.001 (3)	0.008 (4)
C9	0.039 (6)	0.049 (7)	0.054 (6)	-0.006 (4)	-0.002 (4)	0.004 (5)
C10	0.056 (5)	0.059 (6)	0.053 (5)	0.006 (7)	-0.005 (4)	-0.010 (7)
C11	0.059 (7)	0.048 (5)	0.043 (5)	-0.016 (4)	-0.012 (5)	0.005 (4)
C12	0.037 (4)	0.063 (6)	0.041 (4)	0.001 (7)	0.004 (3)	-0.002 (6)
C13	0.042 (5)	0.065 (7)	0.062 (7)	0.005 (5)	0.012 (5)	0.005 (5)
C14	0.063 (6)	0.075 (7)	0.039 (4)	0.006 (8)	-0.009 (4)	-0.004 (9)
C15	0.069 (8)	0.110 (11)	0.034 (6)	0.007 (7)	0.002 (5)	-0.012 (6)
C16	0.074 (8)	0.059 (8)	0.077 (9)	-0.015 (6)	0.002 (7)	-0.023 (7)
C17	0.073 (7)	0.055 (7)	0.066 (7)	-0.007 (6)	-0.004 (6)	0.010 (6)

Geometric parameters (Å, °)

Br1—C5	1.880 (9)	C10—H10	0.9300
S2—C5	1.691 (11)	C11—C12	1.462 (13)
S2—C8	1.697 (10)	C11—H11	0.9300

C12—C13	1.750 (12)	C12—C13	1.370 (14)
O4—C9	1.230 (12)	C12—C17	1.417 (19)
C5—C6	1.329 (16)	C13—C14	1.382 (15)
C6—C7	1.397 (14)	C14—C15	1.36 (3)
C6—H6	0.9300	C14—H14	0.9300
C7—C8	1.395 (16)	C15—C16	1.374 (17)
C7—H7	0.9300	C15—H15	0.9300
C8—C9	1.462 (13)	C16—C17	1.381 (16)
C9—C10	1.473 (15)	C16—H16	0.9300
C10—C11	1.306 (13)	C17—H17	0.9300
C5—S2—C8	90.9 (5)	C10—C11—H11	115.9
C6—C5—S2	114.6 (7)	C12—C11—H11	115.9
C6—C5—Br1	125.4 (9)	C13—C12—C17	116.6 (10)
S2—C5—Br1	120.0 (7)	C13—C12—C11	122.8 (12)
C5—C6—C7	111.2 (10)	C17—C12—C11	120.6 (10)
C5—C6—H6	124.4	C12—C13—C14	123.5 (13)
C7—C6—H6	124.4	C12—C13—Cl2	119.8 (10)
C8—C7—C6	112.7 (10)	C14—C13—Cl2	116.7 (10)
C8—C7—H7	123.7	C15—C14—C13	118.7 (11)
C6—C7—H7	123.7	C15—C14—H14	120.7
C7—C8—C9	129.7 (9)	C13—C14—H14	120.7
C7—C8—S2	110.7 (7)	C14—C15—C16	120.4 (10)
C9—C8—S2	119.6 (8)	C14—C15—H15	119.8
O4—C9—C8	118.4 (10)	C16—C15—H15	119.8
O4—C9—C10	122.2 (10)	C15—C16—C17	120.8 (12)
C8—C9—C10	119.5 (10)	C15—C16—H16	119.6
C11—C10—C9	121.5 (13)	C17—C16—H16	119.6
C11—C10—H10	119.2	C16—C17—C12	119.8 (11)
C9—C10—H10	119.2	C16—C17—H17	120.1
C10—C11—C12	128.2 (12)	C12—C17—H17	120.1
C8—S2—C5—C6	-0.3 (8)	C9—C10—C11—C12	-179.9 (9)
C8—S2—C5—Br1	-178.3 (5)	C10—C11—C12—C13	-166.9 (10)
S2—C5—C6—C7	0.8 (12)	C10—C11—C12—C17	12.5 (16)
Br1—C5—C6—C7	178.7 (7)	C17—C12—C13—C14	3.3 (14)
C5—C6—C7—C8	-1.1 (14)	C11—C12—C13—C14	-177.3 (9)
C6—C7—C8—C9	-178.2 (10)	C17—C12—C13—Cl2	-177.6 (8)
C6—C7—C8—S2	0.9 (12)	C11—C12—C13—Cl2	1.9 (13)
C5—S2—C8—C7	-0.4 (8)	C12—C13—C14—C15	-2.4 (15)
C5—S2—C8—C9	178.8 (8)	Cl2—C13—C14—C15	178.5 (8)
C7—C8—C9—O4	175.0 (10)	C13—C14—C15—C16	1.8 (17)
S2—C8—C9—O4	-4.0 (13)	C14—C15—C16—C17	-2.3 (19)
C7—C8—C9—C10	-5.4 (16)	C15—C16—C17—C12	3.3 (18)
S2—C8—C9—C10	175.6 (7)	C13—C12—C17—C16	-3.7 (15)
O4—C9—C10—C11	3.5 (16)	C11—C12—C17—C16	176.8 (10)
C8—C9—C10—C11	-176.1 (9)		