


 Cite this: *RSC Adv.*, 2020, 10, 4201

Electronic and optical properties of monolayer MoS₂ under the influence of polyethyleneimine adsorption and pressure

 Ong Kim Le,^a Viorel Chihai,  My-Phuong Pham-Ho^{*ac} and Do Ngoc Son ^{*a}

MoS₂ is one of the well-known transition metal dichalcogenides. The moderate bandgap of monolayer MoS₂ is fascinating for the new generation of optoelectronic devices. Unfortunately, MoS₂ is sensitive to gases in the environment causing its original electronic properties to be modified unexpectedly. This problem has been solved by coating MoS₂ with polymers such as polyethyleneimine (PEI). Furthermore, the application of pressure is also an effective method to modify the physical properties of MoS₂. However, the effects of polyethyleneimine and pressure on the electronic and optical properties of monolayer MoS₂ remain unknown. Therefore, we elucidated this matter by using density functional theory calculations. The results showed that the adsorption of the PEI molecule significantly reduces the width of the direct bandgap of the monolayer MoS₂ to 0.55 eV because of the occurrence of the new energy levels in the bandgap region due to the contribution of the N-2p_z state of the PEI molecule. Remarkably, the transition from semiconductor to metal of the monolayer MoS₂ and the MoS₂/PEI system occurs at the tensile pressure of 24.95 and 21.79 GPa, respectively. The bandgap of these systems approaches 0 eV at the corresponding pressures. Importantly, new peaks in the optical spectrum of the clean MoS₂ and MoS₂/PEI appear in the ultraviolet region under compressive pressures and the infrared region under tensile strains.

 Received 1st November 2019
Accepted 19th January 2020

DOI: 10.1039/c9ra09042h

rsc.li/rsc-advances

1. Introduction

MoS₂ is one of the most often studied transition metal dichalcogenides (TMDs)^{1–24} due to the convergence of many advanced properties for optical,¹ electronic,² and mechanical³ applications. Similar to graphene, the bonding between the layers of MoS₂ is the weak van der Waals interaction. Therefore, the monolayer of MoS₂ can be fabricated by exfoliation, which has a thickness of about 0.65 nm. In particular, the monolayer MoS₂ has a direct bandgap of *ca.* 1.8 eV,⁴ which makes this material suitable for transistors,⁵ photodetectors, and light-emitting diodes.⁶ Field-effect transistors (FETs) of monolayer MoS₂ demonstrated a high on/off current ratio exceeding 10⁸ and the electron mobility of at least 200 cm² V⁻¹ s⁻¹.⁵ The main problem of MoS₂ is that it is sensitive to oxygen gas in air, which modifies its electronic properties unexpectedly. Thus, the bandgap becomes narrower and even disappeared after a few days of exposure to oxygen gas.⁷ To solve this problem, the

dichalcogenide can be covered with polymers such as polyethyleneimine (PEI).^{8,9}

Furthermore, control of the electronic and optical properties of the monolayer MoS₂ by changing the crystal structure,¹⁰ layer thickness,⁴ and applying strain¹¹ was achieved. The results showed that the homogeneous biaxial tensile strain of around 10% led to the semiconductor-to-metal transition in all semiconducting TMDs.¹² Several theoretical and experimental studies showed that the bandgap of the monolayer MoS₂ decreases as the tensile strain increases,^{12,13} while it is a parabola for compression.^{14–17} Fan *et al.* demonstrated that the bandgap at the K point changes from direct to indirect with compressive pressure.¹⁴ Generally, the influence on the electronic structure properties of monolayer MoS₂ depends on the type of applied strain. Experimentally, it is difficult to exert a homogeneous hydrostatic strain on a 2D material sample and can only generate a biaxial compressive strain up to 0.2% with elaborate setups.¹⁸ In a recent study, the monolayer MoS₂ was investigated under extreme hydrostatic pressures of up to 30 GPa. Although a higher pressure is not experimentally achievable at present, a metallization at the compressive pressure of 68 GPa was predicted by theoretical calculations.¹⁹ In addition to the ability to tune the electronic properties of the monolayer MoS₂, the applied strain was found to modify the photoluminescence (PL) intensity. The PL maximum peak of the monolayer MoS₂ exhibited a blue shift^{20,21} at the rate of

^aHo Chi Minh City University of Technology, VNU-HCM, 268 Ly Thuong Kiet Street, District 10, Ho Chi Minh City, Vietnam. E-mail: pnhphuong@hcmut.edu.vn; dnson@hcmut.edu.vn

^bInstitute of Physical Chemistry "Ilie Murgulescu" of the Romanian Academy, Splaiul Independentei 202, Sector 6, 060021 Bucharest, Romania

^cInstitute for Computational Science and Technology, Quang Trung Software City, SBI Building, Street No. 3, Tan Chanh Hiep Ward, District 12, Ho Chi Minh City, Vietnam



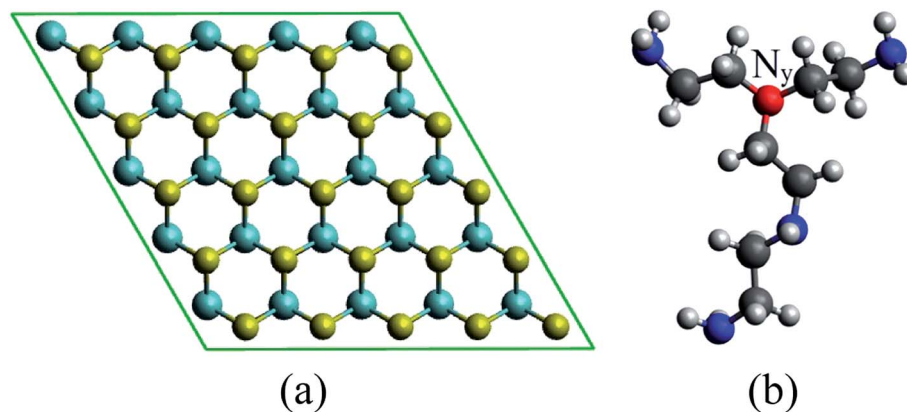


Fig. 1 The optimized structures of (a) the monolayer MoS₂ and (b) the truncated-branched PEI molecule. Cyan, yellow, grey, blue, and white colors represent Mo, S, C, N, and H atoms, respectively. Here, the N_y symbol denotes the N atom (red color) with three alkyl groups.

approximately 20 meV GPa⁻¹. At the pressure of 25 GPa, both real and imaginary parts of the dielectric function were shifted to red, and the peak height increases correspondence with an enhancement of the optical absorption.²¹ These results demonstrated that one can adjust the electronic and optical properties of MoS₂ by applying pressures. Interestingly, the monolayer MoS₂ phototransistor exhibited a better photoresponsivity compared to the graphene-based devices.²²

The effects of organic molecules adsorption such as TCNQ, TCNE, TTF, BV, F4TCNQ, and benzene on the electronic and optical properties of the monolayer MoS₂ have been studied in the literature.^{23–26} A reduction of the bandgap was found due to

the existence of the flat molecular levels of the organic molecules in the bandgap region of the monolayer MoS₂. The theoretical study showed that the adsorption of TCNQ significantly enhances the peak height of the optical absorption of the monolayer MoS₂ in the infrared region of the spectrum.^{23,24} Du *et al.* experimentally studied the adsorption of the PEI on multilayer MoS₂ field-effect transistors.⁸ The experimental results demonstrated that a reduction of 2.6 times in sheet resistance and 1.2 times in contact resistance have been achieved. The enhancement of electrical properties was reflected in an improvement of 70% for ON-current and 50% for extrinsic field-effect mobility. Our previous study showed that the

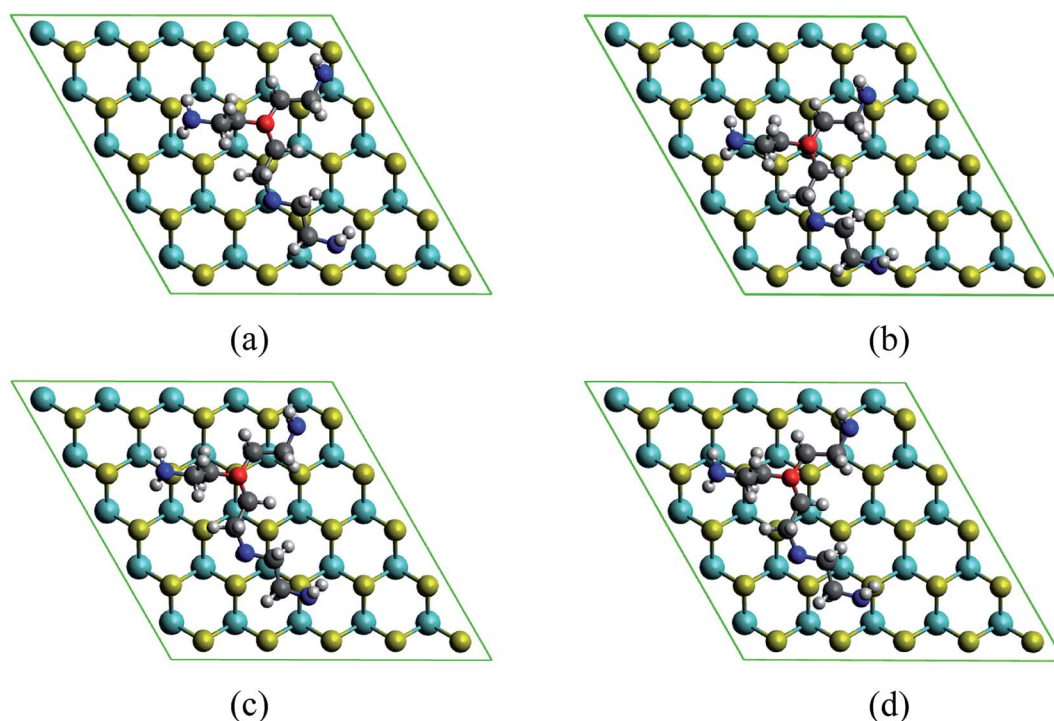


Fig. 2 The favorable adsorption sites of the PEI molecule on the MoS₂ monolayer when the N_y nitrogen atom over the hollow site (a), the molybdenum atom (b), the sulfur atom (c), and the bridge site of two S atoms (d).

Table 1 Adsorption energy E_a , the distances d_{N-S} , d_{C-S} , and d_{H-S} (Å) from the nearest atoms of the PEI fragment to the monolayer MoS₂ with the change of lattice constant a

a (Å)	E_a (eV)	d_{N-S} (Å)	d_{C-S} (Å)	d_{H-S} (Å)
2.84	0.139	3.53	3.63	2.26
3.00	0.063	3.57	3.72	2.30
3.18	-0.007	3.63	3.76	2.37
3.32	-0.085	3.68	3.81	2.42
3.48	-0.315	3.73	3.88	2.46
3.64	-0.479	3.83	3.93	2.51

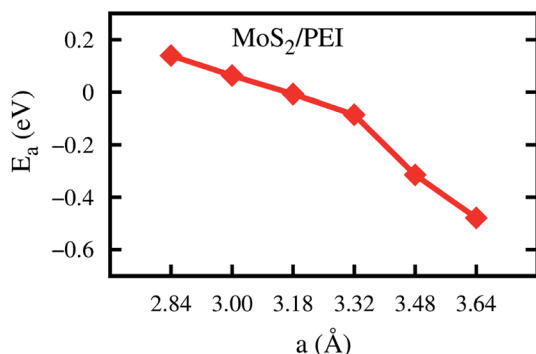


Fig. 3 The adsorption energy of the PEI fragment on the monolayer MoS₂ as a function of the lattice constant.

adsorption of the PEI molecule enhances the luminescence ability of the multi-layer MoS₂ FET from 0.14 to 4.41 AW⁻¹.⁹ However, the influences of both pressure and the PEI adsorption on the electronic and optical properties of MoS₂ remain unknown. Therefore, in the present work, we are going to clarify this matter by using the density functional theory calculations.

1.1. Computational method

We used density functional theory calculations with the aid of the Vienna *ab initio* simulation package.^{27–29} The Perdew–Burke–Ernzerhof version of the generalized gradient approximation (GGA-PBE) was utilized for the exchange–correlation energy.^{30,31} The calculations of the band structure of monolayer MoS₂ using various schemes have been summarized in the literature.³² The GGA functional plus van der Waals corrections underestimate the bandgap, while GW correction and HSE06 functional overestimate it. Local

density approximation and GGA-PBE methods offered the most reasonable band gaps. Considering this result, as well as the accuracy in the geometries obtained by the GGA-PBE functional, in this study we used this functional to determine the effects of PEI doping on the MoS₂ surface. The projector-augmented-wave method was taken into account for the electron–ion interactions.^{33,34} The plane-wave basis set was expanded with the cutoff energy of 600 eV. The surface Brillouin zone integration was performed by using the special k -point sampling technique of Monkhorst–Pack³⁵ with the k -point mesh of $3 \times 3 \times 1$. We also included the dipole corrections^{36,37} in the simulation for a periodic supercell to correct the interaction between the repeated images. The Gaussian smearing of order 0 with the sigma value of 0.1 was used to speed up the convergence of the calculations. The monolayer MoS₂ (Fig. 1a) was modeled by the supercell approach using the 5×5 unit cell with the vacuum space of 16 Å along the z -direction. The vacuum space has been checked to make sure of no significant interaction of repeating images of the supercell. The truncated branched PEI fragment (Fig. 1b) was constructed based on the following requirements:⁹ (1) the total charge of the fragment is neutral, (2) the structure of the truncated fragment should contain nitrogen atoms accompany with one, two, and three alkyl groups. All atoms were allowed to fully relax during the geometry optimization until the Hellmann–Feynman force acting on each atom was less than 0.001 eV Å⁻¹. Spin-polarized calculations were performed for the geometry optimization and the calculation of band structure.

Adsorption energy was calculated to understand the binding strength of the PEI fragment on MoS₂ through the formula:

$$E_a = E_{\text{sub+PEI}} - (E_{\text{sub}} + E_{\text{PEI}}), \quad (1)$$

where $E_{\text{sub+PEI}}$ is the total energy of the MoS₂ + PEI system. The total energy of the monolayer MoS₂ and that of the isolated PEI fragment are denoted as E_{sub} and E_{PEI} , respectively.

The pressure was estimated from the energy cost over the change of volume by:¹⁹

$$P = \frac{E - E_0}{V - V_0}, \quad (2)$$

here, E and V (E_0 and V_0) are the energy and volume of the strained (unstrained) system, respectively. The unit cell volume of the hexagonal lattice of the MoS₂ was calculated by $V = \frac{\sqrt{3}}{2}a^2c$, where a is the lattice constant and c is the thickness of the slab. We perform the modification of pressure by

Table 2 The structural parameters of the MoS₂ monolayer with the change of lattice constant. See Fig. 4 for the atom index of MoS₂

a (Å)		2.84	3.00	3.18	3.32	3.48	3.64
Average bond length (Å)	S ₁ –S ₂	2.85	3.06	3.18	3.32	3.48	3.57
	S ₁ –S ₃	3.38	3.26	3.13	3.05	2.95	2.88
	Mo ₁ –Mo ₂	2.84	3.00	3.19	3.31	3.46	3.66
	Mo–S	2.37	2.38	2.41	2.45	2.49	2.53
Average bond angle (°)	Mo ₁ –S ₁ –Mo ₂	74.17	78.21	82.30	85.28	88.60	91.29
	S ₁ –Mo ₂ –S ₂	74.32	78.28	82.30	85.08	88.54	90.89
	S ₁ –Mo ₁ –S ₃	91.66	87.65	80.54	79.42	73.07	70.98

Table 3 The structural parameters of PEI under the variation of lattice constant. See Fig. 5 for the atom index of PEI

a (Å)		2.84	3.00	3.18	3.32	3.48	3.64	
Bond length (Å)	N _y -C ₅	1.425	1.437	1.467	1.494	1.525	1.519	
	N _y -C ₄	1.427	1.438	1.462	1.484	1.501	1.486	
	N _y -C ₇	1.443	1.451	1.471	1.488	1.498	1.483	
	N ₁ -C ₁	1.457	1.459	1.465	1.494	1.468	1.455	
	N ₂ -C ₂	1.450	1.444	1.461	1.472	1.486	1.474	
	N ₂ -C ₃	1.436	1.451	1.463	1.478	1.488	1.469	
	N ₃ -C ₆	1.459	1.461	1.464	1.470	1.469	1.459	
	N ₄ -C ₈	1.458	1.460	1.463	1.466	1.461	1.448	
	C ₇ -C ₈	1.509	1.519	1.543	1.570	1.615	1.635	
	C ₃ -C ₄	1.512	1.524	1.538	1.556	1.591	1.599	
	C ₅ -C ₆	1.508	1.514	1.537	1.558	1.588	1.578	
	Bond angle (°)	C ₆ C ₅ N _y	111.32	113.10	116.54	119.13	122.96	123.74
		C ₄ C ₃ N ₂	110.41	112.37	115.27	117.23	118.62	118.63
		C ₈ C ₇ N _y	109.56	110.63	113.54	115.63	119.09	119.27
C ₃ C ₄ N _y		109.81	111.11	115.02	117.74	121.79	122.44	
C ₃ N ₂ C ₂		109.57	112.15	116.40	119.52	123.78	126.79	
C ₅ N _y C ₄		113.45	113.52	114.45	115.11	116.75	116.77	
C ₇ N _y C ₄		112.10	113.19	113.98	114.69	116.59	118.82	
C ₇ N _y C ₅		111.90	110.93	111.71	112.22	113.97	111.86	

varying the lattice constant a while remaining the slab thickness.

Optical properties were determined through the frequency-dependent complex dielectric function, $\varepsilon(\omega) = \varepsilon_1(\omega) + i\varepsilon_2(\omega)^{21,38}$ which is the measure of the light absorption and emission of material. The imaginary part of the dielectric constant $\varepsilon_2(\omega)$ was computed by using the following expression:³⁸

$$\varepsilon_2(\omega) = \frac{2\pi e^2}{V\varepsilon_0} \sum_{\mathbf{k}, \mathbf{v}, \mathbf{c}} |\langle \psi_{\mathbf{k}}^{\mathbf{c}} | \hat{u} \cdot \mathbf{r} | \psi_{\mathbf{k}}^{\mathbf{v}} \rangle|^2 \delta[E_{\mathbf{k}}^{\mathbf{c}} - E_{\mathbf{k}}^{\mathbf{v}} - \hbar\omega], \quad (3)$$

where ω is the frequency of light, ε_0 is the dielectric constant of vacuum. $\psi_{\mathbf{k}}^{\mathbf{c}}$ and $\psi_{\mathbf{k}}^{\mathbf{v}}$ are the conduction and valence band wave functions, respectively. V is the volume of the unit cell and \hat{u} is the vector defining the polarization of the electric field of the incident light. The real part $\varepsilon_1(\omega)$ can be calculated through $\varepsilon_2(\omega)$ using the Kramer-Kronig relation,

$$\varepsilon_1(\omega) = 1 + \left(\frac{2}{\pi}\right) \int_0^{\infty} d\omega' \frac{\omega' \varepsilon_2(\omega')}{(\omega')^2 - \omega^2}. \quad (4)$$

2. Results and discussion

2.1. The adsorption of the PEI fragment on the monolayer MoS₂

We have to perform the geometric optimization of the monolayer MoS₂ before the study of the PEI adsorption. The lattice constant of the monolayer MoS₂ was optimized by the GGA-PBE method and obtained the parameters of $a = b = 3.18$ Å. The average bond length of Mo-S is 2.42 Å. The S-Mo-S and Mo-S-Mo angles are 82.30°. The thickness of the triple atomic layers of MoS₂ is 3.13 Å. These results are in good agreement with the previous experimental and theoretical studies.^{23,39,40}

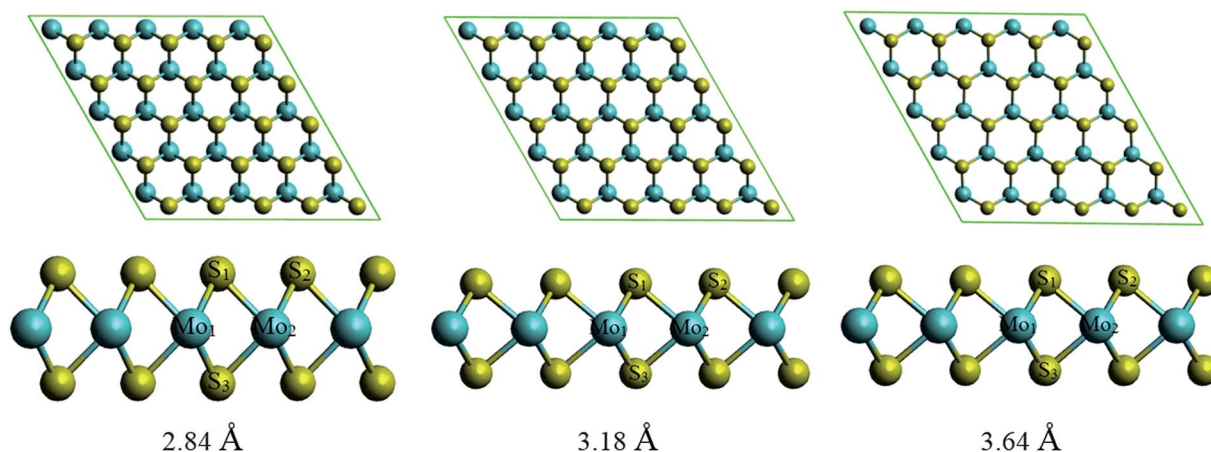


Fig. 4 The upper and lower panels are the top and side views of the MoS₂ slab with the change of lattice constant, respectively.

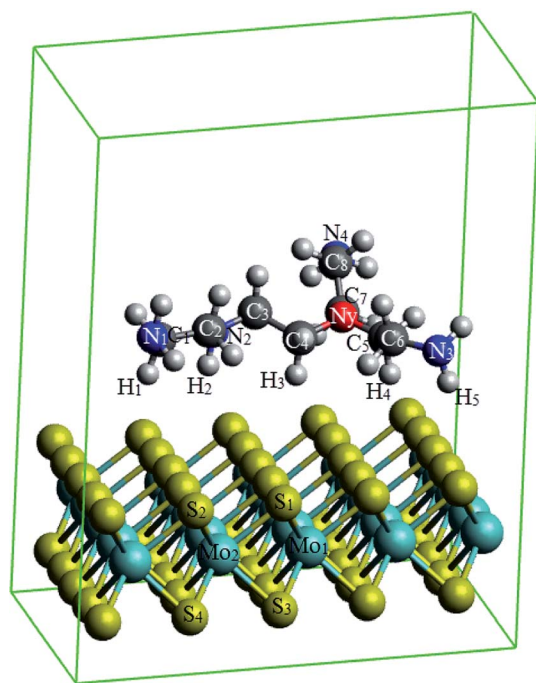


Fig. 5 The atom index of PEI on MoS₂.

To study the influences of the pressure, we varied the lattice constant with the constraint $a = b$ of the clean MoS₂ and the MoS₂/PEI system and explored the differences of two systems before and after changing the lattice constant. We considered the following values of the lattice constant: 2.84, 3.00, 3.18, 3.32, 3.48, and 3.64 Å. Two first values correspond to compressive strains and three last values correspond to the tensile strains.

The MoS₂/PEI system was prepared by loading the PEI fragment on the optimized monolayer MoS₂. The MoS₂/PEI system was allowed to fully relax for every step of the calculations. The PEI fragment was initially placed parallel to the surface of the

Table 4 The bandgap of MoS₂ and MoS₂/PEI

a (Å)	MoS ₂		MoS ₂ /PEI	
	P (GPa)	E_g (eV)	P (GPa)	E_g (eV)
2.84	−56.18	1.05	−50.48	0.53
3.00	−32.44	1.55	−38.51	0.81
3.04	−27.65	1.72	−22.44	0.83
3.12	−10.69	1.80	−11.94	0.82
3.16	−9.46	1.75	−8.12	0.69
3.18	0	1.68	0	0.55
3.20	1.53	1.61	0.95	0.46
3.24	5.04	1.29	5.74	0.02
3.32	10.13	0.81	10.25	0.01
3.48	24.95	0	21.79	0
3.64	41.14	0	31.62	0

monolayer MoS₂ with a vertical distance of around 3.5 Å. Since the stability of the PEI adsorption correlates to the number of nitrogen atoms associated with the surface of the substrate, the stable geometry of the MoS₂/PEI system was obtained with a flat structure of the PEI fragment on the surface of the monolayer MoS₂. We considered several possible adsorption sites of the PEI molecule on the surface of MoS₂, see Fig. 2. After performing the geometric optimization, we obtained the optimized structures of MoS₂/PEI with the total energies of −741.39, −741.38, −741.43, and −741.41 eV for those in Fig. 2a–d, respectively. Based on these energies, we found the most favorable adsorption configuration of the PEI molecule as the N atom with three alkyl groups, denoted as N_y, positioned on the top of the S atom (Fig. 2c). The average vertical distance from the lowest nitrogen atoms, the lowest carbon atoms and the lowest hydrogen atoms of PEI to the surface of the substrate are 3.63, 3.76, and 2.37 Å, respectively.

We now perform the structural optimization for each variation of the lattice constant for the most favorable adsorption

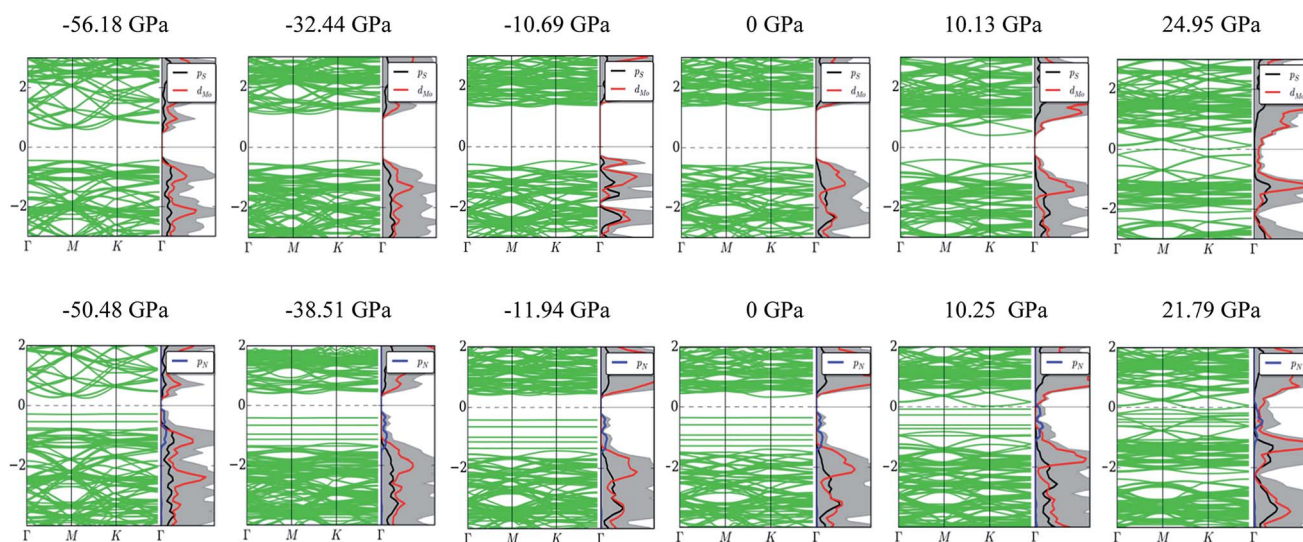


Fig. 6 The band structure and total density of states of MoS₂ (upper panel) and MoS₂/PEI (lower panel) with the variation of pressure.

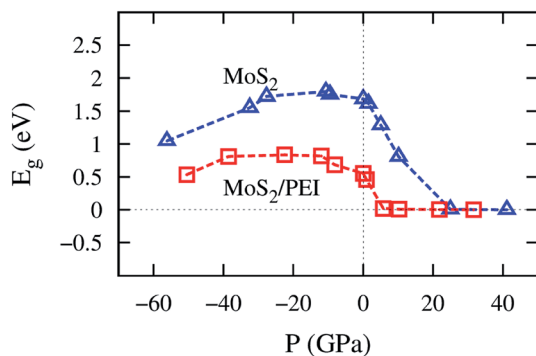


Fig. 7 The bandgap versus pressure of MoS₂ and MoS₂/PEI.

configuration of the PEI molecule on the MoS₂ substrate. The adsorption energy of the PEI fragment on the substrate and the distances from this molecule to the substrate are listed in Table 1. We found that the distances increase slightly with the increase of the lattice constant.

Furthermore, Fig. 3 shows that the adsorption energy becomes more negative; and hence, the favorable order of the PEI adsorption increases with the increase of the lattice constant. For the compression, with the lattice constant $a < 3.18$ Å, the adsorption energy is positive, which indicates that the adsorption of the PEI molecule is unstable on the surface of the monolayer MoS₂. In contrast, for the cases of without strain ($a = 3.18$ Å) and tensile strains ($a > 3.18$ Å), the adsorption energy is negative. This result implies that the adsorption of the PEI molecule is stable. We found that the higher the lattice constant, the stronger the PEI molecule adsorbs. However, the interaction between the PEI molecule and the monolayer MoS₂ is weak and the PEI molecule physisorbed on the MoS₂. Furthermore, the phonon vibrational energy of the stretching mode of PEI is 0.43 eV. This value is comparable to the adsorption energy of PEI; therefore, the adsorption of PEI is thermodynamically unstable except for applying a high enough tensile pressure to the MoS₂/PEI system.

The structural information was shown in Table 2 for MoS₂ and Table 3 for PEI with the change of lattice constant. We found that the average bond length between S₁–S₂, Mo–Mo, Mo–S, and the average bond angles Mo₁–S₁–Mo₂, S₁–Mo₂–S₂

increase, while the thickness of the MoS₂ slab shown by S₁–S₃ and also the angle S₁–Mo₁–S₃ decrease with the increase of lattice constant. Although the structural parameters for the MoS₂ monolayer have been modified, the MoS₂ monolayer under pressure remains the 2H phase similar to that of without strain. We can confirm this information by Fig. 4, where the top view of the MoS₂ shows the honeycomb structure and the side views exhibit a similar structure for all considering lattice constants of 2.84, 3.18, and 3.64 Å. Table 3 shows the structural information of PEI that the bond lengths of N–C and C–C, and the bond angles of C–C–N and C–N–C somehow increase with the increase of the lattice constant.

2.2. Effects of the PEI adsorption and pressure on electronic structure properties of MoS₂

The effects of the PEI adsorption and the pressure variation by changing $a = b$ on the electronic properties of the monolayer MoS₂ were elucidated through the band structure, the density of states (DOS), and the charge exchange of the systems before and after these factors taking place.

Fig. 6 shows that, at zero pressure, the monolayer MoS₂ has a direct bandgap of 1.68 eV at the K point in the Brillouin zone, which is in good agreement with the previous publications.^{4,32,41} The total electronic density of states shows that the valence band maximum (VBM) and the conduction band minimum (CBM) are contributed mainly by Mo-4d states and weakly by S-3p states. The adsorption of the PEI molecule makes the energy levels of the MoS₂/PEI system lower than that of the isolated monolayer MoS₂, simultaneously creates new flat energy levels in the bandgap region which significantly decreases the direct bandgap of the monolayer MoS₂ to 0.55 eV. The new energy levels appear in the region of the valence band of MoS₂/PEI implying that the monolayer MoS₂ became an n-type semiconductor upon the adsorption of the PEI molecule. The new flat energy levels mainly come from the contribution of the N-2p lone pair. Notably, at non-zero pressures, the bandgap of MoS₂ and MoS₂/PEI becomes narrower than that at zero pressure and gradually approaches 0 eV at some specific values of the pressure. When MoS₂ and MoS₂/PEI still show the semiconductor property, the significant difference between the electronic properties of two systems is that the bandgap of MoS₂ changes from direct to indirect upon the variation of pressure, while

Table 5 The Bader charge (e) for the MoS₂/PEI system: (+) charge gain, (–) charge loss. The electrostatic force (e² Å⁻¹) between the H, C, and N atoms of the PEI with the S atoms of the MoS₂ denotes by F_1 , F_2 , and F_3 , respectively. The negative and positive signs of the force imply the attraction and repulsion, respectively. The total force $F = F_1 + F_2 + F_3$

P (GPa)	MoS ₂ /PEI					PEI	MoS ₂	E_g (eV)	F_1	F_2	F_3	F
	23H	8C	5N	25Mo	50S							
–50.48	–1.62	–3.21	4.79	–40.27	40.32	–0.05	0.05	0.53	–28.97	–35.66	54.67	–9.96
–38.51	–1.91	–3.09	4.96	–43.45	43.48	–0.04	0.04	0.81	–36.07	–36.08	60.41	–11.74
0	–1.94	–3.11	5.01	–43.66	43.70	–0.04	0.04	0.55	–35.84	–36.14	60.32	–11.67
10.25	–1.95	–3.10	4.92	–43.27	43.40	–0.13	0.13	0.01	–34.95	–35.30	57.99	–12.25
21.79	–2.52	–2.97	5.07	–42.85	43.27	–0.42	0.42	0	–44.24	–33.16	58.80	–18.60
31.62	–2.76	–3.06	5.24	–42.01	42.59	–0.58	0.58	0	–46.76	–33.21	58.26	–21.71

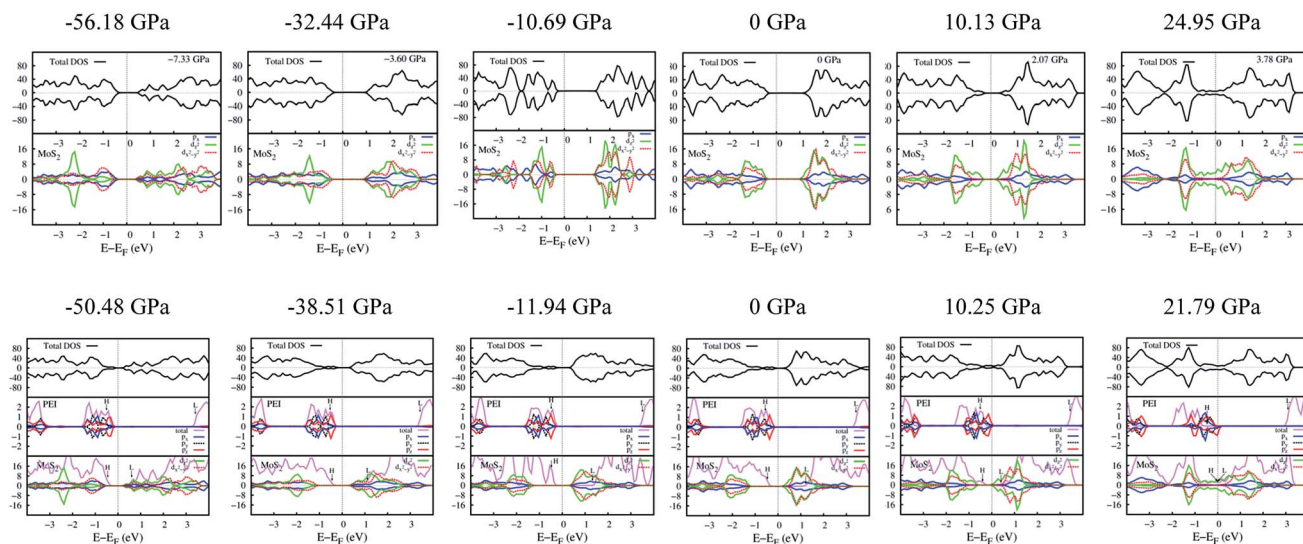


Fig. 8 Total and projected DOS of MoS₂ (upper panel) and MoS₂/PEI (lower panel).

MoS₂/PEI remains direct bandgap with a smaller value due to the flat characteristics of the new energy levels but at a different position of the *k*-point mesh.

The pressure correspondence to the variation of the lattice constant of the MoS₂ and MoS₂/PEI systems was calculated by using the expression (2). The detailed values of the bandgap *versus* the pressure and the lattice constant were listed in Table 4. We found that the pressure varies from −56.18 to 41.14 GPa and −50.48 to 31.62 GPa for the lattice constant from 2.84 to 3.64 Å for the MoS₂ and MoS₂/PEI systems, respectively. The negative and positive signs represent the compressive and tensile strains in that order. We see that the pressure scale for the isolated MoS₂ is similar to that for the MoS₂/PEI system at the same value of the lattice constant.

The bandgap *versus* the pressure is visualized in Fig. 7. We found that the behavior of the bandgap for the isolated MoS₂ is similar to that for MoS₂/PEI, which is a parabola with a maximum value of 1.80 and 0.83 eV at the pressure of −10.69 and −22.44 GPa for the isolated MoS₂ and MoS₂/PEI systems, respectively. Furthermore, when the tensile pressure approaches 24.95 and 21.79 GPa, the bandgap approaches 0 eV for these systems in that order. This result implies that the monolayer MoS₂ and MoS₂/PEI systems transit from semiconductor to metal at the obtained values of the tensile pressure. The transition was found to be a little easier for the MoS₂/PEI than the monolayer MoS₂. The parabolic behavior of the bandgap is in good agreement with the experiment for the isolated MoS₂.¹⁶

The amount of the charge exchange between the monolayer MoS₂ and the PEI fragment was presented by the Bader point charge in Table 5. The plus and minus signs denote the charge gain and loss, respectively. Particularly, the hydrogen and carbon atoms donate while the nitrogen atoms gain charge. The total outcome is that the PEI molecule donates and the MoS₂ gains charge. The charge exchange was found to be inversely proportional to the bandgap. The higher the charge exchange,

the narrower the bandgap becomes. This result supports the nature of the n-type doping to the substrate by the PEI polymer.

In common sense, a simple adsorbate will approach the substrate surface as its adsorption energy becomes more negative. However, for the complicated structure as the PEI molecule, as shown in Table 1, the distances from the nearest N, C, and H atoms of PEI to the surface of the MoS₂ monolayer exhibit that the PEI molecule is slightly moving away from the surface as the lattice constant increases with the more negative

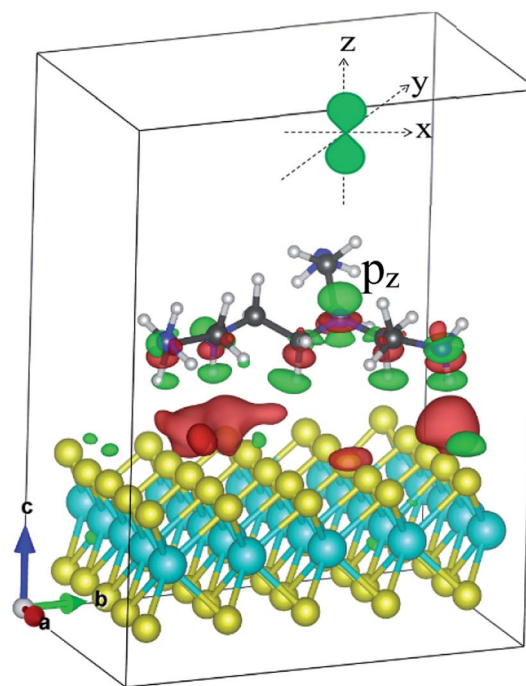


Fig. 9 The charge density difference of the MoS₂/PEI system. Occupied and unoccupied states are presented in red and green, respectively.

Table 6 The HOMO of isolated PEI and the LUMO of isolated MoS₂

	<i>a</i> (Å)	2.84	3.00	3.12	3.16	3.18	3.32	3.48	3.64
Isolated PEI	HOMO (eV)	−0.51	−0.53	−0.49	−0.53	−0.56	−0.51	0.00	0.00
Isolated MoS ₂	LUMO (eV)	0.60	1.11	1.32	1.27	1.22	0.40	0.00	0.00
LUMO–HOMO (eV)		1.11	1.64	1.81	1.80	1.78	0.91	0.00	0.00

adsorption energy. This observation seems to be contradicted; however, it can be explained in terms of the attractive electrostatic force between the PEI and the MoS₂, which increases with the increase of the lattice constant. As shown in Table 5, the attractive force was found for the pairs of H–S and C–S and the repulsive force for the pairs of N–S atoms. The N–S repulsive force is strong enough to win the H–S and C–S attractive forces; and hence, it somehow lifts the whole PEI molecule away from the MoS₂ surface. However, the total electrostatic force *F* remains the increasing attractive property with an increase in the pressure. The increasing attractive property of the total force is attributed mainly to the increase of the attractive interaction of the H atoms with the S atoms.

Fig. 8 presents the total DOS and the orbital projected DOS of the monolayer MoS₂ and MoS₂/PEI systems. At zero pressure, the total DOS exhibits a high symmetry of spin-up and spin-down components implying the non-magnetic properties of both MoS₂ and MoS₂/PEI systems. For the negative pressures, the projected DOS of the monolayer MoS₂ shows that the contribution to the VBM and CBM is attributed to the d_{x²−y²} orbital of the Mo atoms and the p_x state of the S atoms. For the pressure ≥ 0, the d_{z²} orbital becomes dominant for the energy range near the Fermi level. The adsorption of the PEI molecule contributes to the occurrence of the new states, which comes from the contribution of the p_z states of the N atoms. We can see more details in Fig. 9, the charge clouds of the N_y nitrogen atoms clearly exhibit the shape of the p_z orbitals. The charge donation and accumulation distribute on the PEI fragment and the surface of the MoS₂, respectively. This result is in good agreement with the behavior of the Bader point charge.

The parabolic behavior of the bandgap, as shown in Fig. 7, is attributed to the different responses of the d_{x²−y²} and d_{z²} orbitals of the MoS₂ monolayer toward the pressure, see Fig. 8 (upper panel). At the negative pressures, the d_{x²−y²} orbital plays the main role, while at the higher pressures, the d_{z²} orbital gradually becomes dominant at the VBM and CBM. The contribution

from these orbitals is balanced at the VBM and CBM; and hence, the bandgap is broadest for the pressure of −10.69 GPa. When the d_{z²} orbital approaches the Fermi level, the bandgap becomes narrower, as the tensile pressure increases. Furthermore, the study of HOMO and LUMO can support the understanding of the interaction between the MoS₂ substrate and the PEI adsorbate; and hence, the parabolic behavior of the MoS₂/PEI bandgap. We presented the HOMO and LUMO states of the isolated MoS₂ and isolated PEI in Fig. 8 (lower panel). The values of the MoS₂ LUMO and the PEI HOMO were also listed in Table 6. We found that the HOMO–LUMO gap varies with the parabolic behavior as that of the bandgap of the MoS₂/PEI system (Fig. 7), which increases first and then decreases with the increase of the pressure from the negative to the positive value.

2.3. Optical properties of MoS₂ and MoS₂/PEI

In this section, we studied the effects of the PEI adsorption and the pressure on the optical properties of the monolayer MoS₂. The imaginary dielectric function $\epsilon_2(\omega)$ of MoS₂ and MoS₂/PEI systems were calculated through the expression (3) and shown in Table 7. The photon wavelength was calculated by using the formula $\lambda = hc/E_p$, where *h* is the Planck constant, *c* is the speed of light in vacuum, and *E_p* is the photon energy. The obtained result is listed in the third and seventh columns of Table 7.

As shown in Fig. 10a, at *P* = 0 GPa, the photoluminescence spectrum of the monolayer MoS₂ exhibits the main peak at 453 nm within the range of visible light (400–800 nm). The result indicates that the MoS₂ can absorb and emit the blue light, which is in agreement with the previous report.^{22,32} At non-zero pressures, the main PL peak shifts to the longer wavelength and simultaneously suppresses the peak height compared to that at zero pressure. Besides, for the positive pressure, the main peak tends to separate into two peaks. Furthermore, the intensity of the maximum PL is lower for the negative pressure than the positive pressure. We also found new peaks in the

Table 7 The wavelength and dielectric function at the maximum intensity of photoluminescence

<i>P</i> (GPa)	MoS ₂				<i>P</i> (GPa)	MoS ₂ /PEI			
	<i>E_g</i> (eV)	<i>E_p</i> (eV)	λ (nm)	$\epsilon_2(\omega)$		<i>E_g</i> (eV)	<i>E_p</i> (eV)	λ (nm)	$\epsilon_2(\omega)$
−56.18	1.05	4.66	266	11.06	−50.48	0.53	4.61	269	9.98
−32.44	1.55	2.60	477	11.58	−38.51	0.81	2.76	449	11.10
0	1.68	2.73	453	14.88	0	0.55	2.72	456	14.91
10.13	0.81	2.39	521	13.36	10.25	0.01	2.35	527	13.38
24.95	0	2.00	621	13.18	21.79	0	2.01	618	12.86
41.14	0	1.42	873	12.06	31.62	0	1.41	877	11.12

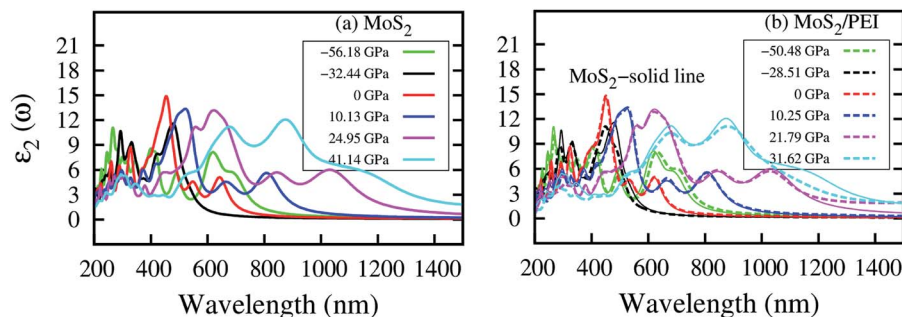


Fig. 10 Imaginary dielectric function $\epsilon_2(\omega)$ versus wavelength for MoS₂ (a) and MoS₂/PEI (b).

photoluminescence of the isolated MoS₂ occurring in the ultraviolet region upon the compression and in the infrared region upon the tensile strain. The photoluminescence spectrum of the MoS₂/PEI system in Fig. 10b remains almost unchanged compared to that of the isolated MoS₂. This result implies that the benefit of the PEI coating is not only to protect the MoS₂ from the adsorption of the unexpected gases but also remain the optical properties of the MoS₂, which can be used for various optoelectronic applications.

3. Conclusion

In this paper, we have studied the electronic and optical properties of the monolayer MoS₂ under the influences of the polyethyleneimine adsorption and the pressure. We found that the bandgap of the monolayer MoS₂ reduces significantly upon the PEI adsorption, which was attributed to the p_z state of the nitrogen atoms occurring in the bandgap region. The bandgap of MoS₂ and MoS₂/PEI systems approaches 0 eV at the tensile pressure of 24.95 and 21.79 GPa, respectively. The pressure also modifies the photoluminescence spectrum of the monolayer MoS₂ and MoS₂/PEI systems as shifting the main peak to the longer wavelength. Particularly, the compression and tensile strain generate new peaks in the ultraviolet and infrared regions, respectively. However, the PEI adsorption does not significantly alter the characteristics of the photoluminescence spectrum of the monolayer MoS₂ at all pressure ranges. The coating of the polyethyleneimine does not only protect the monolayer MoS₂ from the sensitive gases but also remain the optical properties of this system. This result is perhaps useful for the utilization of the MoS₂/PEI in optoelectronic devices.

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

This research was funded by the Ho Chi Minh City Department of Science and Technology under contract number 310/QĐ-KHCNTT (2018). We acknowledge the usage of the computer time and software granted by the Institute of Physical Chemistry of Romanian Academy, Bucharest (HPC infrastructure

developed under the projects Capacities 84 Cp/I of 15.09.2007 and INFRANANOCHEM 19/01.03.2009).

References

- 1 H. Zeng, J. Dai, W. Yao, D. Xiao and X. Cui, Valley polarization in MoS₂ monolayers by optical pumping, *Nat. Nanotechnol.*, 2012, 7(8), 490–493.
- 2 A. Enyashin and G. Seifert, Electronic properties of MoS₂ monolayer and related structures, *Nanosyst.: Phys., Chem., Math.*, 2014, 5(4), 517–539.
- 3 A. Castellanos-Gomez, M. Poot, G. A. Steele, H. S. J. van der Zant, N. Agrait and G. Rubio-Bollinger, Elastic properties of freely suspended MoS₂ nanosheets, *Adv. Mater.*, 2012, 24(6), 772–775.
- 4 K. F. Mak, C. Lee, J. Hone, J. Shan and T. F. Heinz, Atomically thin MoS₂: a new direct-gap semiconductor, *Phys. Rev. Lett.*, 2010, 105, 136805.
- 5 B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti and A. Kis, Single-layer MoS₂ transistors, *Nat. Nanotechnol.*, 2011, 6, 147–150.
- 6 Y. Yu, F. Miao, J. He and Z. Ni, Photodetecting and Light-Emitting Devices Based on Two Dimensional Materials, *Chin. Phys. B*, 2017, 26, 036801.
- 7 J. Martincová, M. Otyepka and P. Lazar, Is Single Layer MoS₂ Stable in the Air?, *Chem.-Eur. J.*, 2017, 23, 13233–13239.
- 8 Y. Du, H. Liu, A. T. Neal, M. Si and P. D. Ye, Molecular Doping of Multilayer MoS₂ Field-Effect Transistors: Reduction in Sheet and Contact Resistances, *IEEE Electron Device Lett.*, 2013, 0741–3106.
- 9 S. Hong, G. Yoo, D. H. Kim, W. G. Song, O. K. Le, Y. Ki Hong, K. Takahashi, I. Omkaram, D. N. Son and S. Kim, The doping mechanism and electrical performance of polyethylenimine-doped MoS₂ transistor, *Phys. Status Solidi C*, 2017, 1600262.
- 10 M. Chhowalla, H. S. Shin, G. Eda, L.-J. Li, K. P. Loh and H. Zhang, The chemistry of two-dimensional layered transition metal dichalcogenide nanosheets, *Nat. Chem.*, 2013, 5(4), 263–275.
- 11 L. Yang, X. D. Cui, J. Zhang, K. Wang, M. Shen, S. Zeng, S. A. Dayeh, L. Feng and B. Xiang, Lattice strain effects on the optical properties of MoS₂ nanosheets, *Sci. Rep.*, 2014, 4, 5649.

- 12 P. Johari and V. B. Shenoy, Tuning the Electronic Properties of Semiconducting Transition Metal Dichalcogenides by Applying Mechanical Strains, *ACS Nano*, 2012, **6**(6), 5449–5456.
- 13 Q. Yue, J. Kang, Z. Shao, X. Zhang, S. Chang, G. Wang, S. Qin and J. Li, Mechanical and electronic properties of monolayer MoS₂ under elastic strain, *Phys. Lett. A*, 2012, **376**, 1166–1170.
- 14 X. Fan, C.-H. Chang, W. T. Zheng, J.-L. Kuo and D. J. Singh, The Electronic Properties of Single-Layer and Multilayer MoS₂ under High Pressure, *J. Phys. Chem. C*, 2015, **119**, 10189–10196.
- 15 F. Li, Y. Yan, B. Han and T. Cui, Pressure confinement effect in MoS₂ monolayers, *Nanoscale*, 2015, **7**(19), 1–8.
- 16 M. López-Suárez, I. Neri and R. Rurali, Bandgap engineering of MoS₂ upon compression, *J. Appl. Phys.*, 2016, **119**, 165105.
- 17 X. Dou, K. Ding, D. Jiang and B. Sun, Tuning and Identification of Interband Transitions in Monolayer and Bilayer Molybdenum Disulfide Using Hydrostatic Pressure, *ACS Nano*, 2014, **8**(7), 7458–7464.
- 18 Y. Y. Hui, X. Liu, W. Jie, N. Y. Chan, J. Hao, Y. T. Hsu, L. J. Li, W. Guo and S. P. Lau, Exceptional tunability of band energy in a compressively strained trilayer MoS₂ sheet, *ACS Nano*, 2013, **7**(8), 7126–7131.
- 19 A. P. Nayak, T. Pandey, D. Voiry, J. Liu, S. T. Moran, A. Sharma, C. Tan, C.-H. Chen, L.-J. Li, M. Chhowalla, J.-F. Lin, A. K. Singh and D. Akinwande, Pressure-Dependent Optical and Vibrational Properties of Monolayer Molybdenum Disulfide, *Nano Lett.*, 2015, **15**(1), 346–353.
- 20 X. Cheng, Y. Li, J. Shang, C. Hu, Y. Ren, M. Liu and Z. Qi, Thickness-dependent phase transition and optical behavior of MoS₂ films under high pressure, *Nano Res.*, 2018, **11**, 855–863.
- 21 J. Shang, L. Zhang, X. Cheng and F. Zhai, Pressure induced effects on the electronic and optical properties of MoS₂, *Solid State Commun.*, 2015, **219**, 33–38.
- 22 Z. Yin, H. Li, H. Li, L. Jiang, Y. Shi, Y. Sun, G. Lu, Q. Zhang, X. Chen and H. Zhang, Single-Layer MoS₂ Phototransistors, *ACS Nano*, 2011, **6**(1), 74–80.
- 23 Y. Jing, X. Tan, Z. Zhou and P. Shen, Tuning electronic and optical properties of MoS₂ monolayer *via* molecular charge transfer, *J. Mater. Chem. A*, 2014, **2**, 16892–16897.
- 24 S. Mouri, Y. Miyauchi and K. Matsuda, Tunable Photoluminescence of Monolayer MoS₂ *via* Chemical Doping, *Nano Lett.*, 2013, **13**(12), 5944–5948.
- 25 Y. Wang, A. Slassi, M.-A. Stoeckel, S. Bertolazzi, J. Cornil, D. Beljonne and P. Samori, Doping of Monolayer Transition-Metal Dichalcogenides *via* Physisorption of Aromatic Solvent Molecules, *J. Phys. Chem. Lett.*, 2019, **10**(3), 540–547.
- 26 R. C. Selhorst, E. Puodziukynaite, J. A. Dewey, P. Wang, M. D. Barnes and A. R. T. Emrick, Tetrathiafulvalene-containing polymers for simultaneous non-covalent modification and electronic modulation of MoS₂ nanomaterials, *Chem. Sci.*, 2016, **7**, 4698–4705.
- 27 G. Kresse and J. Hafner, *Ab initio* molecular dynamics for open-shell transition metals, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **48**, 13115–13118.
- 28 G. Kresse and J. Hafner, *Ab initio* molecular-dynamics simulation of the liquid-metal–amorphous-semiconductor transition in germanium, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **49**, 14251–14269.
- 29 G. Kresse and J. Furthmuller, Efficient iterative schemes for *ab initio* total-energy calculations using a plane-wave basis set, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169–11186.
- 30 J. P. Perdew, J. A. Chevary, S. H. Vosko, K. A. Jackson, M. R. Pederson, D. J. Singh and C. Fiolhais, Atoms, molecules, solids, and surfaces: applications of the generalized gradient approximation for exchange and correlation, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1992, **46**, 6671.
- 31 J. P. Perdew, K. Burke and M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Phys. Rev. Lett.*, 1996, **77**, 3865.
- 32 Y. Li, Y.-L. Li, C. M. Araujo, W. Luo and R. Ahuja, Single-layer MoS₂ as an efficient photocatalyst, *Catal.: Sci. Technol.*, 2013, **3**, 2214.
- 33 P. E. Blochl, Projector augmented-wave method, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **50**, 17953.
- 34 G. Kresse and J. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 1758.
- 35 H. J. Monkhorst and J. D. Pack, Special points for Brillouin-zone integrations, *Phys. Rev. B: Solid State*, 1976, **13**, 5188–5192.
- 36 J. Neugebauer and M. Scheffler, Adsorbate-substrate and adsorbate-adsorbate interactions of Na and K adlayers on Al(111), *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1992, **46**, 16067–16080.
- 37 L. Bengtsson, Dipole correction for surface supercell calculations, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 12301–12304.
- 38 L. J. Kong, G. H. Liu and L. Qiang, Electronic and optical properties of O-doped monolayer MoS₂, *Comput. Mater. Sci.*, 2016, **111**, 416–423.
- 39 N. Wakabayashi, H. G. Smith and R. M. Nicklow, Lattice dynamics of hexagonal MoS₂ studied by neutron scattering, *Phys. Rev. B: Solid State*, 1975, **12**, 659.
- 40 Y. Li, Z. Zhou, S. Zhang and Z. Chen, MoS₂ Nanoribbons: High Stability and Unusual Electronic and Magnetic Properties, *J. Am. Chem. Soc.*, 2008, **130**, 16739–16744.
- 41 A. Splendiani, L. Sun, Y. Zhang, T. Li, J. Kim, C.-Y. Chim, G. Galli and F. Wang, Emerging Photoluminescence in Monolayer MoS₂, *Nano Lett.*, 2010, **10**, 1271.