

Original Article

Evaluation of shear bond strength of orthodontic brackets bonded with Er-YAG laser etching

S. Hamid Raji^{1,2}, Reza Birang^{1,3}, Fateme Majdzade², Reza Ghorbanipour²

¹Torabinejad Dental Research Center, ²Departments of Orthodontics, ³Periodontics, School of Dentistry, Isfahan University of Medical Sciences, Isfahan, Iran

ABSTRACT

Background: Based on contradictory findings concerning the use of lasers for enamel etching, the purpose of this study was to investigate the shear bond strength of teeth prepared for bonding with Er-YAG laser etching and compare them with phosphoric acid etching.

Materials and Methods: In this *in vitro* study forty – eight premolars, extracted for orthodontic purposes were randomly divided in to three groups. Thirty-two teeth were exposed to laser energy for 25 s: 16 teeth at 100 mj setting and 16 teeth at 150 mj setting. Sixteen teeth were etched with 37% phosphoric acid. The shear bond strength of bonded brackets with the Transbond XT adhesive system was measured with the Zwick testing machine. Descriptive statistics, Kolmogorov–Smirnov test, of homogeneity of variances, one- way analysis of variances and Tukey's test and Kruskal Wallis were used to analyze the data.

Results: The mean shear bond strength of the teeth lased with 150 mj was 12.26 ± 4.76 MPa, which was not significantly different from the group with acid etching (15.26 ± 4.16 MPa). Irradiation with 100 mj resulted in mean bond strengths of 9.05 ± 3.16 MPa, which was significantly different from that of acid etching ($P < 0.001$).

Conclusions: laser etching at 150 and 100 mj was adequate for bond strength but the failure pattern of brackets bonded with laser etching is dominantly at adhesive – enamel interface and is not safe for enamel during debonding.

Key Words: Acid etching, bond strength, Er-YAG laser, orthodontic brackets

Received: September 2011
Accepted: February 2012

Address for correspondence:
Dr. Fateme Majdzade,
Department of
Orthodontics, Isfahan
School of Dentistry, Isfahan
University of Medical
Sciences, Hezar- Jerib Ave.,
Isfahan, Iran.
E-mail: fmajdzade@yahoo.
com

INTRODUCTION

Since the publishing of the report by Buonocore in 1955,^[1] the standard protocol to eliminate the smear layer for successful bonding has been acid etching. Phosphoric acid etching is a good technique of preparing tooth enamel for bonding resins and orthodontic attachments.^[1,2]

Despite the fact that the acid etching method is a useful procedure in orthodontics, a potential

disadvantage is the possibility of decalcification, which increases the predisposition of enamel to dental caries critically under orthodontic brackets.^[3,4] Additionally, the acid etch technique involves several steps and is technique sensitive.^[5]

Recently, alternative methods for preparing dental hard tissues, such as laser irradiation, have been developed.^[3]

Since 1960, numerous types of laser have been used in dentistry.^[3] In dental practice, the first generation of lasers was used only for soft tissues.^[4] The serious problem applying them on teeth was the immediate increase in temperature, resulting in inflammation of the dental pulp.^[6] With the invention discovery of two types of lasers, Er: YAG and Er, Cr: YSGG, which were approved by US Food and FDA, Dental hard tissues can now be removed without causing damage.^[7]

Access this article online



Website: www.drj.ir

The preference of the laser etched surface is resistance to dental caries.^[4,8,9] Laser etching of dental hard tissue changes the calcium to phosphate ratio, and forms a more stable and less acid soluble compounds, therefore, decreases the susceptibility to acid attack and caries.^[8,9]

In addition, with laser etching, procedural errors can be reduced and time saved.^[8]

The family of erbium lasers is among the most promising systems because their wave lengths coincide with the main absorption peak of water and hydroxyapatite.^[10] Erbium lasers remove hard tissues without causing thermal damage to the pulp.^[11] Additionally it has been proved that this laser has an antimicrobial effect.^[1,2,12]

Thus, Er: YAG, laser etching method might be a suitable technique to etch the enamel for orthodontic bonding.^[1,2,5,12] Usumez and Aykent^[13] and von Franunhofer *et al.*^[14] found that laser irradiation was not able of etching the enamel, while Ozer *et al.*^[5] and Lee *et al.*^[15] stated that laser etching could be a successful alternative to conventional acid etching. In addition, Tanji *et al.*^[16] reported that the Er: YAG laser interacts well with dental hard tissue and produced higher bond strength in comparison with acid etching.^[16] In contrast, Cardoso *et al.*^[17] and Hossain *et al.*^[18] showed that the mean shear bond strength of laser etching was lower than acid etching. Based on contradictory findings concerning the use of lasers for enamel etching, the aim of this study was to determine the shear bond strength and the adhesive remnant index (ARI) of teeth prepared for bonding with Er:YAG laser etching and compare them with that of acid etching.

MATERIALS AND METHODS

This prospective *in vitro* study was accomplished in Torabinejad Dental Research Center of Isfahan Dental School.

Forty eight human maxillary premolars with intact buccal enamel, extracted for orthodontic purposes, were used in this study. Teeth with caries, cracks or enamel defects were excluded. The teeth were stored in the 0.1% thymol solution for 1 week and then they were washed with distilled water. The teeth were mounted vertically in a self cure acrylic (Rapid Repair, Detry Dentsply Ltd, Surrey, U.K.) cylinder. The long axis of each tooth was aligned vertically to the base of cylinder.

The buccal enamel of the teeth were polished with pumice without fluoride (Prophylaxis Paste, Golchai Co, Tehran, Iran), and were washed and dried with an

air Spray. The teeth were randomly divided into three groups of 16 teeth each.

Acid-etched group (control group)

In this group, the buccal enamel was etched with 37% phosphoric acid (American Orthodontics Co., WI, U.S.A) [Figure 1] for 30 s, rinsed with water thoroughly and then they were dried with an oil free air spray until the etched enamel showed chalky frosty appearance.

Laser-etched groups (100 and 150 mj)

Laser etching was performed with an Er:YAG laser device (Fotona 1210, Ljubljana, Slovenia) [Figure 2] of a wavelength of 2940 nm at 20 HZ, SP mode for 25 s. The two different power settings used in this study were 100 and 150 mj.

The laser was applied on enamel with contact mode and water spray, and then the teeth were dried with an oil free air spray until the chalky frosty appearance of enamel was visible. The calculated energy densities per single dose were 23.59 J per square centimeter and 15.72 J per square centimeter for the 150 and 100 mj lasers, respectively.

Bonding procedure

A thin coating of Transbond XT primer (3 M Unitek, Monrovia, CA, U.S.A) was applied to the etched enamel surfaces. Stainless-Steel 0.018"-slot brackets (Standard edgewise, Ortho organizer, CA, U.S.A.) were bonded with Transbond XT adhesive resin (3 M Unitek, Monrovia, CA, U.S.A) and light cured with Starlight (Dentsply GAC International, NY, U.S.A) for 40 seconds.

The samples were stored in distilled water at 37°C for 24 h and then they were thermocycled for 500 cycles from 5°C to 55°C.

Evaluation of shear bond strength

The shear bond strength (SBS) of the sample was measured with Zwick testing machine (Z020, Zwick GmbH and Co, Ulm, Germany).

The blade of machine was inserted between bracket and resin and started to force vertically in an occluso-gingival direction [Figure 3] at a cross head speed of 1 mm/min. The measured bond strength in Newton was divided by the contact surface of bracket mesh (11.55 mm²) to change it to megapascal.

Residual adhesive

The surface of remained resin on enamel was observed under stereomicroscope (X 10 magnification, Olympus,



Figure 1: Phosphoric acid etching solution (American Orthodontics Co., WI, U.S.A)



Figure 2: Er: YAG laser device (Fotona 1210, Ljubljana, Slovenia)

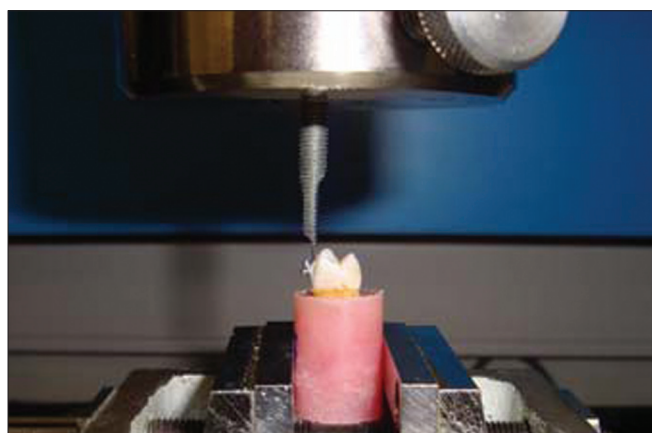


Figure 3: Placing the blade of Zwick machine vertically between the base of bracket and the resin

SZX9, Olympus Corporation, Shinjuku- Ku, Japan), and the amount of remained adhesive was evaluated according ARI developed by Artun and Bergland.^[19]

Table 1: Descriptive statistics of shear bond strength of acid etching and laser etching with two different power doses

Groups	Number	Mean	Standard Deviation	Min	Max
Acid-etched (Control)	16	15.2681	4.16160	8.55	21.81
150 mj laser etching	16	12.2690	4.76848	3.66	19.54
100 mj laser etching	16	9.0400	3.16055	3.56	15.47

The scores of ARI are as:

“0”: no adhesive remained on the tooth; “1”: less than half of the enamel bonding site was covered with adhesive, “2”: more than half of the enamel bonding site was covered with adhesive; “3”: all of the enamel bonding site was covered with adhesive.

Statistical analysis

The data were analyzed with SPSS software (SPSS for windows, version 11.0 SPSS Inc, Chicago, IL, U.S.A.)

Descriptive statistics including the mean, standard deviation, maximum and minimum, were evaluated for each group. The normal distribution of SBS was performed with one sample Kolmogorov–Smirnov test and after test of homogeneity of variances; one-way analysis of variances (ANOVA) evaluated the difference in mean SBS between the groups followed by Post Hoc test of Tukey. Then, the Kruskal Wallis test was performed to determine the difference in ARI between the groups. Significance for all statistical tests was predetermined at $P < 0.05$.

RESULTS

In Table 1, descriptive statistics including mean, standard deviation, minimum and maximum of the three groups are reported.

The one-sample Kolmogorov–Smirnov test was used for analysis of normal distribution of data and then, test of homogeneity of variances was done. The results of the one- way ANOVA showed that there was significant difference in mean SBS between the groups ($P < 0.001$). The Post Hoc Tukey’s test detected no significant difference between control group and 150 mj group ($P = 0.106$) and between 150 and 100 mj group ($P = 0.076$), but there was significant difference between control group and 100 mj group ($P < 0.001$).

Table 2: Distribution of Adhesive remnant Index scores for acid etching and laser etching with two different power outputs

Groups		Adhesive remnant index				Total
		Non adhesive	<50% adhesive	>50% adhesive	100% adhesive	
Acid-etched (control)	Number	7	4	5	0	16
	Percent	43.8	25.0	31.3	0	100
150 mj laser etching	Number	10	6	0	0	16
	Percent	62.5	37.5	0	0	100
100 mj laser etching	Number	12	4	0	0	16
	Percent	75.0	25.0	0	0	100

Distribution of ARI in three groups is presented in Table 2. The Kruskal Wallis test showed no significant difference in ARI between the groups ($P = 0.067$).

DISCUSSION

According to previous studies, the best method for etching enamel is phosphoric acid etching.^[8]

One of disadvantages of acid etching is the demineralization of enamel which makes the enamel prone to future acid attacks and increases the risk of dental caries.^[20,21]

Nowadays, an alternative to acid etching is laser etching.^[8]

The first developed lasers such as CO₂ laser and Nd:YAG laser were used extensively in periodontics and for soft tissue procedures.^[6] However, this group of lasers, when applied on dental hard tissues, led to increase in temperature and resulted in inflammation of dental pulp.^[6] With Er-YAG laser system the temperature could be controlled and easy handling of the device makes this type of laser attractive for clinicians.^[4,18,22] Laser irradiation alters the calcium phosphate ratio and makes more stable and less acid soluble compounds; thus the resistance of enamel to caries would increase.^[12,23-25]

The results of this study showed that the mean SBS of 100 mj group was significantly lower than the mean SBS of control group ($P < 0.001$), but there was no significant difference in the mean SBS between control group and 150 mj group ($P = 0.106$).

Although the SBS of 100 mj group was significantly lower than control group, it was higher than the lower limit of SBS Suggested for clinical use by Smith and Maijir.^[26]

The findings of this study were consistent with the results of previous studies.^[5,15,18,22,27-32] and supported

the efficacy of laser etching for enamel bonding. Conversely, Usumez *et al.*^[13] reported that the half of brackets bonded with laser etching had a SBS lower than the value suggested by Smith and Maijir^[26] and they rejected laser etching for bonding in orthodontics.^[8] Some other studies similar to Usumez *et al.* don't support the efficacy of laser etching.^[14,33-35] Berk *et al.*^[4] and Basaran *et al.*^[36] showed that when the power of laser is lower than 1 W, the SBS of sample is not acceptable and the scanning electron microscopy does not show the pattern of etched enamel.^[36]

The average power output of the laser varies from 0 to 6 W. Cutting the enamel occurs at higher outputs.^[29] In the current study we used 100 and 150 mj for etching the enamel.

The differences in reports of previous studies either supporting or rejecting laser etching might be due to differences in emission mode, contact or non contact mode, irradiation time, water cooling, irradiation distance, power output, and pulse repetition rate.^[10,37] The hand motion during laser etching may result in uneven etching patterns and higher standard deviations of SBS, as it can be seen in the literature,^[8,36] so this problem should be overcome in future investigations.

In the current study, most of the samples in groups bonded with laser etching had the score "0" of ARI. This reveals that after debonding of brackets no adhesive remains on the enamel. This finding is consistent with the results of some previous studies.^[5,8,15] This could be considered a disadvantage of laser etching because although it takes less time to remove remained adhesive on the enamel, this mode of failure may lead to enamel cracks or fracture during debonding and increases the risk of enamel loss specially with debonding of ceramic brackets.

CONCLUSIONS

1. The mean SBS of brackets bonded with 150 mJ Er:YAG laser etching is comparable to acid etching.
2. Although the mean SBS of brackets bonded with 100 mJ Er:YAG laser is lower than acid etching, it is high enough for bonding orthodontic brackets.
3. The site of failure in brackets bonded with laser etching is dominantly at adhesive enamel interface and is not safe for enamel during debonding.

ACKNOWLEDGEMENTS

This study (Nb. 390047) was supported financially by Research Center of Isfahan University of Medical Sciences and Health Services, Isfahan, Iran. Also, the authors wish to express their sincere respect to the deans and staff members of Professor Torabinejad Dental Research Center and Dental Research Center of Shaheed Beheshti University of Medical Sciences.

REFERENCES

1. Buonocore MG. A simple method of increasing the adhesion of acrylic filling materials to enamel surfaces. *J Dent Res* 1955;34:849-53.
2. Driessens FC. Chemical adhesion in dentistry. *Int J Dent* 1977;27:317-23.
3. Basaran G, Hamaci N, Akkurt A. Shear bond strength of bonding to enamel with different laser irradiation distances. *Lasers Med Sci* 2011;26:149-56.
4. Berk N, Basaran G, Ozer T. Comparison of sandblasting, laser irradiation, and conventional acid etching for orthodontic bonding of molar tubes. *Eur J Orthod* 2008;30:183-9.
5. Ozer T, Basaran G, Berk N. Laser etching of enamel for orthodontic bonding. *Am J Orthod Dentofacial Orthop* 2008;134:193-7.
6. Aoki A, Sakaki MK, Watanabe H, Ishikawa I. Lasers in nonsurgical periodontal therapy. *Periodontol* 2000 2004;36: 59-97.
7. Lee BS, Lin PY, Chen MH, Hsieh TT, Lin CP, Lai JY, et al. Tensile bond strength of Er Cr: YSGG laser irradiated human dentin analysis of dentin resin interface. *Dent Mater* 2007;23:570-8.
8. Usumez S, Orthan M, Usumez A. Laser etching of enamel for direct bonding with an Er; Cr: YSGG hydrokinetic laser system. *Am J Orthod Dentofacial Orthop* 2002;122:649-56.
9. Keller U, Hibst R. Ultrastructure changes of enamel and dentin following Er: YAG laser radiation on teeth. *Proc SPIE* 1990;1200:408-15.
10. Schein MT, Bocangel JS, Nogueira GE, Schein PA. SEM evaluation of the interaction pattern between dentin and resin after cavity preparation using Er: YAG laser. *J Dent* 2003;31:127-35.
11. Attrill DC, Davis RM, King TA, Dickinson MR, Blinkhorn AS. Thermal effects of Er: YAG laser on a simulated dental pulp: A quantitative evaluation of the effects of a water spray. *J Dent* 2004;32:35-40.
12. Oho T, Morioka T. A possible mechanism of acquired acid resistance of human dental enamel by laser irradiation. *Caries Res* 1990;24:86-92.
13. Usumez A, Aykent F. Bond strength of porcelain laminate veneers to tooth surfaces prepared with acid and Er: Cr: YSGG laser etching. *J Prosthet Dent* 2003;90:24-30.
14. Von Fraunhofer JA, Allen DJ, Orbell GM. Laser etching of enamel for direct bonding. *Angle Orthod* 1993;63:73-6.
15. Lee BS, Hsieh TT, Lee YL, Lan WH, Hsu YJ, Wen PH, et al. Bond strengths of orthodontic bracket after acid-etched, Er: YAG laser- irradiated and combined treatment on enamel surface. *Angle Orthod* 2003;73:565-70.
16. Tanji EY, Matsumoto K, Eduardo CP. Scanning electron microscopic observations of dentin surface conditioned with the Er: YAG laser. *Deutsche Gesellschaft laser newsletter* 1997;8:6.
17. Cardoso MV, De Munck J, Coutinho E, Emis RB, van Landuyt K, de Carvalho RC, et al. Influence of Er, Cr: YSGG laser treatment on microtensile bond strength of adhesives to enamel. *Oper Dent* 2008;33:448-55.
18. Hossain M, Nakamura Y, Tamaki Y, Yamada Y, Murakami N, Matsumoto K. Atomic analysis and knoop hardness measurement of the cavity floor prepared by Er: Cr: YSGG laser irradiation *in vitro*. *J Oral Rehabil* 2003;30:515-27.
19. Artun J, Bergland S. Clinical trials with crystal growth conditioning as an alternative to acid-etch enamel pretreatment. *Am J Orthod* 1984;85:333-40.
20. Shannon IL, Miller JT. Caries risk in teeth with orthodontic bands: A review. *J Acad Gen Dent* 1972;20:24-8.
21. Zachrisson BU. Cause and prevention of injuries to teeth and supporting structures during orthodontic treatment. *Am J Orthod* 1976;69:285-300.
22. Visuri SR, Gilbert JL, Wright DD, Wigdor HA, Walsh JT Jr. Shear strength of composite bonded to Er: YAG laser prepared dentin. *J Dent Res* 1996;75:599-605.
23. Klein AL, Rodrigues LK, Eduardo CP, Nobre dos Santos M, Cury JA. Caries inhibition around composite restorations by pulsed carbon dioxide laser application. *Eur J Oral Sci* 2005;113:239-44.
24. Sognaes RF, Stern RH. Laser effect on resistance of human dental enamel to demineralization *in vitro*. *J South Calif Dent Assoc* 1965;33:328-9.
25. Morioka T, Suzuki K, Takamori S. Effect of beam absorptive mediators on acid resistance of surface enamel by Nd: YAG laser irradiation. *J Dent Health* 1984;34:40-4.
26. Majjer R, Smith DC. A new surface treatment for bonding. *J Biomed Mater Res* 1979;13:975-85.
27. Basaran G, Ozer T, Berk N, Hamamci O. Etching enamel for orthodontics an erbium, chromium: Yttrium – Scandium- gallium – garnet laser system. *Angle Orthod* 2007;77:117-23.
28. Hossain M, Nakamura Y, Yamada Y, Kimura Y, Matsumoto N, Matsumoto K. Effects of Er; Cr: YSGG laser irradiation in human enamel and dentin: Ablation and morphological studies. *J Clin Laser Med Surg* 1999;17:155-9.
29. Bishara SE, Vonwald L, Laffoon JF, Warren JJ. Effect of a self-etch primer /adhesive on the shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop* 2001;119:621-4.
30. Walsh LJ, Abood D, Brockhurst PJ. Bonding of resin composite to carbon dioxide laser- modified human enamel. *Dent Mater* 1994;10:162-6.

31. Dunn WJ, Davis JT, Bush AC. Shear bond strength and SEM evaluation of composite bonded to Er: YAG laser prepared dentin and enamel. *Dent Mater* 2005;21:616-24.
32. Kameyama A, Kato J, Aizawa K, Suemori T, Nakazawa Y, Ogata T, *et al.* Tensile bond strength of one- step self-etch adhesives to Er; YAG laser – irradiated and non-irradiation distance. *Dent Mater J* 2008;27:386-91.
33. Corpas-Pastor L, Villalba Moreno J, de Dios Lopez-Gonzalez Garrido J, Pedraza Muriel V, Moore K, Elias A. Comparing the tensile strength of brackets adhered to laser – etched enamel vs. acid – etched enamel. *J Am Dent Assoc* 1997;128:732-7.
34. Martinez- Insua A, Dominguez LS, Rivera FG, Satana- Penin UA. Differences in bonding to acid- etced or Er: YAG laser – treated enamel and dentin surfaces. *J Prosthet Dent* 2000;84:280-8.
35. Roberts- Harry DP. Laser etching of teeth for orthodontic bracket placement: A preliminary clinical study. *Lasers Surg Med* 1992;12:467-70.
36. Basaran EG, Ayna E, Basaran G, Beydemir K. Influence of different power outputs of erbium, chromium: Yttrium scandium – gallium – garnet laser and acid etching on shear bond strengths of a dual – cure resin cement to enamel. *Lasers Med Sci* 2011;26:13-9.
37. Goncalves M, Corona SA, Pecora JD, Dibb RG. Influence of the frequency of Er: YAG laser on the bond strength of dental enamel. *J Clin Laser Med Surg* 2003;21:105-8.

How to cite this article: Raji SH, Birang R, Majdzade F, Ghorbanipour R. Evaluation of shear bond strength of orthodontic brackets bonded with Er-YAG laser etching. *Dent Res J* 2012;9:288-93.

Source of Support: This report is based on a thesis which was submitted to the School of Dentistry, Isfahan University of Medical Sciences, in partial fulfillment of the requirements for the MSc degree in Pathology (#390047). This study was financially supported and approved by Isfahan University of Medical Sciences, Isfahan, Iran. **Conflict of Interest:** The authors declare no conflicts of interest, real or perceived, financial or nonfinancial.

New features on the journal's website

Optimized content for mobile and hand-held devices

HTML pages have been optimized of mobile and other hand-held devices (such as iPad, Kindle, iPod) for faster browsing speed.

Click on **[Mobile Full text]** from Table of Contents page.

This is simple HTML version for faster download on mobiles (if viewed on desktop, it will be automatically redirected to full HTML version)

E-Pub for hand-held devices

EPUB is an open e-book standard recommended by The International Digital Publishing Forum which is designed for reflowable content i.e. the text display can be optimized for a particular display device.

Click on **[EPub]** from Table of Contents page.

There are various e-Pub readers such as for Windows: Digital Editions, OS X: Calibre/Bookworm, iPhone/iPod Touch/iPad: Stanza, and Linux: Calibre/Bookworm.

E-Book for desktop

One can also see the entire issue as printed here in a 'flip book' version on desktops.

Links are available from Current Issue as well as Archives pages.

Click on  View as eBook