

Molecular design of dynamically thermoresponsive biomaterials

Jun Kobayashi ^a, Masamichi Nakayama ^a and Kenichi Nagase ^b

^aInstitute of Advanced Biomedical Engineering and Science, Tokyo Women's Medical University, TWIns, Tokyo, Japan;

^bGraduate School of Biomedical and Health Sciences, Hiroshima University, Hiroshima, Japan

ABSTRACT

Dynamically thermoresponsive biomaterials, particularly those utilizing poly(*N*-isopropylacrylamide) (PNIPAAm), have attracted much attention in biomedical applications due to their reversible phase transition near body temperature. These biomaterials provide innovations across drug delivery system, chromatography, and tissue engineering. Molecular designs, such as the incorporation of hydrophilic comonomers or graft copolymers in PNIPAAm hydrogels, enhance rapid kinetics of the gels when jumping the temperature across the phase transition temperature, because of avoiding 'skin layer' formation on the surface of the gels. Nanocarriers possessing PNIPAAm coronas facilitate spatial drug delivery and temporally on-demand drug release to targeted cancers in combination with hyperthermic therapy. Downsizing of PNIPAAm hydrogels accelerates the kinetics of shrinkage/swelling, leading to applications as thermoresponsive chromatographic matrices and cell cultureware. PNIPAAm-modified surfaces support thermoresponsive cell culture systems for the non-invasive recovery of intact cell sheets, enabling advanced regenerative therapies and layered 3D tissue formation. Recent developments also integrate growth factor delivery for sustained cell stimulation on cultureware. Newly developed biomaterials, including dynamically thermoresponsive PNIPAAm, are expected to expand the opportunity for novel treatment technologies such as targeted therapies and regenerative medicine.

ARTICLE HISTORY


Received 9 January 2025

Revised 26 February 2025

Accepted 2 March 2025

KEYWORDS

Thermoresponsive polymer; poly(*N*-isopropylacrylamide); drug delivery system; chromatography; bioseparation; tissue engineering, cell sheet, regenerative medicine

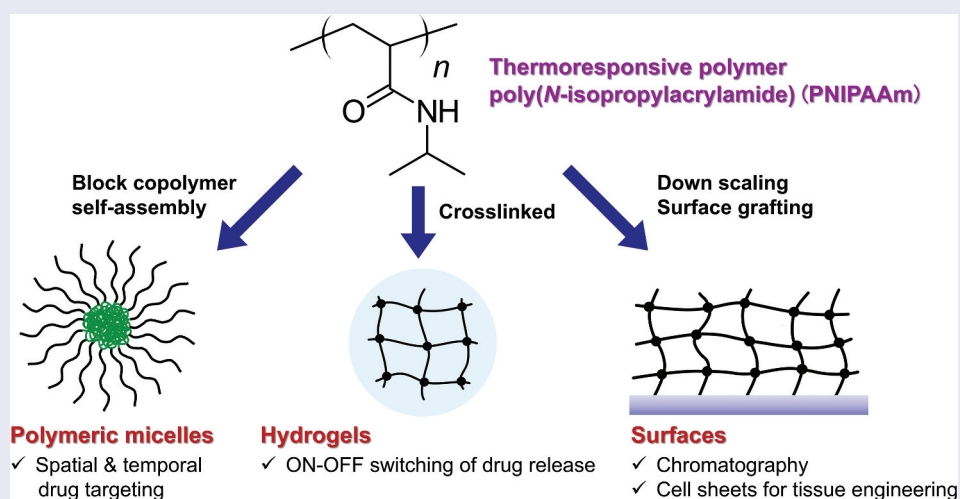



IMPACT STATEMENT

This paper focuses on epoch-making dynamically thermoresponsive biomaterials through designing molecular architectures, such as polymer grafting structures, monomer design, and the size effects of molecules.

1. Introduction

Thermoresponsive polymers in an aqueous milieu exhibit temperature-dependent changes in the physico-chemical properties of the solutions [1–3]. For example, lower critical solution temperature (LCST)-type thermoresponsive polymers are soluble at low

temperatures and insoluble at high temperatures [2]. Furthermore, this phase transition phenomenon is reversible. Among various thermoresponsive polymers, aqueous solutions of poly(*N*-isopropylacrylamide) (PNIPAAm) and their hydrogels show a sharp phase transition [4,5]. More importantly, the LCST of the

CONTACT Jun Kobayashi  kobayashi.jun@twmu.ac.jp  Institute of Advanced Biomedical Engineering and Science, Tokyo Women's Medical University, TWIns, 8-1 Kawadacho Shinjuku-ku, Tokyo 162-8666, Japan

© 2025 The Author(s). Published by National Institute for Materials Science in partnership with Taylor & Francis Group.

This is an Open Access article distributed under the terms of the Creative Commons Attribution-NonCommercial License (<http://creativecommons.org/licenses/by-nc/4.0/>), which permits unrestricted non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited. The terms on which this article has been published allow the posting of the Accepted Manuscript in a repository by the author(s) or with their consent.

PNIPAAm solution is 32°C [6], which is between room temperature and mammalian body temperature (37 °C); therefore, a phase transition undergoes within a very mild range of temperature change. Due to these characteristics, PNIPAAm has been extensively utilized in thermoresponsive biomaterials and has been the subject of numerous studies [7–10]. In recent years, the utilization of other LCST-type thermoresponsive polymers, including poly(oligo ethylene glycol methacrylates) [11] and poly(2-oxazoline)s [12], have been proposed for thermoresponsive biomaterials as an alternative to PNIPAAm. The thermoresponsive behavior of a copolymer composed of 95% 2-(2-methoxyethoxy) ethyl methacrylate and 5% oligo ethylene glycol methacrylate ($M_n = 475$ g/mol) [13,14] was comparable to that of PNIPAAm and in some cases even better than that of PNIPAAm. A copolymer of 2-ethyl-2-oxazoline and 2-*n*-propyl-2-oxazoline [15] is also a potential alternative to PNIPAAm. However, to our knowledge, no specific reports have been published showing their superiority over PNIPAAm as biomaterials.

It is a critical point that thermoresponsive biomaterials can respond quickly to temperature changes. For example, chemically crosslinked PNIPAAm hydrogels undergo significant volume changes across the phase transition temperature around 32°C in response to temperature changes [4]. However, when the temperature is increased rapidly across the phase transition temperature, a skin layer is formed on the surface of the bulk PNIPAAm hydrogel, leading to delayed kinetics of shrinkage [16]. To realize thermoresponsive biomaterials that can dynamically change on demand, molecular design and construction of PNIPAAm-based biomaterials are crucial.

Several strategies have been developed to accelerate the kinetics of PNIPAAm-based biomaterials in response to temperature change. Figure 1 illustrates a concept of dynamically thermoresponsive

biomaterials for biomedical applications. Crosslinked PNIPAAm acts as a matrix of water-soluble drugs, allowing the controlled release rate of the drugs in response to the temperature change (Figure 1, middle). When heating above the phase transition temperature, a skin layer on the outermost surface of the gels prevents drug release (Figure 2a). The formation of a skin layer can be avoided by incorporating PNIPAAm graft chains having freely mobile ends [17] or hydrophilic moieties [18] into bulk PNIPAAm hydrogels (Figure 2b). This strategy has been utilized to release drugs rapidly in response to temperature changes. From the viewpoint of polymer physics, downsizing of PNIPAAm hydrogels accelerates the kinetics of shrinkage/swelling (Figure 1, right) because the time needed for a hydrogel phase transition is proportional to the square of the characteristic length of the hydrogel [19]. This strategy has been applied to thermoresponsive chromatographic matrices and cell cultureware for tissue engineering. Meanwhile, an amphiphilic block copolymer having hydrophobic and thermoresponsive PNIPAAm units assembles spontaneously nano-scale micelles in an aqueous milieu (Figure 1, left) [8]. During the self-assembly, the micelles entrap hydrophobic drugs such as anticancer drugs. Also, the PNIPAAm corona of polymeric micelle independently exhibits thermoresponsive dehydration when heating, leading to aggregation and collapse of the micelles.

This review focuses on epoch-making thermoresponsive biomaterials, especially using PNIPAAm, in terms of molecular design to dynamically and rapidly respond to temperature changes. Furthermore, dynamically thermoresponsive biomaterials are categorized into various types of biomedical applications and discussed. Knowledge of the molecular design of PNIPAAm-based biomaterials in this review can be applied to other thermoresponsive polymers.

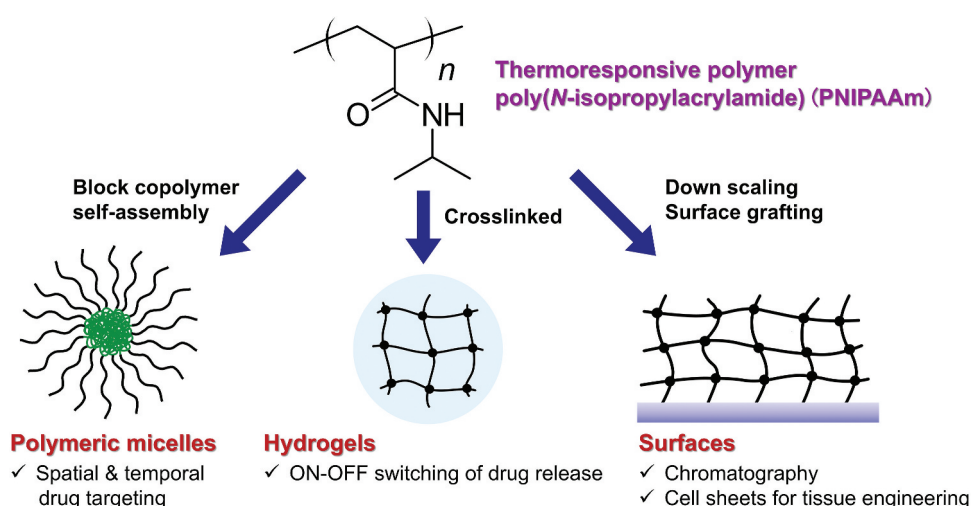


Figure 1. Scheme of molecular design of thermoresponsive poly(*N*-isopropylacrylamide) (PNIPAAm) for biomedical applications.

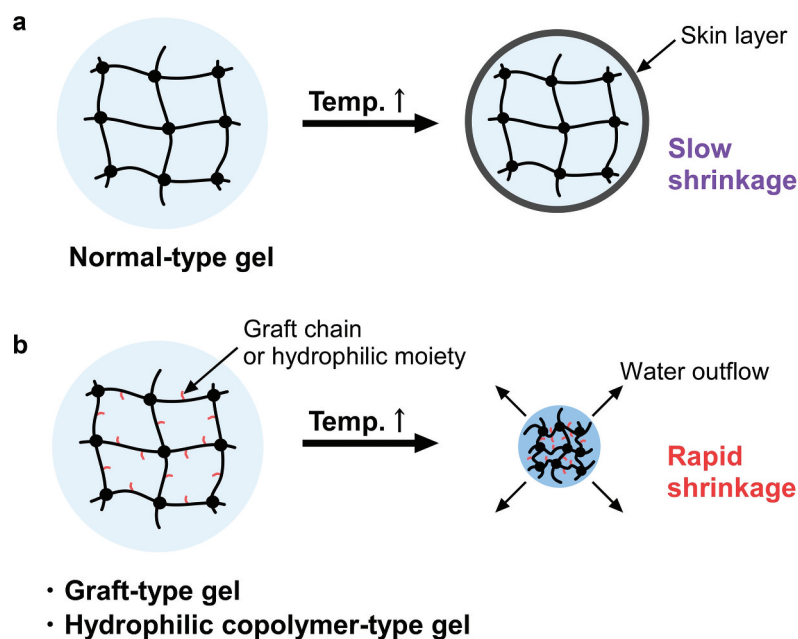


Figure 2. Schematic illustration of deswelling process for (a) Normal-type PNIPAAm gel and (b) Its graft-type or hydrophilic copolymer-type gel.

2. Molecular design of dynamically thermoresponsive biomaterials for controlled release

2.1. Thermoresponsive hydrogels for on-demand drug release

Hydrogel matrices allow for the sustained release of incorporated drugs from the matrices, and the rate of drug release is governed by diffusion, which is determined by the size of the polymer network in the hydrogel [20]. In contrast, thermoresponsive hydrogels, including crosslinked PNIPAAm hydrogel, exhibit their volume and mesh size changes in response to temperature [21], allowing the control of diffusion of incorporated solutes from the hydrogel. Therefore, the swelling/deswelling behaviors of thermoresponsive hydrogels have systematically been investigated for achieving on-off controlled release of water-soluble drugs by temperature changes. In addition, the applications of thermoresponsive hydrogels often have focused on temperature-controlled drug release because a heating/cooling procedure inside the human body is an accessible approach for temporally modulated or pulsatile drug delivery systems.

Crosslinked PNIPAAm and its copolymer hydrogels are hydrated and swollen below their phase transition temperatures. Once the environmental temperature is raised above their phase transition temperatures, the gels shrink via the dehydration of PNIPAAm. However, the outermost surface region of the gels exposed to warmer temperatures readily shrinks to form a polymer-aggregated surface layer, the 'skin layer' (Figure 2a) [16]. Then, this dense skin layer inhibits the outflow of water from the gel

interior, preventing the shrinkage of the gels. Based on the unique deswelling behavior, two modes of temperature-controlled drug release from the hydrogels were designed: 'surface regulation' and 'bulk matrix squeezing' [22].

The 'surface regulation' of PNIPAAm-based gels involves the active use of the skin layer as the barrier of molecular permeation. In particular, PNIPAAm copolymer gels with hydrophobic comonomers such as *n*-butyl methacrylate (BMA) allowed the diffusible release of loaded drugs below their phase transition temperatures, while the dense skin layer on the gels when the deswelling with suddenly increasing the temperature hindered the release of drug and water from the matrix [23,24]. Therefore, the repeated heating/cooling cycles across the phase transition temperatures successfully achieved the pulsatile drug release.

In contrast to the heat-triggered negative drug release mentioned above, heat-triggered positive drug release was achieved by the molecular design for thermoresponsive 'bulk matrix squeezing' without forming dense skin layers. The randomly copolymerized gels of PNIPAAm and hydrophilic monomers such as acrylic acid (AAc) were investigated to demonstrate quick and reversible swelling/deswelling behaviors (Figure 2b) [18]. These copolymer gels exhibited a deswelling response without forming a skin layer when raising the temperature above the phase transition temperature, resulting in sustained gel shrinkage. This shrinkage was due to the formation of water channels through the hydrophilic moieties within the skin layer. However, the increased AAc content up to 10 mol% often induced a higher LCST shift and reduced gel shrinkage force, resulting in poor

deswelling behavior [25]. This phenomenon may be due to disrupting the repeating *N*-isopropylacrylamide (NIPAAm) moieties by inserting AAC units along the PNIPAAm copolymer.

Hoffman et al. reported that PNIPAAm-*g*-poly-(AAc) graft copolymers showed sharp thermal phase transitions independent of total AAC contents, unlike random copolymers [26]. The distinctive phase transition behavior of the graft copolymers was ascribed to the molecularly separated architecture between PNIPAAm and poly(AAc) segments. These results strongly suggest that multi-functional properties with keeping thermoresponsiveness can be achieved by using molecular design of thermoresponsive polymers such as graft copolymers comprising PNIPAAm and other functional polymers. Using the property of graft copolymer architecture, several approaches were developed for accelerating gel deswelling dynamics rather than molecular diffusion processes. Thermoresponsive comb-type grafted hydrogels, which possessed PNIPAAm-graft chains on a PNIPAAm network, showed rapid deswelling dynamics, even though the chemical composition and crosslinking density were the same as those of regular PNIPAAm gels [17]. Upon heating above the phase transition temperature, before the dehydration of the restrained PNIPAAm network, the freely mobile PNIPAAm-graft chains quickly dehydrated and acted as macromolecular hydrophobes. The hydrophobized graft chains triggered the dehydration of total gels and accelerated the release of water from inside the gels [27]. Another example of thermoresponsive comb-type grafted hydrogels involved hydrophilic poly(ethylene glycol) (PEG)-grafted chains [18]. PEG-grafted chains on the PNIPAAm gel network formed the channels for water penetration across the surface layer above the phase transition temperature, and thus, the gels quickly released internal water and underwent rapid shrinkage.

As an alternative approach for random copolymer gels with rapid shrinkable kinetics, Aoyagi et al. reported PNIPAAm copolymer gels with a functional comonomer, 2-carboxyisopropylacrylamide (CIPAAm) [24]. Poly(NIPAAm-*co*-CIPAAm) chains showed a similar sharp phase transition behavior with pure PNIPAAm, regardless of the additional carboxy groups [28]. This was due to the continuous isopropylamide moieties along the polymer backbone can be maintained after copolymerization. Consequently, the installed carboxy groups assisted the rapidly responsive gel shrinkage above the LCST, even at a high content of 10 mol% hydrophilic comonomers [29].

On the other hand, the introduction of macroscale heterogeneous structures inside thermoresponsive hydrogels was also used to accelerate swelling/deswelling dynamics. For example, macroporous structures inside crosslinked gels increased the surface area of

contact between polymer and water, accelerating the diffusion process through polymer networks. Based on this strategy, some researchers have successfully achieved rapid volume changes of hydrogels under the swelling/deswelling process in response to temperature [30].

2.2. Thermoresponsive nanocarriers for on-demand release

In recent decades, nano-scale drug carrier systems, 'nanocarriers', have attracted great interest in cancer chemotherapies because they can passively deliver the encapsulated drugs to solid tumors via the enhanced permeability and retention effect [31,32]. However, current nanocarriers face the dilemma of two contradictory functions: one is to encapsulate drugs in nanocarriers stably during the delivery process, and the other is to actively release drugs from nanocarriers at the target site. Therefore, nanocarriers possessing specific stimuli-responsive drug release functions are significantly attractive in terms of achieving higher therapeutic efficacy. In particular, mild heating up to 41–43°C, hyperthermia, has been used as a potential cancer treatment since cancer cells are sensitive to high temperatures [33]. Therefore, the strategy of temperature-triggered release from thermoresponsive nanocarriers can be combined with local hyperthermia for effective synergic cancer therapy.

2.2.1. Thermoresponsive liposomes

Nano-scale liposomes have been intensively explored as cancer-selective drug carriers, especially for tumor-selective drug targeting. In several decades, functional liposomes were developed by introducing surface functionalization [34], stimuli-responsive functions [35], and polymer-liposome composite technologies [36,37].

In the late 1970s, Yatvin and Weinstein pioneered thermoresponsive liposomal drug carriers, which promoted the release rate of the encapsulated drugs based on the gel-to-liquid crystalline phase transition of phospholipid membranes [38]. However, dipalmitoylphosphatidylcholine-based liposomes have some problems, including small changes in membrane structure and low thermoresponsiveness. To overcome these problems, thermoresponsive lysophospholipid-based liposomal drugs were developed and utilized as the first heat-triggered formulation in human clinical trials [39].

Alternatively, LCST-type polymer-modified liposomes were also investigated to enhance the release of encapsulated drugs [40,41]. The polymer chains were hydrated and extended below the LCSTs of the modified polymers, whereas the conformation of the dehydrated polymers changed to an aggregated form above the LCSTs. The mechanical distortion derived

from the collapse of the modified polymers greatly disturbed the stabilization of liposomal membranes and induced an accelerated release rate of entrapped drugs. The first paper on the temperature-induced distortion of liposomal membrane via the collapse of the modified PNIPAAm chains was reported by Ringsdorf et al. [42]. At the same time, Hoffman et al. proposed a concept of PNIPAAm-modified liposomes as thermoresponsive drug carriers [43].

The modified thermoresponsive polymers' chemical structure and properties significantly influence liposome's thermoresponsive function. The anchoring position of the polymer chain on the liposomal membrane is a significant factor for dynamically thermoresponsive functions (Figure 3a) [40]. Liposomes modified with terminal anchor-possessing PNIPAAm showed a sharper release behavior of loaded drugs within a narrow range of temperature than those fixed via randomly located anchors on PNIPAAm chains. This possible reason was that PNIPAAm chains anchored at the terminal positions induce their thermal coil-to-globule transitions effectively due to their higher conformational flexibility than those anchored at multiple points of the PNIPAAm chain. Nowadays, another type of thermoresponsive polymer is also available for binding to liposomal membranes to achieve the release of the loaded drugs through the conformational change of the polymer [44].

2.2.2. Thermoresponsive polymeric micelles

Multi-molecular assemblies of amphiphilic copolymers, polymeric micelles, possess high structural stability in aqueous milieu with nano-scale sizes (typically 10–100 nm) for effective drug targeting [45]. Okano and co-workers initially designed polymeric micelles with thermoresponsive PNIPAAm-based coronas (Figure 3b) [46]. Corona-forming PNIPAAm chains acted as a stabilizer of a segmented core-corona structure within the micelle due to the packing of the hydrated and expanded PNIPAAm chains below the LCST. Once the rising temperature was above the LCST, the outer corona switched to be hydrophobic, resulting in the collapse of the micellar corona. Thermoresponsive change in the micelles' structure and properties can trigger the release of loaded drugs from the hydrophobic core.

Initially, alkyl-terminated PNIPAAm derivatives were used to form thermoresponsive corona micelles [47]. The contribution of hydrophobic termini to the phase transition temperature of PNIPAAm was significantly notable. The phase transition temperature of hydrophobically terminated PNIPAAm derivatives was lower than unmodified PNIPAAm because the freely mobile hydrophobic tail promoted dehydration of the proximal NIPAAm units. Interestingly, a long alkyl (e.g. stearyl) terminated PNIPAAm assembled to form a micelle structure above its critical micelle concentration, and the aqueous micelle solution showed the same LCST as unmodified PNIPAAm,

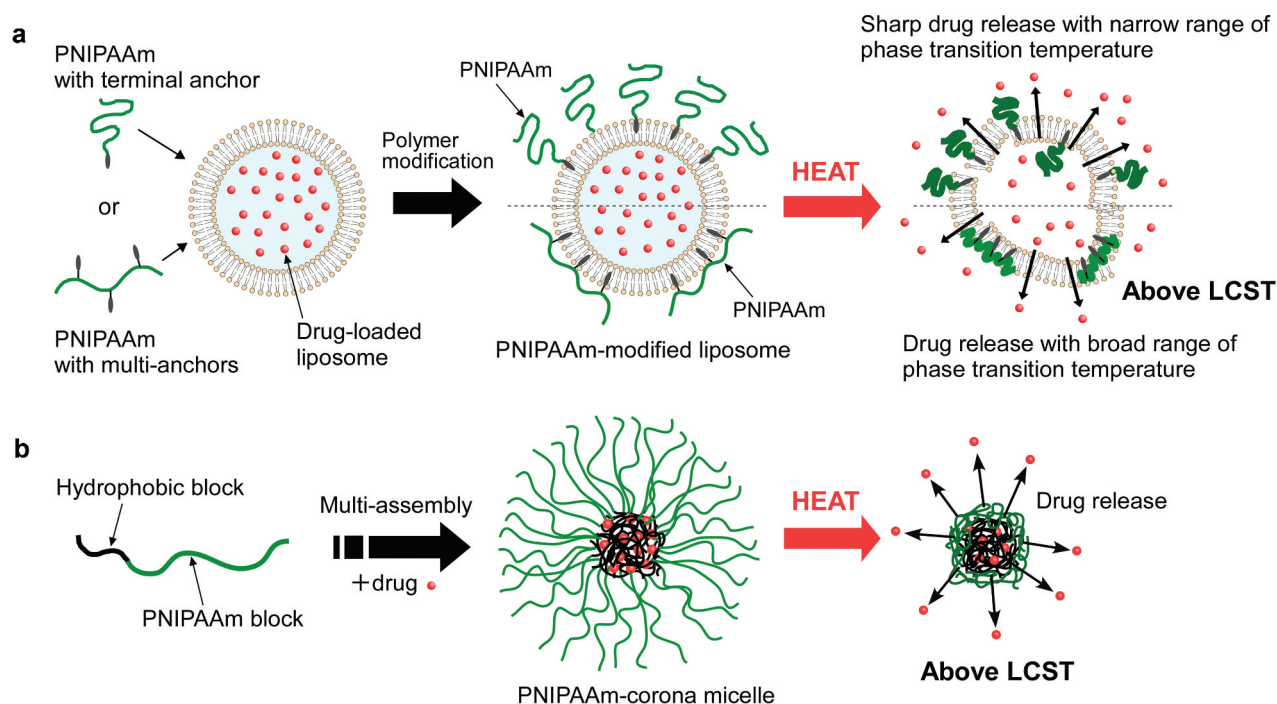


Figure 3. Schematic illustration of thermoresponsive nanocarriers with PNIPAAm segments. (a) PNIPAAm-modified liposome and (b) PNIPAAm-based block copolymer micelles.

presumably because a core-corona structure shielded the hydrophobic alkyl core from interaction with water. Thermoresponsive block copolymer micelles possessing hydrophobic polymeric cores for effective drug loading were prepared using PNIPAAm-based block copolymers [48,49]. An interesting property based on the architectural effect of copolymers was that PNIPAAm-based block copolymer micelles exhibited a unique thermoresponsive behavior compared with randomly copolymerized PNIPAAm derivatives. For example, PNIPAAm-*b*-poly(BMA) (PNIPAAm-*b*-PBMA) block copolymer micelles exhibited an identical thermal phase transition to that of PNIPAAm homopolymer, regardless of hydrophobic PBMA co-introduction [50]. This thermal behavior was attributed to a phase-separated PNIPAAm corona and PBMA core structure. Consequently, the covalently connected hydrophobic PBMA segment does not influence the LCST of the corona-forming PNIPAAm, unlike random copolymers showing lower LCST shifts.

As for the temperature-controlled drug release from thermoresponsive corona polymeric micelles, the consideration of physicochemical properties (e.g. glass transition temperature: T_g) of core-forming polymers is essential for the dramatically accelerated release of the loaded drugs via the phase transition of the micellar corona. Okano et al. investigated two different types of hydrophobic polymers as inner core modes using polystyrene (PS) and PBMA chosen as glassy-like (rigid: $T_g > \text{PNIPAAm's LCST}$) and rubber-like (flexible: $T_g < \text{PNIPAAm's LCST}$) blocks, respectively [48]. The PNIPAAm-*b*-PS micelles demonstrated limited drug release at temperatures both above and below the PNIPAAm's LCST of 32°C. In contrast, the PNIPAAm-*b*-PBMA micelles remarkably released loaded drugs over the LCST of the PNIPAAm corona. Characterization of the inner cores of micelles using a hydrophobic fluorescent pyrene revealed that the polarity inside the rubber-like PBMA core significantly increased at temperature above the LCST of the PNIPAAm corona, unlike that of the glassy-like PS core interior. Therefore, the thermally triggered drug release may be induced by dehydrated outer PNIPAAm coronas aggregation and subsequent structural change of the PBMA core. In addition, for an effective combination of thermoresponsive polymeric micelle carriers with hyperthermic therapy, the thermal transition temperature can be modulated to a desirable temperature of 40°C (above the normal physiological temperature) by introducing hydrophilic comonomers to the corona-forming PNIPAAm chain [51].

On the other hand, the outermost surface functionalization of thermoresponsive corona micelles was available by mixing various end-functional PNIPAAm-based block copolymers before micelle formation [52,53]. The hydrophobicity and polarity

of outermost surface functionalities significantly affected the thermoresponsive behavior of polymeric micelles [54]. Hydrophobic phenyl groups located at the micelle periphery enhanced the dehydration of corona-forming PNIPAAm derivatives. They resulted in a micellar LCST shift to lower temperatures than micelles with surface hydrophilic hydroxy groups [54]. The magnitude of LCST shifts for the polymeric micelles was much larger than that for linear polymers due to a closely packed thermoresponsive polymer brush structure in micellar corona: the accumulation of hydrophobic groups surrounding polymeric micelles increased the overall hydrophobicity of micelle systems. More Interestingly, thermoresponsive corona micelles formed by mixing phenyl- and hydroxy-terminated block copolymers exhibited only a single sharp phase transition at a temperature within the LCST values of the respective homogeneous surface micelles [55]. These phenomena were probably because respective PNIPAAm-based chains in a close-packed environment may be influenced by surrounding polymer chains and end-functional groups, resulting in cooperative thermal transitions. Uniquely, the thermal phase transition of the block copolymer-mixed micelles can be readily modulated, dependent on the blended phenyl/hydroxy end-group ratio. These results strongly suggested that micellar LCST values can be controlled via modulating outermost surface chemistry with various stimuli (e.g., pH, light, and specific compounds) to achieve multi-responsive systems [56]. Recently, various advanced polymeric micelles that undergo structural and physicochemical changes in response to stimuli have been explored to achieve both stable drug loading in the micelles during spatial delivery and on-demand release of loaded drugs at the target cancers [8].

3. Molecular design for dynamically thermoresponsive catch-and-release of biomolecules and cells

3.1. Thermoresponsive chromatography

Chromatography is a separation method that utilizes the interaction between a stationary phase and analytes. In 1996, Okano and Kanazawa developed a new concept of thermoresponsive chromatography that utilizes the properties of PNIPAAm [57] (Figure 4). The chromatography system uses the PNIPAAm-modified silica beads as stationary and aqueous mobile phases. Because PNIPAAm hydrophobicity changes with changing temperature, hydrophobic interactions between PNIPAAm and analytes can be modulated by changing the column temperature, leading to dynamic thermoresponsive modulation of analyte retention on the column.

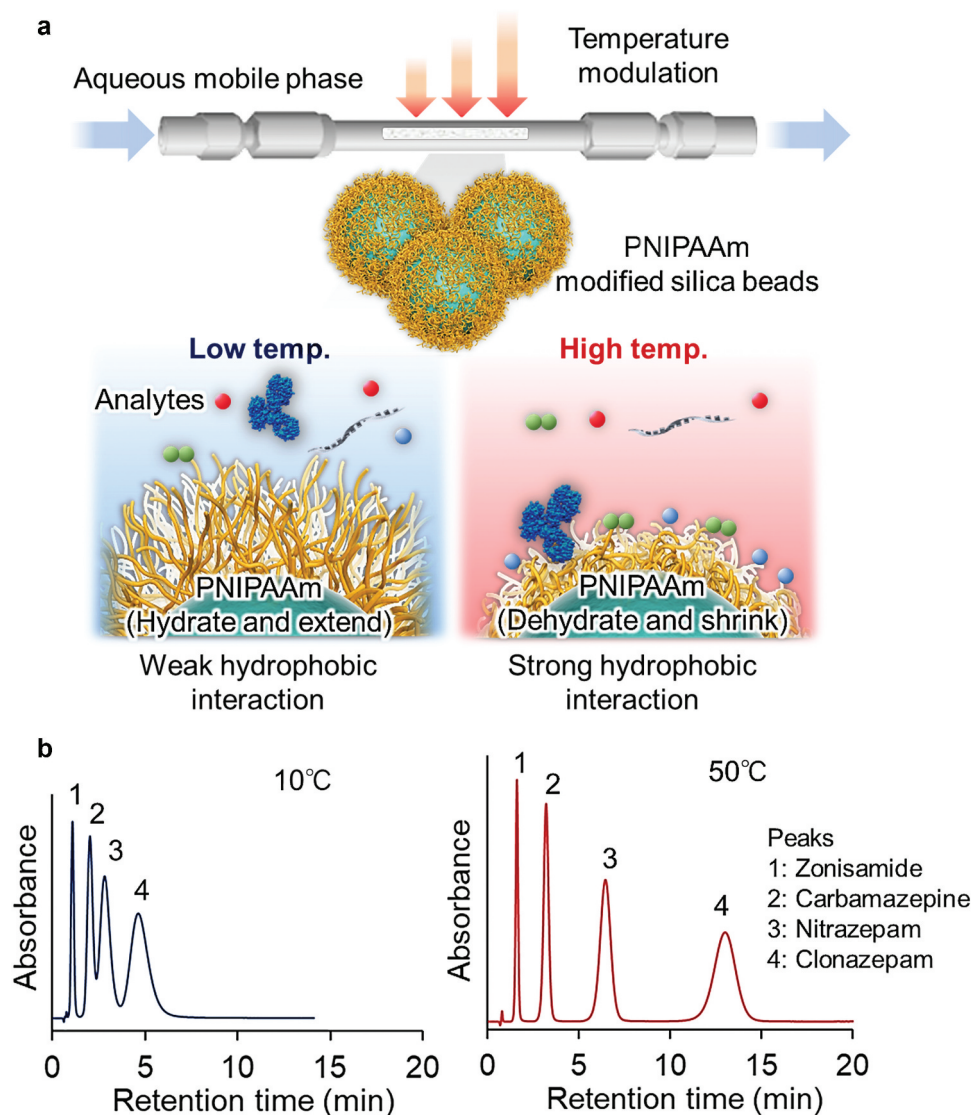


Figure 4. Schematic illustration of thermoresponsive chromatography. (a) Concept of thermoresponsive chromatography and (b) Chromatograms at 10°C and 50°C.

The separation performance of thermoresponsive chromatography is determined mainly by hydrophobic interaction between PNIPAAm and analytes. Thus, the hydrophobicity of PNIPAAm increased with the incorporation of BMA into PNIPAAm by random copolymerization, and poly(NIPAAm-*co*-BMA)-modified silica beads were used as a more hydrophobic stationary phase [58]. Poly(NIPAAm-*co*-BMA)-modified silica beads packed column can separate relatively hydrophilic analytes such as insulin fragments and amino acid phenylthiohydantoins [58,59].

To effectively separate ionic biomolecules, thermoresponsive ionic copolymers have been utilized to modulate electrostatic interactions with analytes. In 1992, Kim et al. reported that a thermoresponsive ionic copolymer exhibited a temperature-dependent ionic property change attributed to the change in the hydrophobicity of the polymer chains near the ionic functional groups [60]. Utilizing the unique property

of thermoresponsive ionic copolymers, thermoresponsive ion-exchange chromatography was developed for effective ionic biomolecules. Poly(NIPAAm-*co*-AAc-*co*-*tert*-butyl acrylamide (tBAAm))-modified silica beads packed column separated basic molecules and peptides by temperature-modulated electrostatic interaction [61,62]. On the contrary, poly(NIPAAm-*co*-*N,N*-dimethylaminopropylacrylamide (DMAPAAm)-*co*-BMA) modified silica beads packed column separate adenosine nucleotides by temperature-modulated electrostatic interaction [63].

In addition, dynamically thermoresponsive biomaterials to modulate affinity interactions with specific biomolecules have a potential for non-invasive separating systems. Hoffman et al. pioneeringly reported that thermoresponsive expansion and shrinkage of PNIPAAm molecule bound near the biotin-binding site in recombinant streptavidin controlled the binding between biotin and streptavidin [64]. They also clarified that the degree of shielding by thermoresponsive

poly(*N,N*-diethylacrylamide) (PDEAAm) depended on both the size of the biotinylated protein and the size of the PDEAAm [65]. These papers revealed that the size of a thermoresponsive polymer and a target protein and the distance between a tethered thermoresponsive polymer and a ligand are dominant for regulating thermoresponsive affinity. However, the binding process was irreversible because the affinity binding between streptavidin and biotin is typically strong (dissociation constant, $K_D = 4 \times 10^{-14}$ mol/L [66]).

For practical applications such as affinity chromatography, an effective method for the purification of proteins, thermoresponsive affinity control needs to be reversible: capturing a target protein and then releasing it on demand. Therefore, utilizing an optimal combination of ligand and protein, a new type of affinity chromatography was developed through thermoresponsive extension and shrinkage of PNIPAAm [67,68]. Both PNIPAAm and Cibacron Blue F3G-A as ligands for albumin were immobilized on polymethacrylate beads, and the prepared beads were used as affinity chromatography matrices [67]. At 37°C, PNIPAAm on the beads shrank, and Cibacron Blue F3G-A was exposed, leading to the capture of albumin. By reducing the temperature to 20°C, the shrunken PNIPAAm on the beads was extended, reducing the interaction between Cibacron Blue F3G-A and albumin and the subsequent elution of albumin from the column. Utilizing this property, the temperature-modulated separation of albumin from human serum was conducted.

Another approach to thermoresponsive affinity chromatography was developed using temperature-modulated competitive inhibition-induced shrinkage of PNIPAAm [68]. *Ricinus communis* agglutinin (RCA₁₂₀) and lactose were conjugated to PNIPAAm, and RCA₁₂₀ and lactose-conjugated PNIPAAm were modified to agarose-based Sepharose beads. At low temperatures, the beads captured asialotransferrin through the affinity between asialotransferrin and RCA₁₂₀. By increasing the temperature, PNIPAAm shrank, and conjugated RCA₁₂₀ and lactose were close, leading to the displacement of asialotransferrin with lactose from the immobilized RCA₁₂₀. Based on this property, asialotransferrin was separated by temperature modulation.

Thermoresponsive ionic copolymer brush-modified beads have been investigated as thermoresponsive protein adsorption materials. Atom transfer radical polymerization (ATRP) can graft PNIPAAm brushes onto silica beads, and the prepared beads exhibit strong hydrophobic interactions with analytes because of the large amount of PNIPAAm on the beads [69–71]. Thermoresponsive ionic copolymer brushes were prepared by introducing ionic monomers into thermoresponsive polymer brushes. The

prepared thermoresponsive ionic copolymer brush exhibited temperature-modulated strong electrostatic and hydrophobic interactions with proteins, leading to the purification of proteins [72–77]. Poly(NIPAAm-*co*-DMAAAm-*co*-tBAAm) brush-modified silica beads exhibited temperature-modulated adsorption of albumin [72]. At low temperatures, the hydrophobic interaction between the copolymer and albumin was weak because the copolymer was hydrated. In contrast, at 40°C, the copolymer dehydrated and became hydrophobic, leading to the adsorption of albumin on the copolymer brush through combined electrostatic and hydrophobic interactions. Similarly, poly(NIPAAm-*co*-2-acrylamido-2-methylpropanesulfonic acid (AMPS)-*co*-BMA) brush exhibited temperature-modulated adsorption and release of antibody drug rituximab [76].

Block copolymer brushes with bottom ionic segments exhibited effective temperature-modulated protein adsorption and desorption [78,79]. Poly(3-acrylamidopropyl trimethylammonium chloride-*b*-PNIPAAm brush-grafted silica beads exhibited temperature-modulated adsorption and desorption of milk serum proteins [78]. At high temperatures, the upper PNIPAAm segment shrank, and proteins tended to access the basal cationic segment, leading to the adsorption of proteins through combined electrostatic and hydrophobic interactions. Poly(AMPS)-*b*-PNIPAAm brushes also exhibit effective temperature-modulated adsorption of basic proteins, α-chymotrypsinogen A, and lysozyme [79].

3.2. Cell separation using thermoresponsive polymer

In tissue engineering and regenerative medicine, cell separation methods that maintain cell activity are in high demand. Thus, the PNIPAAm-modified interface has been investigated as a cell separation material that maintains cell activity (Figure 5).

The PNIPAAm brush-modified glass substrate exhibited temperature-modulated adhesion and detachment of vascular cells and myoblast at 37°C and 20°C, respectively [80]. During cell detachment from the PNIPAAm brush, endothelial cells promptly detached, whereas myoblasts gradually detached. By utilizing the difference in the detachment rate from the PNIPAAm brush, endothelial cells and myoblasts were separated.

As cells have intrinsic electrostatic properties, thermoresponsive ionic polymer brushes have been investigated to improve cell separation performance [81–84]. One example is mesenchymal stem cell (MSC) separation using a thermoresponsive cationic copolymer brush [81] (Figure 5a). MSC exhibits relatively strong anionic properties compared to other cells. Thus, MSC selectively adhered to the

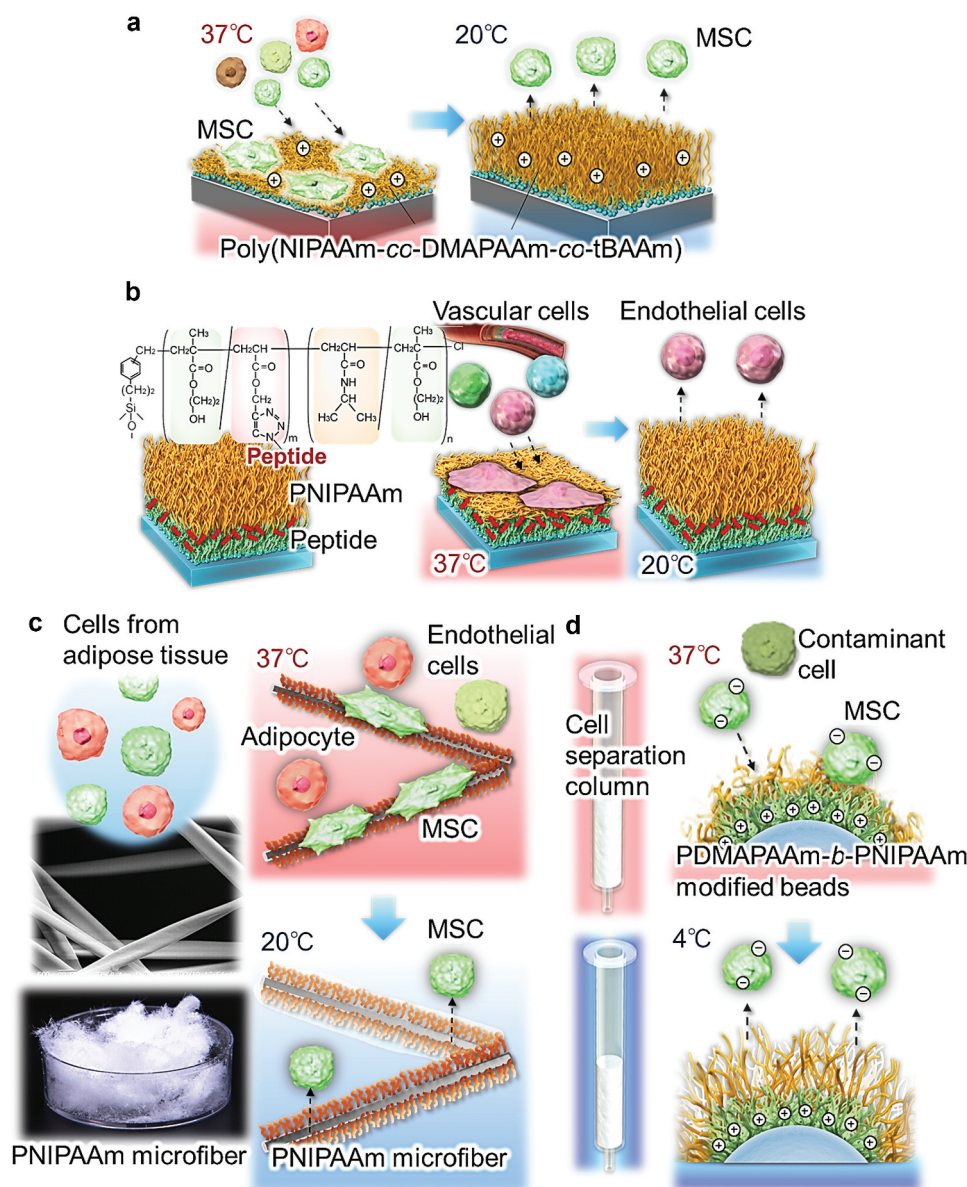


Figure 5. Schematic illustration of thermoresponsive cell separation materials. (a) Thermoresponsive cationic copolymer brush, (b) thermoresponsive polymer brush with affinity peptide, (c) thermoresponsive microfiber, and (d) thermoresponsive cell separation column.

thermoresponsive cationic polymer poly(NIPAAm-co-DMAAm-co-tBAAm) brush-grafted glass substrate, while other types of cells did not. By reducing the temperature to 20°C, the adhered MSCs on the copolymer brush were successfully recovered.

Thermoresponsive block copolymer brushes with affinity ligands have been developed for effective capture of target cells [85–87] (Figure 5b). A block copolymer brush with bottom poly(2-hydroxyethyl methacrylate (HEMA)-co-propargyl acrylate) and top poly(NIPAAm-co-HEMA) segments were prepared through two-step ATRP [85]. Then, the Arg-Glu-Asp-Val (REDV) peptide, which has an affinity for endothelial cells, was introduced into the basal layer of the block copolymer brush. At 37°C, the upper segment poly(NIPAAm-co-HEMA) shrank, and the REDV peptide was exposed on the outer surface of

the copolymer brush, leading to the capture of endothelial cells. By reducing the temperature to 20°C, the upper PNIPAAm segment was extended, leading to shielding of the affinity between the REDV peptide and endothelial cells, and the endothelial cells were recovered from the copolymer brush.

A block copolymer brush with a poly(*N*-*p*-vinylbenzyl-*O*- β -D-galactopyranosyl-(1 \rightarrow 4)-D-gluconamide) (PVLA) segment was utilized for the effective capture of hepatocytes [86]. PVLA-*b*-PNIPAAm was grafted onto a glass substrate through two steps of ATRP. At 37°C, the upper PNIPAAm shrank and the galactose moiety of the bottom PVLA was exposed to the outer surface of the copolymer brush, leading to selective adhesion of hepatocytes on the copolymer brush through the affinity between galactose and asialoglycoprotein receptor

(ASGPR) of hepatocytes. By reducing the temperature to 20°C, the PNIPAAm segment was extended, leading to a decrease in the affinity between PVLA and hepatocytes, and the hepatocytes were recovered from the copolymer brush.

To increase the throughput of cell separation, thermoresponsive polymer-modified microfibers have been investigated because they have larger surface areas than thermoresponsive polymer-modified glass substrates [88,89] (Figure 5c). At 37°C, adipose tissue-derived MSC selectively adhered to dehydrated PNIPAAm brushes on the microfibers, whereas adipocytes and endothelial cells did not. By reducing the temperature to 20°C, the PNIPAAm became hydrophilic, leading to the detachment of adhered MSC from the microfibers. Thus, PNIPAAm brush-modified microfibers can separate MSC from contaminant cells by simply changing the temperature.

PNIPAAm-modified bead-packed columns have been investigated as effective cell-separation systems [90–93]. Poly (DMAPAAm)-*b*-PNIPAAm (PDMAPAAm-*b*-PNIPAAm) brush-modified silica beads packed column was developed as a thermoresponsive MSC separation column [92] (Figure 5d). At 37°C, the upper PNIPAAm segment shrank, and the cationic property of basal PDMAPAAm was expressed, leading to the adsorption of MSC on the copolymer. In contrast, the contaminant cells did not adsorb onto the copolymer but passed through the packed beads. By reducing the temperature to 20°C, the PNIPAAm segment was extended, and the adsorbed MSCs were detached from the copolymer. Thus, the copolymer brush modified beads packed column effectively separated MSC from contaminant cells simply by changing temperature.

3.3. Thermoresponsive cell culture surfaces

Cells adhere and grow via cell-binding proteins such as fibronectin that are non-specifically adsorbed to the surface of culture substrates. These processes are typically passive and irreversible. In 1990, Okano et al.

invented and reported that the immobilization of PNIPAAm molecules onto the surface of the culture substrate, such as a tissue culture polystyrene (TCPS) dish, facilitated dynamic control of the interaction with the adsorbed proteins and cells [94]. Tethered PNIPAAm to the surface of TCPS exhibited reversible hydration/dehydration changes across the phase transition temperature of 32°C. Eventually, the PNIPAAm-grafted TCPS at 37°C showed hydrophobic, allowing cells to attach to the surface via adsorbed serum proteins in the culture medium [95,96]. Cells cultured on the hydrophobized PNIPAAm-grafted TCPS grew [97] and reached confluence as well as on TCPS (Figure 6, left).

A noteworthy feature of the PNIPAAm-grafted TCPS dish is that the interaction between the substrate and the cultured cells can be dynamically regulated only by reducing temperature. When the temperature was lowered below the LCST of PNIPAAm (e.g. 20°C), the grafted PNIPAAm became hydrated [94–96], and the confluent cells spontaneously started to detach themselves (Figure 6, middle). Finally, the contracted ‘cell sheet’ was liberated from the surface [98] (Figure 6, right). In other words, the hydration of PNIPAAm on the surface triggered a weakening of the interaction with the proteins on the bottom of the cultured cells, and the cells were detached as a contiguous sheet by the traction forces of the sheet derived from organized cytoskeleton within spread cells [99–101].

In addition, the sheet was non-invasively detached without proteolytic treatments, such as using trypsin-EDTA. Thus, the extracellular matrix (ECM) was held on the bottom of the sheet [98]. The ECM acts as a glue to adhere to another culture dish or biological tissue. The detached cell sheet is flexible and can fit to the curvature of surfaces. This feature is advantageous when attaching it to curved organs such as eyeballs or hearts, enabling efficient transplantation of cell sheet tissues. To manipulate soft cell sheets, they can be grabbed using a hydrophilic membrane through the surface tension of the medium between the sheet and membrane [10].

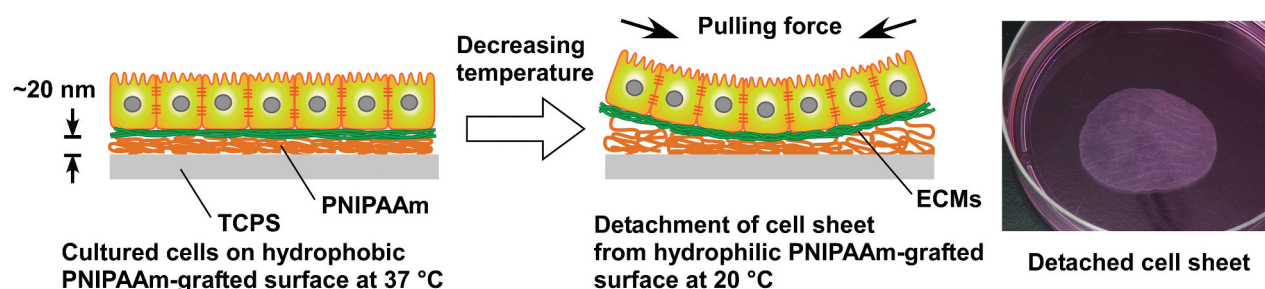


Figure 6. Cell sheet preparation using a temperature-responsive cell culture surface. PNIPAAm-grafted surface exhibits hydrophobicity and is cell adhesive at 37°C, and changes to hydrophilic and cell non-adhesive at 20°C. The PNIPAAm-grafted surface enables the cultured cells to detach themselves as a contiguous sheet only upon reducing temperature. The detached cell sheet holds ECM beneath the sheet. Reprinted from Kobayashi, J. (2019) [10] with permission from Wiley.

Electron beam (EB) polymerization was used to covalently bond crosslinked PNIPAAm to polystyrene surface [94,97]. A uniform NIPAAm monomer solution was spread on the surface of a commercially available TCPS, and then the surface was irradiated with an EB. EB-induced NIPAAm polymerization started from the main polystyrene chain, and crosslinking between PNIPAAm co-occurred. The crosslinked PNIPAAm layer was grafted onto the surface. The most critical factor in allowing cell sheet recovery by temperature change is the controlled thickness of the grafted PNIPAAm. When a grafted PNIPAAm layer of about 30 nm or more was grafted onto TCPS, cells did not adhere or spread even though the temperature was 37°C above the phase transition temperature [96]. In other words, when the thickness was about 20 nm, cell adhesion and detachment could be switched by temperature change. Recently, a thermoresponsive culture dish can be easily fabricated by the physisorption of a block copolymer composed of hydrophobic PBMA and thermoresponsive PNIPAAm using the spin-coating method [102,103]. The coated block copolymer layer on the culture dish showed high water stability owing to the hydrophobic PBMA anchor, regardless of temperature.

In recent years, various types of stimuli-responsive cell culture surfaces that respond to physical and chemical stimuli, such as light [104], electricity [105–107], and pH changes [108,109], have been reported for the fabrication of cell sheets [110]. However, light stimulation requires a light source, and high-energy radiation such as UV may damage the DNA of cells. Guillaume-Gentil et al. reported that a cell sheet on RGD peptide-conjugated polyelectrolyte-coated electrically conductive glass was detached by applying a positive potential to the glass substrate [111]. Fukuda et al. reported that cells were cultured on self-assembled monolayers of RGD peptide-conjugated alkanethiols. They reductively desorbed from the gold substrate by applying negative potential, allowing the cultured cell sheets to rapidly detach from the gold surface [105–107]. However, the detachment of cells occurs irreversibly, and voltage is required for electrical stimulation by a device. On the other hand, a useful feature of thermal control is that cell sheets can be collected using commodity equipment such as a temperature-controlled incubator. Another advantage is that a wealth of knowledge has been accumulated regarding recovering and manipulating cell sheets using thermoresponsive culture dishes.

Noting that biological tissues have a similar structure to laminated sheets, we proposed ‘cell sheet engineering’, a method of reconstructing three-dimensional (3D) tissue structures by laminating cell sheets [10,112]. Specifically, this method involves attaching a detached cell sheet to another cell sheet and repeatedly laminating them to construct 3D

tissue. To date, the first clinical applications in humans using single-layer or laminated autologous cell sheet transplants were conducted to regenerate corneal epithelium, myocardium, esophagus, periodontal ligament, and cartilage. Recent clinical applications of cell sheet transplantation were summarized in another paper [113].

Furthermore, next-generation thermoresponsive culture surfaces that mimic the extracellular matrix, such as cell adhesion and affinity binding with growth factors, were designed. For example, a PNIPAAm-grafted surface modified with heparin can immobilize various heparin-binding proteins, such as basic fibroblast growth factor (bFGF) [114,115] and heparin-binding epidermal growth factor-like growth factor (HB-EGF) [116,117], through affinity interaction. The immobilized heparin molecules and heparin-binding proteins formed complexes that maintain their activity; eventually, the heparin-modified PNIPAAm-grafted culture surface continuously stimulated cultured cells. The surface bound with bFGF accelerated fibroblasts’ proliferation and sheet formation [114]. Meanwhile, the surface bound with HB-EGF inhibited the dedifferentiation of hepatocytes and maintained liver-specific functions [116,117]. More importantly, the swelling/shrinkage changes of PNIPAAm chains caused by temperature can be used to dynamically control the affinity interaction between heparin and heparin-binding proteins through multi-point binding. When the temperature was lowered to 20°C, below the LCST of PNIPAAm, the affinity interaction between heparin and heparin-binding proteins weakened as the PNIPAAm chains swelled and extended, and heparin-binding growth factors were recovered along with the detached cultured cells [114,116]. Thus, the heparin-modified PNIPAAm-grafted culture surface can simultaneously achieve sustained stimulation of cell receptors by heparin-binding proteins and cell sheet recovery by lowering the temperature.

Dynamically, thermoresponsive hydrogels can fabricate 3D structures to form cell tissues of various shapes. Healy et al. proposed that shrunken PNIPAAm hydrogels at body temperature (37 °C) were utilized for efficient cell transplantation, while loosely crosslinked PNIPAAm hydrogels were fluidic as an injectable support at room temperature [118]. Many types of thermoresponsive injectable materials have recently been proposed to apply stem cell transplantation therapies [119]. Matsumoto et al. proposed using a PNIPAAm hydrogel template with various shapes to fabricate large-size aggregates of bone marrow-derived MSCs [120]. The aggregates were detached by lowering the temperature due to the volume change of the PNIPAAm hydrogel template. At the same time, the hydrophilicity of the gel surface was maintained over a wide temperature range. Shin

et al. reported the preparation of thermoresponsive Tetronic[®]-tyramine hydrogel immobilized with cell-adhesive fibronectin via polydopamine coating for imparting cell adhesiveness [121]. A cell sheet cultured on the gel was mechanically detached due to the contraction of the gel on lowering the temperature, allowing the cell sheet to be readily manipulated and transplanted [122,123]. Together, dynamically thermoresponsive biomaterials enable various tissue engineering applications, including 3D organization and easy manipulation, expanding the feasibility of tissue engineering for the application of regenerative therapy.

4. Conclusions

Dynamically thermoresponsive biomaterials have opened up the possibility of various biomedical applications. Furthermore, it is expected that they will be combined with multiple modalities, such as medical devices, diagnostic devices, and regenerative therapies. Thermoresponsive nanocarriers are expected to achieve more precise and location-specific drug delivery in combination with hyperthermia or high-intensity focused ultrasound. In addition, separation technology using thermoresponsive chromatography facilitates the accurate separation of biomolecule-based drugs such as antibodies, cell sources for cell therapy, and tissue engineering. Combining cell sheet engineering with automated robotics for cell sheet manipulation will be promising for the large-scale production of clinical-grade tissues [124,125]. In the future, newly developed biomaterials, including dynamically thermoresponsive PNIPAAm, are highly expected to expand the opportunity for novel treatment technologies.

Acknowledgments

The abstract of this paper was prepared using ChatGPT to create a draft from the author's manuscript, which the authors then revised. The grammar of this paper was checked with the assistance of Grammarly.

Disclosure statement

No potential conflict of interest was reported by the author(s).

Notes on contributors



Dr. Jun Kobayashi obtained his B. S. and M.S. degrees at Waseda University, Tokyo, Japan. He received his Ph.D. degree in Chemical Engineering from Waseda University in 2003. In 2003, he carried out his postdoctoral research at the Institute of Advanced Biomedical Engineering and Science at Tokyo Women's Medical University

(TWMU), Tokyo, Japan. Since 2004, he joined TWMU as Research Assistant Professor, and as Assistant Professor in 2011. Present research topics are intelligent thermoresponsive surfaces for tissue engineering, especially in hepatic tissue engineering.



Dr. Masamichi Nakayama received his B.S., M.S., and Ph.D. degrees from Kyushu University in 1996, 1998, and 2001, respectively. Since 2001, he has worked as Research Assistant Professor at the Institute of Advanced Biomedical Engineering and Science, Tokyo Women's Medical University, and worked as Assistant Professor since 2008. He has been conducting research on the molecular design and physico-chemistry of well-defined polymeric materials via living radical polymerization. Based on his research background, he has developed smart drug delivery systems using thermoresponsive block copolymer micelles and smart culture surfaces for controlled cell adhesion in response to physical stimuli.



Dr. Kenichi Nagase received his B.S., M.S., and Ph.D. from Waseda University in 2000, 2002, and 2005, respectively. From 2005 to 2007, he held a Postdoctoral Position at Tokyo Women's Medical University. From 2007 to 2017, he worked as an assistant professor and lecturer at the Institute of Advanced Biomedical and Science, Tokyo Women's Medical University. From 2017 to 2024, he worked as an Associate Professor at Faculty of Pharmacy, Keio University. From 2024, he has worked as a Professor at Graduate School of Biomedical and Health Sciences, Hiroshima University. His research interests include functional polymers, bioseparation, analytical chemistry and regenerative medicine.

ORCID

Jun Kobayashi <http://orcid.org/0000-0003-0493-6386>

Masamichi Nakayama <http://orcid.org/0000-0002-5484-583X>

Kenichi Nagase <http://orcid.org/0000-0002-6575-0107>

Author contributions

J.K. designed the framework of this review article. M. N. wrote the manuscript on thermoresponsive biomaterials for controlled release. K.N. wrote the manuscript on thermoresponsive chromatography and cell separation. J.K. wrote the other parts. J.K., M.N., and K.N. coedited the manuscript and approved the final version of the manuscript.

References

- [1] Schild HG. Poly(N-isopropylacrylamide): experiment, theory and application. *Prog In Polym Sci.* 1992;17(2):163–249. doi: 10.1016/0079-6700(92)90023-R

- [2] Ward MA, Georgiou TK. Thermoresponsive polymers for biomedical applications. *Polymers*. 2011;3(3):1215–1242. doi: [10.3390/polym3031215](#)
- [3] Akash MS, Rehman K. Recent progress in biomedical applications of pluronic (PF127): pharmaceutical perspectives. *J Control Release*. 2015;209:120–138. doi: [10.1016/j.jconrel.2015.04.032](#)
- [4] Bae YH, Okano T, Kim SW. Temperature dependence of swelling of crosslinked poly(n,n'-alkyl substituted acrylamides) in water. *J Polym Sci B Polym Phys*. 1990;28(6):923–936. doi: [10.1002/polb.1990.090280609](#)
- [5] Ono Y, Shikata T. Hydration and dynamic behavior of poly(n-isopropylacrylamide)s in aqueous solution: a sharp phase transition at the lower critical solution temperature. *J Am Chem Soc*. 2006;128(31):10030–10031. doi: [10.1021/ja063990i](#)
- [6] Heskins M, Guillet JE. Solution properties of Poly (N-isopropylacrylamide). *J Macromol Sci Part A Chem*. 1968;2(8):1441–1455. doi: [10.1080/10601326808051910](#)
- [7] Cole MA, Voelcker NH, Thissen H, et al. Stimuli-responsive interfaces and systems for the control of protein–surface and cell–surface interactions. *Biomaterials*. 2009;30(9):1827–1850. doi: [10.1016/j.biomaterials.2008.12.026](#)
- [8] Nakayama M, Akimoto J, Okano T. Polymeric micelles with stimuli-triggering systems for advanced cancer drug targeting. *J Drug Target*. 2014;22(7):584–599. doi: [10.3109/1061186X.2014.936872](#)
- [9] Nagase K, Yamato M, Kanazawa H, et al. Poly (N-isopropylacrylamide)-based thermoresponsive surfaces provide new types of biomedical applications. *Biomaterials*. 2018;153:27–48.
- [10] Kobayashi J, Kikuchi A, Aoyagi T, et al. Cell sheet tissue engineering: cell sheet preparation, harvesting/manipulation, and transplantation. *J Biomed Mater Res A*. 2019;107(5):955–967. doi: [10.1002/jbm.a.36627](#)
- [11] Vancoillie G, Frank D, Hoogenboom R. Thermoresponsive poly(oligo ethylene glycol acrylates). *Prog in Polym Sci*. 2014;39(6):1074–1095. doi: [10.1016/j.progpolymsci.2014.02.005](#)
- [12] Hoogenboom R. Poly(2-oxazoline)s: a polymer class with numerous potential applications. *Angew Chem Int Ed Engl*. 2009;48(43):7978–7994. doi: [10.1002/anie.200901607](#)
- [13] Lutz JF, Akdemir O, Hoth A. Point by point comparison of two thermosensitive polymers exhibiting a similar LCST: is the age of poly(nipam) over? *J Am Chem Soc*. 2006;128(40):13046–13047. doi: [10.1021/ja065324n](#)
- [14] Lutz J-F, Weichenhan K, Akdemir Ö, et al. About the phase transitions in aqueous solutions of thermoresponsive copolymers and hydrogels based on 2-(2-methoxyethoxy)ethyl methacrylate and Oligo(ethylene glycol) methacrylate. *Macromolecules*. 2007;40(7):2503–2508. doi: [10.1021/ma062925q](#)
- [15] Hoogenboom R, Thijs HM, Jochems MJ, et al. Tuning the LCST of poly(2-oxazoline)s by varying composition and molecular weight: alternatives to poly(n-isopropylacrylamide)? *Chem Commun*. 2008;2008(44):5758–5760. doi: [10.1039/b813140f](#)
- [16] Okano T, Bae YH, Jacobs H, et al. Thermally on-off switching polymers for drug permeation and release. *J Control Release*. 1990;11(1–3):255–265.
- [17] Yoshida R, Uchida K, Kaneko Y, et al. Comb-type grafted hydrogels with rapid deswelling response to temperature changes. *Nature*. 1995;374(6519):240–242. doi: [10.1038/374240a0](#)
- [18] Kaneko Y, Nakamura S, Sakai K, et al. Rapid deswelling response of poly(N-isopropylacrylamide) hydrogels by the formation of water release channels using poly(ethylene oxide) graft chains. *Macromolecules*. 1998;31(18):6099–6105. doi: [10.1021/ma971899g](#)
- [19] Tanaka T, Fillmore DJ. Kinetics of swelling of gels. *J Chem Phys*. 1979;70(3):1214. doi: [10.1063/1.437602](#)
- [20] Li J, Mooney DJ. Designing hydrogels for controlled drug delivery. *Nat Rev Mater*. 2016;1(12). doi: [10.1038/natrevmats.2016.71](#)
- [21] Park TG, Hoffman AS. Estimation of temperature-dependent pore size in poly(n-isopropylacrylamide) hydrogel beads. *Biotechnol Prog*. 1994;10(1):82–86. doi: [10.1021/bp00025a010](#)
- [22] Okano T. Biorelated polymers and gels : controlled release and applications in biomedical engineering. San Diego: Academic Press; 1998. English. (Series in polymers, interfaces, and biomaterials).
- [23] Yoshida R, Sakai K, Ukano T, et al. Surface-modulated skin layers of thermal responsive hydrogels as on-off switches: I Drug Release. *J Biomater Sci Polym Ed*. 1991;3(2):155–162. doi: [10.1163/156856291X00250](#)
- [24] Ebara M, Aoyagi T, Sakai K, et al. Introducing reactive carboxyl side chains retains phase transition temperature sensitivity in N-Isopropylacrylamide copolymer gels. *Macromolecules*. 2000;33(22):8312–8316. doi: [10.1021/ma000121j](#)
- [25] L-C D, Hoffman AS. A novel approach for preparation of pH-sensitive hydrogels for enteric drug delivery. *J Control Release*. 1991;15(2):141–152.
- [26] Chen G, Hoffman AS. Graft copolymers that exhibit temperature-induced phase transitions over a wide range of pH. *Nature*. 1995;373(6509):49–52. doi: [10.1038/373049a0](#)
- [27] Annaka M, Tanaka C, Nakahira T, et al. Fluorescence study on the swelling behavior of comb-type grafted Poly(N-isopropylacrylamide) hydrogels. *Macromolecules*. 2002;35(21):8173–8179. doi: [10.1021/ma020683y](#)
- [28] Aoyagi T, Ebara M, Sakai K, et al. Novel bifunctional polymer with reactivity and temperature sensitivity. *J Biomater Sci Polym Ed*. 2000;11(1):101–110. doi: [10.1163/156856200743526](#)
- [29] Ebara M, Aoyagi T, Sakai K, et al. The incorporation of carboxylate groups into temperature-responsive poly(n-isopropylacrylamide)-based hydrogels promotes rapid gel shrinking. *J Polym Sci A Polym Chem*. 2001;39(3):335–342. doi: [10.1002/1099-0518\(20010201\)39:3<335::AID-POLA1000>3.0.CO;2-H](#)
- [30] Wu XS, Hoffman AS, Yager P. Synthesis and characterization of thermally reversible macroporous poly(N-isopropylacrylamide) hydrogels. *J Polym Sci A Polym Chem*. 2003;30(10):2121–2129. doi: [10.1002/pola.1992.080301005](#)
- [31] Matsumura Y, Maeda H. A new concept for macromolecular therapeutics in cancer chemotherapy: mechanism of tumor tropic accumulation of proteins and the antitumor agent smancs. *Cancer Res*. 1986;46:6387–6392.
- [32] Park J, Choi Y, Chang H, et al. Alliance with EPR effect: combined strategies to improve the EPR effect

- in the tumor microenvironment. *Theranostics*. 2019;9(26):8073–8090. doi: [10.7150/thno.37198](#)
- [33] van Rhooen Gc, Franckena M, Ten Hagen TLM, et al. A moderate thermal dose is sufficient for effective free and TSL based thermochemotherapy. *Adv Drug Deliv Rev*. 2020;163–164:145–156. doi: [10.1016/j.addr.2020.03.006](#)
- [34] Riaz MK, Riaz MA, Zhang X, et al. Surface functionalization and targeting strategies of liposomes in solid tumor therapy: a review. *Int J Mol Sci*. 2018;19(1):195.
- [35] Kneidl B, Peller M, Winter G, et al. Thermosensitive liposomal drug delivery systems: state of the art review. *Int J Nanomedicine*. 2014;9:4387–4398. doi: [10.2147/IJN.S49297](#)
- [36] Ringsdorf H, Schlarb B, Venzmer J. Molecular architecture and function of polymeric oriented systems: models for the study of organization, surface recognition, and dynamics of biomembranes. *Angew Chem Int Ed Engl*. 2003;27(1):113–158. doi: [10.1002/anie.198801131](#)
- [37] Klivanov AL, Maruyama K, Torchilin VP, et al. Amphipathic polyethyleneglycols effectively prolong the circulation time of liposomes. *FEBS Lett*. 1990;268(1):235–237. doi: [10.1016/0014-5793\(90\)81016-H](#)
- [38] Yatvin MB, Weinstein JN, Dennis WH, et al. Design of liposomes for enhanced local release of drugs by hyperthermia. *Science*. 1978;202(4374):1290–1293. doi: [10.1126/science.364652](#)
- [39] Borys N, Dewhirst MW. Drug development of lyso-thermosensitive liposomal doxorubicin: combining hyperthermia and thermosensitive drug delivery. *Adv Drug Deliv Rev*. 2021;178:113985. doi: [10.1016/j.addr.2021.113985](#)
- [40] Kono K. Thermosensitive polymer-modified liposomes. *Adv Drug Deliv Rev*. 2001;53(3):307–319. doi: [10.1016/S0169-409X\(01\)00204-6](#)
- [41] Amin M, Lammers T, Ten Hagen TLM. Temperature-sensitive polymers to promote heat-triggered drug release from liposomes: towards bypassing EPR. *Adv Drug Deliv Rev*. 2022;189:114503. doi: [10.1016/j.addr.2022.114503](#)
- [42] Ringsdorf H, Venzmer J, Winnik FM. INteraction of hydrophobically-modified poly- N - isopropylacrylamides with Model Membranes—or PlayiNg a molecular Accordion. *Angew Chem Int Ed Engl*. 2003;30(3):315–318. doi: [10.1002/anie.199103151](#)
- [43] Wu X, Hoffman A, Yager P. Conjugation of phosphatidylethanolamine to poly(*N*-isopropylacrylamide) for potential use in liposomal drug delivery systems. *Polymer*. 1992;33(21):4659–4662. doi: [10.1016/0032-3861\(92\)90432-V](#)
- [44] Kono K, Ozawa T, Yoshida T, et al. Highly temperature-sensitive liposomes based on a thermosensitive block copolymer for tumor-specific chemotherapy. *Biomaterials*. 2010;31(27):7096–7105. doi: [10.1016/j.biomaterials.2010.05.045](#)
- [45] Kwon GS, Kataoka K. Block copolymer micelles as long-circulating drug vehicles. *Adv Drug Deliv Rev*. 2012;64:237–245.
- [46] Cammas S, Suzuki K, Sone C, et al. Thermo-responsive polymer nanoparticles with a core-shell micelle structure as site-specific drug carriers. *J Control Release*. 1997;48(2–3):157–164. doi: [10.1016/S0168-3659\(97\)00040-0](#)
- [47] Chung JE, Yokoyama M, Suzuki K, et al. Reversibly thermo-responsive alkyl-terminated poly (*N*-isopropylacrylamide) core-shell micellar structures. *Colloids Surfaces B: Biointerfaces*. 1997;9(1–2):37–48. doi: [10.1016/S0927-7765\(97\)00015-5](#)
- [48] Chung JE, Yokoyama M, Okano T. Inner core segment design for drug delivery control of thermo-responsive polymeric micelles. *J Control Release*. 2000;65(1–2):93–103. doi: [10.1016/S0168-3659\(99\)00242-4](#)
- [49] Kohori F, Sakai K, Aoyagi T, et al. Preparation and characterization of thermally responsive block copolymer micelles comprising poly (*N*-isopropylacrylamide-*b*-DL-lactide). *J Control Release*. 1998;55(1):87–98. doi: [10.1016/S0168-3659\(98\)00023-6](#)
- [50] Chung JE, Yokoyama M, Yamato M, et al. Thermo-responsive drug delivery from polymeric micelles constructed using block copolymers of poly (*N*-isopropylacrylamide) and poly(butylmethacrylate). *J Control Release*. 1999;62(1–2):115–127. doi: [10.1016/S0168-3659\(99\)00029-2](#)
- [51] Nakayama M, Okano T, Miyazaki T, et al. Molecular design of biodegradable polymeric micelles for temperature-responsive drug release. *J Control Release*. 2006;115(1):46–56. doi: [10.1016/j.jconrel.2006.07.007](#)
- [52] Akimoto J, Nakayama M, Sakai K, et al. Temperature-induced intracellular uptake of thermoresponsive polymeric micelles. *Biomacromolecules*. 2009;10(6):1331–1336. doi: [10.1021/bm900032r](#)
- [53] Akimoto J, Nakayama M, Sakai K, et al. Synthesis of terminal-functionalized thermoresponsive diblock copolymers using biodegradable macro-raft agents. *Polym J*. 2012;45(2):233–237. doi: [10.1038/pj.2012.108](#)
- [54] Nakayama M, Okano T. Polymer terminal group effects on properties of thermoresponsive polymeric micelles with controlled outer-shell chain lengths. *Biomacromolecules*. 2005;6(4):2320–2327. doi: [10.1021/bm050232w](#)
- [55] Nakayama M, Okano T. Unique thermoresponsive polymeric micelle behavior via cooperative polymer corona phase transitions. *Macromolecules*. 2008;41(3):504–507. doi: [10.1021/ma071775w](#)
- [56] Nakayama M, Kawahara Y, Akimoto J, et al. pH-induced phase transition control of thermoresponsive nano-micelles possessing outermost surface sulfonamide moieties. *Colloids Surfaces B: Biointerfaces*. 2012;99:12–19. doi: [10.1016/j.col surfb.2011.09.028](#)
- [57] Kanazawa H, Yamamoto K, Matsushima Y, et al. Temperature-responsive chromatography using poly (*N*-isopropylacrylamide)-modified silica. *Anal Chem*. 1996;68(1):100–105. doi: [10.1021/ac950359j](#)
- [58] Kanazawa H, Kashiwase Y, Yamamoto K, et al. Temperature-responsive liquid chromatography. 2. Effects of hydrophobic groups in *N*-isopropylacrylamide copolymer-modified silica. *Anal Chem*. 1997;69(5):823–830. doi: [10.1021/ac961024k](#)
- [59] Kanazawa H, Sunamoto T, Matsushima Y, et al. Temperature-responsive chromatographic separation of amino acid phenylthiohydantions using aqueous media as the mobile phase. *Anal Chem*. 2000;72(24):5961–5966. doi: [10.1021/ac0004658](#)

- [60] Feil H, Bae YH, Feijen J, et al. Mutual influence of pH and temperature on the swelling of ionizable and thermosensitive hydrogels. *Macromolecules*. 2002;25(20):5528–5530. doi: [10.1021/ma00046a063](#)
- [61] Kobayashi J, Kikuchi A, Sakai K, et al. Aqueous chromatography utilizing hydrophobicity-modified anionic temperature-responsive hydrogel for stationary phases. *J Chromatogr A*. 2002;958(1–2):109–119. doi: [10.1016/S0021-9673\(02\)00388-6](#)
- [62] Kobayashi J, Kikuchi A, Sakai K, et al. Cross-linked thermoresponsive anionic polymer-grafted surfaces to separate bioactive basic peptides. *Anal Chem*. 2003;75(13):3244–3249. doi: [10.1021/ac026364m](#)
- [63] Kikuchi A, Kobayashi J, Okano T, et al. Temperature-modulated interaction changes with Adenosine nucleotides on intelligent cationic, thermoresponsive Surfaces1. *J Bioact And Compatible Polym*. 2007;22(6):575–588. doi: [10.1177/0883911507084294](#)
- [64] Stayton PS, Shimoboji T, Long C, et al. Control of protein–ligand recognition using a stimuli-responsive polymer. *Nature*. 1995;378(6556):472–474. doi: [10.1038/378472a0](#)
- [65] Ding Z, Fong RB, Long CJ, et al. Size-dependent control of the binding of biotinylated proteins to streptavidin using a polymer shield. *Nature*. 2001;411(6833):59–62. doi: [10.1038/35075028](#)
- [66] Green NM. Avidin and streptavidin. *Methods Enzymol*. 1990;184:51–67.
- [67] Yoshizako K, Akiyama Y, Yamanaka H, et al. Regulation of protein binding toward a ligand on chromatographic matrixes by masking and forced-releasing effects using thermoresponsive polymer. *Anal Chem*. 2002;74(16):4160–4166. doi: [10.1021/ac025523z](#)
- [68] Yamanaka H, Yoshizako K, Akiyama Y, et al. Affinity chromatography with collapsibly tethered ligands. *Anal Chem*. 2003;75(7):1658–1663. doi: [10.1021/ac0263768](#)
- [69] Nagase K, Kobayashi J, Kikuchi A, et al. Interfacial property modulation of thermoresponsive polymer brush surfaces and their interaction with biomolecules. *Langmuir*. 2007;23(18):9409–9415. doi: [10.1021/la700956b](#)
- [70] Nagase K, Kobayashi J, Kikuchi A, et al. Effects of graft densities and chain lengths on separation of bioactive compounds by nanolayered thermoresponsive polymer brush surfaces. *Langmuir*. 2008;24(2):511–517. doi: [10.1021/la701839s](#)
- [71] Nagase K, Kobayashi J, Kikuchi A, et al. High stability of thermoresponsive polymer-brush-grafted silica beads as chromatography matrices. *ACS Appl Mater Interfaces*. 2012;4(4):1998–2008. doi: [10.1021/am201832b](#)
- [72] Nagase K, Kobayashi J, Kikuchi A, et al. Thermally-modulated on/off-adsorption materials for pharmaceutical protein purification. *Biomaterials*. 2011;32(2):619–627. doi: [10.1016/j.biomaterials.2010.09.012](#)
- [73] Nagase K, Yuk SF, Kobayashi J, et al. Thermoresponsive protein adsorbing materials for purifying pharmaceutical protein on exposed charging surface. *J Mater Chem*. 2011;21(8):2590–2593. doi: [10.1039/C0JM03453C](#)
- [74] Nagase K, Geven M, Kimura S, et al. Thermoresponsive copolymer brushes possessing quaternary amine groups for strong anion-exchange chromatographic matrices. *Biomacromolecules*. 2014;15(3):1031–1043. doi: [10.1021/bm401918a](#)
- [75] Nagase K, Kobayashi J, Kikuchi A, et al. Thermoresponsive anionic copolymer brushes containing strong acid moieties for effective separation of basic biomolecules and proteins. *Biomacromolecules*. 2014;15(10):3846–3858. doi: [10.1021/bm5012163](#)
- [76] Nagase K, Ishii S, Ikeda K, et al. Antibody drug separation using thermoresponsive anionic polymer brush modified beads with optimised electrostatic and hydrophobic interactions. *Sci Rep*. 2020;10(1):11896. doi: [10.1038/s41598-020-68707-7](#)
- [77] Nagase K, Suzuki S, Kanazawa H. Temperature-modulated interactions between thermoresponsive strong cationic copolymer-brush-grafted silica beads and biomolecules. *Heliyon*. 2024;10(15):e34668. doi: [10.1016/j.heliyon.2024.e34668](#)
- [78] Nagase K, Kobayashi J, Kikuchi A, et al. Protein separations via thermally responsive ionic block copolymer brush layers. *RSC Adv*. 2016;6(31):26254–26263. doi: [10.1039/C6RA01061J](#)
- [79] Nagase K, Kobayashi J, Kikuchi A, et al. Thermoresponsive anionic block copolymer brushes with a strongly anionic bottom segment for effective interactions with biomolecules. *RSC Adv*. 2016;6(95):93169–93179. doi: [10.1039/C6RA20944K](#)
- [80] Nagase K, Kimura A, Shimizu T, et al. Dynamically cell separating thermo-functional biointerfaces with densely packed polymer brushes. *J Mater Chem*. 2012;22(37):19514–19522. doi: [10.1039/c2jm31797d](#)
- [81] Nagase K, Hatakeyama Y, Shimizu T, et al. Thermoresponsive cationic copolymer brushes for mesenchymal stem cell separation. *Biomacromolecules*. 2015;16(2):532–540. doi: [10.1021/bm501591s](#)
- [82] Nagase K, Uchikawa N, Hirotani T, et al. Thermoresponsive anionic copolymer brush-grafted surfaces for cell separation. *Colloids Surf B Biointerfaces*. 2020;185:110565. doi: [10.1016/j.col surfb.2019.110565](#)
- [83] Nagase K, Ota A, Hirotani T, et al. Thermoresponsive cationic block copolymer brushes for temperature-modulated stem cell separation. *Macromol Rapid Commun*. 2020;41(19):e2000308. doi: [10.1002/marc.202000308](#)
- [84] Hirotani T, Nagase K. Temperature-modulated separation of vascular cells using thermoresponsive-anionic block copolymer-modified glass. *Regen Ther*. 2024;27:259–267. doi: [10.1016/j.reth.2024.03.009](#)
- [85] Nagase K, Shimura M, Shimane R, et al. Selective capture and non-invasive release of cells using a thermoresponsive polymer brush with affinity peptides. *Biomater Sci*. 2021;9(3):663–674. doi: [10.1039/D0BM01453B](#)
- [86] Nagase K, Kojima N, Goto M, et al. Thermoresponsive block copolymer brush for temperature-modulated hepatocyte separation. *J Mater Chem B*. 2022;10(42):8629–8641. doi: [10.1039/D2TB01384C](#)
- [87] Nagase K, Shimane R. Ethylene glycol-based thermoresponsive block copolymer brushes with cell-affinity peptides for thermally controlled interaction with target cells. *Mater & Des*. 2023;233:112234. doi: [10.1016/j.matdes.2023.112234](#)
- [88] Nagase K, Sakurada Y, Onizuka S, et al. Thermoresponsive polymer-modified microfibers

- for cell separations. *Acta Biomater.* **2017**;53:81–92. doi: [10.1016/j.actbio.2017.02.033](https://doi.org/10.1016/j.actbio.2017.02.033)
- [89] Nagase K, Shukuwa R, Takahashi H, et al. Enhanced mechanical properties and cell separation with thermal control of PIPAAm-brushed polymer-blend microfibers. *J Mater Chem B.* **2020**;8(28):6017–6026. doi: [10.1039/D0TB00972E](https://doi.org/10.1039/D0TB00972E)
- [90] Nagase K, Mukae N, Kikuchi A, et al. Thermally modulated retention of lymphocytes on polymer-brush-grafted glass beads. *Macromol Biosci.* **2012**;12(3):333–340. doi: [10.1002/mabi.201100283](https://doi.org/10.1002/mabi.201100283)
- [91] Nagase K, Inanaga D, Ichikawa D, et al. Temperature-modulated cell-separation column using temperature-responsive cationic copolymer hydrogel-modified silica beads. *Colloids Surf B Biointerfaces.* **2019**;178:253–262. doi: [10.1016/j.colsurfb.2019.02.057](https://doi.org/10.1016/j.colsurfb.2019.02.057)
- [92] Nagase K, Edatsune G, Nagata Y, et al. Thermally-modulated cell separation columns using a thermoresponsive block copolymer brush as a packing material for the purification of mesenchymal stem cells. *Biomater Sci.* **2021**;9(21):7054–7064. doi: [10.1039/D1BM00708D](https://doi.org/10.1039/D1BM00708D)
- [93] Nagase K, Okada A, Matsuda J, et al. A thermoresponsive cationic block copolymer brush-grafted silica bead interface for temperature-modulated separation of adipose-derived stem cells. *Colloids Surf B Biointerfaces.* **2022**;220:112928. doi: [10.1016/j.colsurfb.2022.112928](https://doi.org/10.1016/j.colsurfb.2022.112928)
- [94] Yamada N, Okano T, Sakai H, et al. Thermoresponsive polymeric surfaces; control of attachment and detachment of cultured cells. *Makromol Chem Rapid Commun.* **1990**;11(11):571–576. doi: [10.1002/marc.1990.030111109](https://doi.org/10.1002/marc.1990.030111109)
- [95] Kobayashi J, Arisaka Y, Yui N, et al. Effect of temperature changes on serum protein adsorption on Thermoresponsive cell-culture surfaces monitored by a quartz crystal microbalance with dissipation. *Int J Mol Sci.* **2018**;19(5):1516. doi: [10.3390/ijms19051516](https://doi.org/10.3390/ijms19051516)
- [96] Akiyama Y, Kikuchi A, Yamato M, et al. Ultrathin poly(n-isopropylacrylamide) grafted layer on polystyrene surfaces for cell adhesion/detachment control. *Langmuir.* **2004**;20(13):5506–5511. doi: [10.1021/la036139f](https://doi.org/10.1021/la036139f)
- [97] Okano T, Yamada N, Sakai H, et al. A novel recovery system for cultured cells using plasma-treated polystyrene dishes grafted with poly(n-isopropylacrylamide). *J Biomed Mater Res.* **1993**;27(10):1243–1251. doi: [10.1002/jbm.820271005](https://doi.org/10.1002/jbm.820271005)
- [98] Kushida A, Yamato M, Konno C, et al. Decrease in culture temperature releases monolayer endothelial cell sheets together with deposited fibronectin matrix from temperature-responsive culture surfaces. *J Biomed Mater Res.* **1999**;45(4):355–362. doi: [10.1002/\(SICI\)1097-4636\(19990615\)45:4<355::AID-JBM10>3.0.CO;2-7](https://doi.org/10.1002/(SICI)1097-4636(19990615)45:4<355::AID-JBM10>3.0.CO;2-7)
- [99] Okano T, Yamada N, Okuhara M, et al. Mechanism of cell detachment from temperature-modulated, hydrophilic-hydrophobic polymer surfaces. *Biomaterials.* **1995**;16(4):297–303. doi: [10.1016/0142-9612\(95\)93257-E](https://doi.org/10.1016/0142-9612(95)93257-E)
- [100] Yamato M, Okuhara M, Karikusa F, et al. Signal transduction and cytoskeletal reorganization are required for cell detachment from cell culture surfaces grafted with a temperature-responsive polymer. *J Biomed Mater Res.* **1999**;44(1):44–52. doi: [10.1002/\(SICI\)1097-4636\(199901\)44:1<44::AID-JBM5>3.0.CO;2-X](https://doi.org/10.1002/(SICI)1097-4636(199901)44:1<44::AID-JBM5>3.0.CO;2-X)
- [101] Yamato M, Konno C, Kushida A, et al. Release of adsorbed fibronectin from temperature-responsive culture surfaces requires cellular activity. *Biomaterials.* **2000**;21(10):981–986. doi: [10.1016/S0142-9612\(99\)00239-2](https://doi.org/10.1016/S0142-9612(99)00239-2)
- [102] Nakayama M, Yamada N, Kumashiro Y, et al. Thermoresponsive Poly(N-isopropylacrylamide)-based block copolymer coating for optimizing cell sheet fabrication. *Macromol Biosci.* **2012**;12(6):751–760. doi: [10.1002/mabi.201200018](https://doi.org/10.1002/mabi.201200018)
- [103] Nakayama M, Toyoshima Y, Chinen H, et al. Water stable nanocoatings of poly(n-isopropylacrylamide)-based block copolymers on culture insert membranes for temperature-controlled cell adhesion. *J Mater Chem B.* **2020**;8(34):7812–7821. doi: [10.1039/D0TB01113D](https://doi.org/10.1039/D0TB01113D)
- [104] Liu C, Zhou Y, Sun M, et al. Light-induced cell alignment and harvest for anisotropic cell sheet technology. *ACS Appl Mater Interfaces.* **2017**;9(42):36513–36524. doi: [10.1021/acsami.7b07202](https://doi.org/10.1021/acsami.7b07202)
- [105] Seto Y, Inaba R, Okuyama T, et al. Engineering of capillary-like structures in tissue constructs by electrochemical detachment of cells. *Biomaterials.* **2010**;31(8):2209–2215. doi: [10.1016/j.biomaterials.2009.11.104](https://doi.org/10.1016/j.biomaterials.2009.11.104)
- [106] Sadr N, Zhu M, Osaki T, et al. Sam-based cell transfer to photopatterned hydrogels for microengineering vascular-like structures. *Biomaterials.* **2011**;32(30):7479–7490. doi: [10.1016/j.biomaterials.2011.06.034](https://doi.org/10.1016/j.biomaterials.2011.06.034)
- [107] Inaba R, Khademhosseini A, Suzuki H, et al. Electrochemical desorption of self-assembled monolayers for engineering cellular tissues. *Biomaterials.* **2009**;30(21):3573–3579. doi: [10.1016/j.biomaterials.2009.03.045](https://doi.org/10.1016/j.biomaterials.2009.03.045)
- [108] Shahin-Shamsabadi A, Pr S. π -sacs: pH induced self-assembled cell sheets without the need for modified surfaces. *ACS Biomater Sci Eng.* **2020**;6(9):5346–5356. doi: [10.1021/acsbiomaterials.0c01073](https://doi.org/10.1021/acsbiomaterials.0c01073)
- [109] Lee T-J, Wu T, Park JH, et al. Enzyme free cell detachment using pH-responsive poly(amino ester) for tissue regeneration. *J Ind And Eng Chem.* **2020**;88:373–381. doi: [10.1016/j.jiec.2020.05.007](https://doi.org/10.1016/j.jiec.2020.05.007)
- [110] Pu C, Lin R, Liang S, et al. Smart surface-based cell sheet engineering for regenerative medicine. *Trends In Chem.* **2023**;5(1):88–101. doi: [10.1016/j.trechm.2022.11.001](https://doi.org/10.1016/j.trechm.2022.11.001)
- [111] Guillaume-Gentil O, Akiyama Y, Schuler M, et al. Polyelectrolyte coatings with a potential for electronic control and cell sheet engineering. *Adv Mater.* **2008**;20(3):560–565. doi: [10.1002/adma.200700758](https://doi.org/10.1002/adma.200700758)
- [112] Yamato M, Okano T. Cell sheet engineering. *Mater Today.* **2004**;7(5):42–47. doi: [10.1016/S1369-7021\(04\)00234-2](https://doi.org/10.1016/S1369-7021(04)00234-2)
- [113] Kobayashi J. Clinical and pre-clinical application of cell sheet engineering. Routledge resources online - polymers, polymeric materials, and polymer technology. London: Taylor & Francis Group; under review.
- [114] Arisaka Y, Kobayashi J, Yamato M, et al. Switching of cell growth/detachment on heparin-functionalized thermoresponsive surface for rapid cell sheet fabrication and manipulation. *Biomaterials.* **2013**;34(17):4214–4222. doi: [10.1016/j.biomaterials.2013.02.056](https://doi.org/10.1016/j.biomaterials.2013.02.056)
- [115] Onodera Y, Kobayashi J, Mitani S, et al. Terminus-selective covalent immobilization of heparin on a thermoresponsive surface using click chemistry for efficient binding of basic fibroblast growth factor. *Macromol Biosci.* **2024**;24(2):e2300307. doi: [10.1002/mabi.202300307](https://doi.org/10.1002/mabi.202300307)
- [116] Arisaka Y, Kobayashi J, Ohashi K, et al. A heparin-modified thermoresponsive surface with

- heparin-binding epidermal growth factor-like growth factor for maintaining hepatic functions in vitro and harvesting hepatocyte sheets. *Regenerative Ther.* **2016**;3:97–106. doi: [10.1016/j.reth.2016.03.003](https://doi.org/10.1016/j.reth.2016.03.003)
- [117] Kobayashi J, Arisaka Y, Yui N, et al. Preservation of heparin-binding egf-like growth factor activity on heparin-modified poly(n-isopropylacrylamide)-grafted surfaces. *RSC Adv.* **2021**;11(59):37225–37232. doi: [10.1039/D1RA07317F](https://doi.org/10.1039/D1RA07317F)
- [118] Stile RA, Burghardt WR, Healy KE. Synthesis and characterization of injectable Poly (N-isopropylacrylamide)-based hydrogels that support tissue formation in vitro. *Macromolecules.* **1999**;32(22):7370–7379. doi: [10.1021/ma990130w](https://doi.org/10.1021/ma990130w)
- [119] Marquardt LM, Heilshorn SC. Design of injectable materials to improve stem cell transplantation. *Curr STEM Cell Rep.* **2016**;2(3):207–220. doi: [10.1007/s40778-016-0058-0](https://doi.org/10.1007/s40778-016-0058-0)
- [120] Sasaki J, Asoh TA, Matsumoto T, et al. Fabrication of three-dimensional cell constructs using temperature-responsive hydrogel. *Tissue Eng Part A.* **2010**;16(8):2497–2504. doi: [10.1089/ten.tea.2009.0523](https://doi.org/10.1089/ten.tea.2009.0523)
- [121] Jun I, Kim SJ, Choi E, et al. Preparation of biomimetic hydrogels with controlled cell adhesive properties and topographical features for the study of muscle cell adhesion and proliferation. *Macromol Biosci.* **2012**;12(11):1502–1513. doi: [10.1002/mabi.201200148](https://doi.org/10.1002/mabi.201200148)
- [122] Jun I, Kim SJ, Lee J-H, et al. Transfer printing of cell layers with an anisotropic extracellular matrix Assembly using cell-interactive and thermosensitive hydrogels. *Adv Funct Mater.* **2012**;22(19):4060–4069. doi: [10.1002/adfm.201200667](https://doi.org/10.1002/adfm.201200667)
- [123] Jun I, Lee YB, Choi YS, et al. Transfer stamping of human mesenchymal stem cell patches using thermally expandable hydrogels with tunable cell-adhesive properties. *Biomaterials.* **2015**;54:44–54. doi: [10.1016/j.biomaterials.2015.03.016](https://doi.org/10.1016/j.biomaterials.2015.03.016)
- [124] Kikuchi T, Shimizu T, Wada M, et al. Automatic fabrication of 3-dimensional tissues using cell sheet manipulator technique. *Biomaterials.* **2014**;35(8):2428–2435. doi: [10.1016/j.biomaterials.2013.12.014](https://doi.org/10.1016/j.biomaterials.2013.12.014)
- [125] Kikuchi T, Kino-Oka M, Wada M, et al. A novel, flexible and automated manufacturing facility for cell-based health care products: tissue factory. *Regenerative Ther.* **2018**;9:89–99. doi: [10.1016/j.reth.2018.08.004](https://doi.org/10.1016/j.reth.2018.08.004)