


 Cite this: *RSC Adv.*, 2023, 13, 21171

Rational design for the fabrication of bulk Ni₃Sn₂ alloy catalysts for the synthesis of 1,4-pentanediol from biomass-derived furfural without acidic co-catalysts†

 Rodiansono,^a Atina Sabila Azzahra,^b Pathur Razi Ansyah,^c Sadang Husain^d and Shogo Shimazu^e

This study describes the rational design for the fabrication of bulk Ni₃Sn₂ alloy catalysts for the de/hydration–hydrogenation of biomass-derived furfural (FFald) to 1,4-pentanediol (1,4-PeD) without the acidic co-catalyst. The presence of both hydration active sites (Brønsted acid sites (Ni–SnO_x)) and hydrogenation active sites (Ni⁰ or Ni–Sn alloy) in Ni₃Sn₂ alloy could be controlled by changing the pH of Ni–Sn solution during the preparation. Both active sites acted synergistically to catalyse the de/hydration–hydrogenation reactions of FFald to produce a high yield of 1,4-PeD in a batch reaction system at 433 K, 3.0 MPa H₂ after 12 h. Bulk Ni₃Sn₂ obtained at pH of Ni–Sn solution of 8–10, hydrothermal temperature of 423 K for 24 h, and reduction with H₂ at 673 K for 1.5 h demonstrated a high yield of 1,4-PeD (81–87%), which is comparable with that from previous work. A 76% yield of 1,4-PeD was also obtained when the reaction was carried out in a fixed-bed reaction system at 433 K, flow rate 0.065 mL min^{−1}, H₂ flow rate 70 mL min^{−1}, and 3.29 wt% FFald in H₂O/ethanol solution for 12 h. The activity of bulk Ni₃Sn₂ was maintained with 66% yield of 1,4-PeD even after 52 h reaction on stream. The fabricated bulk Ni₃Sn₂ alloy catalysts could be the promising heterogeneous Ni–Sn alloy-based catalysts for the catalytic conversion of biomass-derived-furanic compounds (e.g., FFald, furfuryl alcohol (FFalc), and 2-methylfuran (2-MeF)).

 Received 31st May 2023
 Accepted 28th June 2023

DOI: 10.1039/d3ra03642a

rsc.li/rsc-advances

Introduction

The utilization of renewable biomass and its derived chemical platforms are involved in more important roles to reduce the dependence on non-renewable fossil fuel-based resources through the production of building block monomers of C5 α,ω -diols, including 1,2-pentanediol (1,2-PeD), 1,4-pentanediol (1,4-PeD), and 1,5-pentanediol (1,5-PeD).^{1,2} The C5 α,ω -diols from renewable feedstocks have attracted much attention as they are

promising building blocks for direct replacement of 1,4-butanediol (1,4-BeD) or 1,6-hexanediol (1,6-HeD) from fossil fuel-based in the production of polyesters and thermoplastic polyurethanes.³ Furfural (FFald), a tremendous C5-furan-based chemical platform, is well-known as a substrate for the synthesis of those monomer C5 α,ω -diols using heterogeneous catalysts.^{4–7} The established approaches for the transformation of FFald into C5 α,ω -diols were devoted to the assertion of the C–O hydrogenolysis of tetrahydrofurfuryl alcohol (THFalc), which can be obtained from total hydrogenation of both C=C and C=O bonds of FFald (Fig. 1(#1)). Bimetallic platinum group metals (PGM) (e.g., Pt, Pd, Rh, Ir, Ru, Ni, etc.) in combination with oxophilic metal oxide (e.g., Re, Mo, Ce, Y or W) catalysts have been extensively studied and provided moderate to high yield 1,2- or 1,5-PeD.^{6,8–15} Another approach is the combination between supported PGM catalyst and acidic metal oxide (e.g., γ -Al₂O₃, Nb₂O₅) through the dual ring-opening tautomerisation (hydration/dehydration) and hydrogenation reactions of derived-THFalc pyran or dihydropyran to 1,5-PeD as proposed by Dumesic's group.^{16,17}

The catalytic conversion of C5-furan precursors (e.g., FFald, furfuryl alcohol (FFalc)) to 1,4-PeD is less attractive than that of other C5 α,ω -diols due to some shortcomings (e.g., the

^aDepartment of Chemistry, Lambung Mangkurat University, Jl. A. Yani Km 36, Banjarbaru, Indonesia 70714. E-mail: rodiansono@ulm.ac.id; Fax: +62 5114773112; Tel: +62 5114773112

^bInorganic Materials & Catalysis Laboratory (IMCat), Catalysis for Sustainable Energy and Environment (CATSuRe), Lambung Mangkurat University, Banjarbaru, Indonesia

^cDepartment of Mechanical Engineering, Lambung Mangkurat University, Jl. A. Yani Km 36, Banjarbaru, Indonesia 70714

^dDepartment of Physics, Lambung Mangkurat University, Jl. A. Yani Km 35, Banjarbaru, Indonesia 70714

^eGraduate School of Engineering, Chiba University, 1-33 Yayoi, Inage-ku, Chiba, Japan 263-8522

[†]Research Collaboration Center for Tin Metal, Faculty of Engineering, Universitas Sultan Ageng Tirtayasa, Jl. Jenderal Sudirman Km 3, Cilegon, Indonesia

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ra03642a>



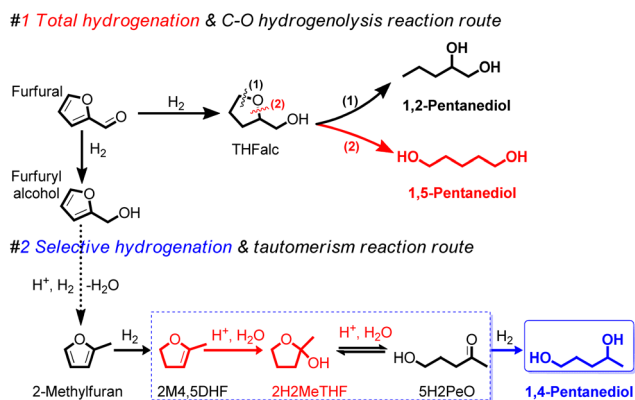


Fig. 1 Conceivable routes for the synthesis of C5 α,ω -diols of 1,2-PeD, 1,5-PeD, and 1,4-PeD from FFald, FFalc, and 2-MeF platforms using bimetallic Ni–Sn alloy catalysts *via* dual selective hydrogenation–tautomerism reactions.^{20,26} PeD = pentenediol. THFalc = tetrahydrofurfuryl alcohol. 2H2MeTHF = 2-hydroxy-2-methyl tetrahydrofuran. 2M4,5DHF = 2-methyl-4,5-dihydrofuran. 5H2PeO = 5-hydroxy-2-pentanone.

requirement of a selective and bifunctional-type catalyst, addition of acidic co-catalyst, or assertion of multiple reaction steps).¹⁸ Leuck *et al.* claimed that trace amounts of glacial acetic acid are substantially required to convert FFald to 1,4-PeD (40%) and 1,2,5-(1,4,5)-pentanetriol (~50%) in the presence of RANEY® Ni catalyst.¹⁹ Schniepp *et al.* reported that a trace amount of formic acid was added to the reaction mixture of 2-methylfuran (2-MeF) in the presence of Ni/Celite catalyst (at H₂ 8.3 MPa, 423 K for 8 h), affording a mixture of 2-methyltetrahydrofuran (2-MeTHF) (36%) and 1,4-PeD (62%).²⁰ In the presence of ReO_x-modified Pd–Ir/SiO₂ or Rh–Ir/SiO₂ catalyst system, the Brønsted acid sites in the catalysts may facilitate the side reactions such as hydration or dehydration, which are the important reaction steps for catalytic conversion of FFald to 1,4-PeD. However, the selectivity of 1,4-PeD was not so high (23%).^{21,22} Liu *et al.* combined Ru/CMK-3 or Ru–FeO_x/AC catalysts and Amberlyst-15 as the acidic co-catalyst for the catalytic reaction of FFald and produced a high yield of 1,4-PeD (up to 90%).^{23,24} Most recently, Cui *et al.* developed bifunctional ruthenium nanoparticles supported on sulfonated carbon layer coated SBA-15 (Ru/SC-SBA-15) catalysts for conversion of FFald and an 86% selectivity of 1,4-PeD was obtained, which is three times higher than that of unmodified Ru/C-SBA-15 catalyst.²⁵ However, the presence of acidic co-catalysts may lead to the formation of undesired products through over-dehydration or polymerization and severely cause the leaching out of active metal catalysts under severe conditions. Therefore, the development of new heterogeneous catalysts with surface acidity (*e.g.*, Brønsted acid sites) without an acidic co-catalyst for the dual hydration–hydrogenation of FFald, FFalc, or 2-methylfuran (2-MeF) into 1,4-PeD is challenging.

The development of heterogeneous bimetallic Ni-based catalysts for the transformation of biomass-derived C5-furan compounds has been a long-standing work in our group. Bulk Ni–Sn(*x*) alloys (*x* = 1.5, 2.0, 3.0 and 4.0, Ni/Sn molar ratio) catalysts have shown very good catalytic performance and

reusability in the chemoselective hydrogenation of α,β -unsaturated carbonyl compounds to unsaturated alcohol,²⁷ hydrogenation of LA to GVL,²⁸ and the one-pot conversion of FFald to high yield of 1,4-PeD (61–92%) under mild conditions (433 K, 3.0 MPa H₂, 12 h) in the ethanol/H₂O mixture solvent and without the presence of acidic co-catalyst.²⁶ The best bulk Ni₃Sn₂ alloy catalyst was obtained at pH 8 of Ni–Sn solution at 423 K for 24 h, and reduction with H₂ at 673 K for 1.5 h.

In the present paper, we report an extended work on the fabrication of bulk Ni₃Sn₂ alloy by revisiting the effect of various synthetic parameters including pH of Ni–Sn solution, additive polyol, hydrothermal time, hydrothermal temperature, and reduction temperature. The bulk Ni₃Sn₂ alloy catalysts were employed for the conversion of furfural to 1,4-PeD from FFald under identical reaction conditions to those from literature.^{26,27} We found that bulk Ni₃Sn₂ alloy catalyst synthesized at pH = 6–10, hydrothermal time of 24–48 h, polyol additives of ethylene glycol (EG), glycerol (G), or 2-methoxy-ethanol (2Me-EtOH), and temperature reduction of 673 K for 1.5 h allowed a high yield of 1,4-PeD (87%), which is comparable with that of previous results over bulk and supported Ni–Sn(*x*) alloy catalysts (92%).^{26,29} This catalyst might be served as a bifunctional catalyst, which comprises two active sites of Ni–Sn alloy riched-Ni⁰ (as Lewis acid) and Ni–SnO_x or support (Brønsted acid). The Ni–Sn alloy enriched Ni⁰ is active and selective for the hydrogenation of C=O in FFald to solely FFalc,²⁷ while the Ni–SnO_x species or support can serve as Brønsted acid sites for the hydration or hydrogenolysis.³⁰ Both active sites played the key role in the synergistic dual reactions of de/hydration as well as hydrogenation/hydrogenolysis of FFald to 1,4-PeD in acidulated H₂O or H₂O/ethanol solvent (Fig. 1(#2)).

Results and discussion

Catalytic reaction

Effect of pH of Ni–Sn solution. In the first set experiment, we evaluated the catalytic performance of various bulk Ni₃Sn₂ obtained at different pH of Ni–Sn solution for the conversion of biomass-derived FFald to 1,4-PeD at 433 K, 3.0 MPa H₂ for 12 h, and the results are shown in Fig. 2.

Using the Ni₃Sn₂ catalyst obtained at pH = 4, 100% FFald was converted to 1% 1,5-PeD, 43% THFalc, 13% 2H2MeTHF, 10% 2-MeTHF, and 33% others (it may be the condensation product of FFald or FFalc according to GC and GC-MS data) without the formation of 1,4-PeD at full conversion of FFald at 433 K, 3.0 MPa H₂ after 12 h. When the pH of Ni–Sn solution was increased to 6 (Ni₃Sn₂ pH = 6), 12% 1,4-PeD was first observed, however, relatively high yields of FFalc (22%), THFalc (38%), and 2H2MeTHF (20%) were also obtained. Interestingly, a high yield of 1,4-PeD (87%) was obtained over Ni₃Sn₂ pH = 8 catalyst, whereas the side products were 1,2- and 1,5-PeD (5%), 2H2MeTHF (7%), and 2-MeTHF (1%). This is the highest yield of 1,4-PeD (87%) obtained at present, which is comparable with the previous result using the same Ni–Sn catalysts,²⁶ or with the previous results over Ru-based catalysts in the presence of an acidic co-catalyst.^{23–25,31} Further increase in pH of Ni–Sn solution to 10 (Ni₃Sn₂ pH = 10) afforded a quite high yield of 1,4-PeD

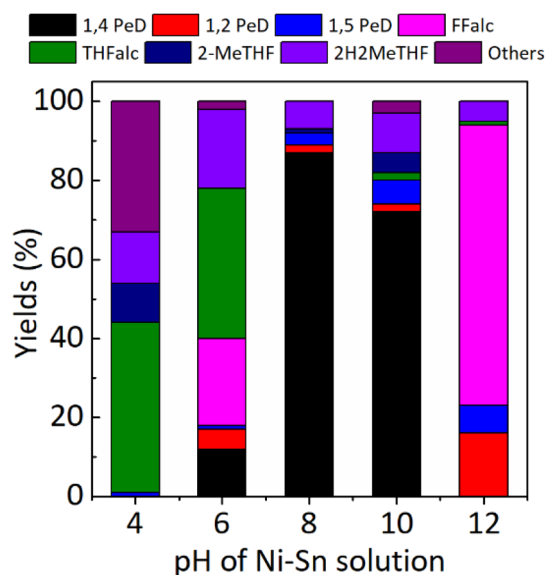


Fig. 2 Yield of 1,4-PeD obtained over bulk Ni_3Sn_2 catalysts synthesised at different pH of Ni-Sn solution. Catalysts were reduced with H_2 at 673 K for 1.5 h. Reaction conditions: catalyst, 44 mg; substrate, 1.2 mmol; solvent, ethanol/ H_2O , 3.5 mL (1.5 : 2.0 volume ratio); 433 K, initial H_2 pressure 3.0 MPa, 12 h.

(72%), however, the side products of 2H2MeTHF, 2-MeTHF, and others remained 10%, 5%, and 3%, respectively. In contrast, the Ni_3Sn_2 pH = 12 catalyst produced 16% 1,2-PeD, 7% 1,5-PeD, 71% FFalc, 1% THFalc, and 5% 2H2MeTHF without the formation of 1,4-PeD. A high yield of remaining FFalc (71%) suggested that the Ni_3Sn_2 pH = 12 catalyst is selective toward C=O hydrogenation of FFald and inactive to catalyse the dual hydrolysis-hydrogenation reactions to form the final product of 1,4-PeD. To gain more understanding of these results, the catalyst structure-activity relationship upon these catalysts will be discussed later in this paper.

Kinetic studies. To understand more about how the active species of Ni and Ni-Sn and the surface acidity of bulk Ni_3Sn_2 alloy catalysts synergistically played a prominent role in the hydration-hydrogenation of FFald to 1,4-PeD, kinetically controlled catalytic reactions were examined for three types of bulk Ni_3Sn_2 catalysts at different pH (pH = 8, 10, 12) and the results are shown in Fig. 3. At the early reaction time of 0.5–1.0 h, for the Ni_3Sn_2 pH = 8 catalyst (total acidity = $276 \mu\text{mol g}^{-1}$), the FFald conversion was 44–84% to produce only FFalc. At the same time, the conversions of FFald over Ni_3Sn_2 pH = 10 (total acidity = $129 \mu\text{mol g}^{-1}$) and 12 (total acidity = $18 \mu\text{mol g}^{-1}$) were 13–55% and 7–12%, respectively. However, at 1.5 h, 100% conversion of FFald was achieved by using Ni_3Sn_2 pH = 8 catalyst, and at this time, the 1,4-PeD was first formed (3.7%) and then increased to achieve 48.7% as the reaction time was prolonged to 3 h. On the other hand, the amount of FFalc decreased smoothly to reach around 14%, meanwhile, other side products *e.g.*, THFalc, 2-MeTHF, 2H2MeTHF, and 1,2- and 1,5-PeD mixtures, increased slowly. The kinetic profiles and product distributions over the Ni_3Sn_2 pH = 10 catalyst were identical to those of the Ni_3Sn_2 pH = 8 catalyst. The similar

results are likely due to their similar surface acidities, which not only improve the selectivity towards 1,4-PeD but also the reaction rate for FFalc formation (Fig. 3). In contrast, over the Ni_3Sn_2 pH = 12 catalyst, the conversion of FFald was 23% after 1.5 h and increased slowly to 76% after 6 h. These results indicate that the Ni_3Sn_2 pH = 12 catalyst is unsuitable for the hydration-hydrogenation of FFald to 1,4-PeD due to the lower surface acidity. The reaction rate of FFalc formation, as the elementary step of the reaction, over three types of Ni_3Sn_2 catalysts was roughly calculated at a reaction time of 30 min (0.5 h). Over Ni_3Sn_2 pH = 8, the reaction rate of FFalc formation was $12.83 \times 10^{-3} \text{ mmol min}^{-1}$ (43% conversion), while over Ni_3Sn_2 pH = 10 and pH = 12, the reaction rates were $8.68 \times 10^{-3} \text{ mmol min}^{-1}$ (13% conversion) and $2.68 \times 10^{-3} \text{ mmol min}^{-1}$ (7% conversion), respectively.

Effect of hydrothermal time. To establish the synthetic procedure of highly selective bulk Ni_3Sn_2 alloy catalysts towards 1,4-PeD, we prepared bulk Ni_3Sn_2 alloy at hydrothermal times of 6 h, 12 h, 24 h, 48 h, and 72 h and tested for the synthesis of 1,4-PeD; the results are shown in Fig. 4. Bulk Ni_3Sn_2 catalyst synthesised at hydrothermal time of 6–12 h afforded only 6% of 1,4-PeD, whereas the main product was others (condensation reaction of FFald (64%)) or THFalc (78%) as the result of total hydrogenation of FFald. The yield of 1,4-PeD remarkably increased to 87% over the bulk Ni_3Sn_2 catalyst that was obtained at a hydrothermal time of 24 h. When the hydrothermal time was prolonged at 48 h and 72 h, the yield of 1,4-PeD slightly decreased to 68% and 62%, respectively. Over these catalysts, quite a high yield of 1,5-PeD (8–11%) was also observed. Although the XRD patterns of bulk Ni_3Sn_2 alloy obtained at different hydrothermal times showed no notable differences (Fig. S1 and Table S4, in the ESI[†]), the reaction results confirmed that the Ni_3Sn_2 alloy obtained at 24 h of hydrothermal time was the most effective catalyst (Fig. 2–4). Therefore, it can be concluded that the optimised hydrothermal time for the synthesis of bulk Ni_3Sn_2 catalyst was 24 h, pH adjustment = 8 and 10 or by employing the appropriated support oxides *c.a.* $\gamma\text{-Al}_2\text{O}_3$ or commercial-aluminium hydroxide (*c*-ALOH) containing gibbsite and bayerite structures.³²

Effect of polyol additives and hydrothermal temperature. To clarify the importance of polyol additives during the synthesis of bulk Ni_3Sn_2 catalysts, ethylene glycol (EG) and glycerol (G) were employed instead of the 2-methoxy ethanol (Me-EtOH) and without the addition of polyols for comparison and the XRD patterns of the results are shown in Fig. S2 and S3, in the ESI[†]. The presence of EG, G, or 2-Me-EtOH polyols significantly affected the formation of Ni_3Sn_2 alloy phases and their crystallinity, whereas upon without polyols resulted in lower crystallinity of $\text{Ni}_3\text{Sn}_2(102)$ and $\text{Ni}_3\text{Sn}_2(110)$ (Fig. S3 and Table S5, in the ESI[†]).^{28,33} The results of 1,4-PeD synthesis from FFald using bulk Ni_3Sn_2 pH = 8 alloy catalysts synthesised at different conditions are summarised in Table 1. Both Ni_3Sn_2 (EG, pH = 8, 673 K/ H_2) and (G, pH = 8, 673 K/ H_2) catalysts gave a high yield of 1,4-PeD, *c.a.* 82% and 81%, respectively (entries 2 and 3), which are comparable to Ni_3Sn_2 (2-Me-EtOH, pH = 8; 673 K/ H_2 (entry 1)). In contrast, the Ni_3Sn_2 catalyst synthesised in the absence of EG/G or Me-EtOH produced only 14% 1,4-PeD, which

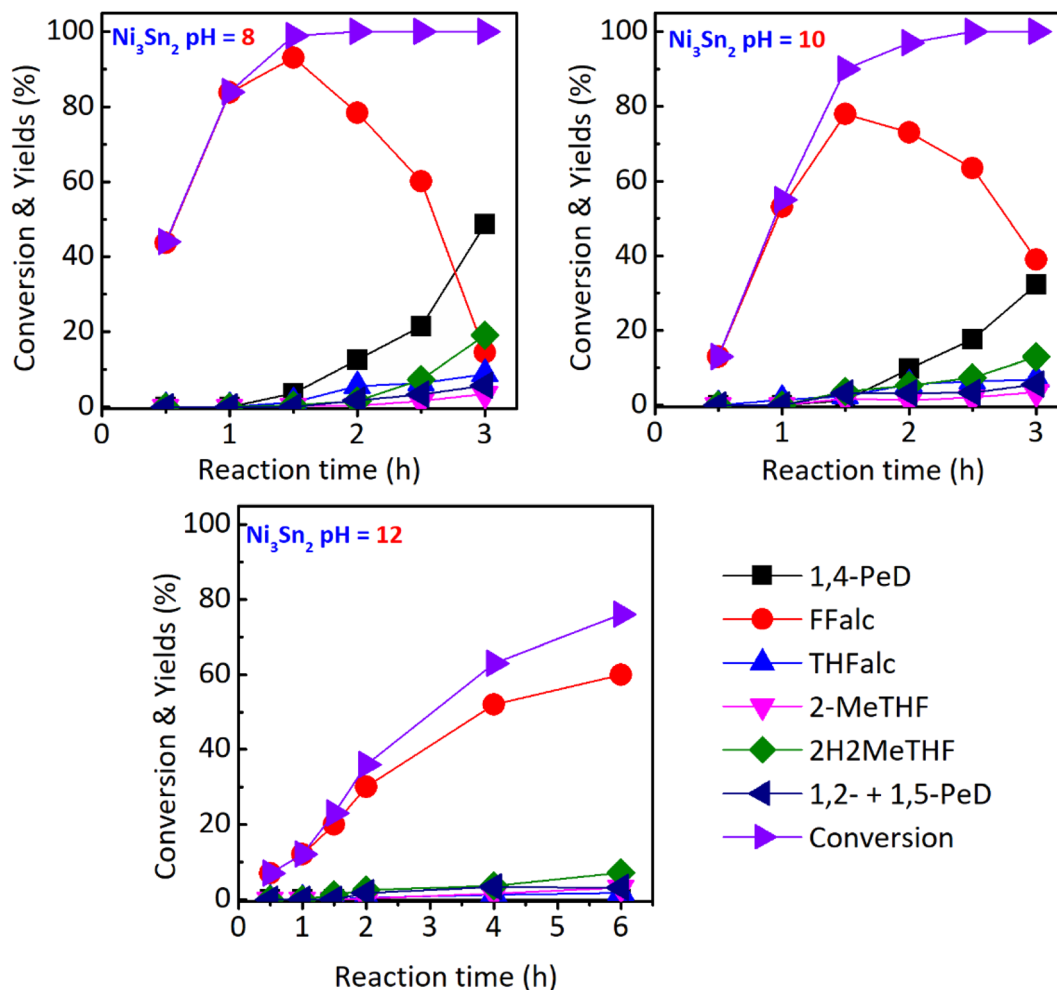


Fig. 3 Kinetic profiles of three types of bulk Ni_3Sn_2 catalysts in the hydration-hydrogenation of FFald 1,4-PeD. Reaction conditions: catalyst, 44 mg; substrate, 1.2 mmol; solvent, ethanol/ H_2O , 3.5 mL (1.5 : 2.0 volume ratio); 433 K, initial H_2 pressure 3.0 MPa, 0–6 h.

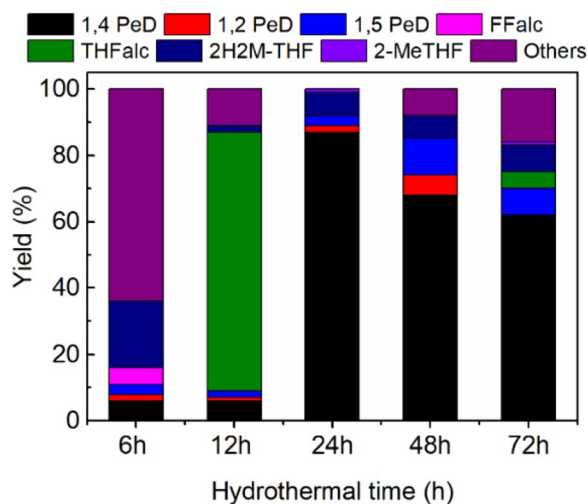


Fig. 4 Yield of 1,4-PeD obtained over bulk Ni_3Sn_2 catalysts synthesised at different hydrothermal times. Catalysts were reduced with H_2 at 673 K for 1.5 h. Reaction conditions are referred to in Fig. 2.

is lower than the yield of 1,2- and 1,5-PeD (28%) (entry 4). So that, we then concluded both the pH of the Ni-Sn solution and the presence of polyol additive are important to obtain the selective bulk Ni_3Sn_2 alloy catalyst for 1,4-PeD synthesis from FFald. Next, we evaluated the effect of hydrothermal temperature (423 K, 473 K, and 523 K for 24 h; the XRD patterns are shown in Fig. S4, in the ESI†) on the 1,4-PeD from FFald hydration-hydrogenation reactions. Bulk Ni_3Sn_2 synthesised at 423 K exhibited the highest yield of 1,4-PeD, as mentioned above. In contrast, bulk Ni_3Sn_2 obtained at hydrothermal temperatures of 473 K and 523 K catalysts were not selective towards 1,4-PeD (entries 5 and 6). Additionally, the bulk Ni_3Sn_2 pH = 8 catalyst was found to be stable even after exposure to the air for 2 months. Obviously, a high yield of 1,4-PeD (79%) was obtained at 100% FFald conversion (entry 7). Therefore, it can be concluded that the optimised hydrothermal temperature was 423 K for 24 h and easy to handle during the preparation as well as the catalytic reaction.

Effect of reduction temperature. The effect of reduction temperature on the FFald conversion and 1,4-PeD yield was examined over the most effective Ni_3Sn_2 catalyst obtained at pH

Table 1 Results of the selective synthesis of 1,4-PeD from FFald using bulk Ni₃Sn₂ pH = 8 alloy catalysts synthesised at different conditions^a

Entry	Catalyst ^b	Conv. ^c (%)	Yield ^c (%)							
			1,4-PeD	1,2-PeD	1,5-PeD	FFalc	THFalc	2H2MeTHF	2-MeTHF	Others ^d
1	Ni ₃ Sn ₂ (2-Me-EtOH; pH = 8; 24 h; 673 K/H ₂)	100	87	2	3	0	0	7	1	0
2	Ni ₃ Sn ₂ (EG; pH = 8; 24 h; 673 K/H ₂)	100	82	1	0	0	0	16	1	0
3	Ni ₃ Sn ₂ (G; pH = 8; 24 h; 673 K/H ₂)	100	81	3	2	0	0	11	3	0
4	Ni ₃ Sn ₂ (without polyol; pH = 8; 673 K/H ₂)	100	14	16	12	0	22	36	0	0
5 ^e	Ni ₃ Sn ₂ (HT 473 K; pH = 8; 673 K/H ₂)	100	15	0	1	0	2	35	12	36
6 ^e	Ni ₃ Sn ₂ (HT 523 K; pH = 8; 673 K/H ₂)	100	3	5	3	0	7	22	0	61
7 ^f	Ni ₃ Sn ₂ (2-Me-EtOH; pH = 8; 24 h; 673 K/H ₂)	100	79	1	2	0	0	11	0	10
8 ^g	Ni ₃ Sn ₂ (2-Me-EtOH; pH = 8; 24 h; 673 K/H ₂)	100	83	0	5	0	0	12	0	0

^a Reaction conditions: catalyst, 44 mg; substrate, 1.2 mmol; solvent, ethanol/H₂O, 3.5 ml (1.5 : 2.0 volume ratio); initial H₂ pressure, 3.0 MPa, 433 K, 12 h. ^b The bulk Ni₃Sn₂ catalysts were synthesized at various conditions. ^c Conversion of FFald and yield of the product were determined by GC and GC-MS analyses using an internal standard technique. ^d Unknown product may be the condensation product of FFald or FFalc according to GC and GC-MS data. ^e HT = hydrothermal at 473 K and 523 K. ^f The catalyst was stored in a sample bin under exposure to the air for 2 months. ^g Recyclability test after the fourth reaction run in the batch reactor system. The recovered catalyst was reactivated by H₂ at 673 K for 1 h before reuse for the next run.

of 8, with the presence of 2-Me-EtOH, at 423 K for 24 h and the results are shown in Fig. 5. The reduction with H₂ was conducted at temperatures of 573–873 K for 1.5 h. Bulk Ni₃Sn₂ catalyst activated at 573 K converted 96% of FFald and produced 1,4-PeD (45%), 1,2- and 1,5-PeD mixture (7%), THFalc (8%), 2H₂MeTHF (31%) and 2-MeTHF (11%). The highest yield of 1,4-PeD (87%) was obtained over the Ni₃Sn₂ catalyst activated at 673 K for 3 h. When the temperature reduction was furtherly increased to 773 K and 873 K, the conversion of FFald and the yield of 1,4-PeD decreased to 57–91% and 31–61%, respectively. It was found that the conversion of FFald increased as the reduction temperature was increased from 573 K (96%) to 673 K (100%), then gradually decreased as the reduction temperature was increased to 773 K (91%) and 873 K (57% conversion). This volcano-type activity relationship verified that less activity and

selectivity were mainly due to the massive aggregation of Ni or Ni-Sn particles at high temperatures. The XRD analysis results confirmed that the diffraction peaks of the Ni₃Sn₂ alloy phases at $2\theta = 30.6$, 43.3 , and 44.3° corresponding to Ni₃Sn₂(101), Ni₃Sn₂(102), and Ni₃Sn₂(110), respectively, intensified when the temperature reductions were increased to 673–873 K (Fig. S5, in the ESI[†]). The average crystallite sizes of Ni₃Sn₂(101) in bulk Ni₃Sn₂ 673 K/H₂; 773 K/H₂; and 873 K/H₂ were 17.0 nm; 26.5 nm; and 28.4 nm, respectively (Tables S1, S2 and S6, in the ESI[†]). In addition, this suggestion is consistent with the fact that the specific surface area BET (S_{BET}) drastically decreased from 9.7–12.0 m² g⁻¹ (573 and 673 K) to 1.7–2.9 m² g⁻¹ after reduction at 773 K and 873 K, respectively.³³

Catalyst structure–activity relationship

The results of hydration–hydrogenation of FFald to 1,4-PeD over various bulk Ni₃Sn₂ catalysts synthesised at different synthetic parameters confirmed that the pH of Ni–Sn solution, hydrothermal temperature, the temperature of reduction, and the presence of polyols additives were important for the fabrication of bulk Ni₃Sn₂ alloy catalysts.³⁴ Fig. 6 shows the XRD patterns of the as-prepared (after hydrothermal processes) and the presence of NiO, Ni(OH)₂, SnO, and SnO₂ phases were clearly observed in all of the samples. The diffraction peak of SnO ($2\theta = 30.6^\circ$) and NiO ($2\theta = 43.7^\circ$) gradually intensified when the pH of the Ni–Sn solution was increased. On the other hand, the diffraction peak at $2\theta = 26.4^\circ$ that can be assigned to SnO₂ was observed in samples of pH = 6–8. Both nickel and tin ions will exist in the forms of metal-oxides or hydroxides, which depend on the pH of the solution system (Pourbaix diagram).³⁵ This might affect the formation of a well-crystallite Ni₃Sn₂ alloy during the reduction with H₂. However, unfortunately, the as-prepared bulk Ni–Sn alloys are inactive for the hydration–hydrogenation of FFald under the current reaction conditions.

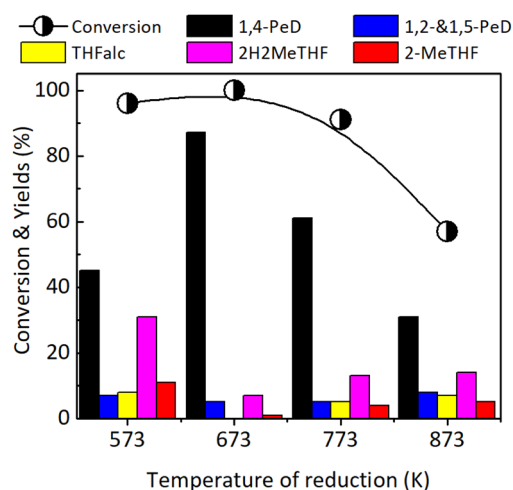


Fig. 5 Conversion of FFald and yields obtained over bulk Ni₃Sn₂ catalysts after reduction with H₂ at 573–873 K for 1.5 h. Reaction conditions are referred to in Fig. 2.

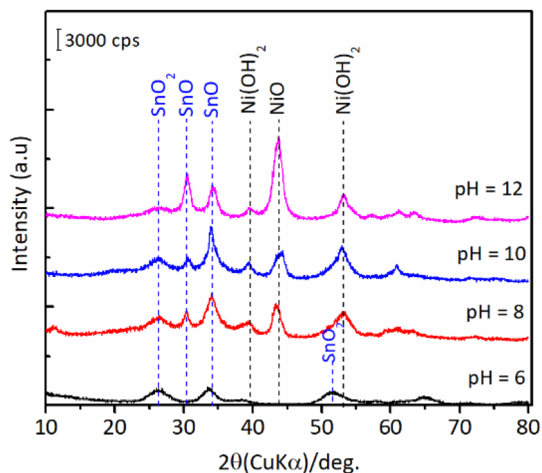


Fig. 6 XRD patterns of the as-prepared bulk Ni_3Sn_2 with different pH of nickel–tin solution (pH = 6–12) obtained after hydrothermal treatment at 423 K for 24 h.

Furthermore, the as-prepared Ni_3Sn_2 samples were reduced with H_2 at 673 K for 1.5 h, and the XRD patterns of bulk Ni_3Sn_2 are shown in Fig. 7.

For Ni_3Sn_2 at a pH adjustment of 4 (Ni_3Sn_2 pH = 4), no diffraction peaks of the Ni_3Sn_2 alloy phase were observed, suggesting that the acidic environment inhibited the formation of metal hydroxides or metal oxides during the hydrothermal processes. A small diffraction peak at $2\theta = 51.2^\circ$ was observed, which can be attributed to the typical diffraction peak of metallic Ni(200)³⁶ (Fig. S6, in the ESI[†]). This is caused by the main product THFalc obtained over the Ni_3Sn_2 pH = 4 catalyst as a result of total hydrogenation of C=C and C=O bonds of FFald. When the pH of Ni–Sn solution of 6 was applied, a series of diffraction peaks of the Ni_3Sn_2 alloy phase was clearly observed following the JCPDS-6-414 (Ni_3Sn_2 standard), and the diffraction peaks of the Ni_3Sn_2 alloy phase intensified as the pH adjustment was increased to 8–12.

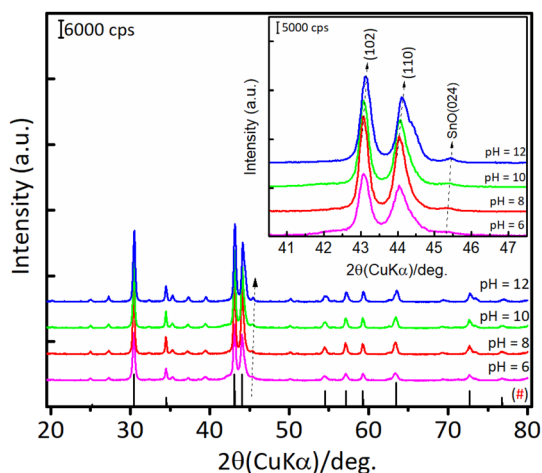


Fig. 7 XRD patterns of the bulk Ni_3Sn_2 after reduction with H_2 at 673 K for 1.5 h obtained with different pH nickel–tin solution (pH = 6–12). (#) The plotted data were compared with JCPDS card of #06-414 (Ni_3Sn_2).

The increase in pH of Ni–Sn solution from 6 to 12 not only enhanced the crystallite sizes of $\text{Ni}_3\text{Sn}_2(101)$ (at $2\theta = 30.6^\circ$) but also caused a slight shifting in the distance of crystal unit (d) as indicated by the shifting of 2θ to the higher degree (inserted figure). By using a Bragg's law equation, it was found that the d (nm) values of bulk Ni_3Sn_2 alloy obtained at pH 6, 8, 10, and 12 were 0.2057 nm, 0.2057 nm, 0.2055 nm, and 0.2054 nm, respectively (Table S3, in ESI[†]). Moreover, a low-intensity peak at $2\theta = 45.44^\circ$ could be assigned to the remaining SnO (JCPDS #13-111). This is slightly intensified as the pH of the Ni–Sn solution was increased. This remaining SnO is consistent with the fact that the SnO in the as-prepared samples may aggregate and transform into another phase during the hydrogen treatment as indicated by the XRD patterns. The systematic studies of the intermetallic microstructure of Ni–Sn reported by Yang *et al.*³⁷ and Marakatti *et al.*³⁸ showed that the defect structure of Ni_3Sn_2 occurred during the preparation or non-stoichiometric alloy composition may strongly affect the geometrical and electronic structure of Ni_3Sn_2 alloy. Then, we took into account the unique and extraordinary catalytic behavior of Ni_3Sn_2 pH = 8 by examining their surface acidity using the ammonia-temperature programmed desorption (NH_3 -TPD), and the profiles are shown in Fig. 8.

The NH_3 -TPD profiles were formally divided into three desorption temperature regions to denote three types of acid sites:^{39–42} (1) weak acid sites, ranging from 373 to 573 K, (2) moderate acid sites, ranging from 573 to 823 K, and (3) strong acid sites, ranging from 823 to 1023 K (Table 2). The total acid sites decreased as the pH adjustment was increased from 8, 10, and 12 (Fig. 8). Bulk Ni_3Sn_2 pH = 8 catalyst has total acid sites of $276 \mu\text{mol g}^{-1}$, while Ni_3Sn_2 pH = 6, Ni_3Sn_2 pH = 10, and Ni_3Sn_2 pH = 12 catalysts had the total acid sites of $133 \mu\text{mol g}^{-1}$, $129 \mu\text{mol g}^{-1}$, and $18 \mu\text{mol g}^{-1}$, respectively (Fig. 8 and Table 2). The portion of strong acid sites, as well as the total acid sites, decreased after the pH adjustment was increased from 6 to 8, 10, and 12. Bulk Ni_3Sn_2 pH = 8 catalyst had $87 \mu\text{mol g}^{-1}$ portion of the strong acid sites and produced the highest yield of 1,4-PeD (87%) from FFald (Fig. 2). Ni_3Sn_2 pH = 10 ($63 \mu\text{mol g}^{-1}$) and Ni_3Sn_2 pH = 6 ($34 \mu\text{mol g}^{-1}$) catalysts produced 72% and 12% 1,4-PeD, respectively (Fig. 8). In contrast, bulk Ni_3Sn_2 pH = 12 ($14 \mu\text{mol g}^{-1}$) catalyst did not produce 1,4-PeD, whereas the main product was FFald without the formation of hydrogenolysed products (*e.g.*, 1,2- or 1,5-PeD) (Fig. 2). These results suggest that the presence of high portion strong acid sites in the bulk Ni_3Sn_2 pH samples may affect its activity and selectivity during the hydration–hydrogenation of FFald to 1,4-PeD. In the literature, it has been reported that the oxidic tin (in the form of Sn^{2+} , $\text{Sn}(\text{OH})$, SnO_x) could be generated during the reaction in the aqueous phase and serve as Brønsted acid.^{30,43–45} The generated Ni^0 – SnO_x species in H_2O or $\text{H}_2\text{O}/\text{ethanol}$ will synergistically act to hydrogenate the C=O of FFald to FFalc on specific Ni^0 and the formed FFalc will be protonated and then subsequently dehydrated by the oxidic tin in H_2O or $\text{H}_2\text{O}/\text{ethanol}$ (in the form of SnO_x) to 2-MeF.^{46,47}

Fig. 9 shows the IR spectra of pyridine adsorbed on bulk Ni_3Sn_2 pH = 8 catalyst. The spectra of the adsorbed species were obtained after the introduction of 1–2 mL pyridine at room temperature, followed by purging with N_2 flow at 323 K and 423

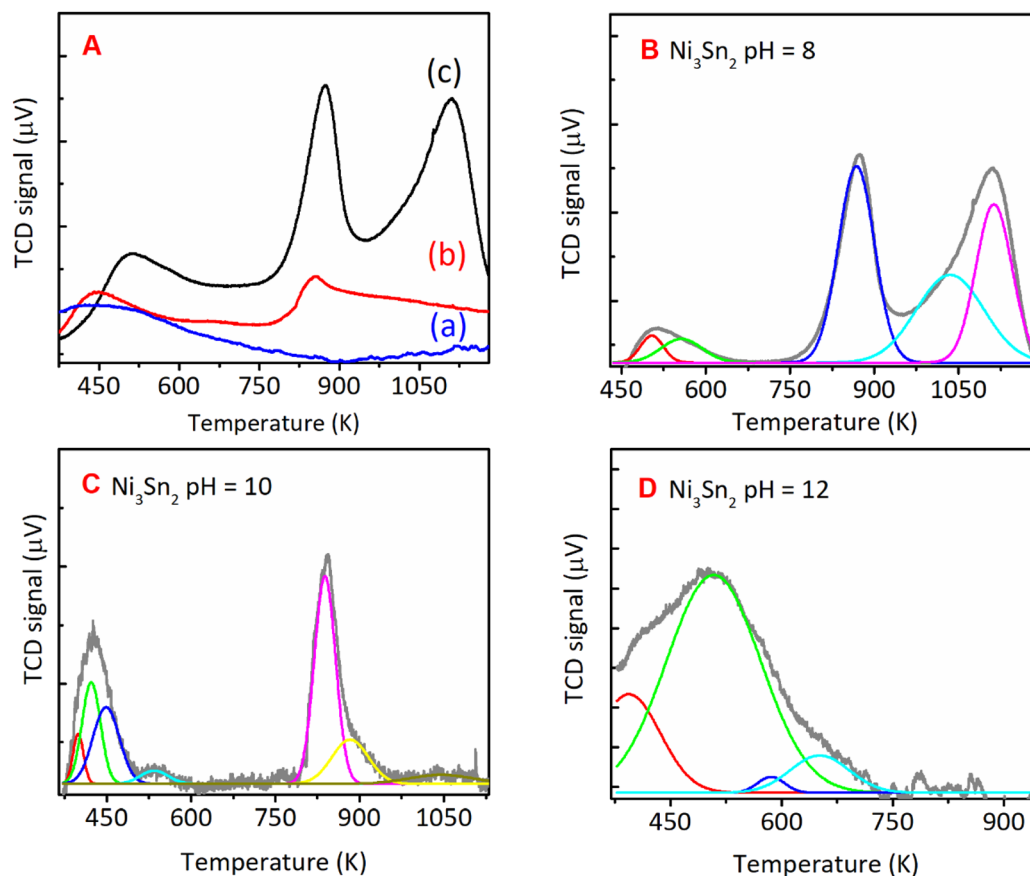


Fig. 8 NH_3 -TPD spectra of (A) the bulk Ni_3Sn_2 with different pH of nickel–tin solution and deconvoluted NH_3 -TPD spectra of bulk Ni_3Sn_2 synthesised with Ni–Sn solution pH of (B) 8, (C) 10, and (D) 12, hydrothermal synthesis at 423 K for 24 h and followed by reduction with H_2 at 673 K for 1.5 h.

Table 2 Physico-chemical properties of the bulk Ni_3Sn_2 alloy catalysts with different pH adjustments after reduction with H_2 at 673 K for 1.5 h

Entry	Catalyst ^a	S_{BET}^b ($\text{m}^2 \text{g}^{-1}$)	H_2 uptake ^c ($\mu\text{mol g}^{-1}$)	D^d (nm)	Amount of acid sites ^e ($\mu\text{mol g}^{-1}$)			Total
					373–623 K (w)	623–823 K (m)	823–1023 K (s)	
1	Ni_3Sn_2 (2-Me-EtOH; pH = 6; 673 K/ H_2)	72.4	10	10	99	0	34	133
2	Ni_3Sn_2 (2-Me-EtOH; pH = 8; 673 K/ H_2)	101.5	9.8	14	90	99	87	276
3	Ni_3Sn_2 (2-Me-EtOH; pH = 10; 673 K/ H_2)	18.6	9.3	15	33	33	63	129
4	Ni_3Sn_2 (2-Me-EtOH; pH = 12; 673 K/ H_2)	12.0	8.6	17	18	0.0	0.0	18

^a The value in the parenthesis is Ni/Sn molar ratio. The composition was determined by using ICP-AES. ^b Determined by N_2 adsorption at 77 K. ^c Based on total H_2 uptake at 273 K (noted after corrections for physical and chemical adsorption). ^d Average crystallite sizes were calculated by using Scherer's equation at $2\theta = 30.37^\circ$ of $\text{Ni}_3\text{Sn}_2(101)$ alloy phase. ^e The amount of acid sites was derived from NH_3 -TPD spectra and the weak (w), moderate (m), and strong (s) acid sites are referred to the temperature regions of NH_3 desorption according to the ref. 42 and 48.

K until the spectra were stable. According to the literature on pyridine adsorption on Sn-containing catalysts,^{49,50} the bands are assigned in the following way. The pyridinium ion (PyH^+) produced by the reaction of pyridine with Brønsted acid sites (B) shows bands around 1633 cm^{-1} (ν_{8a}). Coordinatively bound pyridine on Lewis acid sites (L) shows bands around 1445 (ν_{19b}) and 1575 cm^{-1} . Physisorbed or hydrogen-bonded pyridine (H) shows bands around 1437 and 1599 cm^{-1} . The band around 1490 cm^{-1} is common to vibrations due to PyH^+ (B) and

coordinatively bound pyridine (L).⁵¹ These results indicate that acid sites of bulk Ni_3Sn_2 pH = 8 are both Lewis and Brønsted acidic under the conditions shown in Fig. 8. Additionally, The maximum specific surface area BET (S_{BET}) of the bulk Ni_3Sn_2 alloy was achieved at pH adjustment of 8 ($101.5 \text{ m}^2 \text{g}^{-1}$), followed by pH adjustment of 6 ($72.4 \text{ m}^2 \text{g}^{-1}$), then drastically decreased to $18.6 \text{ m}^2 \text{g}^{-1}$ and $12.0 \text{ m}^2 \text{g}^{-1}$ at the pH adjustment of 10 and 12, respectively (entries 1–4). The average crystallite sizes of $\text{Ni}_3\text{Sn}_2(101)$ increased smoothly, while the H_2 uptake

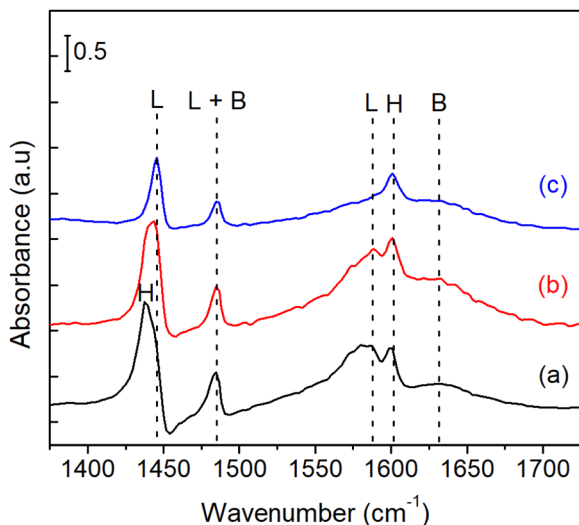


Fig. 9 Pyridine-FTIR profiles of bulk Ni_3Sn pH = 8 after (a) adsorption at room temperature, and degassing at (b) 323 K, and (c) 423 K. L = Lewis acid site; B = Brønsted acid sites; H = physisorption of pyridine.

slightly decreased as the pH adjustment was increased. The total H_2 uptake decreased with the increase of pH from 6 to 12 (from 10 mmol g^{-1} to 9.8 mmol g^{-1} , 9.3 mmol g^{-1} , and 8.6 mmol g^{-1}) and is in good accordance with the increase in the average crystallite sizes of $\text{Ni}_3\text{Sn}_2(101)$ alloys (from 10 nm to 14 nm, 15 nm, and 17 nm), respectively (entries 1–4).

Recyclability and stability tests. The recyclability test of the Ni_3Sn_2 pH = 8 catalyst was performed in the batch reactor system (TAIATSU Techno Japan). The used bulk Ni alloy was easily separated by either simple centrifugation or filtration after the reaction. The recovered catalyst was reactivated by H_2 at 673 K for 1.5 h prior to use in the next reaction run. The yield of 1,4-PeD on the reused catalyst decreased slightly after the second reaction run, but the activity was maintained for at least four consecutive runs (Table 1, entry 8). On the other hand, the stability test was evaluated at a long-term stream under the reaction conditions of flow rate 0.065 mL min^{-1} , H_2 flow rate 70 mL min^{-1} , and 3.29 wt% FFald in $\text{H}_2\text{O}/\text{ethanol}$ solution, and the results are shown in Fig. 10. The activity of bulk Ni_3Sn_2 pH = 8 was maintained at $\sim 100\%$ conversion of FFald with 66% yield of 1,4-PeD even after 52 h reaction on stream. The main side products were THFalc and 2H2MeTHF; THFalc is the result of over hydrogenation of FFald on metallic Ni^0 , while 2H2MeTHF is a stable intermediate of hydrolysis furan ring of FFalc or 2-MeF on SnO_x species. The amounts of metals that leached into the reaction solution were analysed by ICP-AES and were found to be 1.5 mol% (Ni) and 5.0 mol% (Sn) after the fourth run. These results suggested that partial metallic Ni or Sn may leach out into the reaction solution during the reusability test, which can be expected to increase with the number of reaction runs. Moreover, the XRD patterns of the recovered Ni_3Sn_2 pH = 8 alloy before and after H_2 treatment appeared to indicate that no change in the alloy structure occurred (Fig. S6, ESI†).²⁶ Dumescic⁵² and Linic⁵³ have shown that carbon tolerance of Ni-based catalysts could be improved by synthesising Ni-containing

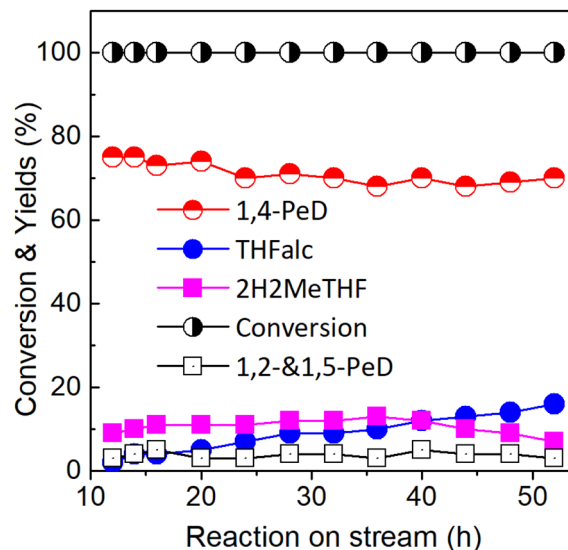


Fig. 10 Conversion of FFald and Yield of 1,4-PeD as a function of reaction on stream over bulk Ni_3Sn_2 (G; pH = 8; 673 K/ H_2) catalyst. Reaction conditions: catalyst, 67 mg; 433 K; flow rate 0.065 mL min^{-1} , H_2 flow rate 70 mL min^{-1} and 3.29 wt% FFald in $\text{H}_2\text{O}/\text{ethanol}$ solution.

surface alloys with the second electropositive metal of tin (Sn). XRD and Mössbauer spectroscopy studies suggested that Sn migrates into the Ni particles to form intermetallic Ni–Sn.⁵⁴

Conclusions

The fabrication of bulk Ni_3Sn_2 alloy catalysts was examined under different conditions (*e.g.*, pH adjustment of the nickel–tin solution, hydrothermal time, hydrothermal temperature, polyol additives, and reduction temperature). Bulk Ni_3Sn_2 that was synthesised at pH = 8, hydrothermal time of 24 h, and reduction temperature of 673 K for 1.5 h (Ni_3Sn_2 pH = 8) catalyst allowed a high yield of 1,4-PeD (87%) in a batch reaction system at 433 K, 3.0 MPa of H_2 , 12 h without the presence of acidic co-catalyst. A 76% yield of 1,4-PeD was also obtained when the reaction was carried out in a fixed-bed reaction system at 433 K, flow rate 0.065 mL min^{-1} , H_2 flow rate 70 mL min^{-1} , and 3.29 wt% FFald in $\text{H}_2\text{O}/\text{ethanol}$ solution for 12 h. The activity of bulk Ni_3Sn_2 was maintained with a 66% yield of 1,4-PeD even after a 52 h reaction on stream. The high yield of 1,4-PeD over this catalyst can be attributed to high specific surface area BET ($S_{\text{BET}} = 101.5 \text{ m}^2 \text{ g}^{-1}$), H_2 uptake, and the portion of strong acid sites (87 mmol g^{-1}). The presence of both hydration active sites (Brønsted acid sites (Ni-SnO_x) in Ni_3Sn_2 alloy) and hydrogenation active sites (Ni^0 or Ni–Sn alloy) could be controlled by changing the pH of the Ni–Sn solution during the preparation. Both the active sites acted synergistically to catalyze the hydration–hydrogenation reactions of FFald to produce a high yield of 1,4-PeD in the batch reaction system. The results of hydration–hydrogenation of FFald to 1,4-PeD over various bulk Ni_3Sn_2 catalysts synthesised at different synthetic parameters confirmed that the pH of Ni–Sn solution, hydrothermal temperature, the temperature of reduction, and the addition of polyols were the important parameters for the fabrication of bulk Ni_3Sn_2 alloy

catalysts. The developed synthetic procedures of Ni₃Sn₂ alloy catalysts are precisely controlled to ensure the production of promising heterogeneous Ni–Sn alloy-based catalysts for the catalytic conversion of biomass-derived-furanic compounds (e.g., FFald, furfuryl alcohol (FFalc), and 2-methylfuran (2-MeF)).

Experimental

Material and chemicals

Nickel(II) chloride hexahydrate (NiCl₂·6H₂O), tin(II) chloride dihydrate (SnCl₂·2H₂O), active carbon ($S_{\text{BET}} = 815 \text{ m}^2 \text{ g}^{-1}$), MgO, and commercial aluminum hydroxide (c-ALOH) were purchased from WAKO Pure Chemical Industries, Ltd. and used as received unless otherwise stated. g-Al₂O₃ ($S_{\text{BET}} = 100 \text{ m}^2 \text{ g}^{-1}$) was purchased from Japan Aerosil Co. Furfural (98%), furfuryl alcohol (97%), 2-methylfuran (98%), and tetrahydrofurfuryl alcohol (99%) were purchased from Tokyo Chemical Industry, Ltd. All organic chemical compounds were purified using standard procedures prior to use.⁵⁵

Catalysis synthesis

Synthesis of bulk Ni₃Sn₂. A typical procedure for the synthesis of the bulk Ni₃Sn₂ alloy catalyst is described as follows:²⁷ NiCl₂·6H₂O (7.2 mmol) was dissolved in deionised water (denoted as solution A), and SnCl₂·2H₂O (4.8 mmol) was dissolved in ethanol/2-methoxy ethanol (2:1) (denoted as solution B) at room temperature. Solutions A and B were mixed at room temperature; the temperature was subsequently raised to 323 K and the mixture was stirred for 12 h. The pH of the mixture was adjusted to 12 by the dropwise addition of an aqueous solution of NaOH (3.1 M). The mixture was then placed in a sealed Teflon autoclave for the hydrothermal reaction at 423 K for 24 h. The resulting black precipitate was filtered, washed with distilled water, and then dried under a vacuum overnight. Prior to the catalytic reaction, the obtained black powder was reduced with H₂ at 673 K for 1.5 h.

Catalyst characterization

XRD measurements were recorded on a Mac Science M18XHF instrument using monochromatic Cu K α radiation ($\lambda = 0.15418 \text{ nm}$). The XRD equipment operated at 40 kV and 200 mA with a step width of 0.02° and a scan speed of 4° min⁻¹ ($\alpha_1 = 0.154057 \text{ nm}$, $\alpha_2 = 0.154433 \text{ nm}$). The mean crystallite size of Ni–Sn was calculated from the full width at half maximum (FWHM) of the Ni₃Sn₂(101) alloy diffraction peak at $2\theta = 30.4^\circ$ according to the Scherrer equation.

Inductively coupled plasma (ICP) measurements were performed on an SPS 1800H plasma spectrometer of Seiko Instruments Inc. (Ni: 221.7162 nm and Sn: 189.898 nm). The Brunauer–Emmett–Teller surface area (S_{BET}) and pore volume (V_{p}) were measured using N₂ physisorption at 77 K on a Belsorp Max (BEL Japan). The samples were degassed at 473 K for 2 h to remove physisorbed gases prior to the measurement. The amount of nitrogen adsorbed onto the samples was used to calculate the BET surface area *via* the BET equation. The pore volume was estimated to be the liquid volume of nitrogen at

a relative pressure of 0.995 according to the Barrett–Joyner–Halenda (BJH) approach based on desorption data.

The H₂ uptake was determined through irreversible H₂ chemisorption. After the catalyst was heated at 393 K under vacuum for 30 min, it was then heated at 673 K under H₂ for 30 min. The catalysts were subsequently cooled to room temperature under vacuum for 30 min. The H₂ measurement was performed at 273 K, and the H₂ uptake was calculated according to a method described in the literature.⁵⁶

The ammonia-temperature programmed desorption (NH₃-TPD) was carried out on a Belsorp Max (BEL Japan). The samples were degassed at an elevated temperature of 373–473 K for 2 h to remove physisorbed gases prior to the measurement. The temperature was then maintained at 473 K for 2 h while flushing with He gas. NH₃ gas (balanced NH₃, 80% and He, 20%) was introduced at 373 K for 30 min, then treated with helium gas to remove the physisorbed also for 30 min. Finally, temperature-programmed desorption was carried out at a temperature of 273–1073 K and the desorbed NH₃ was monitored by TCD.

Catalytic reaction

A typical reaction for the hydration–hydrogenation of FFald was carried out in the following manner.³² The catalyst (44 mg), FFald (1.2 mmol) in ethanol/H₂O 1.5/2.0 v/v (3.5 mL) solvent mixture, dodecane (0.25 mmol) as an internal standard, were placed in an autoclave reactor system of Taiatsu Techno (a Pyrex tube was fitted inside of a sus316 jacket to protect the vessel from corrosion in acidic media). After H₂ was introduced into the reactor (initial pressure of H₂ was 3.0 MPa) at room temperature, the temperature of the reactor was raised to 433 K for 12 h. After 12 h, the conversion of FFald and the yields of 1,4-PeD, FFalc, THFalc, and 2H₂MeTHF, 2-MeTHF, 1,2-PeD, and 1,5-PeD were determined by GC analysis using an internal standard technique. The used bulk Ni₃Sn₂ catalyst was easily separated using either simple centrifugation or filtration, then finally dried overnight under vacuum at room temperature. Prior to the reusability testing, the recovered Ni₃Sn₂ alloy catalyst was re-reduced with H₂ at 673 K for 1 h.

Product analysis

Gas chromatography (GC) analysis of the reactant (FFald) and products (FFalc, THFalc, 1,4-PeD, 1,2-PeD, 1,5-PeD, and 2-MeTHF) was performed on a PerkinElmer Autosystem XL equipped with a flame ionization detector and an Rtx®-BAC PLUS 1 (i.d. 0.32 mm, length of 30 m, and d.f. 1.8 mm) capillary column of RESTEK, US. Gas chromatography-mass spectrometry (GC-MS) was performed on a Shimadzu GC-17B equipped with a thermal conductivity detector and an RT- β DEXsm capillary column. ¹H and ¹³C NMR spectra were obtained on a JNM-AL400 spectrometer at 400 MHz; the samples for NMR analysis were dissolved in chloroform-*d*₁ with TMS as the internal standard. The products were confirmed by a comparison of their GC retention time, mass, ¹H, and ¹³C NMR spectra with those of authentic samples.

The conversion and yield of products were calculated according to the following equations:

$$\text{Conversion} : \frac{\text{initial mol reactant}(F_0) - \text{remained mol reactant}(F_t)}{\text{initial mol reactant}(F_0)} \times 100\% \quad (1)$$

$$\text{Yield} : \frac{\text{mol product}}{\text{consumed mol reactant}(\Delta F)} \times \text{conversion} \quad (2)$$

where F_0 is the introduced mol reactant (FFald), F_t is the remaining mol reactant, and ΔF is the consumed mol reactant (introduced mol reactant – remained mol reactant), which are all obtained from GC analysis using an internal standard technique.

Author contributions

Rodiansono: conceptualization, methodology, investigation, writing-original draft, writing-review and editing. Atina Sabila Azzahra, Pathur Razi Ansyah, Sadang Husain: formal analysis, investigation. Shogo Shimadzu: conceptualization and writing-review and editing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by Hibah Penelitian Dasar Kompetitif Nasional (PDKN) FY 2021-2023 under grant number 026/E5/PG.02.00.PT/2023 from the Ministry of Education, Culture, Research and Technology, Indonesian Government.

Notes and references

- J. Zhu and G. Yin, *ACS Catal.*, 2021, **11**, 10058–10083.
- A. Gandini, D. Coelho, M. Gomes, B. Reis and A. Silvestre, *J. Mater. Chem.*, 2009, **19**, 8656–8664.
- B. M. Stadler, A. Brandt, A. Kux, H. Beck and J. G. de Vries, *ChemSusChem*, 2020, **13**, 556–563.
- D. Sun, S. Sato, W. Ueda, A. Primo, H. Garcia and A. Corma, *Green Chem.*, 2016, **18**, 2579–2597.
- X. Li, P. Jia and T. Wang, *ACS Catal.*, 2016, **6**, 7621–7640.
- K. Huang, Z. J. Brentzel, K. J. Barnett, J. A. Dumesic, G. W. Huber and C. T. Maravelias, *ACS Sustainable Chem. Eng.*, 2017, **5**, 4699–4706.
- D. M. Alonso, S. G. Wettstein and J. A. Dumesic, *Chem. Soc. Rev.*, 2012, **41**, 8075–8098.
- S. Koso, I. Furikado, A. Shima, T. Miyazawa, K. Kunimori and K. Tomishige, *Chem. Commun.*, 2009, 2035–2037.
- S. Koso, N. Ueda, Y. Shinmi, K. Okumura, T. Kizuka and K. Tomishige, *J. Catal.*, 2009, **267**, 89–92.
- Z. Wang, B. Pholjaroen, M. Li, W. Dong, N. Li, A. Wang, X. Wang, Y. Cong and T. Zhang, *J. Energy Chem.*, 2014, **23**, 427–434.
- H. W. Wijaya, T. Kojima, T. Hara, N. Ichikuni and S. Shimazu, *ChemCatChem*, 2017, **9**, 2869–2874.
- H. W. Wijaya, T. Hara, N. Ichikuni and S. Shimazu, *Chem. Lett.*, 2018, **47**, 103–106.
- E. Soghrati, C. Kok Poh, Y. Du, F. Gao, S. Kawi and A. Borgna, *ChemCatChem*, 2018, **10**, 4652–4664.
- H. W. Wijaya, T. Sato, H. Tange, T. Hara, N. Ichikuni and S. Shimazu, *Chem. Lett.*, 2017, **46**, 744–746.
- W. Xu, H. Wang, X. Liu, J. Ren, Y. Wang and G. Lu, *Chem. Commun.*, 2011, **47**, 3924–3926.
- Z. J. Brentzel, K. J. Barnett, K. Huang, C. T. Maravelias, J. A. Dumesic and G. W. Huber, *ChemSusChem*, 2017, **10**, 1351–1355.
- K. J. Barnett, D. J. McClelland and G. W. Huber, *ACS Sustainable Chem. Eng.*, 2017, **5**, 10223–10230.
- H. Mehdi, V. Fábos, R. Tuba, A. Bodor, L. T. Mika and I. T. Horváth, *Top. Catal.*, 2008, **48**, 49–54.
- G. J. Leuck, Evanston, J. Pokorny and F. N. Peters Jr, *US Pat*, 2097493, 1937.
- L. E. Schniepp, H. H. Geller and R. W. von Korff, *J. Am. Chem. Soc.*, 1947, **69**, 672–674.
- S. Liu, Y. Amada, M. Tamura, Y. Nakagawa and K. Tomishige, *Green Chem.*, 2014, **16**, 617.
- S. Liu, Y. Amada, M. Tamura, Y. Nakagawa and K. Tomishige, *Catal. Sci. Technol.*, 2014, **4**, 2535–2549.
- F. Liu, Q. Liu, J. Xu, L. Li, Y. T. Cui, R. Lang, L. Li, Y. Su, S. Miao, H. Sun, B. Qiao, A. Wang, F. Jérôme and T. Zhang, *Green Chem.*, 2018, **20**, 1770–1776.
- Q. Liu, B. Qiao, F. Liu, L. Zhang, Y. Su, A. Wang and T. Zhang, *Green Chem.*, 2020, **22**, 3532–3538.
- K. Cui, W. Qian, Z. Shao, X. Zhao, H. Gong, X. Wei, J. Wang, M. Chen, X. Cao and Z. Hou, *Catal. Lett.*, 2021, **151**, 2513–2526.
- R. Rodiansono, M. Dewi Astuti, T. Hara, N. Ichikuni and S. Shimazu, *Green Chem.*, 2019, **21**, 2307–2315.
- R. Rodiansono, S. Khairi, T. Hara, N. Ichikuni and S. Shimazu, *Catal. Sci. Technol.*, 2012, **2**, 2139–2145.
- R. Rodiansono, M. D. Astuti, A. Ghofur and K. C. Sembiring, *Bull. Chem. React. Eng. Catal.*, 2015, **10**, 192–200.
- R. Rodiansono, M. D. Astuti, K. Mustikasari, S. Husain and S. Sutomo, *Catal. Sci. Technol.*, 2020, **10**, 7768–7778.
- L. Wang, J. Zhang, X. Wang, B. Zhang, W. Ji, X. Meng, J. Li, D. S. Su, X. Bao and F. S. Xiao, *J. Mater. Chem. A*, 2014, **2**, 3725–3729.
- M. K. Stones, E. M. J. Banz Chung, I. T. Da Cunha, R. J. Sullivan, P. Soltanipanah, M. Magee, G. J. Umphrey, C. M. Moore, A. D. Sutton and M. Schlaf, *ACS Catal.*, 2020, **10**, 2667–2683.

- 32 R. Rodiansono, M. D. Astuti, K. Mustikasari, S. Husain, F. R. Ansyah, T. Hara and S. Shimazu, *RSC Adv.*, 2022, **12**, 241–250.
- 33 R. Rodiansono, A. S. Azzahra, S. Husain and P. R. Ansyah, *Bull. Chem. React. Eng. Catal.*, 2022, **17**, 743–754.
- 34 R. E. Cable and R. E. Schaak, *Chem. Mater.*, 2005, **17**, 6835–6841.
- 35 B. Beverskog and I. Puigdomenech, *Corros. Sci.*, 1997, **39**, 969–980.
- 36 JCPDS-ICDD, Powder diffraction files, JCPDS-International center for diffraction data (JCPDS-ICDD), 1991.
- 37 Y. Yang, L. Chen, Y. Chen, W. Liu, H. Feng, B. Wang, X. Zhang and M. Wei, *Green Chem.*, 2019, **21**, 5352–5362.
- 38 V. S. Marakatti, N. Arora, S. Rai, S. C. Sarma and S. C. Peter, *ACS Sustainable Chem. Eng.*, 2018, **6**, 7325–7338.
- 39 E. Dumitriu and V. Hulea, *J. Catal.*, 2003, **218**, 249–257.
- 40 J. Wang, P. A. Chernavskii, Y. Wang and A. Y. Khodakov, *Fuel*, 2013, **103**, 1111–1122.
- 41 F. Arena, R. Dario and A. Parmaliana, *Appl. Catal., A*, 1998, **170**, 127–137.
- 42 N. Khandan, M. Kazemeini and M. Aghaziarati, *Appl. Catal., A*, 2008, **349**, 6–12.
- 43 L. Ma, H. Wang, C. Zhu, Q. Liu, J. Tan, C. Wang and Z. Liang, *ChemSusChem*, 2019, **12**, 2154–2160.
- 44 X. Liu, X. Liu, G. Xu, Y. Zhang, C. Wang, Q. Lu and L. Ma, *Green Chem.*, 2019, **21**, 5647–5656.
- 45 S. Xu, D. Yu, T. Ye and P. Tian, *RSC Adv.*, 2017, **7**, 1026–1031.
- 46 N. S. Date, A. M. Hengne, K. W. Huang, R. C. Chikate and C. v. Rode, *Green Chem.*, 2018, **20**, 2027–2037.
- 47 S. Iqbal, X. Liu, O. F. Aldosari, P. J. Miedziak, J. K. Edwards, G. L. Brett, A. Akram, G. M. King, T. E. Davies, D. J. Morgan, D. K. Knight and G. J. Hutchings, *Catal. Sci. Technol.*, 2014, **4**, 2280–2286.
- 48 E. Dumitriu and V. Hulea, *J. Catal.*, 2003, **218**, 249–257.
- 49 E. Tututi-Ríos, H. González, D. A. Cabrera-Munguia, A. Gutiérrez-Alejandre and J. L. Rico, *Catal. Today*, 2022, **394–396**, 235–246.
- 50 A. Rezayan, K. Wang, R. Nie, T. Lu, J. Wang, Y. Zhang and C. Charles Xu, *Chem. Eng. J.*, 2022, **429**, 132261.
- 51 M. Tamura, K. I. Shimizu and A. Satsuma, *Appl. Catal., A*, 2012, **433–434**, 135–145.
- 52 J. W. Shabaker, G. W. Huber and J. A. Dumesic, *J. Catal.*, 2004, **222**, 180–191.
- 53 E. Nikolla, J. Schwank and S. Linic, *J. Catal.*, 2007, **250**, 85–93.
- 54 T. B. L. W. Marinelli and V. Ponc, *J. Catal.*, 1995, **156**, 51–59.
- 55 W. L. F. Armarego and C. L. L. Chai, *Purification of Laboratory Chemicals*, Elsevier/BH, 6th edn, 2009.
- 56 C. H. Bartholomew and R. B. Pannell, *J. Catal.*, 1980, **65**, 390–401.