


 Cite this: *RSC Adv.*, 2020, 10, 25988

Uncovering the origin of enhanced field emission properties of rGO–MnO₂ heterostructures: a synergistic experimental and computational investigation†

 Sachin R. Rondiya,^a Indrapal Karbhal,^b Chandradip D. Jadhav,^c Mamta P. Nasane,^d Thomas E. Davies,^a Manjusha V. Shelke,^b Sandesh R. Jadhkar,^d Padmakar G. Chavan^e and Nelson Y. Dzade^{*a}

The unique structural merits of heterostructured nanomaterials including the electronic interaction, interfacial bonding and synergistic effects make them attractive for fabricating highly efficient optoelectronic devices. Herein, we report the synthesis of MnO₂ nanorods and a rGO/MnO₂ nano-heterostructure using low-cost hydrothermal and modified Hummers' methods, respectively. Detailed characterization and confirmation of the structural and morphological properties are done via X-ray Diffraction (XRD), Field Emission Scanning Electron Microscopy (FESEM) and Transmission Electron Microscopy (TEM). Compared to the isolated MnO₂ nanorods, the rGO/MnO₂ nano-heterostructure exhibits impressive field emission (FE) performance in terms of the low turn-on field of 1.4 V μm⁻¹ for an emission current density of 10 μA cm⁻² and a high current density of 600 μA cm⁻² at a relatively very low applied electric field of 3.1 V μm⁻¹. The isolated MnO₂ nanorods display a high turn-on field of 7.1 for an emission current density of 10 μA cm⁻² and a low current density of 221 μA cm⁻² at an applied field of 8.1 V μm⁻¹. Besides the superior FE characteristics of the rGO/MnO₂ nano-heterostructure, the emission current remains quite stable over the continuous 2 h period of measurement. The improvement of the FE characteristics of the rGO/MnO₂ nano-heterostructure can be ascribed to the nanometric features and the lower work function (6.01 and 6.12 eV for the rGO with 8% and 16% oxygen content) compared to the isolated α-MnO₂(100) surface ($\Phi = 7.22$ eV) as predicted from complementary first-principles electronic structure calculations based on density functional theory (DFT) methods. These results suggest that an appropriate coupling of rGO with MnO₂ nanorods would have a synergistic effect of lowering the electronic work function, resulting in a beneficial tuning of the FE characteristics.

 Received 15th April 2020
 Accepted 15th June 2020

DOI: 10.1039/d0ra03360j

rsc.li/rsc-advances

1. Introduction

Nanoscale heterostructure design comprising different material compositions is emerging as an attractive strategy and essential building block for functional devices to achieve improved performance. The desired physicochemical properties of the

participating nanomaterials in nanostructured hybrids/composites complement each other by tuning their electronic properties to meet the requirements for the fabrication of efficient electronic devices.¹ Reduced Graphene Oxide (rGO) is an attractive and ideal nanomaterial to be paired with another suitable semiconductor for the development of multifunctional heterostructures because of its unique electronic properties, high electrical conductivity (5×10^{-3} S cm⁻¹), flexible structure, high aspect ratio, and high specific surface area (2630 m² g⁻¹).^{2–5} Owing to its unique physicochemical properties, rGO is being recognized as a material of great interest for potential applications in nanoelectronics,⁶ nanoelectromechanical systems,⁷ sensors,⁸ catalysis,⁹ energy storage devices,^{10,11} optics,¹² and field emission (FE).^{13–15} There exist several reports of the successful synthesis of rGO or modified graphene heterostructures with various semiconducting nanomaterials such as TiO₂, SnO₂, ZnO, Si, CdSe, *etc.* in the literature.^{16–18}

^aSchool of Chemistry, Cardiff University, Main Building, Park Place, Cardiff, CF10 3AT, Wales, UK. E-mail: RondiyaS@cardiff.ac.uk; DzadeNY@cardiff.ac.uk

^bPhysical and Materials Chemistry Division, CSIR-National Chemical Laboratory, Pune 411008, MH, India

^cThe State Key Laboratory of Refractories and Metallurgy, Institute of Advanced Materials and Nanotechnology, College of Materials and Metallurgy, Wuhan University of Science and Technology, Wuhan 430081, P. R. China

^dDepartment of Physics, Savitribai Phule Pune University, Pune 411007, India

^eDepartment of Physics, School of Physical Sciences, Kavayitri Bahinabai Chaudhari North Maharashtra University, Jalgaon 425001, India

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ra03360j



For field emission applications, where electrons are extracted from the surface of a metal/semiconductor by an electrostatic field through quantum mechanical tunneling, rGO-based nanocomposites such as rGO-Bi₂S₃¹⁹ and WS₂-RGO,²⁰ have demonstrated superior field emission properties. Among transition metal oxides, manganese dioxide (MnO₂) has attracted increasing interest for field emission applications, owing to their wide structural diversity combined with unique chemical and physical properties.^{21,22} The advantages of MnO₂ as field emitter are the lower cost for raw materials and the fact that manganese is more environmentally friendly than other metal oxide.^{23,24} MnO₂ has also attracted a lot of attention as an electrochemical pseudocapacitor material due to its high theoretical capacitance (1370 F g⁻¹).²⁵⁻²⁷ Wu *et al.* reported inspiring results such as low turn-on field value of 8.4 V μm⁻¹ at current density of 1 μA cm⁻² and maximum emission current density of 160 μA cm⁻² at an applied field 18 V μm⁻¹.²¹ The field emission applications of MnO₂ is, however, limited by its low specific surface area and poor electrical conductivity (10⁻⁵ to 10⁻⁶ S cm⁻¹). Compared to its flat films, by fabricating rGO/MnO₂ nanocomposite the interface area can be significantly enlarged, which is desirable for field emission application.²⁸ Besides, rGO is solution-processable and thus can be deposited in large areas onto different kinds of substrates enabling simple and cost-effective fabrication of field electron emitters for display applications. The formation of rGO-MnO₂ nanostructures and their electrochemical performance have been extensively investigated and it was demonstrated that compared to the single metal-oxide, rGO/MnO₂ nanocomposites show superior electric conductivity, electric capacity and charge/discharge efficiency for supercapacitor performance.²⁹⁻³⁴ These characteristics make rGO/metal-oxide nanocomposites promising materials for energy applications. Considering that field emission is geometry (shape, size, aspect ratio, alignment, and


areal density of the nanostructure) and work function dependent phenomenon, well-aligned rGO/MnO₂ nanostructures is promising for enhancement of field emission characteristics.³⁵

Herein, we report a simple and cost-effective solution-based method to prepared MnO₂ nanorods and rGO/MnO₂ nano-heterostructure. The structural and morphological verifications have been done by using X-ray diffraction (XRD), Field Emission Scanning Electron Microscope (FESEM), and Transmission Electron Microscopy (TEM). Finally, the field emission properties of the as-prepared MnO₂ nanorods and rGO/MnO₂ nano-heterostructure was systematically characterized and compared. The rGO/MnO₂ nano-heterostructure exhibits superior field emission characteristics compared to the MnO₂ nanorod. The rGO/MnO₂ nano-heterostructure demonstrates a low turn-on field of 1.4 V μm⁻¹ for an emission current density of 10 μA cm⁻² compared to 7.1 V μm⁻¹ for MnO₂ nanorod. The combined contribution of the sharp edges of the thin rGO sheets and high aspect ratio of the MnO₂ nanorods, coupled with synergetic effect in the rGO/MnO₂ nano-heterostructure are responsible for the observed enhanced field emission behavior. Consistent with the experimental data, our complementary first-principles DFT calculations predict lower work function for the rGO/MnO₂ nano-heterostructure compared to the isolated MnO₂ as the primary origin for improved field emission.

2. Experimental, characterization, and computational methods

2.1 Synthesis of MnO₂ and rGO/MnO₂

The rGO has been synthesized by modified Hummer's method³⁶ whereas the MnO₂ nanorods has been synthesized by the hydrothermal method.³⁷ For the preparation of the rGO/MnO₂ composite, 1 mg ml⁻¹ rGO was dispersed in the 100 ml of DI

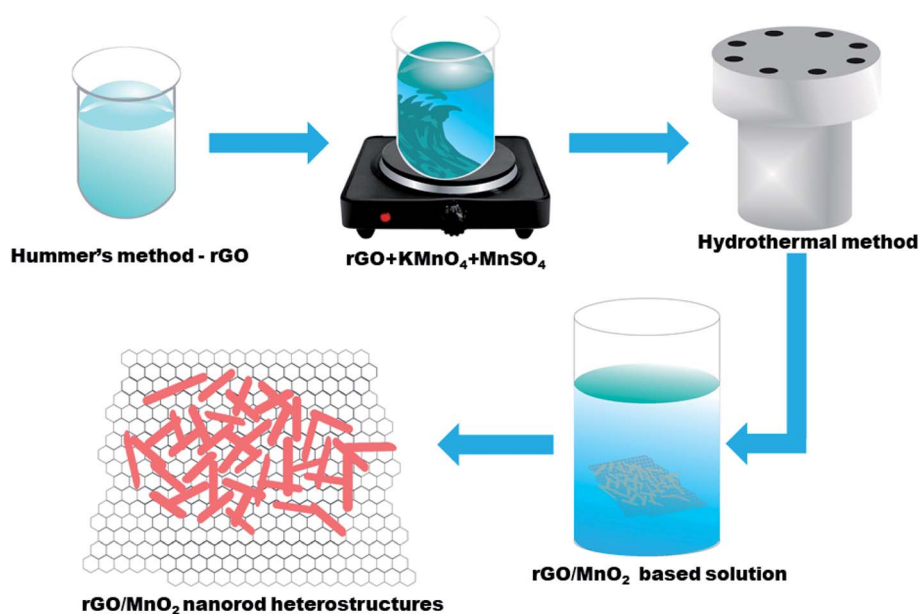

Scheme 1 The facile synthesis of MnO₂ nanorods and rGO/MnO₂ heterostructure.

water in a beaker. Later, 10 mM of KMnO_4 and 10 mM of MnSO_4 were added into the rGO solution and stirred for 30 min form a homogenous solution. The prepared solution was transferred into a stainless steel autoclave and kept at 160 °C for 24 h. After cooling to room temperature, the material was filter washed with DI water and ethanol to obtain rGO/ MnO_2 composite, which was dried in an oven at 80 °C for 12 hours and used for various characterizations presented next. Scheme 1 represents the synthesis steps which were followed for synthesis of rGO, MnO_2 and rGO/ MnO_2 heterostructure.

2.2 Materials characterization

The MnO_2 nanorods and rGO/ MnO_2 nano-heterostructure were characterized by various complementary experimental methods. The XRD patterns were obtained with a Bruker D8 Advance X-ray diffractometer using the Cu K α line ($\lambda = 1.54 \text{ \AA}$) at 1° grazing angle. The HR-TEM micrographs and selected area electron diffraction (SAED) patterns were obtained with JEOL-JEM 2100 microscope operating at 200 kV. The samples were dry dispersed over 300 mesh copper grids coated with holey carbon film. A Field Emission Scanning Electron Microscope (FEG-SEM Model – Tescan MAIA3) was used to examine the morphology and surface topography of the MnO_2 nanorods and rGOs/ MnO_2 composite. The accelerating voltage was 15 kV. X-ray spectroscopy (EDS) measurements were done using Oxford Instruments X-Max^N 80 detector and analyzed using Aztec software. X-ray Photoelectron Spectroscopy (XPS) was carried on the samples using a Kratos Axis Ultra DLD photoelectron spectrometer utilizing monochromatic AlK α radiation operating at an energy of 120 W (10 × 12 kV). Data were analyzed using Casa XPS and modified Wagner sensitivity factors as supplied by the instrument manufacturer after subtraction of a Shirley background. All spectra were calibrated to the C(1s) line taken to be 284.8 eV.

2.3 Field emission

The field emission studies of the MnO_2 nanorods and rGO/ MnO_2 heterostructure were carried out in the Ultra-High Vacuum (UHV) chamber at a base pressure of $\sim 1 \times 10^{-8}$ mbar (Excel Instruments model: I-100). Detail experimental procedure may found in our earlier paper.³⁸ The configuration of the field emission experiment steps up is shown in ESI (scheme S1).† The distance between inter-electrode was maintained at 1 mm. The area of both specimens (MnO_2 nanorods and rGOs/ MnO_2 heterostructure) was 0.25 cm².

2.4 Computational methods

The first-principles spin polarized density functional theory (DFT) calculations were performed using the Vienna *Ab initio* Simulation Package (VASP),^{39–41} a periodic plane wave DFT code which includes the interactions between the core and valence electrons using the Project Augmented Wave (PAW) method.⁴² An energy cut-off of 600 eV, and Monkhorst–Pack⁴³ *k*-point mesh of $7 \times 7 \times 3$ was used to sample the Brillouin zone of bulk α - MnO_2 . Geometry optimizations were performed based on the conjugate-gradient algorithm until the residual

Hellmann–Feynman forces on all relaxed atoms reached $10^{-3} \text{ eV \AA}^{-1}$. The electronic exchange–correlation potential was calculated using the Perdew–Burke–Ernzerhof (PBE) generalized gradient approximation (GGA) functional.⁴⁴ To accurately reproduce the experimentally known band gaps and density of states features of α - MnO_2 and rGO, the screened hybrid functional HSE06⁴⁵ was used with the exchange value of 25%. The projected density of states (PDOS) was calculated using tetrahedron method with Bloch correction.⁴⁶

The most stable α - MnO_2 (100) surface⁴⁷ was employed to form the nano-heterostructure with rGO (rGO/ α - MnO_2). The α - MnO_2 (100) surface was created from the optimized bulk material using the METADISE code, which ensures the creation of surfaces with zero dipole moment perpendicular to the surface plane. The rGO/ α - MnO_2 nano-heterostructure was constructed with (2×4) - α - MnO_2 (100) and (5×5) -rGO supercells. We used *k*-point meshes of $9 \times 9 \times 1$ for the rGO monolayer, $5 \times 5 \times 1$ for the α - MnO_2 (100) surface, and $5 \times 5 \times 1$ for the rGO/ α - MnO_2 composite. In each simulation cell, a vacuum region of length 20 Å was added perpendicular to the surface to avoid interactions between periodic slabs. The electrostatic potential of each surface was averaged along the *c*-direction, using the Macro Density package.^{48–50} The work function (Φ) was calculated as $\Phi = V_{\text{vacuum}} - E_{\text{F}}$, where V_{vacuum} and E_{F} are the vacuum and Fermi level, respectively. Dipole correction perpendicular to all surfaces was accounted for, which ensured that there is no net dipole perpendicular to the surfaces that may affect the potential in the vacuum level.^{51–53}

3. Results and discussions

3.1 Characterization of MnO_2 and rGO/ MnO_2

The crystalline structures of the MnO_2 nanorods and rGO/ MnO_2 nano-heterostructure were confirmed by XRD and the corresponding results are presented in Fig. S1.† All the diffraction peaks in Fig. S1† can be indexed to the tetragonal crystal structure of MnO_2 (ICDD card no. 72-1982) with lattice constant $a = b = 9.815 \text{ \AA}$ and $c = 2.847 \text{ \AA}$. We have observed the highest growth of α - MnO_2 in the (211) plane.⁵⁴ The XRD diffraction pattern of the rGO- MnO_2 nanostructure is shown in inset of Fig. S1.† The broad peak at 2θ around 26° corresponds to the (002) plane of the reduced graphene oxide.⁵⁵ The field emission scanning electron microscope (FESEM) images in Fig. 1, reveal the morphological properties of the MnO_2 nanorods and rGO/ MnO_2 nano-heterostructure. The FESEM images recorded at different magnifications (panels a–c of Fig. 1) show the formation of randomly distributed MnO_2 nanorods. The low magnification image shown in Fig. 1a depicts large coverage of the MnO_2 nanorods. The diameter of the formed ultra-long nanorods is estimated in the range of 140–150 nm as revealed by the high magnification FESEM images analyses (Fig. 1b and c). It is evident from the FESEM image of the rGO/ MnO_2 nano-heterostructure that the MnO_2 nanorods are embedded in the rGO network (Fig. 1b–d). The high magnification image in Fig. 1f reveals the enormous coverage of the rGO/ MnO_2 nano-heterostructure.

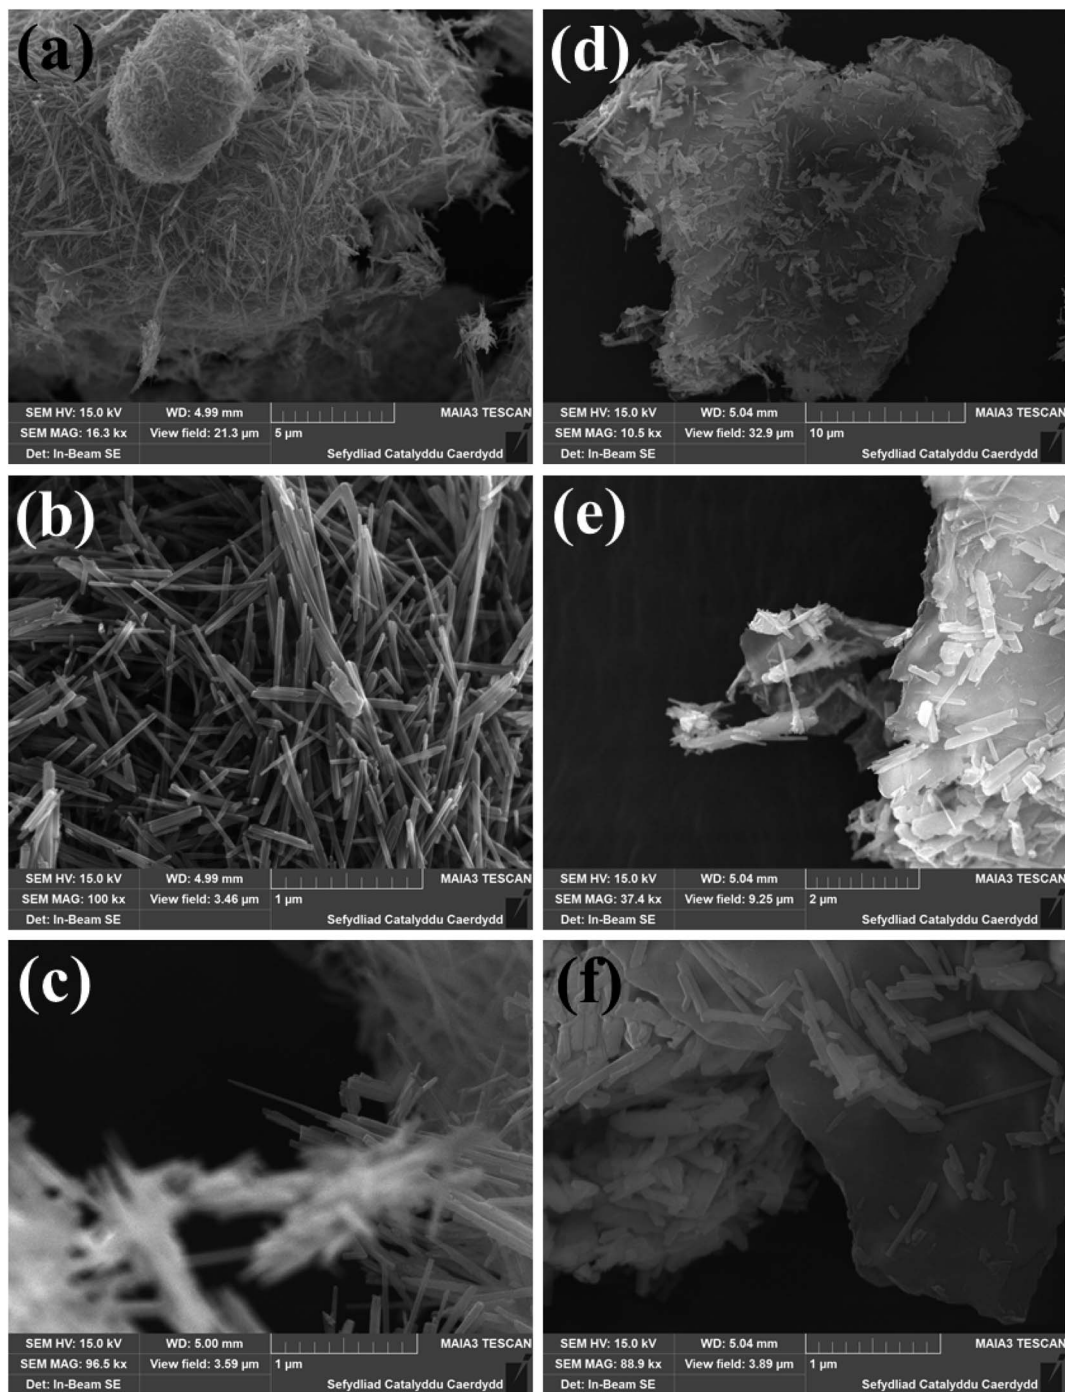


Fig. 1 FESEM images of MnO₂ nanorods (a–c) and rGO–MnO₂ heterostructures (d–f) recorded at different magnification.

Energy dispersive X-ray spectroscopy (EDX) composition analysis in the 0–10 keV energy range (ESI, Fig. S2[†]) confirmed that the MnO₂ nanorods and rGO/MnO₂ nano-heterostructure have the optimal stoichiometric atomic Mn : O and Mn : O : C ratios, respectively. Moreover, the FESEM-EDS elemental mapping (ESI, Fig. S2[†]) confirms an even distribution of the chemical constituents (Mn, O, and C). For detail structural analysis of the as-synthesized MnO₂ nanorods and rGO/MnO₂ nano-heterostructure, TEM studies were carried out. The TEM

micrograph (Fig. 2a) reveals the morphology of the MnO₂ nanorods, with sizes ranging between 50 and 70 nm in width and the average length of 1 μm. The selected area electron diffraction (SAED) pattern, depicted in Fig. 2b, confirms the polycrystalline nature of the MnO₂ nanorods. The lattice-resolved high-resolution transmission electron microscopy (HRTEM) image of the MnO₂ nanorod (Fig. 2c) clearly reveals its crystalline nature. The lattice fringes are clearly observed in the HR-TEM image (Fig. 2c and d) and a 0.69 nm interplanar

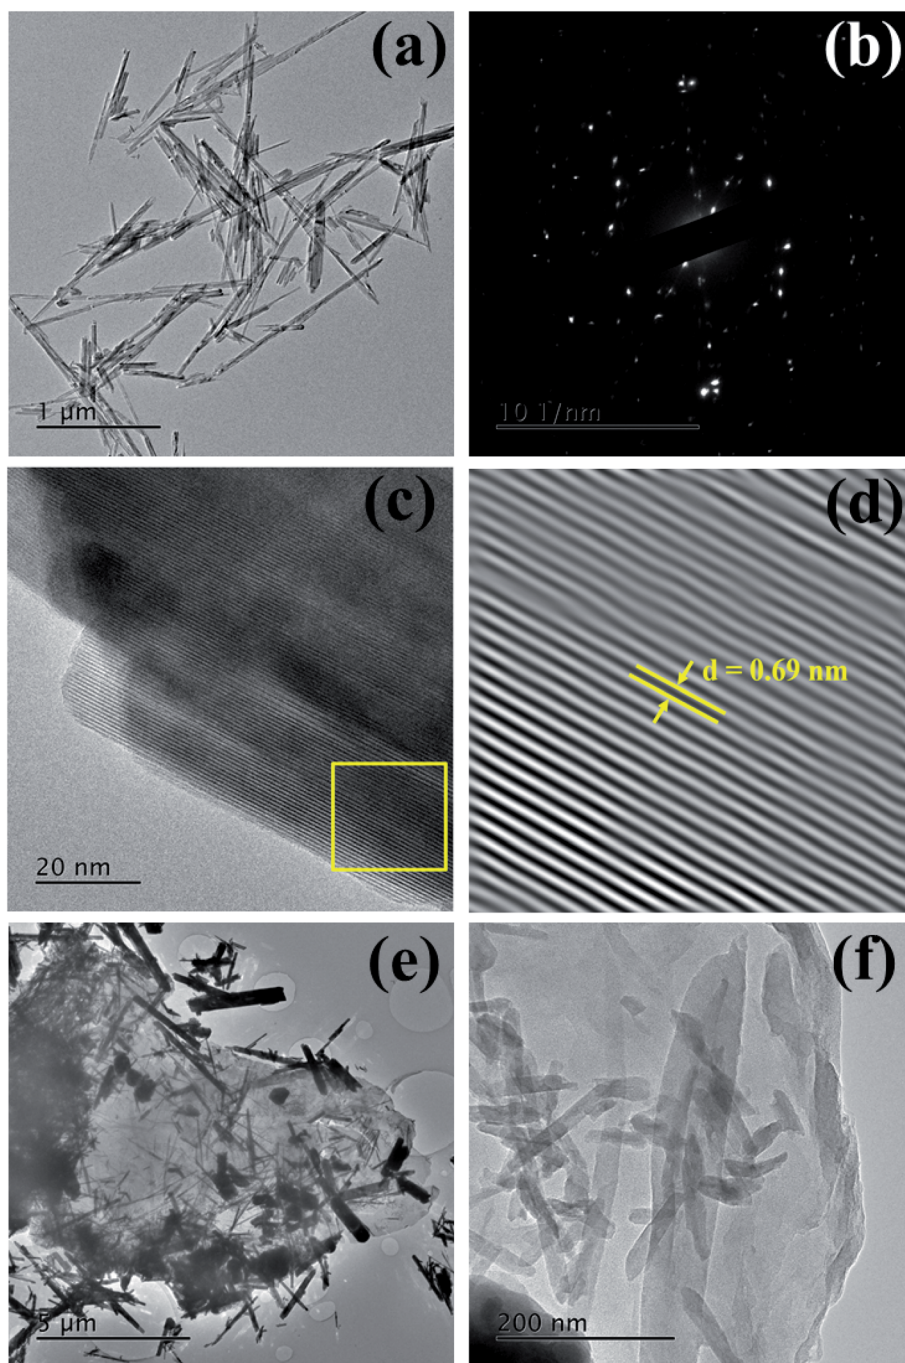


Fig. 2 (a) TEM images of MnO₂ nanorods (b) selected area electron diffraction (SAED) pattern of MnO₂ nanorods (c) HR-TEM image of MnO₂ nanorods with clear lattice resolution (d) Inverse Fourier transform of area shown in (c) with interplanar spacing of MnO₂ (e and f) TEM images of rGO-MnO₂ heterostructures.

distance indicates these planes to be of the (110) character.⁵⁶ The inverse FFT HR-TEM image and the corresponding profile plot of the MnO₂ nanorod are shown in Fig. S3(a and b).[†] A number of firmly attached α -MnO₂ nanorods onto the rGO sheets can be clearly seen from Fig. 2e and f. X-ray photoelectron spectroscopy (XPS) analysis was applied to determine the oxidation state and elemental composition of the prepared MnO₂ nanorods and rGO/MnO₂ nano-heterostructure. The XPS

results for the MnO₂ nanorods are shown in Fig. S4(a and b)[†] and the rGO/MnO₂ nano-heterostructure in Fig. S4(c–e).[†] The peaks centered at 642.63 and 654.53 eV in the high-resolution spectrum of Mn 2p (Fig. S4a[†]) can be assigned to the Mn 2p_{3/2} and Mn 2p_{1/2} peaks, respectively, confirming the presence of MnO₂.^{57–60} The deconvolution peaks of the O 1s spectrum (Fig. S4b[†]) can be divided into three peaks which correspond to O–Mn bonding. The high-resolution spectrum of Mn 2p and O

1s shown in Fig. S4c and S4d,[†] respectively, for rGO/MnO₂ nano-heterostructure, confirm the presence of MnO₂, whereas the C (1s) spectra (Fig. S4e[†]) exhibit peaks that originates from the rGO sheets.

3.2 Field emission investigations

Fig. 3(a and b) shows the emission current density as a function of the applied electrical field (J - E curves) for the MnO₂ nanorods and rGO/MnO₂ nano-heterostructure. In this work, the turn-on field defined as the field required to draw an emission current density (J) of 10 $\mu\text{A cm}^{-2}$ is found to be 7.1 and 1.4 $\text{V } \mu\text{m}^{-1}$ for

the MnO₂ nanorods and the rGO/MnO₂ nano-heterostructure, respectively. The rGO/MnO₂ nano-heterostructure also attains an impressive current density of 600 $\mu\text{A cm}^{-2}$ at an applied field of 3.1 $\text{V } \mu\text{m}^{-1}$ compared to the isolated MnO₂ which displayed a lower current density of 221 $\mu\text{A cm}^{-2}$ at a relatively higher applied field of 8.1 $\text{V } \mu\text{m}^{-1}$. A comparison between the turn-on field values obtained in the present study and previously reported MnO₂ nanostructures and the MnO₂/rGO nano-heterostructures is provided in Table 1.^{21,22,61-66}

The Fowler–Nordheim (F–N) plot for MnO₂ nanorods and rGO/MnO₂ nano-heterostructure obtained from $\ln(J/E^2)$ verses

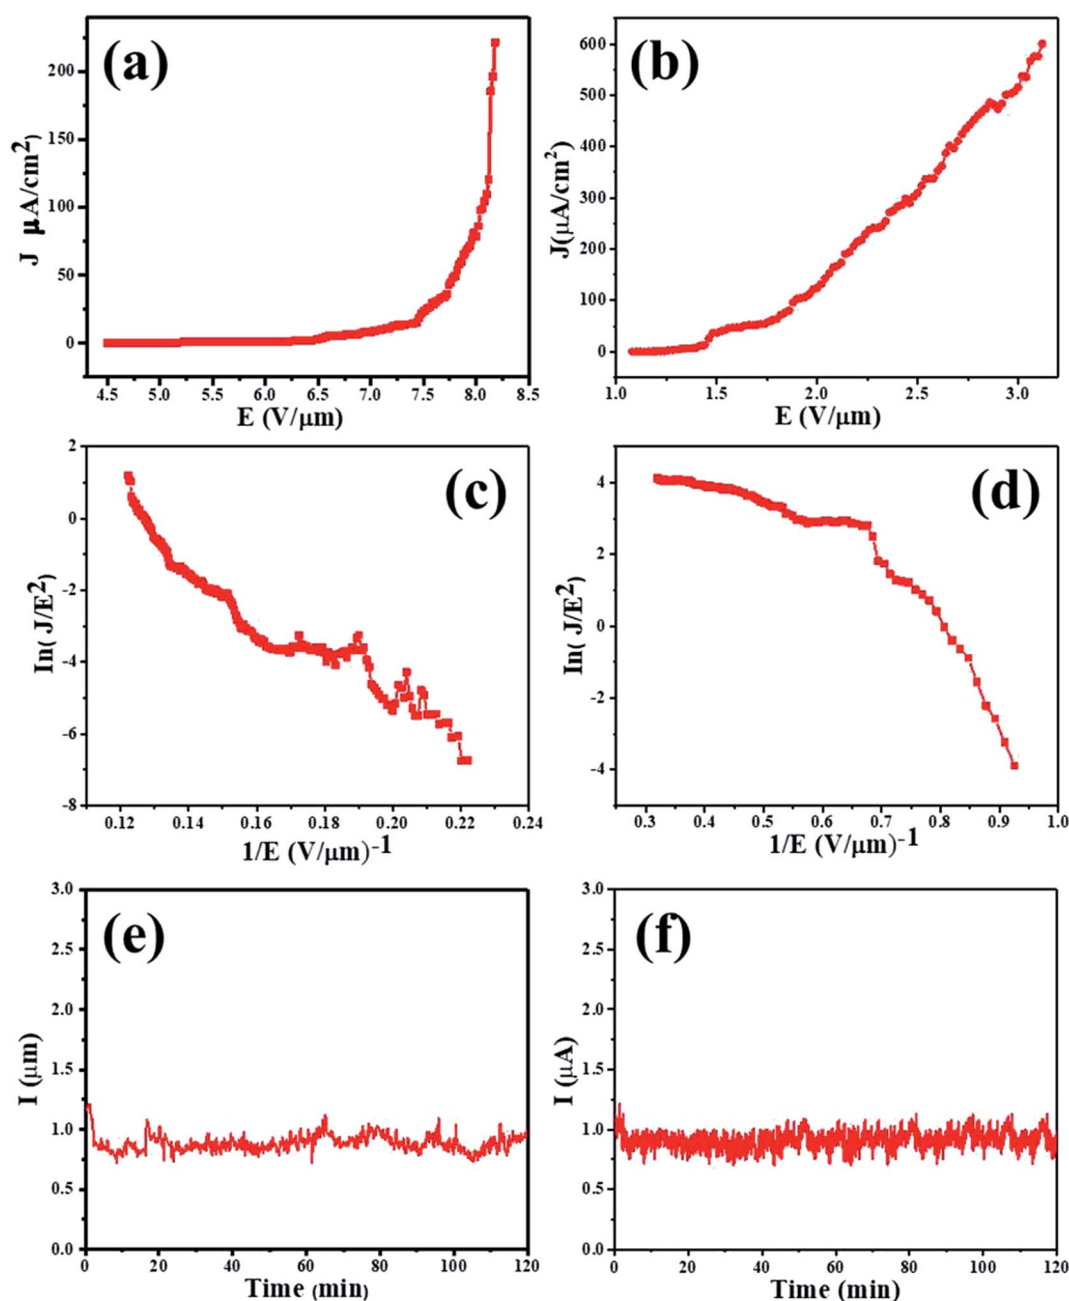


Fig. 3 FE characteristics of the MnO₂ nanorods and rGO–MnO₂ heterostructures: (a and b) emission current density versus applied electric field (J - E) curve, (c and d) F–N plot, and (e and f) emission current versus time (I - t) plot.

Table 1 Comparison of the turn-on field with reported MnO₂ nanomaterials and the MnO₂/rGO nano-heterostructures in the present study

Sr. no.	Specimen	Turn-on field (V μm^{-1}) (for $J = 10 \mu\text{A cm}^{-2}$)	Reference
1	MnO ₂ nanotubes	8.4 (1 $\mu\text{A cm}^{-2}$)	21
2	MnO ₂ nanorods	5.90 (1 $\mu\text{A cm}^{-2}$)	22
3	MnO ₂ /rGO nanocomposite	3.6 (1 $\mu\text{A cm}^{-2}$)	
4	rGO/TiO ₂ nanocomposite	2.6	61
5	T-ZnO/rGO nanocomposite	1.54 (1 $\mu\text{A cm}^{-2}$)	62
6	SnO ₂ /rGO nanocomposite	1.8 (1 $\mu\text{A cm}^{-2}$)	63
7	ZnO/graphene nanocomposite	1.3 (1 $\mu\text{A cm}^{-2}$)	64
8	ZnO/graphene nanocomposite	2.1	65
9	SnO ₂ /graphene nanocomposite	3.85 (1 $\mu\text{A cm}^{-2}$)	66
10	MnO ₂ nanorods	7.1	Present work
11	MnO ₂ /rGO nano-heterostructure	1.4	

($1/E$) is shown in Fig. 3(c and d). Consistent previous reports,^{21,22} the FN plots of the MnO₂ nanorods and rGO/MnO₂ nano-heterostructure exhibit linear behavior in good agreement with their semiconducting nature. The nanometric features of the rGO/MnO₂ nano-heterostructure coupled with the high electrical conductivity of rGO are suggested as the key factors

behind the observed superior field emission properties.²⁻⁵ Apart from the improved field emission performance, the electron emission current stability is an important parameter for device fabrication considerations. We have therefore measured the emission current as a function of time in order to ascertain the robustness of the rGO/MnO₂ nano-heterostructure. The

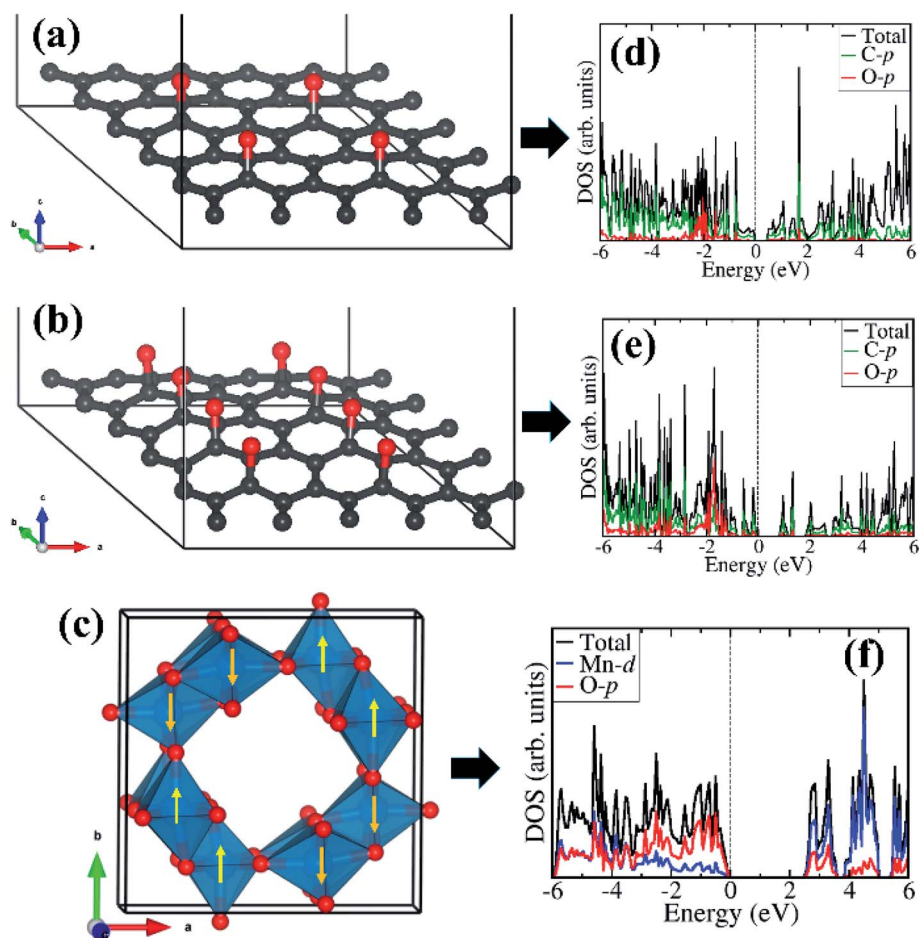


Fig. 4 Optimized structure of rGO with epoxide functional group with (a) 8% and (b) 16% oxygen content. The tetragonal structure of α -MnO₂ showing the AFM spin ordering in (c). The corresponding partial density of states are shown in the right column (d-f). Atomic color: C = grey, O = oxygen, Mn = blue.

emission current *versus* time ($I-t$) plot of the MnO_2 nanorods and rGO/MnO_2 nano-heterostructure were recorded continuously for 2 h at a preset value of emission current of $\sim 1 \mu\text{A}$ as shown in Fig. 3(e and f). Generally, the results show that the emission current remains quite stable without showing any sign of diminishing over the 2 h period of continuous testing. Instabilities in the form of spikes can be attributed to the presence of residual gas molecules across the emitter surface.

3.3 Density functional theory analyses

Considering that field emission is a geometry and work function (Φ) dependent phenomenon, with lower Φ enhancing the field emission characteristics, we have carried out first-principles density functional theory calculations to gain atomic-level insight into the electronic structure and work function of the isolated rGO , $\alpha\text{-MnO}_2$ (100) surface, and the $\text{rGO}/\alpha\text{-MnO}_2$ (100) nanocomposite. As the electronic band gap of rGO vary depending on the degree of reduction, the rGO monolayer with two concentrations of epoxide functional groups with 8% and 16% oxygen contents were modelled as

shown in Fig. 4(a and b). The band gap of the rGO with 8% and 16% oxygen contents are predicted at 0.48 eV (Fig. 4d) and 0.81 eV (Fig. 4e). This is consistent with experimental data that showed that the band gap of rGO can be tuned from 0.264–0.786 eV by controlling the surface concentration of epoxide groups.⁶⁷ The bulk $\alpha\text{-MnO}_2$ was modelled tetragonal crystal structure (space group – $I4/m$, no. 87) in the antiferromagnetic AFM-C2 configuration⁶⁸ as shown in Fig. 4c. A full unit cell relaxation yielded a strain-free $\alpha\text{-MnO}_2$ with lattice parameters $a = b = 9.763 \text{ \AA}$, $c = 2.872 \text{ \AA}$, which compares closely with known experimental data ($a = b = 9.71 \text{ \AA}$ and $c = 2.88 \text{ \AA}$).^{69,70} The electronic band gap of $\alpha\text{-MnO}_2$ is predicted at 2.42 eV (Fig. 4f), in close agreement with an experimental estimate of 2.23 eV⁷¹ and previous theoretical prediction of 2.7 eV.⁷² The valence band edge of $\alpha\text{-MnO}_2$ is demonstrated to consist mainly of O-p states whereas the conduction band edge is dominated by Mn-d states. The smaller band gap of the rGO compared to the MnO_2 suggests that the rGO has better electrical conductivity than the metal oxide.

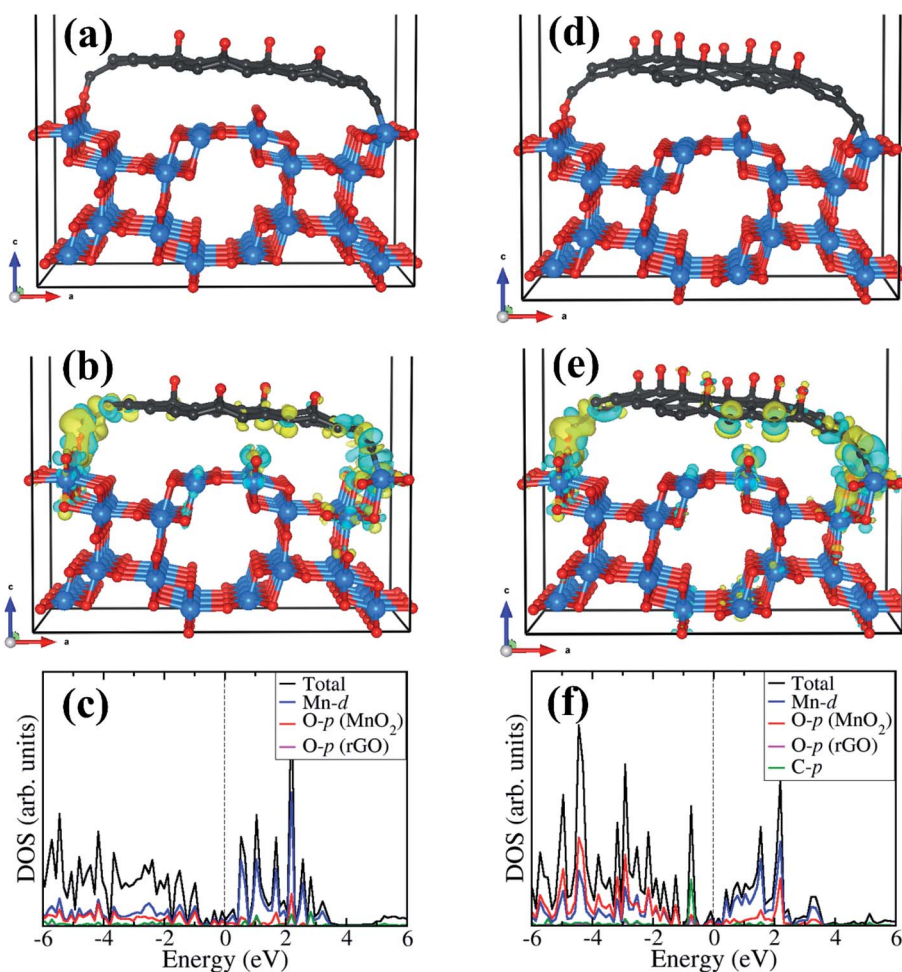


Fig. 5 Optimized structures of the $\text{rGO}/\alpha\text{-MnO}_2(100)$ nanocomposite formed by rGO with epoxide functional group (a) 8% and (d) 16% oxygen content. The corresponding differential charge density iso surface contours and partial density of states are shown in (b) and (c) for 8% oxygen content, and in (e) and (f) for 16% oxygen content. The yellow and cyan regions indicate electron density depletion and accumulation by 0.003 e \AA^{-3} , respectively. Atomic color: C = grey, O = oxygen, Mn = blue.

The optimized structures of the rGO/ α -MnO₂(100) nanocomposite formed by rGO with epoxide functional group with 8% and 16% oxygen contents are shown in Fig. 5a and d, respectively. The rGO is stabilized on the MnO₂ surface *via* C–O and C–Mn chemical bonds through the terminal C atoms. The interactions of the rGO with the MnO₂ surface gave rise to electron density redistribution within the rGO/ α -MnO₂(100) nanocomposite, which was analyzed by determining the three-dimensional-charge density difference iso surface contours as shown in Fig. 5b for the rGO with 8% oxygen content and Fig. 5e for rGO with 16% oxygen content. The yellow and cyan regions represent charge depletion and accumulation in the space, respectively. We observe electron density accumulations mainly in the interfacial bonding regions in the rGO/ α -MnO₂(100) nanocomposite, suggesting strong interactions between rGO and MnO₂(100) surface. Consistent with the strong interaction, we observe strong hybridization between the C-p orbitals of the rGO with the Mn-d and O-p of the MnO₂ surface as shown in Fig. 5c and f, resulting in metallic conductivity of the composite systems.

The analysis of the work function (Φ) for the rGO monolayer, α -MnO₂(100) and the rGO/ α -MnO₂(100) nanocomposite can

help us to understand the origin/direction of charge transfer at the rGO/ α -MnO₂(100) interface. The Φ for the isolated rGO is predicted at 5.21 and 5.85 eV for the 8% and 16% oxygen contents, respectively (Fig. 6a and b). This is consistent with a previous theoretical investigation which predicted a work function of rGO with epoxy groups to be 4.35 eV for 1.5% oxygen content and 5.6 eV for 20% oxygen content.⁷³ The Φ for the α -MnO₂(100) surface is predicted at 7.22 eV (Fig. 6c), also in good agreement with earlier theoretical pH-corrected work function of 7.7 eV for the α -MnO₂ (110) surface.⁷² The work function of the rGO/ α -MnO₂(100) nanocomposite is predicted at 6.01 and 6.12 eV for the rGO with 8% and 16% oxygen contents (Fig. 6d and e), both of which are lower than that of the isolated α -MnO₂(100) surface (Fig. 6c). The reduction in the work function of rGO/ α -MnO₂(100) nanocomposite relative to the isolated α -MnO₂(100) surface can be ascribed to the interfacial bonding, electronic interaction and synergistic effects. Considering that the electron emission capability of a material is dictated by its work function, the observed superior field emission characteristics of the rGO/ α -MnO₂ nanocomposite compared to the isolated α -MnO₂ material can be attributed to the predicted lower work function for the rGO/ α -MnO₂(100) nanocomposite.

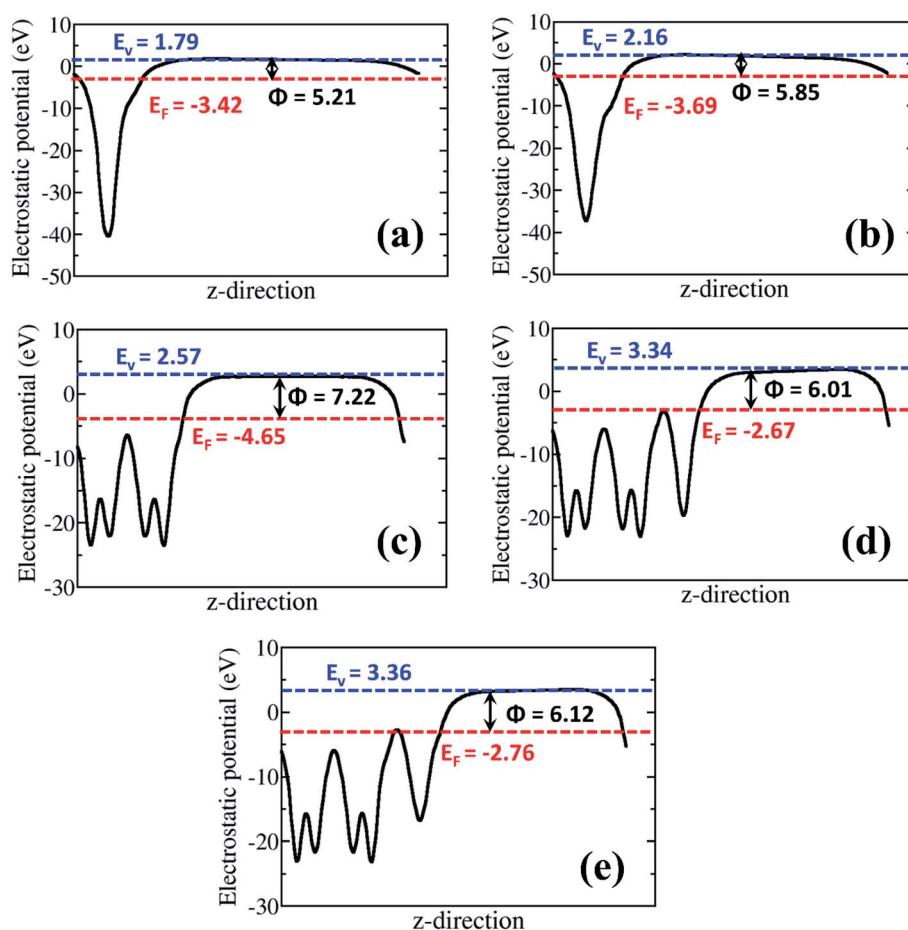


Fig. 6 The electrostatic potentials for isolated epoxide-rGO with (a) 8% and (b) 16% oxygen content; (c) isolated α -MnO₂(100) surface, and rGO/ α -MnO₂(100) nanocomposite formed rGO with (d) 8% and (e) 16% oxygen content. The blue and red dashed lines represent the vacuum level (E_{vac}) and the Fermi level (E_F), respectively. Φ denotes the work function.

Reduction in the work function has been observed in other composite materials compared to the isolated materials.^{52,53} For instance, Susaki *et al.*, have shown that the deposition of a single unit cell of MgO on an Nb:SrTiO₃ substrate reduces the work function by about 0.8 eV.⁷⁴ Similarly, by decorating SnSe nanosheets with Au nanoparticles (Au/SnSe) and porous ZnO nanosheets with CuSCN nanocoins (CuSCN/ZnO) resulted in significant improvements in the FE characteristics owing to predicted lower functions.^{52,53} The higher work function predicted for the α -MnO₂(100) surface compared to rGO monolayer (Fig. 6) suggests that spontaneous electrons transfer will flow from the rGO monolayer to the α -MnO₂(100) after the two are coupled together. Besides the reduction of the work function, the formation of nano-protrusions (denoted by red circles) in the rGO/MnO₂ nano-heterostructure (Fig. S5†) can act as effective emission sites. In addition, the better electrical conductivity ($5 \times 10^{-3} \text{ S cm}^{-1}$) of rGO is expected to play an important role in electron transportation. The rGO as backbone may result in easy and high percolation of electrons from the rGO to MnO₂ nanorods giving rise to the observed superior field emission behavior of the rGO/MnO₂ nano-heterostructure.

4. Conclusion

In summary, we report the successful synthesis of MnO₂ nanorods and rGO/MnO₂ nano-heterostructure using cost effective hydrothermal and modified Hummer's methods, respectively. The coupling of rGO sheets with MnO₂ nanorods is demonstrated to have a synergistic effect in improving the FE characteristics of formed rGO/MnO₂ nano-heterostructure. The dramatic reduction of the turn-on field by $5.7 \text{ V } \mu\text{m}^{-1}$ for an emission current density of $10 \text{ } \mu\text{A cm}^{-2}$ and the achieved high current density of $600 \text{ } \mu\text{A cm}^{-2}$ with an applied field of $3.1 \text{ V } \mu\text{m}^{-1}$ demonstrate the superior FE characteristics of the rGO/MnO₂ nano-heterostructure compared to the isolated porous MnO₂ nanorods. The results are corroborated by first principles DFT calculations, which predict lower work function for the rGO/MnO₂ nano-heterostructure (6.01 and 6.12 eV for the rGO with 8% and 16% oxygen contents, respectively) compared to the isolated MnO₂ (7.22 eV) as the primary origin for the improved field emission of the rGO/MnO₂ nanocomposite. The controlled nanofabrication of rGO/MnO₂ heterostructure reported here provides a promising approach for designing highly efficient MnO₂-based next generation FE electron sources and extend their practical applications in micro/nano electronic devices.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

S. R. R. and N. Y. D. acknowledge the UK Engineering and Physical Sciences Research Council (EPSRC) for funding (Grant No. EP/S001395/1). This work has also used the computational facilities of the Advanced Research Computing at Cardiff (ARCCA) Division, Cardiff University, and HPC Wales. This work

also made use of the facilities of ARCHER (<http://www.archer.ac.uk>), the UK's national supercomputing service via the membership of the UK's HEC Materials Chemistry Consortium, which is funded by EPSRC (EP/L000202). P. G. C. acknowledges the Consortium for Scientific Research (CSR) Indore, India for financial support (CSR project-CSR-IC-MSRSR-19/CRS-227/2017-2018/1308). Information on the data that underpins the results presented here, including how to access them, can be found in the Cardiff University data catalogue at <http://doi.org/10.17035/d.2020.0111099343>.

References

- 1 D. J. Milliron, S. M. Hughes, Y. Cui, L. Manna, J. Li, L. W. Wang and A. P. Alivisatos, *Nature*, 2004, **430**, 190–195.
- 2 M. D. Stoller, S. Park, Y. Zhu, J. An and R. S. Ruoff, *Nano Lett.*, 2008, **8**(10), 3498–3502.
- 3 Y. Sun, Q. Wu and G. Shi, *Energy Environ. Sci.*, 2011, **4**, 1113–1132.
- 4 G. A. M. Ali, S. A. Makhlof, M. M. Yusoff and K. F. Chong, *Rev. Adv. Mater. Sci.*, 2015, **41**, 35–43.
- 5 G. A. M. Ali, M. M. Yusoff and K. F. Chong, *ARPN J. Eng. Appl. Sci.*, 2016, **16**, 9712–9717.
- 6 G. Eda, G. Fanchini and M. Chhowalla, *Nat. Nanotechnol.*, 2008, **3**, 270–274.
- 7 J. T. Robinson, M. Zalalutdinov, J. W. Baldwin, E. S. Snow, Z. Wei, P. Sheehan and B. H. Houston, *Nano Lett.*, 2008, **8**(10), 3441–3445.
- 8 J. T. Robinson, F. K. Perkins, E. S. Snow, Z. Q. Wei and P. E. Sheehan, *Nano Lett.*, 2008, **8**, 3137–3140.
- 9 D. R. Dreyer, H. Jia and C. W. Bielawski, *Angew. Chem. Int. Ed.*, 2010, **49**, 6813–6816.
- 10 D. Wang, R. Kou, D. Choi, Z. Yang, Z. Nie, J. Li, L. V. Saraf, D. Hu, J. Zhang, G. L. Graff, J. Liu, M. A. Pope and I. A. Aksay, *ACS Nano*, 2010, **4**, 1587–1595.
- 11 W. Gao, N. Singh, L. L. Song, A. L. Reddy, L. Ci, R. Vajtai, Q. Zhang, B. Wei and P. M. Ajayan, *Nat. Nanotechnol.*, 2011, **6**, 496–500.
- 12 K. P. Loh, Q. Bao, G. Eda and M. Chhowalla, *Nat. Chem.*, 2010, **2**, 1015–1024.
- 13 H. Yamaguchi, K. Murakami, G. Eda, T. Fujita, P. Guan, W. Wang, C. Gong, J. Boisse, S. Miller, M. Acik, K. Cho, Y. Chabal, M. Chen, F. Wakaya, M. Takai and M. Chhowalla, *ACS Nano*, 2011, **5**(6), 4945–4952.
- 14 R. Kumar, R. Singh, A. Vaz, R. Yadav, C. Rout and S. Moshkalev, *New J. Chem.*, 2017, **41**, 8431–8436.
- 15 R. Roy, A. Jha, D. Sen, D. Banerjee and K. K. Chattopadhyay, *J. Mater. Chem. C*, 2014, **2**, 7608–7613.
- 16 C. Chen, W. Cai, M. Long, B. Zhou, Y. Wu, D. Wu and Y. Feng, *ACS Nano*, 2010, **4**(11), 6425–6432.
- 17 C. Zhu, S. Guo, P. Wang, L. Xing, X. Y. Fang, Y. M. Zhai and S. J. Dong, *Chem. Commun.*, 2010, **46**, 7148–7150.
- 18 Z. Rujia, Z. Zhang, L. Jiang, K. Xu, Q. Tian, S. Xue, J. Hu, Y. Bando and D. Golberg, *Mater. Chem.*, 2012, **22**, 19196–19201.
- 19 G. H. Gote, S. R. Bhopale, M. A. More and D. J. Late, *Phys. Status Solidi A*, 2019, **216**, 1900121.

- 20 C. S. Rout, P. D. Joshi, R. V. Kashid, D. S. Joag, M. A. More, A. J. Simbeck, M. Washington, S. K. Nayak and D. J. Late, *Sci. Rep.*, 2013, **3**, 3282.
- 21 M. Wu, J. Lee, Y. Wang and C. Wan, *J. Phys. Chem. B*, 2004, **108**(42), 16331–16333.
- 22 K. Hareesh, S. R. Suryawanshi, A. B. Phatangare, M. A. More, V. N. Bhoraskar and S. D. Dhole, *Mater. Lett.*, 2016, **185**, 472–475.
- 23 J. Wu, H. Huang, L. Yu and J. Hu, *Adv. Mater. Phys. Chem.*, 2013, **3**, 201–205.
- 24 W. Wei, X. Cui, W. Chen and D. G. Ivey, *Chem. Soc. Rev.*, 2011, **40**, 1697–1721.
- 25 T. Bordjiba and D. Belanger, *Electrochim. Acta*, 2010, **55**, 3428–3433.
- 26 K. Sun, H. Wang, H. Peng, Y. Wu, G. Ma and Z. Lei, *Int. J. Electrochem. Sci.*, 2015, **10**, 2000–2013.
- 27 S. R. Majid Rusi, *Solid State Ionics*, 2014, **262**, 220–225.
- 28 G. A. M. Alia, M. M. Yusoff, H. Algarnic and K. F. Chonga, *Ceram. Int.*, 2018, **44**, 7799–7807.
- 29 S. Ghasemi, S. R. Hosseini and O. Boore-talari, *Ultrason. Sonochem.*, 2018, **40**, 675–685.
- 30 R. Rajagopal and K. Ryu, *ChemElectroChem*, 2018, **5**, 2218.
- 31 S. Ghosal and P. Bhattacharyya, *IEEE Trans. Electron. Dev.*, 2019, **66**, 3882.
- 32 J. Hong, T. T. Mengesha, S. Hong, H. Kim and Y. Hwang, *J. Korean Phys. Soc.*, 2020, **76**, 264–272.
- 33 O. Sadak, W. Wang, J. Guan, A. K. Sundramoorthy and S. Gunasekaran, *ACS Appl. Nano Mater.*, 2019, **2**, 4386–4394.
- 34 J. G. Radich and P. V. Kamat, *ACS Catal.*, 2012, **2**, 807–816.
- 35 B. Q. Zeng, G. Y. Xiong, S. Chen, H. Jo, W. Z. Wang, D. Z. Wang and Z. F. Ren, *Appl. Phys. Lett.*, 2006, **88**, 213108.
- 36 D. C. Marcano, D. V. Kosynkin, J. M. Berlin, A. Sinitskii, Z. Sun, A. Slesarev, L. B. Alemany, W. Lu and J. M. Tour, *ACS Nano*, 2010, **4**(8), 4806–4814.
- 37 S. Santhanagopalan, A. Balram and D. D. Meng, *ACS Nano*, 2013, **7**(3), 2114–2125.
- 38 G. P. Patil, P. K. Baviskar, V. S. Bagal, R. D. Ladhe, A. B. Deore, M. A. More, B. R. Sankapal and P. G. Chavan, *RSC Adv.*, 2016, **6**, 71958.
- 39 G. Kresse and J. Hafner, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **47**, 558.
- 40 G. Kresse and D. Joubert, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 1758.
- 41 G. Kresse and G. J. Furthmüller, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169–11189.
- 42 P. E. Blöchl, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **50**, 17953–17979.
- 43 H. J. Monkhorst and J. D. Pack, *Phys. Rev. B: Solid State*, 1976, **13**, 5188–5192.
- 44 I. Biaggio, R. W. Hellwarth and J. P. Partanen, *Phys. Rev. Lett.*, 1997, **78**, 891.
- 45 V. Krukau, O. A. Vydrov, A. F. Izmaylov and G. E. Scuseria, *J. Chem. Phys.*, 2006, **125**, 224106-1–224106-5.
- 46 P. E. Blöchl, O. Jepsen and O. K. Andersen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **49**, 16223–16233.
- 47 D. A. Tompsett, S. C. Parker and M. S. Islam, *J. Mater. Chem. A*, 2014, **2**, 15509–15518.
- 48 A. Walsh and K. T. Butler, *Acc. Chem. Res.*, 2013, **47**, 364–372.
- 49 M. Ganose, K. T. Butler, A. Walsh and D. O. Scanlon, *J. Mater. Chem. A*, 2016, **4**, 2060–2068.
- 50 L. Wu, N. Y. Dzade, L. Gao, D. O. Scanlon, Z. Öztürk, N. Hollingsworth, B. M. Weckhuysen, E. J. M. Hensen, N. H. L. Leeuw and J. P. Hofmann, *J. Adv. Mater.*, 2017, **28**, 9602–9607.
- 51 N. Y. Dzade and N. H. Leeuw, *Phys. Chem. Chem. Phys.*, 2017, **19**, 27478–27488.
- 52 P. K. Baviskar, S. R. Rondiya, G. P. Patil, B. R. Sankapal, H. M. Pathan, P. G. Chavan and N. Y. Dzade, *ACS Omega*, 2020, **5**(12), 6715–6724.
- 53 S. R. Rondiya, C. D. Jadhav, P. G. Chavan and N. Y. Dzade, *Sci. Rep.*, 2020, **10**(1), 1–10.
- 54 B. He, G. Cheng, S. Zhao, X. Zeng, Y. Li, R. Yang, M. Sun and L. Yu, *J. Solid State Chem.*, 2019, **269**, 305–311.
- 55 P. K. S. Mural, M. Sharma, A. Shukla, S. Bhadra, B. Padmanabhan, G. Madras and S. Bose, *RSC Adv.*, 2015, **5**, 32441–32451.
- 56 H. Wang, Z. Lu, D. Qian, Y. Li and W. Zhang, *Nanotechnology*, 2007, **18**, 115616.
- 57 B. J. Tan, K. J. Klabunde and P. M. A. Sherwood, *J. Am. Chem. Soc.*, 1991, **113**, 855–861.
- 58 V. Subramanian, H. Zhu, R. Vajtai, P. M. Ajayan and B. Wei, *J. Phys. Chem. B*, 2005, **109**, 20207–20214.
- 59 B. Li, G. Rong, Y. Xie, L. Huang and C. Feng, *Inorg. Chem.*, 2006, **45**, 6404–6410.
- 60 H. Huang and X. Wang, *Nanoscale*, 2011, **3**, 3185–3191.
- 61 G. P. Patil, V. S. Bagal, C. R. Mahajan, V. R. Chaudhari, S. R. Suryawanshi, M. A. More and P. G. Chavan, *Vacuum*, 2016, **123**, 167–174.
- 62 C. Wu, T. W. Kim and T. Guo F. Li, *Sci. Rep.*, 2016, **6**, 38613.
- 63 S. R. Bansode, R. T. Khare, K. K. Jagtap, M. A. More and P. Koinkar, *Mater. Sci. Semicond. Process.*, 2017, **63**, 90–96.
- 64 W. T. Zheng, Y. M. Ho, H. W. Tian, M. Wen, J. L. Qi and Y. A. Li, *J. Phys. Chem. C*, 2009, **113**, 9164.
- 65 R. Zou, G. He, K. Xu, Q. Liu, Z. Zhang and J. Hu, *J. Mater. Chem. A*, 2013, **1**, 8445.
- 66 J. Ding, X. Yan, J. Li, B. Shen, J. Yang, J. Chen and Q. Xue, *ACS Appl. Mater. Interfaces*, 2011, **3**, 4299.
- 67 Y. Jin, Y. Zheng, S. G. Podkolzin and W. Lee, *J. Mater. Chem. C*, 2020, **8**, 4885–4894.
- 68 G. Kruthika, J. Karthikeyan and P. Murugan, *Phys. Chem. Chem. Phys.*, 2017, **19**, 3770–3776.
- 69 F. Cheng, T. Zhang, Y. Zhang, J. Du, X. Han and J. Chen, *Angew. Chem. Int. Ed.*, 2013, **52**, 2474–2477.
- 70 C. S. Johnson, D. W. Dees, M. F. Mansuetto, M. M. Thackeray, D. R. Vissers, D. Argyriou, C. K. Loong and L. Christensen, *J. Power Sources*, 1997, **68**, 570–577.
- 71 N. Sakai, Y. Ebina, K. Takada and T. Sasaki, *J. Phys. Chem. B*, 2005, **109**, 9651–9655.
- 72 M. J. Young, A. M. Holder, S. M. George and C. B. Musgrave, *Chem. Mater.*, 2015, **27**, 1172–1180.
- 73 P. V. Kumar, M. Bernardi and J. C. Grossman, *ACS Nano*, 2013, **7**, 1638–1645.
- 74 T. Susaki, A. Makishima and H. Hosono, *Phys. Rev.*, 2011, **83**, 115435.