

Cite this: *RSC Adv.*, 2019, 9, 23526

Co²⁺ substituted for Bi³⁺ in BiVO₄ and its enhanced photocatalytic activity under visible LED light irradiation†

Trinh Duy Nguyen,^a Quynh Thi Phuong Bui,^b Tien Bao Le,^b T. M. Altahtamouni,^c Khanh Bao Vu,^d Dai-Viet N. Vo,^e Nhan Thi Hong Le,^e Tuan Duy Luu,^e Seong Soo Hong^f and Kwon Taek Lim^g

We investigated the fabrication of Co-doped BiVO₄ (Bi_{1-x}Co_xVO_{4+δ}, 0.05 < x < 0.5) by the substitution of Co ions for Bi sites in BiVO₄. The X-ray diffraction (XRD), Raman, and X-ray photoelectron spectroscopy (XPS) results indicated that the substitution of Co²⁺ ions for Bi³⁺ sites in BiVO₄ was successful, although a change in the crystal phase of BiVO₄ did not occur. UV-vis DRS and PL results suggested that the Co-incorporation could slightly improve the visible light absorption of BiVO₄ and induce the separation of photoinduced electron–hole pairs; therefore, a significant enhancement of photocatalytic performance was achieved. The Bi_{0.8}Co_{0.2}VO_{4+δ} sample showed superior photocatalytic activity in comparison with other samples, achieving 96.78% methylene blue (MB) removal within 180 min. In addition, the proposed mechanism of improved photocatalytic activities and the stability of the catalyst were also investigated.

Received 3rd June 2019

Accepted 12th July 2019

DOI: 10.1039/c9ra04188e

rsc.li/rsc-advances

1 Introduction

Monoclinic scheelite bismuth vanadate (m-s BiVO₄), a p-type semiconductor with a direct band gap (E_g) of 2.4 eV, has generated considerable interest as a visible light-responsive photocatalyst.^{1–4} Reportedly, different morphologies of monoclinically structured BiVO₄ crystallites, such as nanospheres,⁵ nanorods,^{6,7} nanoflowers,⁸ nanosheets,⁹ nanotubes,^{10–12} olive,^{13,14} and hyperbranched,¹⁵ have been clearly created by the hydrothermal or solvothermal technique. Nevertheless, the poor charge transport and weak surface adsorption properties associated with pristine BiVO₄ could cause prompt recombination of photogenerated electron–hole pairs, reducing its overall photocatalytic efficiency. Hence, various strategies

aiming to enhance the photocatalytic performance of m-s BiVO₄ have been explored. Such approaches could include doping BiVO₄ with metals and/or non-metals,^{16–21} controlling the morphology and facets of BiVO₄,^{5,13,22,23} constructing a novel p–n heterojunction photocatalyst,^{24–27} and controlling the monoclinic-tetragonal heterostructure of BiVO₄.²⁸

Among the many methods for improving the photocatalytic activity, metal and/or non-metal doping is regarded as a simple and effective strategy. For metal-doped BiVO₄, metal ions can substitute the V or Bi sites in the crystal lattice of BiVO₄, exhibiting a quite different photocatalytic performance. For instance, Luo and co-workers observed that the photocurrent of the BiVO₄ semiconductor could be substantially improved by Mo⁶⁺ or W⁶⁺ doping, and further demonstrated the substitution of Mo⁶⁺ or W⁶⁺ ions in V⁵⁺ positions.²⁹ Contrarily, the incorporation of lanthanide ions Ce^{III,IV} occurring at Bi³⁺ sites in the BiVO₄ lattice caused a pronounced change in the crystal phase, optical properties, and the separation of photoinduced electron–hole pairs, resulting in a prominent improvement of photocatalytic activity.³⁰ Substitution of Fe³⁺ ions for Bi³⁺ sites in BiVO₄ also significantly enhanced photocatalytic performance for the decomposition of ibuprofen and greatly inactivated *Escherichia coli* bacteria under visible light irradiation.³¹ However, modification of BiVO₄ by doping of cobalt ions seemed to yield contradictory results. Specifically, Regmi and co-workers found that Co substituted for V in the crystal lattice, indicated by the shift in the symmetric V–O stretching mode to lower wavenumber, was confirmed by the Raman result.³² To the contrary, another study showed that Co²⁺ substituted for Bi³⁺ in BiVO₄, which was confirmed by Bo Zhang *et al.*³³ On the

^aCenter of Excellence for Green Energy and Environmental Nanomaterials (CE@GrEEN), Nguyen Tat Thanh University, Ho Chi Minh City, Vietnam. E-mail: ndrtrinh@ntt.edu.vn; Fax: +84-028-39-404-759; Tel: +84-028-3941-1211

^bFaculty of Chemical Technology, Ho Chi Minh City University of Food Industry, 140 Le Trong Tan, Tan Phu District, Ho Chi Minh City, Vietnam

^cMaterials Science and Technology Program, College of Arts and Sciences, Qatar University, Doha 2713, Qatar

^dNTT Hi-Tech Institute, Nguyen Tat Thanh University, Ho Chi Minh City, Vietnam

^eDepartment of Chemical Engineering, HCMC University of Technology, VNU-HCM, Ho Chi Minh City, Vietnam

^fDepartment of Chemical Engineering, Pukyong National University, Busan, Korea

^gDepartment of Display Engineering, Pukyong National University, Busan, Korea

† Electronic supplementary information (ESI) available: XRD analysis, Raman spectra, SEM images, photo-stability tests, trapping experiments, and a comparison of photocatalytic activity of photocatalysts. See DOI: 10.1039/c9ra04188e



other hand, it was suggested by Zhou *et al.* that the incorporation of cobalt as an oxide on the surface of larger BiVO catalysts caused no change in the crystal structure of the composites.³⁴ Co-doped BiVO was also investigated by Geng *et al.*,³⁵ but they did not identify the substitution of Co ions for Bi³⁺ or V³⁺ sites in BiVO₄.

Therefore, the present study aimed to identify the substitution of Co ions for Bi³⁺ sites in BiVO₄. We proposed the synthesis of Co-doped BiVO₄ (Bi_{1-x}Co_xVO_{4+δ}, 0.05 < x < 0.5) by the hydrothermal method. The effect of Co²⁺ ions substituted for Bi³⁺ sites in BiVO₄ on the crystal structure, morphology, optical behavior, photoinduced charges separation, and photocatalytic performance for decomposition of methylene blue (MB) under visible LED light irradiation was carefully explored. The proposed mechanism for the improved photocatalytic activities in Co²⁺ doped BiVO₄ is discussed. In addition, the stability and reusability of catalyst were also investigated.

2 Experimental

2.1 Synthesis of photocatalysts

The hydrothermal procedure employing Bi(NO₃)₃·5H₂O, Co(NO₃)₂·6H₂O, and NH₄VO₃ as the precursors were adopted to synthesize the Co-doped BiVO₄ samples. Firstly, two clear solutions were prepared as follows: (i) Bi(NO₃)₃·5H₂O (4 mmol) and a predetermined amount of Co(NO₃)₂·6H₂O were dissolved in 20 mL of HNO₃ 2 M; (ii) 4 mmol of NH₄VO₃ was dissolved in 40 mL of NaOH 0.3 M. Estimation of the concentration of Co(NO₃)₂·6H₂O followed the stoichiometric formulation of Bi_{1-x}Co_xVO_{4+δ} (where x = 0, 0.05, 0.1, 0.2, 0.3, and 0.5; abbreviated as BVO, 0.05Co-BVO, 0.1Co-BVO, 0.2Co-BVO, 0.3Co-BVO, and 0.5Co-BVO, respectively). Then, a mixture was created by mixing the two solutions under vigorous stirring for 30 min; pH was adjusted to 10 using NaOH 4 M solution. Next, the resulting suspension was adjusted for volume to 80 mL using distilled water and then transferred to a 100 mL hydrothermal autoclave reactor with a Teflon chamber vessel. The reactor then underwent thermal treatment at 180 °C in an oven for 24 h. The obtained yellow paste was rinsed with water until the pH of the filtrate solution was around 7. Finally, the obtained powder was dried at 110 °C for 24 h, followed by calcination at 300 °C for 2 h.

2.2 Characterization of photocatalysts

To characterize the crystal structure of the undoped and doped BiVO₄ photocatalysts, multiple techniques including X-ray diffraction (XRD, D8 ADVANCE-Bruker), Raman spectra (HORIBA Jobin Yvon), and X-ray photoelectron spectroscopy (XPS, Thermo VG Multilab 2000) were employed. Morphological characteristics were observed by Field Emission Scanning Electron Microscopy (FE-SEM, JSM-6700F, Jeol) and transmission electron microscopy (TEM, JEM 1400, JEOL). Energy band structure was evaluated through the UV-visible diffuse reflectance spectrum (UV-Vis DRS, Shimadzu UV-2450) with BaSO₄ as the standard. Photoluminescence (PL) spectroscopy was performed using an F-4500 Spectro-fluorometer (Hitachi) with an excitation wavelength of 315 nm.

2.3 Photocatalytic test

The assessment of the photocatalytic performance of the bare BiVO₄ and Co-doped BiVO₄ was executed by the photodecomposition of MB dye in aqueous media under white LED light irradiation. Six LED lamps (XLamp XT-E White, Cree X6) with a max power of 10 W and max light output of 1040 lm acted as the white light source for this study. To perform this experiment, a mixture containing catalyst powder (0.5 g L⁻¹) and MB aqueous solution (100 mL, 15 mg L⁻¹) was mixed in a 250 mL double layer interbed interlayer glass beaker and vigorously stirred for 100 min to ensure the adsorption-desorption equilibrium between the surface of BiVO₄ and the MB molecules. Under light exposure, aliquots of the reaction solution were withdrawn at defined time intervals, and the solid was immediately isolated by centrifugation at 8000 rpm. The concentration of MB was determined by the intensity change of absorption peak at 664 nm using a UV-visible spectrophotometer (Model Evolution 60S, Thermo Fisher Scientific). In addition, to investigate the stability of catalyst, repeated photodecomposition of MB dye over five consecutive cycles was conducted using a method similar to the above. After each reaction run, the catalyst was washed with water three times and isolated by centrifugation at 8000 rpm.

2.4 Analysis of hydroxyl radical productions

We also used the PL technique with benzene-1,4-dicarboxylic acid (H₂BDC) as the sensor molecule to detect the ·OH radicals produced by 0.2Co-BVO during the photocatalytic processes. H₂BDC molecule reacted with the ·OH radicals to form a fluorescent molecule (2-hydroxy-1,4-benzenedicarboxylic acid, H₂BDC-OH). The experimental procedures were conducted based on the above photocatalytic activity test, but MB solution was replaced by H₂BDC solution ([H₂BDC] = 5 × 10⁻⁴ M and [NaOH] = 2 × 10⁻³ M).¹⁴ After 60 min of irradiation, the reaction solution after eliminating catalyst was analyzed by a Hitachi F4500 fluorescence spectrometer at an excitation wavelength of 315 nm.

3 Results and discussion

3.1 Crystal structure

Fig. 1A presents XRD patterns of the bare BiVO₄ and Co-doped BiVO₄ samples. The bare BiVO₄ sample had a pure monoclinic scheelite phase structure (m-s BiVO₄, JCPDs 14-0688) with sharp characteristic peaks at 28.9°, and 30.5°, and double peaks at 18.9°, 35°, and 47°. Similarly, all XRD peaks of the 0.05Co-BVO, 0.1Co-BVO, and 0.2Co-BVO samples were also correctly indexed to the m-s BiVO₄, and no peaks of tetragonal phase (t-z BiVO₄) were detected. This result indicated that the presence of Co with x = 0.05–0.2 caused no significant change in the crystal phase of BiVO₄, which was consistent with previous studies.^{33–35} However, when further increasing the Co molar ratio to 0.3, diffraction peaks of impurities including Bi₂O₃ (JCPDs 41-1449) and Co₂V₂O₇ (JCPDs 70-1189) were detected. The XRD pattern of the 0.5Co-BVO sample also showed the mixed phases of BiVO₄, Bi₂O₃, Co₂V₂O₇, and Co₃V₂O₈ (JCPDs 74-1487). The presence of

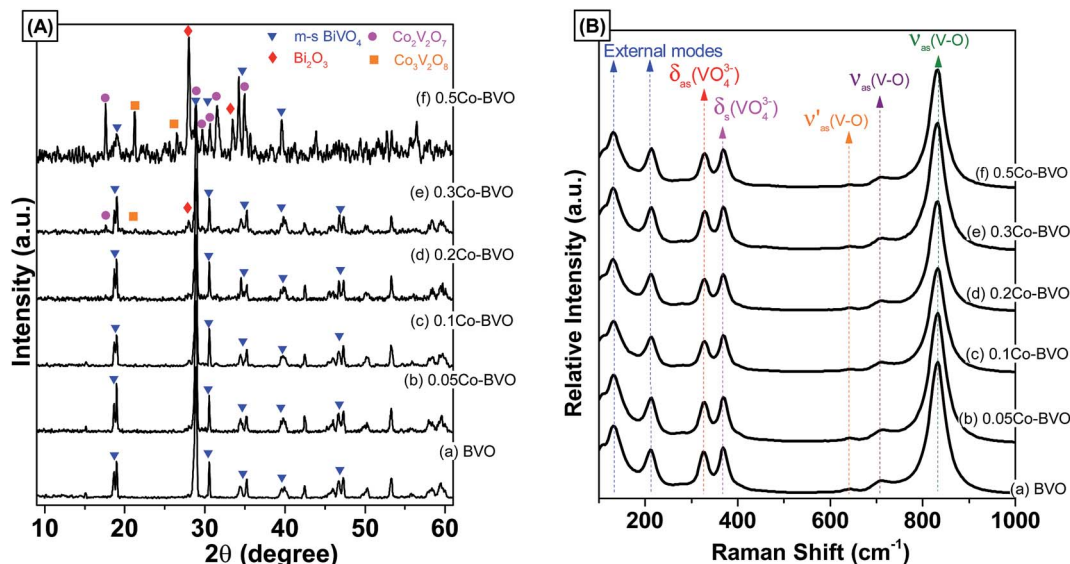


Fig. 1 XRD patterns (A) and Raman spectra (B) of the pristine BiVO_4 and Co-doped BiVO_4 samples.

Bi_2O_3 could be due to the hydrolysis of $\text{Bi}(\text{NO}_3)_3$,³⁶ $\text{Co}_3\text{V}_2\text{O}_7$ and $\text{Co}_3\text{V}_2\text{O}_8$ could be formed when the excess of Co^{2+} content under hydrothermal condition.³⁷ In addition, there was no peak indexed to the cobalt oxide or cobalt hydroxide for all Co-doped BiVO_4 samples, suggesting the possible doping of the cobalt ions into the lattice of BiVO_4 instead of loading to the BiVO_4 surface as hydroxide or oxide crystal grains. For the 0.2Co-BVO sample, we also observed that the peak at 28.9° had slightly shifted to a higher angle (Fig. S1†), implying that Co could be doped into the lattice of BiVO_4 crystal.^{31,32}

The crystallite size (d , nm) of $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ samples were evaluated from {121} peak of XRD patterns using the Scherrer's equation.^{14,30} The d values of the $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ samples are presented in Table 1. As shown in Table 1, the crystallite size of Co-doped BiVO_4 slightly increased compared to that of bare BiVO_4 sample, implying that the presence of Co^{2+} could influence the formation of crystalline particles of BiVO_4 .

The as-synthesized samples then had their phase structure confirmed by Raman spectra as plotted in Fig. 1B. It was observed that all samples expressed main Raman shifts at around 131 cm^{-1} (external mode), 212 cm^{-1} (external mode), 326 cm^{-1} (the asymmetric bending mode $\delta_{\text{as}}(\text{VO}_4^{3-})$), 368 cm^{-1} (the symmetric bending mode $\delta_{\text{s}}(\text{VO}_4^{3-})$), 639 cm^{-1} (the asymmetric V–O stretching mode $\nu'_{\text{as}}(\text{V–O})$), 709 cm^{-1} (the asymmetric V–O stretching mode $\nu_{\text{as}}(\text{V–O})$), and 832 cm^{-1} (the

symmetric V–O stretching mode $\nu_{\text{s}}(\text{V–O})$), which were similar to those of the m-s BiVO_4 phase. It was indicated that the existence of Co ion did not affect the crystal phase of BiVO_4 , which was confirmed by the XRD results. Also, a downtrend according to the increase of doped ion content in the intensity the symmetric V–O stretching mode was observed (Fig. S2†), which was caused by the weak deformation of the VO_4 tetrahedron. A similar effect was reported previously in terms of Fe-doped BiVO_4 (ref. 31) and Ce-doped BiVO_4 ,³⁰ in which this weak deformation could be due to the metal ion substitution at the Bi^{3+} site in the lattice of the BiVO_4 crystal.

The presence of substitution sites of Co in Co-doped BiVO_4 was also validated by the XPS spectrum. The survey and high-resolution XPS spectrum of the pristine BiVO_4 and 0.2Co-BVO photocatalysts are shown in Fig. 2A–F. Meanwhile, characteristic peaks of Bi, V, and O were present for pristine BiVO_4 and 0.2Co-BVO photocatalysts exhibiting Bi, V, O, and Co peaks (Fig. 2A). In addition, according to the peak area, the molar ratios of Bi/Co in 0.2Co-BVO photocatalysts reached the value of 3.59/1, which is close to the estimated value of 4/1, indicating well-dispersion of Co in BiVO_4 . The C 1s peak at 284.6 eV (Fig. 2B), assigning to the signal from carbon in the instrument, was used for calibration. Co 2p could be deconvoluted into two pairs of individual peaks at 780.9 eV (Co 2p_{3/2}) and 797.3 eV (Co 2p_{1/2}) (Fig. 2C), which were identified as the major binding energies (BE) of Co^{2+} .³⁸ As also presented in Fig. 2C, the BE indexed to the cobalt metal or cobalt oxides was not detected, implying that Co could be doped into the lattice of BiVO_4 crystal. Bi 4f spectrum of BVO (Fig. 2D) showed characteristic peak of Bi 4f_{5/2} and Bi 4f_{7/2} at 164.1 eV and 158.7 eV respectively, with $\Delta E = \text{Bi 4f}_{5/2} - \text{Bi 4f}_{7/2}$ of 5.4 eV. Similarly, Bi 4f_{5/2} (164.2 eV) and Bi 4f_{7/2} (158.9 eV) with ΔE of 5.3 eV were also observed in the Bi 4f spectrum of 0.2Co-BiVO₄ samples (Fig. 2D). After the Gaussian–Lorentzian fitting, the asymmetric V 2p_{3/2} spectra can be deconvoluted into two pairs

Table 1 The physical properties and photocatalytic activity of the bare BiVO_4 and the Co-doped BiVO_4 samples

Samples	d (nm)	E_g (eV)	k_{app} (10^{-3} min^{-1})	R^2
BVO	25.45	2.31	0.775	0.99742
0.1Co-BVO	29.09	2.30	1.185	0.95483
0.2Co-BVO	28.65	2.29	1.882	0.98230
0.3Co-BVO	31.88	2.26	0.633	0.98225
0.5Co-BVO	30.31	2.14	0.333	0.98070

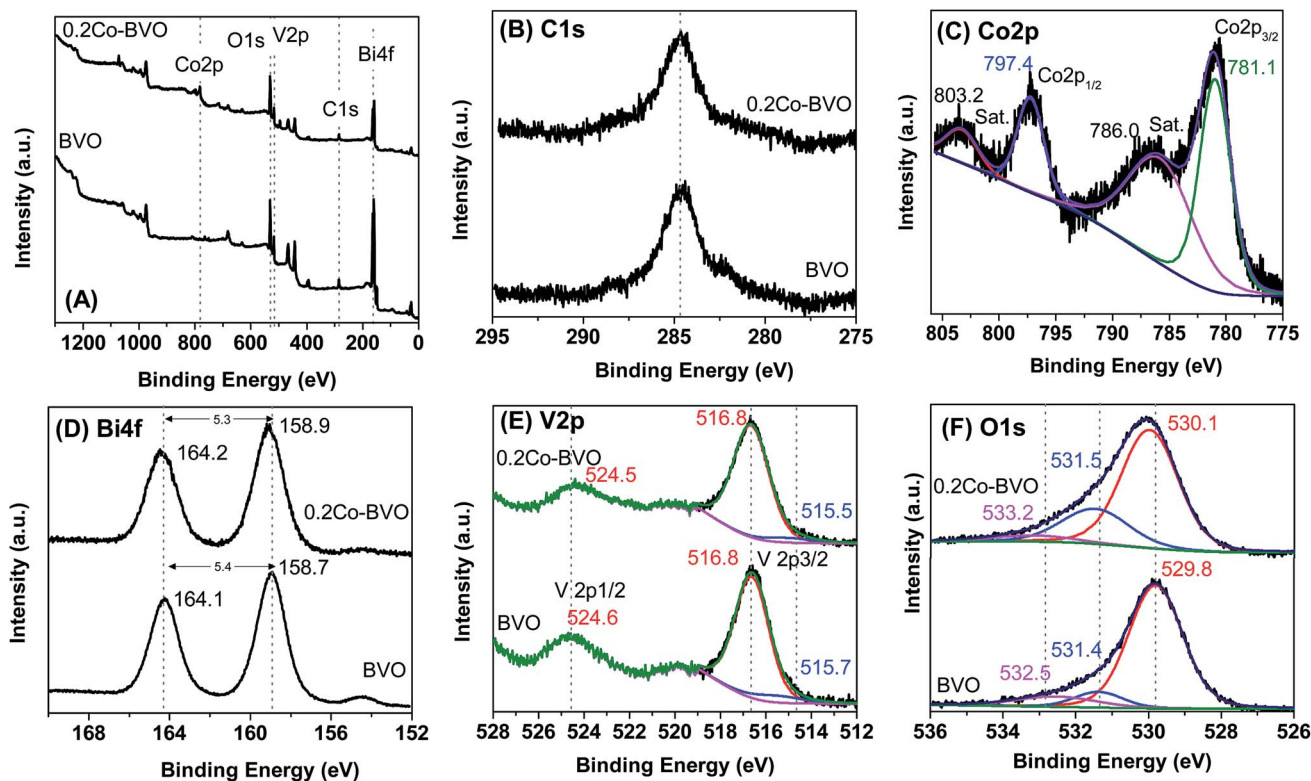


Fig. 2 The survey and high-resolution XPS spectrum of the pristine BiVO_4 and 0.2Co-BVO.

of individual components referring to the surface V^{4+} and V^{5+} states; they were 515.6 and 516.8 eV for BVO, and 515.0 and 516.7 eV for 0.2Co-BiVO₄ (Fig. 2E). The $\text{V}^{4+}/\text{V}^{5+}$ molar ratios of BVO and 0.2Co-BVO samples were 0.165 and 0.214, respectively. These results showed the slight shift of Bi 4f and V 2p for the 0.2Co-BVO sample as compared with the BVO sample, implying the interaction of Co^{2+} with Bi^{3+} and V^{5+} ions. Moreover, considering to the ion radius of Co^{2+} , V^{5+} , and Bi^{3+} , the ion radius of Co^{2+} (0.79 Å)³² was smaller than that of the Bi^{3+} (1.03 Å)³⁰ but larger than that of V^{5+} (0.36 Å),^{29,39} thus, doping with Co^{2+} tended to replace some Bi^{3+} in the internal lattice structure of BiVO_4 . This outcome was also supported by Bo Zhang *et al.* when using periodic density functional calculations within the GGA + U approach for calculating the formation energy.³³

Fig. 2F displays O 1s spectrum of the pure BiVO_4 sample with the BE positions at 529.8 eV, 531.4 eV, and 532.5 eV, which indexed to the lattice oxide (V–O or Bi–O bonds) in BiVO_4 (O_{latt}), the hydroxide hydrated or defective oxide (O_{ads}) species, and the surface adsorbed water, respectively.³⁰ As also shown in Fig. 2F, no other BE positions were observed due to the BE of V–O and Bi–O bonds being approximately the same. In terms of 0.2Co-BVO sample, after the Gaussian-Lorentzian fitting, the O 1s spectrum was also deconvoluted into three pairs of individual components: (1) the lattice oxide at BE of 530.1 eV; (2) the hydroxide hydrated or defective oxide at BE of 531.5 eV; (3) and the surface adsorbed water at BE of 533.2 eV. Notably, these peaks were slightly shifted to the high BE region in comparison to that of the bare BiVO_4 . This outcome could be due to the

doping Co^{2+} replacing some Bi^{3+} positions in the internal lattice structure of BiVO_4 , implying the formation of Co–O–Bi bonds. Also, the varied $\text{O}_{\text{ads}}/\text{O}_{\text{latt}}$ molar ratio was 0.49 for 0.2Co-BVO and 0.24 for the bare BiVO_4 sample. These results indicated that Co-doped BiVO_4 further increases the content of O_{ads} and oxygen vacancy, which are possibly responsible for improving the photocatalytic performance of BiVO_4 , as discussed below.

3.2 Morphological characteristics

The presence of Co also considerably altered the morphology of the as-synthesized samples, as exhibited in Fig. 3. The bare BiVO_4 sample consisted of large quantities of corner-cut truncated bipyramid and granular like structures with smooth surfaces (Fig. 3a). The 0.05Co-BVO (Fig. S3A†), 0.1Co-BVO (Fig. S3B†), and 0.2Co-BVO (Fig. 3b) were morphologically similar to the Co-doped BiVO_4 sample. However, the surface of these Co-doped BiVO_4 sample (Fig. 3b) was much rougher than those of the bare BiVO_4 sample and covered amorphous particles. Consistent with the results of the XRD patterns, the 0.3Co-BVO (Fig. S3C†) and 0.5Co-BVO (Fig. S3D†) samples mostly had amorphous nanoparticles because of the presence of the mixture containing BiVO_4 , Bi_2O_3 , $\text{Co}_2\text{V}_2\text{O}_7$, and $\text{Co}_3\text{V}_2\text{O}_8$. Also, as presented in Fig. 4, the EDS-Mapping analysis of Bi, V, O, and Co in the 0.2Co-BVO was both in line with the aforementioned XPS results and indicative of uniform distribution over the BiVO_4 surface. The TEM images of 0.2Co-BVO sample (Fig. S4†) also confirms that the crystal of 0.2Co-BVO sample was not homogeneous with different shapes and sizes.

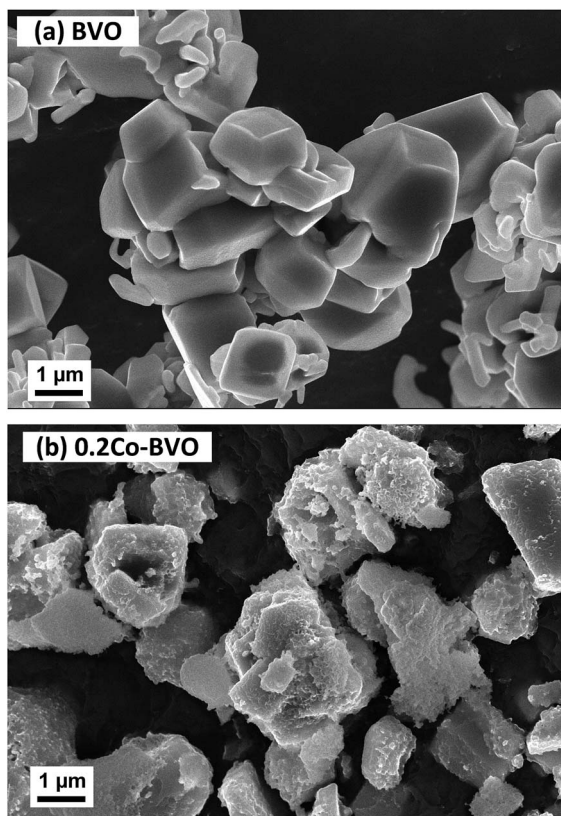


Fig. 3 SEM images of the (a) BVO and (b) 0.2Co-BVO samples.

3.3 Optical absorption properties

UV-vis DRS spectra of the $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ samples are displayed in Fig. 5A. All samples demonstrated intensive absorption bands in the visible light region with the absorption edges of 550–600 nm, which ascribed to the electron transfer from the valence band (VB) to the conduction band (CB). The direct band gap energy (E_g , eV) of the as-synthesized photocatalysts were derived from the tangent in the Tauc plots when plotting the $(\alpha h\nu)^2$ function with respect to $h\nu$ (α , h , and ν are the absorption coefficient, Planck's constant, and incident light frequency, respectively) as shown in Fig. 5B.^{13,30,40,41} The E_g values of the $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ samples are presented in Table 1. Accordingly, the E_g appeared to be slightly declining with increasing Co molar ratio. This behavior indicated the slightly narrowed BiVO_4 band gap, which could be due to Co incorporation and the introduction of an energy level (E_f) near the top of the VB in the forbidden band gap (Fig. 11), caused by substitution of cobalt ions to Bi^{3+} in BiVO_4 .³³

The separation and transfer of photoinduced charges in $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ semiconductors could be clarified by PL spectra as presented in Fig. 6. For the undoped BiVO_4 catalyst, the emission peak at an excitation wavelength of 340 nm was observed at around 478 nm. For 0.2Co-BVO, the absence of an emission peak indicated that Co incorporation, due to the increased electron mobility, could prevent photogenerated electron-hole pairs from recombining. As a result, it is apparent that the photocatalytic activity of the $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$

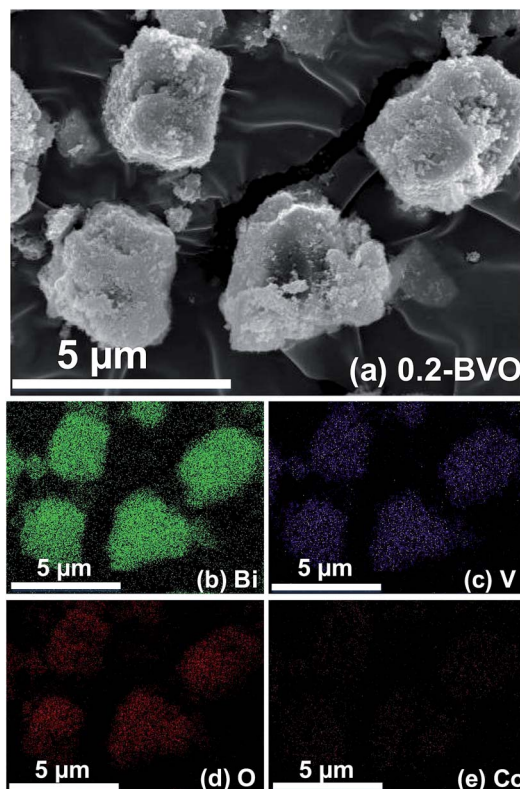


Fig. 4 Element mapping images of 0.2Co-BVO sample: SEM image (a), Bi element (b), V element (c), O element (d) and Co element (e).

samples was improved due to the efficient separation and transfer of photoinduced charges.

3.4 Photocatalytic performance

To demonstrate the improvement in photocatalytic performance of Co-doped BiVO_4 catalysts in comparison with the bare BiVO_4 , we conducted the photodegradation of MB under white LED light irradiation using the pristine BiVO_4 and Co-doped BiVO_4 samples. Fig. 7 shows UV-vis absorption spectra of MB solution isolated from a reaction mixture containing 0.2Co-BVO catalyst, water, and MB. As shown in Fig. 7, the intensity of the absorption spectra decreased after the first 20 min in the dark and then remained unchanged after 60 min in the dark, indicating the adsorption-desorption equilibrium between the surface of the 0.2Co-BVO sample and the MB molecules. When visible light was provided, the intensity of the absorption peak (664 nm) dramatically declined, and the position of this peak tended to shift toward a shorter wavelength. These signs were attributed to the photodegradation of MB molecules, which was caused by 0.2Co-BVO catalyst.

Fig. 8A displays the removal efficiency of MB by the pristine BiVO_4 and Co-doped BiVO_4 samples. In comparison with the bare BiVO_4 samples, Co-doped BiVO_4 catalysts exhibited significantly improved photocatalytic activity after 180 min of irradiation in response to the incorporation of Co. The degradation rate of 0.2Co-BVO sample reached its highest value (about 98%) while the figure was 72% for the bare BiVO_4

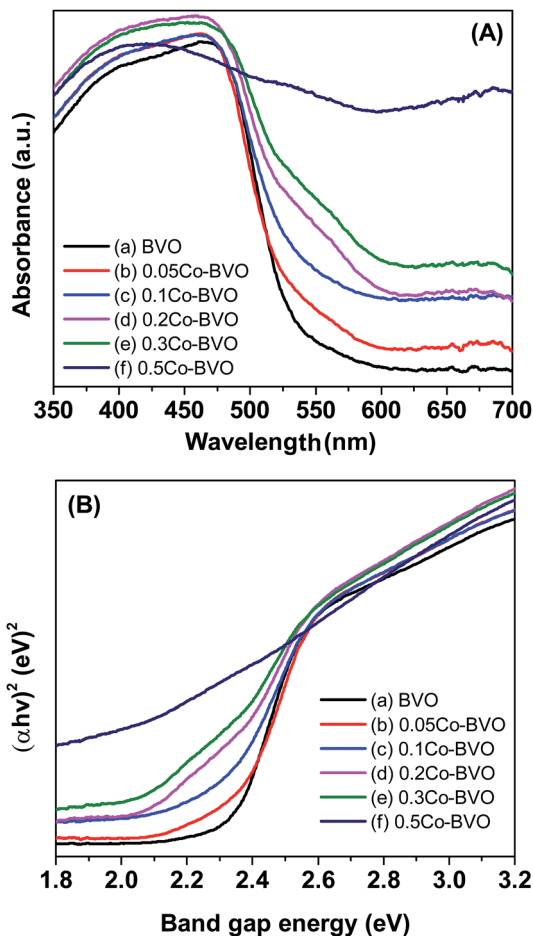


Fig. 5 UV-vis DRS spectra (A) and band gap energy (B) of the pristine BiVO₄ (a), 0.05Co-BVO (b), 0.1Co-BVO (c), 0.2Co-BVO (d), 0.3Co-BVO (e), and 0.5Co-BVO (f).

sample. However, when further increasing Co content (0.3Co-BVO and 0.5Co-BVO samples), the degradation rate witnessed a sharp decline. Such an outcome could be due to the formation

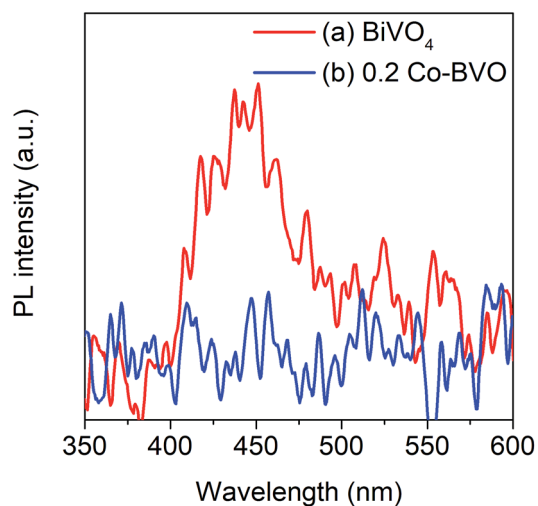


Fig. 6 Room temperature PL spectra of the pristine BiVO₄ (a) and 0.2Co-BVO (b).

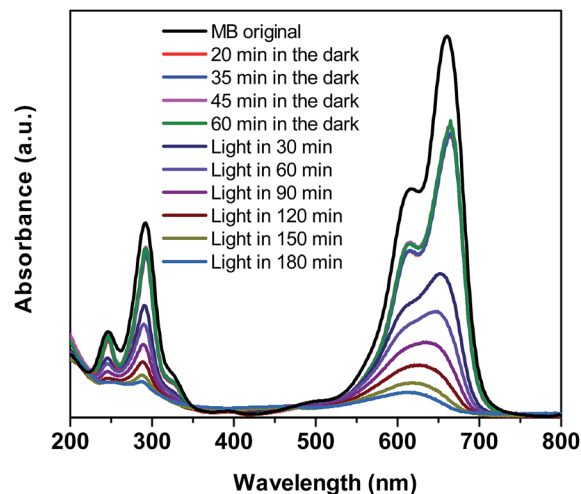


Fig. 7 UV-vis absorption spectra of MB solution separated from catalyst suspensions during illumination using 0.2Co-BVO.

of Bi₂O₃, Co₂V₂O₇, and Co₃V₂O₈ phase in 0.3Co-BVO and 0.5Co-BVO samples as described by the above XRD analysis. In addition, we employed the pseudo-first-order kinetic equation ($\ln(C/C_0)$

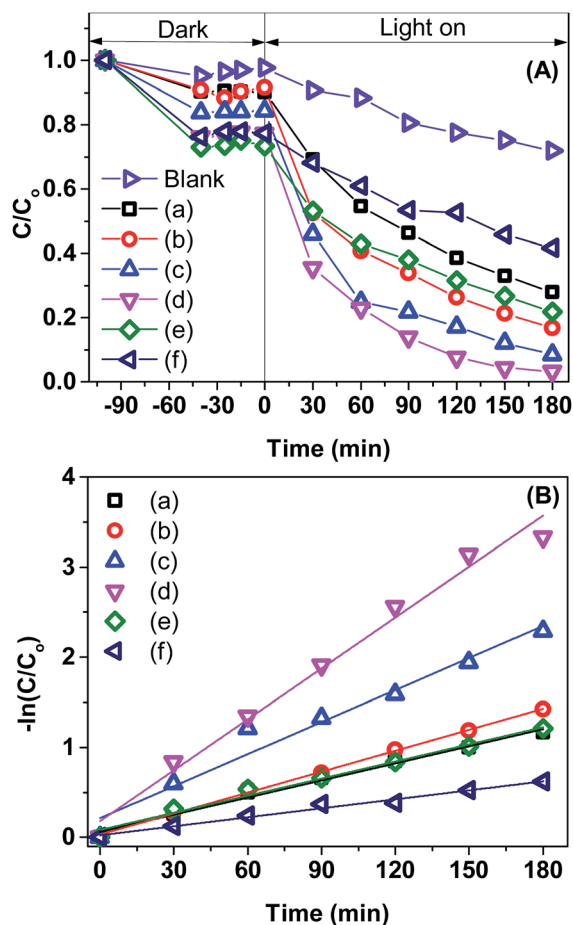


Fig. 8 Photocatalytic degradation of MB over BiVO₄ samples (A): BiVO₄ (a), 0.05Co-BVO (b), 0.1Co-BV (c), 0.2Co-BV (d), 0.3Co-BV4 (e), and 0.5Co-BV (f) and plots of $\ln(C_0/C)$ versus irradiation time representing the fit using a pseudo-first-order reaction rate (B).

$C_0 = kt$; C_0 and C are the concentration of MB at 0 min and t min of irradiation, respectively) to fit the degradation of MB (Fig. 8B) and obtain the reaction rate constant (k , 10^{-3} min^{-1}) of the as-synthesized samples.²⁸ The k values of $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ samples are presented in Table 1, indicating that the 0.2Co-BVO sample exhibited superior photocatalytic performance.

A comparison table for photocatalytic MB degradation performance of the as-synthesized Co-doped BiVO_4 with other materials reported in the literature was also conducted (Table S1†). As shown in Table S1,† the degradation rate of MB over Co-doped BiVO_4 samples was equal to or higher than those reported from previous studies, which further indicated that Co-doped BiVO_4 could be a promising photocatalyst for the degradation of organic dyes.

To investigate the stability of the 0.2Co-BVO catalyst, five cycling photocatalytic tests were conducted by collecting and reusing the same photocatalyst. The result (Fig. S5†) exhibited an only negligible decrease in photocatalytic activity after five runs, which may have been caused by an incomplete collection of the catalyst after each runs. Moreover, no obvious differences were observed in the XRD results of the 0.2Co-BVO catalyst before/after five runs (Fig. S6†), suggesting the excellent stability and reusability of the 0.2Co-BVO catalyst.

3.5 Photodegradation mechanism

To explore the mechanism for the reactive species responsible for MB degradation over 0.2Co-BVO, radical trapping experiments in the photodegradation were performed (Fig. 9). The experimental steps were similar to the above photocatalytic activity test; however, radical scavengers were added to the reaction solution at the beginning of light irradiation. Employed radical scavengers included *tert*-butanol (TBA), ammonium oxalate monohydrate (AO), 1,4-benzoquinone (BQ) and potassium dichromate ($\text{K}_2\text{Cr}_2\text{O}_7$) for hydroxyl radicals ($\cdot\text{OH}$), hole (h^+), superoxide (O_2^-), and electron (e^-). Following the addition of TBA and AO, the photodegradation rate showed a marked decline. Meanwhile, the reduction in the

photodegradation rate is expected in the presence of BQ and $\text{K}_2\text{Cr}_2\text{O}_7$. This observation implies that the presence of two dominant active oxidative species, namely $\cdot\text{OH}$ and h^+ , directly oxidized MB molecules adsorbed on the surface of the 0.2Co-BVO catalyst. Similarly, trapping experiments of photocatalytic degradation of MB over the pure BiVO_4 sample (Fig. S7†) also indicated that $\cdot\text{OH}$ and h^+ are the main active oxidative species. Therefore, the substitution of cobalt ions to Bi^{3+} in the BiVO_4 did not influence the dominant oxidative species.

The essential role of $\cdot\text{OH}$ radicals in the photocatalytic processes was further proved by the photoluminescence spectra of $\text{H}_2\text{BDC-OH}$ (Fig. 10). As displayed in Fig. 10, the intensity of $\text{H}_2\text{BDC-OH}$ caused by Co-BVO samples was enhanced as compared to the intensity of $\text{H}_2\text{BDC-OH}$ caused by the bare BiVO_4 sample. The highest intensity of $\text{H}_2\text{BDC-OH}$ caused by the 0.2Co-BVO sample corresponded to the peak photocatalytic activity due to the increased formation of $\cdot\text{OH}$ radicals on the surface of this sample.

The complete mechanism for photodegradation over Co-doped BiVO_4 catalyst was suggested based on prior investigations^{3,6,42} and illustrated in Fig. 11. The process included four steps: (i) the generation of photo-excited electrons (e^-) from the VB into the CB of $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ when visible LED light was provided; (ii) the corresponding holes (h^+) leaving the VB; (iii) the photo-excited electrons (e^-) being trapped by the acceptor defects (Co^{2+}); (iv) the holes (h^+) being transferred to the surface to oxidize the H_2O and OH^- to $\cdot\text{OH}$ radicals which played an essential role in the photocatalytic oxidation process. In comparison with the pristine BiVO_4 samples, the fabrication of Co-doped BiVO_4 catalyst could encourage the efficient separation and transfer of photoinduced charges, corresponding to production of a significant amount of $\cdot\text{OH}$ radicals for degradation of MB. As a result of this success, the photocatalytic performance of BiVO_4 was significantly enhanced.

In addition, as described above, the photocatalytic performance of the $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ samples were not linear to the Co

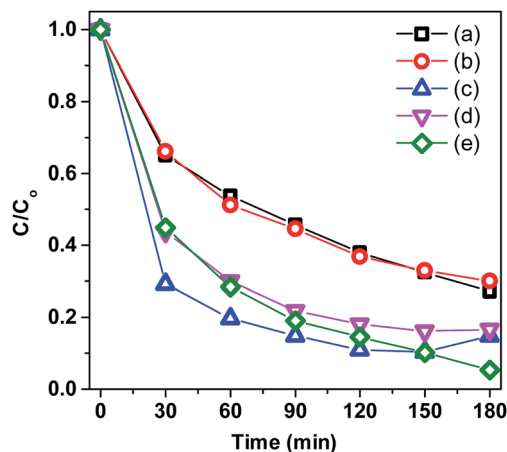


Fig. 9 Trapping experiments of photocatalytic degradation of MB over 0.2Co-BVO with the presence of scavengers: TBA (a), AO (b), BQ (c) and $\text{K}_2\text{Cr}_2\text{O}_7$ (d), and without the presence of scavenger (e).

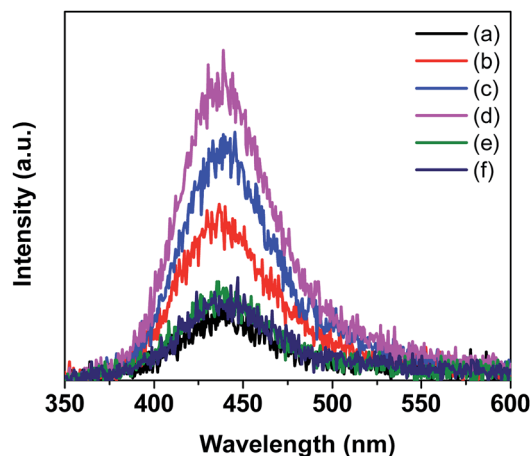


Fig. 10 Photoluminescence spectrum of $\text{H}_2\text{BDC-OH}$ that formed upon the reaction between the $\cdot\text{OH}$ radicals produced by the pristine BiVO_4 (a), 0.05Co-BVO (b), 0.1Co-BVO (c), 0.2Co-BVO (d), 0.3Co-BVO (e) and 0.5Co-BVO (f) and H_2BDC .

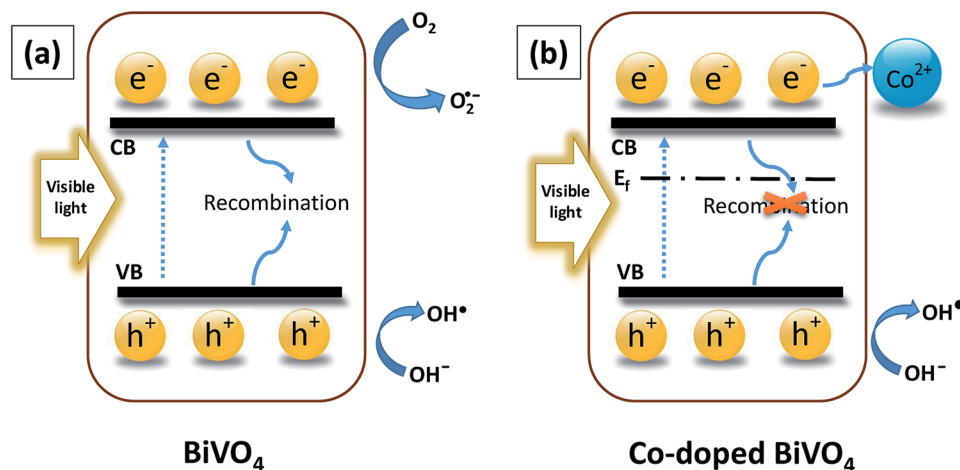


Fig. 11 An entire mechanism for photocatalytic degradation: (a) BiVO_4 and (b) Co-doped BiVO_4 .

ion contents, but tended to increase first and then steadily decline. This downward trend could be attributed to the formation of Bi_2O_3 , $\text{Co}_2\text{V}_2\text{O}_7$, and $\text{Co}_3\text{V}_2\text{O}_8$ as a result of the excessive doping Co ion content. Moreover, the excessively doped Co ion content could lead to the fast recombination of electron–hole pairs.⁴³ Wang *et al.* also indicated the excessive doping metal content could occupy the space charge and hinder the penetration depth of irradiation into BiVO_4 as result of fast recombination of electron–hole pairs and poor photoactivity.⁴⁴

Our work first reported Co-doped BiVO_4 materials synthesized according to the chemical formula $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ ($0.05 < x < 0.5$). Based on the XRD, Raman, and XPS results, as well as the previous studies, we could conclude that the substitution of Co^{2+} ions for Bi^{3+} sites in BiVO_4 , resulting in the improvement of the photocatalytic activity of BiVO_4 .

4 Conclusion

Monoclinic scheelite phase $\text{Bi}_{1-x}\text{Co}_x\text{VO}_{4+\delta}$ have been successfully synthesized by the substitution of Co ions for Bi sites in BiVO_4 using a hydrothermal procedure. As revealed by the crystal structural and optical absorption characterizations, the substitution of Co^{2+} for Bi^{3+} in the BiVO_4 lattice was achieved; therefore, Co-doped BiVO_4 exhibited the slight narrow band gap and the reduction of charge recombination. Co-doped BiVO_4 catalysts show a higher removal efficiency and mineralization degree of MB than that of the pristine BiVO_4 under white LED light illumination. Based on the characterization results, an entire mechanism for photocatalytic degradation of MB over Co-doped BiVO_4 catalyst was proposed, in which $\cdot\text{OH}$ and h^+ are the predominant active oxidative species for directly oxidizing MB molecules adsorbed on the surface of the catalyst. In addition, the stability of catalyst was also investigated.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This research is funded by Vietnam National Foundation for Science and Technology Development (NAFOSTED) under grant number 104.05-2017.315.

Notes and references

- 1 Y. Ma, H. Jiang, X. Zhang, J. Xing and Y. Guan, *Ceram. Int.*, 2014, **40**, 16485–16493.
- 2 D. Wang, H. Jiang, X. Zong, Q. Xu, Y. Ma, G. Li and C. Li, *Chem.–Eur. J.*, 2011, **17**, 1275–1282.
- 3 Y. Hu, D. Li, F. Sun, H. Wang, Y. Weng, W. Xiong and Y. Shao, *RSC Adv.*, 2015, **5**, 54882–54889.
- 4 M. Hofmann, M. Rainer, S. Schulze, M. Hietschold and M. Mehring, *ChemCatChem*, 2015, **7**, 1357–1365.
- 5 M. Hojamberdiev, G. Zhu, Z. C. Kadirova, J. Han, J. Liang, J. Zhou, X. Wei and P. Liu, *Mater. Chem. Phys.*, 2015, **165**, 188–195.
- 6 Y. Zhang, Y. Guo, H. Duan, H. Li, C. Sun and H. Liu, *Phys. Chem. Chem. Phys.*, 2014, **16**, 24519–24526.
- 7 G. Xi and J. Ye, *Chem. Commun.*, 2010, **46**, 1893.
- 8 H. Li, K. Yu, X. Lei, B. Guo, H. Fu and Z. Zhu, *J. Phys. Chem. C*, 2015, **119**, 22681–22689.
- 9 L. Zhang, D. Chen and X. Jiao, *J. Phys. Chem. B*, 2006, **110**, 2668–2673.
- 10 L. Ren, L. Jin, J.-B. Wang, F. Yang, M.-Q. Qiu and Y. Yu, *Nanotechnology*, 2009, **20**, 115603.
- 11 L. Zhou, W. Wang, L. Zhang, H. Xu and W. Zhu, *J. Phys. Chem. C*, 2007, **111**, 13659–13664.
- 12 L. Ren, L. Ma, L. Jin, J.-B. Wang, M. Qiu and Y. Yu, *Nanotechnology*, 2009, **20**, 405602.
- 13 B. Wang, L. Guo and T. He, *RSC Adv.*, 2016, **6**, 30115–30124.
- 14 D. T. Nguyen and S.-S. Hong, *J. Nanosci. Nanotechnol.*, 2017, **17**, 2690–2694.
- 15 M. Y. A. Khan, M. Zahoor, A. Shaheen, N. Jamil, M. I. Arshad, S. Z. Bajwa, N. A. Shad, R. Butt, I. Ali, M. Z. Iqbal, A. Wu,

- G. Nabi, S. Hussain, T. Mahmood, I. Aslam and W. S. Khan, *Mater. Res. Bull.*, 2018, **104**, 38–43.
- 16 M. Wang, H. Zheng, J. Liu, D. Dong, Y. Che and C. Yang, *Mater. Sci. Semicond. Process.*, 2015, **30**, 307–313.
- 17 J. Q. Li, Z. Y. Guo, H. Liu, J. Du and Z. F. Zhu, *J. Alloys Compd.*, 2013, **581**, 40–45.
- 18 W. Yang, G. Tan, H. Ren, L. Zhang, C. Zhao and A. Xia, *RSC Adv.*, 2015, **5**, 7324–7329.
- 19 B. Zhou, X. Zhao, H. Liu, J. Qu and C. P. Huang, *Sep. Purif. Technol.*, 2011, **77**, 275–282.
- 20 Z. Jiang, Y. Liu, T. Jing, B. Huang, X. Zhang, X. Qin, Y. Dai and M.-H. Whangbo, *J. Phys. Chem. C*, 2016, **120**, 2058–2063.
- 21 T. Liu, G. Tan, C. Zhao, C. Xu, Y. Su, Y. Wang, H. Ren, A. Xia, D. Shao and S. Yan, *Appl. Catal., B*, 2017, **213**, 87–96.
- 22 L. Chen, J. Wang, D. Meng, Y. Xing, C. Wang, F. Li, Y. Wang and X. Wu, *Mater. Lett.*, 2015, **147**, 1–3.
- 23 L. Ma, W. H. Li and J. H. Luo, *Mater. Lett.*, 2013, **102–103**, 65–67.
- 24 S. Y. Chae, C. S. Lee, H. Jung, O.-S. Joo, B. K. Min, J. H. Kim and Y. J. Hwang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 19780–19790.
- 25 H. Yuan, J. Liu, J. Li, Y. Li, X. Wang, Y. Zhang, J. Jiang, S. Chen, C. Zhao and D. Qian, *J. Colloid Interface Sci.*, 2015, **444**, 58–66.
- 26 M. Xie, Y. Feng, X. Fu, P. Luan and L. Jing, *J. Alloys Compd.*, 2015, **631**, 120–124.
- 27 A. Petala, R. Bontemps, A. Spartatouille, Z. Frontistis, M. Antonopoulou, I. Konstantinou, D. I. Kondarides and D. Mantzavinos, *Catal. Today*, 2017, **280**, 122–131.
- 28 D. T. Nguyen and S. S. Hong, *Top. Catal.*, 2017, **60**, 782–788.
- 29 W. Luo, J. Wang, X. Zhao, Z. Zhao, Z. Li and Z. Zou, *Phys. Chem. Chem. Phys.*, 2013, **15**, 1006–1013.
- 30 S. Gu, W. Li, F. Wang, H. Li and H. Zhou, *Catal. Sci. Technol.*, 2016, **6**, 1870–1881.
- 31 C. Regmi, Y. K. Kshetri, T.-H. Kim, R. P. Pandey and S. W. Lee, *Mol. Catal.*, 2017, **432**, 220–231.
- 32 C. Regmi, T.-H. Kim, S. K. Ray, T. Yamaguchi and S. W. Lee, *Res. Chem. Intermed.*, 2017, **43**, 5203–5216.
- 33 B. Zhang, H. Zhang, Z. Wang, X. Zhang, X. Qin, Y. Dai, Y. Liu, P. Wang, Y. Li and B. Huang, *Appl. Catal., B*, 2017, **211**, 258–265.
- 34 B. Zhou, X. Zhao, H. Liu, J. Qu and C. P. Huang, *Appl. Catal., B*, 2010, **99**, 214–221.
- 35 Y. Geng, P. Zhang, N. Li and Z. Sun, *J. Alloys Compd.*, 2015, **651**, 744–748.
- 36 Y. Cheng, H. Wang, Y. Zhu, F. Liao, Z. Li and J. Li, *J. Mater. Sci.: Mater. Electron.*, 2014, **26**, 1268–1274.
- 37 G. Yang, H. Cui, G. Yang and C. Wang, *ACS Nano*, 2014, **8**, 4474–4487.
- 38 J. Yang, H. Liu, W. N. Martens and R. L. Frost, *J. Phys. Chem. C*, 2010, **114**, 111–119.
- 39 R. Liu, J. Ren, D. Zhao, J. Ning, Z. Zhang, Y. Wang, Y. Zhong, C. Zheng and Y. Hu, *Inorg. Chem. Front.*, 2017, **4**, 2045–2054.
- 40 M. Yan, Y. Yan, Y. Wu, W. Shi and Y. Hua, *RSC Adv.*, 2015, **5**, 90255–90264.
- 41 M. Guo, Y. Wang, Q. He, W. Wang, W. Wang, Z. Fu and H. Wang, *RSC Adv.*, 2015, **5**, 58633–58639.
- 42 S. Nikam and S. Joshi, *RSC Adv.*, 2016, **6**, 107463–107474.
- 43 M. Wang, P. Guo, T. Chai, Y. Xie, J. Han, M. You, Y. Wang and T. Zhu, *J. Alloys Compd.*, 2017, **691**, 8–14.
- 44 Y. Wang, F. Liu, Y. Hua, C. Wang, X. Zhao, X. Liu and H. Li, *J. Colloid Interface Sci.*, 2016, **483**, 307–313.