

RESEARCH

Open Access



Effect of staining beverages and bleaching on optical properties of a CAD/CAM nanohybrid and nanoceramic restorative material

Shaymaa Elsaka^{1,2*}, Salwa Taibah² and Amr Elnaghy³

Abstract

Background: The purpose of this study was to evaluate the optical properties of nanohybrid Grandio (GR) and nanoceramic Lava Ultimate (LU) CAD/CAM restorative materials subjected to different beverage solutions and subsequently bleached.

Methods: Five groups of each restorative material (n = 20/group, shade A2-high translucent) were immersed in distilled water, coffee, tea, cola, and ginger for one week. Changes in whiteness index, translucency parameter, and color changes of the specimens were evaluated. The data of color measurements after staining, bleaching, and the residual differences were statistically analyzed using Kruskal–Wallis and Mann–Whitney U tests at the significance level of $P < 0.05$.

Results: LU and GR revealed the highest differences in whiteness index after coffee staining ($P < 0.001$). GR revealed lower translucency parameter differences after staining with coffee than LU ($P = 0.007$). There were no significant differences in translucency changes between LU and GR after staining with tea, cola, or ginger ($P > 0.05$). LU revealed significantly greater color changes than GR after staining ($P < 0.001$).

Conclusions: LU nanoceramic CAD/CAM restorative material revealed higher color changes than GR nanohybrid material. Staining beverage solutions had a distinct influence on the optical properties of the tested CAD/CAM restorative materials.

Keywords: Beverages, Bleaching, CAD/CAM, Optical properties, Restorative materials

Background

The advancement of computer-aided design and computer-aided manufacturing (CAD/CAM) technologies have made indirect esthetic restorations easier to create [1]. In recent years, CAD/CAM composite resin blocks for tooth-colored restorations have been produced [2, 3]. Because of their resin composition, CAD/CAM composites blocks have improved edge stability, which allows for

a better milling process with less thickness, polishability, and intraoral reparability [4–8].

Lava Ultimate (LU; 3M ESPE; St Paul, MN, USA) is a machinable CAD/CAM resin nanoceramic restorative material [8]. It had been reported that the resin nanoceramic blocks have adequate fracture toughness and esthetic properties than commonly used composite resin materials [1, 9, 10]. In addition, the mechanical properties of resin nanoceramic materials were found to be close to those of enamel [9, 10]. Grandio blocs (GR; VOCO, Cuxhaven, Germany), a nanohybrid machinable CAD/CAM restorative material, are made up of inorganic fillers that are incorporated in

*Correspondence: shaymanaghy@mans.edu.eg

¹ Department of Dental Biomaterials, Faculty of Dentistry, Mansoura University, Mansoura 35516, Egypt

Full list of author information is available at the end of the article



a polymer matrix and include 86 wt% inorganic fillers [8, 11]. It had been reported that GR nanohybrid material revealed enhanced mechanical properties [12] and improved clinical performance [13].

The clinical esthetic stability of CAD/CAM composite resin restorations affects their performance and success in oral environments [14]. Different composition and microstructures of different CAD/CAM restorations influence their color stability [14]. Discoloration of restorative materials might be due to extrinsic or intrinsic factors [15]. The cause of external staining of restorative materials is due to adsorption or absorption of the colorants from exogenous sources [16]. Different solutions have been reported to discolor the composite resin restorations including coffee, tea, sport drinks, and chlorohexidine [17].

Various attempts have been performed to enhance the affected esthetic appearance of resin restorations [18]. One of the most common treatments for eliminating stains from resin restorations is dental bleaching [18, 19]. Hydrogen peroxide and carbamide peroxide with different concentrations are the most common bleaching agents used in dentistry [20]. The success of treatment depends on the type and concentration of bleaching agent, type of stain, the application procedure, and microstructure and composition of resin restorations [15, 18, 20].

There is no data available about the effect of staining beverages and bleaching agents on the optical properties of CAD/CAM Grandio nanohybrid restorative material. The aim of this study was to evaluate the color change, translucency, and whiteness index of CAD/CAM nanohybrid and nanoceramic restorative materials subjected to staining beverages and subsequently bleached. The null hypothesis of the study was that there was no difference in stain susceptibility, translucency changes, and whiteness index between the two CAD/CAM restorative materials; GR nanohybrid and

LU nanoceramic, after staining with beverage solutions and bleaching.

Methods

Sample size

GPower v3.1.3 software (University of Düsseldorf; Düsseldorf, Germany) was used to calculate the sample size. According to the power assessment, a sample size of 20 specimens per subgroup meets the constraints of 0.05 and power = 0.85.

Specimen preparation

The CAD/CAM restorative materials assessed in the present study are presented in Table 1. The CAD/CAM blocks were sectioned into 12 × 14 × 1.5 mm specimens using a low-speed diamond saw (ISOMET 1000, Buehler, Lake Bluff, IL, USA). Then, the specimens were polished (Buehler, Lake Bluff, IL, USA) using a series of silicon carbide papers P600 to P1200. The specimens were cleaned ultrasonically in distilled water. The final thickness of the specimens was verified with a digital micrometer (Mitutoyo IP65, Mitutoyo Corp., Japan) to ensure a uniform thickness of 1.5 ± 0.15 mm after polishing [17, 18]. A fine carbide bur mounted on a low-speed handpiece was used to mark the side used during color measurements for each specimen [18].

Grouping of specimens

The study design is presented in Fig. 1. Five groups of each restorative material were immersed in 200 mL of distilled water (control medium), coffee, tea, cola, and ginger for one week (24 h/day) [17]. The container holding the staining solutions was sealed with paraffin to minimize evaporation [17]. For the coffee group, the specimens were stored in a 37 °C coffee (Nescafe Classic, Nestle Middle East, United Arab Emirates) solution where a 3.6 g of coffee was dissolved in 300 mL of boiling distilled water. After 10 min of stirring, the solution was filtered through a filter paper. Specimens in the tea group were stored in a 37 °C tea (Twinings; Twinings Company, Poland) solution that was prepared by immersing 2 tea-bags (2 × 2 g) into 300 mL of boiling distilled water for 10 min. For the cola group, the specimens were stored in 37 °C cola (Coca-Cola; Coca-Cola Co, Riyadh, Saudi Arabia) [21]. For the ginger group, the specimens were stored in a 37 °C ginger (Ginger; Wadi Al Nahil, Egypt) solution that was prepared by immersing 2 packets (2 × 2 g) into 300 mL of boiling distilled water for 10 min. Distilled water (Health Aqua, Alexandria, Egypt) was used as the control medium. The pH of staining solutions was measured using a pH meter (pH/mV/Temp Meter Set, SP-2100; Suntex, Taipei, Taiwan) and determined to be 5.5, 5, 2.6, 8, and 6.9 for coffee, tea, cola, ginger,

Table 1 CAD/CAM restorative materials used in the study

Product	Composition*	Shade**	Code
Grandio Blocs (VOCO, Cuxhaven, Germany)	86 wt% nanohybrid fillers, 14% UDMA + DMA	A2 HT	GR
Lava Ultimate (3M ESPE; St. Paul, MN, USA)	20 nm silica filler, 4–11 nm zirconia filler, aggregated zirconia/silica microcluster, 80 wt% Bis-GMA, UDMA, TEGDMA, Bis-EMA	A2 HT	LU

* Bis-GMA, bisphenol-A-glycidyl methacrylate; UDMA, urethane dimethacrylate; TEGDMA, triethyleneglycol dimethacrylate; Bis-EMA, bisphenol-A-polyethyleneglycol diether dimethacrylate; DMA, dimethacrylate

** HT, high translucency

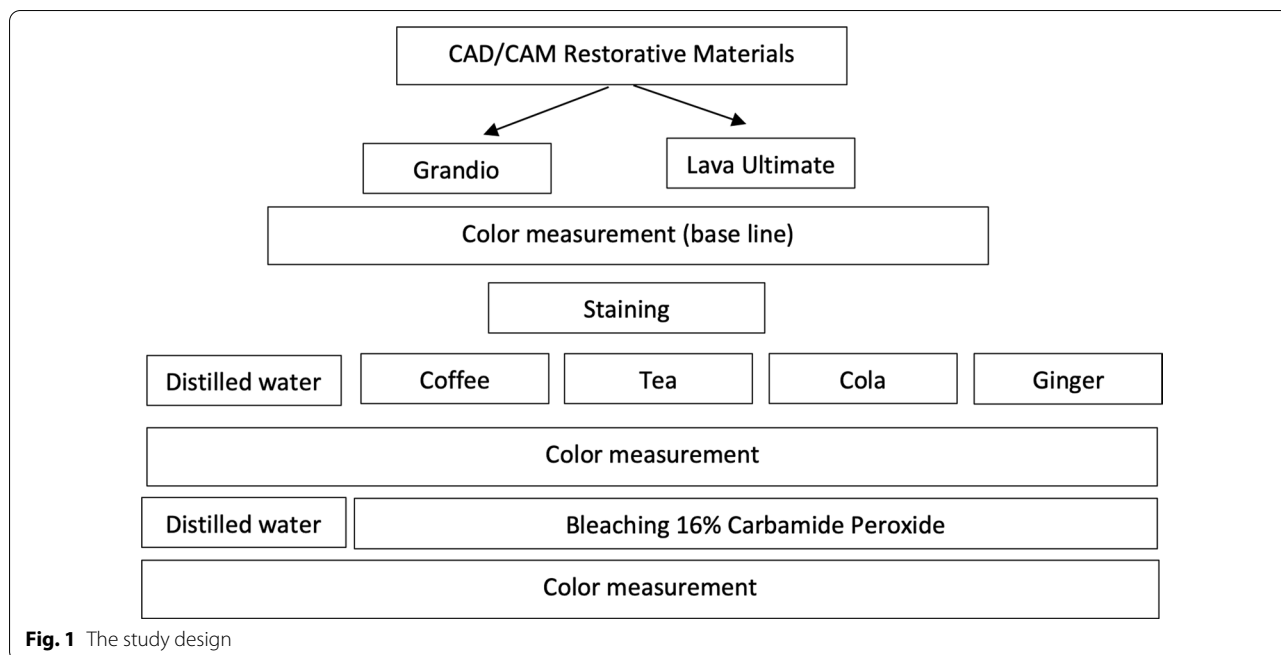


Fig. 1 The study design

and distilled water; respectively. Each medium contains twenty specimens for each restorative material. After that, the specimens were stored in distilled water for 24 h at 37 °C. Every two days, the solutions were replaced to avoid the probability of bacteria and yeast contamination [1, 17]. Then, the specimens were rinsed with distilled water for 10 s and gently dried before being measured. According to the manufacturer’s recommendations, an at-home bleaching treatment utilizing 16% carbamide peroxide gel (Perfect Bleach, VOCO) was applied 2 h/day for 14 consecutive days. The specimens were bleached by applying an approximately 1 mm (0.168 mL) thick gel layer. After treatment, the specimens were rinsed with distilled water for 60 s to remove the bleaching material and then stored individually in distilled water at 37 °C between bleaching sessions [15, 18].

Color measurements

A spectrophotometer (VITA Easyshade Advance 4.0, VITA Zahnfabrik, Bad Säckingen, Germany) with D65 illuminant light was used to measure the color of specimens on black, white, and gray backgrounds. Each specimen was measured three times and at three separate times: before staining (baseline; i, after staining; st, and after the bleaching method; bl), with CIELAB parameters recorded at each time point. The spectrophotometer was calibrated before each measurement [18, 20].

The following formula was used to compute the translucency parameter (TP) [22, 23]:

$$TP = \sqrt{(L_B^* - L_W^*)^2 + (a_B^* - a_W^*)^2 + (b_B^* - b_W^*)^2}$$

where L_B^* , a_B^* , b_B^* are color parameters recorded on a black background and L_W^* , a_W^* , b_W^* are CIELAB parameters recorded on white background [18].

The changes in translucency after staining (ΔTP_{st-i}), bleaching (ΔTP_{bl-st}), and between the initial and final situation (ΔTP_{bl-i}) were calculated [18].

The whiteness index (WI_D) was calculated after staining (WI_{Dst}) and after bleaching (WI_{Dbl}) based on CIELAB parameters according to the following equation [24]:

$$WI_D = 0511L^* - 2.324a^* - 1.100b^*$$

where L^* , a^* , b^* are color parameters recorded on gray background.

The variations in whiteness index (WI_D) were calculated after staining (WI_{Dst-i}), bleaching (WI_{Dbl-st}), and between the initial and final condition (WI_{Dbl-i}) [18].

For gray background, differences in color changes after staining (E_{00st-i}), bleaching ($E_{00bl-st}$), and between initial and final condition (E_{00bl-i}) were determined using the CIEDE2000 (E_{00}) equation as follows [15, 18]:

$$\Delta E_{00} = \left[(\Delta L/k_L \cdot S_L)^2 + (\Delta C/k_C \cdot S_C)^2 + (\Delta H/k_H \cdot S_H)^2 + RT \cdot (\Delta C/k_C \cdot S_C) \times (\Delta H/k_H \cdot S_H) \right]^{1/2}$$

The values of k_L , k_C , and k_H in the CIEDE2000 were set to 1 [15].

The data of color measurements were statistically analyzed using SPSS 22.0 software (IBM Corp., Armonk, NY, USA). The Kolmogorov–Smirnov test was used to analyze the normality of data. As a result of the normality test, the Kruskal–Wallis and Mann–Whitney U tests were used to analyze the data of ΔWI_D , ΔTP , and ΔE_{00} . The level of statistical significance was set at $P < 0.05$.

Results

Mean and standard deviations of differences in $\Delta WI_{D_{st-i}}$, $\Delta WI_{D_{bl-st}}$ and $\Delta WI_{D_{bl-i}}$ are presented in Table 2. LU and GR revealed the highest differences in $\Delta WI_{D_{st-i}}$ after coffee staining ($P < 0.001$). In addition, after coffee staining and bleaching, LU and GR showed the highest differences in $\Delta WI_{D_{bl-st}}$ than the other staining solutions ($P < 0.001$). The differences in the $\Delta WI_{D_{st-i}}$ values after staining for LU and GR from the highest to the lowest were as

follows: coffee > tea > cola > ginger > distilled water. The differences in the $\Delta WI_{D_{bl-st}}$ values after bleaching for LU and GR from the highest to the lowest were as follows: coffee > tea > ginger > cola > distilled water.

Mean and standard deviations of differences in ΔTP_{st-i} , ΔTP_{bl-st} and ΔTP_{bl-i} are presented in Table 3. In general, TP was significantly higher before staining and bleaching ($P < 0.001$). GR revealed lower TP differences (ΔTP_{st-i}) after staining with coffee than LU ($P = 0.007$). There were no significant differences in ΔTP_{st-i} between LU and GR after staining with tea, cola, or ginger ($P > 0.05$). The greatest TP differences after bleaching were observed for LU stained with coffee (0.46 ± 0.06). Staining with ginger revealed a higher residual translucency difference for LU and GR (-0.36 ± 0.06 , -0.25 ± 0.04 ; respectively).

The higher color changes were recorded for LU and GR CAD/CAM restorative materials due to coffee staining (Fig. 2, Table 4). Both LU and GR showed color changes above the acceptability threshold of 1.8 due to staining. However, GR revealed color changes below the acceptability threshold after bleaching for tea, cola, and ginger groups. LU revealed significantly greater color changes than GR after staining ($P < 0.001$). The greatest

Table 2 Mean differences and standard deviations of whiteness indexes after staining ($\Delta WI_{D_{st-i}}$), bleaching ($\Delta WI_{D_{bl-st}}$), and the residual difference compared to baseline ($\Delta WI_{D_{bl-i}}$)

Staining solutions	CAD/CAM restorative materials	
	LU	GR
$\Delta WI_{D_{st-i}}$		
Distilled water	-0.06 ± 0.01^{Aa}	-0.05 ± 0.02^{Ba}
Coffee	-8.75 ± 1.33^{Ab}	-7.91 ± 1.02^{Bb}
Tea	-4.12 ± 0.96^{Ac}	-3.37 ± 0.86^{Bc}
Cola	-3.04 ± 0.49^{Ac}	-3.08 ± 0.39^{Ac}
Ginger	-2.18 ± 0.25^{Ad}	-2.19 ± 0.27^{Ad}
$\Delta WI_{D_{bl-st}}$		
Distilled water	-0.51 ± 0.06^{Aa}	-0.46 ± 0.07^{Ba}
Coffee	5.23 ± 1.22^{Ab}	4.83 ± 0.89^{Ab}
Tea	2.41 ± 0.42^{Ac}	2.09 ± 0.59^{Bc}
Cola	1.62 ± 0.28^{Ad}	1.74 ± 0.26^{Bc}
Ginger	2.24 ± 0.44^{Ac}	1.17 ± 0.23^{Bd}
$\Delta WI_{D_{bl-i}}$		
Distilled water	-0.45 ± 0.08^{Aa}	-0.49 ± 0.08^{Aa}
Coffee	-2.51 ± 1.04^{Ab}	-2.48 ± 0.7^{Ab}
Tea	-1.65 ± 0.41^{Ab}	-1.09 ± 0.24^{Bc}
Cola	-1.62 ± 0.21^{Ab}	-1.41 ± 0.18^{Bd}
Ginger	-0.64 ± 0.09^{Ac}	-1.06 ± 0.19^{Bc}

Mean values represented with different superscript lowercase letter (column) are significantly different ($P < 0.05$)


Mean values represented with different superscript uppercase letter (row) are significantly different ($P < 0.05$)

Table 3 Mean differences and standard deviations of translucency parameter (TP) after staining (ΔTP_{st-i}), bleaching (ΔTP_{bl-st}), and the residual difference compared to baseline (ΔTP_{bl-i})

Staining solutions	CAD/CAM restorative materials	
	LU	GR
ΔTP_{st-i}		
Distilled water	-0.15 ± 0.03^{Aa}	-0.13 ± 0.03^{Aa}
Coffee	-0.62 ± 0.07^{Ab}	-0.56 ± 0.07^{Bb}
Tea	-0.51 ± 0.04^{Accd}	-0.53 ± 0.06^{Ab}
Cola	-0.42 ± 0.04^{Ae}	-0.39 ± 0.05^{Ac}
Ginger	-0.55 ± 0.07^{Abc}	-0.54 ± 0.07^{Ab}
ΔTP_{bl-st}		
Distilled water	-0.09 ± 0.03^{Aa}	-0.13 ± 0.02^{Ba}
Coffee	0.46 ± 0.06^{Ab}	0.33 ± 0.04^{Bbc}
Tea	0.38 ± 0.05^{Abc}	0.37 ± 0.05^{Ab}
Cola	0.16 ± 0.04^{Ad}	0.17 ± 0.04^{Ad}
Ginger	0.19 ± 0.04^{Ad}	0.31 ± 0.04^{Bc}
ΔTP_{bl-i}		
Distilled water	-0.24 ± 0.03^{Aa}	-0.22 ± 0.03^{Aa}
Coffee	-0.17 ± 0.02^{Ab}	-0.24 ± 0.04^{Ba}
Tea	-0.14 ± 0.03^{Ab}	-0.13 ± 0.03^{Ab}
Cola	-0.26 ± 0.05^{Aa}	-0.22 ± 0.04^{Ba}
Ginger	-0.36 ± 0.06^{Ac}	-0.25 ± 0.04^{Ba}

Mean values represented with different superscript lowercase letter (column) are significantly different ($P < 0.05$)

Mean values represented with different superscript uppercase letter (row) are significantly different ($P < 0.05$)

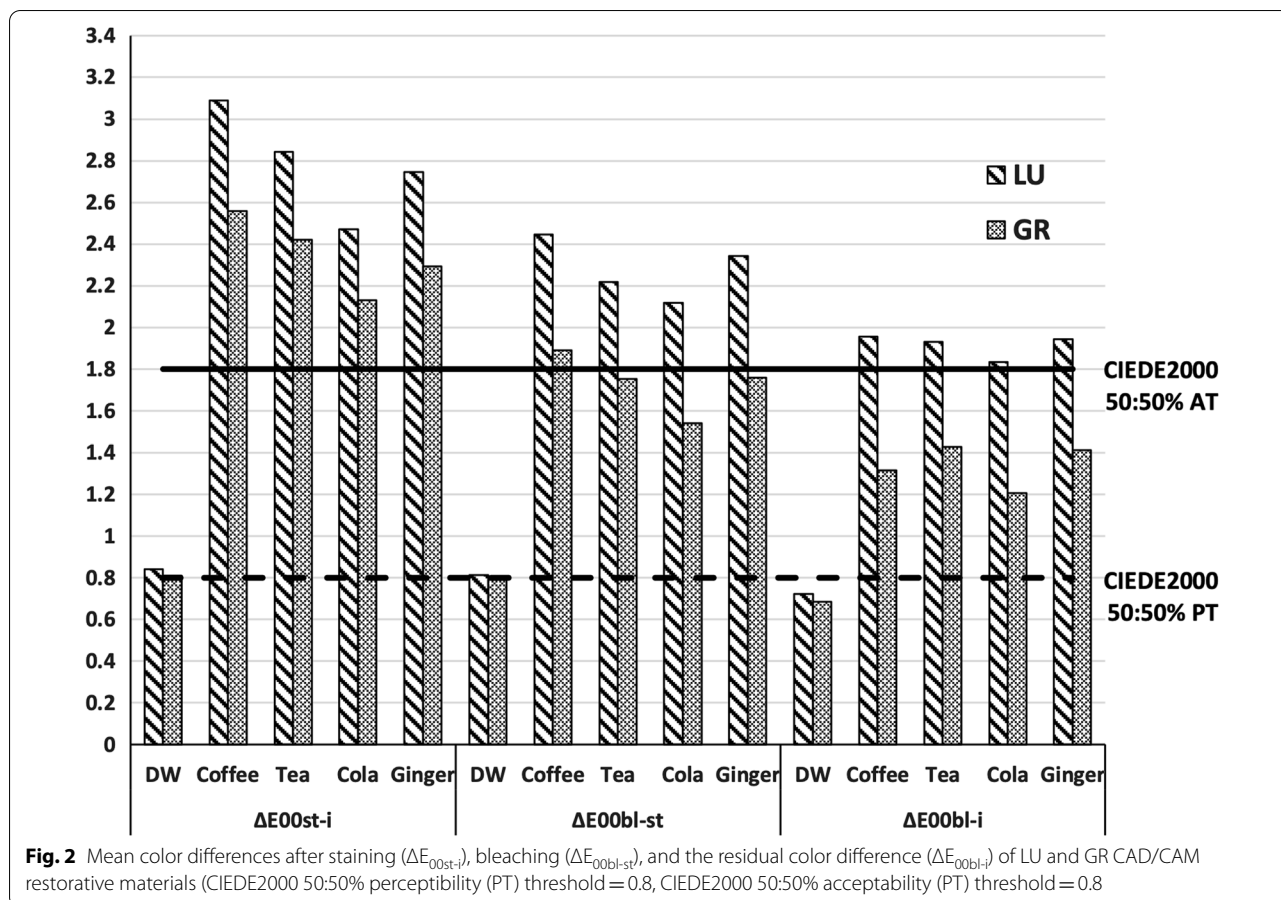

color changes caused by bleaching were recorded for LU stained with coffee (2.44 ± 0.34).

Discussion

It is important to evaluate the optical properties of newly developed CAD/CAM restorative materials for expecting the durability of the esthetic characteristic of restorations [14]. The consumption of different daily beverages exposes teeth and restorations to staining, which might affect the esthetic properties of restorative materials [14, 25]. Due to esthetics demand, bleaching treatment became a routine practice for the patients and throughout the bleaching process, the existing restorations are exposed to bleaching agent [20]. Superficial staining with beverages can be removed by bleaching [18, 26]. However, if the discoloration includes deeper layers, bleaching is no longer effective, and replacement of restoration should be considered [18].

In the present study, the effects of different beverages solutions and bleaching on the optical properties of CAD/CAM GR nanohybrid and LU nanoceramic restorative materials were evaluated. Based on the findings of the present study, the null hypothesis was

rejected as there were significant differences in stain susceptibility, translucency changes, and whiteness index between GR and LU CAD/CAM restorative materials after staining with beverage solutions and bleaching.

The immersion period for staining the specimens was 7 days as the composites absorb considerable staining within the first week of exposure [17, 18]. This in vitro immersion time is equivalent to seven months of clinical aging in vivo [18, 27]. The thickness of the specimens was 1.5 mm as this was the recommended minimum thickness for anterior and posterior bonded restorations [17]. In the present study, 16% carbamide peroxide at-home bleaching agent was utilized which corresponds to 6% hydrogen peroxide. It has been reported that 10% carbamide peroxide (corresponds to 3.5% hydrogen peroxide) has no significant differences in bleaching efficiency over composite resins [18, 19].

The color difference between tested materials was evaluated by CIEDE2000 as it was proven to be more closely related to visual perception than CIELAB [18, 28]. The analysis of the color difference results has to be correlated to the perceptibility (PT) and acceptability

Table 4 Mean color differences and standard deviations after staining (ΔE_{00st-i}), bleaching ($\Delta E_{00bl-st}$), and the residual difference compared to baseline (ΔE_{00bl-i})

Staining solutions	CAD/CAM restorative materials	
	LU	GR
ΔE_{00st-i}		
Distilled water	0.84 ± 0.06 ^{Aa}	0.81 ± 0.08 ^{Aa}
Coffee	3.09 ± 0.18 ^{Ab}	2.56 ± 0.41 ^{Bb}
Tea	2.84 ± 0.38 ^{Abc}	2.42 ± 0.26 ^{Bb}
Cola	2.47 ± 0.39 ^{Ad}	2.13 ± 0.17 ^{Bc}
Ginger	2.74 ± 0.35 ^{Ac}	2.29 ± 0.34 ^{Bbc}
$\Delta E_{00bl-st}$		
Distilled water	0.81 ± 0.08 ^{Aa}	0.79 ± 0.08 ^{Aa}
Coffee	2.44 ± 0.34 ^{Ab}	1.89 ± 0.53 ^{Bb}
Tea	2.22 ± 0.26 ^{Abc}	1.75 ± 0.46 ^{Bc}
Cola	2.12 ± 0.19 ^{Ac}	1.54 ± 0.41 ^{Bc}
Ginger	2.34 ± 0.29 ^{Abc}	1.76 ± 0.53 ^{Bbc}
ΔE_{00bl-i}		
Distilled water	0.72 ± 0.06 ^{Aa}	0.68 ± 0.05 ^{Aa}
Coffee	1.95 ± 0.28 ^{Ab}	1.31 ± 0.25 ^{Bb}
Tea	1.93 ± 0.36 ^{Ab}	1.43 ± 0.37 ^{Bbc}
Cola	1.83 ± 0.33 ^{Ab}	1.21 ± 0.19 ^{Bc}
Ginger	1.94 ± 0.37 ^{Ab}	1.41 ± 0.29 ^{Bbc}

Mean values represented with different superscript lowercase letter (column) are significantly different ($P < 0.05$)

Mean values represented with different superscript uppercase letter (row) are significantly different ($P < 0.05$)

thresholds (AT) for obtaining the actual clinical impact of results [18]. In dentistry, the 50:50% PT and 50:50% AT are 0.8 and 1.8; respectively [29]. In the present study, GR revealed color changes below the perceptibility threshold of 0.8 after bleaching ($\Delta E_{00bl-st}$) and in the residual color difference (ΔE_{00bl-i}) in distilled water. However, LU showed color changes below perceptibility threshold of 0.8 only in the residual color difference (ΔE_{00bl-i}) in distilled water.

LU and GR CAD/CAM restorative materials revealed higher color changes after immersion in beverage solutions compared with distilled water. It has been reported that discoloration is mostly caused by the organic matrix [18]. Composite-resin based restorative materials have increased percentages of the organic matrix which is correlated to the lower color stability [18]. LU showed greater stain susceptibility than GR. The difference in chemical composition and structural organization of tested materials is the main cause of color changes after staining and bleaching [18]. LU has Bis-GMA monomers in the composition which is more hydrophilic compared to UDMA or TEGDMA [18, 26]. However, GR has 14% UDMA with no Bis-GMA. The final color is perceivable differently compared with the initial state (after staining

and bleaching), indicating that the bleaching procedure did not neutralize completely the discoloration [18]. Bleaching agents degrade the material structure by affecting the organic structure and pigments [20]. Consequently, it could be postulated color alterations of LU and GR after bleaching might be correlated to pigments degradation and surface structure of the specimens [20]. Additionally, staining and bleaching caused greater alteration of the WI_D for LU than GR. Bleaching treatments have been shown to have a considerable effect on the WI_D of human teeth both in vivo and in vitro [30]. Consequently, in clinical practice, the impact of bleaching on the resin matrix of CAD/CAM restorative materials in the oral cavity where teeth and restorative materials are present should be considered [20].

Color changes in coffee and tea were greater than in cola, ginger, and distilled water following immersion. This finding is in accordance with previous studies [14, 17]. The higher capability of coffee and tea to stain resin-containing materials might be due to the potential of yellow pigments to enter the microstructures of these materials [14]. Tea contains a higher amount of tannins, while coffee contains a lot of chromogens [17]. Tannins increase the capacity of chromogens to bind to the surfaces of materials, promoting staining [17]. The low polarity of coffee and tea solutions may also contribute to the color change by allowing pigments to penetrate deeper into the resin matrix [14, 27]. It has been shown that solutions with a pH of 4 to 6 have a higher possibility for infiltrating resin compounds [31]. In the current study, the pH of coffee and tea was 5.5 and 5; respectively, which could be an enhancing factor [14, 31]. Tea contains oxalic, malic, and citric acid, whereas coffee has about 22 types of acids with citric acid, acetic acid, malic acid, and other high molecular weight acids accounting for the majority of the acidity [17]. On the other hand, cola staining solution has higher acidity than coffee and tea; but lower staining ability on LU and GR. Cola drinks, as compared to other dark beverages, have been shown to cause minimal staining of resinous materials [14, 32, 33]. Also, because phosphate ions have been found to have a similar impact on tooth surfaces, the presence of phosphate ions in cola drinks may prevent resin surface breakdown [14, 34]. The ginger solution prepared in this study had an alkaline pH (8). LU showed more color changes with the ginger solution than GR. This finding could be contributed to the differences in the compositions between LU and GR.

Translucency and opacity are material properties that change over time and can be influenced by water sorption, chemical degradation, and microstructures of restorative materials [18, 35]. The passage of light through the material is referred to as translucency, and it can give the restoration a natural appearance [36].

Differences in material translucency have been contributed to the various chemical composition, grain size, crystalline structure, porosity, additives, flaws, and surface texture of the materials [37]. In the present study, the possible alteration in the translucency of CAD/CAM restorative materials after being exposed to beverages solutions and bleaching was evaluated in order to analyze the optical changes of the materials to enable material selection to conform to different clinical circumstances [14, 38]. The translucency of LU and GR was decreased after staining and bleaching procedures. The translucency decreased because of the absorption of stain on the surface of the specimens [18]. The weakening of the resin/filler bond and subsequent penetration of colorants into the resin matrix has been attributed to the decrease in translucency [17, 39]. The scatter of visible light passing through the materials after staining can also be affected by the differing refractive indexes of the filler particles and resin of LU and GR [17]. Similar to color changes, the highest translucency changes were observed after exposure to coffee. LU revealed higher translucency changes than GR after staining in coffee. However, there was no significant difference in translucency changes between LU and GR after staining with tea, cola, and ginger. Same finding after bleaching except that there was a difference in translucency changes between LU and GR for coffee and ginger groups.

One of the limitations of the present study is that only 1.5 mm thickness and A2 high translucency shaded specimens were evaluated. Further studies should be performed using different shades, thickness, translucency, and aging to give reliable recommendations for practitioners. In addition, the effect of staining and bleaching agent on the microstructures and mechanical properties of the tested CAD/CAM restorative materials should be further investigated.

Conclusion

Within the limitations of the study, it can be concluded that LU nanoceramic CAD/CAM restorative material revealed higher color changes than GR nanohybrid material. Staining beverage solutions had a marked effect on the optical properties of tested CAD/CAM restorative materials.

Abbreviations

AT: Acceptability thresholds; Bis-GMA: Bisphenol-A-glycidyl methacrylate; Bis-EMA: Bisphenol-A-polyethylene glycol diether dimethacrylate; CAD/CAM: Computer-aided design and computer-aided manufacturing; DMA: Dimethacrylate; E_{00st-i} : Color changes after staining; $E_{00bl-st}$: Color changes after bleaching; E_{00bl-i} : Color changes between initial and final condition; GR: Grandio; LU: Lava ultimate; PT: Perceptibility; UDMA: Urethane dimethacrylate; TEGDMA: Triethyleneglycol dimethacrylate; HT: High translucency; TP: Translucency

parameter; ΔTP_{st-i} : Changes in translucency after staining; ΔTP_{bl-st} : Changes in translucency after bleaching; ΔTP_{bl-i} : Changes in translucency between initial and final situation; WI_D : Whiteness index; WI_{Dst-i} : Whiteness index after staining; WI_{Dbl-st} : Whiteness index after bleaching; WI_{Dbl-i} : Whiteness index between the initial and final condition.

Acknowledgements

Not applicable.

Authors' contributions

SE, ST, and AE were responsible for the concept, design, and implementation of the work, analyzed the participant data, and interpretation of data. SE and AE were major contributors in writing the manuscript. All authors read and approved the final manuscript.

Funding

Open access funding provided by The Science, Technology & Innovation Funding Authority (STDF) in cooperation with The Egyptian Knowledge Bank (EKB).

Availability of data and materials

The datasets generated and analyzed during the current study are not publicly available due to (ownership of data) but are available from the corresponding author on reasonable request.

Declarations

Ethics approval and consent to participate

Not applicable.

Consent for publication

Not applicable.

Competing interests

The authors declare that they have no competing interests.

Author details

¹Department of Dental Biomaterials, Faculty of Dentistry, Mansoura University, Mansoura 35516, Egypt. ²Department of Restorative Dental Science, Vision Colleges, Jeddah, Saudi Arabia. ³Department of Endodontics, Faculty of Dentistry, Mansoura University, Mansoura, Egypt.

Received: 25 January 2022 Accepted: 17 March 2022

Published online: 27 March 2022

References

- Barutcuoglu C, Bilgili D, Barutcuoglu K, Dundar A, Buyukkaplan US, Yilmaz B. Discoloration and translucency changes of CAD-CAM materials after exposure to beverages. *J Prosthet Dent.* 2019;122(3):325–31. <https://doi.org/10.1016/j.prosdent.2019.01.009>.
- Edelhoff D, Beuer F, Schweiger J, Brix O, Stimmelmayer M, Guth JF. CAD/CAM-generated high-density polymer restorations for the pretreatment of complex cases: a case report. *Quintessence Int.* 2012;43(6):457–67.
- Stawarczyk B, Krawczuk A, Ilie N. Tensile bond strength of resin composite repair *in vitro* using different surface preparation conditionings to an aged CAD/CAM resin nanoceramic. *Clin Oral Investig.* 2015;19(2):299–308. <https://doi.org/10.1007/s00784-014-1269-3>.
- Miyazaki T, Hotta Y. CAD/CAM systems available for the fabrication of crown and bridge restorations. *Aust Dent J.* 2011;56(Suppl 1):97–106. <https://doi.org/10.1111/j.1834-7819.2010.01300.x>.
- Magne P, Schlichting LH, Maia HP, Baratieri LN. *In vitro* fatigue resistance of CAD/CAM composite resin and ceramic posterior occlusal veneers. *J Prosthet Dent.* 2010;104(3):149–57. [https://doi.org/10.1016/S0022-3913\(10\)60111-4](https://doi.org/10.1016/S0022-3913(10)60111-4).
- Reymus M, Roos M, Eichberger M, Edelhoff D, Hickel R, Stawarczyk B. Bonding to new CAD/CAM resin composites: influence of air abrasion

- and conditioning agents as pretreatment strategy. *Clin Oral Investig*. 2019;23(2):529–38. <https://doi.org/10.1007/s00784-018-2461-7>.
7. Alp G, Subaşı MG, Johnston WM, Yılmaz B. Effect of different resin cements and surface treatments on the shear bond strength of ceramic-glass polymer materials. *J Prosthet Dent*. 2018;120(3):454–61. <https://doi.org/10.1016/j.prosdent.2017.12.016>.
 8. Elsaka SE, Elnaghy AM. Effect of surface treatment and aging on bond strength of composite cement to novel CAD/CAM nanohybrid composite. *J Adhes Dent*. 2020;22(2):195–204. <https://doi.org/10.3290/jjad.a44284>.
 9. Acar O, Yılmaz B, Altıntaş SH, Chandrasekaran I, Johnston WM. Color stainability of CAD/CAM and nanocomposite resin materials. *J Prosthet Dent*. 2016;115(1):71–5. <https://doi.org/10.1016/j.prosdent.2015.06.014>.
 10. Zhi L, Bortolotto T, Krejci I. Comparative in vitro wear resistance of CAD/CAM composite resin and ceramic materials. *J Prosthet Dent*. 2016;115(2):199–202. <https://doi.org/10.1016/j.prosdent.2015.07.011>.
 11. Pfeilschifter M, Preis V, Behr M, Rosentritt M. Edge strength of CAD/CAM materials. *J Dent*. 2018;74:95–100. <https://doi.org/10.1016/j.jdent.2018.05.004>.
 12. Grzebieluch W, Mikulewicz M, Kaczmarek U. Resin composite materials for chairside CAD/CAM restorations: a comparison of selected mechanical properties. *J Healthc Eng*. 2021;2021:8828954. <https://doi.org/10.1155/2021/8828954>.
 13. Rocha Gomes Torres C, Caroline Moreira Andrade A, Valente Pinho Mafetano AP, Stabile de Abreu F, de Souza Andrade D, Cintra Mailart M, et al. Computer-aided design and computer-aided manufacturing indirect versus direct composite restorations: a randomized clinical trial. *J Esthet Restor Dent*. 2021. <https://doi.org/10.1111/jerd.12820>.
 14. Eldwakhly E, Ahmed DRM, Soliman M, Abbas MM, Badrawy W. Color and translucency stability of novel restorative CAD/CAM materials. *Dent Med Probl*. 2019;56(4):349–56. <https://doi.org/10.17219/dmp/111400>.
 15. Tinastepe N, Malkondu O, İscan I, Kazazoglu E. Effect of home and over the contour bleaching on stainability of CAD/CAM esthetic restorative materials. *J Esthet Restor Dent*. 2021;33(2):303–13. <https://doi.org/10.1111/jerd.12604>.
 16. Topcu FT, Sahinkesen G, Yamanel K, Erdemir U, Oktay EA, Ersahan S. Influence of different drinks on the colour stability of dental resin composites. *Eur J Dent*. 2009;3(1):50–6.
 17. Quek SHQ, Yap AUJ, Rosa V, Tan KBC, Teoh KH. Effect of staining beverages on color and translucency of CAD/CAM composites. *J Esthet Restor Dent*. 2018;30(2):E9–17. <https://doi.org/10.1111/jerd.12359>.
 18. Gasparik C, Culic B, Varvara MA, Grecu A, Burde A, Dudea D. Effect of accelerated staining and bleaching on chairside CAD/CAM materials with high and low translucency. *Dent Mater J*. 2019;38(6):987–93. <https://doi.org/10.4012/dmj.2018-335>.
 19. Alharbi A, Ardu S, Bortolotto T, Krejci I. In-office bleaching efficacy on stain removal from CAD/CAM and direct resin composite materials. *J Esthet Restor Dent*. 2018;30(1):51–8. <https://doi.org/10.1111/jerd.12344>.
 20. Öztürk C, Çelik E, Özden AN. Influence of bleaching agents on the color change and translucency of resin matrix ceramics. *J Esthet Restor Dent*. 2020;32(5):530–5. <https://doi.org/10.1111/jerd.12580>.
 21. Guler AU, Yılmaz F, Kulunk T, Guler E, Kurt S. Effects of different drinks on stainability of resin composite provisional restorative materials. *J Prosthet Dent*. 2005;94(2):118–24. <https://doi.org/10.1016/j.prosdent.2005.05.004>.
 22. Johnston WM, Ma T, Kienle BH. Translucency parameter of colorants for maxillofacial prostheses. *Int J Prosthodont*. 1995;8(1):79–86.
 23. Labban N, Al Amri M, Alhijji S, Alnafaiy S, Alfouzan A, Iskandar M, et al. Influence of toothbrush abrasion and surface treatments on the color and translucency of resin infiltrated hybrid ceramics. *J Adv Prosthodont*. 2021;13(1):1–11. <https://doi.org/10.4047/jap.2021.13.1.1>.
 24. Pérez Mdel M, Ghinea R, Rivas MJ, Yebra A, Ionescu AM, Paravina RD, et al. Development of a customized whiteness index for dentistry based on CIELAB color space. *Dent Mater*. 2016;32(3):461–7. <https://doi.org/10.1016/j.dental.2015.12.008>.
 25. Erdemir U, Yildiz E, Eren MM, Ozel S. Surface hardness evaluation of different composite resin materials: influence of sports and energy drinks immersion after a short-term period. *J Appl Oral Sci*. 2013;21(2):124–31. <https://doi.org/10.1590/1678-7757201302185>.
 26. Stawarczyk B, Sener B, Trottmann A, Roos M, Özcan M, Hammerle CH. Discoloration of manually fabricated resins and industrially fabricated CAD/CAM blocks versus glass-ceramic: effect of storage media, duration, and subsequent polishing. *Dent Mater J*. 2012;31(3):377–83. <https://doi.org/10.4012/dmj.2011-238>.
 27. Arocha MA, Basilio J, Llopis J, Di Bella E, Roig M, Ardu S, et al. Colour stainability of indirect CAD-CAM processed composites vs. conventionally laboratory processed composites after immersion in staining solutions. *J Dent*. 2014;42(7):831–8. <https://doi.org/10.1016/j.jdent.2014.04.002>.
 28. Luo MR, Cui G, Rigg B. The development of the CIE 2000 colour-difference formula: CIEDE2000. *Color Res Appl*. 2001;26(5):340–50. <https://doi.org/10.1002/col.1049>.
 29. Paravina RD, Ghinea R, Herrera LJ, Bona AD, Igiel C, Linninger M, et al. Color difference thresholds in dentistry. *J Esthet Restor Dent*. 2015;27(Suppl 1):S1–9. <https://doi.org/10.1111/jerd.12149>.
 30. Tao D, Sun JN, Wang X, Zhang Q, Naeeni MA, Philpotts CJ, et al. In vitro and clinical evaluation of optical tooth whitening toothpastes. *J Dent*. 2017;67S:S25–8. <https://doi.org/10.1016/j.jdent.2017.08.014>.
 31. Borges AL, Costa AK, Saavedra GS, Komori PC, Borges AB, Rode SM. Color stability of composites: effect of immersion media. *Acta Odontol Latinoam*. 2011;24(2):193–9.
 32. Tan BL, Yap AU, Ma HN, Chew J, Tan WJ. Effect of beverages on color and translucency of new tooth-colored restoratives. *Oper Dent*. 2015;40(2):E56–65. <https://doi.org/10.2341/149027-L>.
 33. Mundim FM, Garcia Lda F, Pires-de-Souza FC. Effect of staining solutions and repolishing on color stability of direct composites. *J Appl Oral Sci*. 2010;18(3):249–54. <https://doi.org/10.1590/s1678-77572010000300009>.
 34. Aliping-McKenzie M, Linden RW, Nicholson JW. The effect of Coca-Cola and fruit juices on the surface hardness of glass-ionomers and 'compomers'. *J Oral Rehabil*. 2004;31(11):1046–52. <https://doi.org/10.1111/j.1365-2842.2004.01348.x>.
 35. Lee BS, Huang SH, Chiang YC, Chien YS, Mou CY, Lin CP. Development of in vitro tooth staining model and usage of catalysts to elevate the effectiveness of tooth bleaching. *Dent Mater*. 2008;24(1):57–66. <https://doi.org/10.1016/j.dental.2007.01.012>.
 36. Heffernan MJ, Aquilino SA, Diaz-Arnold AM, Haselton DR, Stanford CM, Vargas MA. Relative translucency of six all-ceramic systems. Part I: core materials. *J Prosthet Dent*. 2002;88(0022-3913 (Print)):10–5.
 37. Kurtulmus-Yılmaz S, Cengiz E, Ongun S, Karakaya I. The effect of Surface treatments on the mechanical and optical behaviors of CAD/CAM restorative materials. *J Prosthodont*. 2019;28(2):e496–503. <https://doi.org/10.1111/jopr.12749>.
 38. Vichi A, Carrabba M, Paravina R, Ferrari M. Translucency of ceramic materials for CEREC CAD/CAM system. *J Esthet Restor Dent*. 2014;26(4):224–31. <https://doi.org/10.1111/jerd.12105>.
 39. Azzopardi N, Moharamzadeh K, Wood DJ, Martin N, van Noort R. Effect of resin matrix composition on the translucency of experimental dental composite resins. *Dent Mater*. 2009;25(12):1564–8. <https://doi.org/10.1016/j.dental.2009.07.011>.

Publisher's Note

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Ready to submit your research? Choose BMC and benefit from:

- fast, convenient online submission
- thorough peer review by experienced researchers in your field
- rapid publication on acceptance
- support for research data, including large and complex data types
- gold Open Access which fosters wider collaboration and increased citations
- maximum visibility for your research: over 100M website views per year

At BMC, research is always in progress.

Learn more biomedcentral.com/submissions

