



Edible films and coatings – Not just packaging materials

Henriette M.C. Azeredo^{a,*}, Caio G. Otoni^b, Luiz Henrique C. Mattoso^a

^a Embrapa Instrumentation, R. 15 de Novembro, 1452, Caixa Postal 741, 13560-970, São Carlos, SP, Brazil

^b Department of Materials Engineering (DEMa), Federal University of São Carlos (UFSCar), Rod. Washington Luís, km 235, 13565-905, São Carlos, SP, Brazil

ARTICLE INFO

Editor Name: Dr. Xing Chen

Keywords:

B
iopolymers
W
ater vapor permeability
Active food packaging
A
ntimicrobial packaging

ABSTRACT

Edible films and coatings (EFC) are macromolecular-based structures forming thin layers that are usually studied as tools to improve food stability, sometimes being considered as parts of both the packaging system and the food itself. However, EFC are not mere packaging materials, and sometimes they do not even play roles related to those of packaging. This graphical review summarizes possible roles of EFC, including primary packaging, keeping water activity gradients between food components, controlling mass transfer on food processing, carrying active components, or serving as sources of sensory appeal. EFC may even be designed in a way that two or more of those roles may be played simultaneously.

1. Introduction

Edible films and coatings (EFC) have been studied as protecting layers to be applied on food products, extending their stability mainly by acting as protecting barriers. Films differ from coatings in that films are stand-alone structures formed separately, while coatings are formed directly onto food surface (Otoni et al., 2017). Fig. 1 presents a schematic comparison of film and coating formation, and examples.

The main component of EFC is an edible biomacromolecule (matrix, binder or binding agent) – usually polysaccharide and/or protein – able to form a continuous and cohesive layer. Moreover, plasticizers (e.g. polyols, sugars) are usually required to reduce brittleness. Sometimes, other components are added with specific purposes, e.g. reinforcement. While the resulting material is a cohesive layer that may benefit food stability, EFC are not usually able to completely substitute conventional fossil-based plastics for packaging applications – in fact, it is not their goal to do so.

First of all, biomacromolecules bear some important limitations when replacing conventional polymers. One of them is that most of them degrade at temperatures close to – usually lower than – their melting points, making the traditional thermal processing methods in the molten state (e.g. extrusion, compression molding, injection molding) challenging and generally unfeasible (Zhao et al., 2020). Therefore, their processing typically requires engineering adaptations or wet processes (based on separation from a solvent) such as casting or regeneration

methods (Azeredo et al., 2014; Otoni et al., 2021). Moreover, biomacromolecules usually lead to limited tensile and barrier properties, implying poor performance for classical packaging applications (Otoni et al., 2021; Zhao et al., 2020). The hydrophilic nature of most biomacromolecules is another drawback, making the films highly permeable to water vapor and sensitive to contact with moist surfaces, thus restricting some applications. Finally, their use is limited by their relatively high cost. Although biomacromolecules may be isolated from cheap and abundant feedstocks such as food losses and waste (Otoni et al., 2021), the isolation processes involve time-consuming and expensive methods.

Moreover, food packaging materials are typically exposed to chemical and biological contaminants along the food distribution chain. Without a package, the food itself would be contaminated, affecting food safety. If edible films were used as substitutes for any food packaging materials, their contamination would make them not suitable to be eaten (thus, no longer edible).

On the other hand, EFC have a peculiar characteristic that classical packaging materials lack: their very edibility (and, sometimes, the sensory appeal that comes with it). Indeed, EFC should be viewed as part of the food itself rather than of packaging (although they may be used as packaging materials for specific applications, as we will show). This graphical review proposes to summarize the main rational functions and applications of EFC.

* Corresponding author.

E-mail address: henriette.azeredo@embrapa.br (H.M.C. Azeredo).

<https://doi.org/10.1016/j.crf.2022.09.008>

Received 31 May 2022; Received in revised form 16 August 2022; Accepted 7 September 2022

Available online 14 September 2022

2665-9271/© 2022 Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

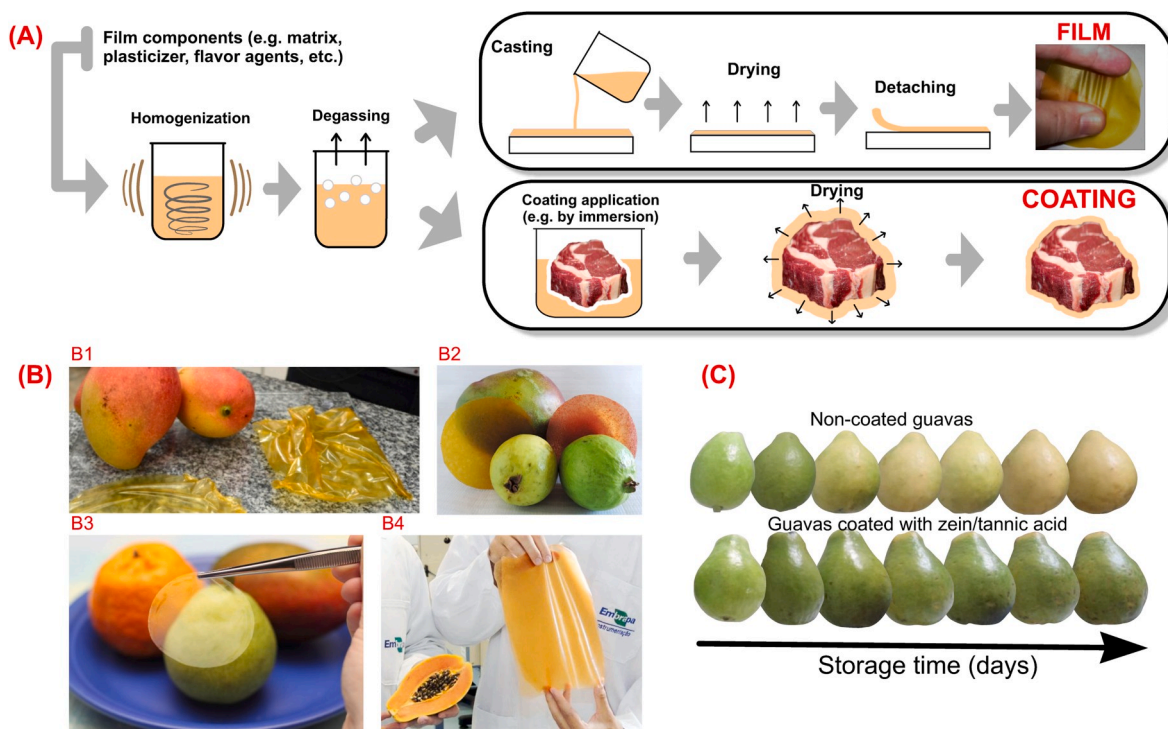


Fig. 1. (A) Typical procedures to form films and coatings, either edible or not (adapted from Otoni et al. (2017), with permission from John Wiley and Sons. (B) Examples of edible films made by our team at Embrapa. B1: mango puree-based films; B2: bacterial cellulose films added with guava and mango puree (Viana et al., 2018); B3: alginate/cashew tree gum film sample; B4: pectin/papaya puree/cinnamaldehyde nanoemulsion film (Otoni et al., 2014). (C) An example of coating on guavas slowing down their ripening process (adapted from Santos et al., 2018, with permission from Elsevier).

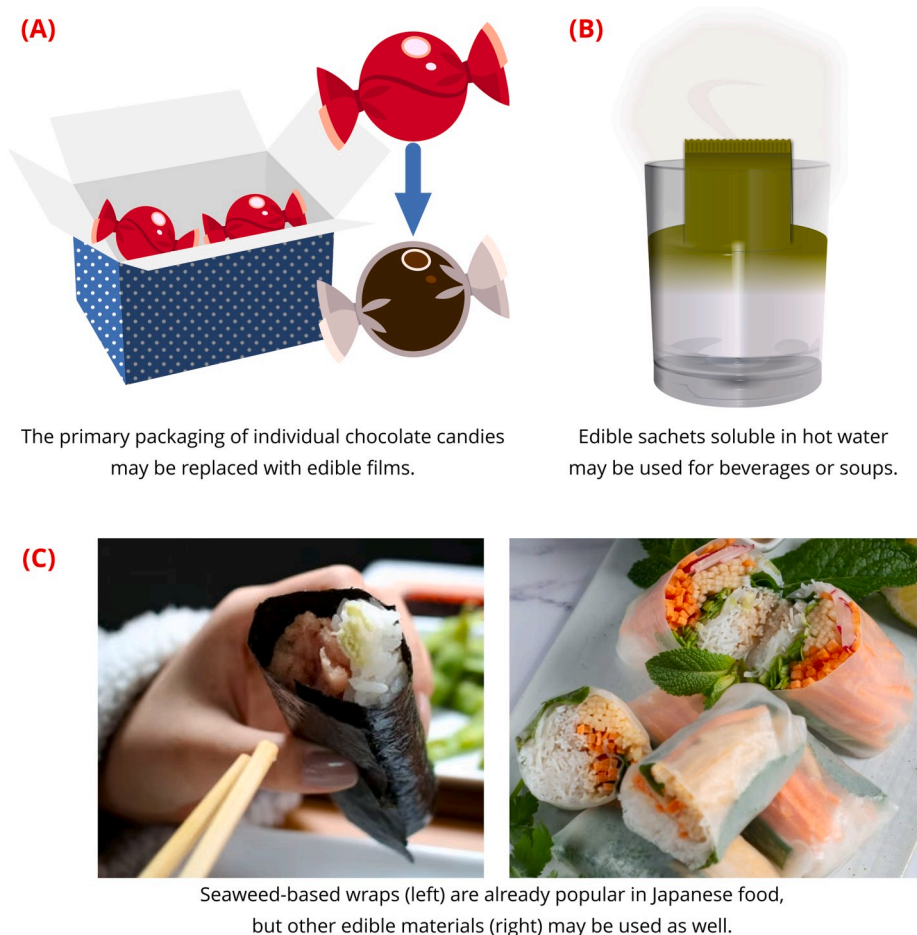


Fig. 2. Showcases of films used as primary food packaging.

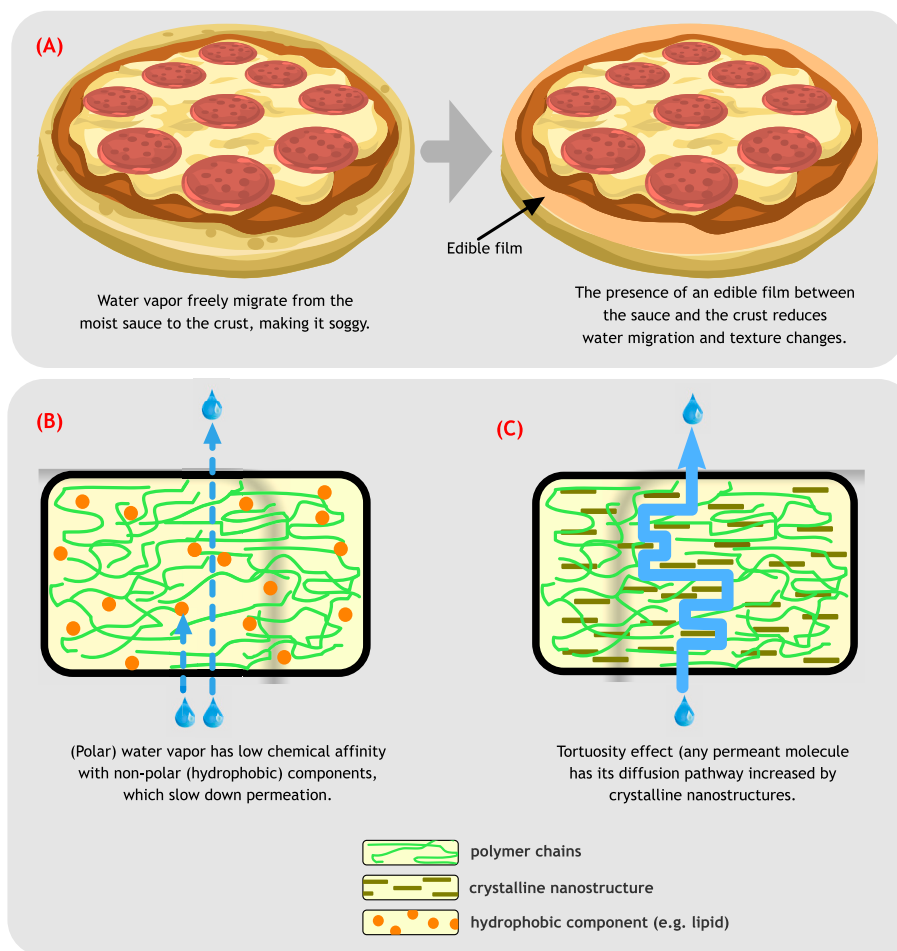


Fig. 3. Edible films as water vapor barrier layers in multicomponent foods. (A): Schematic representation of a film applied between pizza crust and toppings (containing tomato sauce). (B) and (C): Effects of a hydrophobic component and a crystalline nanostructure (respectively) on the water vapor permeability of a film.

2. Primary packaging (when there is a secondary one)

Some food products contain not only a primary packaging (directly in contact with the food), but also a secondary packaging containing the primary one. As an example, some breakfast cereals are packaged into plastic bags (primary packaging) that act mainly as barrier to water vapor (minimizing texture changes) inside a cardboard box (secondary packaging) that, in turn, provides mechanical protection, barrier to light, and communication (printability). Other products are constituted by a number of smaller units, each one inside a primary packaging, with a secondary one grouping them together into a saleable unit and protecting them from contamination, such as in a box of chocolate candies (Fig. 2A). In such cases, EFC should not replace the secondary packaging, but they may replace the primary ones.

Sachets are frequently used as primary packaging for particulate products, which are to be mixed to other food components (e.g. yogurt) or solubilized in water (e.g. beverages and soups) (Fig. 2B). Although sachets are usually non-edible, edible sachets contribute to reduce the waste disposal, and may even carry flavor compounds, contributing for the whole sensory experience. There is also the case of accidental ingestion of loose sachets packaged together with the food itself, the risk of which being eliminated when the sachet and its content are edible. The choice of a sachet matrix should be based on a variety of factors, including heat sealability and seal strength (avoiding premature release of contents), tensile properties (to support the contents), and barrier properties (to minimize chemical degradation of the contents) (Liu et al., 2020). When the sachet is to be solubilized in water, instant water solubility is also desirable (Liu et al., 2020). Moreover, rheological

properties should be taken into account, since viscosity changes may be desirable or not, depending on the intended properties of the final product.

Wraps (e.g. seaweed sheets, Fig. 2C) are not conventionally considered as packaging, since they are loose around the food (not sealed). However, they have functions of a packaging material (i.e. unitizing and facilitating handling, even providing some barrier). Gelatin-pectin edible films have been used as wraps for ricotta cheese, decreasing the moisture loss by the product, thus contributing for keeping its soft texture (Jridi et al., 2020). Pectin/fenucreek gum films with phenolic extracts were used to wrap fresh-cut carrots, extending their microbial shelf life, which was ascribed to the polyphenols (Jayaprada and Umashathy, 2020).

3. Keeping water activity gradients in multicomponent foods

Pizza is a typical example of a multicomponent food product with a high water activity (A_w) gradient between a crispy crust and moist toppings. During storage, water molecules move from the toppings to the crust, which tends to become soggy. Other examples of multicomponent foods that lose texture on storage (or delivery) due to water migration between components include tacos and frozen dessert cones.

EFC between food components with high A_w gradients (Fig. 3A) may reduce water migration, helping to keep the crust as crispy as expected. For this kind of application, the EFC should have low water vapor permeability (WVP). Some approaches may decrease the WVP of EFC, including the incorporation of a hydrophobic component (Fig. 3B) such as rapeseed oil (Galus, 2018) or clove essential oil (Xu et al., 2020), or

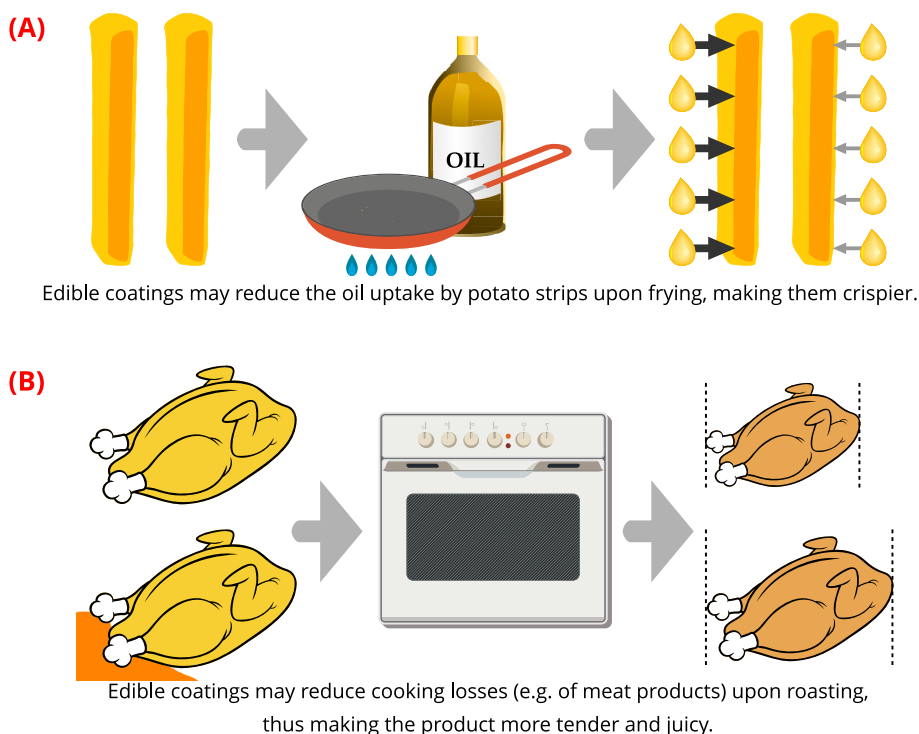


Fig. 4. Examples of edible coatings acting to control mass transfer on food processing.

the addition of hydroxyl-rich compounds such as polyphenols, whose hydroxyl groups may form hydrogen bonds with polar groups of the matrix, limiting their availability for interaction with water (Fabra et al., 2018). The WVP may also be decreased by crystalline nanostructures

(Fig. 3C) such as cellulose nanocrystals (CNC) (Sá et al., 2020) and montmorillonite (Ribeiro et al., 2018). The concomitant addition of tannic acid and CNC sharply reduced the WVP of gelatin films, which was ascribed to both tortuosity effect (increasing the diffusion pathway

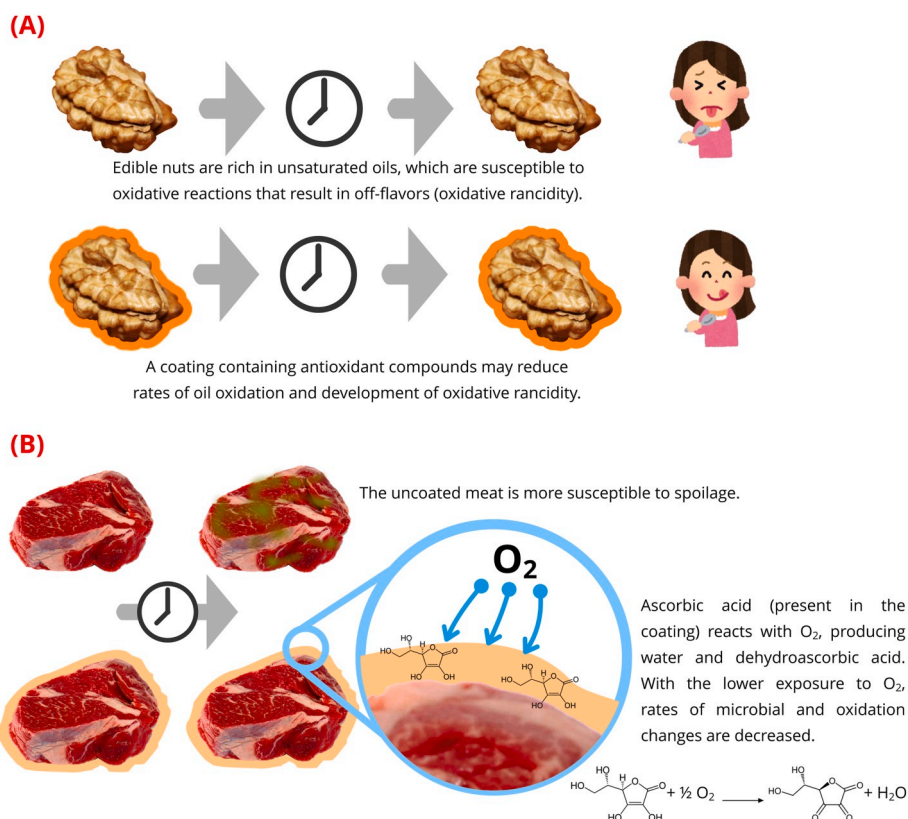


Fig. 5. Schematic representation of edible coatings as potential carriers of (A) antioxidant and (B) oxygen absorbing compounds.

for water vapor) and hydrogen bonds between CNC, tannic acid, and amine groups from gelatin (Leite et al., 2021).

4. Controlling mass transfer on food processing

In deep frying, a food product is immersed in hot oil, which induces water vaporization and oil absorption, among other changes, including starch gelatinization, protein denaturation, and Maillard reaction. Potato fries are popular products of deep frying. While their crispy texture and the flavors from Maillard reaction are highly appreciated, the oil uptake is considered as an undesirable side effect (from both the sensory point of view, since the strips tend to become soggy and less crispy, and also from a health perspective). Coating the strips (previously to frying) with a layer of hydrophilic macromolecules creates a barrier to restrict oil uptake (Lumanlan et al., 2020; Salehi, 2020) (Fig. 4A).

Coatings may also reduce moisture losses on cooking. In meat products, for instance, tenderness and juiciness are important sensory aspects. The texture of cooked meats depends mainly on heat-induced changes in proteins, but it is also affected by cooking losses resulting from water evaporation as well as oil and water dripping on cooking. Cooking losses may be reduced by edible coatings or wraps (Fig. 4B), which has been demonstrated by wrapping chicken meat with caseinate-based films before roasting (Küçüközet and Uslu, 2018).

5. Sources of sensory appeal

EFC may have sensory appealing components such as fruit and/or vegetable purees, which, apart from providing desirable sensory properties, may still contribute for the mechanical properties of the material, since they contain film-forming biopolymers and plasticizing sugars. Edible films have been produced from mango (Oldoni et al., 2021; Viana et al., 2018), papaya (Otoni et al., 2014; Rodríguez et al., 2020), guava (Viana et al., 2018) etc.

Films containing such components may be consumed alone as snacks, being in this context related to the concept of fruit and vegetable leathers, differing from those in that films are thinner (Otoni et al., 2017) and usually containing a biopolymer matrix. EFC with flavorful components may also act as functional materials (e.g. barriers to water vapor in multicomponent foods) while also contributing for the whole sensory experience, e.g. having flavors that are complementary or contrasting to those of the main food components.

6. Carriers of active components

EFC may also be carriers of active components, which are capable of extending food stability by mechanisms different from those related to mere (passive) barrier effects. Active EFC (Fig. 5) may either release compounds that enhance food stability, e.g. antimicrobials and antioxidants, or absorb components that shorten food stability, e.g. ethylene, water vapor and oxygen, as reviewed elsewhere (Mellinas et al., 2016; Salgado et al., 2015).

Moreover, EFC may also incorporate bioactive components that confer health benefits for consumers, such as those containing probiotics (Oliveira et al., 2021; Singh et al., 2019).

7. Final remarks

This graphical review has presented possible roles for EFC, but two or more roles may be played simultaneously. As an example, a film between pizza components (designed to act as a moisture barrier) may be formulated with sensory appealing ingredients in such a way as to enrich the sensory properties of the pizza, and may also contain an antimicrobial compound to extend the microbial stability of susceptible components (e.g. cheese and tomato sauce).

Independently on the roles played by EFC, they should be considered as part of food rather than of the packaging system, although they may

play some packaging-related function (and usually do so). Moreover, their possible roles should ideally be explored in such a way as to maximize their benefits for both food stability (and safety), the sensory experience of the consumer, and including health benefits whenever there is such an opportunity.

Future studies are required to enhance the feasibility of large-scale processing of edible films, as well as to improve the physical performance of the materials while keeping their food-grade character and safety. One of the greatest challenges on EFC is to create biomimetic edible structures that reproduce the mechanical and barrier performance of fruit skins, pursuing the difficult task of mimicking mother nature.

CRediT authorship contribution statement

Henriette M.C. Azeredo: Conceptualization, Writing – original draft. **Caio G. Otoni:** Writing – review & editing. **Luiz Henrique C. Mattoso:** Writing – review & editing.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

The authors acknowledge the financial support of the Nanotechnology Network for Research in Agriculture (Rede AgroNano, EMBRAPA, Brazil). Authors Azeredo and Mattoso also thank the National Council for Scientific and Technological Development (CNPq) for their Research Productivity Fellowships (308777/2021-2 and 304044/2019-9 respectively).

References

- Azeredo, H.M.C., Rosa, M.F., De Sá, M., Souza Filho, M., Waldron, K., 2014. The use of biomass for packaging films and coatings. In: *Advances in Biorefineries: Biomass and Waste Supply Chain Exploitation*. <https://doi.org/10.1533/9780857097385.2.819>.
- Fabra, M.J., Falcó, I., Randazzo, W., Sánchez, G., López-Rubio, A., 2018. Antiviral and antioxidant properties of active alginate edible films containing phenolic extracts. *Food Hydrocolloids* 81, 96–103. <https://doi.org/10.1016/j.foodhyd.2018.02.026>.
- Galus, S., 2018. Functional properties of soy protein isolate edible films as affected by rapeseed oil concentration. *Food Hydrocolloids* 85, 233–241. <https://doi.org/10.1016/j.foodhyd.2018.07.026>.
- Jayaprada, M., Umamathy, M.J., 2020. Preparation and properties of a microfibrillated cellulose reinforced pectin/fenugreek gum biocomposite. *New J. Chem.* 44 (43), 18792–18802. <https://doi.org/10.1039/D0NJ03101A>.
- Jridi, M., Abdelhedi, O., Salem, A., Kechaou, H., Nasri, M., Menchari, Y., 2020. Physicochemical, antioxidant and antibacterial properties of fish gelatin-based edible films enriched with orange peel pectin: wrapping application. *Food Hydrocolloids* 103, 105688. <https://doi.org/10.1016/j.foodhyd.2020.105688>.
- Küçüközet, A.O., Uslu, M.K., 2018. Cooking loss, tenderness, and sensory evaluation of chicken meat roasted after wrapping with edible films. *Food Science and Technology International = Ciencia y Tecnología de Los Alimentos Internacional* 24 (7), 576–584. <https://doi.org/10.1177/1082013218776540>.
- Leite, L.S.F., Pham, C., Bilatto, S., Azeredo, H.M.C., Cranston, E.D., Moreira, F.K., Mattoso, L.H.C., Bras, J., 2021. Effect of tannic acid and cellulose nanocrystals on antioxidant and antimicrobial properties of gelatin films. *ACS Sustain. Chem. Eng.* 9 (25), 8539–8549. <https://doi.org/10.1021/acssuschemeng.1c01774>.
- Liu, C., Huang, J., Zheng, X., Liu, S., Lu, K., Tang, K., Liu, J., 2020. Heat sealable soluble soybean polysaccharide/gelatin blend edible films for food packaging applications. *Food Packag. Shelf Life* 24, 100485. <https://doi.org/10.1016/j.fpsl.2020.100485>.
- Lumanlan, J.C., Fernando, W.M.A.D.B., Jayasena, V., 2020. Mechanisms of oil uptake during deep frying and applications of predrying and hydrocolloids in reducing fat content of chips. *Int. J. Food Sci. Technol.* 55 (4), 1661–1670. <https://doi.org/10.1111/ijfs.14435>.
- Mellinas, C., Valdés, A., Ramos, M., Burgos, N., Garrigós, M., del, C., Jiménez, A., 2016. Active edible films: current state and future trends. *J. Appl. Polym. Sci.* 133 (2) <https://doi.org/10.1002/app.42631>.
- Oldoni, F.C.A., Bernardo, M.P., Oliveira Filho, J.G., de Aguiar, A.C., Moreira, F.K.V., Mattoso, L.H.C., Colnago, L.A., Ferreira, M.D., 2021. Valorization of mangoes with internal breakdown through the production of edible films by continuous solution casting. *Lebensm. Wiss. Technol.* 145, 111339 <https://doi.org/10.1016/j.lwt.2021.111339>.

- Oliveira, A.S., Niro, C.M., Bresolin, J.D., Soares, V.F., Ferreira, M.D., Sivieri, K., Azeredo, H.M.C., 2021. Dehydrated strawberries for probiotic delivery: influence of dehydration and probiotic incorporation methods. *Lebensm. Wiss. Technol.* 144, 111105 <https://doi.org/10.1016/j.lwt.2021.111105>.
- Otoni, C.G., Azeredo, H.M.C., Mattos, B.D., Beaumont, M., Correa, D.S., Rojas, O.J., 2021. The food–materials nexus: next generation bioplastics and advanced materials from agri-food residues. *Adv. Mater.* 33 (43), 2102520 <https://doi.org/10.1002/adma.202102520>.
- Otoni, C.G., Avena-Bustillos, R.J., Azeredo, H.M.C., Lorevice, M.V., Moura, M.R., Mattoso, L.H.C., McHugh, T.H., 2017. Recent advances on edible films based on fruits and vegetables—a review. *Compr. Rev. Food Sci. Food Saf.* 16 (5) <https://doi.org/10.1111/1541-4337.12281>.
- Otoni, Caio G., Moura, M.R.d., Aouada, F.A., Camilloto, G.P., Cruz, R.S., Lorevice, M.V., Soares, N. de F.F., Mattoso, L.H.C., 2014. Antimicrobial and physical-mechanical properties of pectin/papaya puree/cinnamaldehyde nanoemulsion edible composite films. *Food Hydrocolloids* 41, 188–194. <https://doi.org/10.1016/j.foodhyd.2014.04.013>.
- Ribeiro, H.L., Brito, E.S., Souza Filho, M. de sá M., Azeredo, H.M.C., 2018. Montmorillonite as a reinforcement and color stabilizer of gelatin films containing acerola juice. *Appl. Clay Sci.* 165, 1–7. <https://doi.org/10.1016/j.clay.2018.07.041>.
- Rodríguez, G.M., Sibaja, J.C., Espitia, P.J.P., Otoni, C.G., 2020. Antioxidant active packaging based on papaya edible films incorporated with *Moringa oleifera* and ascorbic acid for food preservation. *Food Hydrocolloids* 103, 105630. <https://doi.org/10.1016/j.foodhyd.2019.105630>.
- Sá, N.M.S.M., Mattos, A.L.A., Silva, L.M.A., Brito, E.S., Rosa, M.F., Azeredo, H.M.C., 2020. From cashew byproducts to biodegradable active materials: bacterial cellulose-lignin-cellulose nanocrystal nanocomposite films. *Int. J. Biol. Macromol.* 161, 1337–1345. <https://doi.org/10.1016/j.ijbiomac.2020.07.269>.
- Salehi, F., 2020. Effect of coatings made by new hydrocolloids on the oil uptake during deep-fat frying: a review. *J. Food Process. Preserv.* 44 (11), e14879 <https://doi.org/10.1111/jfpp.14879>.
- Salgado, P.R., Ortiz, C.M., Musso, Y.S., Di Giorgio, L., Mauri, A.N., 2015. Edible films and coatings containing bioactives. *Curr. Opin. Food Sci.* 5, 86–92. <https://doi.org/10.1016/j.cofs.2015.09.004>.
- Santos, T.M., Souza Filho, M. de S.M., Silva, E. de O., Silveira, M. R. S. da, Miranda, M. R. A. de, Lopes, M.M.A., Azeredo, H.M.C., 2018. Enhancing storage stability of guava with tannic acid-crosslinked zein coatings. *Food Chem.* 257, 252–258. <https://doi.org/10.1016/j.foodchem.2018.03.021>.
- Singh, P., Magalhães, S., Alves, L., Antunes, F., Miguel, M., Lindman, B., Medronho, B., 2019. Cellulose-based edible films for probiotic entrapment. *Food Hydrocolloids* 88, 68–74. <https://doi.org/10.1016/j.foodhyd.2018.08.057>.
- Viana, R.M., Sá, N.M.S.M., Barros, M.O., Borges, M.D.F., Azeredo, H.M.C., 2018. Nanofibrillated bacterial cellulose and pectin edible films added with fruit purees. *Carbohydr. Polym.* 196 <https://doi.org/10.1016/j.carbpol.2018.05.017>.
- Xu, Y., Chu, Y., Feng, X., Gao, C., Wu, D., Cheng, W., Meng, L., Zhang, Y., Tang, X., 2020. Effects of zein stabilized clove essential oil Pickering emulsion on the structure and properties of chitosan-based edible films. *Int. J. Biol. Macromol.* 156, 111–119. <https://doi.org/10.1016/j.ijbiomac.2020.04.027>.
- Zhao, X., Cornish, K., Vodovotz, Y., 2020. Narrowing the gap for bioplastic use in food packaging: an update. *Environ. Sci. Technol.* 54 (8), 4712–4732. <https://doi.org/10.1021/acs.est.9b03755>.