


 Cite this: *RSC Adv.*, 2024, 14, 11266

Medium-temperature calcination and acid pressure leaching extract the Al₂O₃ from coal gangue: activation mechanism and kinetic analysis

 Zhiyong Yang,^{†ab} Yunsheng Zheng,^{†*c} Zhijun Ma,^{†*cd} Liang Cheng,^c Guangming Wang^c and Ying Qin^c

Bauxite is an important strategic resource, and it is facing with the problem of balance between high demand of bauxite ore and low resource of bauxite reserves in China. This research takes the Fuxin coal gangue as the object and extracts Al₂O₃ by medium-temperature calcination and acid pressure leaching process. The results show that at a calcination temperature of 650 °C, calcination time of 2 h, acid pressure leaching temperature of 160 °C and acid pressure leaching time of 6 h, the extraction ratio of Al₂O₃ reaches 80.19%. Furthermore, the research finding that the complete activation temperatures of kaolinite and muscovite are 650 °C and 850 °C, respectively, and the decomposition reactions of active Si, active Al, and metakaolinite occur above 800 °C, which leads to a low extraction ratio of Al₂O₃. The acid pressure leaching process can directly destroy the muscovite structure at a calcination temperature of 650 °C. The acid pressure leaching kinetic equations are studied by three kinetic models, and the apparent activation energies of the reactions are calculated by the Arrhenius formula. The results show that acid pressure leaching is subject to solid residue in-layer diffusion control, and the kinetic equation

 Received 28th December 2023
 Accepted 20th March 2024

DOI: 10.1039/d3ra08901k

rsc.li/rsc-advances

is $1 - \frac{2}{3}x - (1-x)^3 = 0.7803e^{\left(\frac{-13.48}{8.3147}\right)t}$. The apparent activation energy is 13.48 kJ mol⁻¹.

1 Introduction

Bauxite is an important strategic resource, and China is the world's largest producer of alumina. Bauxite is faced with the problem of balance between the high demand of bauxite ore and the low resource of bauxite reserves. The dependence on foreign bauxite in China exceeded 55% at this stage, the import ratio is expected to reach 80% by 2030.^{1,2} China's bauxite import demand is mainly for higher-quality overseas gibbsite bauxite, which accounts for 75% of global bauxite imports.³ Therefore, Seeking alternatives to bauxite is important for the sustainable development of China's aluminum industry. Coal gangue is a mixture of carbonaceous, muddy, and sandy shale, which is a solid waste thrown out by coal through the process of mining

and washing.^{4,5} It is considered to be a potential mineral resource and is elemental composed primarily of SiO₂ and Al₂O₃, which account for approximately 50–80% elemental composition of coal gangue.^{6–8} Coal gangue can be used for the production of chemical products such as alumina,⁹ aluminum sulfate,¹⁰ and polymeric aluminum chloride,¹¹ as well as for the preparation of molecular sieve materials.¹² Therefore, coal gangue can be used as a substitute for bauxite to provide raw materials for the development of the downstream aluminum industry. Currently, the amount of coal gangue accumulation has reached 45–50 Bt.¹³ Massive long-term accumulation of coal gangue leads to environmental pollution, landslides, and other problems, threatening the safety of human life and property.^{14,15} Fuxin is one of the important energy bases in China and is known as the “city of coal and electricity”. According to the statistics, there are 23 coal gangue storage sites, covering an area of 29 037 acres, with a stockpile of 2 Bt in Fuxin. The accumulation of large amounts of coal gangue puts great pressure on land resources and the ecological environment. In addition, the Al₂O₃ content of coal gangue is in the range of 13.34–18.74% in Fuxin, and it is of great significance to carry out Al₂O₃ extraction studies.^{16,17}

At present, the commonly used methods for extracting Al₂O₃ from coal gangue include an acid method and an alkali fusion

^aSchool of Mechanical Engineering, Liaoning Technical University, Fuxin 123000, China

^bZhondong Energy Research Institute, Xinjiang Tianchi Energy Sources Co., Ltd, 831100, Changji, China

^cCollege of Mining, Liaoning Technical University, Fuxin 123000, China. E-mail: zhijunma0930@126.com; zys_lgd@126.com; Tel: +86-139-4188-1359. Fax: +86-183-4284-7818

^dCollege of Materials Science & Engineering, Liaoning Technical University, Fuxin 123000, China

[†] These authors contributed equally.



method. The alkali fusion method has the shortcomings of high alkali consumption, complex processing, and a large amount of waste residue, while the acid method of extracting Al_2O_3 from coal gangue has the advantages of high efficiency and simplicity. Guan *et al.*,¹⁸ extracted Al_2O_3 directly under a hydrochloric acid system by adding sodium fluoride, and the extraction ratio of Al_2O_3 only reached only 70.40%. The structures of kaolinite, muscovite, and orthoclase within coal gangue are stable, and hydrochloric acid is not reactive and cannot efficiently extract Al_2O_3 . Therefore, activation treatment is needed before the acid method,^{19–22} with thermal activation being the most common among these methods. Under the action of thermal activation, internal and external hydroxyl groups are removed from kaolinite, generating the more active product metakaolinite, which is beneficial to increase the extraction ratio of Al_2O_3 . Jia *et al.*,¹⁶ used coal gangue with a high mineral content of kaolinite and a high chemical element content of Al as the raw material, and applied a calcination process and atmospheric pressure “one-step acid dissolution method” to extract Al_2O_3 , for which the extraction ratio reached 94.09%. The alumina product index reached the international metallurgical grade standard. In contrast, Li¹⁷ subjected coal gangue from the Fuxin area to the “one-step acid dissolution method” to extract Al_2O_3 , and the extraction ratio reached only 35%. The reason is that the Al_2O_3 extracted by the calcination activation method and one-step acid dissolution method mainly exist in the form of kaolinite, and the content of kaolinite in the Fuxin coal gangue is low. Therefore, the “one-step acid dissolution method” has strict requirements for the content of Al_2O_3 and the mineral composition of coal gangue. However, the aluminum content of coal gangue in China is low, so the above research is not universal. In this paper, the acid pressure leaching process is adopted based on a one-step acid dissolution method. Compared with the above process, the acid pressure leaching provides pressure to the reaction system, and H^+ more easily penetrates within the pores of the coal gangue, improving the extraction ratio of Al_2O_3 .

This research addresses the problem of a low Al_2O_3 extraction ratio when performing a “one-step acid dissolution method” with coal gangue in Fuxin. The complete activation temperatures of kaolinite and muscovite are 650 °C and 850 °C respectively, and the decomposition of active Si, active Al, and metakaolinite occurs above 800 °C, which leads to a low extraction ratio of Al_2O_3 . Therefore, the key to improving the leaching rate of alumina from coal gangue in the Fuxin area is to solve the problem that kaolinite and muscovite cannot be activated simultaneously. In this paper, the methods of medium temperature calcination and acid pressure leaching were used to extract Al_2O_3 . The structure of kaolinite can be destroyed directly by a medium-temperature calcination process at a calcination temperature of 650 °C, and the structure of muscovite can be destroyed directly by an acid pressure leaching process. It has solved the problem that kaolinite and muscovite in coal gangue cannot be activated at the same temperature, and the extraction ratio of Al_2O_3 is significantly improved. This study provides basic data for the high-value

utilization of coal gangue and sustainable development of the aluminum industry in China.

2 Materials and methods

2.1 Materials

Coal gangue was taken from the Hengda Coal Processing Plant of the Liaoning Fuminous Group. The coal gangue was passed through a 200 mesh sieve (0.074 mm) and called CG. The CG elemental analysis data are shown in Table 1.

2.2 Methods

2.2.1 Medium temperature calcination and acid pressure leaching of coal gangue. First, a certain amount of coal gangue (CG), was placed in a box-type electric furnace for calcination at 600–850 °C for 1–3 h. The sample was removed from the furnace and naturally cooled to room temperature. Thus, a calcined sample was obtained, and called CG-*T-H*, where *T* represents the calcination temperature, and *H* represents the calcination time. Hydrochloric acid solution (2–10 mol L⁻¹) was added to the calcined sample at a solid–liquid ratio of 1 : 10. The mixture was stirred evenly, placed in a high-pressure reactor, immersed in a drying oven at 120 °C (pressure value 0.11 MPa), 140 °C (pressure value 0.32 MPa), 160 °C (pressure value 0.55 MPa), 180 °C (pressure value 0.82 MPa) under self-generated pressure for 2–10 h, and then allowed to naturally cool to room temperature. The sample was then washed with distilled water (homemade in the laboratory) to neutralize, and dried in a 100 °C drying oven for 12 h to obtain acid leaching samples, called SJZ-*T-H*, where *T* represents the calcination temperature, and *H* represents the calcination time.

2.2.2 Evaluation of the Al_2O_3 extraction ratio. The mass fraction of Al_2O_3 (w_0 , w_e) in the samples before and after acid pressure leaching was determined using the fluorine salt substituted EDTA complex titration method described in GB/T 1574-2007, and the extraction ratio of Al_2O_3 (*R*, %) was calculated as follows:

$$R = \left(\frac{m_0 w_0 - m_e w_e}{m_0 w_0} \right) \times 100\% \quad (\text{A.1})$$

where “*R*” is the extraction ratio of Al_2O_3 after acid pressure leaching, %. “ m_0 , m_e ” are the mass of the sample before and after acid pressure leaching, g. “ w_0 , w_e ” are the mass fraction of Al_2O_3 in the sample before and after acid pressure leaching, %.

2.3 Sample characterization

An X-ray diffractometer (XRD) (D8 ADVANCE, Bruker, Germany) was used to determine the phase structure of the samples under the following test conditions: Cu targeted K α -ray, 1.5406 Å wavelength, 40 kV working voltage, 40 mA tube current, 0.05 s step length, and 5–70° scanning range. Fourier transform infrared spectroscopy (FT-IR) (Tensor II, Bruker, Germany) was used to analyze the chemical bonds of the samples under the following test conditions: wave number range of 400–4000 cm⁻¹; a fully automated volumetric vapor adsorption instrument (3H-2000PMV, BEST) was used to analyze the

Table 1 Elemental composition of coal gangue

Component	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	K ₂ O	MgO	CaO	TiO ₂	P ₂ O ₅	Loss on ignition
Contents (wt%)	46.19	12.60	7.13	2.19	1.34	2.06	0.74	0.17	25.19

specific surface area, pore size distribution, and pore volume of the samples under the following test conditions: degassing temperature of 573.15 K and degassing time of 4 h. Additionally, the influence of medium temperature calcination and acid pressure leaching on the pore structure of coal gangue was studied; TG-DSC (STA 449F3, Netzsch, Germany) was used to study phase changes during sample warming. The test conditions were as follows: temperature increase rate of 10° per min, temperature range of 0 to 1200 °C, and atmosphere of air; SEM (Sigma, ZEISS, Germany) was used to analyze the surface morphology of the samples.

3 Results and discussion

3.1. Effect of calcination temperature on the extraction ratio of Al₂O₃

The effect of calcination temperature on the extraction ratio of Al₂O₃ was studied. The analysis in Fig. 1 shows that the extraction ratio of Al₂O₃ tends to increase and then decrease with increasing calcination temperature. The extraction ratio of Al₂O₃ was highest at a calcination temperature of 650 °C, under which it reached 80.19%. When the calcination temperature reached 800 °C, the extraction ratio of Al₂O₃ decreased significantly. When the calcination temperature was 850 °C, the extraction ratio of Al₂O₃ decreased to its lowest value. This was due to the metakaolin further decomposing to form amorphous SiO₂, γ-Al₂O₃, and sillimanite (Al₂O₃·SiO₂) at 800 °C, which is not reactive with hydrochloric acid, resulting in the extraction ratio of Al₂O₃ decreased.²³

3.2. Effect of calcination time on the extraction ratio of Al₂O₃

The effect of calcination time on the extraction ratio of Al₂O₃ was also investigated. The analysis in Fig. 2 shows that the extraction ratio of Al₂O₃ tends to increase first and then stabilize with increasing calcination time. This is because the calcination

time is short, and the calcination process is not sufficient, thus leading to a low extraction ratio of Al₂O₃. When the calcination time reached 2 h, the extraction ratio of Al₂O₃ was stable and reached 80.19%. The acid pressure leaching process is accompanied by the leaching of Fe, the extraction ratio is 98.11%, so the iron removal problem should be fully considered in industrial production.

3.3 Activation mechanism

3.3.1 XRD and FT-IR of the samples. The extraction ratio of Al₂O₃ is influenced by the phase structure within the coal gangue. Changes in the phase structure of the coal gangue, calcined samples, and acid pressure leaching samples were analyzed *via* XRD and FT-IR. Due to the complex mineral composition of the samples, the FT-IR absorption peaks are close to each other, and adjacent peaks can easily overlap. The second-order derivative method was used to analyze overlapping absorption peaks in the FT-IR spectra.²⁴ The XRD and FT-IR results are shown in Fig. 3.

The XRD and FT-IR analyses in Fig. 3a show that the main phase components of coal gangue are 38.1% quartz, 16.1% kaolinite, 21.4% orthoclase, 10.3% muscovite, 13.7% chlorite, and 0.3% iron-bearing minerals (magnetite, hematite, and pyrite). Based on elemental analysis, the main elemental components of coal gangue are SiO₂, Al₂O₃, and Fe₂O₃, which means that Si exists primarily in the form of quartz. Al and a portion of Si exist in the form of aluminosilicate minerals. And Fe exists in the form of chlorite.^{25,26}

The analysis in Fig. 3b shows that the kaolinite diffraction peak completely disappears at $2\theta = 8.89^\circ$ in the XRD pattern, and the metakaolinite absorption peaks appear at 1065.80 cm⁻¹, 562.91 cm⁻¹, and 481.20 cm⁻¹ in the FT-IR pattern, under calcination temperature at 650 °C. These results indicate that the phase structure of kaolinite is transformed to generate more active metakaolinite at a calcination

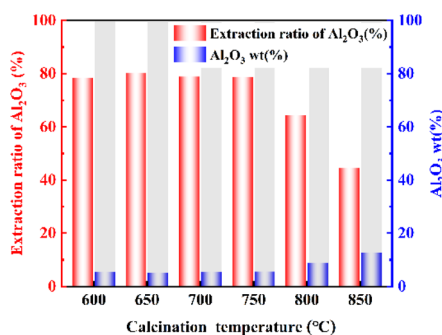


Fig. 1 Effect of calcination temperature on the extraction ratio of Al₂O₃.

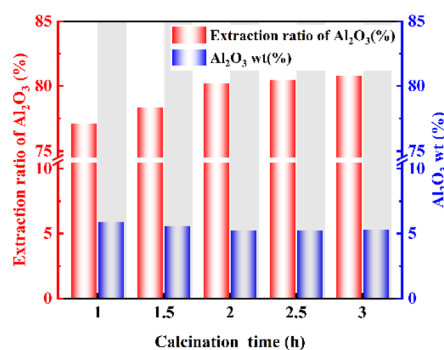


Fig. 2 Effect of calcination time on the extraction ratio of Al₂O₃.

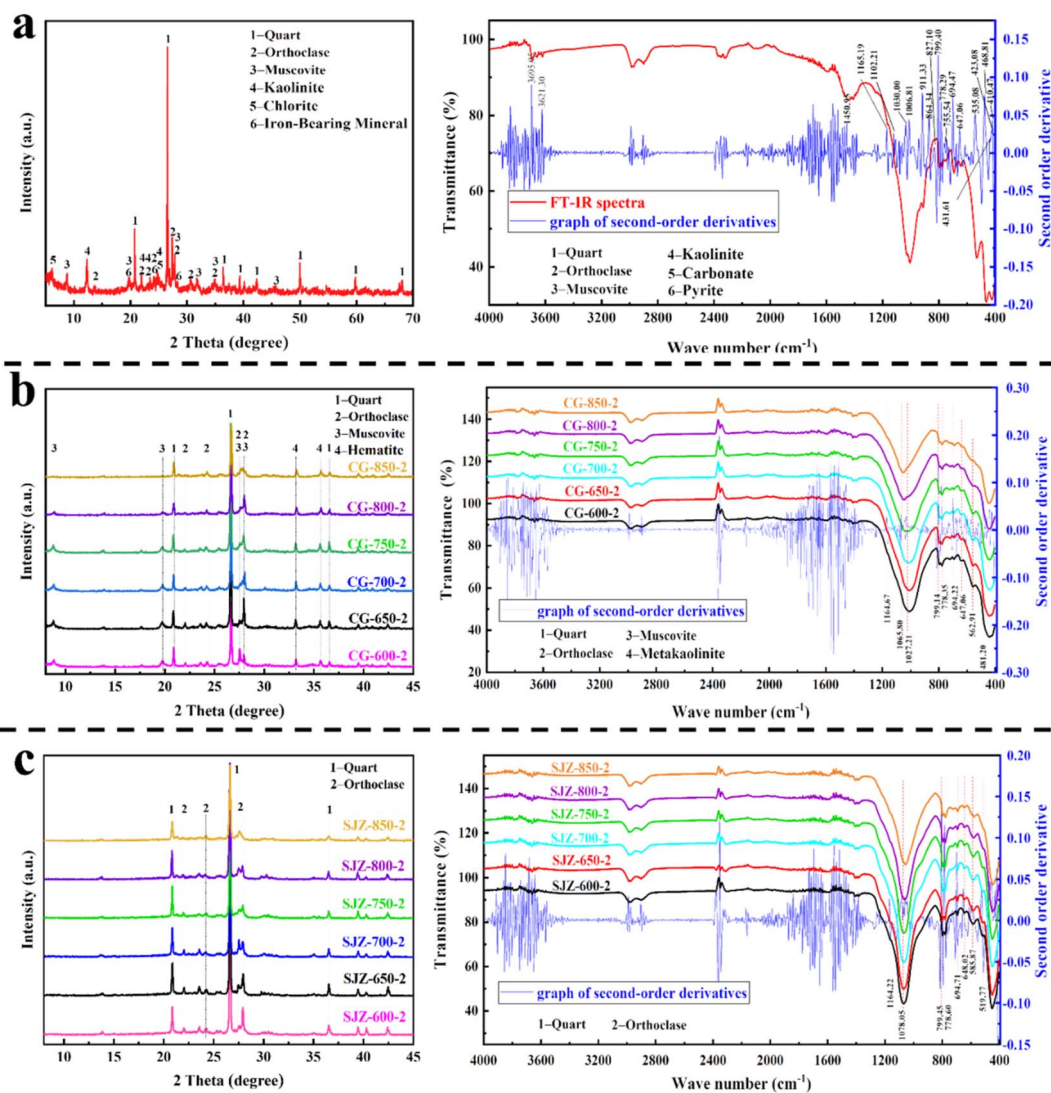


Fig. 3 XRD and FT-IR of the samples ((a) CG. (b) CG-T-H. (c) SJZ-T-H).

temperature of 650 °C.²⁷ When the calcination temperature reaches 800 °C, these three absorption peaks of metakaolinite weaken in the FT-IR pattern. These results indicate that the metakaolinite further decomposes to form amorphous SiO₂, γ-Al₂O₃, and sillimanite (Al₂O₃·SiO₂) at a calcination temperature of 800 °C. Moreover, hematite diffraction peaks appear at 2θ = 33.12° and 35.64°, indicating that the phase structure of the iron-bearing minerals transforms to hematite. On the one hand, this is due to the oxidation of Fe²⁺ to Fe³⁺ in iron-bearing minerals;²⁸ on the other hand, the dehydroxylation of iron-bearing minerals transforms into hematite under calcination conditions. When the calcination temperature is 850 °C, the muscovite diffraction peak completely disappears at 2θ = 19.88° in the XRD pattern, and the muscovite absorption peaks disappear at 827.10 cm⁻¹, 468.81 cm⁻¹, and 423.08 cm⁻¹ in the FT-IR pattern. These results indicate that the phase structure of muscovite is transformed at 850 °C. To summarize, it can be found that kaolinite and muscovite cannot be activated at the same time by calcination alone, so the “one-step acid

dissolution method” has a low extraction ratio of Al₂O₃ for coal gangue in Fuxin.

The analysis in Fig. 3c shows that the method of acid pressure leaching is further adopted at a calcination temperature of 650 °C, at which point only quartz and orthoclase diffraction peaks remain, and hematite and muscovite diffraction peaks disappear in the XRD and FT-IR patterns. These results indicate that acid pressure leaching can destroy the muscovite structure within coal gangue. The reason is that acid pressure leaching provides pressure to the reaction system, and H⁺ more easily penetrates within the pores of the coal gangue, improving the extraction ratio of Al₂O₃. With an increase in calcination temperature to 800 °C, further decomposition of metakaolinite sillimanite (Al₂O₃·SiO₂), which is not easily leached by acid pressure leaching due to their lower activity. These changes reduced the extraction ratio of Al₂O₃ and increased the residual amount of Al₂O₃,²⁹ resulting in a reduced diffraction peak intensity for quartz and orthoclase in the XRD pattern.

In summary, phase structure transformation during the process of medium-temperature calcination and acid pressure leaching of coal gangue was analyzed. The phase structure of kaolinite could be transformed into metakaolinite at a calcination temperature of 650 °C, and the phase structure of muscovite was destroyed by acid pressure leaching, which could increase the extraction ratio of Al_2O_3 . The problem that the phase structure of kaolinite and muscovite cannot be activated at the same time in the “one-step acid dissolution method” is solved.

3.3.2 Thermogravimetric analysis of coal gangue. Furthermore, thermogravimetric analysis was used to observe the weight change in coal gangue during the heating process and research the phase structure change of coal gangue. The TG-DTA curve analysis in Fig. 4 shows that the weight loss within the range of 30 to 200 °C is mainly related to the external water bound to the coal gangue in a mechanical manner and the internal water bound to the coal gangue in a physicochemical manner. The temperature reached the maximum rate of weight loss at 83.8 °C. The overall mass loss was 2.24%, which was lower than that of coal gangue ($\text{Mad} = 3.47\%$). These results indicate that the water does not disappear completely when the temperature increases at a rate of 10° per min. The weight loss in the latter is accompanied by the evaporation of water, so there is no obvious oxygen uptake weight gain in the weight loss curve. The weight loss curve produced a significant weight loss state at 290.0 °C, and the weight loss rate reached its maximum at 439.7 °C. These results are due to the oxidative decomposition and combustion of carbonaceous components within the coal gangue.³⁰ The rate of weight loss briefly increased at 585.5 °C due to the removal of internal and external hydroxyl groups from kaolinite within the coal gangue.³¹ The weight loss from 290.0 °C to 871.5 °C was 21.95%, and the theoretical burn loss was 24.19%. The observed partial weight loss after 871.5 °C, was mainly due to the decomposition of metakaolinite and the generation of new crystalline phases, leading to a weight loss of 0.81%. The analysis of the DTG curves in Fig. 4 shows that the processes of coal gangue oxide decomposition, carbonaceous component combustion, and kaolinite conversion are exothermic. Therefore, the calcination temperature needed for the extraction of Al_2O_3 is higher than the activation temperature of kaolinite and lower than the temperature at which the decomposition reaction of metakaolinite occurs.

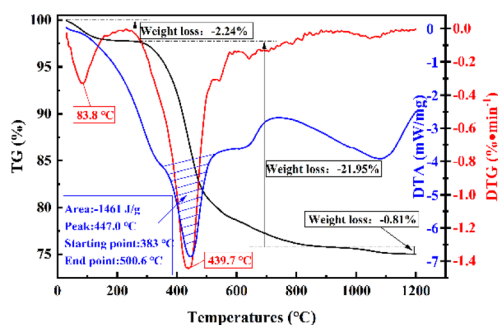


Fig. 4 TG-DTG-DTA curve of coal gangue.

3.3.3 Pore structure of samples. Fig. 5 shows the pore structure of the samples after coal gangue extraction, calcination, and acid pressure leaching. The N_2 adsorption-desorption isotherms of all the samples conformed to the type III isotherm curve. The adsorption capacity approaches 0 in relative pressure $P/P_0 < 0.1$ partial pressure section, indicating that the samples contain a small number of micropores. In the relative pressure $0.1 < P/P_0 < 0.4$ partial pressure section, the adsorption capacity is low, and there is no inflection point, indicating that the relative force between the samples and nitrogen molecules is weak. With increasing relative pressure P/P_0 , the adsorption capacity also gradually increases, indicating that pores fill the sample. In the relative pressure $0.8 < P/P_0 < 1$ partial pressure section, the adsorption capacity increases sharply, and the typical capillary coalescence phenomenon occurs; these results indicate the presence of a certain amount of mesopores within the samples.³² Calcination has a certain effect on the internal pore structure of coal gangue. Comparing the coal gangue (Fig. 5a) with the acid pressure leaching sample (Fig. 5b), the BET-specific surface area of the samples decreased from $20.5090 \text{ m}^2 \text{ g}^{-1}$ to $10.9940 \text{ m}^2 \text{ g}^{-1}$, the mean pore size increased from 12.31 nm to 19.08 nm, the pore volume increased from $0.0733 \text{ cm}^3 \text{ g}^{-1}$ to $0.0842 \text{ cm}^3 \text{ g}^{-1}$. The reason is that hydroxyl group removal from kaolinite within coal gangue and the chemical bond breakage of mineral components during the calcination process at 650 °C result in internal defects, collapse, and hollowing of coal gangue, which will increase the pore size of coal gangue and reduce the BET specific surface area. After medium temperature calcination and acid pressure leaching of the coal gangue, the adsorption capacity in the high-pressure zone of the sample increased, the mean pore size increased to 22.38 nm, and the pore volume increased to $0.1683 \text{ cm}^3 \text{ g}^{-1}$, as shown in Fig. 5c. The reason is that after the active aluminum components, metakaolinite, and muscovite blocked in the samples are leached by acid pressure leaching, the pore channels are dredged to increase the specific surface area and the pore size.

In summary, under medium calcination conditions, the dehydroxylation of kaolinite and the decomposition of organic matter lead to the collapse of the skeleton structure and the production of defects, which increase the pore volume and pore size. Under pressure acid leaching, the active components, metakaolinite, and muscovite are leached, leading to channel dredging and a large number of pores while increasing the pore volume and specific surface area.

3.3.4 Samples morphology and particle size. Fig. 6a shows that the presence of the clay minerals of chlorite and kaolinite causes the coal gangue particles to stick to each other, agglomerate, and have uneven size distribution of the lumpy particles. Fig. 6b shows that the coal gangue has a lamellar morphology and that there are slit holes with lamellar accumulations, which is consistent with the pore structure analysis in Fig. 5a. From the particle point of view in Fig. 6c and e, After acid pressure leaching of coal gangue samples, the particle size of the samples did not change significantly. The carbon component of coal gangue is removed after medium-

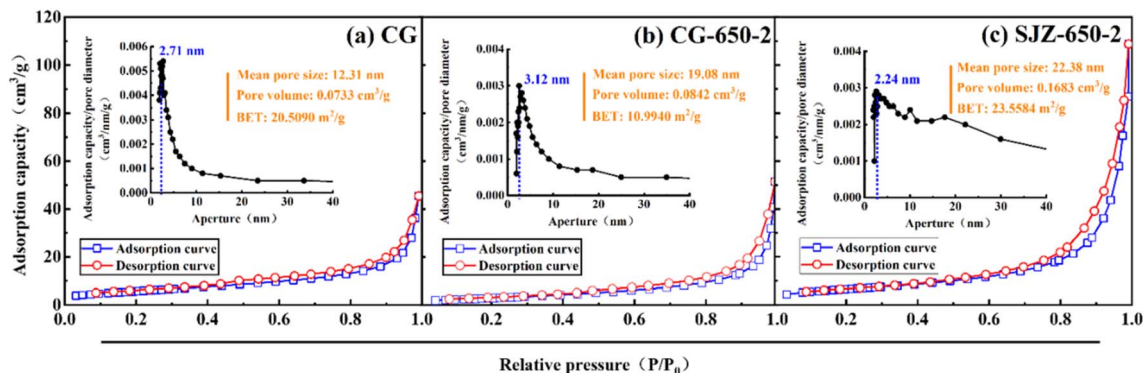


Fig. 5 Pore structure of the samples.

temperature calcination, and the surface is smooth in Fig. 6d. There are obvious cavities and defects in the acid pressure leaching samples in Fig. 6f, the reason is that active components such as metakaolinite were selectively leached from acid pressure leaching samples, while quartz and orthoclase are not reactive with hydrochloric acid and will form many voids and defects on the surface. This is consistent with the increase in the specific surface area of the SJZ-650-2 sample (Fig. 5c). Laser particle size analysis was performed on the samples before and after acid pressure leaching (Fig. 6g and f), calcination sample $D_{50} = 13.25 \mu\text{m}$, and acid pressure sample $D_{50} = 14.07 \mu\text{m}$. Therefore, it can be considered that the particle size of the sample did not change basically after acid pressure leaching, which is consistent with the analysis results in Fig. 6c and e.

3.4 Kinetic analysis of acid pressure leaching

The macrokinetic research method is used to study the kinetic model and kinetic control type of the coal gangue pressurized acid leaching process. The coal gangue pressurized acid leaching reaction is a typical liquid–solid noncatalytic reaction. Quartz and feldspar are not reactive when mixed with

hydrochloric acid, and only active substances are selectively leached. Therefore, there will be a certain amount of solid residual products in the acid pressure leaching process. This result is in line with the kinetic principle of hydrometallurgy³³ of the “unreacted shrinking core model” (Fig. 7).

Solid–liquid leaching reaction based on steady state, and according to Fick’s first law, the total reaction rate of hydrochloric acid solution through the boundary layer can be expressed by the amount of Al_2O_3 leached per unit time (see eqn (A.2)).

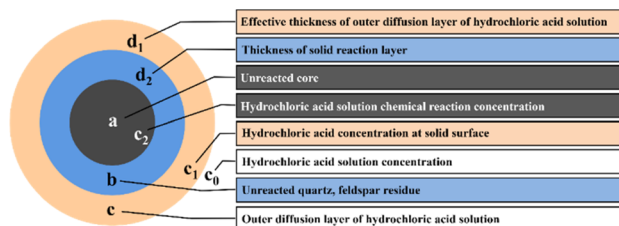


Fig. 7 Unreacted shrinking core model.

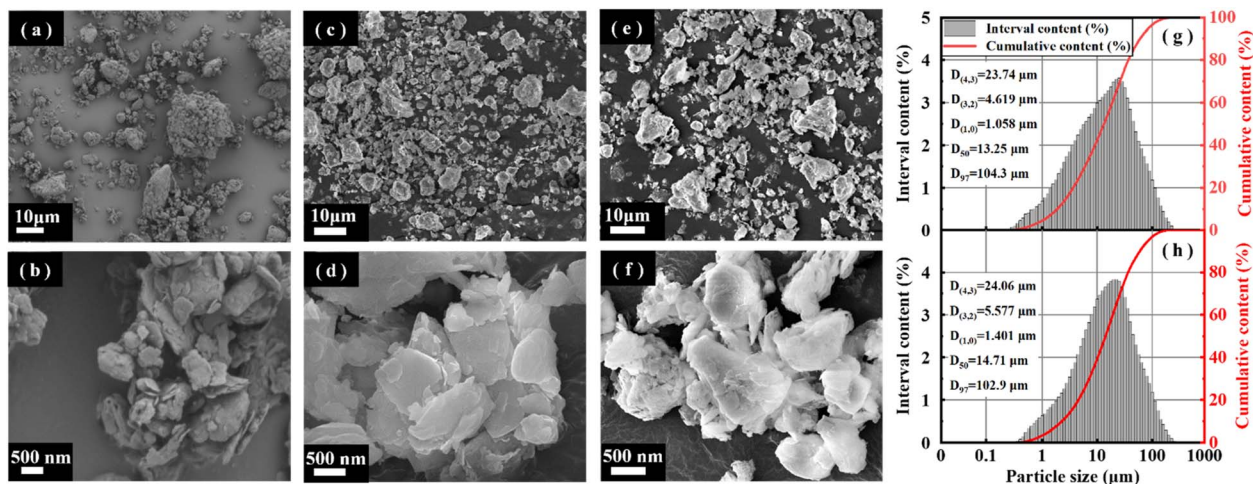


Fig. 6 SEM morphology analysis: ((a and b) – coal gangue; (c and d) – calcination sample (e and f) – acid pressure leaching sample, (g) – calcination sample size analysis, (h) – acid pressure leaching sample size analysis).

$$\frac{-dN}{dt} = -SD \frac{dC}{dr} \quad (\text{A.2})$$

where “ N ” is the amount of substance for Al_2O_3 at reaction time t , mol; “ S ” is the reactant particle surface area, m^2 ; “ D ” is the diffusion coefficient, $\text{m}^2 \text{s}^{-1}$; and “ dC/dr ” is the concentration gradient, mol m^{-4} .

It is assumed that the density of coal gangue is ρ , the radius is r , the surface area is S , and the relative molecular weight of the material involved in the leaching reaction is M . The amount of substance at time t of reaction between surface area and alumina is expressed by eqn (A.3) and (A.4).

$$S = 4\pi r^2 \quad (\text{A.3})$$

$$N = \frac{4}{3} \frac{\pi r^3}{M} \quad (\text{A.4})$$

Because the radius of the coal gangue particle is not easy to obtain during the reaction process, the relationship between the extraction ratio X of Al_2O_3 and reaction time is chosen to express the kinetic equation. N_0 was set as the amount of initial substance in the reaction, and the Al_2O_3 extraction ratio is shown in eqn (A.5).

$$X = \frac{N_0 - N}{N_0} = 1 - \frac{r^3}{r_0^3} \quad (\text{A.5})$$

where “ X ” is the extraction ratio of Al_2O_3 , %; “ r ” is the particle radius of coal gangue at reaction time t , mm; and “ r_0 ” is the initial reaction particle radius, mm.

When the acid pressure leaching process is controlled by the diffusion boundary layer, $C_1 \approx 0$, then the amount of substance leached Al_2O_3 per unit time is shown in eqn (A.6).

$$\frac{-dN}{dt} = \frac{C_0 DS}{d_1} \quad (\text{A.6})$$

where “ S ” is the surface area of the coal gangue particles in the solid residual layer, $\text{m}^2 \text{g}^{-1}$.

It is assumed that the reaction particle size during the process of Al_2O_3 acid pressure leaching does not change with the reaction and that S is a constant. The kinetic equation of external diffusion control is shown in eqn (A.7).

$$X = k_1 t \quad (\text{A.7})$$

where “ k_1 ” is the rate constant of the external diffusion process.

When the acid pressure leaching process is controlled by internal diffusion of the solid residual layer, then the amount of substance leached Al_2O_3 per unit time is shown in eqn (A.8).

$$\frac{-dN}{dt} = SD_2 \frac{dC}{dr} \quad (\text{A.8})$$

where “ D_2 ” is the diffusion coefficient of the hydrochloric acid solution in the solid residual layer, $\text{m}^2 \text{s}^{-1}$.

It is assumed that the volume of the residual layer is equal to the volume of coal gangue particles and that r_0 remains unchanged; then, $C_1 \approx C_0$ and $C_2 \approx 0$. Eqn (A.3) can be substituted into eqn (A.8) and integrated to obtain eqn (A.9).

$$\frac{-dN}{dt} = 4\pi D^2 \frac{r_0 r}{r_0 - r} C_0 = 4\pi \frac{\rho}{M} r^2 \frac{dr}{dt} \quad (\text{A.9})$$

To construct eqn (A.9), r is represented by X to obtain the internal diffusion equation of the solid residual layer, which is shown in eqn (A.10).

$$1 - \frac{2}{3} X - (1 - X)^{\frac{2}{3}} = k_2 t \quad (\text{A.10})$$

where “ k_2 ” is the internal diffusion reaction rate constant.

When the acid pressure leaching process is controlled by a chemical reaction, the chemical reaction is a first-order reaction, and the amount of substance leached Al_2O_3 per unit time is shown in eqn (A.11).

$$\frac{-dN}{dt} = kSC_0 \quad (\text{A.11})$$

Eqn (A.3) and (A.5) are substituted into eqn (A.11) and the integral result is shown in eqn (A.12).

$$r_0 - r_0(1 - X)^{\frac{1}{3}} = \frac{kC_0 M}{\rho} t \quad (\text{A.12})$$

The equation for chemical reaction control is shown in eqn (A.13).

$$1 - (1 - X)^{\frac{1}{3}} = k_3 t \quad (\text{A.13})$$

where “ k_3 ” is the rate constant of the chemical reaction process.

The results of fitting the temperature and time of the acid pressure leaching process on the Al_2O_3 extraction ratio and kinetic analysis are shown in Fig. 8.

After 6 h of acid pressure leaching of coal gangue, the extraction ratio of Al_2O_3 no longer increased, so the kinetic equation was fitted to the data of the Al_2O_3 extraction ratio from 0–6 h. The results of the boundary layer diffusion control, solid residue in-layer diffusion control, and chemical reaction control fit are shown in Fig. 8. The data were fitted to give the reaction rate constant k and the correlation coefficient R^2 . Among them, the internal diffusion reaction control equation fits the best, the linear correlation coefficient $R^2 > 0.93$, and the fitted straight line tends to be close to the origin. Therefore, it can be judged that the process of acid pressure leaching Al_2O_3 from coal gangue is likely controlled by solid residue in-layer diffusion control.

The activation energy of the acid pressure process was calculated according to the “Arrhenius” formula (A.14) and (A.15):

$$k = A e^{\frac{-E_a}{RT}} \quad (\text{A.14})$$

$$\ln k = \ln A - \frac{E_a}{RT} \quad (\text{A.15})$$

where “ k ” is the apparent reaction rate constant, “ E_a ” is the apparent activation energy, kJ mol^{-1} , “ R ” is the molar gas constant, $8.314 \text{ J (mol}^{-1} \text{ K}^{-1})$, and “ A ” is a constant. The fitting

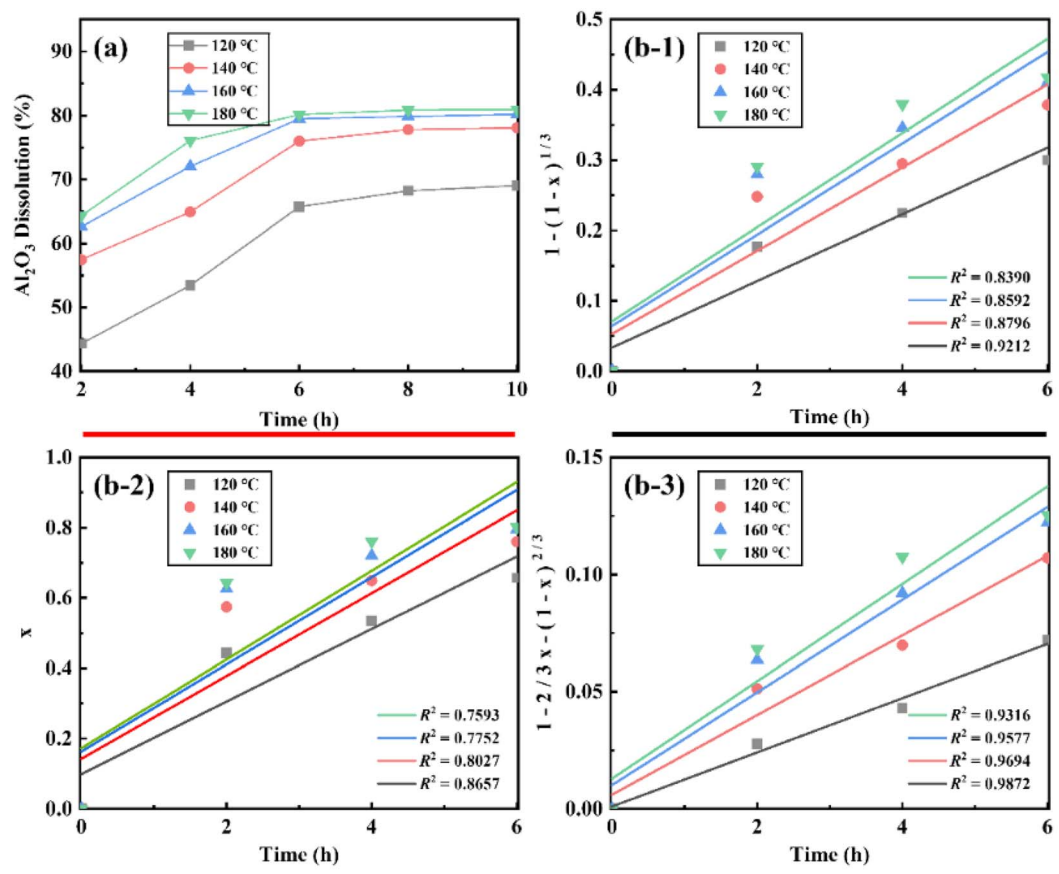


Fig. 8 Acid pressure leaching data and kinetic fitting results ((a) – acid pressure leaching temperature and time relationship, (b) – acid pressure leaching kinetics fitting results).

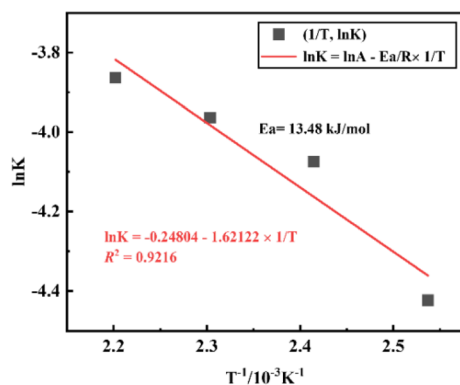


Fig. 9 Arrhenius fitting results for acid pressure leaching reactions.

curves of “ $\ln k - 1/T$ ” for Al_2O_3 are shown in Fig. 9. The apparent activation energies can be calculated from the slope of the fitting equations based on the Arrhenius formula, where the slope is “ $-E_a/RT$ ” and the intercept is “ $\ln A$ ”.

The fitted linear equation in Fig. 9, $\ln k = -0.24808 - 1.62122 \times 1/T$, the activation energy $E_a = 13.48 \text{ kJ mol}^{-1}$ and $A = 0.7803$. Therefore, the kinetic equation of the coal gangue acid pressure leaching process is:

$$1 - \frac{2}{3}x - (1-x)^{\frac{2}{3}} = 0.7803e^{\left(\frac{-13.48}{8.314T}\right)t} \quad (\text{A.16})$$

Based on the “one-step acid dissolution method”, the extraction ratio of Al_2O_3 reached 80.19% by the acid pressure leaching process, which has certain advantages compared with the alkali method and atmospheric pressure acid leaching method (Table 2). First of all, the alkali method has a higher extraction ratio of Al_2O_3 , but the sintering temperature is much higher than that of the acid pressure leaching process, and a higher energy consumption is required. In addition, the alkaline process produces a large amount of calcium silicate waste residue in the production process, resulting in low environmental benefits. Although the submolten salt method and supercritical water method reduces the activation energy consumption, it needs to consume a lot of strong alkali and cannot be recycled, resulting in high cost and difficult to achieve large-scale production. In addition, supercritical water method uses strong alkali for extraction at high temperature and pressure, resulting in simultaneous leaching of Si and Al, resulting in difficult separation in later stage. The acid pressure leaching provides pressure to the reaction system, and H^+ more easily penetrates within the pores of the coal gangue and

Table 2 Comparison of Al₂O₃ extraction process data

Number	Technology	Method	Origin of raw materials	Calcination/sintering temperature (°C)	Alumina extraction ratio (%)	Reference source
1	Alkali process	Limestone sintering method	Datong	1260	85.6	35
2			—	1340–1360	80	36
3		Submolten salt method	Pingshuo	280	87.47	37
4	Acid process	Supercritical water method	Shanyin	400	78.9	38
5			Acid atmospheric leaching	Luan	800	62.4
6		Acid pressure leaching	Fuxin	700	35	17
6			Fuxin	750	80.19	This work

extracts the Al₂O₃ inside the muscovite and other minerals that are not fully activated. The extraction ratio of Al₂O₃ from Fuxin coal gangue is increased from 35% to 80.19%. The problem of simultaneous activation of muscovite and kaolinite was solved without increasing the complexity of the process, and the extraction ratio of Al₂O₃ was improved. It has been calculated that 84.56 kg of Al₂O₃ can be extracted for every 1000 kg of coal gangue consumed, and at the same time, high silica waste residue will be left, which can prepare molecular sieve materials.³⁴ In addition, acid pressure leaching is self-generated pressure in the heating process, without external pressure treatment, which can adapt to industrial scale production. China's bauxite imports more than 60 million tons, to achieve the industrial production of coal gangue extraction Al₂O₃, can reduce the import pressure of bauxite, with high economic value and environmental benefits. However, the extraction process will produce HCl gas, which has a certain impact on the environment. The HCl can be condensation recovered and then recycled. At the same time, hydrochloric acid is corrosive, easy to cause the erosion of pipelines and equipment, the production of pipelines and equipment materials have higher requirements.

4 Conclusions

(1) Medium-temperature calcination and acid pressure leaching effectively improved the extraction ratio of Al₂O₃ from the Fuxin coal gangue. At a calcination temperature of 650 °C, calcination time of 2 h, HCl concentration of 8 mol L⁻¹, acid pressure leaching temperature of 160 °C, and acid pressure leaching time of 6 h, the dissolution ratio of Al₂O₃ reached 80.19%.

(2) The complete activation temperatures of kaolinite and muscovite are 650 °C and 850 °C, respectively. The decomposition reaction of active Si, active Al, and metakaolinite occurs above 800 °C, and these minerals decompose to form amorphous SiO₂, γ-Al₂O₃, and sillimanite (Al₂O₃-SiO₂), which leads to a low extraction ratio of Al₂O₃. The research used medium temperature calcination and acid pressure leaching process, the phase structure of kaolinite could be transformed into metakaolinite at a calcination temperature of 650 °C, and the phase structure of muscovite was destroyed by acid pressure leaching, which could achieve the purpose of increasing the extraction ratio of Al₂O₃. The problem that the phase structure of kaolinite and muscovite cannot be activated at the same time in the “one-step acid dissolution method” is solved.

(3) The acid pressure leaching process of Al₂O₃ can be described by the “unreacted shrinking core model”, and its reaction rate is controlled by solid residue in-layer diffusion control. The apparent activation energy of the acid pressure leaching $E_a = 13.48 \text{ kJ mol}^{-1}$, and the kinetic rate equation of the acid pressure leaching is $1 - \frac{2}{3}x - (1-x)^{\frac{2}{3}} = 0.7803e^{\left(\frac{-13.48}{8.314T}\right)t}$.

Author contributions

Conceptualization, Z. Y., Y. Z. and Z. M.; methodology, Z. Y., Y. Z., L. C.; validation, L. C., G. W., and Y. Q.; formal analysis, Z. Y., Y. Z., L. C., G. W., and Y. Q.; investigation, Z. M., G. W., and Y. Q.; resources, Z. M.; data curation, Z. Y., Y. Z.; writing-original draft preparation, Z. Y., Y. Z.; writing-review and editing, Z. Y., Y. Z.; visualization, G. W., and Y. Q.; supervision, L. C.; project administration, Z. M.; funding acquisition, Z. M. All authors have read and agreed to the published version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This research was funded by the Science and Technology Research Project of the Liaoning Provincial Department of Education (entry name: “Research on Key Technologies for Preparation of Molecular Sieve Materials Based on Coal Gangue Resource Attribute in Fuxin” (grant number LJ2020ZD006)).

Notes and references

- I. Smičiklas, M. Jović, M. Janković, S. Smiljanić and A. Onjia, *Water, Air, Soil Pollut.*, 2021, **232**, 324–338.
- J. Ding, S. H. Ma, S. Shen, Z. L. Xie, S. L. Zheng and Y. Zhang, *Waste Manage.*, 2017, **60**, 357–387.
- S. T. Cao, Y. F. Zhang and Y. Zhang, *Hydrometallurgy*, 2009, **98**, 298–303.
- Y. L. Zhang and T. C. Ling, *Constr. Build. Mater.*, 2020, **234**, 117424.
- Z. N. Su, X. H. Li and Q. Zhang, *J. Cleaner Prod.*, 2022, **363**, 132408.

- 6 I. Baic and K. B. Witkowska, *Rocz. Ochr. Sr.*, 2011, **13**, 1315–1325.
- 7 J. Y. Li, L. F. You and Y. Wei, *Adv. Mater. Res.*, 2012, **1792**, 915.
- 8 I. Hilary, D. John, O. Frank and S. Sue, *Min. Sci. Technol.*, 2010, **20**, 215–223.
- 9 Y. X. Guo, K. Z. Yan, L. Cui and F. Q. Cheng, *Powder Technol.*, 2016, **302**, 33–41.
- 10 D. K. Zeng, *Preparation of polyaluminum ferric sulfate from acid leaching of coal gangue and its application*, Kunming University of Science and Technology, 2021.
- 11 D. H. Kong, Z. H. Zhou, S. J. Song, S. Feng, M. L. Lian and R. L. Jiang, *Materials*, 2022, **15**(6), 2253.
- 12 Y. S. Zheng, J. X. Zhou, Z. J. Ma, X. Y. Weng, L. Cheng and G. R. Tang, *Materials*, 2023, **16**(12), 4338.
- 13 X. D. Wang, Y. Zhang, S. Chen, H. M. Ding and Y. Zhang, *Chem. Eng.*, 2021, **35**(04), 68.
- 14 M. L. Sheng, *Energy and Energy Conservation*, 2020, **05**, 62–63.
- 15 B. Lv, Z. Y. Zhao, X. W. Deng, C. J. Fang, B. B. Dong and B. Zhang, *J. Mater. Cycles Waste Manage.*, 2022, **24**, 1579–1590.
- 16 M. Jia and L. Yang, *Multipurp. Util. Miner. Resour.*, 2020, **02**, 140–144.
- 17 J. Y. Li, Y. Guo, X. W. Lu, K. Wu, H. Z. Cheng and K. Tang, *Tianjin Chemical*, 2017, **31**, 16–19.
- 18 C. P. Guan and C. H. Yan, *Sichuan Nonferrous Metals*, 2011, **4**, 35–39.
- 19 G. Mucsi, N. H. Papné, C. Ulsen, P. O. Figueiredo and F. Kristály, *ACS Sustain. Chem. Eng.*, 2021, **9**(9), 3416–3427.
- 20 S. Ravaszová and K. Dvořák, *IOP Conference Series: Materials Science and Engineering*, 2021, **1205**, 012003.
- 21 A. Mitrović and M. Zdujčić, *Int. J. Miner. Process.*, 2014, **132**, 59–66.
- 22 Y. X. Guo, K. Z. Yan, L. Cui and F. Q. Cheng, *Powder Technol.*, 2016, **302**, 33–41.
- 23 L. Cao, L. Zhang, Y. Guo and F. Cheng, *Clean Coal Technol.*, 2020, **26**, 203–208.
- 24 Y. Zhang, *Study on mineral transformation during pulverized coal combustion by INFRARED spectroscopy*, Changsha University of Science and Technology, 2017.
- 25 S. L. Cui, Q. P. Zhang, J. Y. Zhang and L. K. Gu, *Non-Met. Mines*, 2010, **33**, 25–27.
- 26 S. C. Liu, Q. Zhou, G. Li, L. H. Feng, Q. Zhang, X. Y. Wang, J. Zhang and Z. J. Ma, *Fuel*, 2022, **326**, 124971.
- 27 H. H. Zhang, F. L. Yu and J. J. Tang, *Chemical Minerals and Processing*, 2019, **48**, 57–61.
- 28 V. Strezov, J. A. Lucas, T. J. Evans and L. Strezov, *J. Therm. Anal. Calorim.*, 2004, **78**, 385–397.
- 29 L. Q. Cao, L. H. Zhang, Y. X. Guo and F. Q. Cheng, *Clean Coal Technol.*, 2020, **26**, 203–208.
- 30 D. D. Zhang, S. Q. Wu and S. Hu, *Non-Met. Mines*, 2014, **37**, 47–49.
- 31 C. C. Zhou, G. J. Liu, Z. C. Yan, T. Fang and R. W. Wang, *Fuel*, 2012, **97**, 644–650.
- 32 Z. J. Ma, Q. Zhang and H. T. Zhao, *Journal of Liaoning University of Engineering and Technology*, 2018, **37**, 575–579.
- 33 H. G. Li, *Hydrometallurgy*, Zhongnan University Press, Changsha, 1998.
- 34 J. F. Han, Y. Ha, M. Y. Guo, P. P. Zhao, Q. L. Liu, C. X. Liu, C. F. Song, N. J. X. B. Lu, D. G. Ma and Z. G. Li, *Ultrason. Sonochem.*, 2019, **59**, 104703.
- 35 G. K. Ren, D. L. Zhu and C. Tan, *J. Saf. Environ.*, 2014, **14**(1), 160–163.
- 36 J. Y. Zhang, J. W. Tong and P. M. Sun, *Hydrometall. China*, 2011, **30**(4), 316–319.
- 37 Q. C. Yang, *Research on extraction of alumina from coal gangue and preparation of functional materials*, China University of Mining and Technology, Beijing, 2020.
- 38 L. Han, W. G. Ren, B. Wang, X. X. He, L. J. Ma, Q. H. Huo, J. C. Wang, W. R. Bao and L. P. Chang, *Fuel*, 2019, **253**, 1184–1192.
- 39 K. Z. Yan, Y. X. Guo, J. C. Zhang, Q. Zhang and F. Q. Cheng, *Coal Convers.*, 2014, **37**(4), 85–90.