

# SCIENTIFIC REPORTS

OPEN

## Triple-doped $\text{KMnF}_3:\text{Yb}^{3+}/\text{Er}^{3+}/\text{Tm}^{3+}$ nanocubes: four-color upconversion emissions with strong red and near-infrared bands

Received: 16 June 2015  
Accepted: 23 October 2015  
Published: 26 November 2015

Hao Wang<sup>1</sup>, Xiaodong Hong<sup>1,3</sup>, Renlu Han<sup>1</sup>, Junhui Shi<sup>1</sup>, Zongjun Liu<sup>1,2</sup>, Shujuan Liu<sup>1</sup>, You Wang<sup>1</sup> & Yang Gan<sup>2</sup>

Triple-doped ( $\text{Yb}^{3+}/\text{Er}^{3+}/\text{Tm}^{3+}$ )  $\text{KMnF}_3$  nanocubes with uniform sizes of 250 nm were synthesized by a facile hydrothermal route using the oleic acid as the capping agent. It was found that these nanocubes can simultaneously exhibited four-color (blue, green, red and NIR) upconversion emissions under a single 980 nm near-infrared (NIR) laser excitation, which should have potential multicolor *in vivo* imaging applications. Specifically, the red (660 nm) and NIR (800 nm) peaks, known as two “optical windows” for imaging biological tissues, were strong. The spectral and pump analyses indicated the two-photon processes were responsible for the both red and NIR emissions.

Upconversion nano-particles (UCNPs) have the ability to convert lower energy (near-infrared (NIR) or infrared (IR)) radiation into high-energy radiation (ultraviolet or visible) via multiphoton absorption and energy transfer (ET) processes<sup>1</sup>, which are promising for applications in optical bioimaging<sup>2,3</sup>, bio-detection<sup>4,5</sup>, clinical diagnosis<sup>6</sup>, three-dimensional display technologies<sup>7</sup>, photocatalysis<sup>8</sup>, as well as solar cells<sup>9–13</sup>. To date, the rather popular UCNPs systems for biomedical imaging applications are mainly based on  $\text{Er}^{3+}$  and  $\text{Tm}^{3+}$  ions sensitized by  $\text{Yb}^{3+}$  ions with visible and near-infrared emissions<sup>14</sup>. The emissions of UCNPs in the red (660 nm,  $\text{Er}^{3+}/\text{Yb}^{3+}$ ) and NIR regions (800 nm,  $\text{Tm}^{3+}/\text{Yb}^{3+}$ ) are known as the two “optical windows” for imaging biological tissues<sup>15–17</sup>. The red emission is suitable for *in vitro* imaging because the images can be observed by naked eyes. *In vivo* imaging prefers NIR-to-NIR emissions, allowing certain penetration depth for inspection. For the red emissions, Bai *et al.*<sup>15</sup> and Tian *et al.*<sup>16</sup> showed that varying  $\text{Yb}^{3+}$  concentration or doping  $\text{Mn}^{2+}$  ions into the  $\text{NaYF}_4$  matrix were effective for red luminescence enhancement. For the NIR emissions, Chen *et al.*<sup>18</sup> reported that the UC NIR emission at 800 nm was increased by 43 times in  $\text{NaYF}_4:\text{Yb}^{3+}/\text{Tm}^{3+}$  nanoparticles by heavily doping with  $\text{Yb}^{3+}$  ions. Recently, Liu group<sup>19</sup> successfully prepared  $\text{KMnF}_3$  nanocrystals codoped with  $\text{Yb}^{3+}/\text{Er}^{3+}$  or  $\text{Yb}^{3+}/\text{Tm}^{3+}$  ions and found them showing substantially higher red and NIR emission intensity than that of the rare-earth doped  $\text{NaYF}_4$  nanocrystals. In general, most of the conventional imaging methods are monochrome and only able to detect one contrast agent at a time, limiting us to single parametric data. However, the unique properties of multicolor emissions, photostability, high penetration depth, and low photo damaging in principle enable UC materials to act as multi-color imaging probes for biomedical applications. In the pioneer work of multicolor imaging *in vivo*, Kobayashi *et al.*<sup>20</sup> employed a polyamidoamine dendrimer platform linked to five dye molecules as different optical probes, permitting five-color optical imaging using a multiple-excitation spectrally resolved fluorescence imaging technique. However, simultaneously providing multicolor excitation lights and guarantee their penetration depths

<sup>1</sup>School of Materials Science and Engineering, Harbin Institute of Technology, Harbin 150001. P. R. China. <sup>2</sup>School of Chemical Engineering and Technology, Harbin Institute of Technology, Harbin 150001. P. R. China. <sup>3</sup>College of Materials Science and Engineering, Liaoning Technical University, Fuxin city 123000. P. R. China. Correspondence and requests for materials should be addressed to Y.W. (email: y-wang@hit.edu.cn) or Y.G. (email: ygan@hit.edu.cn)

which are determined by the nature of light color itself are difficult, and thus it limits the practical applications of multicolor *in vivo* imaging.

Due to multicolor emission characteristics of UCNPs, simultaneous detection of multiple analytes or optical probes in a complex sample should be feasible if appropriate UCNPs were prepared and used. Ideally, *in vivo* multicolor tissue characterization<sup>21</sup> relies on: (1) the identification of multiple targets; (2) target-specific optical probes with distinct fluorescent properties; and (3) effective real-time multi-color optical cameras that permit accurate unmixing of different fluorescent probes with a single NIR excitation *in vivo*. The present rare-earth doped nanocrystals are generally not suitable for multiplexing biodetection, due to their limited number of colors. It is therefore necessary to develop UCNPs with multicolor fluorescence emissions under NIR excitation at the same wavelength. Along this line, several recent studies focused on multicolor UC emission with a more boarder spectrum of color output by using different host/activator combinations. Rantanen *et al.*<sup>22</sup> demonstrated simultaneous detection of two analytes using UC donors with multipeak emission characteristics. Nann *et al.*<sup>23</sup> reported the preparation of complex colloidal UCNPs systems and observation of the four-color (blue, green, red and NIR) emissions. They synthesized four different types of UCNPs by doping NaYbF<sub>4</sub> with different rare-earth ions, and thus obtain a four-color UC emission system for the potential multiplexing analysis by mixing these UCNPs. Jiang *et al.*<sup>24</sup> prepared core-shell structured nanoparticles with UCNP core and dye-doped silica shell to enable multi-color emissions for multiplex bioassays.

Herein, we developed a facile hydrothermal strategy to obtain multicolor emissions by preparing tri-doped KMnF<sub>3</sub>:Yb<sup>3+</sup>/Er<sup>3+</sup>/Tm<sup>3+</sup>. The as-prepared UCNPs exhibit four-color (blue, green, red and NIR) UC emissions upon a single excitation at 980 nm, which should have a potential use in multicolor *in vivo* imaging for simultaneously providing multi-color excitation lights with deep imaging depth. In addition, UCNPs are a promising candidate to harvest NIR sunlight and improve the power conversion efficiency of solar cells, i.e., dye sensitized solar cell (DSSC)<sup>25</sup>. As some DSSC are designed based on the simultaneous adsorption of different dyes which have different absorption bands, the developed UCNPs with multi-color emission bands matching the absorption bands of dyes may have a potential to improve overall absorption efficiency<sup>12</sup>.

## Results and Discussion

Figure 1a is a typical SEM image of as-prepared KMnF<sub>3</sub>:20%Yb<sup>3+</sup>/2%Er<sup>3+</sup>/2%Tm<sup>3+</sup> UCNPs and Fig. 1b shows the average size distribution of the samples corresponding to those in Fig. 1a. It can be seen that the UCNPs are well dispersed and exhibit uniform nanocube shape with an average size of 250 nm. The crystal structures and the phase purity of the as-prepared tri-doped KMnF<sub>3</sub> nanocubes were examined by the X-ray diffraction (XRD) analysis (see Fig. 1c). All peaks are sharp and match well with the standard JCPDS No.17-0116 of KMnF<sub>3</sub>, indicating high phase purity and crystallinity of obtained samples.


Typical UC emission spectra for various samples under diode laser excitation of 980 nm are shown in Fig. 2. KMnF<sub>3</sub>:Yb<sup>3+</sup>/Tm<sup>3+</sup> samples show one blue emission band at 476 nm and one NIR band at 800 nm (Fig. 2a), corresponding to the <sup>1</sup>G<sub>4</sub> (Tm<sup>3+</sup>) → <sup>3</sup>H<sub>6</sub> (Tm<sup>3+</sup>), and <sup>3</sup>H<sub>4</sub> (Tm<sup>3+</sup>) → <sup>3</sup>H<sub>6</sub> (Tm<sup>3+</sup>) transitions of Tm<sup>3+</sup> ions, respectively. KMnF<sub>3</sub>:20%Yb<sup>3+</sup>/2%Er<sup>3+</sup> samples show only a single red emission at 660 nm corresponds to the <sup>4</sup>F<sub>9/2</sub> → <sup>4</sup>I<sub>15/2</sub> transitions of Er<sup>3+</sup> ions (Fig. 2b). Very interestingly, tri-doped KMnF<sub>3</sub>:Yb<sup>3+</sup>/Er<sup>3+</sup>/Tm<sup>3+</sup> nanocubes exhibits four-colored bands (Fig. 2c). Noteworthy that, besides three emission bands of 476 nm, 800 nm owing to Tm<sup>3+</sup> ions and the 660 nm band owing to Er<sup>3+</sup> ions are all preserved in the spectra, a new green UC emission centered at 540 nm is also observed at the same time.

Firstly, appearance of the new 540 nm green UC emission can be explained as follows. Usually, the single red UC emission (660 nm) is observed for Yb<sup>3+</sup>/Er<sup>3+</sup> codoped KMnF<sub>3</sub> samples. However, for tri-doped KMnF<sub>3</sub>:Yb<sup>3+</sup>/Er<sup>3+</sup>/Tm<sup>3+</sup> samples, owing to the coexistence of Er<sup>3+</sup> and Tm<sup>3+</sup>, the cross relaxation <sup>3</sup>F<sub>4</sub> (Tm) + <sup>4</sup>F<sub>9/2</sub> (Er) → <sup>1</sup>G<sub>4</sub> (Tm) + <sup>4</sup>I<sub>15/2</sub> (Er) between Tm<sup>3+</sup> and Er<sup>3+</sup> ions in KMnF<sub>3</sub> may cause decreases in population of <sup>4</sup>F<sub>9/2</sub> state and increases in population of <sup>1</sup>G<sub>4</sub> state<sup>26</sup>. The green emission is thus generated through the <sup>2</sup>H<sub>11/2</sub>/<sup>4</sup>S<sub>3/2</sub> → <sup>4</sup>I<sub>15/2</sub> transition of Er<sup>3+</sup> ions as explained in detail below.


Secondly, UC emission intensity (*I*) was further measured as a function of laser power (*P*) (Fig. 3) to explore the UC mechanism of Yb<sup>3+</sup>, Tm<sup>3+</sup>, and Er<sup>3+</sup> ions in KMnF<sub>3</sub> matrix. Because  $I_{UC} \propto P^n$  holds for the unsaturated UC process, where *n* is the number of pump photons absorbed per upconverted photons emitted<sup>27</sup>, the value of *n* can thus be determined to be the slope after linearly fitting the I-P data in a double logarithmic plot. For the tri-doped KMnF<sub>3</sub>:Yb<sup>3+</sup>/Er<sup>3+</sup>/Tm<sup>3+</sup> sample, the obtained *n* values are 2.94, 1.95, 1.92, and 1.99 respectively for the UC emission peaks at 476 nm (blue), 540 nm (green), 660 nm (red), and 800 nm (NIR). Therefore, it can be deduced that the three-photon process is responsible for blue UC emission, two-photon process is responsible for green red and 800 nm UC emissions.

At last, the overall UC emission mechanism and population process in rare-earth doped KMnF<sub>3</sub> is schematically illustrated in Fig. 4. Upon excitation at 980 nm, the red UC emission (660 nm) can be ascribed to nonradiative energy transfer from the <sup>4</sup>S<sub>3/2</sub> levels of Er<sup>3+</sup> to the <sup>4</sup>T<sub>1</sub> level of Mn<sup>2+</sup>, followed by the falling-back transition to the <sup>4</sup>F<sub>9/2</sub> level of Er<sup>3+</sup> and the <sup>4</sup>F<sub>9/2</sub> to <sup>4</sup>I<sub>15/2</sub> transition.

It would be interesting to have a closer look at the role of Mn<sup>2+</sup> played in the multi-photon excited mechanism, based on the literature findings, for both double-doped KMnF<sub>3</sub>:Yb/Er system and triple-doped KMnF<sub>3</sub>:Yb/Er/Tm system. For the simpler double-doped KMnF<sub>3</sub>:Yb/Er system, it is accepted that Mn<sup>2+</sup> ions play the important role in the single-band UC emission (the complete disappearance of 540 nm green emission and appearance of only 660 nm red emission). According to the literature, close proximity

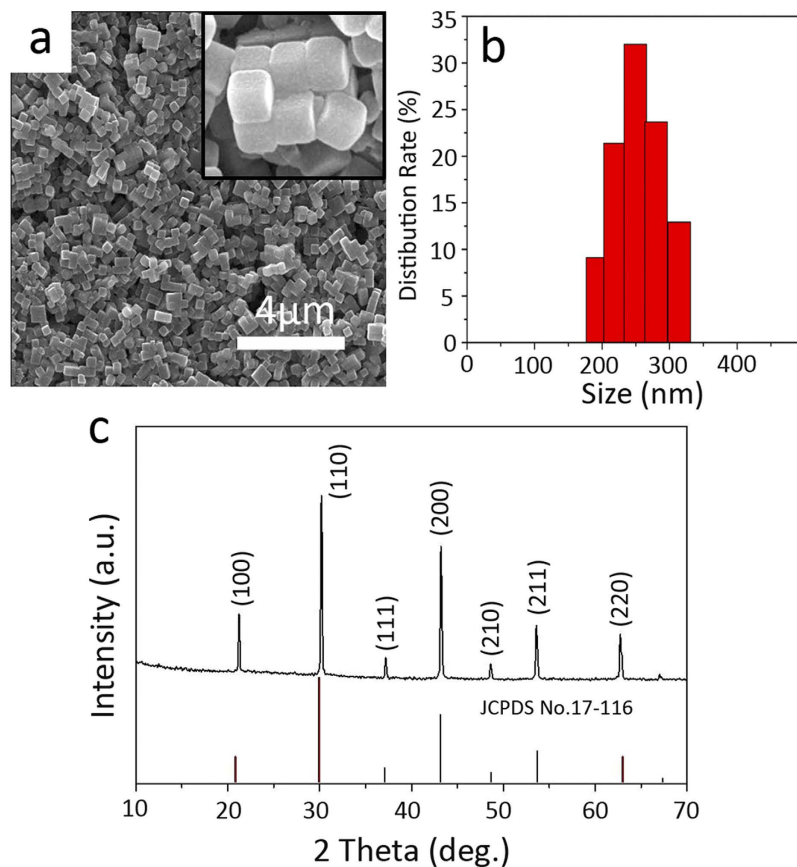


**Figure 1.** (a) SEM images of the as-synthesized  $\text{KMnF}_3:20\% \text{Yb}^{3+}$ ,  $2\% \text{Er}^{3+}$ ,  $2\% \text{Tm}^{3+}$  nanocubes. (b) Size distribution of  $\text{KMnF}_3:20\% \text{Yb}^{3+}$ ,  $2\% \text{Er}^{3+}$ ,  $2\% \text{Tm}^{3+}$  nanocubes. (c) XRD patterns of  $\text{KMnF}_3:20\% \text{Yb}^{3+}$ ,  $2\% \text{Er}^{3+}$ ,  $2\% \text{Tm}^{3+}$  nanocubes.

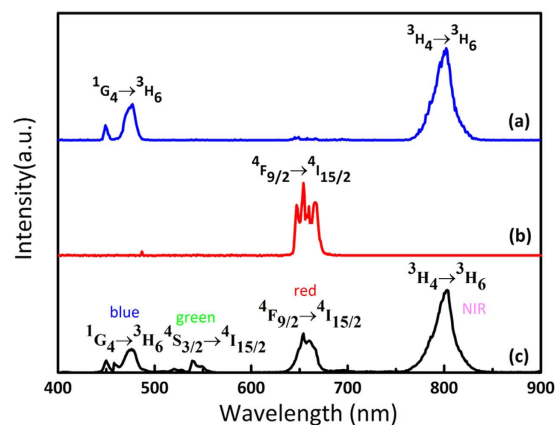


**Figure 2.** Calibrated UC emission spectra of  $\text{KMnF}_3$  samples under the excitation of a 980 nm. (a) Doped with 2 mol %  $\text{Tm}^{3+}$  and 20 mol %  $\text{Yb}^{3+}$ , (b) doped with 2 mol %  $\text{Er}^{3+}$  and 20 mol %  $\text{Yb}^{3+}$ , and (c) doped with 2 mol %  $\text{Tm}^{3+}$ , 2 mol %  $\text{Er}^{3+}$  and 20 mol %  $\text{Yb}^{3+}$ .

and excellent overlap of energy levels of the  $\text{Mn}^{2+}$  and  $\text{Er}^{3+}$  ions in the host lattices cause very efficient nonradiative energy transfer from the  $^2\text{H}_{11/2}$  and  $^4\text{S}_{3/2}$  levels of  $\text{Er}^{3+}$  to the  $^4\text{T}_1$  level of  $\text{Mn}^{2+}$ <sup>16,28</sup>. And this nonradiative energy transfer process is followed by the back-energy transfer to the  $^4\text{F}_{9/2}$  level of  $\text{Er}^{3+}$ , thus leading to only 660 nm red emission. The mechanism is illustrated in the right part of Fig. 4 where only three  $\text{Yb}^{3+}$ ,  $\text{Mn}^{2+}$  and  $\text{Er}^{3+}$  ions are involved. On the other hand, for the more complex triple-doped  $\text{KMnF}_3:\text{Yb}/\text{Er}/\text{Tm}$  system, as illustrated in Fig. 4 where all four  $\text{Yb}^{3+}$ ,  $\text{Mn}^{2+}$ ,  $\text{Er}^{3+}$  and  $\text{Tm}^{3+}$

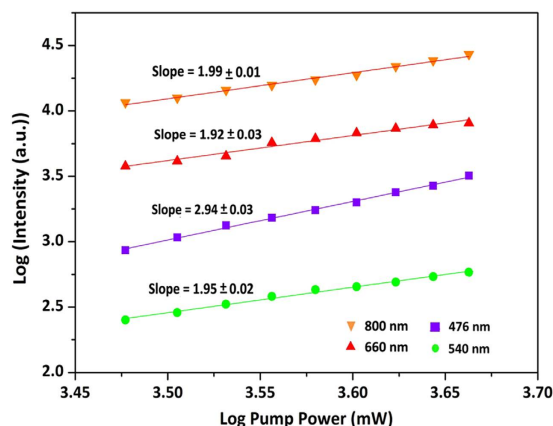

**Figure 3.** Logarithmic plots of the intensity of each upconversion band in Fig. 2c versus the excitation density in the dispersed  $\text{KMnF}_3$  nanocubes tridoped with 2 mol %  $\text{Tm}^{3+}$ , 2 mol %  $\text{Er}^{3+}$  and 20 mol %  $\text{Yb}^{3+}$ . The initial input power employed for the measurement is 2W.

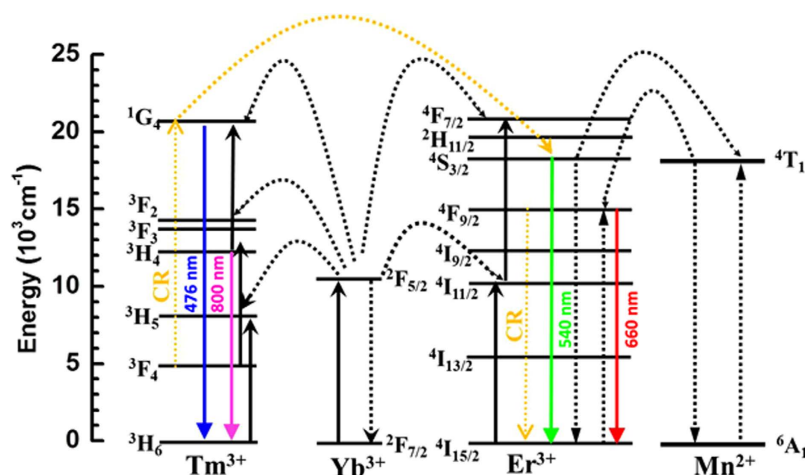

**Figure 4.** Schematic of the energy level diagram for the  $\text{Er}^{3+}$ ,  $\text{Tm}^{3+}$ , and  $\text{Yb}^{3+}$  ions as well as the proposed UC mechanisms to explain the blue, green, red and NIR UC emissions. CR = Cross relaxation.

ions are involved, reappearance of 540 nm green emission is due to the additional resonant cross relaxation process between  $\text{Er}^{3+}$  and  $\text{Tm}^{3+}$  ions:  ${}^3\text{F}_4$  ( $\text{Tm}^{3+}$ ) +  ${}^4\text{F}_{9/2}$  ( $\text{Er}^{3+}$ )  $\rightarrow$   ${}^1\text{G}_4$  ( $\text{Tm}^{3+}$ ) +  ${}^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ). This process causes the population of  ${}^1\text{G}_4$  state of  $\text{Tm}^{3+}$  ions and depopulation of  ${}^4\text{F}_{9/2}$  state of  $\text{Er}^{3+}$  ions. Because the energy level of  ${}^1\text{G}_4$  state ( $\text{Tm}^{3+}$ ) equals to that of  ${}^4\text{F}_{7/2}$ , photons loose fraction of energy in  ${}^4\text{F}_{7/2}$  ( $\text{Er}^{3+}$ ) and drop to  ${}^2\text{H}_{11/2}/{}^4\text{S}_{3/2}$  ( $\text{Er}^{3+}$ ) state through the multiphonon assisted relaxations, and finally leading to 540 nm green emission.

For the blue (476 nm) and NIR (800 nm) emissions, the energy transfer from the first  $\text{Yb}^{3+} \rightarrow \text{Tm}^{3+}$  excites the  ${}^3\text{H}_6 \rightarrow {}^3\text{H}_5$  transition, at the same time the redundant energy dissipated by phonons. Then, the  $\text{Tm}^{3+}$  ion is firstly relaxes to the lower  ${}^3\text{F}_4$  state and further promoted to the  ${}^3\text{F}_{2,3}$  state through a continuous  $\text{Yb}^{3+} \rightarrow \text{Tm}^{3+}$  energy transfer process. The  ${}^3\text{H}_4$  state can be populated by the efficient non-radiative relaxation from the  ${}^3\text{F}_{2,3}$  state. The strong NIR UC (800 nm) is due to the  ${}^3\text{H}_4 \rightarrow {}^3\text{H}_6$  transition. In addition, the blue emission (476 nm) corresponds to the of  ${}^1\text{G}_4 \rightarrow {}^3\text{H}_6$  transition, where the  ${}^1\text{G}_4$  level is populated by the efficient energy transfer from the  ${}^3\text{H}_4$  state. The unexpected green emission (540 nm) is attributed to the co-doping of  $\text{Tm}^{3+}/\text{Er}^{3+}$  ions in  $\text{KMnF}_3$  matrix. The resonant cross relaxation process  ${}^3\text{F}_4$  ( $\text{Tm}^{3+}$ ) +  ${}^4\text{F}_{9/2}$  ( $\text{Er}^{3+}$ )  $\rightarrow$   ${}^1\text{G}_4$  ( $\text{Tm}^{3+}$ ) +  ${}^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) between  $\text{Er}^{3+}$  and  $\text{Tm}^{3+}$  ions leads to the population of  ${}^1\text{G}_4$  state of  $\text{Tm}^{3+}$  ions and depopulation of  ${}^4\text{F}_{9/2}$  state of  $\text{Er}^{3+}$  ions, and then to  ${}^2\text{H}_{11/2}/{}^4\text{S}_{3/2}$  state through the multiphonon assisted relaxations<sup>29</sup>.

## Conclusions

In summary, we have developed a facile hydrothermal method for preparation of tri-doped  $\text{KMnF}_3$  nanocubes with simultaneous four-color (blue, green, red and NIR) UC emissions. Of particular interests, the red and NIR bands, known as so-called “optical window” for imaging biological tissues, are strong. The

spectral and pump dependence analyses indicate that two-photon process is responsible for the red and NIR emissions. We believe that this proof-of-concept demonstration of a multicolor emission across a broader spectra (blue to NIR) using tri-doped single  $\text{KMnF}_3$  host system may have potential applications for multiplexing analysis and/or multi-optical window imaging of biological tissues.

## Methods

**Materials.**  $\text{MnCl}_2$ , KF, KOH, ethanol, oleic acid (OA) at AR grade were obtained from Sinopharm Chemical Reagent Company, China.  $\text{YbCl}_3 \cdot 6\text{H}_2\text{O}$ ,  $\text{ErCl}_3 \cdot 6\text{H}_2\text{O}$ ,  $\text{TmCl}_3 \cdot 6\text{H}_2\text{O}$  were obtained from CongHua City JianFeng Rare Earth Company, China. All other chemical agents obtained from commercial routes were of analytical grade and were used without further purification.

**Preparation of tri-doped  $\text{KMnF}_3$  nanocubes.** The rare-earth tri-doped  $\text{KMnF}_3$  nanocubes were hydrothermally prepared by using  $\text{MnCl}_2$  and KF as precursors at  $180^\circ\text{C}$ . Typically, 1.5 g (27 mmol) KOH, 2 mL  $\text{H}_2\text{O}$ , 4 mL ethanol (48 mmol) and 9 mL of (24 mmol) OA (90 wt%) were well mixed at the room temperature for 10 min. A white viscous solution was obtained. The 10 mL (0.2 mol/L)  $\text{MnCl}_2$  solution, 15.5 mg (0.4 mmol)  $\text{YbCl}_3 \cdot 6\text{H}_2\text{O}$ , 1.5 mg (0.04 mmol)  $\text{ErCl}_3 \cdot 6\text{H}_2\text{O}$  and 1.5 mg (0.04 mmol)  $\text{TmCl}_3 \cdot 6\text{H}_2\text{O}$  was subsequently added and vigorously stirred for 20 min. Then 8 mL (1.25 mol/L) KF was added into the above solution. After incubation for 1 h, the mixture was transferred to a 50 mL Teflon-lined autoclave, and then heated at  $180^\circ\text{C}$  for 24 h. After cooling down, the products were removed by centrifugation then washed with ethanol, and dried under vacuum at room temperature for 24 h.

**Characterization.** X-Ray powder diffraction (XRD) characterization were carried out on a Rigaku D/max- $\gamma$ B diffractometer equipped with a rotating anode and a Cu  $K\alpha$  source ( $\lambda = 0.15418\text{ nm}$ ). SEM micrographs were obtained using a field emission scanning electron microscope (FESEM, MX2600FE). Upconversion luminescence spectra were measured by a regeneratively amplified 980 nm diode laser (Hi-Tech Optoelectronics Co. Ltd., Beijing). The emitted UC fluorescence signal was collected by a lens-coupled monochromator (Zolix Instruments Co. Ltd., Beijing) at 3 nm spectral resolution with an attached photomultiplier tube (Hamamatsu CR131). All measurements were performed at room temperature.

## References

- Zou, W., Visser, C., Maduro, J. A., Pshenichnikov, M. S. & Hummelen, J. C. Broadband dye-sensitized upconversion of near-infrared light. *Nat. Photonics*. **6**, 560–564 (2012).
- Zhan, Q. *et al.* Using 915 nm Laser Excited  $\text{Tm}^{3+}/\text{Er}^{3+}/\text{Ho}^{3+}$ -Doped  $\text{NaYbF}_4$  Upconversion Nanoparticles for *in vitro* and Deeper *in vivo* Bioimaging without Overheating Irradiation. *ACS Nano*. **5**, 3744–3757 (2011).
- Zhou, J. *et al.* Efficient Dual-Modal NIR-to-NIR Emission of Rare Earth Ions Co-doped Nanocrystals for Biological Fluorescence Imaging. *J. Phys. Chem. Lett.* **4**, 402–408 (2013).
- Chen, G. *et al.* ( $\alpha$ - $\text{NaYbF}_4$ : $\text{Tm}^{3+}$ )/ $\text{CaF}_2$  Core/Shell Nanoparticles with Efficient Near-Infrared to Near-Infrared Upconversion for High-Contrast Deep Tissue Bioimaging. *ACS Nano*. **6**, 8280–8287 (2012).
- Liu, Y. *et al.* Amine-Functionalized Lanthanide-Doped Zirconia Nanoparticles: Optical Spectroscopy, Time-Resolved Fluorescence Resonance Energy Transfer Biodetection, and Targeted Imaging. *J. Am. Chem. Soc.* **134**, 15083–15090 (2012).
- Yi, G., Peng, Y. & Gao, Z. Strong Red-Emitting near-Infrared-to-Visible Upconversion Fluorescent Nanoparticles. *Chem. Mater.* **23**, 2729–2734 (2011).
- Wang, F. *et al.* Simultaneous phase and size control of upconversion nanocrystals through lanthanide doping. *Nature* **463**, 1061–1065 (2010).
- Wang, W. *et al.* Graphene supported  $\beta$ - $\text{NaYF}_4$ : $\text{Yb}^{3+}$ ,  $\text{Tm}^{3+}$  and N doped P25 nanocomposite as an advanced NIR and sunlight driven upconversion photocatalyst. *Appl. Surf. Sci.* **282**, 832–837 (2013).
- Shalav, A., Richards, B. S. & Green, M. A. Luminescent layers for enhanced silicon solar cell performance: Up-conversion. *Sol. Energy Mater. Sol. Cells*. **91**, 829–842 (2007).
- Liang, L. *et al.* Highly uniform, bifunctional core/double-shell-structured  $\beta$ - $\text{NaYF}_4$ : $\text{Er}^{3+}$ ,  $\text{Yb}^{3+}$ @  $\text{SiO}_2$ @ $\text{TiO}_2$  hexagonal sub-microprisms for high-performance dye sensitized solar cells. *Adv. Mater.* **25**, 2174–2180 (2013).
- De Wild, J. *et al.* Upconverter solar cells: materials and applications. *Energy Environ. Sci.* **4**, 4835–4848 (2011).
- Shan, G. B. & Demopoulos, G. P. Near-Infrared Sunlight Harvesting in Dye-Sensitized Solar Cells Via the Insertion of an Upconverter- $\text{TiO}_2$  Nanocomposite Layer. *Adv. Mater.* **22**, 4373–4377 (2010).
- Shan, G. B., Assaoui, H. & Demopoulos, G. P. Enhanced Performance of Dye-Sensitized Solar Cells by Utilization of an External, Bifunctional Layer Consisting of Uniform  $\beta$ - $\text{NaYF}_4$ : $\text{Er}^{3+}/\text{Yb}^{3+}$  Nanoplatelets. *ACS Appl. Mater. Interfaces*. **3**, 3239–3243 (2011).
- Heer, S., Kömpe, K., Güdel, H. U. & Haase, M. Highly efficient multicolour upconversion emission in transparent colloids of lanthanide-doped  $\text{NaYF}_4$  nanocrystals. *Adv. Mater.* **16**, 23–24 (2004).
- Bai, Z. *et al.* The single-band red upconversion luminescence from morphology and size controllable  $\text{Er}^{3+}/\text{Yb}^{3+}$  doped  $\text{MnF}_2$  nanostructures. *J. Mater. Chem. C*. **2**, 1736–1741 (2014).
- Tian, G. *et al.*  $\text{Mn}^{2+}$  Dopant-Controlled Synthesis of  $\text{NaYF}_4$ : $\text{Yb}/\text{Er}$  Upconversion Nanoparticles for *in vivo* Imaging and Drug Delivery. *Adv. Mater.* **24**, 1226–1231 (2012).
- König, K. Multiphoton microscopy in life sciences. *J. Microsc.* **200**, 83–104 (2000).
- Chen, G., Ohulchanskyy, T. Y., Kumar, R., Ågren, H. & Prasad, P. N. Ultrasmall monodisperse  $\text{NaYF}_4$ : $\text{Yb}^{3+}/\text{Tm}^{3+}$  nanocrystals with enhanced near-Infrared to near-Infrared upconversion photoluminescence. *ACS Nano*. **4**, 3163–3168 (2010).
- Wang, J., Wang, F., Wang, C., Liu, Z. & Liu, X. Single-Band Upconversion Emission in Lanthanide-Doped  $\text{KMnF}_3$  Nanocrystals. *Angew. Chem., Int. Ed.* **50**, 10369–10372 (2011).
- Kobayashi, H. *et al.* Multimodal nanoprobes for radionuclide and five-color near-infrared optical lymphatic imaging. *ACS Nano*. **1**, 258–264 (2007).
- Longmire, M., Kosaka, N., Ogawa, M., Choyke, P. L. & Kobayashi, H. Multicolor *in vivo* targeted imaging to guide real-time surgery of HER2-positive micrometastases in a two-tumor coincident model of ovarian cancer. *Cancer. Sci.* **100**, 1099–1104 (2009).

22. Rantanen, T. *et al.* Upconverting phosphors in a dual-parameter LRET-based hybridization assay. *Analyst.* **134**, 1713–1716 (2009).
23. Ehlert, O., Thomann, R., Darbandi, M. & Nann, T. A four-color colloidal multiplexing nanoparticle system. *ACS Nano.* **2**, 120–124 (2008).
24. Li, Z., Zhang, Y. & Jiang S. Multicolor core/shell-structured upconversion fluorescent Nanoparticles. *Adv. Mater.* **20**, 4765–4769 (2008).
25. Yuan, C. *et al.* Simultaneous Multiple Wavelength Upconversion in a Core-Shell Nanoparticle for Enhanced Near Infrared Light Harvesting in a Dye-Sensitized Solar Cell. *ACS Appl. Mater. Interfaces.* **6**, 18018–18025 (2014).
26. Li, J. J. *et al.* Pump-power tunable white upconversion emission in lanthanide-doped hexagonal NaYF<sub>4</sub> nanorods. *Opt. Mater.* **33**, 882–887 (2011).
27. Guan, Y., Huang, Y. & Jin Seo, H. The blue cooperative up-conversion luminescence in Ca<sub>9</sub>Yb[VO<sub>4</sub>]<sub>7</sub> ceramic. *Mater. Lett.* **89**, 126–128 (2012).
28. Zhang, Y., Lin, J., Vijayaragavan, D., V., Bhakoo, K. K. & Tan, T. Y. Tuning sub-10 nm single-phase NaMnF<sub>3</sub> nanocrystals as ultrasensitive hosts for pure intense fluorescence and excellent T<sub>1</sub> magnetic resonance imaging. *Chem. Commun.* **48**, 10322–10324 (2012).
29. Lü, W. *et al.* White up-conversion luminescence in rare-earth-ion-doped YAlO<sub>3</sub> nanocrystals. *J. Phys. Chem. C.* **112**, 15071–15074 (2008).

### Acknowledgements

We thank Prof. Zhiguo Zhang for the fruitful discussion on UC emission mechanism. This project was sponsored by the National Basic Research Program of China (973 Program) under grant nos.2012CB934100 and 2011CB013200, the Key Laboratory Fund of HIT, interdisciplinary Basic Research of Science-Engineering-Medicine in HIT, and National Natural Science Foundation of China (NSFC).

### Author Contributions

H.W. designed and performed the experiments and wrote the manuscript together with Y.W. and X.D.H. R.L.H. synthesized the KMnF<sub>3</sub> NPs and provided the SEM images. J.H.S. and Z.J.L. designed and managed the upconversion luminescence spectra. S.J.L. and Y.G. reviewed the discussed the results. All the authors reviewed the manuscript.

### Additional Information

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Wang, H. *et al.* Triple-doped KMnF<sub>3</sub>:Yb<sup>3+</sup>/Er<sup>3+</sup>/Tm<sup>3+</sup> nanocubes: four-color upconversion emissions with strong red and near-infrared bands. *Sci. Rep.* **5**, 17088; doi: 10.1038/srep17088 (2015).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>