

1-Butylpyridinium bis(1,2-dicyanoethene-1,2-dithiolato)nickelate(III)

Hai-Bao Duan

School of Biochemical and Environmental Engineering, Nanjing Xiaozhuang College, Nanjing 210017, People's Republic of China
Correspondence e-mail: duanhaibao4660@163.com


Received 5 October 2011; accepted 12 October 2011

Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(\text{C}-\text{C}) = 0.005$ Å; R factor = 0.036; wR factor = 0.109; data-to-parameter ratio = 13.0.

The Ni^{III} atom in the anion of the title complex, (C₉H₁₄N)⁺[Ni(C₄N₂S₂)₂]⁻, is coordinated by four S atoms of two maleonitriledithiolate ligands, and exhibits a square-planar coordination geometry.

Related literature

For background to designed functional materials, see: Nishijo *et al.* (2000); Robertson & Cronin (2002); Ni *et al.* (2005). For related structures, see: Ni *et al.* (2004); Ren *et al.* (2004, 2008); Duan *et al.* (2010). For the synthesis of disodium maleonitriledithiolate and 1-butane-pyridinium bromide, see: Davison & Holm (1967); Yao *et al.* (2008).

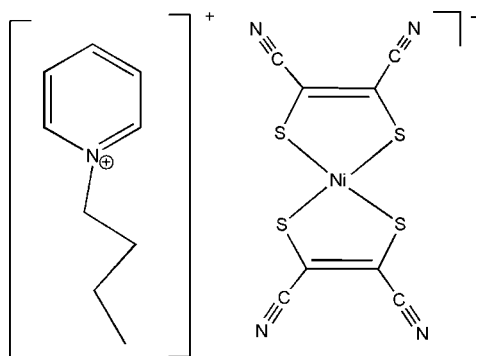

Experimental

Crystal data

(C₉H₁₄N)[Ni(C₄N₂S₂)₂]
 $M_r = 475.30$
Triclinic, $P\bar{1}$
 $a = 9.2764$ (11) Å
 $b = 9.9863$ (11) Å
 $c = 12.7115$ (15) Å
 $\alpha = 81.695$ (9)°
 $\beta = 75.882$ (10)°

$\gamma = 64.480$ (11)°
 $V = 1029.5$ (2) Å³
 $Z = 2$
Cu $K\alpha$ radiation
 $\mu = 5.25$ mm⁻¹
 $T = 293$ K
 $0.3 \times 0.1 \times 0.1$ mm

Data collection

Bruker SMART CCD area-detector diffractometer
Absorption correction: multi-scan (SADABS; Sheldrick, 2002)
 $T_{\min} = 0.559$, $T_{\max} = 0.591$
7461 measured reflections
3196 independent reflections
2499 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.018$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.036$
 $wR(F^2) = 0.109$
 $S = 1.04$
3196 reflections
245 parameters
1 restraint
H-atom parameters constrained
 $\Delta\rho_{\text{max}} = 0.36$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.33$ e Å⁻³

Table 1

Selected bond lengths (Å).

Ni1—S1	2.1501 (8)	Ni1—S3	2.1458 (8)
Ni1—S2	2.1436 (8)	Ni1—S4	2.1461 (8)

Data collection: *SMART* (Bruker, 2000); cell refinement: *SAINTE* (Bruker, 2000); data reduction: *SAINTE*; program(s) used to solve structure: *SHELXTL* (Sheldrick, 2008); program(s) used to refine structure: *SHELXTL*; molecular graphics: *SHELXTL*; software used to prepare material for publication: *SHELXTL*.

The author thanks the Nanjing Xiaozhuang College of Jiangsu Province, P. R. China, for financial support (grant No. 2010KYQN28).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: TK2798).

References

- Bruker (2000). *SMART* and *SAINTE* Bruker AXS Inc., Madison, Wisconsin, USA.
- Davison, A. & Holm, H. R. (1967). *Inorg. Synth.* **10**, 8–26.
- Duan, H. B., Ren, X. M. & Meng, Q. J. (2010). *Coord. Chem. Rev.* **254**, 1509–1522.
- Ni, C. L., Dang, D. B., Song, Y., Song, G., Li, Y. Z., Ni, Z. P., Tian, Z. F., Wen, L. L. & Meng, Q. J. (2004). *Chem. Phys. Lett.* **396**, 353–358.
- Ni, Z. P., Ren, X. M., Ma, J., Xie, J. L., Ni, C. L., Chen, Z. D. & Meng, Q. J. (2005). *J. Am. Chem. Soc.* **127**, 14330–14338.
- Nishijo, J., Ogura, E., Yamaura, J., Miyazaki, A., Enoki, T., Takano, T., Kuwatani, Y. & Lyoda, M. (2000). *Solid State Commun.* **116**, 661–664.
- Ren, X. M., Okudera, H., Kremer, R. K., Song, Y., He, C., Meng, Q. J. & Wu, P. H. (2004). *Inorg. Chem.* **43**, 2569–2576.
- Ren, X. M., Sui, Y. X., Liu, G. X. & Xie, J. L. (2008). *J. Phys. Chem. A*, **112**, 8009–8014.
- Robertson, N. & Cronin, L. (2002). *Coord. Chem. Rev.* **227**, 93–127.
- Sheldrick, G. M. (2002). *SADABS*. University of Göttingen, Germany.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Yao, B. Q., Sun, J. S., Tian, Z. F., Ren, X. M., Gu, D. W., Shen, L. J. & Xie, J. L. (2008). *Polyhedron*, **27**, 2833–2844.

supplementary materials

Acta Cryst. (2011). E67, m1567 [doi:10.1107/S1600536811042103]

1-Butylpyridinium bis(1,2-dicyanoethene-1,2-dithiolato)nickelate(III)

H.-B. Duan

Comment

Supramolecular chemistry and molecular crystal engineering, which is the planning and utilization of crystal-oriented syntheses for the bottom-up construction of functional molecular solids from molecules and ions, are powerful tools for the assembly of designed functional materials (Robertson & Cronin, 2002). Bis-1,2-dithiolene complexes of transition metals have been widely studied due to their novel properties and applications in the areas of near-infrared (near-IR) dyes, conducting, magnetic and non-linear optical materials (Nishijo *et al.*, 2000; Ni *et al.*, 2005). These applications arise due to a combination of functional properties, specific geometries and intermolecular interactions. Herein, we report the crystal structure of the title compound (I).

The molecular structure of (I) is illustrated in Fig. 1. and selected bond distances are given in Table 1. The asymmetric units comprises one $[\text{Ni}(\text{mnt})_2]^-$ monoanion and one 1-butyl-pyridinium cation. The Ni ion in the $[\text{Ni}(\text{mnt})_2]^-$ anion is coordinated by four sulfur atoms of two mnt^{2-} ligands, and exhibits square-planar coordination geometry. The bond lengths in the anion are in good agreement with those found in other $[\text{Ni}(\text{mnt})_2]^-$ compounds (Ni *et al.*, 2004; Ren *et al.*, 2004; Duan *et al.*, 2010; Ren *et al.*, 2008).

Experimental

All reagents and chemicals were purchased from commercial sources and used without further purification. The starting materials disodium maleonitriledithiolate (Davison *et al.*, 1967) and 1-butyl-pyridinium bromide (Yao *et al.*, 2008) were synthesized following the literature procedures. Disodium maleonitriledithiolate (456 mg, 2.5 mmol) and nickel chloride hexahydrate (297 mg, 1.25 mmol) were mixed under stirring in water (20 ml) at room temperature. Subsequently, a solution of 1-butyl-pyridinium bromide (1.5 mmol) in methanol (10 ml) was added to the mixture. The red precipitate that was immediately formed was filtered off and washed with methanol. Then, a methanol solution of I_2 (205 mg, 0.8 mmol) was added slowly. After stirring for 40 minutes, the mixture was allowed to stand overnight. The microcrystals formed were recrystallized from acetone to give black blocks.

Refinement

The C-bound H atoms were geometrically placed ($\text{C}-\text{H} = 0.93-0.97 \text{ \AA}$) and refined as riding with $U_{\text{iso}}(\text{H}) = 1.2-1.5U_{\text{eq}}(\text{C})$.

Figures

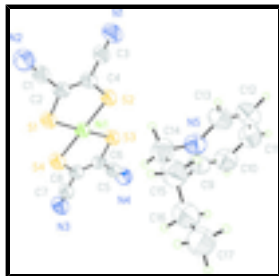


Fig. 1. The molecular structures of the ionic components of (I), showing the atom-numbering scheme and displacement ellipsoids at the 30% probability level.

1-Butylpyridinium bis(1,2-dicyanoethene-1,2-dithiolato)nicklate(III)

Crystal data

(C₉H₁₄N)[Ni(C₄N₂S₂)₂]

$M_r = 475.30$

Triclinic, $P\bar{1}$

Hall symbol: -P 1

$a = 9.2764$ (11) Å

$b = 9.9863$ (11) Å

$c = 12.7115$ (15) Å

$\alpha = 81.695$ (9)°

$\beta = 75.882$ (10)°

$\gamma = 64.480$ (11)°

$V = 1029.5$ (2) Å³

$Z = 2$

$F(000) = 486$

$D_x = 1.533$ Mg m⁻³

Cu $K\alpha$ radiation, $\lambda = 1.54178$ Å

$\mu = 5.25$ mm⁻¹

$T = 293$ K

Block, black

$0.3 \times 0.1 \times 0.1$ mm

Data collection

Bruker SMART CCD area-detector diffractometer

Radiation source: fine-focus sealed tube graphite

φ and ω scans

Absorption correction: multi-scan (SADABS; Sheldrick, 2002)

$T_{\min} = 0.559$, $T_{\max} = 0.591$

7461 measured reflections

3196 independent reflections

2499 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.018$

$\theta_{\max} = 62.6^\circ$, $\theta_{\min} = 3.6^\circ$

$h = -10 \rightarrow 9$

$k = -11 \rightarrow 11$

$l = -14 \rightarrow 12$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.036$

$wR(F^2) = 0.109$

$S = 1.04$

Primary atom site location: structure-invariant direct methods

Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from neighbouring sites

H-atom parameters constrained

$w = 1/[\sigma^2(F_o^2) + (0.0752P)^2]$

3196 reflections
245 parameters
1 restraint

$$\text{where } P = (F_o^2 + 2F_c^2)/3$$

$$(\Delta/\sigma)_{\max} < 0.001$$

$$\Delta\rho_{\max} = 0.36 \text{ e } \text{\AA}^{-3}$$

$$\Delta\rho_{\min} = -0.33 \text{ e } \text{\AA}^{-3}$$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Ni1	0.17351 (5)	0.21297 (4)	0.32522 (3)	0.05459 (18)
S1	-0.01043 (8)	0.19088 (7)	0.45807 (6)	0.0601 (2)
S2	0.04693 (8)	0.45024 (7)	0.31675 (6)	0.0634 (2)
S3	0.34944 (8)	0.23715 (8)	0.18766 (6)	0.0646 (2)
S4	0.30030 (9)	-0.02462 (7)	0.33157 (6)	0.0681 (2)
N1	-0.3268 (3)	0.7577 (3)	0.4479 (2)	0.0791 (7)
N2	-0.4145 (3)	0.4193 (3)	0.6218 (2)	0.0862 (8)
N3	0.6747 (3)	-0.3235 (3)	0.1797 (2)	0.0886 (8)
N4	0.7294 (3)	0.0134 (3)	0.0023 (2)	0.0882 (8)
N5	0.1415 (3)	0.7746 (2)	0.81191 (17)	0.0575 (5)
C1	-0.2966 (3)	0.3967 (3)	0.5591 (2)	0.0611 (7)
C2	-0.1507 (3)	0.3709 (3)	0.4772 (2)	0.0531 (6)
C3	-0.2387 (3)	0.6364 (3)	0.4331 (2)	0.0599 (7)
C4	-0.1257 (3)	0.4844 (3)	0.4169 (2)	0.0550 (6)
C5	0.6208 (3)	0.0325 (3)	0.0733 (2)	0.0652 (7)
C6	0.4856 (3)	0.0568 (3)	0.1630 (2)	0.0565 (6)
C7	0.4645 (3)	-0.0567 (3)	0.2251 (2)	0.0569 (6)
C8	0.5794 (3)	-0.2072 (3)	0.2023 (2)	0.0659 (7)
C9	0.2814 (3)	0.6993 (3)	0.7434 (2)	0.0650 (7)
H9	0.3298	0.5961	0.7497	0.078*
C10	0.3530 (4)	0.7722 (3)	0.6651 (2)	0.0731 (8)
H10	0.4497	0.7186	0.6182	0.088*
C11	0.2837 (4)	0.9231 (4)	0.6549 (2)	0.0777 (9)
H11	0.3331	0.9734	0.6020	0.093*
C12	0.1386 (4)	1.0006 (3)	0.7248 (3)	0.0782 (9)
H12	0.0884	1.1037	0.7190	0.094*
C13	0.0705 (4)	0.9233 (3)	0.8022 (2)	0.0686 (8)
H13	-0.0272	0.9748	0.8491	0.082*

supplementary materials

C14	0.0666 (4)	0.6954 (3)	0.8999 (2)	0.0675 (7)
H14A	0.1108	0.5915	0.8837	0.081*
H14B	-0.0502	0.7374	0.9038	0.081*
C15	0.0995 (4)	0.7078 (4)	1.0100 (2)	0.0785 (9)
H15A	0.0642	0.8119	1.0222	0.094*
H15B	0.0340	0.6697	1.0668	0.094*
C16	0.2730 (4)	0.6270 (4)	1.0199 (3)	0.0827 (9)
H16A	0.3399	0.6628	0.9625	0.099*
H16B	0.3082	0.5220	1.0108	0.099*
C17	0.2978 (4)	0.6479 (4)	1.1299 (3)	0.0867 (10)
H17A	0.2674	0.7513	1.1377	0.130*
H17B	0.4104	0.5924	1.1341	0.130*
H17C	0.2311	0.6131	1.1868	0.130*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Ni1	0.0448 (3)	0.0471 (3)	0.0603 (3)	-0.0124 (2)	-0.0012 (2)	-0.0050 (2)
S1	0.0525 (4)	0.0452 (4)	0.0670 (4)	-0.0135 (3)	0.0015 (3)	-0.0008 (3)
S2	0.0567 (4)	0.0489 (4)	0.0689 (4)	-0.0174 (3)	0.0060 (3)	-0.0021 (3)
S3	0.0525 (4)	0.0501 (4)	0.0736 (4)	-0.0146 (3)	0.0055 (3)	-0.0022 (3)
S4	0.0579 (4)	0.0488 (4)	0.0742 (5)	-0.0127 (3)	0.0096 (4)	-0.0021 (3)
N1	0.0769 (17)	0.0505 (15)	0.0934 (19)	-0.0155 (13)	-0.0048 (14)	-0.0097 (13)
N2	0.0728 (18)	0.0701 (17)	0.0859 (18)	-0.0194 (14)	0.0192 (15)	-0.0071 (14)
N3	0.0788 (18)	0.0535 (16)	0.103 (2)	-0.0110 (14)	0.0082 (15)	-0.0122 (14)
N4	0.0702 (18)	0.0761 (18)	0.0905 (19)	-0.0213 (14)	0.0174 (16)	-0.0071 (15)
N5	0.0505 (12)	0.0568 (13)	0.0561 (12)	-0.0137 (10)	-0.0055 (10)	-0.0116 (10)
C1	0.0588 (17)	0.0468 (14)	0.0640 (16)	-0.0144 (12)	-0.0012 (14)	-0.0049 (12)
C2	0.0487 (14)	0.0487 (14)	0.0529 (13)	-0.0139 (11)	-0.0031 (12)	-0.0079 (11)
C3	0.0610 (17)	0.0499 (17)	0.0608 (15)	-0.0200 (13)	-0.0031 (13)	-0.0034 (12)
C4	0.0512 (15)	0.0477 (14)	0.0581 (14)	-0.0143 (11)	-0.0040 (12)	-0.0104 (12)
C5	0.0555 (17)	0.0548 (16)	0.0709 (18)	-0.0164 (13)	0.0016 (15)	-0.0049 (13)
C6	0.0425 (14)	0.0557 (15)	0.0617 (15)	-0.0135 (11)	-0.0023 (12)	-0.0097 (12)
C7	0.0469 (14)	0.0512 (15)	0.0615 (15)	-0.0125 (12)	-0.0024 (12)	-0.0091 (12)
C8	0.0583 (17)	0.0542 (17)	0.0709 (17)	-0.0181 (14)	0.0033 (14)	-0.0048 (14)
C9	0.0559 (17)	0.0590 (16)	0.0660 (17)	-0.0105 (13)	-0.0073 (14)	-0.0122 (14)
C10	0.0630 (18)	0.075 (2)	0.0645 (17)	-0.0190 (16)	0.0043 (15)	-0.0130 (15)
C11	0.086 (2)	0.081 (2)	0.0653 (17)	-0.0384 (18)	-0.0079 (17)	0.0008 (16)
C12	0.090 (2)	0.0564 (17)	0.0769 (19)	-0.0210 (16)	-0.0151 (18)	-0.0030 (15)
C13	0.0653 (18)	0.0539 (16)	0.0689 (17)	-0.0092 (14)	-0.0057 (15)	-0.0130 (14)
C14	0.0621 (18)	0.0705 (18)	0.0689 (17)	-0.0297 (15)	-0.0060 (14)	-0.0053 (14)
C15	0.072 (2)	0.078 (2)	0.0735 (18)	-0.0302 (16)	0.0003 (16)	0.0052 (16)
C16	0.083 (2)	0.071 (2)	0.082 (2)	-0.0255 (17)	-0.0114 (18)	0.0043 (16)
C17	0.096 (2)	0.093 (2)	0.079 (2)	-0.046 (2)	-0.0262 (19)	0.0118 (18)

Geometric parameters (\AA , $^\circ$)

Ni1—S1	2.1501 (8)	C9—C10	1.359 (4)
Ni1—S2	2.1436 (8)	C9—H9	0.9300

Ni1—S3	2.1458 (8)	C10—C11	1.361 (4)
Ni1—S4	2.1461 (8)	C10—H10	0.9300
S1—C2	1.715 (2)	C11—C12	1.384 (4)
S2—C4	1.721 (3)	C11—H11	0.9300
S3—C6	1.717 (3)	C12—C13	1.364 (4)
S4—C7	1.719 (3)	C12—H12	0.9300
N1—C3	1.145 (3)	C13—H13	0.9300
N2—C1	1.139 (4)	C14—C15	1.536 (4)
N3—C8	1.141 (4)	C14—H14A	0.9700
N4—C5	1.143 (3)	C14—H14B	0.9700
N5—C13	1.341 (4)	C15—C16	1.485 (4)
N5—C9	1.344 (3)	C15—H15A	0.9700
N5—C14	1.483 (3)	C15—H15B	0.9700
C1—C2	1.439 (4)	C16—C17	1.527 (5)
C2—C4	1.348 (4)	C16—H16A	0.9700
C3—C4	1.435 (4)	C16—H16B	0.9700
C5—C6	1.432 (4)	C17—H17A	0.9600
C6—C7	1.343 (4)	C17—H17B	0.9600
C7—C8	1.440 (4)	C17—H17C	0.9600
S2—Ni1—S3	86.97 (3)	C11—C10—H10	119.8
S2—Ni1—S4	179.28 (3)	C10—C11—C12	118.9 (3)
S3—Ni1—S4	92.59 (3)	C10—C11—H11	120.6
S2—Ni1—S1	92.34 (3)	C12—C11—H11	120.6
S3—Ni1—S1	177.33 (3)	C13—C12—C11	119.0 (3)
S4—Ni1—S1	88.08 (3)	C13—C12—H12	120.5
C2—S1—Ni1	103.03 (9)	C11—C12—H12	120.5
C4—S2—Ni1	103.36 (9)	N5—C13—C12	121.3 (3)
C6—S3—Ni1	102.87 (10)	N5—C13—H13	119.3
C7—S4—Ni1	102.92 (9)	C12—C13—H13	119.3
C13—N5—C9	119.7 (3)	N5—C14—C15	111.1 (2)
C13—N5—C14	119.5 (2)	N5—C14—H14A	109.4
C9—N5—C14	120.7 (2)	C15—C14—H14A	109.4
N2—C1—C2	178.1 (3)	N5—C14—H14B	109.4
C4—C2—C1	121.1 (2)	C15—C14—H14B	109.4
C4—C2—S1	121.02 (19)	H14A—C14—H14B	108.0
C1—C2—S1	117.88 (19)	C16—C15—C14	114.5 (3)
N1—C3—C4	178.3 (3)	C16—C15—H15A	108.6
C2—C4—C3	122.3 (2)	C14—C15—H15A	108.6
C2—C4—S2	120.21 (19)	C16—C15—H15B	108.6
C3—C4—S2	117.5 (2)	C14—C15—H15B	108.6
N4—C5—C6	179.3 (3)	H15A—C15—H15B	107.6
C7—C6—C5	121.6 (2)	C15—C16—C17	111.7 (3)
C7—C6—S3	120.9 (2)	C15—C16—H16A	109.3
C5—C6—S3	117.5 (2)	C17—C16—H16A	109.3
C6—C7—C8	120.0 (2)	C15—C16—H16B	109.3
C6—C7—S4	120.7 (2)	C17—C16—H16B	109.3
C8—C7—S4	119.3 (2)	H16A—C16—H16B	107.9
N3—C8—C7	176.4 (3)	C16—C17—H17A	109.5
N5—C9—C10	120.7 (3)	C16—C17—H17B	109.5

supplementary materials

N5—C9—H9	119.6	H17A—C17—H17B	109.5
C10—C9—H9	119.6	C16—C17—H17C	109.5
C9—C10—C11	120.3 (3)	H17A—C17—H17C	109.5
C9—C10—H10	119.8	H17B—C17—H17C	109.5

Fig. 1

