


 Cite this: *RSC Adv.*, 2020, 10, 11831

Tuning slow magnetic relaxation behaviour in a {Dy₂}-based one-dimensional chain *via* crystal field perturbation†

 Shui Yu,^a Qinhu Zhang,^c Huancheng Hu,^{*a} Zilu Chen,^{ID *a} Dongcheng Liu,^a Yuning Liang^a and Fupei Liang^{ID *ab}

Two novel {Dy₂}-based one dimensional chain compounds {[Dy₂(H₃L)₄(OAc)₆]·2MeOH}_n (**1**) and {[Dy₂(H₃L)₄(OAc)₄(NCS)₂]·2MeOH}_n (**2**) (H₃L = 1,3-bis(2-hydroxynaphthalenemethyleneamino)-propan-2-ol) have been prepared under solvothermal conditions. Crystal structure analyses indicate that **1** and **2** feature similar 1D chain structures bearing dinuclear secondary building units. The difference between these two structures is that one chelated acetate ligand of Dy(III) ion in **1** is replaced by one monodentate coordinated NCS⁻ ion in **2**, leading to their different coordination numbers and geometry configurations to Dy(III) ion. Magnetic properties indicate that **1** and **2** display slow magnetic relaxation behavior with an effective energy barrier of 16.44(2) K in **1** and 8.02(2) K in **2**, respectively, which is maybe attributed to the subtle crystal field perturbation of Dy(III) ions.

Received 19th February 2020

Accepted 10th March 2020

DOI: 10.1039/d0ra01604g

rsc.li/rsc-advances

Introduction

Recently single-molecule magnets (SMMs) have attracted much attention because of their promising applications in ultrahigh-density information storage, molecular spintronic devices and quantum computing, *etc.*^{1–3} Comparing with transition metal ions, lanthanide (Ln) ions often possess large orbital angular momentum and inherent magnetic anisotropy, which contribute to improving the effective energy barrier (U_{eff}) and blocking temperature (T_{B}) of SMM materials.^{4–7} As a result, Ln ions particularly Dy(III) ion have become ideal candidates to construct SMM materials since Ishikawa *et al.* reported the first Ln-based SMM of [Pc₂Ln]⁻·TBA⁺ (Ln = Tb or Dy, Pc = dianion of phthalocyanine; TBA⁺ = N(C₄H₉)₄⁺) in 2003.⁸ After that, numerous Ln-based SMM materials including discrete Ln_x ($x \geq 1$) coordination clusters, chainlike, two dimensional and three

dimensional coordination compounds have been prepared and investigated in detail.^{9–11}

Aiming at enhancing the performance of Ln-based SMM materials, many effective efforts have been dedicated by researchers in the past decades.^{12–15} It is noteworthy that fine-tuning the symmetry of ligand field and/or the orientations of single-ion easy axes of lanthanide ions have been viewed as general and satisfactory approaches to increase the single-ion anisotropy of Ln(III) ions and further improve the values of U_{eff} and T_{B} of SMM materials.^{16,17} For example, two essentially isomorphous planar {Dy₄} coordination clusters of [Dy₄(μ₃-OH)₂(hmmph)₂(hmp)₂Cl₄]·3MeCN·MeOH and [Dy₄(μ₃-OH)₂(hmmph)₂(hmp)₂(N₃)₄]·4MeOH {hmmph₂ = 2-[(2-hydroxy-ethylimino)methyl]-6-methoxyphenol} exhibit an anion-dependent magnetic slow relaxation behavior.¹⁸ When coordination water molecules in compound [Dy(acac)₃(H₂O)₂] are replaced by 1,10-phenanthroline or its derivatives with large aromatic groups, the energy barrier can also be enhanced.¹⁹ Comparing with compound [Dy(H₂L)(NO₃)(H₂O)(EtOH)](NO₃)₂·H₂O (H₂L = 2,6-diylbis(ethan-1-yl-1-ylidene) di(isonicotinohydrazide)), the slow magnetic behavior of [Dy(L)(NO₃)(MeOH)₂] is changed obviously by deprotonating H₂L ligand and using different solvents.²⁰ Therefore, it is necessary to design and prepare compounds with similar or isomorphous structure by tuning ligands to control the anisotropy of Dy(III) ions and further explore the structure–property relationships of SMM materials. But up to now, the investigations of this field are still limited.

In this context, we report two polyhydroxylamine-derived Schiff-base {Dy₂}-based one dimensional chain compounds {[Dy₂(H₃L)₄(OAc)₆]·2MeOH}_n (**1**) and {[Dy₂(H₃L)₄(OAc)₄(NCS)₂]·

^aState Key Laboratory for Chemistry and Molecular Engineering of Medicinal Resources, School of Chemistry and Pharmaceutical Sciences, Guangxi Normal University, Guilin 541004, P. R. China. E-mail: zlichen@mailbox.gxnu.edu.cn; siniantongnian@126.com; fliangoffice@yahoo.com

^bGuangxi Key Laboratory of Electrochemical and Magnetochemical Functional Materials, College of Chemistry and Bioengineering, Guilin University of Technology, Guilin, 541004, P. R. China

^cState Key Laboratory of Heavy Oil Processing, Institute of New Energy, College of Chemical Engineering, China University of Petroleum (East China), Qingdao 266580, P. R. China

† Electronic supplementary information (ESI) available: IR curves, TGA curves, PXRD patterns, additional structural and magnetic figures, selected bond lengths and bond angles for the three titled compounds. CCDC 1984194 and 1984195. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0ra01604g



$2\text{MeOH}\}_n$ (**2**) featuring with similar structures. The different coordination groups of Dy(III) in **1** and **2** lead to different geometrical configurations and symmetries and coordination numbers of Dy(III) ions. The slow magnetic relaxation behaviors of **1** and **2** are obviously perturbed by their difference of crystal field for Dy(III) ion. The energy barrier is 16.44(2) K and 8.02(2) K with pre-exponential factor of 3.25×10^{-6} s and 5.6×10^{-5} s in **1** and **2**, respectively.

Experimental

Materials and physical measurements

All chemicals were purchased from commercial companies and used directly without further purification. The Fourier transform infrared (FT-IR) data were collected on PerkinElmer Spectrum One FT-IR spectrometer using the corresponding KBr pellets in the wavenumber range of 4000–400 cm^{-1} . The powder X-ray diffraction (PXRD) measurements were carried out on a Rigaku D/max 2500v/pc diffractometer equipped with Cu-K α radiation ($\lambda = 1.5418 \text{ \AA}$) at 40 kV and 40 mA, with a step size of 0.02° in 2θ and a scan speed of 5° min^{-1} . Elemental analyses for C, H and N elements were performed on an Elementar Micro cube C, H, N elemental analyzer. The TG analyses were conducted on a PerkinElmer Diamond TG/DTA thermal analyzer in a flowing nitrogen atmosphere with a heating rate of $5^\circ \text{ C min}^{-1}$. All magnetic data were measured on a Quantum Design MPMS SQUID-XL-7 SQUID magnetometer. The magnetic data were corrected with a consideration of diamagnetic contribution from the sample and the sample holder.

X-ray crystal structure analysis

The single crystal X-ray diffraction experiments were collected on SuperNova diffractometer with graphite monochromated Mo-K α radiation ($\lambda = 0.71073 \text{ \AA}$). The single crystal structures were solved by the direct method using SHELXT²¹ and refined by means of full-matrix least-squares procedures on F^2 by the SHELXL program.²² All non-hydrogen atoms (C, N, O, S and Dy) were located by different Fourier maps and subsequently refined with anisotropic displacement parameters. The H atoms attached on C and N atoms were refined at the geometrical sites. The details of crystallographic data of **1** and **2** are presented in Table S1.† Selected bond lengths and bond angles in **1** and **2** are listed in Tables S2 and S3,† respectively.

Synthesis

Preparation of compound 1. A solution of H_3L (0.1 mmol, 0.0414 g) and $\text{Dy}(\text{OAc})_3 \cdot 10\text{H}_2\text{O}$ (0.1 mmol, 0.0513 g) in methanol (1.5 mL) and acetonitrile (0.5 mL) was sealed in a Pyrex tube under vacuum and then the tube was heated at 80° C for 3 days. The resulted clear yellow solution was placed at room temperature for evaporation to give pale yellow crystals after 3 days (yield 23% based on $\text{Dy}(\text{OAc})_3 \cdot 10\text{H}_2\text{O}$). Anal. calcd for $\text{C}_{64}\text{H}_{68}\text{Dy}_2\text{N}_4\text{O}_{20}$: C, 49.97; H, 4.46; N, 3.64%. Found: C, 49.84; H, 4.52; N, 3.73%. IR (KBr pellet, cm^{-1}): 3426 (m), 2919 (w), 2854 (w), 1634 (s), 1545 (m), 1448 (m), 1401 (m), 1436 (m), 1304 (m),

1194 (w), 1033 (w), 957 (w), 844 (w), 744 (w), 675 (w), 607 (w), 544 (w), 463 (w), 411 (m).


Preparation of compound 2. Methanol (1.5 mL) and acetonitrile (0.5 mL) were added in a Pyrex tube containing H_3L (0.1 mmol, 0.0414 g), KSCN (0.2 mmol, 0.0194 g) and $\text{Dy}(\text{OAc})_3 \cdot 10\text{H}_2\text{O}$ (0.2 mmol, 0.1026 g). The tube was sealed under vacuum and heated at 80° C for 3 days. The resulted clear yellow solution was placed at room temperature for 3 days, and the pale yellow crystals were collected (yield 28% based on $\text{Dy}(\text{OAc})_3 \cdot 10\text{H}_2\text{O}$). Anal. calcd for $\text{C}_{62}\text{H}_{66}\text{Dy}_2\text{N}_6\text{O}_{16}\text{S}_2$: C, 48.34; H, 4.32; N, 5.46%. Found: C, 48.56; H, 4.50; N, 5.36%. IR (KBr pellet, cm^{-1}): 3425 (s), 2923 (w), 2850 (w), 2053 (m), 1635 (s), 1545 (m), 1459 (m), 1387 (s), 1307 (w), 1194 (w), 1112 (w), 1033 (w), 954 (w), 820 (w), 755 (w), 672 (w), 476 (w).

Results and discussion

Structural characterization

Crystal structure of compound 1. Single crystal X-ray diffraction analysis revealed that **1** crystallizes in triclinic crystal system $P\bar{1}$ space group. The asymmetric unit of **1** contains one crystallographically independent Dy(III) ion, one H_3L ligand, three OAc^- ions and one lattice methanol molecule. Dy(III) ion is coordinated by nine O atoms from two H_3L ligands and four carboxylate groups, giving a distorted muffin coordination geometry with C_s symmetry by SHAPE analysis (Table S4†). Two adjacent Dy(III) ions with the distance of 4.120 \AA are bridged by two bidentate carboxylate oxygen atoms to form a dinuclear $[\text{Dy}_2\text{O}_2]$ unit, and these $[\text{Dy}_2\text{O}_2]$ units are further connected by H_3L ligands to form 1D chain structure (Fig. 1d). The Dy(III)–O bond distances range from 2.285(2) to 2.564(3) \AA and Dy–O–Dy bond angles are in the range of $49.70(12)^\circ$ to $148.94(12)^\circ$.^{23,24}


Crystal structure of compound 2. Single crystal X-ray diffraction analysis implies that the structure of **2** is similar to **1** except for one chelated carboxylate group of central Dy(III) ion in **1** replaced by one NCS^- ion in **2**, leading to the different

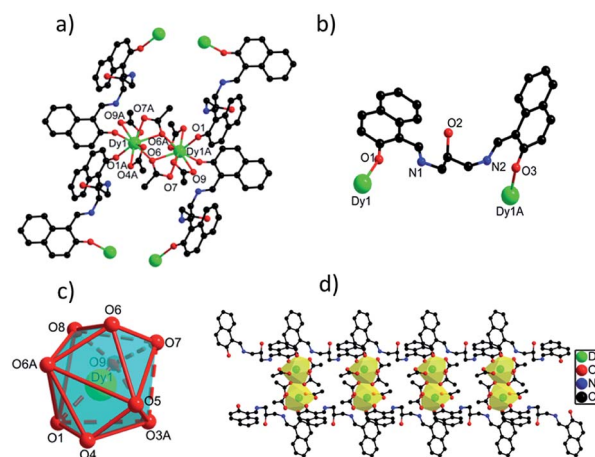

coordination numbers and geometry configurations of Dy(III) ions in **1** and **2**. Similar to **1**, **2** as well crystallizes in triclinic crystal system $P\bar{1}$ space group. The asymmetric unit of **2** contains one crystallographically independent Dy(III) ion, one H₃L ligand, two carboxylate groups, one SCN⁻ ion and one lattice methanol molecule. As depicted in Fig. S2,[†] the Dy(III) ion in **2** is coordinated by seven O atoms from two H₃L ligands and three carboxylate groups and one N atom from one SCN⁻ ion, showing a triangular dodecahedron with D_{2d} symmetry by SHAPE analysis (Table S5[†]). Two neighboring Dy(III) ions with the distance of 4.027 Å are bridged by two O atoms from two carboxylate groups to form a [Dy₂O₂] unit, which are further linked to build 1D chain structure *via* bridging H₃L ligands (Fig. 2d). The bond lengths of Dy(III)–O and Dy(III)–N are in the range of 2.270(4)–2.501(5) Å, and the angles of O–Dy(III)–O and O–Dy(III)–N range from 51.63(14) to 165.86(17)°. Interestingly, although different {Dy₂} units exist in **1** and **2**, they still exhibit similar 1D chain structures owing to the same bridging H₃L ligands. The flexibility of H₃L ligand leads to its slightly different coordination modes in **1** and **2**, thus they show different crystal packing structures which are constructed from the one-dimensional chains through $\pi\cdots\pi$ interaction rooting from aromatic rings (Fig. S1[†]).

Powder X-ray diffraction and thermogravimetric analysis

The experimental powder X-ray diffraction (PXRD) patterns of **1** and **2** match well with the corresponding simulated ones obtained from the single crystal X-ray diffraction data, respectively, confirming the high purity of the bulk samples of **1** and **2** (Fig. S3[†]). As shown in Fig. S4,[†] the thermogravimetric analysis (TGA) curve of **1** shows an obvious weight loss of 5.90% before 131 °C, due to the loss of MeOH molecules (calcd: 4.20%). With the temperature increasing, a platform is occurred before the collapse of the structure of **1** above 214 °C. The TGA curve of **2** exhibits a gradual weight loss of 4.75% below 248 °C, which is as well attributed to the loss of MeOH molecules (calcd: 4.20%). As

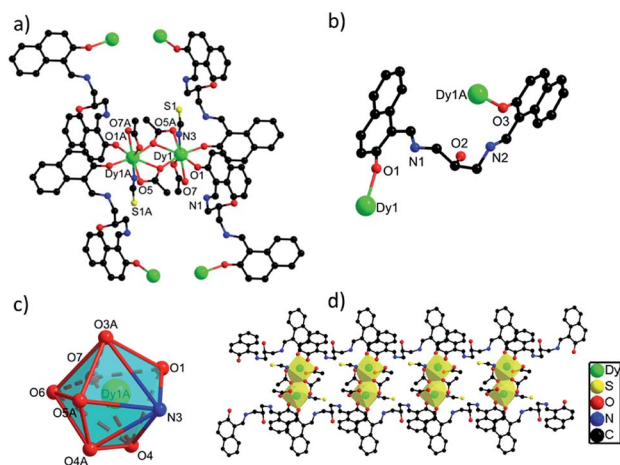

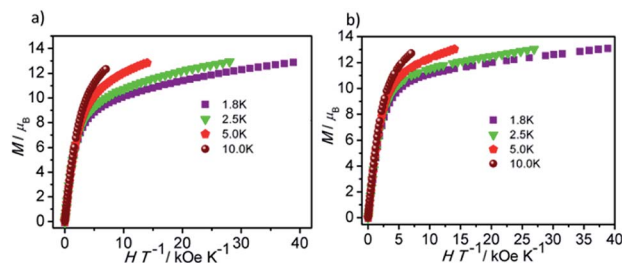


Fig. 4 Plots of M vs. HT^{-1} for 1 (a) and 2 (b) measured at 1.8, 2.5, 5.0 and 10 K.

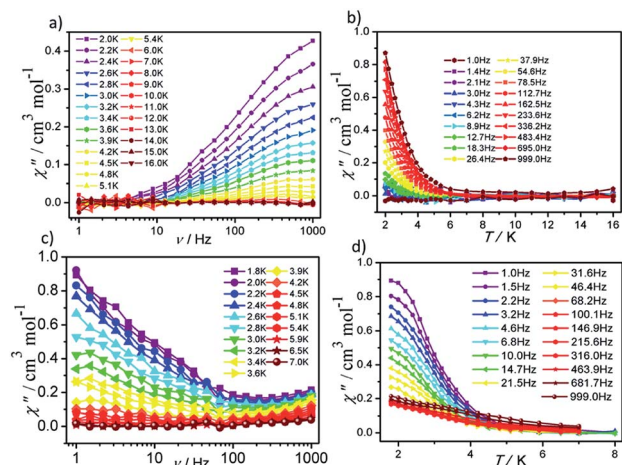


Fig. 5 Frequency- and temperature-dependent out-of phase (χ'') ac susceptibilities for 1 (a and b) and 2 (c and d) under zero dc field.

observed although no obvious peaks were detected in 1 and 2, illuminating the existence of typical slow magnetic relaxation processes in 1 and 2. The obvious difference of χ' signals vs. temperature plots and frequency dependencies plots for 1 and 2 (Fig. S9 and S10†) maybe derive from their different coordination numbers and geometry configurations and symmetries of the central Dy(III) ion.

The effective energy barrier (U_{eff}) and relaxation time (τ_0) of 1 and 2 can be obtained by fitting $\ln(\chi''/\chi')$ vs. $1/T$ data with the following equation: $\ln(\chi''/\chi') = \ln(\omega\tau_0) + E_a/(k_B T)$,^{33–35} and the excellent linear fitting between $\ln(\chi''/\chi')$ and $1/T$ can be depicted at different frequencies, yield $U_{\text{eff}} \approx 16.44$ K and 8.02 K, $\tau_0 \approx$

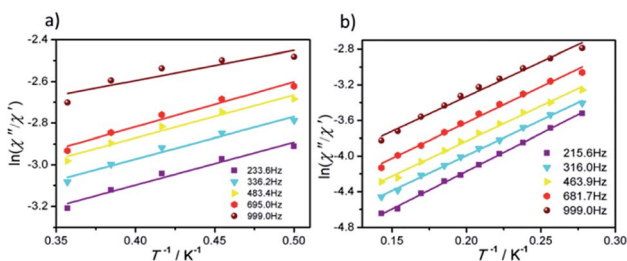


Fig. 6 Plots of $\ln(\chi''/\chi')$ vs. $1/T$ for 1 (a) and 2 (b) under 0 Oe dc field, the solid lines represent the best fits.

3.25×10^{-6} s and 5.6×10^{-5} s for 1 and 2, respectively. The different effective energy barrier and relaxation time for 1 and 2 are due to the different anisotropy of their Dy(III) ions from subtle crystal field perturbation caused by the change of one chelated acetate in 1 by one NCS⁻ ligand (Fig. 6).

Conclusions

In conclusion, two new {Dy₂}-based 1D chain structures bearing a Schiff-base ligand were constructed and characterized in detail. Magnetic properties indicate that they exhibit similar slow magnetic relaxation behavior under zero dc field. Interestingly, one chelated acetate ligand in 1 is replaced by one NCS⁻ ion in 2, which leads to the different coordination geometries of their Dy(III) ions, and thus their different Dy(III) anisotropies. All of these factors results in their different effective energy barriers. This phenomena indicates that the slight crystal field perturbation of Dy(III) ions will affect the slow magnetic behavior for the compounds with similar structures. This work will enrich the methods of tuning the performance of SMM materials *via* crystal field perturbation effect.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by National Natural Science Foundation of China (grant no. 21661009 and 21901050), Guangxi Natural Science Foundation of China (grant no. 2018GXNSFB050031), the project for improving the basic scientific research ability of young and middle-aged teachers in Guangxi Universities (grant no. 2019KY0054), the Key Project of Guangxi Normal University (grant no. 2018ZD003) and Innovation Project of Guangxi Graduate Education (title: Study on the synthesis and magnetic properties of dysprosium complexes).

References

- 1 L. Ungur, S.-Y. Lin, J. Tang and L. F. Chibotaru, *Chem. Soc. Rev.*, 2014, **43**, 6894–6905.
- 2 D. N. Woodruff, R. E. Winpenney and R. A. Layfield, *Chem. Rev.*, 2013, **113**, 5110–5148.
- 3 J. Liu, Y. C. Chen, J. L. Liu, V. Vieru, L. Ungur, J. H. Jia, L. F. Chibotaru, Y. Lan, W. Wernsdorfer, S. Gao, X. M. Chen and M. L. Tong, *J. Am. Chem. Soc.*, 2016, **138**, 5441–5450.
- 4 Y.-X. Wang, Y. Ma, Y. Chai, W. Shi, Y. Sun and P. Cheng, *J. Am. Chem. Soc.*, 2018, **140**, 7795–7798.
- 5 B. S. Dolinar, D. I. Alexandropoulos, K. R. Vignesh, T. James and K. R. Dunbar, *J. Am. Chem. Soc.*, 2018, **140**, 908–911.
- 6 M. K. Singh and G. Rajaraman, *Inorg. Chem.*, 2019, **58**, 3175–3188.
- 7 A. Bhanja, R. Herchel, Z. Travnicek and D. Ray, *Inorg. Chem.*, 2019, **58**, 12184–12198.

- 8 N. Ishikawa, M. Sugita, T. Ishikawa, S.-y. Koshihara and Y. Kaizu, *J. Am. Chem. Soc.*, 2003, **125**, 8694–8695.
- 9 Z.-H. Zhu, X.-F. Ma, H.-L. Wang, H.-H. Zou, K.-Q. Mo, Y.-Q. Zhang, Q.-Z. Yang, B. Li and F.-P. Liang, *Inorg. Chem. Front.*, 2018, **5**, 3155–3162.
- 10 A. B. Canaj, M. Siczek, M. Otreba, T. Lis, G. Lorusso, M. Evangelisti and C. J. Milios, *Dalton Trans.*, 2016, **45**, 18591–18602.
- 11 J. Kobylarczyk, M. Liberka, P. Konieczny, S. Baran, M. Kubicki, T. Korzeniak and R. Podgajny, *Dalton Trans.*, 2020, **49**, 300–311.
- 12 L. F. Chibotaru, L. Ungur and A. Soncini, *Angew. Chem., Int. Ed.*, 2008, **47**, 4126–4129.
- 13 J. Mayans, Q. Saez, M. Font-Bardia and A. Escuer, *Dalton Trans.*, 2019, **48**, 641–652.
- 14 Y. N. Guo, G. F. Xu, W. Wernsdorfer, L. Ungur, Y. Guo, J. Tang, H. J. Zhang, L. F. Chibotaru and A. K. Powell, *J. Am. Chem. Soc.*, 2011, **133**, 11948–11951.
- 15 A. A. Patrascu, M. Briganti, S. Soriano, S. Calancea, R. A. Allao Cassaro, F. Totti, M. G. F. Vaz and M. Andruh, *Inorg. Chem.*, 2019, **58**, 13090–13101.
- 16 R. J. Blagg, C. A. Muryn, E. J. McInnes, F. Tuna and R. E. Winpenny, *Angew. Chem., Int. Ed.*, 2011, **50**, 6530–6533.
- 17 F. Habib, P. H. Lin, J. Long, I. Korobkov, W. Wernsdorfer and M. Murugesu, *J. Am. Chem. Soc.*, 2011, **133**, 8830–8833.
- 18 Y.-Z. Zheng, Y. Lan, C. E. Anson and A. K. Powell, *Inorg. Chem.*, 2008, **47**, 10813–10815.
- 19 G.-J. Chen, Y.-N. Guo, J.-L. Tian, J. Tang, W. Gu, X. Liu, S.-P. Yan, P. Cheng and D.-Z. Liao, *Chem.–Eur. J.*, 2012, **18**, 2484–2487.
- 20 J. Wang, H. Wang, Y. Ma, J. Tang, L. Li, Q. Wang, B. Zhao, P. Cheng and J. Ma, *Cryst. Growth Des.*, 2019, **19**, 3365–3371.
- 21 G. Sheldrick, *Acta Crystallogr., Sect. A: Found. Crystallogr.*, 2008, **64**, 112–122.
- 22 G. Sheldrick, *Acta Crystallogr., Sect. C: Struct. Chem.*, 2015, **71**, 3–8.
- 23 S.-D. Jiang and S.-X. Qin, *Inorg. Chem. Front.*, 2015, **2**, 613–619.
- 24 K. Griffiths, P. Kumar, G. R. Akién, N. F. Chilton, A. Abdul-Sada, G. J. Tizzard, S. J. Coles and G. E. Kostakis, *Chem. Commun.*, 2016, **52**, 7866–7869.
- 25 H. L. Wang, X. F. Ma, J. M. Peng, Z. H. Zhu, B. Li, H. H. Zou and F. P. Liang, *Inorg. Chem.*, 2019, **58**, 9169–9174.
- 26 S. Biswas, L. Mandal, Y. Shen and M. Yamashita, *Dalton Trans.*, 2019, **48**, 14096–14102.
- 27 H. Ke, W. Wei, Y. Yang, J. Zhang, Y. Q. Zhang, G. Xie and S. Chen, *Dalton Trans.*, 2019, **48**, 7844–7852.
- 28 K. H. Zangana, E. Moreno Pineda and R. E. Winpenny, *Dalton Trans.*, 2015, **44**, 12522–12525.
- 29 W. Cao, C. Gao, Y. Q. Zhang, D. Qi, T. Liu, K. Wang, C. Duan, S. Gao and J. Jiang, *Chem. Sci.*, 2015, **6**, 5947–5954.
- 30 J. Lu, X.-L. Li, Z. Zhu, S. Liu, Q. Yang and J. Tang, *Dalton Trans.*, 2019, **48**, 14062–14068.
- 31 J. Vallejo, J. Cano, I. Castro, M. Julve, F. Lloret, O. Fabelo, L. Canadillas-Delgado and E. Pardo, *Chem. Commun.*, 2012, **48**, 7726–7728.
- 32 Q. Zhou, F. Yang, D. Liu, Y. Peng, G. Li, Z. Shi and S. Feng, *Inorg. Chem.*, 2012, **51**, 7529–7536.
- 33 M. J. Liu, J. Yuan, Y. Q. Zhang, H. L. Sun, C. M. Liu and H. Z. Kou, *Dalton Trans.*, 2017, **46**, 13035–13042.
- 34 H. Li, J. Sun, M. Yang, Z. Sun, J. Tang, Y. Ma and L. Li, *Inorg. Chem.*, 2018, **57**, 9757–9765.
- 35 I. A. Kühne, K. Griffiths, A.-J. Hutchings, O. P. E. Townrow, A. Eichhöfer, C. E. Anson, G. E. Kostakis and A. K. Powell, *Cryst. Growth Des.*, 2017, **17**, 5178–5190.