



OPEN

# Fluoroindate glasses co-doped with Pr<sup>3+</sup>/Er<sup>3+</sup> for near-infrared luminescence applications

Wojciech A. Pisarski<sup>1✉</sup>, Joanna Pisarska<sup>1</sup>, Marta Kuwik<sup>1</sup>, Marcin Kochanowicz<sup>2</sup>, Jacek Żmojda<sup>2</sup>, Piotr Miluski<sup>2</sup>, Agata Baranowska<sup>2</sup>, Jan Dorosz<sup>2</sup>, Magdalena Leśniak<sup>3</sup> & Dominik Dorosz<sup>3</sup>

Fluoroindate glasses co-doped with Pr<sup>3+</sup>/Er<sup>3+</sup> ions were synthesized and their near-infrared luminescence properties have been examined under selective excitation wavelengths. For the Pr<sup>3+</sup>/Er<sup>3+</sup> co-doped glass samples several radiative and nonradiative relaxation channels and their mechanisms are proposed under direct excitation of Pr<sup>3+</sup> and/or Er<sup>3+</sup>. The energy transfer processes between Pr<sup>3+</sup> and Er<sup>3+</sup> ions in fluoroindate glasses were identified. In particular, broadband near-infrared luminescence (FWHM = 278 nm) associated to the <sup>1</sup>G<sub>4</sub> → <sup>3</sup>H<sub>5</sub> (Pr<sup>3+</sup>), <sup>1</sup>D<sub>2</sub> → <sup>1</sup>G<sub>4</sub> (Pr<sup>3+</sup>) and <sup>4</sup>I<sub>13/2</sub> → <sup>4</sup>I<sub>15/2</sub> (Er<sup>3+</sup>) transitions of rare earth ions in fluoroindate glass is successfully observed under direct excitation at 483 nm. Near-infrared luminescence spectra and their decays for glass samples co-doped with Pr<sup>3+</sup>/Er<sup>3+</sup> are compared to the experimental results obtained for fluoroindate glasses singly doped with rare earth ions.

Fluoroindate glasses belong to the low-phonon *Heavy Metal Fluoride Glass (HMFG)* family, which have been extensively studied for their numerous optical applications. From literature data it is well-known that fluoroindate glasses containing rare earth ions with their lower phonon energies close to 510 cm<sup>-1</sup> are promising materials for up-conversion luminescence applications. For example, the laser based on the orange-to-ultraviolet conversion in a Nd<sup>3+</sup> doped fluoroindate glass powder has been well demonstrated<sup>1</sup>. These effects are practically not possible to obtain in Nd<sup>3+</sup> doped oxide or oxyfluoride glass host matrices. Generally, the efficient up-conversion luminescence of Pr<sup>3+</sup>, Tm<sup>3+</sup> and Ho<sup>3+</sup> ions in fluoroindate glasses<sup>2–4</sup> was successfully observed. Moreover, the up-conversion luminescence spectra of Pr<sup>3+</sup>, Ho<sup>3+</sup> and Tm<sup>3+</sup> ions in fluoroindate glasses<sup>5–9</sup> are enhanced drastically in the presence of Yb<sup>3+</sup>. In the later system<sup>9</sup>, i.e. Tm<sup>3+</sup>/Yb<sup>3+</sup> co-doped fluoroindate glass, the blue up-conversion luminescence of Tm<sup>3+</sup> ions is highly increased with Yb<sup>3+</sup> concentration. For the optimum Tm<sup>3+</sup> concentration (0.5 mol%), the up-conversion emission intensity was increased by a factor about 100 by co-doping with 2.25 mol% of Yb<sup>3+</sup>. In particular, fluoroindate glasses singly doped with Er<sup>3+</sup> ions and doubly doped with Er<sup>3+</sup>/Yb<sup>3+</sup> ions have been examined for up-conversion luminescence<sup>10–13</sup>, which was measured under 790 nm, 980 nm or 1480 nm laser excitation. The up-conversion luminescence processes of Er<sup>3+</sup> were analyzed with activator concentration, temperature, pumping wavelength and power of diode laser used as the excitation source. In general, the up-conversion results in a strong green emission and weaker blue and red emissions and the Yb<sup>3+</sup> co-doping will certainly increase the efficiency of an up-conversion-based optical device. Further investigations confirmed this hypothesis. An intensity enhancement of 4.5 for the green up-conversion luminescence in Er<sup>3+</sup>/Yb<sup>3+</sup> co-doped fluoroindate glass has been obtained by focusing the incoming beam with a 3.8 μm silica microsphere<sup>14</sup>. Also, these experimental results open a new method to improve the up-conversion emission intensity in biological samples with rare earth doped nanoparticles that can be used as nano-sensors. In another case, the generation of photocurrent in a commercial solar cell has been achieved under excitation at 1480 nm in fluoroindate glass samples co-doped with Er<sup>3+</sup>/Yb<sup>3+</sup> ions<sup>15</sup>.

Fluoroindate glasses with their excellent spectroscopic properties offer the possibility of using these materials not only in the operation of erbium up-conversion lasers. Also, they belong to promising glass materials emitting near-infrared radiation. Nowadays there is a great interest in compact lasers operating in the near-infrared (1.5 μm) and mid-infrared (2.8 μm) for optical communications, medical and eye-safe light detecting and ranging applications. However, the near-infrared luminescence studies were limited practically to fluoroindate glasses containing Er<sup>3+</sup> or Er<sup>3+</sup>/Yb<sup>3+</sup> ions<sup>10,13</sup>. Luminescence spectra exhibit a highly intense signal at 1.5 μm due to

<sup>1</sup>Institute of Chemistry, University of Silesia, Szkolna 9, 40-007 Katowice, Poland. <sup>2</sup>Białystok University of Technology, Wiejska 45D Street, 15-351 Białystok, Poland. <sup>3</sup>AGH University of Science and Technology, 30 Mickiewicza Av, 30-059 Krakow, Poland. ✉email: wojciech.pisarski@us.edu.pl

$^4I_{13/2} \rightarrow ^4I_{15/2}$  transition of  $Er^{3+}$ . Decay measurements indicate that luminescence lifetime for the upper  $^4I_{13/2}$  laser state of  $Er^{3+}$  ions in fluoroindate glass is quite long and its value is close nearly to 10 ms at room temperature<sup>10</sup>. The mid-infrared luminescence results obtained for  $Er^{3+}/Yb^{3+}$  ions in fluoroindate glass suggest that co-doping with  $Yb^{3+}$  favors only the up-conversion processes which depopulate efficiently the  $^4I_{11/2}$  state, reducing the emission intensity related to  $^4I_{11/2} \rightarrow ^4I_{13/2}$  transition of  $Er^{3+}$  ions at 2.8  $\mu m$ <sup>13</sup>. These phenomena are important for diode-pumped solid-state lasers, which could provide a compact and efficient device with the advantage of easy coupling with fiber integrated optical systems. For diode-pumped lasers luminescence at near-infrared (1.5  $\mu m$ ) and mid-infrared (2.8  $\mu m$ ) spectral ranges, the trivalent  $Er^{3+}$  seems to be an excellent candidate due to  $^4I_{13/2} \rightarrow ^4I_{15/2}$  and  $^4I_{11/2} \rightarrow ^4I_{13/2}$  electronic transitions, respectively. From accumulated data it is quite well-known that the transmission capacity of WDM systems (wavelength division multiplexing) should be improved. Many research groups are looking for a new glass matrices and their fibers in order to obtain signal amplification beyond the conventional optical NIR window between 1530 and 1565 nm, commonly known as the C-band. In fact, spectral bandwidth for the commercial EDFA system (Erbium Doped Fiber Amplifiers) based on silicate glass is equal to 40 nm at C-band and broadband near-infrared transmission is limited, unfortunately<sup>16</sup>. For that reason, several glass matrices containing rare earth ions are still tested in order to obtain excellent materials with broader emission bands and longer lifetimes. These improved spectroscopic parameters are necessary for signal amplification in telecommunication and laser technology. Some recently published works for fluoroindate glass clearly indicate that a logical extension of  $Er^{3+}$ -doped systems would be the addition of other rare earth ions such as  $Tm^{3+}$  or  $Ho^{3+}$  ions<sup>17,18</sup>. The interesting results for fluoroindate glasses co-doped with  $Ho^{3+}/Tm^{3+}$  and  $Ho^{3+}/Nd^{3+}$  ions<sup>19,20</sup> emitting near-infrared and mid-infrared radiation at 2  $\mu m$  and 3.9  $\mu m$  under direct excitation (888 nm or 808 nm) have been also well presented and discussed in details. Among rare earths, the trivalent  $Pr^{3+}$  ions exhibit broadband near-infrared luminescence covering a wavelength range from 1.2  $\mu m$  to 1.7  $\mu m$ , which is really important for optical fiber amplifiers operating at O-band (1260–1360 nm), E-band (1360–1460 nm), S-band (1460–1530 nm), C-band (1530–1565 nm), and L-band (1565–1625 nm)<sup>21</sup>. The recent results indicate that glasses<sup>22–25</sup> and crystals<sup>26</sup> co-doped with  $Pr^{3+}/Er^{3+}$  seems to be quite good candidates for broadband near-IR luminescence. The superbroadband near-IR luminescence is contributed mainly by the  $^1D_2 \rightarrow ^1G_4$  ( $Pr^{3+}$ ) and  $^4I_{13/2} \rightarrow ^4I_{15/2}$  ( $Er^{3+}$ ) transitions which lead to emission lines located at about 1.48 and 1.53  $\mu m$ <sup>25</sup>. To the best of our knowledge, these phenomena were not yet examined for fluoroindate glasses co-doped with  $Pr^{3+}/Er^{3+}$ .

## Results and discussion

**Fluoroindate glasses singly doped with  $Pr^{3+}$  and  $Er^{3+}$ .** The optical absorption spectra of fluoroindate glasses singly doped with  $Pr^{3+}$  and  $Er^{3+}$  ions were recorded at room temperature. They are presented in Fig. 1.

In general, the absorption bands are inhomogeneously broadened and clearly resolved, characteristic for  $4f^1$  ( $Pr^{3+}$ ) and  $4f^1$  ( $Er^{3+}$ ) transitions of rare earths. They are attributed to the electronic transitions originating from the  $^3H_4$  ( $Pr^{3+}$ ) and  $^4I_{15/2}$  ( $Er^{3+}$ ) ground states to the higher-lying excited states of rare earths. From the optical absorption spectra the experimental oscillator strengths have been determined. The band intensities are estimated by measuring the areas under the absorption lines using the equations:

$$P_{meas} = 4.318 \times 10^{-9} \int \varepsilon(\nu) d\nu \quad (1)$$

$$\varepsilon(\nu) = A / c l \quad (2)$$

where:  $\int \varepsilon(\nu) d\nu$  represents the area under the absorption line,  $A$  indicates the absorbance,  $c$  is the concentration of the  $Ln^{3+}$  ion ( $Ln = Pr$  or  $Er$ ) in  $mol\ l^{-1}$  and  $l$  denotes the optical path length. In the next step, the theoretical oscillator strengths for each transition of  $Pr^{3+}$  and  $Er^{3+}$  ions were calculated using the Judd–Ofelt theory<sup>27,28</sup>. The theoretical oscillator strength is defined as follows:


$$P_{calc} = \frac{8\pi^2 mc(n^2 + 2)^2}{3h\lambda(2J + 1) \cdot 9n} \times \sum_{t=2,4,6} \Omega_t \langle 4f^N J || U^t || 4f^N J' \rangle^2 \quad (3)$$

where  $m$  is the mass of the electron,  $c$  is the velocity of light,  $h$  is the Planck constant and  $\lambda$  is the mean wavelength of the each transition. In order to perform the analysis, the refractive index of the medium ( $n = 1.48$  for fluoroindate glass) and  $U^t$  from Ref.<sup>29</sup> representing the square of the matrix elements of the unit tensor operator  $U^t$  (connecting the initial  $J$  and final  $J'$  states) were used for calculations. Next, the experimental and theoretical oscillator strengths have been compared. They are listed in Table 1.

Transitions are from the  $^3H_4$  ( $Pr^{3+}$ ) and  $^4I_{15/2}$  ( $Er^{3+}$ ) ground states to the levels indicated. The three phenomenological intensity parameters  $\Omega_t$  ( $t = 2, 4, 6$ ) are found to be (in  $10^{-20} cm^2$  units):  $\Omega_2 = 2.01 \pm 0.81$ ,  $\Omega_4 = 5.25 \pm 0.90$ ,  $\Omega_6 = 5.10 \pm 0.35$ , rms =  $1.4 \times 10^{-6}$  (for  $Pr^{3+}$ ) and  $\Omega_2 = 1.47 \pm 0.22$ ,  $\Omega_4 = 1.51 \pm 0.30$ ,  $\Omega_6 = 1.69 \pm 0.11$ , rms =  $0.7 \times 10^{-6}$  (for  $Er^{3+}$ ), respectively.

The three phenomenological Judd–Ofelt intensity parameters  $\Omega_t$  ( $t = 2, 4, 6$ ) for rare earth ions in fluoroindate glasses are found to be (in  $10^{-20} cm^2$  units);  $\Omega_2 = 2.01 \pm 0.81$ ,  $\Omega_4 = 5.25 \pm 0.90$ ,  $\Omega_6 = 5.10 \pm 0.35$ , rms =  $1.4 \times 10^{-6}$  (for  $Pr^{3+}$ ) and  $\Omega_2 = 1.47 \pm 0.22$ ,  $\Omega_4 = 1.51 \pm 0.30$ ,  $\Omega_6 = 1.69 \pm 0.11$ , rms =  $0.7 \times 10^{-6}$  (for  $Er^{3+}$ ). The fit quality was expressed by the magnitude of the root-mean-square deviation, which is defined by rms =  $\sum (P_{meas} - P_{calc})^2$ .

In the next step, the intensity parameters  $\Omega_t$  ( $t = 2, 4, 6$ ) were applied to calculate the radiative transition rates, luminescence branching ratios and radiative lifetimes. The radiative transition rates  $A_J$  for excited levels of  $Pr^{3+}$  and  $Er^{3+}$  ions from an initial level  $J$  to a final ground level  $J'$  were calculated using the following relation:

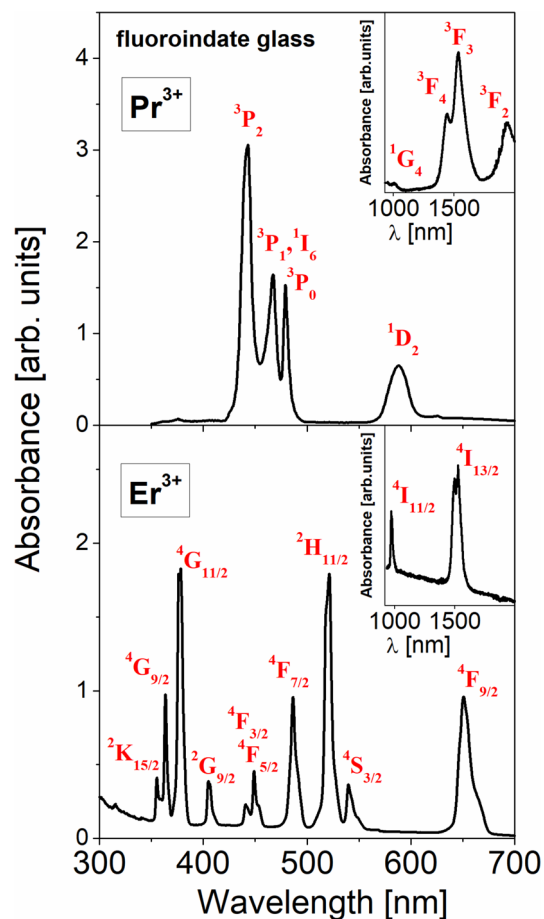

**Figure 1.** Absorption spectra of fluoroindate glasses singly doped with  $\text{Pr}^{3+}$  (top) and  $\text{Er}^{3+}$  (bottom).

$\text{Ln}^{3+}$	Levels	Average energy $\nu$ ( $\text{cm}^{-1}$ )	Oscillator strengths ( $\times 10^{-6}$ )		
			$P_{\text{meas}}$	$P_{\text{calc}}$	Residuals
$\text{Pr}^{3+}$	${}^3\text{H}_6, {}^3\text{F}_2$	5000	3.688	3.689	0.001
	${}^3\text{F}_4, {}^3\text{F}_3$	6700	8.850	8.865	0.015
	${}^1\text{G}_4$	9900	0.160	0.265	0.105
	${}^1\text{D}_2$	17,000	1.950	1.050	0.900
	${}^3\text{P}_0$	20,900	2.400	2.950	0.550
	${}^3\text{P}_1, {}^1\text{I}_6$	21,400	4.990	4.461	0.529
$\text{Er}^{3+}$	${}^4\text{I}_{13/2}$	6650	1.670	1.550	0.120
	${}^4\text{I}_{11/2}$	10,200	0.550	0.650	0.100
	${}^4\text{F}_{9/2}$	15,300	2.140	2.180	0.040
	${}^4\text{S}_{3/2}$	18,200	0.510	0.610	0.100
	${}^2\text{H}_{11/2}$	19,200	3.440	3.160	0.280
	${}^4\text{F}_{7/2}$	20,500	1.870	2.370	0.500
	${}^4\text{F}_{5/2}, {}^4\text{F}_{3/2}$	22,200	0.900	1.190	0.290
	${}^2\text{G}_{9/2}$	24,600	0.660	0.900	0.240
	${}^4\text{G}_{11/2}$	26,400	5.220	5.530	0.310
${}^4\text{G}_{9/2}, {}^2\text{K}_{15/2}$	27,750	2.190	1.840	0.350	

**Table 1.** Measured and calculated oscillator strengths for  $\text{Pr}^{3+}$  and  $\text{Er}^{3+}$  ions in fluoroindate glasses.

Ln <sup>3+</sup>	transition	λ [nm]	A <sub>j</sub> [s <sup>-1</sup> ]	β	τ <sub>rad</sub> [ms]	τ <sub>m</sub> [ms]	η [%]
Pr <sup>3+</sup>	<sup>1</sup> D <sub>2</sub> - <sup>3</sup> H <sub>4</sub>	588	800	0.33	0.41	0.308	75
	<sup>3</sup> H <sub>5</sub>	680	14	0.01			
	<sup>3</sup> H <sub>6</sub>	805	300	0.12			
	<sup>3</sup> F <sub>2</sub>	845	540	0.22			
	<sup>3</sup> F <sub>3</sub>	950	75	0.03			
	<sup>3</sup> F <sub>4</sub>	995	480	0.20			
	<sup>1</sup> G <sub>4</sub>	1450	230	0.09			
	<sup>1</sup> G <sub>4</sub> - <sup>3</sup> H <sub>4</sub>	1010	24	0.07	2.80	0.365	13
	<sup>3</sup> H <sub>5</sub>	1335	232	0.65			
	<sup>3</sup> H <sub>6</sub>	1890	75	0.21			
	<sup>3</sup> F <sub>2</sub>	2110	1	<0.01			
	<sup>3</sup> F <sub>3</sub>	2950	1	<0.01			
	<sup>3</sup> F <sub>4</sub>	3400	24	0.07			
	<sup>4</sup> I <sub>11/2</sub> - <sup>4</sup> I <sub>15/2</sub>	980	134	0.90			
<sup>4</sup> I <sub>13/2</sub>	2817	15	0.10				
<sup>4</sup> I <sub>13/2</sub> - <sup>4</sup> I <sub>15/2</sub>	1535	116	1.00	8.62	8.60	99.8	

**Table 2.** Calculated radiative transition rates  $A_j$ , luminescence branching ratios  $\beta$  and corresponding radiative lifetimes  $\tau_{rad}$  for Pr<sup>3+</sup> and Er<sup>3+</sup> ions in fluoroindate glasses. The values of measured lifetimes  $\tau_m$  and quantum efficiencies  $\eta$  for excited levels of Pr<sup>3+</sup> and Er<sup>3+</sup> ions are also indicated.

$$A_j = \frac{64\pi^4 e^2}{3h(2J+1)\lambda^3} \times \frac{n(n^2+2)^2}{9} \times \sum_{t=2,4,6} \Omega_t \langle 4f^N J || U^t || 4f^N J' \rangle^2 \quad (4)$$

The total radiative emission rate  $A_T$  involving all the intermediate terms is the sum of the  $A_j$  terms. The radiative lifetime  $\tau_{rad}$  of an excited level is the inverse of the total radiative emission rate (Eq. 5), whereas the luminescence branching ratio  $\beta$  is due to the relative intensities of transitions from excited level to all terminal levels (Eq. 6).

$$\tau_{rad} = \frac{1}{\sum_i A_{ji}} = \frac{1}{A_T} \quad (5)$$

$$\beta = \frac{A_j}{\sum_i A_{ji}} \quad (6)$$

The calculated radiative transition rates  $A_j$ , luminescence branching ratios  $\beta$  and corresponding radiative lifetimes  $\tau_{rad}$  for Pr<sup>3+</sup> and Er<sup>3+</sup> ions in fluoroindate glasses are presented in Table 2. The calculation results are limited to transitions originating from the <sup>1</sup>D<sub>2</sub> and <sup>1</sup>G<sub>4</sub> excited levels of Pr<sup>3+</sup> as well as the <sup>4</sup>I<sub>11/2</sub> and <sup>4</sup>I<sub>13/2</sub> excited levels of Er<sup>3+</sup>, from which the main luminescence lines in the near-infrared spectral range (950–1650 nm) occur.


Measured lifetimes  $\tau_m$  for the <sup>1</sup>D<sub>2</sub> and <sup>1</sup>G<sub>4</sub> (Pr<sup>3+</sup>) and the <sup>4</sup>I<sub>11/2</sub> and <sup>4</sup>I<sub>13/2</sub> (Er<sup>3+</sup>) excited levels are also given in Table 2 in order to determine quantum efficiencies  $\eta$  of rare earth ions in fluoroindate glasses using the following equation:

$$\eta = \frac{\tau_m}{\tau_{rad}} \times 100\% \quad (7)$$

Figure 2 presents near-infrared luminescence spectra of fluoroindate glasses singly doped with Er<sup>3+</sup> and Pr<sup>3+</sup>. The spectra were measured for glass samples in the 950–1650 nm ranges. For both Er<sup>3+</sup> and Pr<sup>3+</sup> doped glass samples, the activator concentration is equal to 0.1 mol%.

For Er<sup>3+</sup> singly doped glass, the spectra consist of luminescence bands centered at 980 nm and 1535 nm, which correspond to transitions originating from the <sup>4</sup>I<sub>11/2</sub> and <sup>4</sup>I<sub>13/2</sub> excited levels to the <sup>4</sup>I<sub>15/2</sub> ground level, respectively. When glass sample is excited at higher-lying <sup>4</sup>F<sub>7/2</sub> (488 nm) or <sup>2</sup>H<sub>11/2</sub> (523 nm) level, luminescence band near 1230 nm associated to the <sup>4</sup>S<sub>3/2</sub> → <sup>4</sup>I<sub>11/2</sub> (Er<sup>3+</sup>) transition is also well observed.

The most intense luminescence band is related to the main <sup>4</sup>I<sub>13/2</sub> → <sup>4</sup>I<sub>15/2</sub> near-infrared laser transition of Er<sup>3+</sup>. Its luminescence intensity depends strongly on excitation wavelengths. Several spectroscopic parameters for the <sup>4</sup>I<sub>13/2</sub> → <sup>4</sup>I<sub>15/2</sub> near-infrared transition of Er<sup>3+</sup> ions in fluoroindate glass at 1535 nm, necessary for optical and laser characteristics, were determined. The luminescence linewidth defined as the full width at half maximum (FWHM) for the <sup>4</sup>I<sub>13/2</sub> → <sup>4</sup>I<sub>15/2</sub> (Er<sup>3+</sup>) transition is equal to 72 nm. The measured luminescence lifetime for the upper <sup>4</sup>I<sub>13/2</sub> laser level of Er<sup>3+</sup> ions in fluoroindate glass is close to 8.6 ms, whereas radiative lifetime calculated from the Judd–Ofelt framework seems to be 8.62 ms (Table 2). Thus, the quantum efficiency for the upper <sup>4</sup>I<sub>13/2</sub> laser level of Er<sup>3+</sup> ions in fluoroindate glass is nearly ~100%. The same situation is also observed

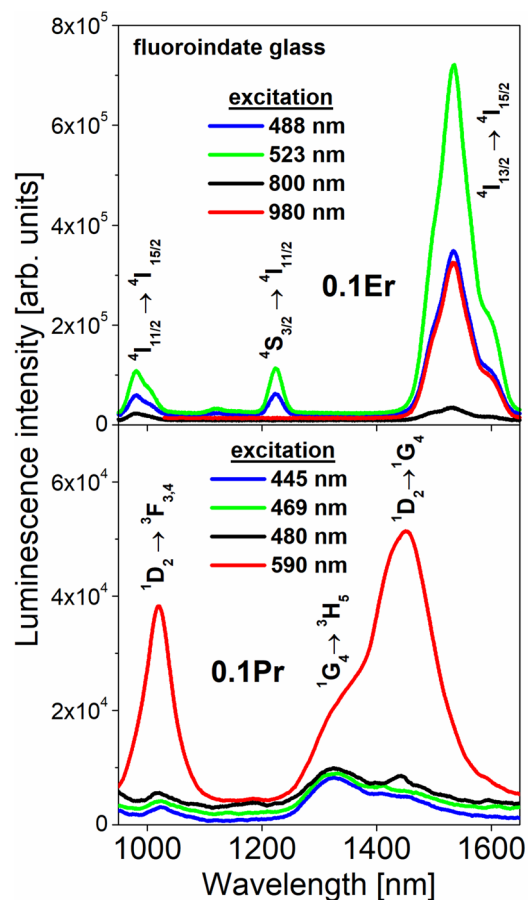

**Figure 2.** Near-infrared luminescence spectra of fluoroindate glasses doped with  $\text{Pr}^{3+}$  (top) and  $\text{Er}^{3+}$  (bottom).


for the higher-lying  ${}^4\text{I}_{11/2}$  level of  $\text{Er}^{3+}$ , for which the measured and calculated radiative lifetimes and the quantum efficiency are close to  $\tau_m = 6.65$  ms,  $\tau_{\text{rad}} = 6.71$  ms and  $\eta = \sim 99\%$ . The quantum efficiency for the main  ${}^4\text{I}_{13/2} \rightarrow {}^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) laser transition at 1535 nm in fluoroindate glass is significantly higher in comparison to the values obtained earlier for borate ( $\eta = 3\%$ ) and germanate ( $\eta = 71\%$ ) glasses<sup>30</sup>. This phenomenon is related directly to the lower phonon energy ( $\hbar\omega = 510$   $\text{cm}^{-1}$ ) of the fluoroindate glass-host<sup>17</sup>.

The peak stimulated emission cross-section  $\sigma_{\text{em}}$  is one of the most important radiative parameters and should be also examined because the strong luminescence band at 1535 nm due to the  ${}^4\text{I}_{13/2} \rightarrow {}^4\text{I}_{15/2}$  transition has been considered as a potential near-infrared laser emission of  $\text{Er}^{3+}$  ions in fluoroindate glass. It is generally accepted that an efficient laser transition is characterized by relatively large value of  $\sigma_{\text{em}}$ . The peak stimulated emission cross-section  $\sigma_{\text{em}}$  can be obtained from the calculated radiative transition rate  $A_j$  using the following relation:

$$\sigma_{\text{em}} = \frac{\lambda_p^4}{8\pi c n^2 \Delta\lambda} A_j \quad (8)$$

where  $\lambda_p$  is the peak luminescence wavelength,  $\Delta\lambda$  is the effective linewidth (FWHM),  $n$  is the refractive index and  $c$  is the velocity of light. The maximum peak stimulated emission cross-section is close to nearly  $5.4 \times 10^{-21}$   $\text{cm}^2$  at 1535 nm for fluoroindate glass and its value is typical for fluoride laser glasses containing  $\text{Er}^{3+}$  ions<sup>31</sup>.

Near-infrared luminescence spectra of  $\text{Pr}^{3+}$  ions in fluoroindate glasses are also presented on Fig. 2 (bottom). In general, three near-infrared luminescence bands are quite well observed under different excitation wavelengths. They correspond to  ${}^1\text{D}_2 \rightarrow {}^3\text{F}_{3,4}$  (1050 nm),  ${}^1\text{G}_4 \rightarrow {}^3\text{H}_5$  (1335 nm) and  ${}^1\text{D}_2 \rightarrow {}^1\text{G}_4$  (1450 nm) electronic transitions of  $\text{Pr}^{3+}$ . However, the intensities of luminescence bands of  $\text{Pr}^{3+}$  are extremely low, when glass sample was excited at higher lying  ${}^3\text{P}_2$  (445 nm),  ${}^3\text{P}_1$  (469 nm) or  ${}^3\text{P}_0$  (480 nm) level, respectively. In this case, the  ${}^1\text{G}_4 \rightarrow {}^3\text{H}_5$  transition with its FWHM value equal to about 195 nm is dominant transition of trivalent  $\text{Pr}^{3+}$ . The  ${}^1\text{G}_4$  measured lifetime of  $\text{Pr}^{3+}$  ( $\tau_m = 0.365$  ms) is considerably lower than corresponding calculated radiative lifetime ( $\tau_m = 2.8$  ms). Although the luminescence branching ratio for the  ${}^1\text{G}_4 \rightarrow {}^3\text{H}_5$  transition at 1335 nm is relatively high and its value is close to  $\beta = 65\%$ , the quantum efficiency ( $\eta = 13\%$ ) for the  ${}^1\text{G}_4$  excited level of  $\text{Pr}^{3+}$  ions is rather low (Table 2). Completely different situation is observed for  $\text{Pr}^{3+}$  ions in fluoroindate glass under direct excitation of  ${}^1\text{D}_2$  state at 590 nm. The near-infrared luminescence bands originating to transitions from the  ${}^1\text{D}_2$  level of  $\text{Pr}^{3+}$  ions are highly intense compared to the  ${}^1\text{G}_4 \rightarrow {}^3\text{H}_5$  transition at 1335 nm. In particular, broadband near-infrared spectra covering a wavelength range from 1300 nm to about 1650 nm are

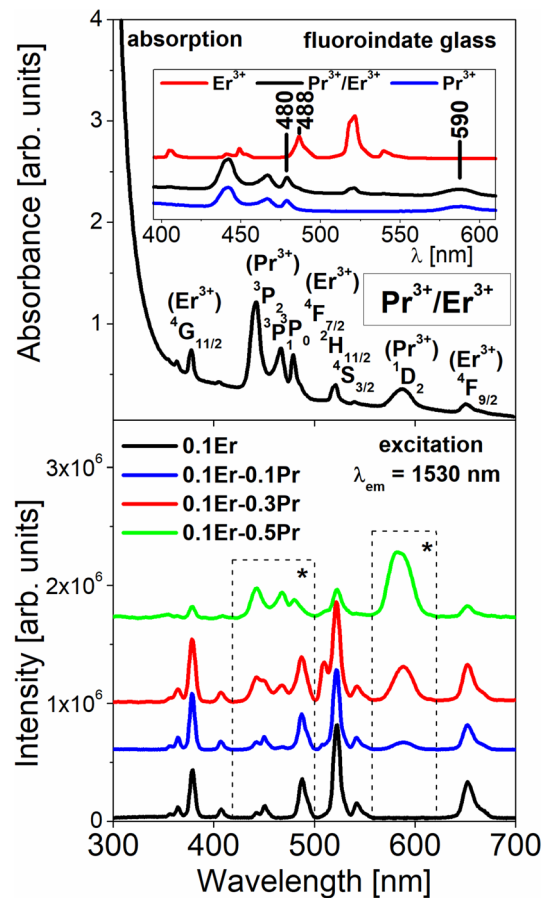


**Figure 3.** Absorption (top) and excitation (bottom) spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . The results are compared to the spectra, which were measured for rare earth singly doped glass samples.

great of interest and really important for optical telecommunication<sup>21</sup>. The main most intense near-infrared luminescence band near 1450 nm is assigned to the  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transition of  $\text{Pr}^{3+}$  and its value of FWHM is close to 130 nm. Although the luminescence branching ratio ( $\beta = 9\%$ ), the measured ( $\tau_m = 0.308$  ms) and calculated radiative ( $\tau_m = 0.410$  ms) lifetimes are not too high, the quantum efficiency for the  $^1\text{D}_2$  level of  $\text{Pr}^{3+}$  is close to  $\eta = 75\%$  (Table 2). Furthermore, the peak stimulated emission cross-section for the  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transition of  $\text{Pr}^{3+}$  ions in fluoroindate glass was determined. From literature data it is well-known that inorganic glasses singly doped with praseodymium exhibit fascinating prospects in broadband near-infrared fiber amplifier, when the emission cross-section profile is large<sup>21</sup>. In our case, the peak stimulated emission cross-section for the  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transition of  $\text{Pr}^{3+}$  ions is also relatively large. Its value is close to  $0.5 \times 10^{-20} \text{ cm}^2$ . Finally, the stimulated emission cross-section ( $\sigma_{em}$ ), the emission linewidth (FWHM) and the measured lifetime ( $\tau_m$ ) were applied to calculate the gain bandwidth ( $\sigma_{em} \times \text{FWHM}$  product) and the figure of merit (FOM) given by  $\sigma_{em} \times \tau_m$ , respectively. It is interesting to see that the  $\sigma_{em} \times \text{FWHM}$  product for the  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transition of  $\text{Pr}^{3+}$  ions in fluoroindate glass is equal to  $65 \times 10^{-27} \text{ cm}^3$ , which is rather low compared to the following values:  $176.4 \times 10^{-27} \text{ cm}^3$  for fluorotellurite glass<sup>32</sup> and  $203.5 \times 10^{-27} \text{ cm}^3$  for gallo-germanate glass with  $\text{BaF}_2$ <sup>33</sup>. This behavior is mainly due to the fact that luminescence linewidth for the  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transition of  $\text{Pr}^{3+}$  ions in fluoroindate glass (FWHM = 130 nm) is considerably lower than values obtained for fluorotellurite glass (FWHM = 196 nm) and gallo-germanate glass (FWHM = 208.5 nm). On the other hand, the figure of merit (FOM) for the  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transition of  $\text{Pr}^{3+}$  ions in fluoroindate glass is relatively larger ( $\sigma_{em} \times \tau_m = 154 \times 10^{-26} \text{ cm}^2\text{s}$ ) in comparison to the values  $83.1 \times 10^{-26} \text{ cm}^2\text{s}$  for fluorotellurite glass<sup>32</sup> and  $107.5 \times 10^{-26} \text{ cm}^2\text{s}$  for gallo-germanate glass modified by  $\text{BaF}_2$ <sup>33</sup>. Our experimental studies and theoretical calculations demonstrate that  $\text{Pr}^{3+}$  singly doped fluoroindate glasses are promising for broadband near-infrared amplifiers.

**Fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ .** Figure 3 present absorption (top) and excitation (bottom) spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . The results are compared to the absorption spectra, which were measured for rare earth singly doped glass samples (inset).

The absorption spectrum for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass sample consists of several bands corresponding to both electronic transitions of rare earths originating from the ground levels  $^3\text{H}_4$  ( $\text{Pr}^{3+}$ ) and  $^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) to the excited levels. In particular, two spectral ranges near 590 nm and between 480 and 488 nm are important from the

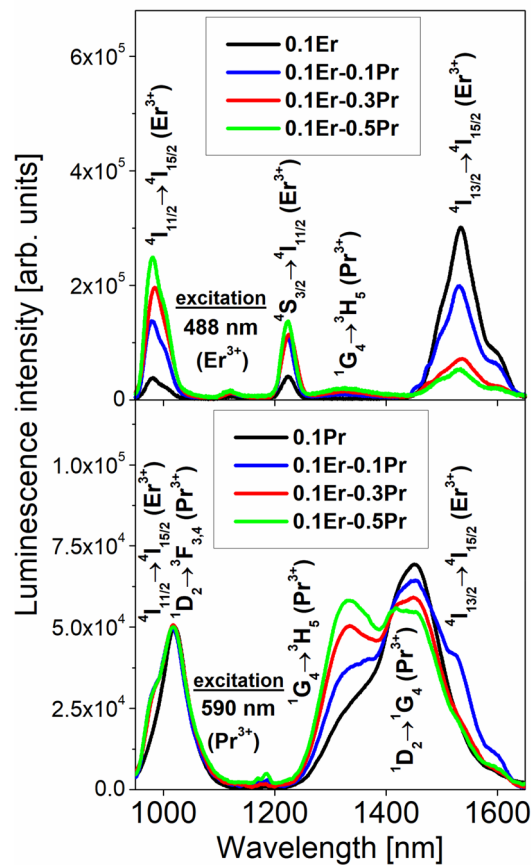


**Figure 4.** Near-infrared luminescence spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  ions under direct 488 nm (top) and 590 nm (bottom) excitation. The results are compared to the spectra, which were measured for rare earth singly doped glass samples.

spectroscopic point of view. In the first spectral range near 590 nm, the absorption band associated to  $^3\text{H}_4 \rightarrow ^1\text{D}_2$  transition of  $\text{Pr}^{3+}$  is located. In the second spectral range, two absorption bands related to  $^3\text{H}_4 \rightarrow ^3\text{P}_0$  transition of  $\text{Pr}^{3+}$  (480 nm) and  $^4\text{I}_{15/2} \rightarrow ^4\text{F}_{7/2}$  transition of  $\text{Er}^{3+}$  (488 nm) are quite well overlapped.

The excitation spectra measured for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass samples under monitoring emission wavelength 1530 nm ( $^4\text{I}_{13/2} \text{Er}^{3+}$ ) give interesting results. It is clearly shown in these two spectral ranges denoted as (\*) that the intensity of band at 590 nm assigned to  $^3\text{H}_4 \rightarrow ^3\text{P}_0$  transition of  $\text{Pr}^{3+}$  ions increase, whereas the relative band intensities of  $^3\text{H}_4 \rightarrow ^3\text{P}_0$  ( $\text{Pr}^{3+}$ ) and  $^4\text{I}_{15/2} \rightarrow ^4\text{F}_{7/2}$  ( $\text{Er}^{3+}$ ) transitions located between 480 and 488 nm are drastically changed with increasing  $\text{Pr}^{3+}$  concentration. It also suggests that the energy transfer process between  $\text{Pr}^{3+}$  and  $\text{Er}^{3+}$  ions in fluoroindate glass occurs.

In the next step, luminescence spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  have been examined under different excitation wavelengths. In general,  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glasses belong to amorphous systems emitting visible light and near-infrared radiation. It is quite well-known that several visible emission bands from the  $^3\text{P}_0$ ,  $^1\text{D}_2$  ( $\text{Pr}^{3+}$ ) and the ( $^2\text{H}_{11/2}$ ,  $^4\text{S}_{3/2}$ ),  $^4\text{F}_{9/2}$  excited levels of rare earth ions can be well observed for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glasses<sup>34</sup>. These aspects for fluoroindate glass are not presented and discussed here. Our investigations are limited to  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glass emitting near-infrared radiation. Figure 4 shows near-infrared luminescence spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  under direct 488 nm (top) and 590 nm (bottom) excitation. The results are compared to the spectra, which were measured for rare earth singly doped glass samples.

Four emission bands at 980 nm, 1230 nm, 1335 nm and 1535 nm are observed for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses under direct excitation of  $^4\text{F}_{7/2}$  level of  $\text{Er}^{3+}$  at 488 nm. They correspond to  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ),  $^4\text{S}_{3/2} \rightarrow ^4\text{I}_{11/2}$  ( $\text{Er}^{3+}$ ),  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  ( $\text{Pr}^{3+}$ ) and  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) transitions, respectively. In contrast to  $\text{Er}^{3+}$  singly doped glass, the intensity of emission band at 1535 nm due to the main  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) near-infrared laser transition is reduced, whereas the emission band intensities related to  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  and  $^4\text{S}_{3/2} \rightarrow ^4\text{I}_{11/2}$  ( $\text{Er}^{3+}$ ) transitions increase with increasing  $\text{Pr}^{3+}$  concentration in samples co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . The emission linewidth for  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) near-infrared laser transition is nearly independent on  $\text{Pr}^{3+}$  concentration and its FWHM value is close to  $75 \pm 3$  nm. The intensity of emission band at 1335 nm associated to the  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  ( $\text{Pr}^{3+}$ ) transition increase with increasing activator ( $\text{Pr}^{3+}$ ) concentration. The experimental results for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses clearly suggest (a) the presence of the energy transfer process from  $\text{Er}^{3+}$  to  $\text{Pr}^{3+}$  and (b) near-infrared emission of  $\text{Pr}^{3+}$  at 1335 nm under direct excitation of  $\text{Er}^{3+}$ . Further investigations indicate that five near-infrared

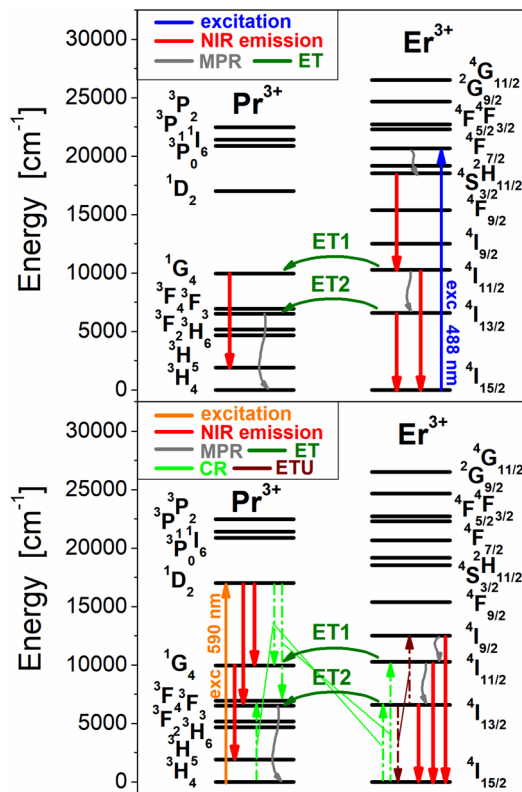


**Figure 5.** Energy level scheme for fluoroindate glass co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . All transitions are also indicated for glass samples excited at 488 nm (top) and 590 nm (bottom).

luminescence bands at about 980 nm, 1050 nm, 1335 nm, 1450 nm and 1535 nm are quite well observed for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses under direct excitation of  $^1\text{D}_2$  level of  $\text{Pr}^{3+}$  at 590 nm. Emission bands are due to the  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ),  $^1\text{D}_2 \rightarrow ^3\text{F}_{3,4}$  ( $\text{Pr}^{3+}$ ),  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  ( $\text{Pr}^{3+}$ ),  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  ( $\text{Pr}^{3+}$ ) and  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ), respectively. The presence of  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  and  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  transitions of  $\text{Er}^{3+}$  in the luminescence spectra measured under direct excitation of  $\text{Pr}^{3+}$  confirms the energy transfer process from  $\text{Pr}^{3+}$  to  $\text{Er}^{3+}$  ions in fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . Firstly, broadband near-infrared luminescence at around 1000 nm in  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass samples is due to two overlapped  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) and  $^1\text{D}_2 \rightarrow ^3\text{F}_{3,4}$  ( $\text{Pr}^{3+}$ ) transitions. These phenomena were studied previously for fluorotellurite glass co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  ions<sup>35</sup>. Secondly, the near-infrared emission band at 1535 nm due to  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) transition is overlapped with  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  transition of  $\text{Pr}^{3+}$  in glass samples co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . These effects are not observed for  $\text{Pr}^{3+}$  singly doped glass sample. Furthermore, the intensity of emission band at 1335 nm due to the  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  ( $\text{Pr}^{3+}$ ) transition enhance, whereas the intensity of emission band at 1450 nm corresponding to  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  ( $\text{Pr}^{3+}$ ) is reduced with increasing  $\text{Pr}^{3+}$  concentration in glass composition. Interestingly, luminescence linewidth for broadband near-infrared luminescence covering a wavelength range from 1300 nm to about 1650 nm and associated to two overlapped  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  and  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transitions of  $\text{Pr}^{3+}$  enhance drastically in fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . In contrast to  $\text{Pr}^{3+}$  singly doped glass (FWHM = 130 nm), emission linewidth for glass samples co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  increase to nearly  $225 \pm 5$  nm and its value slightly depends on  $\text{Pr}^{3+}$  concentration. All near-infrared transitions indicated for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses excited directly at 488 nm or 590 nm are schematized on the energy level diagram (Fig. 5).

The mechanisms for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass system involving possible energy transfer and radiative/nonradiative relaxation channels, i.e. energy transfer routes (ET), multiphonon relaxation (MPR) and cross-relaxation (CR) processes, have been proposed and discussed in details by Zhou et al.<sup>25</sup>.

When glass sample co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  is directly pumped at 488 nm, the excited level  $^4\text{F}_{7/2}$  ( $\text{Er}^{3+}$ ) is well populated by the ground-state absorption process (GSA). The energy transfer process (ET) from the  $^4\text{F}_{7/2}$  ( $\text{Er}^{3+}$ ) level to the  $^3\text{P}_0$  ( $\text{Pr}^{3+}$ ) level is not observed and it is rather impossible, because the  $^3\text{P}_0$  level of  $\text{Pr}^{3+}$  is higher-lying than the  $^4\text{F}_{7/2}$  level of  $\text{Er}^{3+}$ . There is also the main reason that near-infrared luminescence bands from the higher-lying  $^1\text{D}_2$  level of  $\text{Pr}^{3+}$  ions in fluoroindate glasses are not observed under 488 nm excitation of  $\text{Er}^{3+}$ . The excitation energy transfers very fast nonradiatively to the  $^4\text{S}_{3/2}$  level by multiphonon relaxation (MPR) and then relaxes radiatively generating near-infrared emission at 1230 nm associated to the  $^4\text{S}_{3/2} \rightarrow ^4\text{I}_{11/2}$  transition of  $\text{Er}^{3+}$ . The another possible way to depopulate  $^4\text{F}_{7/2}$  level is nonradiative relaxation to the  $^4\text{I}_{11/2}$  level by MPR process owing to small energy gaps between the  $^4\text{F}_{7/2}$  excited level and lower-lying levels or cross-relaxation process (CR): [ $^4\text{F}_{7/2}, ^4\text{I}_{15/2} \rightarrow ^4\text{I}_{11/2}, ^4\text{I}_{11/2}$ ], when concentration of  $\text{Er}^{3+}$  ions in glass sample is relatively high. Next, part of excitation energy is transferred nonradiatively from the  $^4\text{I}_{11/2}$  level to the lower-lying  $^4\text{I}_{13/2}$  level by MPR process, and consequently two near-infrared luminescence bands centered at 980 nm and 1535 nm due to  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$



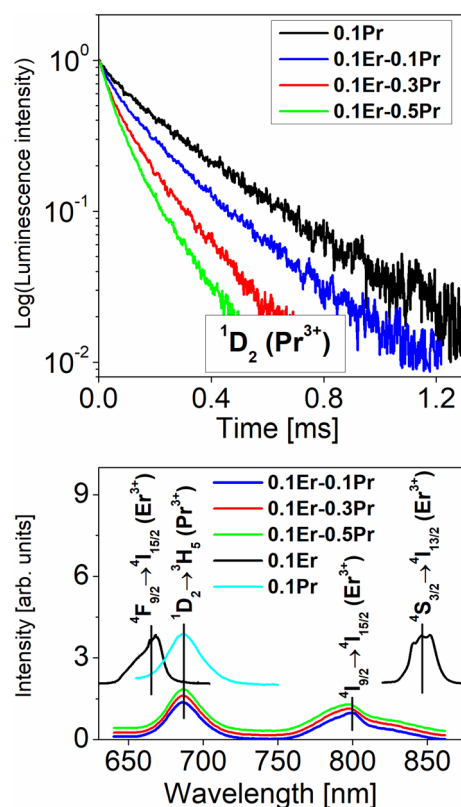

**Figure 6.** Luminescence decays from  $^1D_2$  ( $Pr^{3+}$ ) excited state (top) and visible-NIR emission spectra (bottom) of fluorindate glasses containing  $Pr^{3+}$ ,  $Er^{3+}$  and  $Pr^{3+}/Er^{3+}$ .

and  $^4I_{13/2} \rightarrow ^4I_{15/2}$  transitions are well observed. Finally, the excitation energy is successfully transferred from the  $^4I_{11/2}$  ( $Er^{3+}$ ) level to the  $^1G_4$  ( $Pr^{3+}$ ) level (ET1) and the  $^4I_{13/2}$  ( $Er^{3+}$ ) level to the  $^3F_{3,4}$  ( $Pr^{3+}$ ) level (ET2) by energy transfer processes. In particular, the ET1 process plays the important role, leading to near-infrared luminescence at 1335 nm due to  $^1G_4 \rightarrow ^3H_5$  transition of  $Pr^{3+}$  under direct excitation of  $Er^{3+}$ .

When glass sample co-doped with  $Pr^{3+}/Er^{3+}$  is directly pumped at 590 nm, the excited level  $^1D_2$  ( $Pr^{3+}$ ) is well populated by the ground-state absorption process (GSA). Part of excitation energy relaxes radiatively and two near-infrared luminescence bands at about 1050 nm and 1450 nm are observed, which correspond to transitions originating from the  $^1D_2$  excited level to the lower-lying  $^3F_{3,4}$  and  $^1G_4$  levels of  $Pr^{3+}$ . Another part of excitation energy is transferred nonradiatively by well-known CR process: [ $^1D_2$ ,  $^3H_4 \rightarrow ^1G_4$ ,  $^3F_{3,4}$ ]<sup>36</sup>. At this moment, it should be also pointed that the second CR process [ $^1D_2$ ,  $^3H_4 \rightarrow ^3F_{3,4}$ ,  $^1G_4$ ] was also proposed, but it is still not sure which one is more dominant. For  $Pr^{3+}/Er^{3+}$  co-doped samples, another cross-relaxation route that depopulate efficiently the  $^1D_2$  ( $Pr^{3+}$ ) level is also possible. This can be attributed to the following CR process: [ $^1D_2$  ( $Pr^{3+}$ ),  $^4I_{15/2}$  ( $Er^{3+}$ )  $\rightarrow$   $^1G_4$  ( $Pr^{3+}$ ),  $^4I_{13/2}$  ( $Er^{3+}$ )]. Thus, part of the excitation energy is transferred from  $Pr^{3+}$  to  $Er^{3+}$  ions, giving important contribution to near-infrared emission at 1535 nm related to  $^4I_{13/2} \rightarrow ^4I_{15/2}$  transition of  $Er^{3+}$ . However, the near-infrared luminescence at 980 nm due to  $^4I_{11/2} \rightarrow ^4I_{15/2}$  transition of  $Er^{3+}$  is also successfully observed under excitation of  $Pr^{3+}$  ions at 590 nm (Fig. 4). The back energy transfer process from the  $^1G_4$  ( $Pr^{3+}$ ) level to the  $^4I_{11/2}$  ( $Er^{3+}$ ) level is rather impossible, because the  $^4I_{11/2}$  level of  $Er^{3+}$  is higher-lying than the  $^1G_4$  level of  $Pr^{3+}$ .

Based on the energy level diagram, the  $^4I_{11/2}$  level of  $Er^{3+}$  ions in  $Pr^{3+}/Er^{3+}$  co-doped glass samples can be populated in two ways. First, the presence of the phonon-assisted energy transfer process from the  $^1D_2$  ( $Pr^{3+}$ ) level to the  $^4F_{9/2}$  ( $Er^{3+}$ ) is proposed but it should be ignored considering the relatively large energy gap between them ( $\sim 1500$   $cm^{-1}$ ) and the absence of luminescence lines from the  $^4F_{9/2}$  level<sup>25</sup>, for example well-known  $^4F_{9/2} \rightarrow ^4I_{15/2}$  red transition of  $Er^{3+}$  ions at 670 nm. The second way is the possible cross-relaxation process: [ $^1D_2$  ( $Pr^{3+}$ ),  $^4I_{15/2}$  ( $Er^{3+}$ )  $\rightarrow$   $^3F_{3,4}$  ( $Pr^{3+}$ ),  $^4I_{11/2}$  ( $Er^{3+}$ )]. The question how higher-lying  $^4I_{11/2}$  level of  $Er^{3+}$  is populated under direct 590 nm excitation of  $Pr^{3+}$  is still open and actual, and further experiments are necessary to understand the population mechanism and multichannel relaxation in  $Pr^{3+}/Er^{3+}$  co-doped glass systems. The presence of cross-relaxation processes from the  $^1D_2$  ( $Pr^{3+}$ ) level in fluorindate glasses co-doped with  $Pr^{3+}/Er^{3+}$  was confirmed by luminescence spectra and decay measurements.

Luminescence decays from the  $^1D_2$  level of  $Pr^{3+}$  ions in fluorindate glasses co-doped with  $Pr^{3+}/Er^{3+}$  are presented in Fig. 6 (top). The luminescence decay curves for the  $^1D_2$  level of  $Pr^{3+}$  were measured under monitoring emission wavelength 1450 nm.

Based on decays, luminescence lifetimes for the  $^1D_2$  level of  $Pr^{3+}$  were determined. For  $Pr^{3+}/Er^{3+}$  co-doped glass samples, the  $^1D_2$  luminescence lifetime is reduced from 197  $\mu s$  (0.1Er-0.1Pr) to 127  $\mu s$  (0.1Er-0.3Pr) and


92  $\mu\text{s}$  (0.1Er-0.5Pr) with increasing  $\text{Pr}^{3+}$  concentration. This behavior may be attributed to the presence of cross-relaxation processes between neighboring pairs  $\text{Pr}^{3+}\text{-Pr}^{3+}$  and  $\text{Pr}^{3+}\text{-Er}^{3+}$  in fluoroindate glasses. Also, we compare results for  $\text{Pr}^{3+}$ -doped fluoroindate glasses in the absence and presence of  $\text{Er}^{3+}$ . Thus, the measured  $^1\text{D}_2$  lifetime is reduced from 308  $\mu\text{s}$  (0.1Pr) to 197  $\mu\text{s}$  (0.1Er-0.1Pr), whereas the quantum efficiency for the  $^1\text{D}_2$  excited level of  $\text{Pr}^{3+}$  decreases from 75% (0.1Pr) to 48% (0.1Er-0.1Pr).

Figure 6 (bottom) shows the visible-NIR emission spectra of fluoroindate glasses singly doped with  $\text{Pr}^{3+}$  and  $\text{Er}^{3+}$  and doubly doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . In the 630–880 nm spectral range, two emission bands are well observed for  $\text{Er}^{3+}$  singly doped glass under 488 nm excitation. They correspond to the  $^4\text{F}_{9/2} \rightarrow ^4\text{I}_{15/2}$  red transition near 670 nm and the  $^4\text{S}_{3/2} \rightarrow ^4\text{I}_{13/2}$  NIR transition at about 840 nm. The  $^4\text{F}_{9/2} \rightarrow ^4\text{I}_{15/2}$  red transition at 670 nm is not observed for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass samples under direct excitation of  $\text{Pr}^{3+}$  at 590 nm. It was also verified for fluorotellurite glass co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  excited at 594 nm<sup>25</sup>. In comparison to the results obtained for  $\text{Pr}^{3+}$  singly doped glass, the emission band at about 690 nm related to the  $^1\text{D}_2 \rightarrow ^3\text{H}_5$  ( $\text{Pr}^{3+}$ ) transition was registered in this spectral range for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass samples. Unexpectedly, the additional NIR luminescence band at 800 nm corresponding to the  $^4\text{I}_{9/2} \rightarrow ^4\text{I}_{15/2}$  transition of  $\text{Er}^{3+}$  ions was also detected in  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses under direct excitation  $^1\text{D}_2$  ( $\text{Pr}^{3+}$ ) level at 590 nm. For that reason, it is interesting to explain how the  $^4\text{I}_{9/2}$  ( $\text{Er}^{3+}$ ) level is populated in  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass samples excited at the  $^1\text{D}_2$  ( $\text{Pr}^{3+}$ ) level. We postulate the following mechanisms involving cross-relaxation (CR) and energy transfer up-conversion (ETU) processes applied to populate  $^4\text{I}_{9/2}$ ,  $^4\text{I}_{11/2}$  and  $^4\text{I}_{13/2}$  excited levels of  $\text{Er}^{3+}$ . The excited level  $^1\text{D}_2$  ( $\text{Pr}^{3+}$ ) is depopulated through the cross-relaxation processes: [ $^1\text{D}_2$  ( $\text{Pr}^{3+}$ ),  $^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ )  $\rightarrow$   $^1\text{G}_4$  ( $\text{Pr}^{3+}$ ),  $^4\text{I}_{13/2}$  ( $\text{Er}^{3+}$ )] and [ $^1\text{D}_2$  ( $\text{Pr}^{3+}$ ),  $^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ )  $\rightarrow$   $^3\text{F}_{3,4}$  ( $\text{Pr}^{3+}$ ),  $^4\text{I}_{11/2}$  ( $\text{Er}^{3+}$ )]. Thus, both  $^4\text{I}_{11/2}$  and  $^4\text{I}_{13/2}$  levels are well populated and near-infrared emission bands at 980 nm and 1535 nm due to the  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  and  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  transitions of  $\text{Er}^{3+}$  occur. Additionally, other processes play significant role in changing the population of  $^4\text{I}_{11/2}$  and  $^4\text{I}_{13/2}$  excited levels of  $\text{Er}^{3+}$  ions. The energy transfer up-conversion process (ETU): [ $^4\text{I}_{13/2}$ ,  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{9/2}$ ,  $^4\text{I}_{15/2}$ ] gives important contribution to efficient population of higher-lying  $^4\text{I}_{9/2}$  level of  $\text{Er}^{3+}$  ions<sup>37</sup>. Further studies for the  $\text{Er}^{3+}/\text{Tm}^{3+}/\text{Pr}^{3+}$  triply doped fluoride glass indicate that the ETU process [ $^4\text{I}_{13/2}$ ,  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{9/2}$ ,  $^4\text{I}_{15/2}$ ] increases population of the  $^4\text{I}_{9/2}$  level and then the lower-lying  $^4\text{I}_{11/2}$  level can be populated by a fast multiphonon relaxation from the  $^4\text{I}_{9/2}$  level, which leads to an increase of mid-infrared emission at 2700 nm<sup>38</sup>. Owing to presence of ETU process, it is possible to detect near-infrared emission peaking at 800 nm for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glass, which corresponds to the  $^4\text{I}_{9/2} \rightarrow ^4\text{I}_{15/2}$  transition of  $\text{Er}^{3+}$ . The origin of near-infrared luminescence of  $\text{Er}^{3+}$  at 800 nm has been examined in an excellent work published recently<sup>39</sup>. It was stated that there is no NIR emission found at 800 nm, when the samples are excited to the higher-lying levels ( $^2\text{H}_{11/2}$  or  $^4\text{F}_{9/2}$ ) than the  $^4\text{I}_{9/2}$  level, and the nonradiative relaxation from the upper excited levels to the  $^4\text{I}_{9/2}$  emitting level of  $\text{Er}^{3+}$  ions is extremely inefficient. The  $^4\text{I}_{9/2}$  level of  $\text{Er}^{3+}$  is mainly populated by the adjacent lower-lying  $^4\text{I}_{11/2}$  level upon excitation at 980 nm<sup>39</sup>. It was also confirmed for  $\text{Er}^{3+}$  doped chalcogenide glasses and fibers, where the conversion of incoherent infrared light around 4400 nm into a near-infrared signal at 810 nm was obtained by simultaneously 982 nm pumping<sup>40</sup>.


Further spectroscopic analysis of  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses excited at 488 nm (Fig. 4) clearly indicate that the intensity of near-infrared luminescence band at 1535 nm due to the main  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) laser transition is decreased with increasing  $\text{Pr}^{3+}$  concentration in comparison to the intensities of  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  and  $^4\text{S}_{3/2} \rightarrow ^4\text{I}_{11/2}$  ( $\text{Er}^{3+}$ ) transitions of  $\text{Er}^{3+}$ . Zhou et al.<sup>25</sup> suggested that the relative increase of the near-infrared luminescence of  $\text{Er}^{3+}$  at 1230 nm compared with of 1530 nm can be ascribed to the improved population inversion between the upper and lower levels. Moreover, the decrease of near-infrared luminescence at 1530 nm is due to the energy transfer process from the  $^4\text{I}_{13/2}$  ( $\text{Er}^{3+}$ ) level to the  $^3\text{F}_{3,4}$  ( $\text{Pr}^{3+}$ ) levels. As a consequence, near-infrared emission bands related to transitions originating from the  $^4\text{I}_{11/2}$  level to the lower-lying  $^4\text{I}_{13/2}$  (2700 nm) and  $^4\text{I}_{15/2}$  (980 nm) levels can be enhanced. The luminescence decay analysis for the  $^4\text{I}_{11/2}$  and  $^4\text{I}_{13/2}$  excited levels of  $\text{Er}^{3+}$  ions in  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses confirms this hypothesis.

Figure 7 shows luminescence decay curves for the  $^4\text{I}_{13/2}$  and  $^4\text{I}_{11/2}$  excited states of  $\text{Er}^{3+}$  ions in fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . The decay curves were measured under monitoring emission wavelength 980 nm and 1530 nm, respectively. In both cases, luminescence decay curves measured for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass samples are shortened with increasing  $\text{Pr}^{3+}$  concentration in comparison to glasses singly doped with  $\text{Er}^{3+}$ . Based on decay curves, luminescence lifetimes for the  $^4\text{I}_{13/2}$  and  $^4\text{I}_{11/2}$  excited levels of  $\text{Er}^{3+}$  were determined. Based on measured lifetimes for glass samples with the absence and presence of  $\text{Pr}^{3+}$ , the energy transfer efficiencies for the  $^4\text{I}_{13/2}$  and  $^4\text{I}_{11/2}$  levels of  $\text{Er}^{3+}$  ions were also calculated. Luminescence lifetimes and energy transfer efficiencies varying with  $\text{Pr}^{3+}$  concentration are schematically presented on Fig. 8.


The luminescence lifetime for the  $^4\text{I}_{13/2}$  level of  $\text{Er}^{3+}$  is decreased from 8.60 ms (0.1Er) to 3.40 ms (0.1Er-0.1Pr), 1.96 ms (0.1Er-0.3Pr) and 1.36 ms (0.1Er-0.5Pr) with increasing  $\text{Pr}^{3+}$  concentration. The reduction of luminescence lifetime for the  $^4\text{I}_{11/2}$  level of  $\text{Er}^{3+}$  ions is also observed. The measured lifetime is changed from 6.65 ms (0.1Er) to 5.91 ms (0.1Er-0.1Pr), 4.92 ms (0.1Er-0.3Pr) and 4.14 ms (0.1Er-0.5Pr) for glass samples with the presence of  $\text{Pr}^{3+}$ . Trends in luminescence lifetimes  $^4\text{I}_{11/2}$  and  $^4\text{I}_{13/2}$  ( $\text{Er}^{3+}$ ) varying with  $\text{Pr}^{3+}$  concentration are similar, but changes in lifetimes and their corresponding values for glasses singly doped with  $\text{Er}^{3+}$  and co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  are significant from the spectroscopic point of view. It is worthy to notice that luminescence lifetimes obtained for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glasses are generally lower for the  $^4\text{I}_{13/2}$  level than  $^4\text{I}_{11/2}$  level, in contrast to measured lifetime for  $\text{Er}^{3+}$  singly doped glass which is higher for the  $^4\text{I}_{13/2}$  level (8.60 ms) than  $^4\text{I}_{11/2}$  level (6.65 ms). This is also the experimental proof that the intensity of near-infrared emission band at 980 nm due to the  $^4\text{I}_{11/2} \rightarrow ^4\text{I}_{15/2}$  transition increase, whereas the intensity luminescence band at 1535 nm related to the  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  transition of  $\text{Er}^{3+}$  is reduced with increasing  $\text{Pr}^{3+}$  concentration in fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . It was confirmed by luminescence decay curve measurements for similar fluoride ZBLAN glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  ions<sup>41</sup>, where the influence of the  $\text{Pr}^{3+}$  codopant on the  $^4\text{I}_{13/2}$  and  $^4\text{I}_{11/2}$  emission lifetimes has been also studied. For ZBLAN glasses, a significant reduction in the  $^4\text{I}_{13/2}$  lifetime was observed following the addition of a small amount of  $\text{Pr}^{3+}$ , while the  $^4\text{I}_{11/2}$  lifetime of  $\text{Er}^{3+}$  was affected to a lesser degree. Thus, the

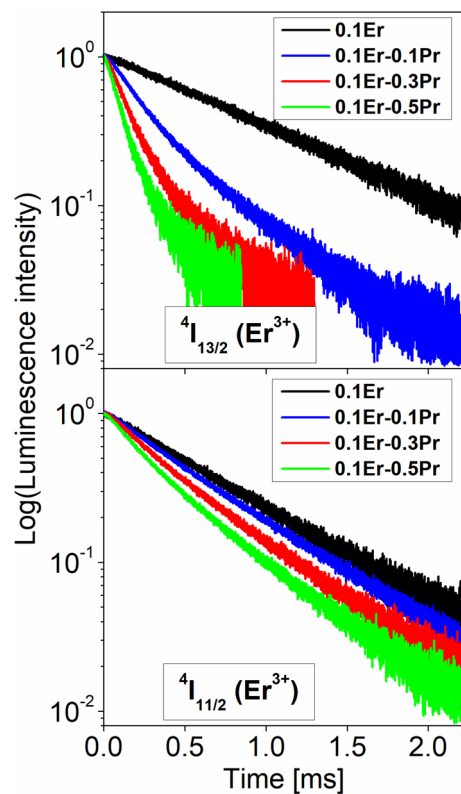

**Figure 7.** Luminescence decays from  $^4I_{13/2}$  (top) and  $^4I_{11/2}$  (bottom) excited states of  $Er^{3+}$  ions in fluoroindate glasses co-doped with  $Pr^{3+}/Er^{3+}$ .

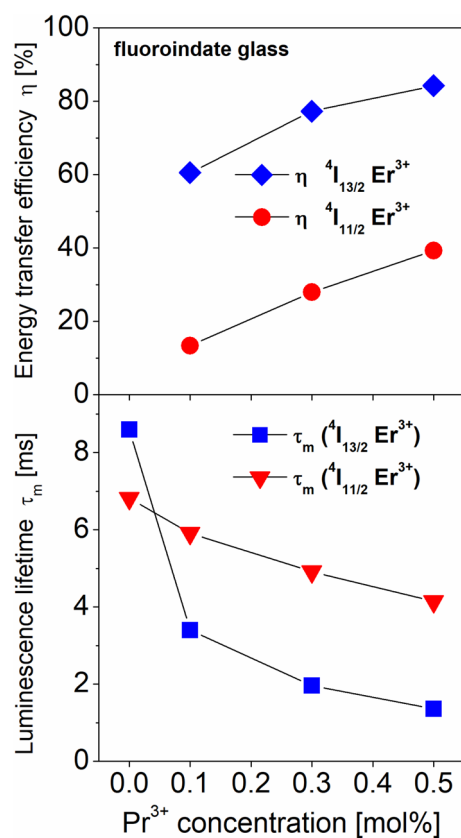

**Figure 8.** Luminescence lifetimes and energy transfer efficiencies varying with  $Pr^{3+}$  concentration.

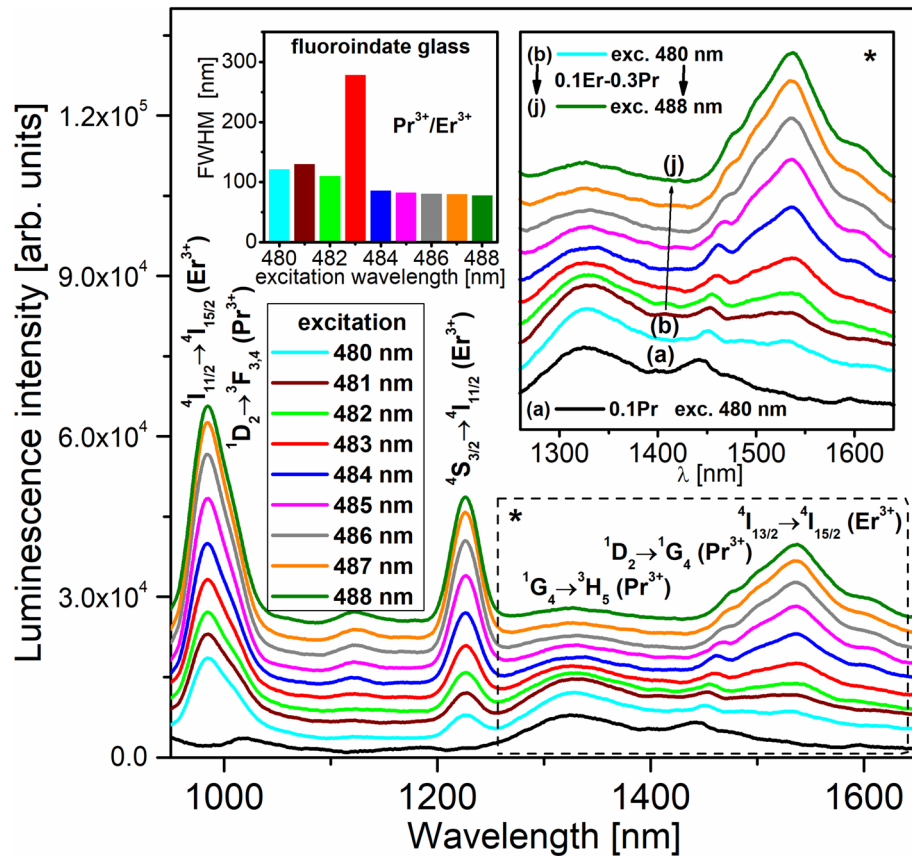


**Figure 9.** Near-infrared luminescence spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  under selective blue excitation. The inset shows values of FWHM depending on the excitation wavelength.

degree of energy transfer process from  $\text{Er}^{3+}$  to  $\text{Pr}^{3+}$  ions is found to be much higher for the  $^4\text{I}_{13/2}$  level (ET2) than for the  $^4\text{I}_{11/2}$  level (Fig. 5). It was also confirmed by calculation of the energy transfer efficiencies in fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ , where the values of  $\eta_{\text{ET}}$  are higher for the  $^4\text{I}_{13/2}$  level than for the  $^4\text{I}_{11/2}$  level. The energy transfer efficiency for the  $^4\text{I}_{13/2}$  level of  $\text{Er}^{3+}$  is increased from 60.5% (0.1Er-0.1Pr) to 77.2% (0.1Er-0.3Pr) and 84.2% (0.1Er-0.5Pr), whereas the value of  $\eta_{\text{ET}}$  for the  $^4\text{I}_{11/2}$  level of  $\text{Er}^{3+}$  is changed from 13.3% (0.1Er-0.1Pr) to 27.9% (0.1Er-0.3Pr) and 39.3% (0.1Er-0.5Pr) with increasing  $\text{Pr}^{3+}$  concentration.

Figure 9 present near-infrared luminescence spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  under selective excitation wavelengths in the spectral range from 480 to 488 nm. This experiment motivated us to demonstrate unambiguously how the excitation wavelengths playing the crucial role in  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped system influence on broadband near-infrared luminescence covering a spectral range from 1250 to 1650 nm. The inset shows schematically values of emission linewidth (FWHM) depending on the selective excitation wavelengths.

The mechanisms for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass system upon selective excitation wavelength at 488 nm ( $^4\text{F}_{7/2}$   $\text{Er}^{3+}$ ) involving several relaxation routes and two energy transfer processes ET1 (from the  $^4\text{I}_{11/2}$  level) and ET2 (from the  $^4\text{I}_{13/2}$  level) have been already discussed here.

Upon selective pumping at 480 nm, the  $^3\text{P}_0$  level of  $\text{Pr}^{3+}$  is well populated by the ground state absorption process (GSA) and then the excitation energy transfers by means of two ways. Part of the excitation energy is transferred from the  $^3\text{P}_0$  level of  $\text{Pr}^{3+}$  to the  $^4\text{F}_{7/2}$  level of  $\text{Er}^{3+}$  ions by the energy transfer process ET3. The second way to depopulate the  $^3\text{P}_0$  level is very fast non-radiative relaxation to the next lower-lying  $^1\text{D}_2$  level of  $\text{Pr}^{3+}$  ions through multiphonon relaxation (MPR) and cross-relaxation process (CR):  $^3\text{P}_0, ^3\text{H}_4 \rightarrow ^1\text{D}_2, ^3\text{H}_6$ . In the next step, several near-infrared emission bands originating to radiative transitions from the  $^1\text{D}_2$  and  $^1\text{G}_4$  levels to the lower-lying levels of  $\text{Pr}^{3+}$  are quite well observed and these aspects have been examined by us in this work. In particular, three near-infrared emission bands of  $\text{Pr}^{3+}$  and  $\text{Er}^{3+}$  located at spectral range denoted as (\*) are the most interesting and important from the optical point of view. They are due to the  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  ( $\text{Pr}^{3+}$ ),  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  ( $\text{Pr}^{3+}$ ) and  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) transitions of rare earths in fluoroindate glass. Their relative intensities are changed drastically when the excitation wavelength varies from 480 to 488 nm. It is evidently to see that the luminescence band intensities of  $\text{Pr}^{3+}$  ions are reduced drastically, while the intensity of band due to the  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  transition of  $\text{Er}^{3+}$  ions is enhanced when the excitation wavelength is selectively changed from 480 to 488 nm. The inset of Fig. 9 shows values of FWHM depending on the excitation wavelength. When sample co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  is excited at 480, 481 or 482 nm, the  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  transition of  $\text{Pr}^{3+}$  ions is dominant transition and emission linewidth seems to be 120–130 nm, which is similar to the value obtained for  $\text{Pr}^{3+}$  singly doped glass (FWHM = 130 nm). When glass sample co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  is excited at spectral range 484/488 nm, the  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  transition of  $\text{Er}^{3+}$

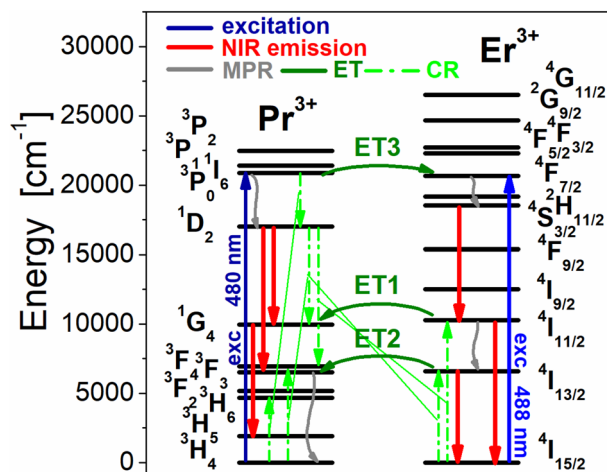

**Figure 10.** Energy level scheme and all transitions for fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  excited at blue spectral region.

ions is dominant transition and values of FWHM are close to about 75–85 nm, similar to the  $\text{Er}^{3+}$  singly doped glass (72 nm). Super-broadband near-infrared luminescence with corresponding value of FWHM = 278 nm is successfully observed, when  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped sample was excited selectively at 483 nm. The luminescence linewidth for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glass (278 nm) is similar to the values of FWHM equal to 236 nm and 296 nm, which were obtained for tellurite glasses doubly doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  ions<sup>42</sup> and triply doped with  $\text{Pr}^{3+}/\text{Er}^{3+}/\text{Nd}^{3+}$  ions<sup>43</sup>. Our experimental investigations confirm that the selective excitation wavelength 483 nm is an optimal pump source to obtain super-broadband luminescence in fluoroindate glass co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$ . The previous results suggest that the  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped phosphate glasses with a 483 nm pump source exciting simultaneously both  $^3\text{P}_0$  ( $\text{Pr}^{3+}$ ) and  $^4\text{F}_{7/2}$  ( $\text{Er}^{3+}$ ) levels are promising amorphous materials for broadband optical amplifiers<sup>44</sup>. The energy level diagram and all transitions for fluoroindate glass co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  excited selectively at blue spectral region are schematized on Fig. 10.

Based on previous scientific reports we confirm that our glass with  $\text{Pr}^{3+}/\text{Er}^{3+}$  is a potential material for broadband fiber amplifiers<sup>45</sup> and its near-IR emission property depends critically on the excitation wavelengths<sup>46</sup>. Similar to oxyfluoroaluminate and fluorozirconate systems<sup>47</sup>, fluoroindate glasses doped with rare earths have potential applications as laser materials.


To summarize, near-infrared luminescence spectra of fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  at 1200–1650 nm range have been examined under different excitation wavelengths and the results are compared to glass samples singly doped with  $\text{Pr}^{3+}$  and  $\text{Er}^{3+}$  (Fig. 11).

$\text{Pr}^{3+}$ -singly doped fluoroindate glass shows near-infrared emission centered at 1335 nm and 1450 nm corresponding to the  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  and  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transitions and their relative emission band intensities depend critically on the excitation wavelengths (480 and 590 nm).  $\text{Er}^{3+}$ -singly doped fluoroindate glass under 488 nm excitation shows near-infrared emission near 1535 nm associated to the main  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  laser transition. When fluoroindate glass co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  is excited at 590 nm, the intensity of emission band at 1335 nm due to the  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  transition is increased in comparison to the  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  transition at 1450 nm, and the spectral linewidth is larger for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass sample (FWHM = 225 nm) than  $\text{Pr}^{3+}$  singly doped glass (FWHM = 130 nm).

Superbroadband near-infrared luminescence in  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glass under selective excitation wavelength (483 nm) is successfully observed. Broadband emission with its linewidth equal to FWHM = 278 nm covering a wavelength range from 1200 to 1650 nm corresponds to the overlapped  $^1\text{G}_4 \rightarrow ^3\text{H}_5$  ( $\text{Pr}^{3+}$ ),  $^1\text{D}_2 \rightarrow ^1\text{G}_4$  ( $\text{Pr}^{3+}$ ) and  $^4\text{I}_{13/2} \rightarrow ^4\text{I}_{15/2}$  ( $\text{Er}^{3+}$ ) transitions of rare earth ions. However, we cannot unambiguously exclude the presence of  $^3\text{F}_{3/4} \rightarrow ^3\text{H}_4$  ( $\text{Pr}^{3+}$ ) transition at about 1600 nm, which was quite well observed in selenide glasses doped with  $\text{Pr}^{3+}$  and co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  ions<sup>48</sup>. Further luminescent studies for  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped fluoroindate glasses excited at 488 nm suggest that they are promising candidates as dual-wavelength fiber-optic amplifiers for 1335 nm and 1535 nm windows similar to the previous excellent results published for Ge-As-Ga-S glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  ions<sup>49</sup>. Moreover reported emission properties of  $\text{Pr}^{3+}/\text{Er}^{3+}$  and  $\text{Er}^{3+50}$  doped glasses inclined to use them in optical fiber construction as a fluoroindate fibers started to be valuable for SC generation<sup>51</sup> and lasers<sup>52–54</sup> beyond 3  $\mu\text{m}$ . Future research will be devoted for fiber development and its length optimization as we believe to obtain superbroadband emission.

## Conclusions

Fluoroindate glasses co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  have been investigated for near-infrared luminescence applications. Near-infrared luminescence properties have been examined under selective excitation wavelengths. The radiative and nonradiative relaxation channels involving several processes like multiphonon relaxation (MPR), cross-relaxation (CR), energy transfer up-conversion (ETU) and their mechanisms are proposed in  $\text{Pr}^{3+}/\text{Er}^{3+}$  co-doped glass samples under direct excitation of  $\text{Pr}^{3+}$  and/or  $\text{Er}^{3+}$  ions and the energy transfer processes (ET) from  $\text{Pr}^{3+}$  to  $\text{Er}^{3+}$  and from  $\text{Er}^{3+}$  to  $\text{Pr}^{3+}$  were identified. In particular, near-infrared luminescence covering a

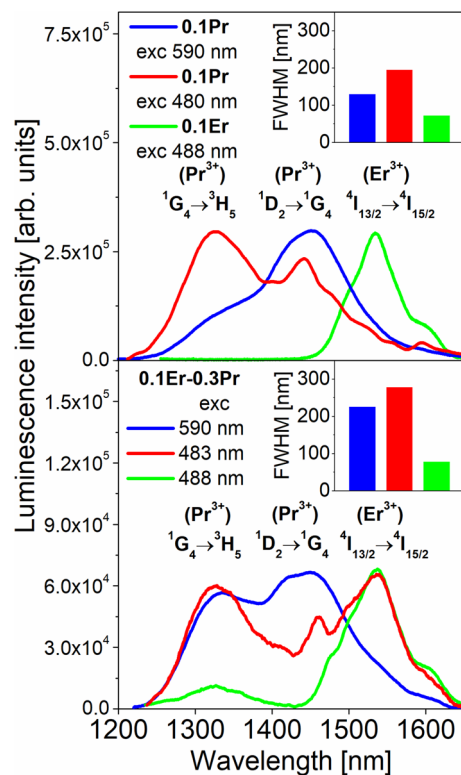

**Figure 11.** Normalized near-infrared emission spectra corresponding to the  ${}^1G_4 \rightarrow {}^3H_5$  ( $\text{Pr}^{3+}$ ),  ${}^1D_2 \rightarrow {}^1G_4$  ( $\text{Pr}^{3+}$ ) and  ${}^4I_{13/2} \rightarrow {}^4I_{15/2}$  ( $\text{Er}^{3+}$ ) transitions of rare earth ions in fluoroindate glasses.

wavelength range from 1200 to 1650 nm is really important for broadband optical amplifiers and these aspects for fluoroindate glasses have been analyzed in details. Broadband near-infrared emission (FWHM = 278 nm) corresponding to the  ${}^1G_4 \rightarrow {}^3H_5$  ( $\text{Pr}^{3+}$ ),  ${}^1D_2 \rightarrow {}^1G_4$  ( $\text{Pr}^{3+}$ ) and  ${}^4I_{13/2} \rightarrow {}^4I_{15/2}$  ( $\text{Er}^{3+}$ ) transitions in fluoroindate glass co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  is successfully observed under direct 483 nm excitation. Based on luminescence decay measurements, the measured lifetimes for the excited levels of rare earth ions and the energy transfer efficiencies were determined. Near-infrared luminescence spectra and their decays for glass samples co-doped with  $\text{Pr}^{3+}/\text{Er}^{3+}$  are compared to the experimental results obtained for fluoroindate glasses singly doped with rare earth ions and theoretical calculations using the Judd–Ofelt framework.

## Methods

**Synthesis.** Fluoroindate glasses singly and doubly doped with rare earth ions ( $\text{Ln}^{3+}$ ) with the following molar composition:  $37.9\text{InF}_3-20\text{ZnF}_2-20\text{SrF}_2-16\text{BaF}_2-4\text{GaF}_3-2\text{LaF}_3-0.1\text{LnF}_3$ , where  $\text{Ln} = \text{Pr}$  or  $\text{Er}$  (referred as 0.1Pr and 0.1Er), and  $(38-x-y)\text{InF}_3-20\text{ZnF}_2-20\text{SrF}_2-16\text{BaF}_2-4\text{GaF}_3-2\text{LaF}_3-x\text{ErF}_3-y\text{PrF}_3$ , where  $x = 0.1$ ;  $y = 0.1, 0.3, 0.5$  (referred as 0.1Er-0.1Pr, 0.1Er-0.3Pr and 0.1Er-0.5Pr), were prepared by melting (covered platinum crucible) and quenching method in glove box in a nitrogen atmosphere ( $\text{O}_2, \text{H}_2\text{O} < 0.5$  ppm). Ammonium bifluoride ( $\text{NH}_4\text{HF}_2$ ) was added as a fluorinating agent to the batch before melting. For the studied glass system, the concentration of  $\text{ErF}_3$  is relatively low (0.1 mol%). Thus, the energy transfer processes between  $\text{Er}^{3+}$  ions are negligibly small. With increasing  $\text{ErF}_3$  concentration the thermal stability reduces and strong luminescence quenching is observed due to nonradiative processes corresponding to the  $\text{Er}^{3+}-\text{Er}^{3+}$  interaction increase. Also, previous investigations for fluoroindate glasses clearly indicate that the higher activator ( $\text{Er}^{3+}$ ) concentrations lead to partial crystallization of fluoroindate glasses<sup>50</sup>. The glass batches were firstly fluorinated at 270 °C for 2 h and then melted at 900 °C for 1 h. Finally, the glass was cast into a stainless steel plate and then annealed at 290 °C for 2 h slowly cooled to room temperature to minimize internal stress during the quenching process. Transparent glassy plates of  $10 \times 10$  mm dimension were obtained. Each glass sample of 1 mm in thickness was polished for optical measurements.

**Measurement and characterization.** Similar to our previous works for fluoroindate glasses<sup>17,18</sup>, the appropriate laser equipment was used for measurements of luminescence spectra and decay curves. The laser system consists of PTI QuantaMaster QM40 spectrofluorimeter, optical parametric oscillator (OPO), Nd:YAG laser (Opotek Opolette 355 LD), double 200 mm monochromators and multimode UVISVIS PMT (R928) and Hamamatsu H10330B-75 detectors, and PTI ASOC-10 [USB-2500] oscilloscope. The Varian Cary 5000 UV-VIS-NIR spectrophotometer was used for the absorption spectra measurements and the Metricon 2010 prism

coupler for the refractive index at a wavelength of 632.8 nm. Resolution for spectral measurements was 0.1 nm, whereas an accuracy for decay curves was  $\pm 0.5 \mu\text{s}$ .

## Data availability

All data regarding the work presented here is available upon reasonable request to the corresponding author.

Received: 24 July 2020; Accepted: 18 November 2020

Published online: 03 December 2020

## References

- de Oliveira, M. A. S., de Araujo, C. B. & Messaddeq, Y. Upconversion ultraviolet random lasing in Nd<sup>3+</sup> doped fluoroindate glass powder. *Opt. Express* **19**, 5620–5626. <https://doi.org/10.1364/OE.19.005620> (2011).
- de Araujo, L. E. E. *et al.* Frequency upconversion of orange light into blue light in Pr<sup>3+</sup>-doped fluoroindate glasses. *Phys. Rev. B* **50**, 16219–16223. <https://doi.org/10.1103/PhysRevB.50.16219> (1994).
- Kishimoto, S. & Hirao, K. Intense ultraviolet and blue upconversion fluorescence in Tm<sup>3+</sup>-doped fluoroindate glasses. *J. Appl. Phys.* **80**, 1965–1969. <https://doi.org/10.1063/1.363087> (1996).
- Rakov, N., Maciel, G. S., de Araujo, C. B. & Messaddeq, Y. Energy transfer assisted frequency upconversion in Ho<sup>3+</sup> doped fluoroindate glass. *J. Appl. Phys.* **91**, 1272–1276. <https://doi.org/10.1063/1.1430889> (2002).
- Lozano, W. *et al.* Upconversion of infrared-to-visible light in Pr<sup>3+</sup>-Yb<sup>3+</sup> codoped fluoroindate glass. *Opt. Commun.* **153**, 271–274. [https://doi.org/10.1016/S0030-4018\(98\)00268-5](https://doi.org/10.1016/S0030-4018(98)00268-5) (1998).
- Oliveira, A. S. *et al.* Twentyfold blue upconversion emission enhancement through thermal effects in Pr<sup>3+</sup>/Yb<sup>3+</sup>-codoped fluoroindate glasses excited at 1.064  $\mu\text{m}$ . *J. Appl. Phys.* **87**, 4274–4278. <https://doi.org/10.1063/1.373065> (2000).
- Borrero-Gonzalez, L. J., Galleani, G., Manzani, D., Nunes, L. A. O. & Ribeiro, S. J. L. Visible to infrared energy conversion in Pr<sup>3+</sup>-Yb<sup>3+</sup> co-doped fluoroindate glasses. *Opt. Mater.* **35**, 2085–2089. <https://doi.org/10.1016/j.optmat.2013.05.024> (2013).
- Martin, I. R., Rodriguez, V. D., Lavin, V. & Rodriguez-Mendoza, U. R. Upconversion dynamics in Yb<sup>3+</sup>-Ho<sup>3+</sup> doped fluoroindate glasses. *J. Alloys Compd.* **275–277**, 345–348. [https://doi.org/10.1016/S0925-8388\(98\)00336-3](https://doi.org/10.1016/S0925-8388(98)00336-3) (1998).
- Martin, I. R., Mendez-Ramos, J., Rodriguez, V. D., Romero, J. J. & Garcia-Sole, J. Increase of the 800 nm excited Tm<sup>3+</sup> blue upconversion emission in fluoroindate glasses by codoping with Yb<sup>3+</sup> ions. *Opt. Mater.* **22**, 327–333. [https://doi.org/10.1016/S0925-3467\(02\)00292-6](https://doi.org/10.1016/S0925-3467(02)00292-6) (2003).
- Catunda, T., Nunez, L. A. O., Florez, A., Messaddeq, Y. & Aegerter, M. A. Spectroscopic properties and upconversion mechanisms in Er<sup>3+</sup>-doped fluoroindate glasses. *Phys. Rev. B* **53**, 6065–6070. <https://doi.org/10.1103/PhysRevB.53.6065> (1996).
- Maciel, G. S., de Araujo, C. B., Messaddeq, Y. & Aegerter, M. A. Frequency upconversion in Er<sup>3+</sup>-doped fluoroindate glasses pumped at 1.48  $\mu\text{m}$ . *Phys. Rev. B* **55**, 6335–6342. <https://doi.org/10.1103/PhysRevB.55.6335> (1997).
- Ribeiro, C. T. B., Zanatta, A. R., Nunes, L. A. O., Messaddeq, Y. & Aegerter, M. A. Optical spectroscopy of Er<sup>3+</sup> and Yb<sup>3+</sup> co-doped fluoroindate glasses. *J. Appl. Phys.* **83**, 2256–2260. <https://doi.org/10.1063/1.366965> (1998).
- de Sousa, D. F. *et al.* Er<sup>3+</sup>:Yb<sup>3+</sup> codoped lead fluoroindogallate glasses for mid infrared and upconversion applications. *J. Appl. Phys.* **85**, 2502–2507. <https://doi.org/10.1063/1.369612> (1999).
- Perez-Rodriguez, C. *et al.* Upconversion emission obtained in Yb<sup>3+</sup>-Er<sup>3+</sup> doped fluoroindate glasses using silica microspheres as focusing lens. *Opt. Express* **21**, 10667–10675. <https://doi.org/10.1364/OE.21.010667> (2013).
- Hernandez-Rodriguez, M. A., Imanieh, M. H., Martin, L. L. & Martin, I. R. Experimental enhancement of the photocurrent in a solar cell using upconversion process in fluoroindate glasses exciting at 1480 nm. *Solar Energy Mater. Solar Cells* **116**, 171–175. <https://doi.org/10.1016/j.solmat.2013.04.023> (2013).
- Bradley, J. D. B. & Pollnau, M. Erbium-doped integrated waveguide amplifiers and lasers. *Laser Photonics Rev.* **5**, 368–403. <https://doi.org/10.1002/lpor.201000015> (2011).
- Kochanowicz, M. *et al.* Near-IR and mid-IR luminescence and energy transfer in fluoroindate glasses co-doped with Er<sup>3+</sup>/Tm<sup>3+</sup>. *Opt. Mater. Express* **9**, 4772–4781. <https://doi.org/10.1364/OME.9.004772> (2019).
- Kochanowicz, M. *et al.* Structure, luminescence and energy transfer of fluoroindate glasses codoped with Er<sup>3+</sup>/Ho<sup>3+</sup>. *Ceram. Int.* **46**, 26403–26409. <https://doi.org/10.1016/j.ceramint.2020.02.210> (2020).
- Wang, R. *et al.* Enhancement mechanisms of Tm<sup>3+</sup>-codoping on 2  $\mu\text{m}$  emission in Ho<sup>3+</sup> doped fluoroindate glasses under 888 nm laser excitation. *Ceram. Int.* **46**, 6973–6977. <https://doi.org/10.1016/j.ceramint.2019.11.108> (2020).
- Wang, R. *et al.* 3.9  $\mu\text{m}$  emission and energy transfer in ultra-low OH<sup>-</sup>, Ho<sup>3+</sup>/Nd<sup>3+</sup> co-doped fluoroindate glasses. *J. Lumin.* **225**, 117363. <https://doi.org/10.1016/j.jlumin.2020.117363> (2020).
- Liu, X., Chen, B. J., Pun, E. Y. B. & Lin, H. Ultra-broadband near-infrared emission in praseodymium doped germanium tellurite glasses for optical fiber amplifier operating at E-, S-, C-, and L-band. *J. Appl. Phys.* **111**, 116101. <https://doi.org/10.1063/1.4722997> (2012).
- Coleman, D. J., Jackson, S. D., Golding, P. & King, T. A. Measurements of the spectroscopic and energy transfer parameters for Er<sup>3+</sup>-doped and Er<sup>3+</sup>, Pr<sup>3+</sup>-codoped PbO–Bi<sub>2</sub>O<sub>3</sub>–Ga<sub>2</sub>O<sub>3</sub> glasses. *J. Opt. Soc. Am. B* **19**, 2927–2937. <https://doi.org/10.1364/JOSAB.19.002927> (2002).
- Park, S. H., Lee, D. C., Heo, J. & Shin, D. W. Energy transfer between Er<sup>3+</sup> and Pr<sup>3+</sup> in chalcogenide glasses for dual-wavelength fiber-optic amplifiers. *J. Appl. Phys.* **91**, 9072–9077. <https://doi.org/10.1063/1.1476965> (2002).
- Li, G. *et al.* Er<sup>3+</sup> doped and Er<sup>3+</sup>/Pr<sup>3+</sup> co-doped gallium antimony-sulphur chalcogenide glasses for infrared applications. *Opt. Mater. Express* **6**, 3849–3856. <https://doi.org/10.1364/OME.6.003849> (2016).
- Zhou, B., Tao, L., Tsang, Y. H., Jin, W. & Pun, E. Y. B. Superbroadband near-infrared emission and energy transfer in Pr<sup>3+</sup>-Er<sup>3+</sup> codoped fluorotellurite glasses. *Opt. Express* **20**, 12205–12211. <https://doi.org/10.1364/OE.20.012205> (2012).
- Xu, Q. *et al.* Er<sup>3+</sup> cross-section spectra of Er<sup>3+</sup>/Pr<sup>3+</sup>:Gd<sub>3</sub>Ga<sub>5</sub>O<sub>12</sub> single-crystal: Pr<sup>3+</sup>-codoping effect. *J. Am. Ceram. Soc.* **102**, 6407–6413. <https://doi.org/10.1111/jace.16554> (2019).
- Judd, B. R. Optical absorption intensities of rare-earth ions. *Phys. Rev.* **127**, 750–761. <https://doi.org/10.1103/PhysRev.127.750> (1962).
- Ofelt, G. S. Intensities of crystal spectra of rare-earth ions. *J. Chem. Phys.* **37**, 511–520. <https://doi.org/10.1063/1.1701366> (1962).
- Carnall, W. T., Fields, P. R. & Rajnak, K. Electronic energy levels in the trivalent lanthanide aquo ions. I. Pr<sup>3+</sup>, Nd<sup>3+</sup>, Pm<sup>3+</sup>, Sm<sup>3+</sup>, Dy<sup>3+</sup>, Ho<sup>3+</sup>, Er<sup>3+</sup>, and Tm<sup>3+</sup>. *J. Chem. Phys.* **49**, 4424–4442. <https://doi.org/10.1063/1.1669893> (1968).
- Zur, L., Janek, J., Sołtys, M., Pisarska, J. & Pisarski, W. A. Effect of BaF<sub>2</sub> content on luminescence of rare-earth ions in borate and germanate glasses. *J. Am. Ceram. Soc.* **99**, 2009–2016. <https://doi.org/10.1111/jace.14223> (2016).
- Zhang, L., Hu, H. & Lin, F. Emission properties of highly doped Er<sup>3+</sup> fluoroaluminate glass. *Mater. Lett.* **47**, 189–193. [https://doi.org/10.1016/S0167-577X\(00\)00233-0](https://doi.org/10.1016/S0167-577X(00)00233-0) (2001).
- Zhou, B., Tao, L., Tsang, Y. H., Jin, W. & Pun, E. Y. B. Superbroadband near-IR photoluminescence from Pr<sup>3+</sup>-doped fluorotellurite glasses. *Opt. Express* **20**, 3803–3813. <https://doi.org/10.1364/OE.20.003803> (2012).
- Pisarska, J. *et al.* Influence of BaF<sub>2</sub> and activator concentration on broadband near-infrared luminescence of Pr<sup>3+</sup> ions in gallo-germanate glasses. *Opt. Express* **24**, 2427–2435. <https://doi.org/10.1364/OE.24.002427> (2016).

34. Zhang, F., Bi, Z., Huang, A. & Xiao, Z. Visible luminescence properties of Er<sup>3+</sup>-Pr<sup>3+</sup> codoped fluorotellurite glasses. *Opt. Mater.* **41**, 112–115. <https://doi.org/10.1016/j.optmat.2014.10.029> (2015).
35. Zhou, M. *et al.* Broadband near-infrared luminescence at around 1.0 μm in Pr<sup>3+</sup>/Er<sup>3+</sup> codoped tellurite glass. *J. Lumin.* **203**, 689–695. <https://doi.org/10.1016/j.jlumin.2018.07.021> (2018).
36. Choi, Y. G., Baik, J. H. & Heo, J. Spectroscopic properties of Pr<sup>3+</sup>: <sup>1</sup>D<sub>2</sub> → <sup>1</sup>G<sub>4</sub> transition in SiO<sub>2</sub>-based glasses. *Chem. Phys. Lett.* **406**, 436–440. <https://doi.org/10.1016/j.cplett.2005.03.028> (2005).
37. Chen, F. *et al.* Investigation of mid-infrared emission characteristics and energy transfer dynamics in Er<sup>3+</sup> doped oxyfluoride tellurite glass. *Sci. Rep.* **5**, 10676. <https://doi.org/10.1038/srep10676> (2015).
38. Tian, Y., Xu, R., Hu, L. & Zhang, J. Enhanced 2.7 μm emission from Er<sup>3+</sup>/Tm<sup>3+</sup>/Pr<sup>3+</sup> triply doped fluoride glass. *J. Am. Ceram. Soc.* **94**, 2289–2291. <https://doi.org/10.1111/j.1551-2916.2011.04645.x> (2011).
39. Li, L., Zhou, Y., Qin, F., Zheng, Y. & Zhang, Z. On the Er<sup>3+</sup> NIR photoluminescence at 800 nm. *Opt. Express* **28**, 3995–4000. <https://doi.org/10.1364/OE.386792> (2020).
40. Pelé, A. L. *et al.* Wavelength conversion in Er<sup>3+</sup> doped chalcogenide fibers for optical gas sensors. *Opt. Express* **23**, 4163–4172. <https://doi.org/10.1364/OE.23.004163> (2015).
41. Golding, P. S., Jackson, S. D., King, T. A. & Pollnau, M. Energy transfer processes in Er<sup>3+</sup>-doped and Er<sup>3+</sup>, Pr<sup>3+</sup>-codoped ZBLAN glasses. *Phys. Rev. B* **62**, 856–864. <https://doi.org/10.1103/PhysRevB.62.856> (2000).
42. Cheng, P. *et al.* Pr<sup>3+</sup>/Er<sup>3+</sup> co-doped tellurite glass with ultra-broadband near-infrared fluorescence emission. *J. Lumin.* **197**, 31–37. <https://doi.org/10.1016/j.jlumin.2018.01.005> (2018).
43. Shen, X. *et al.* Dual super-broadband NIR emissions in Pr<sup>3+</sup>-Er<sup>3+</sup>-Nd<sup>3+</sup> tri-doped tellurite glass. *Ceram. Int.* **46**, 14284–14286. <https://doi.org/10.1016/j.ceramint.2020.02.196> (2020).
44. Li, G. S. *et al.* Broadband near-infrared emission in Pr<sup>3+</sup>-Er<sup>3+</sup> codoped phosphate glasses for optical amplifiers. *Ceram. Int.* **42**, 5558–5561. <https://doi.org/10.1016/j.ceramint.2015.12.026> (2016).
45. Chu, Y. *et al.* Ce<sup>3+</sup>/Yb<sup>3+</sup>/Er<sup>3+</sup> triply doped bismuth borosilicate glass: a potential fiber material for broadband near-infrared fiber amplifiers. *Sci. Rep.* **6**, 33865. <https://doi.org/10.1038/srep33865> (2016).
46. Huang, F. *et al.* Origin of near to middle infrared luminescence and energy transfer process of Er<sup>3+</sup>/Yb<sup>3+</sup> co-doped fluorotellurite glasses under different excitations. *Sci. Rep.* **5**, 8233. <https://doi.org/10.1038/srep08233> (2015).
47. Huang, F., Liu, X., Hu, L. & Chen, D. Spectroscopic properties and energy transfer parameters of Er<sup>3+</sup>-doped fluorozirconate and oxyfluoroaluminate glasses. *Sci. Rep.* **4**, 5053. <https://doi.org/10.1038/srep05053> (2014).
48. Choi, Y. G., Kim, K. H., Park, B. J. & Heo, J. 1.6 μm emission from Pr<sup>3+</sup>:(3F<sub>3</sub>, 3F<sub>4</sub>) → 3H<sub>4</sub> transition in Pr<sup>3+</sup>- and Pr<sup>3+</sup>/Er<sup>3+</sup>-doped selenide glasses. *Appl. Phys. Lett.* **78**, 1249–1251. <https://doi.org/10.1063/1.1350958> (2001).
49. Park, S. H., Lee, D. C., Heo, J. & Kim, H. S. Pr<sup>3+</sup>/Er<sup>3+</sup> codoped Ge-As-Ga-S glasses as dual-wavelength fiber-optic amplifiers for 1.31 and 1.55 μm windows. *J. Am. Ceram. Soc.* **83**, 1284–1286. <https://doi.org/10.1111/j.1151-2916.2000.tb01370.x> (2000).
50. Pisarski, W. A., Pisarska, J. & Ryba-Romanowski, W. Effect of erbium concentration on physical properties of fluorindate glass. *Chem. Phys. Lett.* **380**, 604–608. <https://doi.org/10.1016/j.cplett.2003.08.055> (2003).
51. Gauthier, J.-C. *et al.* Mid-IR supercontinuum from 2.4 to 5.4 μm in a low-loss fluorindate fiber. *Opt. Lett.* **41**, 1756–1759. <https://doi.org/10.1364/OL.41.001756> (2016).
52. Jia, S. *et al.* 2875 nm lasing from Ho<sup>3+</sup>-doped fluorindate glass fibers. *IEEE Photon. Technol. Lett.* **30**, 223–226. <https://doi.org/10.1109/LPT.2017.2787119> (2018).
53. Majewski, M. R. *et al.* Emission beyond 4 μm and mid-infrared lasing in a dysprosium-doped indium fluoride (InF<sub>3</sub>) fiber. *Opt. Lett.* **43**, 1926–1929. <https://doi.org/10.1364/OL.43.001926> (2018).
54. Maes, F. *et al.* Room-temperature fiber laser at 392 μm. *Optica* **5**, 761–764. <https://doi.org/10.1364/OPTICA.5.000761> (2018).

## Acknowledgements

The research project was funded by the National Science Centre (Poland) granted on the basis of the decision No. 2017/25/B/ST8/02530.

## Author contributions

W.A.P. and D.D. originated the research concept and interpreted results. M.K., M.K., J.Ż., P.M., A.B., M.L. carried out most of the experiments and data analysis. J.P., J.D., D.D. discussed the results and commented on the manuscript. W.A.P. wrote the manuscript.

## Competing interests

The authors declare no competing interests.

## Additional information

**Correspondence** and requests for materials should be addressed to W.A.P.

**Reprints and permissions information** is available at [www.nature.com/reprints](http://www.nature.com/reprints).

**Publisher's note** Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



**Open Access** This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2020