



Received 22 November 2015

Accepted 14 December 2015

Edited by G. Smith, Queensland University of  
Technology, Australia**Keywords:** coordination polymers; crystal  
structure; lanthanide; luminescence; terbium(III)**CCDC reference:** 1436132**Supporting information:** this article has  
supporting information at journals.iucr.org/e


# Crystal structure of a mixed-ligand terbium(III) coordination polymer containing oxalate and formate ligands, having a three-dimensional fcu topology

Chainok Kittipong,<sup>a\*</sup> Phailyn Khemthong,<sup>b</sup> Filip Kielar<sup>b</sup> and Yan Zhou<sup>c</sup><sup>a</sup>Department of Physics, Faculty of Science and Technology, Thammasat University, Khlong Luang, Pathum Thani, 12120, Thailand, <sup>b</sup>Department of Chemistry, Faculty of Science, Naresuan University, Muang, Phitsanulok, 65000, Thailand, and <sup>c</sup>Department of Chemistry, The Hong Kong University of Science and Technology, Clear Water Bay, Kowloon, Hong Kong. \*Correspondence e-mail: kc@tu.ac.th



The title compound, poly[( $\mu_3$ -formato)( $\mu_4$ -oxalato)terbium(III)], [Tb(CHO<sub>2</sub>)(C<sub>2</sub>O<sub>4</sub>)]<sub>n</sub>, is a three-dimensional coordination polymer, and is isotypic with the La<sup>III</sup>, Ce<sup>III</sup> and Sm<sup>III</sup> analogues. The asymmetric unit contains one Tb<sup>III</sup> ion, one formate anion (CHO<sub>2</sub><sup>-</sup>) and half of an oxalate anion (C<sub>2</sub>O<sub>4</sub><sup>2-</sup>), the latter being completed by application of inversion symmetry. The Tb<sup>III</sup> ion is nine-coordinated in a distorted tricapped trigonal-prismatic manner by two chelating carboxylate groups from two C<sub>2</sub>O<sub>4</sub><sup>2-</sup> ligands, two carboxylate oxygen atoms from another two C<sub>2</sub>O<sub>4</sub><sup>2-</sup> ligands and three oxygen atoms from three CHO<sub>2</sub><sup>-</sup> ligands, with the Tb–O bond lengths and the O–Tb–O bond angles ranging from 2.4165 (19) to 2.478 (3) Å and 64.53 (6) to 144.49 (4)°, respectively. The CHO<sub>2</sub><sup>-</sup> and C<sub>2</sub>O<sub>4</sub><sup>2-</sup> anions adopt  $\mu_3$ -bridging and  $\mu_4$ -chelating-bridging coordination modes, respectively, linking adjacent Tb<sup>III</sup> ions into a three-dimensional 12-connected fcu topology with point symbol (3<sup>24</sup>.4<sup>36</sup>.5<sup>6</sup>). The title compound exhibits thermal stability up to 623 K, and also displays strong green photoluminescence in the solid state at room temperature.

## 1. Chemical context

Owing to their high colour purity, high luminescence quantum yields, narrow bandwidths, relatively long lifetimes and large Stokes shifts arising from 4*f* orbitals, coordination polymers of lanthanide(III) ions and organic linker ligands have received much attention from chemists during the past decade for the development of fluorescent probes and electroluminescent devices (Hasegawa & Nakanishi, 2015). In particular, polymeric Eu<sup>III</sup> and Tb<sup>III</sup> compounds with a range of organic linker ligands are the most intense emitters among the lanthanide(III) series, and they have been developed extensively as ion sensing and optical materials (Cui *et al.*, 2014). Lanthanide(III) ions are known to have a high affinity and preference for hard donor atoms. Thus, dicarboxylic acid ligands containing aliphatic, aromatic and *N*-heterocyclic moieties have been widely employed in the construction of luminescent lanthanide coordination polymers (So *et al.*, 2015). Among the ligands in this class, for instance, terephthalic acid is known to provide an efficient energy transfer to support strong lanthanide(III)-centered luminescent emission *via* the ‘antenna effect’ (Samuel *et al.*, 2009). On the other hand, small rigid planar species with versatile coordination oxygen donor sites such as oxalate, carbonate, nitrate, and formate anions are also a very important class of ligands for the preparation of

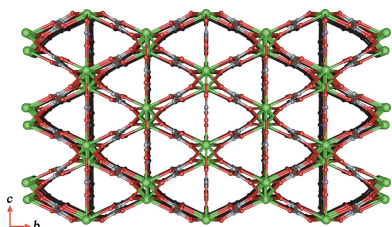

lanthanide coordination polymers (Hong *et al.*, 2014; Gupta *et al.*, 2015). These small versatile ligands can bind to metals in different modes, resulting in the formation of multi-dimensional coordination networks with short intermetallic distances, which can aid the energy-transfer process between chromophoric antenna ligands and lanthanide(III) ions (Wang *et al.*, 2012). In addition, the oxalate anion has proved to be an efficient sensitizer for lanthanide(III)-based emission (Cheng *et al.*, 2007). Recently, many multi-dimensional luminescent lanthanide coordination polymers containing antenna and small rigid planar mixed ligands have been reported (Xu *et al.*, 2013; Wang *et al.*, 2013). However, only a few compounds with mixed small rigid planar ligands alone have been described in the literature (Zhang *et al.*, 2007; Huang *et al.*, 2013; Tang *et al.*, 2014).

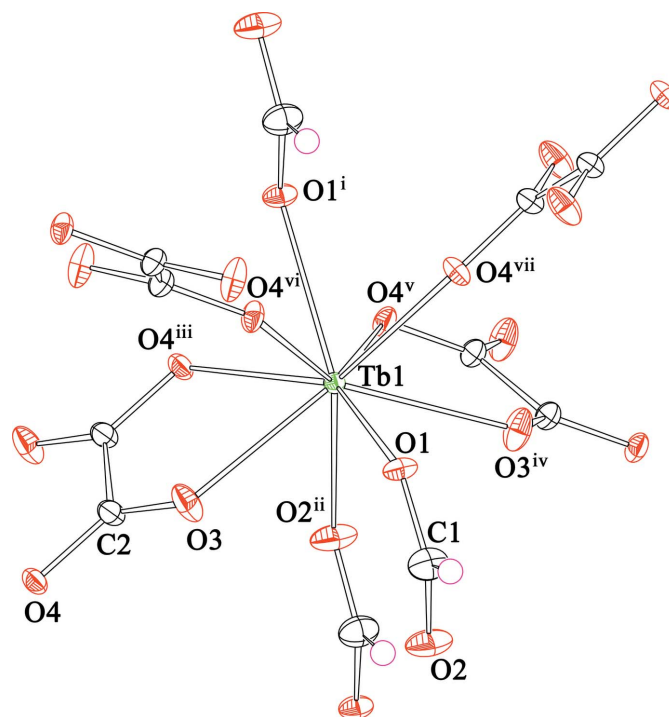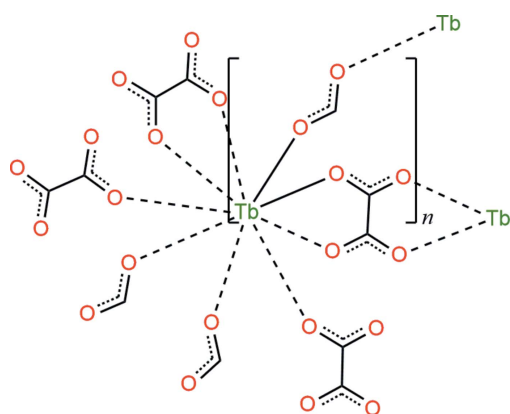

**Figure 1**  
Coordination environment of the Tb<sup>III</sup> ion in (I). Displacement ellipsoids are drawn at the 50% probability level and H atoms are shown as small spheres of arbitrary radii. For symmetry codes, see Table 1.

oxalate ligands and three oxygen atoms from three formate ligands, with the O—Tb—O bond angles ranging from 64.53 (6) to 144.49 (4)°. The Tb—O bond lengths in (I) are in the range of 2.4165 (19) to 2.478 (3) Å (Table 1), which is in good agreement with the reported distances for other Tb<sup>III</sup>

Herein, we report the synthesis and structure of a terbium(III) coordination polymer containing formate and oxalate mixed ligands, [Tb(CHO<sub>2</sub>)(C<sub>2</sub>O<sub>4</sub>)]<sub>n</sub>, (I), having a three-dimensional 12-connected fcu topology with point symbol (3<sup>2</sup>.4<sup>3</sup>.6<sup>5</sup>.6). The thermal stability and luminescent properties of compound (I) have also been investigated.

## 2. Structural commentary


Single crystal X-ray diffraction analysis revealed that (I) is isotopic in the orthorhombic *Pnma* space group with the La<sup>III</sup>, Ce<sup>III</sup> and Sm<sup>III</sup> analogues (Romero *et al.*, 1996). The asymmetric unit contains one Tb<sup>III</sup> ion, one formate anion, and half of an oxalate anion. As shown in Fig. 1, each Tb<sup>III</sup> ion is nine-coordinated in a distorted tricapped trigonal prismatic manner (Fig. 1) by two chelating carboxylate groups from two oxalate ligands, two carboxylate oxygen atoms from another two

**Table 1**  
Selected bond lengths (Å).

Tb1—O1	2.417 (3)	Tb1—O4 <sup>iv</sup>	2.4370 (18)
Tb1—O1 <sup>i</sup>	2.478 (3)	Tb1—O4 <sup>v</sup>	2.4651 (17)
Tb1—O2 <sup>ii</sup>	2.437 (3)	Tb1—O4 <sup>vi</sup>	2.4370 (17)
Tb1—O3 <sup>iii</sup>	2.4165 (19)	Tb1—O4 <sup>vii</sup>	2.4651 (17)
Tb1—O3	2.4165 (19)		

Symmetry codes: (i)  $x - \frac{1}{2}, y, -z + \frac{3}{2}$ ; (ii)  $x - \frac{1}{2}, y, -z + \frac{1}{2}$ ; (iii)  $x, -y + \frac{3}{2}, z$ ; (iv)  $-x, -y + 1, -z + 1$ ; (v)  $-x + \frac{1}{2}, -y + 1, z + \frac{1}{2}$ ; (vi)  $-x, y + \frac{1}{2}, -z + 1$ ; (vii)  $-x + \frac{1}{2}, y + \frac{1}{2}, z + \frac{1}{2}$ .


**Figure 2**  
A view of the two-dimensional terbium-formate network in (I), showing the monolayer structure projected in the *ac* plane. The dashed lines indicate the intralayer C—H...O hydrogen bonds (Table 2).

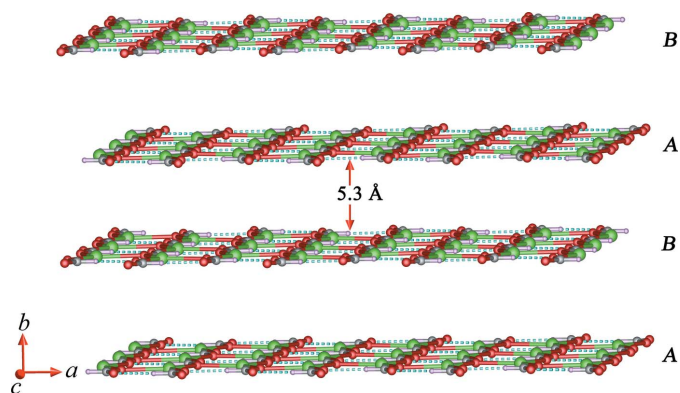


**Figure 3**  
The terbium-formate layered structure viewed along the *c* axis.

complexes containing oxygen donor ligands (Cheng *et al.*, 2007; Zhu *et al.*, 2007). All of the bond lengths and bond angles in the formate and oxalate anions are also within normal ranges (Rossin *et al.*, 2012; Hong *et al.*, 2014; Gupta *et al.*, 2015). The coordination modes of the formate and oxalate ligands in (I) (Fig. 2) are commonly observed in lanthanide coordination polymers (Zhang *et al.*, 2007; Rossin *et al.*, 2012).

As shown in Fig. 2, each formate anion adopts a  $\mu_3$ -bridging coordination mode connecting three  $\text{Tb}^{\text{III}}$  ions, forming a two-dimensional (2-D) layer in the *ac* plane. In the 2-D terbium-formate monolayer, the  $\text{Tb1}\cdots\text{Tb1}$  separations along the formate ligands in *syn-anti* and *anti-anti* O1,O2-bridging coordination modes (Rossin *et al.*, 2012) are 6.1567 (3) and 6.6021 (2) Å, respectively. The adjacent 2-D monolayers are stacked in an *-ABA-* sequence running perpendicular to the *b* axis with an interlayer spacing of *ca* 5.3 Å (Fig. 3). The oxalate ligand adopts a  $\mu_4$ -chelating-bridging coordination mode, linking four  $\text{Tb}^{\text{III}}$  ions along the *a* axis to form a three-dimensional (3-D) terbium-oxalate open framework (Fig. 3). The  $\text{Tb1}\cdots\text{Tb1}$  distance *via* the formate O1- and oxalate O4-bridging ligands is 3.8309 (2) Å with the  $\text{Tb1}-\text{O1}-\text{Tb1}$  and  $\text{Tb1}-\text{O4}-\text{Tb1}$  bond angles being 103.00 (9) and 102.79 (6)°, respectively. On the other hand, the channels in the 3-D open framework have an approximate rhombic shape with a

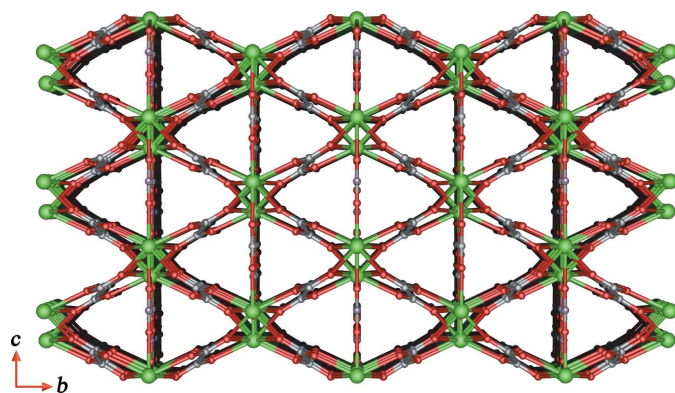

**Figure 4**  
A perspective view along the *a* axis of the three-dimensional framework.

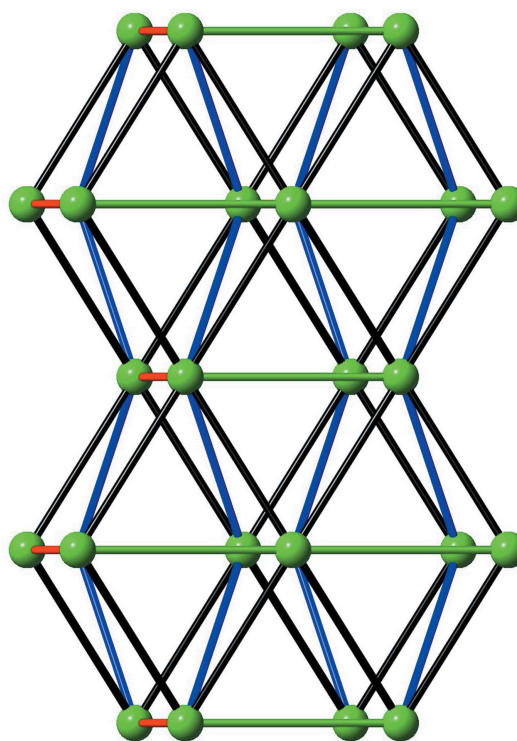

**Figure 5**  
Schematic representation of the 12-connected fcu topology in (I).

$\text{Tb1}\cdots\text{Tb1}$  separation of 6.2670 (2) Å, and are cross-linked parallel to the *c* axis by bridging formate ligands as shown in Fig. 4. The presence of guest molecules in the lattice as well as the formation of interpenetrated networks of (I) are thus prevented. Furthermore, the topology of the network in (I) was analysed using *TOPOS* (Blatov *et al.*, 2000). As schematically depicted in Fig. 5, the overall framework can be defined as a 12-connected fcu topology with point symbol  $(3^{24}.4^{36}.5^6)$  by linking each adjacent layer of  $\text{Tb}^{\text{III}}$  atoms *via* formate and oxalate ligands.

The infrared spectrum of (I) was collected from a polycrystalline sample pelletized with KBr, in the range 4000–400  $\text{cm}^{-1}$ . This spectrum indicates the presence of the carboxylate groups of the ligands by appearance of the strong absorption bands at 1630 and 1315  $\text{cm}^{-1}$  for the asymmetric ( $\nu_{\text{asym}}\text{COO}^-$ ) and the symmetric ( $\nu_{\text{sym}}\text{COO}^-$ ) carboxylate vibrations, respectively (Deacon & Phillips, 1980). To examine the thermal stability of (I), thermogravimetric analysis was performed on a polycrystalline sample under a nitrogen atmosphere in the temperature range of 303–1273 K. There is no weight loss before 623 K due to the stability of the fcu-type 3-D frameworks. The decomposition of the framework, however, occurred rapidly at temperatures above 628 K.

The photoluminescence properties of (I) were investigated in the solid state at room temperature. The emission spectrum is shown in Fig. 6. The emission spectrum upon excitation at 305 nm exhibits the characteristic *f-f* transitions of  $\text{Tb}^{\text{III}}$  ions (Bünzli, 2010). The emission peaks at 487, 543, 585, and 617 nm can be assigned to the  $^5D_4 \rightarrow ^7F_J$  ( $J = 6, 5, 4, 3$ ) transitions, respectively. The most intense transition is

**Table 2**  
Hydrogen-bond geometry (Å, °).

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
$C1-H1\cdots O2^{viii}$	0.93	2.15	3.051 (5)	164

Symmetry code: (viii)  $x + \frac{1}{2}, -y + \frac{3}{2}, -z + \frac{1}{2}$ .

$^5D_4 \rightarrow ^7F_5$ , which implies the emitted light is green. The emission lifetime of (I) is 1.79 ms.

### 3. Supramolecular features


The two-dimensional terbium-formate monolayers are stabilized by weak intra-layer  $C1-H1\cdots O2^{viii}$  hydrogen bonds giving  $S(7)$  graph-set motifs (Bernstein *et al.*, 1995), in which each formate anion acts as a donor and acceptor for one hydrogen bond (Table 2, Fig. 2).

### 4. Database survey

A search of the Cambridge Structural Database (Groom & Allen, 2014) for lanthanide coordination polymers containing mixed oxalate and formate ligands gave four hits (RIFQIG, RIFRED, RIFRIH; Romero *et al.*, 1996; RIFQIG01; Tan *et al.*, 2009), which are isotopic with the title compound (I) as previously mentioned. The structures involving oxalate and acetate analogues have also been reported (AZOCIC; Di *et al.*, 2011; Gutkowski *et al.*, 2011; SOPPIX; Zhang *et al.*, 2009; VORBUA; Koner & Goldberg, 2009).

### 5. Synthesis and crystallization

All reagents were of analytical grade and were used as obtained from commercial sources without further purification. Synthesis of (I):  $TbCl_3 \cdot 6H_2O$  (0.187 g, 0.5 mmol), oxalic

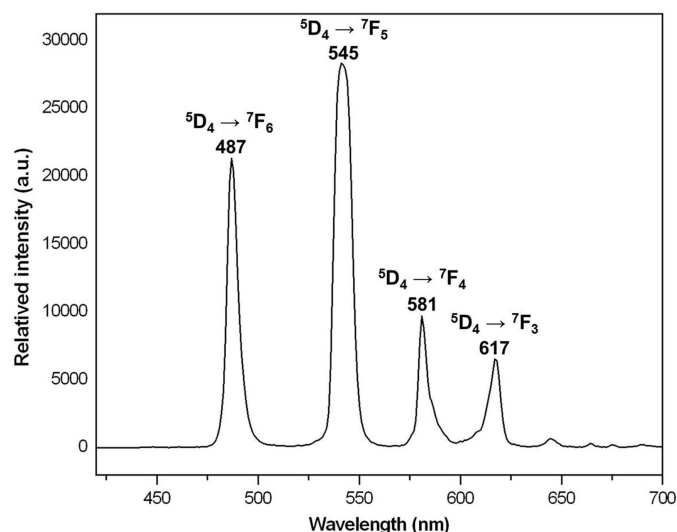

**Figure 6**  
The solid-state emission spectrum of (I) at room temperature.

**Table 3**  
Experimental details.

Crystal data	
Chemical formula	$[Tb(CHO_2)(C_2O_4)]$
$M_r$	291.96
Crystal system, space group	Orthorhombic, $Pnma$
Temperature (K)	296
$a, b, c$ (Å)	7.0138 (3), 10.6077 (4), 6.6021 (2)
$V$ (Å <sup>3</sup> )	491.20 (3)
$Z$	4
Radiation type	Mo $K\alpha$
$\mu$ (mm <sup>-1</sup> )	14.36
Crystal size (mm)	$0.2 \times 0.12 \times 0.08$
Data collection	
Diffractometer	Bruker D8 QUEST CMOS
Absorption correction	Multi-scan (SADABS; Bruker, 2014)
$T_{min}, T_{max}$	0.655, 0.746
No. of measured, independent and observed [ $I > 2\sigma(I)$ ] reflections	6517, 638, 594
$R_{int}$	0.028
$(\sin \theta/\lambda)_{max}$ (Å <sup>-1</sup> )	0.666
Refinement	
$R[F^2 > 2\sigma(F^2)], wR(F^2), S$	0.012, 0.025, 1.10
No. of reflections	638
No. of parameters	52
H-atom treatment	H-atom parameters constrained
$\Delta\rho_{max}, \Delta\rho_{min}$ (e Å <sup>-3</sup> )	0.75, -0.63

Computer programs: APEX2 and SAINT (Bruker, 2014), SHELXS2014 (Sheldrick, 2008), SHELXL2014 (Sheldrick, 2015), OLEX2 (Dolomanov *et al.*, 2009), pubCIF (Westrip, 2010) and enCIFer (Allen *et al.*, 2004).

acid (0.045 g, 0.5 mmol),  $Na_2CO_3$  (0.011 g, 0.1 mmol), and a mixture (1:1 v/v) of *N,N'*-dimethylformamide (DMF) and water (6 ml) was sealed in a 23 ml Teflon-lined stainless steel vessel and heated under autogenous pressure at 463 K for two days. After the reactor was cooled to room temperature, colorless block-shaped crystals were filtered off and dried in air. Yield: 0.118 g (63% based on the  $Tb^{III}$  source). Analysis (%) calculated for  $C_3HO_6Tb$  (291.96): C, 12.34; H, 0.35%. Found: C, 12.40; H, 0.33%. IR (KBr,  $cm^{-1}$ ): 2823 (w), 2491 (w), 1630 (s), 1440 (w), 1315 (s), 1022 (m), 914 (w), 795 (s), 611 (w), 492 (s), 408 (w).

### 6. Refinement

Crystal data, data collection and structure refinement details are summarized in Table 3. The formate H atom was found in a difference electron-density map and was refined using a riding-model approximation, with  $C-H = 0.93$  Å and with  $U_{iso}(H) = 1.2U_{eq}(C)$ .

### Acknowledgements

This research was supported financially by the National Research Council of Thailand through the Thammasat University Research Scholar (No. 216919). We thank Central Scientific Instrument Center (CSIC), Faculty of Science and Technology, Thammasat University, for providing access to the equipment.



## References

- Allen, F. H., Johnson, O., Shields, G. P., Smith, B. R. & Towler, M. (2004). *J. Appl. Cryst.* **37**, 335–338.
- Bernstein, J., Davis, R. E., Shimon, L. & Chang, N.-L. (1995). *Angew. Chem. Int. Ed. Engl.* **34**, 1555–1573.
- Blatov, V. A., Shevchenko, A. P. & Serezhkin, V. N. (2000). *J. Appl. Cryst.* **33**, 1193.
- Bruker (2014). *APEX2, SADABS and SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Bünzli, J. G. (2010). *Chem. Rev.* **110**, 2729–2755.
- Cheng, J. W., Zheng, S. T. & Yang, G. Y. (2007). *Dalton Trans.* pp. 4059–4066.
- Cui, Y., Chen, B. & Qian, G. (2014). *Coord. Chem. Rev.* **273–274**, 76–86.
- Deacon, G. B. & Phillips, R. J. (1980). *Coord. Chem. Rev.* **33**, 227–250.
- Di, W.-J., Lan, S.-M., Zhang, Q. & Liang, Y.-X. (2011). *Acta Cryst. E67*, m1436–m1437.
- Dolomanov, O. V., Bourhis, L. J., Gildea, R. J., Howard, J. A. K. & Puschmann, H. (2009). *J. Appl. Cryst.* **42**, 339–341.
- Groom, C. R. & Allen, F. H. (2014). *Angew. Chem. Int. Ed.* **53**, 662–671.
- Gupta, S. K., Rajeshwari, B., Achary, S. N., Patwe, S. J., Tyagi, A. K., Natarajan, V. & Kadam, R. M. (2015). *Eur. J. Inorg. Chem.* pp. 4429–4436.
- Gutkowsky, K., Freire, E. & Baggio, R. (2011). *Acta Cryst. C67*, m77–m80.
- Hasegawa, Y. & Nakanishi, T. (2015). *RSC Adv.* **5**, 338–353.
- Hong, F., Zhou, L., Li, L., Xia, Q. & Ye, M. (2014). *Mater. Res. Bull.* **60**, 252–257.
- Huang, D.-Q., Zhang, H., Sheng, L.-Q., Liu, Z.-D., Xu, H.-J. & Fan, S.-H. (2013). *Chin. J. Inorg. Chem.* **29**, 1–6.
- Koner, R. & Goldberg, I. (2009). *Acta Cryst. C65*, m160–m164.
- Romero, S., Mosset, A. & Trombe, J. C. (1996). *J. Solid State Chem.* **127**, 256–266.
- Rossin, A., Giambastiani, G., Peruzzini, M. & Sessoli, R. (2012). *Inorg. Chem.* **51**, 6962–6968.
- Samuel, A. P. S., Xu, J. & Raymond, K. N. (2009). *Inorg. Chem.* **48**, 687–698.
- Sheldrick, G. M. (2008). *Acta Cryst. A64*, 112–122.
- Sheldrick, G. M. (2015). *Acta Cryst. C71*, 3–8.
- So, M. C., Wiederrecht, G. P., Mondloch, J. E., Hupp, J. T. & Farha, O. K. (2015). *Chem. Commun.* **51**, 3501–3510.
- Tan, J. C., Furman, J. D. & Cheetham, A. K. (2009). *J. Am. Chem. Soc.* **131**, 14252–14254.
- Tang, Q., Liu, Y., Liu, S., He, D., Miao, J., Wang, X., Yang, G., Shi, Z. & Zheng, Z. (2014). *J. Am. Chem. Soc.* **136**, 12444–12449.
- Wang, P., Fan, R.-Q., Liu, X.-R., Wang, L.-Y., Yang, Y.-L., Cao, W.-W., Yang, B., Hasi, W., Su, Q. & Mu, Y. (2013). *CrystEngComm*, **15**, 1931–1949.
- Wang, H., Liu, S.-J., Tian, D., Jia, J.-M. & Hu, T.-L. (2012). *Cryst. Growth Des.* **12**, 3263–3270.
- Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.
- Xu, X., Zhou, Y., Huang, D., Xiong, W., Su, M., Wang, K., Han, S. & Hong, M. (2013). *Cryst. Growth Des.* **13**, 5420–5432.
- Zhang, L.-Z., Gu, W., Li, B., Liu, X. & Liao, D.-Z. (2007). *Inorg. Chem.* **46**, 622–624.
- Zhang, X., Xing, Y., Wang, C., Han, J., Li, J., Ge, M., Zeng, X. & Niu, S. (2009). *Inorg. Chim. Acta*, **362**, 1058–1064.
- Zhu, W. H., Wang, Z. M. & Gao, S. (2007). *Inorg. Chem.* **46**, 1337–1342.

## supporting information

*Acta Cryst.* (2016). E72, 87-91 [doi:10.1107/S205698901502397X]

## Crystal structure of a mixed-ligand terbium(III) coordination polymer containing oxalate and formate ligands, having a three-dimensional fcu topology

Chainok Kittipong, Phailyn Khemthong, Filip Kielar and Yan Zhou

### Computing details

Data collection: *APEX2* (Bruker, 2014); cell refinement: *SAINTE* (Bruker, 2014); data reduction: *SAINTE* (Bruker, 2014); program(s) used to solve structure: *SHELXS2014* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL2014* (Sheldrick, 2015); molecular graphics: *OLEX2* (Dolomanov *et al.*, 2009); software used to prepare material for publication: *publCIF* (Westrip, 2010) and *enCIFer* (Allen *et al.*, 2004).

Poly[( $\mu_3$ -formato)( $\mu_4$ -oxalato)terbium(III)]

#### Crystal data

[Tb(CHO<sub>2</sub>)(C<sub>2</sub>O<sub>4</sub>)<sub>2</sub>]

$M_r = 291.96$

Orthorhombic, *Pnma*

$a = 7.0138$  (3) Å

$b = 10.6077$  (4) Å

$c = 6.6021$  (2) Å

$V = 491.20$  (3) Å<sup>3</sup>

$Z = 4$

$F(000) = 528$

$D_x = 3.948$  Mg m<sup>-3</sup>

Mo  $K\alpha$  radiation,  $\lambda = 0.71073$  Å

Cell parameters from 3952 reflections

$\theta = 3.6$ – $28.3^\circ$

$\mu = 14.36$  mm<sup>-1</sup>

$T = 296$  K

Block, colourless

$0.2 \times 0.12 \times 0.08$  mm

#### Data collection

Bruker D8 QUEST CMOS  
diffractometer

Radiation source: microfocus sealed x-ray tube,  
Incoatec  $\lambda\mu$ s

Graphite Double Bounce Multilayer Mirror  
monochromator

Detector resolution: 10.5 pixels mm<sup>-1</sup>

$\omega$  and  $\varphi$  scans

Absorption correction: multi-scan  
(*SADABS*; Bruker, 2014)

$T_{\min} = 0.655$ ,  $T_{\max} = 0.746$

6517 measured reflections

638 independent reflections

594 reflections with  $I > 2\sigma(I)$

$R_{\text{int}} = 0.028$

$\theta_{\max} = 28.3^\circ$ ,  $\theta_{\min} = 3.6^\circ$

$h = -9 \rightarrow 9$

$k = -13 \rightarrow 14$

$l = -8 \rightarrow 8$

#### Refinement

Refinement on  $F^2$

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.012$

$wR(F^2) = 0.025$

$S = 1.10$

638 reflections

52 parameters

0 restraints

Primary atom site location: structure-invariant  
direct methods

Secondary atom site location: difference Fourier  
map

Hydrogen site location: inferred from  
neighbouring sites

H-atom parameters constrained  
 $w = 1/[\sigma^2(F_o^2) + (0.0092P)^2 + 0.8666P]$   
 where  $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} = 0.001$   
 $\Delta\rho_{\max} = 0.75 \text{ e } \text{\AA}^{-3}$   
 $\Delta\rho_{\min} = -0.63 \text{ e } \text{\AA}^{-3}$

*Special details*

**Experimental.** *SADABS2014* (Bruker, 2014) was used for absorption correction.  $wR2(\text{int})$  was 0.0566 before and 0.0416 after correction. The ratio of minimum to maximum transmission is 0.8789. The  $\lambda/2$  correction factor is 0.00150.

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > \sigma(F^2)$  is used only for calculating  $R$ -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

*Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )*

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Tb1	0.20226 (2)	0.7500	0.63323 (2)	0.00749 (6)
O1	0.5347 (4)	0.7500	0.5364 (4)	0.0132 (5)
O2	0.5527 (4)	0.7500	0.2000 (4)	0.0237 (7)
O3	0.2384 (3)	0.54490 (18)	0.4786 (3)	0.0186 (4)
O4	0.0873 (3)	0.37671 (16)	0.3522 (3)	0.0120 (4)
C1	0.6227 (6)	0.7500	0.3693 (6)	0.0197 (8)
H1	0.7551	0.7500	0.3761	0.024*
C2	0.0956 (4)	0.4788 (2)	0.4518 (4)	0.0124 (5)

*Atomic displacement parameters ( $\text{\AA}^2$ )*

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
Tb1	0.00799 (8)	0.00750 (8)	0.00698 (9)	0.000	-0.00049 (7)	0.000
O1	0.0110 (13)	0.0209 (14)	0.0076 (13)	0.000	0.0013 (10)	0.000
O2	0.0235 (16)	0.0381 (18)	0.0096 (14)	0.000	-0.0010 (12)	0.000
O3	0.0133 (9)	0.0143 (9)	0.0282 (11)	-0.0028 (7)	0.0010 (8)	-0.0093 (9)
O4	0.0136 (8)	0.0093 (8)	0.0131 (9)	-0.0011 (7)	0.0027 (7)	-0.0041 (7)
C1	0.0141 (17)	0.029 (2)	0.016 (2)	0.000	-0.0009 (16)	0.000
C2	0.0151 (12)	0.0112 (11)	0.0109 (12)	0.0003 (10)	-0.0002 (10)	-0.0020 (10)

*Geometric parameters ( $\text{\AA}$ ,  $^\circ$ )*

Tb1—O1	2.417 (3)	Tb1—O4 <sup>vii</sup>	2.4651 (17)
Tb1—O1 <sup>i</sup>	2.478 (3)	O1—C1	1.265 (5)
Tb1—O2 <sup>ii</sup>	2.437 (3)	O2—C1	1.221 (5)
Tb1—O3 <sup>iii</sup>	2.4165 (19)	O3—C2	1.235 (3)
Tb1—O3	2.4165 (19)	O4—C2	1.268 (3)
Tb1—O4 <sup>iv</sup>	2.4370 (18)	C1—H1	0.9300
Tb1—O4 <sup>v</sup>	2.4651 (17)	C2—C2 <sup>iv</sup>	1.551 (5)
Tb1—O4 <sup>vi</sup>	2.4370 (17)		

Tb1 <sup>viii</sup> —Tb1—Tb1 <sup>i</sup>	132.533 (9)	O4 <sup>vi</sup> —Tb1—Tb1 <sup>viii</sup>	138.32 (4)
O1—Tb1—Tb1 <sup>viii</sup>	39.06 (6)	O4 <sup>v</sup> —Tb1—Tb1 <sup>viii</sup>	38.34 (4)
O1 <sup>i</sup> —Tb1—Tb1 <sup>i</sup>	37.94 (6)	O4 <sup>vi</sup> —Tb1—Tb1 <sup>i</sup>	38.87 (4)
O1—Tb1—Tb1 <sup>i</sup>	171.60 (6)	O4 <sup>vii</sup> —Tb1—Tb1 <sup>i</sup>	108.19 (4)
O1 <sup>i</sup> —Tb1—Tb1 <sup>viii</sup>	94.59 (6)	O4 <sup>iv</sup> —Tb1—Tb1 <sup>i</sup>	38.87 (4)
O1—Tb1—O1 <sup>i</sup>	133.65 (7)	O4 <sup>iv</sup> —Tb1—Tb1 <sup>viii</sup>	138.33 (4)
O1—Tb1—O2 <sup>ii</sup>	100.16 (9)	O4 <sup>v</sup> —Tb1—Tb1 <sup>i</sup>	108.19 (4)
O1—Tb1—O4 <sup>vii</sup>	65.01 (6)	O4 <sup>vii</sup> —Tb1—Tb1 <sup>viii</sup>	38.34 (4)
O1—Tb1—O4 <sup>vi</sup>	144.49 (4)	O4 <sup>iv</sup> —Tb1—O1 <sup>i</sup>	64.53 (6)
O1—Tb1—O4 <sup>v</sup>	65.01 (6)	O4 <sup>vii</sup> —Tb1—O1 <sup>i</sup>	76.57 (6)
O1—Tb1—O4 <sup>iv</sup>	144.49 (4)	O4 <sup>vi</sup> —Tb1—O1 <sup>i</sup>	64.53 (6)
O2 <sup>ii</sup> —Tb1—Tb1 <sup>viii</sup>	139.22 (7)	O4 <sup>v</sup> —Tb1—O1 <sup>i</sup>	76.57 (6)
O2 <sup>ii</sup> —Tb1—Tb1 <sup>i</sup>	88.25 (7)	O4 <sup>vi</sup> —Tb1—O2 <sup>ii</sup>	71.16 (7)
O2 <sup>ii</sup> —Tb1—O1 <sup>i</sup>	126.19 (9)	O4 <sup>iv</sup> —Tb1—O2 <sup>ii</sup>	71.16 (7)
O2 <sup>ii</sup> —Tb1—O4 <sup>v</sup>	141.92 (5)	O4 <sup>v</sup> —Tb1—O4 <sup>vii</sup>	66.08 (8)
O2 <sup>ii</sup> —Tb1—O4 <sup>vii</sup>	141.92 (5)	O4 <sup>vi</sup> —Tb1—O4 <sup>v</sup>	140.95 (3)
O3—Tb1—Tb1 <sup>viii</sup>	94.25 (5)	O4 <sup>iv</sup> —Tb1—O4 <sup>vi</sup>	66.94 (8)
O3 <sup>iii</sup> —Tb1—Tb1 <sup>i</sup>	105.42 (5)	O4 <sup>iv</sup> —Tb1—O4 <sup>v</sup>	100.09 (6)
O3 <sup>iii</sup> —Tb1—Tb1 <sup>viii</sup>	94.25 (5)	O4 <sup>vi</sup> —Tb1—O4 <sup>vii</sup>	100.09 (6)
O3—Tb1—Tb1 <sup>i</sup>	105.42 (5)	O4 <sup>iv</sup> —Tb1—O4 <sup>vii</sup>	140.95 (3)
O3—Tb1—O1	77.72 (5)	Tb1—O1—Tb1 <sup>viii</sup>	103.00 (9)
O3—Tb1—O1 <sup>i</sup>	114.93 (5)	C1—O1—Tb1 <sup>viii</sup>	122.4 (2)
O3 <sup>iii</sup> —Tb1—O1 <sup>i</sup>	114.93 (5)	C1—O1—Tb1	134.6 (2)
O3 <sup>iii</sup> —Tb1—O1	77.72 (5)	C1—O2—Tb1 <sup>ix</sup>	130.8 (3)
O3—Tb1—O2 <sup>ii</sup>	70.35 (5)	C2—O3—Tb1	119.13 (17)
O3 <sup>iii</sup> —Tb1—O2 <sup>ii</sup>	70.35 (5)	Tb1 <sup>iv</sup> —O4—Tb1 <sup>x</sup>	102.79 (6)
O3—Tb1—O3 <sup>iii</sup>	128.40 (10)	C2—O4—Tb1 <sup>x</sup>	137.90 (16)
O3—Tb1—O4 <sup>vii</sup>	132.53 (6)	C2—O4—Tb1 <sup>iv</sup>	119.27 (16)
O3—Tb1—O4 <sup>vi</sup>	126.90 (6)	O1—C1—H1	116.5
O3 <sup>iii</sup> —Tb1—O4 <sup>iv</sup>	126.90 (6)	O2—C1—O1	127.1 (4)
O3 <sup>iii</sup> —Tb1—O4 <sup>vi</sup>	66.88 (6)	O2—C1—H1	116.5
O3 <sup>iii</sup> —Tb1—O4 <sup>v</sup>	132.52 (6)	O3—C2—O4	126.6 (2)
O3 <sup>iii</sup> —Tb1—O4 <sup>vii</sup>	72.19 (6)	O3—C2—C2 <sup>iv</sup>	118.5 (3)
O3—Tb1—O4 <sup>v</sup>	72.19 (6)	O4—C2—C2 <sup>iv</sup>	114.9 (3)
O3—Tb1—O4 <sup>iv</sup>	66.88 (6)		
Tb1 <sup>viii</sup> —Tb1—O1—C1	180.0	O2 <sup>ii</sup> —Tb1—O3—C2	-67.5 (2)
Tb1 <sup>i</sup> —Tb1—O3—C2	14.9 (2)	O3 <sup>iii</sup> —Tb1—O1—Tb1 <sup>viii</sup>	112.87 (5)
Tb1 <sup>viii</sup> —Tb1—O3—C2	151.3 (2)	O3—Tb1—O1—Tb1 <sup>viii</sup>	-112.87 (5)
Tb1—O1—C1—O2	0.0	O3 <sup>iii</sup> —Tb1—O1—C1	-67.13 (5)
Tb1 <sup>viii</sup> —O1—C1—O2	180.0	O3—Tb1—O1—C1	67.13 (5)
Tb1 <sup>ix</sup> —O2—C1—O1	180.0	O3 <sup>iii</sup> —Tb1—O3—C2	-109.9 (2)
Tb1—O3—C2—O4	171.1 (2)	O4 <sup>v</sup> —Tb1—O1—Tb1 <sup>viii</sup>	-36.98 (5)
Tb1—O3—C2—C2 <sup>iv</sup>	-9.4 (4)	O4 <sup>vi</sup> —Tb1—O1—Tb1 <sup>viii</sup>	108.29 (11)
Tb1 <sup>x</sup> —O4—C2—O3	-6.7 (5)	O4 <sup>vii</sup> —Tb1—O1—Tb1 <sup>viii</sup>	36.98 (5)
Tb1 <sup>iv</sup> —O4—C2—O3	170.9 (2)	O4 <sup>iv</sup> —Tb1—O1—Tb1 <sup>viii</sup>	-108.29 (11)
Tb1 <sup>iv</sup> —O4—C2—C2 <sup>iv</sup>	-8.7 (4)	O4 <sup>v</sup> —Tb1—O1—C1	143.02 (5)
Tb1 <sup>x</sup> —O4—C2—C2 <sup>iv</sup>	173.74 (18)	O4 <sup>vi</sup> —Tb1—O1—C1	-71.71 (11)



O1 <sup>i</sup> —Tb1—O1—Tb1 <sup>viii</sup>	0.0	O4 <sup>vii</sup> —Tb1—O1—C1	-143.02 (5)
O1 <sup>i</sup> —Tb1—O1—C1	180.0	O4 <sup>iv</sup> —Tb1—O1—C1	71.71 (11)
O1 <sup>i</sup> —Tb1—O3—C2	54.2 (2)	O4 <sup>iv</sup> —Tb1—O3—C2	9.75 (19)
O1—Tb1—O3—C2	-173.1 (2)	O4 <sup>vi</sup> —Tb1—O3—C2	-21.7 (2)
O2 <sup>ii</sup> —Tb1—O1—Tb1 <sup>viii</sup>	180.0	O4 <sup>v</sup> —Tb1—O3—C2	119.5 (2)
O2 <sup>ii</sup> —Tb1—O1—C1	0.0	O4 <sup>vii</sup> —Tb1—O3—C2	148.72 (19)

Symmetry codes: (i)  $x-1/2, y, -z+3/2$ ; (ii)  $x-1/2, y, -z+1/2$ ; (iii)  $x, -y+3/2, z$ ; (iv)  $-x, -y+1, -z+1$ ; (v)  $-x+1/2, -y+1, z+1/2$ ; (vi)  $-x, y+1/2, -z+1$ ; (vii)  $-x+1/2, y+1/2, z+1/2$ ; (viii)  $x+1/2, y, -z+3/2$ ; (ix)  $x+1/2, y, -z+1/2$ ; (x)  $-x+1/2, -y+1, z-1/2$ .

*Hydrogen-bond geometry (Å, °)*

<i>D</i> —H $\cdots$ <i>A</i>	<i>D</i> —H	H $\cdots$ <i>A</i>	<i>D</i> $\cdots$ <i>A</i>	<i>D</i> —H $\cdots$ <i>A</i>
C1—H1 $\cdots$ O2 <sup>xi</sup>	0.93	2.15	3.051 (5)	164

Symmetry code: (xi)  $x+1/2, -y+3/2, -z+1/2$ .