

Nano Hydroxyapatite & Mineral Trioxide Aggregate Efficiently Promote Odontogenic Differentiation of Dental Pulp Stem Cells

Ahmed Khaled Hanafy^{1*}, Souzy F. Shinaishin², Ghada Nour Eldeen^{3,4}, Riham M. Aly^{5,6}

¹Department of Oral Biology, Faculty of Dentistry, Egyptian Russian University in Cairo, Egypt; ²Department of Oral Biology, Faculty of Dentistry, Ain Shams University, Cairo, Egypt; ³Department of Molecular Genetics and Enzymology, National Research Centre, Cairo, Egypt; ⁴Stem Cell Research Group, Medical Research Centre of Excellence, National Research Centre, Cairo, Egypt; ⁵Basic Dental Science Department, Oral & Dental Research Division, National Research Centre, Cairo, Egypt; ⁶Stem Cell Laboratory, Centre of Excellence for Advanced Sciences, National Research Centre, Cairo, Egypt;

Abstract

Citation: Hanafy AK, Shinaishin SF, Eldeen GN, Aly RM. Nano Hydroxyapatite & Mineral Trioxide Aggregate Efficiently Promote Odontogenic Differentiation of Dental Pulp Stem Cells. Open Access Maced J Med Sci. 2018 Sep 25; 6(9):1727-1731. <https://doi.org/10.3889/oamjms.2018.368>

Keywords: Dental Pulp Stem Cells; Odontogenic Differentiation; Mineral trioxide aggregate; Nano hydroxyapatite

***Correspondence:** Ahmed Khaled Hanafy. Department of Oral Biology, Faculty of Dentistry, Egyptian Russian University in Cairo, Egypt. E-mail: ahmed70884@gmail.com

Received: 20-Jun-2018; **Revised:** 18-Aug-2018; **Accepted:** 19-Aug-2018; **Online first:** 23-Sep-2018

Copyright: © 2018 Ahmed Khaled Hanafy, Souzy F. Shinaishin, Ghada Nour Eldeen, Riham M. Aly. This is an open-access article distributed under the terms of the Creative Commons Attribution-NonCommercial 4.0 International License (CC BY-NC 4.0)

Funding: This research did not receive any financial support

Competing Interests: The authors have declared that no competing interests exist

BACKGROUND: There has been an urge to shift from conventional therapies to the more promising regenerative strategy since conventional treatment relies on synthetic materials to fill defects and replace missing tissues, lacking the ability to restore the tissues' physiological architecture and function.

AIM: The present study focused on the assessment of the role of two commonly used biomaterials namely; mineral trioxide aggregate (MTA) and nano hydroxy-apatite as promoters of odontogenic differentiation of dental pulp stem cells (DPSCs).

METHODS: DPSCs were isolated, cultured in odontogenic media and divided into three groups; control group, MTA group and nanohydroxyapatite group. Odontogenic differentiation was assessed by tracing genes characteristic of different stages of odontoblasts via qRT-PCR. Calcific nodules formation was evaluated by Alizarin red staining.

RESULTS: Results demonstrated that both MTA and nanohydroxyapatite were capable of enhancing odontogenic differentiation of DPSCs.

CONCLUSION: Nano hydroxyapatite was found to have a higher promoting effect. However, in the absence of an odontogenic medium, MTA and nanohydroxyapatite could not enhance the odontogenic differentiation of DPSCs.

Introduction

Regenerative and cell-based therapies represent a promising alternative to conventional therapies to maintain pulp vitality and to avoid the more extensive treatment dictated by extraction or endodontic therapy. Mineral Trioxide Aggregate (MTA) and nano hydroxyapatite are promising materials which have wide clinical and regenerative uses. Different studies performed on MTA, showed that it plays an important role in regenerative endodontics, mainly through the activation of cementoblasts and the formation of cementum [1].

MTA was also reported to play a role in stimulation of the odontogenic differentiation of stem cells [2] and the induction of stem cell proliferation with excellent biocompatibility [3]. Another material that is widely used is nano hydroxyapatite, due to its particle size that is close to the apatite crystals present naturally in human mineralised tissue which is useful when used as a scaffold material in tissue engineering [4]. It also presents superior properties regarding enhancing stem cells proliferation and differentiation into osteoblasts resulting in bone formation [5]. Moreover, nano hydroxyapatite plays a remarkable role in guided tissue regeneration to enhance bone regeneration in the field of periodontology [6].

In this study, the role of MTA and nano hydroxyapatite as promoters of odontogenic differentiation is assessed on dental pulp stem cells.

Material and Methods

Dental pulp stem cells isolation and culture

Human dental pulp tissues were obtained from three impacted third molars. Teeth were collected from patients aged from 16–26 years. Extraction of teeth was performed in the department of Oral Surgery Department at Ain Shams University clinics under the approval of its ethics committee. The extirpated pulp tissues were minced into small pieces and digested with 2mg/mL collagenase type I (Serva) for 30 minutes at 37°C. Cell suspensions were cultured in 6-cm dishes in high-glucose Dulbecco modified Eagle medium (Lonza, Belgium) supplemented with 10% fetal bovine serum (FBS, Invitrogen) and antibiotics (100 U/mL penicillin and 100 mg/mL streptomycin) at 37°C in 5% CO₂. Passaging was performed when adherent cells reached 70% confluence.

Induction of odontogenic differentiation

To induce odontogenic differentiation, DPSCs from the third passage were seeded into 6-well plates at a density of 1x10⁵/well. Odontogenic differentiation was performed for 21 days by culturing DPSCs in odontogenic differentiation medium containing DMEM medium supplemented with 15% FBS, 10 mol/L β-glycerophosphate (Sigma-Aldrich), 0.2 mmol/L ascorbate-2-phosphate (Sigma-Aldrich), and 100 nmol/L dexamethasone (Sigma-Aldrich). DPSCs were divided into three groups according to the media and biomaterial used as follows; 1) Controls; positive controls were grown in odontogenic media with 15% FBS whereas negative controls were grown in DMEM with 15% FBS. 2) MTA group; which was supplied with MTA powder (Angelus, Brazil) and odontogenic medium (as above mentioned). For MTA preparation, a concentration of 0.02 mg/ml was implemented according to previous protocols [7]. Briefly, 0.02 mg MTA was dissolved in 1ml of odontogenic media and vortexed until suspended. The suspension was then left to settle for 10 minutes followed by 24 hours incubation in 37°C and 5% CO₂ to extract the bioactive contents of MTA. The resultant supernatant from this preparation was used to treat cells every other day with for 3 weeks. Finally, nano hydroxyapatite group; which comprised nano hydroxyapatite (Sigma–Aldrich, UK) at a concentration of 10 µg/mL suspended in odontogenic media [8]. For

all groups media was changed three times a week for 21 days.

Real time RT-PCR analysis for odontogenic gene expression

After 3 weeks of odontogenic induction of the 3 groups of cells (nano hydroxyapatite, MTA and control groups). Total RNA was isolated using PureLink RNA Min Kit (Invitrogen, <http://www.invitrogen.com>). All RNA samples were checked for purity using a ND-1000 spectrophotometer (Nano Drop Technologies, Wilmington, DE, USA). Total RNA samples were reverse transcribed into cDNA using RevertAid First Strand cDNA Synthesis Kit (Thermo Fisher) and quantitative real time PCR was performed using 1 µg of cDNA and Maxima SYBR Green qPCR master mix (Thermo Fisher) in a LightCycler® 480 Instrument (Roche life science). Real-Time Quantitative Polymerase Chain Reaction Analysis Differential expressions of five odontogenic genes; Alkaline Phosphatase (ALP), Osteopontin (OPN), RUNX2, Osteocalcin (OCN) and collagen1 was carried out. The primer sequences are provided in (Table 1). Samples were run twice. The raw data were then analyzed with the Relative expression software tool (REST) using the automatic cycle threshold (Ct) setting to assign baselines and thresholds for the Ct determination. Delta Ct ($\Delta\Delta Ct$) values were used for this analysis. The relative expressions (REs) of the sample genes were calculated using the $\Delta\Delta Ct$ method and GAPDH was used as the internal control or housekeeping gene. q RT-PCR experiments were carried out at least three times. Data were presented as the average values \pm SEM (standard error of the mean). Statistical significance was analyzed with paired Student t-test. Significance levels or P-values are indicated in the figure legends.

Table 1: Primer sequences for quantitative real-time PCR analysis

Gene	Forward	Reverse
<i>Runx2</i>	5'-AAGTGCCTGCAAACTTCT-3'	5'-TCTCGGTGGCTGCTAGTGA-3'
<i>Osteocalcin</i>	5'-TCA CAC TCC TCG CCC TAT TG-3'	5'-TCG CTG CCC TCC TGC TTG-3'
<i>ALP</i>	5'-AGC TGA ACA GGA ACA ACG TGA-3'	5'-CTT CAT GGT GCC CGT GGT C-3'
<i>Collagen1</i>	5'-ACC GCC CTC CTG ACG CAC -3'	5'-GCA GAC GCA GAT CCG GCA G-3'
<i>Osteopontin</i>	5'-AAGCGCATTACAGCAAACACTCA	3'-CTCATCGGACTCCTGGCTCTTCA
<i>GAPDH</i>	5'-ACCACAGTCCATGCCATCAC	3'-TCCACCACCTGTTGCTGTA

Alizarin Red Staining

To assess in vitro mineralization, cells were washed twice with phosphate-buffered saline, fixed with 4% paraformaldehyde (Sigma- Aldrich) for 1 hour, washed with deionized H₂O, and stained with 1% Alizarin Red S (Sigma-Aldrich) for 20 minutes. They were then rinsed 3 times with deionized H₂O, the mineralized nodules were observed under inverted light microscope (Leica, 6000B-4) using Suite V3 (Leica).

Results

Isolation of human dental pulp stem cells (DPSCs)

Human dental pulp stem cells (DPSCs) were successfully isolated from pulps of extracted third molars. The cultured DPSCs were observed on a regular basis using an inverted light microscope (Figure 1). After 24 hours of isolation, DPSCs began to develop processes assuming a spindle and stellate shape which is the typical appearance of mesenchymal stem cell and attached to the bottom of the culture dish. Approximately ten days following the initial isolation, cells reached 70% confluence. At this stage, cells were passaged to passage three where differentiation was initiated.

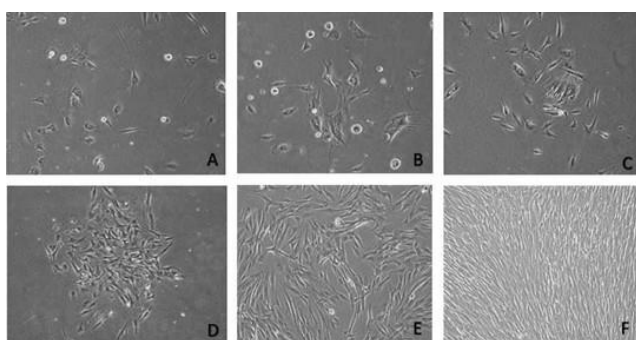


Figure 1: Isolation and morphological observation of human dental pulp stem cells (DPSCs) by phase contrast microscopy; (A) DPSCs after 24 hours from isolation; (B) Isolated DPSCs with different morphological appearances following isolation; (C) DPSCs assuming colonies on day 3 of isolation; (D) DPSCs on day 5 of isolation showing increase in colony size with increase in cell number; (E) DPSCs a week after isolation; cells are approaching confluence; (F) DPSCs reaching 80% confluence 10 days after isolation (Magnification 100X)

Successful induction of odontogenic differentiation of DPSCs

After applying the odontogenic medium for differentiation, DPSCs were observed on a regular basis for morphological alterations. During the first week after induction, DPSCs which have reached confluency began to change their spindle-shape developing into rounded cells which gathered to form clusters. Rounded aggregates of DPSCs appeared as a result of cell migration chiefly from the periphery toward the centre of the plates (Figure 2).

On day 21, staining with Alizarin Red was done. Orange-red nodules indicating the beginning of mineralisation was demonstrated (Figure 3B).

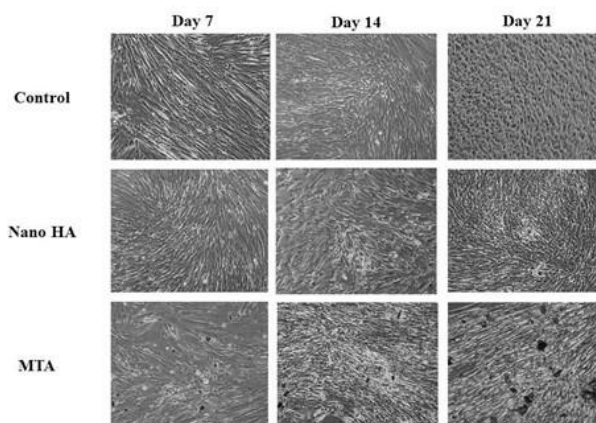


Figure 2: Morphological observation of DPSCs during odontogenic differentiation; Photomicrographs illustrating the morphological appearance of DPSCs while cultured either in odontogenic differentiation media supplemented with nano-hydroxyapatite (NanoHA) or MTA over a period of 21 days. DPSCs gradually transformed from spindle/stellate shape into a more rounded polygonal morphology. However, there was an apparent gradual decrease in cell number in the MTA group (Magnification 100X)

MTA and nano hydroxyapatite promoted odontogenic differentiation

Gene expression and statistical analysis were performed to assess the differential expression of five odontogenic markers in cells differentiated with either MTA or nano hydroxyapatite compared with control counterparts. The studied genes were ALP, OPN, RUNX2, OCN, and collagen1 genes (Figure 3A).

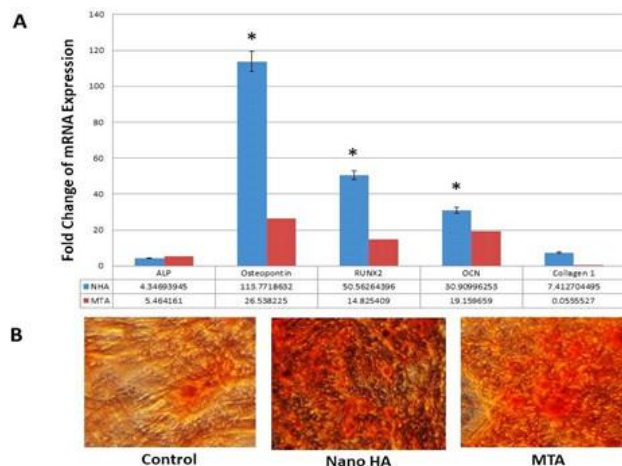


Figure 3: Evaluation of odontogenic differentiation capacity of DPSCs cultured under different conditions; (A) Expression of genes characteristic of odontogenic differentiation; Alkaline Phosphatase (ALP), Osteopontin, RUNX2, Osteocalcin (OCN), Collagen1 in nano-hydroxyapatite (NHA) and MTA groups. GAPDH was used as housekeeping gene. The data were analysed by qRT-PCR and compared with positive control, i.e. cells cultured in odontogenic media only. Results are presented as mean \pm SEM of three independent experiments ($n = 3$). * $P < 0.05$; (B) Alizarin Red staining was used to determine mineral nodule formation on day 21 in all groups

Using q RT-PCR, we detected the expression of all studied genes in all groups although the quantities varied. OPN, RUNX2 and OCN were

overexpressed in all groups with significantly higher expression in groups supplemented with nano hydroxyapatite. *Collagen1* was showed higher expression in Nano hydroxyapatite group than in MTA but with no statistical significance, whereas *ALP* was the only gene that illustrated increased expression MTA group.

It is worthy to note that both MTA and nano hydroxyapatite added to DMEM only without odontogenic supplements were not able to induce odontogenic differentiation (Supplementary Figure 1).

Discussion

In the present study, we focused on two promising biomaterials, MTA and nano hydroxyapatite, which have been known to play an imperative role in the field of dentistry. Evaluation of the effect of the MTA and the nano hydroxyapatite on the odontogenic differentiation potential of the DPSCs was done by tracing the expression levels of genes characteristic of odontoblastic differentiation markers including *ALP*, *OC*, *OPN*, *RUNX2* and *Collagen 1*. Primary pulp cells are known to express type I collagen, *ALP*, bone sialoprotein, and osteocalcin [2]. The expression of these markers relates to different stages during odontogenic differentiation. *OPN* was highly expressed in both groups with a significant increase in nano hydroxyapatite group. The role of *OPN* in dentinogenesis is well described in the literature. During reparative dentinogenesis, *OPN* expression was found to play an undeniable role in the differentiation of odontoblast-like cells during pulpal healing following tooth transplantation [9].

In accordance to our study, Kuratate M. et al., suggested that pulpal responses to MTA capping involve proliferation and migration of pulp stem cells followed by their differentiation into odontoblast-like cells where osteopontin played a triggering role in the initiation of the pulpal reparative process [10]. Similarly, *RUNX2*; which is a key factor that is essential for odontoblastic differentiation, was highly expressed in both MTA and nanohydroxyapatite supplemented media. In accordance to our study, Matsumoto S. et al. proved that in the presence of MTA, the expression levels of *RUNX2* in C2C12 cells (cell line obtained from RIKEN Cell Bank, Japan) were significantly increased indicating odontoblastic differentiation [11]. Furthermore, in accordance to our study, Mohamed et al. concluded that nano hydroxyapatite promoted odontogenic differentiation of DPSCs [12]. Also, Liu H-C et al. found that DPSCs seeded on nano-hydroxyapatite/collagen/Poly (L-lactide) could undergo odontogenic and osteogenic differentiation evident by the expression of *OCN*, *COL 1* and *ALP* [13].

Next, we assessed the expression level of *OCN*. *OCN* has been known to be expressed only

during the later stages of odontoblasts cytodifferentiation during tooth development. *OCN* was also detected in odontoblasts and their processes within the extracellular matrix at the maturation stage of enamel formation. It was shown that *OCN* is produced by human odontoblasts and determine the expression pattern of *DSPP* in human teeth [14]. Our results showed that *OCN* was highly expressed in both MTA and nanohydroxyapatite supplemented with odontogenic media indicating odontogenic differentiation of the DPSCs.

The role of *ALP* has been suggested to be implicated in early mineralisation. In our study, *ALP* was expressed both in MTA and nano hydroxyapatite groups. However, its expression in both groups was less than other genes studied. This finding is by Alliot-Licht B. et al., and Zhang W. et al., who revealed that *ALP* activity gradually increased after reaching its peak expression on the day and then declined [15] [16]. In accordance to our study, Min K-S. et al. found that DPSCs treated with MTA showed up-regulation of m-RNA expression levels of *ALP* and *OCN* which confirmed successful odontogenic differentiation of the DPSCs [17]. *ALP* also participates in dentin formation and was found to be highly expressed by mature odontoblasts; its absence indicates defective dentin mineralisation [18].

According to our results of genes tracing, it was noted that nano-hydroxyapatite showed higher levels of odontogenic genes expression in comparison to MTA supplemented with odontogenic medium suggesting a higher odontogenic differentiation potential of the nano hydroxyapatite. This increased differentiation potential might be attributed to the difference in their chemical composition and surface topography. Nano hydroxyapatite composition is similar to crystals present in dental hard tissues (calcium and phosphates) and has special biological and physicochemical properties [19]. Also, nanoscale of hydroxy-apatite had been shown to positively affect the adhesion and differentiation of stem cells and has excellent biological properties compared to their larger micron-structured counterparts which are attributed to increased surface reactivity [20]. Successful odontogenic differentiation of DPSCs was further confirmed by Alizarin red staining assay. Positive colorimetric changes were observed in both MTA and nano hydroxy-apatite groups as well as in the positive control group, which indicated calcific nodules formation. In accordance with our study, Jung J-Y. et al., suggested that MTA plays a role in differentiation of DPSCs into odontoblasts as evidenced by the alizarin red staining of calcified nodules [21].

Moreover, Woo S-M. et al., found that calcium ions released from MTA has a major impact on the odontoblastic differentiation of DPSCs and enhancement of mineralized nodule formation [22]. In accordance with our experiment, Liu H-C. et al., found that sporadic nodules-shaped islands after alizarin red staining as a result of the differentiation of DPSCs into

odontoblast and osteoblast when nano hydroxyapatite was used as a scaffold [13]. In our study, MTA extract was used to induce odontogenic differentiation of DPSCs after 24 hours of incubation of MTA powder in odontogenic media. By this method, we aimed to avoid direct contact of MTA with DPSCs and thus simulating the clinical conditions achieved when MTA is used for direct pulp capping. However, it was observed that MTA exerted an observable decrease in cell viability during culture, despite using a very low concentration. The concentration used was according to Hakki SS. et al., which was described as the least cytotoxic concentration capable of inducing differentiation [7]. It is worthy to mention that our results revealed that both MTA & nano hydroxyapatite were not sufficient to induce odontogenic differentiation by their selves. This was clearly evident, from the minimal expression of *ALP*, *OCN*, *OPN*, *RUNX2* and *collagen1* exhibited by MTA and nano hydroxyapatite added to DMEM media in the absence of odontogenic differentiation supplementation.

In conclusion, it was observed that both MTA and nano hydroxyapatite in the presence of odontogenic medium could enhance the odontogenic differentiation of the DPSCs. It was also clear that nano hydroxyapatite possess higher odontogenic differentiation potential than MTA, evidenced by higher fold increase in the expression of most of the odontogenic genes studied. These data may be useful in future studies to promote odontogenic differentiation of DPSCs and may be useful in designing regenerative therapies for dentin.

References

- Baek SH, Plenk H, Kim S. Periapical tissue responses and cementum regeneration with amalgam, superEBA, and MTA as root-end filling materials. *J Endod.* 2005; 31(6):444–9. <https://doi.org/10.1097/01.don.0000148145.81366.a5> PMID:15917684
- Seo M-S, Hwang K-G, Lee J, Kim H, Baek S-H. The Effect of Mineral Trioxide Aggregate on Odontogenic Differentiation in Dental Pulp Stem Cells. *J Endod [Internet].* 2013; 39(2):242–8. <https://doi.org/10.1016/j.joen.2012.11.004> PMID:23321238
- Amit V, Vishwakarma SK, Vanka GS, Bhat MK, Khan AA. In vitro proliferation of MSCs using mineral trioxide aggregate: A most recent material for in situ stem cells mobilisation. *International Journal.* 2014; 2(2):561-7.
- He H, Yu J, Cao J, E L, Wang D, Zhang H, et al. Biocompatibility and osteogenic capacity of periodontal ligament stem cells on nHAC/PLA and HA/TCP scaffolds. *J Biomater Sci Polym Ed.* 2011; 22(1–3):179–94.
- Lee JK, Hwang KH. Particle size effects on the bone formation of hydroxyapatite/stem cell biocomposites. *Journal of Ceramic Processing Research.* 2012; 13(2):158-63.
- Vitti RP, Prati C, Silva EJNL, Sinhoreti MAC, Zanchi CH, De Souza E Silva MG, et al. Physical properties of MTA fillapex sealer. *J Endod.* 2013; 39(7):915–8. <https://doi.org/10.1016/j.joen.2013.04.015> PMID:23791263
- Hakki SS, Bozkurt SB, Hakki EE, Belli S. Effects of Mineral Trioxide Aggregate on Cell Survival, Gene Expression Associated with Mineralized Tissues, and Biomineralization of Cementoblasts. *J Endod.* 2009; 35(4):513–9. <https://doi.org/10.1016/j.joen.2008.12.016> PMID:19345796
- Remya NS, Syama S, Gayathri V, Varma HK, Mohanan PV. An in vitro study on the interaction of hydroxyapatite nanoparticles and bone marrow mesenchymal stem cells for assessing the toxicological behaviour. *Colloids Surfaces B Biointerfaces.* 2014; 117:389–97. <https://doi.org/10.1016/j.colsurfb.2014.02.004> PMID:24675277
- Saito K, Nakatomi M, Ida-Yonemochi H, Ohshima H. Osteopontin Is Essential for Type I Collagen Secretion in Reparative Dentin. *J Dent Res.* 2016; 95(9):1034–41. <https://doi.org/10.1177/0022034516645333> PMID:27126446
- Kuratate M, Yoshida K, Shigetani Y, Yoshida N, Ohshima H, Okiji T. Immunohistochemical Analysis of Nestin, Osteopontin, and Proliferating Cells in the Reparative Process of Exposed Dental Pulp Capped with Mineral Trioxide Aggregate. *J Endod.* 2008; 34(8):970–4. <https://doi.org/10.1016/j.joen.2008.03.021> PMID:18634929
- Matsumoto S, Hayashi M, Suzuki Y, Suzuki N, Maeno M, Ogiso B. Calcium Ions Released from Mineral Trioxide Aggregate Convert the Differentiation Pathway of C2C12 Cells into Osteoblast Lineage. *J Endod.* 2013; 39(1):68–75. <https://doi.org/10.1016/j.joen.2012.10.006> PMID:23228260
- Mohamed, Fayyad DM. The effect of different bioactive materials on the odontogenic differentiation potential of dental pulp stem cells using two different culture mediums. *Tanta Dent J.* 2018; 14(3):120. https://doi.org/10.4103/tj.tdj.32_17
- Liu H-C, E L-L, Wang D-S, Su F, Wu X, Shi Z-P, et al. Reconstruction of Alveolar Bone Defects Using Bone Morphogenetic Protein 2 Mediated Rabbit Dental Pulp Stem Cells Seeded on Nano-Hydroxyapatite/Collagen/Poly(L-lactide). *Tissue Eng Part A.* 2011; 17(19–20):2417–33. <https://doi.org/10.1089/ten.tea.2010.0620> PMID:21563858
- Papagerakis P, Berdal A, Mesbah M, Peuchmaur M, Malaval L, Nydegger J, et al. Investigation of osteocalcin, osteonectin, and dentin sialophosphoprotein in developing human teeth. *Bone.* 2002; 30(2):377–85. [https://doi.org/10.1016/S8756-3282\(01\)00683-4](https://doi.org/10.1016/S8756-3282(01)00683-4)
- Alliot-Licht B, Bluteau G, Magne D, Lopez-Cazaux S, Lieubeau B, Daculsi G, et al. Dexamethasone stimulates differentiation of odontoblast-like cells in human dental pulp cultures. *Cell Tissue Res.* 2005; 321(3):391–400. <https://doi.org/10.1007/s00441-005-1115-7> PMID:15988617
- Zhang W, Walboomers XF, Wolke JGC, Bian Z, Fan MW, Jansen J a. Differentiation ability of rat postnatal dental pulp cells in vitro. *Tissue Eng.* 2005; 11(3–4):357–68. <https://doi.org/10.1089/ten.2005.11.357> PMID:15869416
- Min K-S, Yang S-H, Kim E-C. The Combined Effect of Mineral Trioxide Aggregate and Enamel Matrix Derivative on Odontoblastic Differentiation in Human Dental Pulp Cells. *J Endod.* 2009; 35(6):847–51. <https://doi.org/10.1016/j.joen.2009.03.014> PMID:19482184
- Foster BL, Nagatomo KJ, Tso HW, Tran AB, Nociti FH, Narisawa S, et al. Tooth root dentin mineralization defects in a mouse model of hypophosphatasia. *J Bone Miner Res.* 2013; 28(2):271–82. <https://doi.org/10.1002/jbmr.1767> PMID:22991301 PMID:PMC3541444
- Yousefi A-M, Oudadesse H, Akbarzadeh R, Wers E, Lucas-Girot A. Physical and biological characteristics of nanohydroxyapatite and bioactive glasses used for bone tissue engineering. *Nanotechnol Rev.* 2014; 3(6). <https://doi.org/10.1515/ntrev-2014-0013>
- Zhou GS, Su ZY, Cai YR, Liu YK, Dai LC, Tang RK, Zhang M. Different effects of nanophase and conventional hydroxyapatite thin films on attachment, proliferation and osteogenic differentiation of bone marrow derived mesenchymal stem cells. *Bio-medical materials and engineering.* 2007; 17(6):387-95. PMID:18032820
- Jung J-Y, Woo S-M, Lee B-N, Koh J-T, Nör JE, Hwang Y-C. Effect of Biodentine and Bioaggregate on odontoblastic differentiation via mitogen-activated protein kinase pathway in human dental pulp cells. *Int Endod J.* 2015; 48(2):177–84. <https://doi.org/10.1111/iej.12298> PMID:24738842
- Woo S-M, Kim W-J, Lim H-S, Choi N-K, Kim S-H, Kim S-M, et al. Combination of Mineral Trioxide Aggregate and Platelet-rich Fibrin Promotes the Odontoblastic Differentiation and Mineralization of Human Dental Pulp Cells via BMP/Smad Signaling Pathway. *J Endod.* 2016; 42(1):82–8. <https://doi.org/10.1016/j.joen.2015.06.019> PMID:26364004