



## PAPER

Cite this: *Nanoscale Adv.*, 2023, 5, 970

# Zero-strain strategy incorporating TaC with Ta<sub>2</sub>O<sub>5</sub> to enhance its rate capacity for long-term lithium storage†

Yinhong Gao, Xu Nan, Bing Sun, Wenli Xu, Qiang Huang, Ye Cong, Yanjun Li,  Xuanke Li\* and Qin Zhang \*

Ta<sub>2</sub>O<sub>5</sub> holds great potential for lithium storage due to its high theoretical capacity and long-life cycling. However, it still suffers from an unsatisfactory rate capability because of its low conductivity and significant volume expansion during the charging/discharging process. In this study, a zero-strain strategy was developed to composite Ta<sub>2</sub>O<sub>5</sub> with zero-strain TaC as an anode for lithium-ion batteries (LIBs). The zero-strain TaC, featuring negligible lattice expansion, can alleviate the volume variation of Ta<sub>2</sub>O<sub>5</sub> when cycling, thereby enhancing the rate capacity and long-term cycling stability of the whole electrode. Further, the formation of a heterostructure between Ta<sub>2</sub>O<sub>5</sub> and TaC was confirmed, giving rise to an enhancement in the electrical conductivity and structural stability. As expected, this anode displayed a reversible specific capacity of 395.5 mA h g<sup>-1</sup> at 0.5 A g<sup>-1</sup> after 500 cycles. Even at an ultrahigh current density of 10 A g<sup>-1</sup>, the Ta<sub>2</sub>O<sub>5</sub>/TaC anode delivered a high capacity of 144 mA h g<sup>-1</sup> and superior durability with a low-capacity decay rate of 0.08% per cycle after 1000 cycles. This zero-strain strategy provides a promising avenue for the rational design of anodes, sequentially contributing to the development of high-rate capacity and long cycling LIBs.

Received 31st October 2022  
Accepted 28th December 2022

DOI: 10.1039/d2na00764a

rsc.li/nanoscale-advances

## Introduction

The global energy crisis and increasing concerns about environmental pollution are driving the exploration of clean sustainable energy, which has also triggered a new upsurge in the study of energy-storage systems,<sup>1,2</sup> particularly rechargeable lithium-ion batteries (LIBs). LIBs possess the merits of high energy density, high power density, good safety, and environmental friendliness.<sup>3–6</sup> However, there is an urgent need for high-rate, fast-charging, and long-cycling LIBs to meet the rising demands of portable electronic devices and electric vehicles.<sup>7,8</sup> To date, commercial graphite anodes tend to be low-cost and eco-friendly but suffer from a very limited theoretical capacity (372 mA h g<sup>-1</sup>). Furthermore, the formation of irreversible Li dendrites in the graphite anode can result in safety issues at a low operating potential (~0.1 V vs. Li/Li<sup>+</sup>) and high current density.<sup>9–12</sup> Therefore, graphite anodes fail to satisfy the high requirements for next-generation LIBs. As such, an alternative anode is desired for LIBs that can meet the demands for long-term cycling, fast charging, and good safety.

Tantalum-based compounds have aroused enormous interest, particularly as electrodes for energy-related applications, owing to their natural abundance, and superior chemical and thermal stability, as well as for having an open matrix accessible to alkali metal ions.<sup>13,14</sup> Among such compounds, tantalum pentoxide (Ta<sub>2</sub>O<sub>5</sub>), despite its large atomic mass, reportedly furnished a high theoretical capacity of 482 mA h g<sup>-1</sup> through a partial conversion mechanism.<sup>14,15</sup> Hence, it has long been a decent choice for a LIB anode. Recently, Ta<sub>2</sub>O<sub>5</sub> was reported to possess an extrinsic pseudo-capacitance property and has shown great potential for fast-charging LIBs.<sup>16,17</sup> For instance, Xia *et al.*<sup>18</sup> proposed a three-dimensional (3D) Ta<sub>2</sub>O<sub>5</sub> electrode and achieved a stable capacity of 205 mA h g<sup>-1</sup> at 5C (2410 mA g<sup>-1</sup>). Ta<sub>2</sub>O<sub>5</sub> aerogels prepared by Pan *et al.*<sup>19</sup> presented an outstanding rate capability of 97.0 mA h g<sup>-1</sup> at a current density of 5 A g<sup>-1</sup>. However, its poor conductivity and the large and repeating volume variations during the charging/discharging process hinder Ta<sub>2</sub>O<sub>5</sub> from demonstrating a high-rate performance. To overcome the above issues, constructing a heterostructure has been verified to be an efficient strategy for optimizing the electrochemical performance of materials.<sup>20–23</sup> The generation of an internal electric field between different components can facilitate charge transfer, and greatly elevate the electrical and ionic conductivities, thereby contributing to a superior rate capability and cycle life of the electrode materials.<sup>24,25</sup>

Hubei Province Key Laboratory of Coal Conversion and New Carbon Materials, Wuhan University of Science and Technology, Wuhan, 430081, China. E-mail: zhangqin627@wust.edu.cn; lixuanke@wust.edu.cn

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2na00764a>



Herein, we propose a zero-strain strategy involving constructing Ta<sub>2</sub>O<sub>5</sub> with zero-strain TaC to form a Ta<sub>2</sub>O<sub>5</sub>/TaC heterostructure. The Ta<sub>2</sub>O<sub>5</sub>/TaC heterostructure was fabricated *via* a reflux polymerization and solvothermal precipitation process, followed by a partial reduction of Ta<sub>2</sub>O<sub>5</sub> to generate TaC. TaC with a high elastic modulus (537 GPa) was inferred to feature a zero-strain property,<sup>26</sup> which was further confirmed by the *ex situ* and *in situ* X-ray diffraction (XRD) patterns. Such a zero-strain and conductive TaC alleviated the large volume expansion of the whole electrode during the lithiation/delithiation process. The heterostructure possessed abundant active sites, enhanced electrical conductivity and structural stability, and reduced diffusion barrier of Li ions. Furthermore, the Ta<sub>2</sub>O<sub>5</sub>/TaC heterostructure also demonstrated typical faradaic pseudocapacitance characteristics, ensuring a high-rate capacity and long cycling performance. As expected, this anode displayed a high reversible specific capacity of 395.5 mA h g<sup>-1</sup> at 0.5 A g<sup>-1</sup> after 500 cycles. Even at an ultrahigh current density of 10 A g<sup>-1</sup>, the Ta<sub>2</sub>O<sub>5</sub>/TaC anode presented a high capacity of 144 mA h g<sup>-1</sup> and superior durability with a low-capacity decay rate of 0.08% per cycle after 1000 cycles. This study highlights the significance of the zero-strain strategy for boosting the high-rate capability and provides invaluable guidance for designing advanced anodes towards next-generation high-power LIBs.

## Experimental

### Materials synthesis

All the chemical reagents used in this work were of analytical grade and used without further purification. Based on a reported method with a slight modification,<sup>27</sup> in a typical synthesis, 3 mM TaCl<sub>5</sub> and 0.15 mM phenolic resin (PF) were dissolved in a mixed solvent of 40 mL ethanol and 10 mL acetylacetone under magnetic stirring, and then refluxed at 80 °C for 2 h to generate the yellow liquid polymer precursor. After that, the yellow solution was transferred into a steel autoclave and treated at 200 °C for 3 h. After cooling to ambient temperature, the resultant yellow precipitates were collected through centrifugation, washed with ethanol several times, and dried at 80 °C overnight. Finally, the above yellow precipitates were transferred into a furnace, and the temperature was increased to the optimized value of 1100 °C, 1200 °C, or 1400 °C (10 °C min<sup>-1</sup>), and maintained at the specified temperature for 1 h annealing under an argon-protecting environment to obtain the desired Ta<sub>2</sub>O<sub>5</sub>, Ta<sub>2</sub>O<sub>5</sub>/TaC, and TaC respectively.

### Materials characterizations

The crystallographic phases of all the as-obtained samples were investigated by X-ray diffraction (XRD; Bruker D8 Advance) equipped with Cu K $\alpha$  radiation,  $\lambda = 1.542 \text{ \AA}$ . The scanning rate and scanning step size were 5° min<sup>-1</sup> and 0.033°, respectively. *In situ* XRD tests were also performed on the Bruker D8 Advance X-ray diffractometer. The *in situ* cell employed Be foil as an X-ray penetrator window. The corresponding Li<sup>+</sup> insertion/extraction potential ranged from 0.01 V to 3 V vs. Li/Li<sup>+</sup> during the initial two cycles at a current density of 50 mA g<sup>-1</sup>. The *in situ* XRD

patterns of Ta<sub>2</sub>O<sub>5</sub>/TaC were collected in the two-theta region between 20° and 60° with a step size of 0.02° and a scanning speed of 0.07° s<sup>-1</sup>. The morphology and structure of products were characterized by scanning electron microscopy (SEM, JSM-7610F PLUS) and transmission electron microscopy (TEM, JEM-2100UHR). The surface chemical states of the products were investigated by X-ray photoelectron spectroscopy (XPS, Thermo Fischer, ESCALAB 250Xi).


### Electrochemical measurements

The electrochemical tests were conducted in a CR2016 coin-type cells configuration. The electrodes were prepared by blending the active materials with Super P and polyvinylidene fluoride (PVDF) binder, in a mass ratio of 6 : 3 : 1, respectively, together with *N*-methyl-2-pyrrolidone (NMP) as the blending solvent. The resulting slurry was spread on Cu foil as a current collector, followed by drying in a vacuum oven at 80 °C overnight. The coin cells were assembled in an Ar-filled glovebox with O<sub>2</sub> and H<sub>2</sub>O concentrations less than 0.1 ppm. A lithium pellet acted as the counter and reference electrodes. The employed electrolyte was 1 M LiPF<sub>6</sub> in a mixture of ethylene carbonate (EC) and dimethyl carbonate (DEC) with a volume ratio (v/v) of 1 : 1 (DoDoChem, 99.9%), and with 5 wt% fluoroethylene carbonate (FEC) additive. Galvanostatic charge/discharge measurements were performed at 25 °C on a LAND battery testing system. Galvanostatic intermittent titration technique (GITT) tests were conducted by charge/discharge at 0.1C with a current pulse duration of 10 min and an interval time of 20 min. Cyclic voltammetry (CV) and electrochemical impedance spectra (EIS, with a frequency range of 100 kHz to 0.01 Hz) were measured on a CHI660D electrochemical workstation (Chenhua Inc., Shanghai, China). The CV profiles were recorded in the potential range from 0.005 to 3.0 V with various scan speeds (0.2–3 mV s<sup>-1</sup>).

## Results and discussion

To better present the zero-strain strategy, Scheme 1 manifests the structural evolution of the pure Ta<sub>2</sub>O<sub>5</sub> and Ta<sub>2</sub>O<sub>5</sub>/TaC anode in the Li<sup>+</sup>-storage process. The Ta<sub>2</sub>O<sub>5</sub> stores the Li<sup>+</sup> ions by means of the typical intercalation and conversion reaction mechanism during the lithiation process. When the Li<sup>+</sup> ions insert into pure Ta<sub>2</sub>O<sub>5</sub>, it leads to a lattice expansion of Ta<sub>2</sub>O<sub>5</sub>. Followed by the formation of TaO, it then suffers from significant pulverization, thus giving rise to capacity attenuation of the electrode. As for TaC, it followed a solid-solution mechanism, demonstrating negligible volume change. For the Ta<sub>2</sub>O<sub>5</sub>/TaC heterostructure, even when experiencing the repeated charging/discharging process, Ta<sub>2</sub>O<sub>5</sub> and its reduction products could be confined in a limited space by the zero-strain TaC. Thus, the structural integrity of the whole Ta<sub>2</sub>O<sub>5</sub>/TaC electrode could be maintained, which would guarantee the long-term cycling stability and high-rate capacity.

The Ta<sub>2</sub>O<sub>5</sub>/TaC heterostructure was fabricated through a reflux polymerization, convenient solvothermal coprecipitation, and post-heat treatment carbonization. The

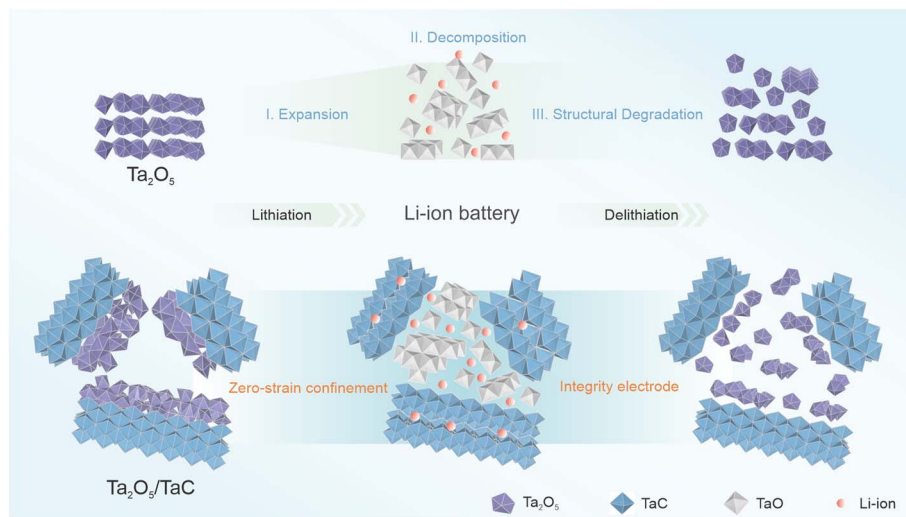

**Scheme 1** Illustration of the reaction mechanism during the initial lithiation/delithiation of the pure  $\text{Ta}_2\text{O}_5$  and  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode.


experimental conditions and processes are described in detail in the Experimental section. Primarily, polycondensation between phenolic resin (PF) and  $\text{Ta}^{5+}$  took place to form an organic liquid precursor. This could be expected to promote the uniform mixing of tantalum and carbon sources, and prevent the agglomeration of metal compounds during the following carbonization process. Subsequently, the dispersed inorganic hybrid intermediate (amorphous  $\text{Ta}_2\text{O}_5@PF$  hybrid) was obtained by the solvothermal reaction. Finally, the partial carbonization of the  $\text{Ta}_2\text{O}_5@PF$  hybrid gave rise to the *in situ* formation of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode. XRD characterization was employed to investigate the components of the solvothermal intermediate and the findings are presented in Fig. S1a.† The two broad peaks located at  $26^\circ$  and  $55^\circ$  indicated the formation of amorphous  $\text{Ta}_2\text{O}_5$  nanospheres.<sup>28</sup> The field-emission scanning electron microscopy (FESEM) image in Fig. S1b† shows the uniformly dispersed nanosphere structure of  $\text{Ta}_2\text{O}_5@PF$  with a smooth surface.

We utilized FESEM, high-resolution transmission electron microscopy (HRTEM), and energy dispersive spectrometry (EDS) to characterize the crystal structure, heterointerface, and chemical composition of the synthesized  $\text{Ta}_2\text{O}_5/\text{TaC}$  composite (Fig. 1). Fig. 1a presents the morphology of the as-prepared  $\text{Ta}_2\text{O}_5/\text{TaC}$ . Compared with pure  $\text{Ta}_2\text{O}_5$  and TaC (Fig S2a and d†), the  $\text{Ta}_2\text{O}_5/\text{TaC}$  nanoparticles displayed the smallest average particle size, which was measured to be about 80 nm (Fig. 1b), which would be conducive to a shorter ion-diffusion path. However, pure TaC exhibited the largest particle size, due to agglomeration at high temperatures. The microstructure of  $\text{Ta}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5/\text{TaC}$ , and TaC were further investigated by transmission electron microscopy (TEM), as shown in Fig. 1c and S2b and e,† respectively. The HRTEM image displayed the clear lattice fringes of  $\text{Ta}_2\text{O}_5$  and TaC (Fig. 1d). The interplanar spacing (highlighted in yellow) was measured to be 0.31 nm, which was identified as the (1110) plane of  $\text{Ta}_2\text{O}_5$ . The lattice fringes with a *d*-spacing of 0.22 nm (marked in red) corresponded to the (200) crystalline plane of cubic phase TaC.<sup>28,29</sup> A

clear heterointerface between  $\text{Ta}_2\text{O}_5$  and TaC could be observed in Fig. 1d (marked in yellow dotted lines). Nonetheless, in the HRTEM image of  $\text{Ta}_2\text{O}_5$  (Fig. S2c†) and TaC (Fig. S2f†), only typical lattice fringes of the single oxide and carbide phases could be recognized, respectively. Moreover, the EDS mapping images of  $\text{Ta}_2\text{O}_5/\text{TaC}$  revealed the uniform distribution of Ta, C, and O elements in the composite, as presented in Fig. 1e.

XRD was conducted to further confirm the structural constitution and crystalline phase. For comparison, pure  $\text{Ta}_2\text{O}_5$  and TaC synthesized *via* the same route served as the contrast samples. The XRD patterns of  $\text{Ta}_2\text{O}_5$ , TaC, and  $\text{Ta}_2\text{O}_5/\text{TaC}$  are shown in Fig. 2a. The main peaks were located at  $22.8^\circ$ ,  $28.2^\circ$ ,  $28.7^\circ$ ,  $36.6^\circ$ ,  $37.1^\circ$ ,  $46.6^\circ$ ,  $49.7^\circ$ ,  $50.6^\circ$ , and  $55.7^\circ$  and were assigned to the (001), (1110), (200), (1111), (201), (002), (0220), (3110), and (1112) lattice planes of  $\text{Ta}_2\text{O}_5$ , respectively. The peaks at  $34.9^\circ$ ,  $40.5^\circ$ ,  $58.6^\circ$ ,  $70.0^\circ$ , and  $73.6^\circ$  were indexed to the (111), (200), (220), (311), and (222) lattice planes of TaC. Clearly, the obtained XRD patterns matched well with the standard patterns of rhomboidal  $\text{Ta}_2\text{O}_5$  (PDF: 71-0639) and cubic TaC ( $Fm\bar{3}m$ ) (PDF: 35-0801). According to the zoom-in regions shown in Fig. 2b, the (001), (1110), (200), (1111), and (201) planes of  $\text{Ta}_2\text{O}_5$  in  $\text{Ta}_2\text{O}_5/\text{TaC}$  were slightly shifted to a lower diffraction angle in comparison with the bare  $\text{Ta}_2\text{O}_5$ . This phenomenon indicated the synergistic effect between  $\text{Ta}_2\text{O}_5$  and TaC, confirming the formation of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  heterostructure. Then, a Rietveld-refined XRD pattern was applied to  $\text{Ta}_2\text{O}_5/\text{TaC}$  and the results are displayed in Fig. S3.† The small residual of 1.34% revealed that the calculated curve matched well with the experimental result.<sup>30</sup> Also, the refinement result manifested the good crystallinity of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  composite. Moreover, the contents of  $\text{Ta}_2\text{O}_5$  and TaC were calculated to be 67.4% and 32.6%, respectively. According to the results, the unit-cell volume of  $\text{Ta}_2\text{O}_5$  was calculated to be  $977.9 \text{ nm}^3$ , while the value was  $88.4 \text{ nm}^3$  for TaC. The unit-cell volume of  $\text{Ta}_2\text{O}_5$  in  $\text{Ta}_2\text{O}_5/\text{TaC}$  was larger than for pure  $\text{Ta}_2\text{O}_5$  ( $970.9 \text{ nm}^3$ ).


The surface electronic states and compositions of  $\text{Ta}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5/\text{TaC}$ , and TaC were further probed by X-ray photoelectron

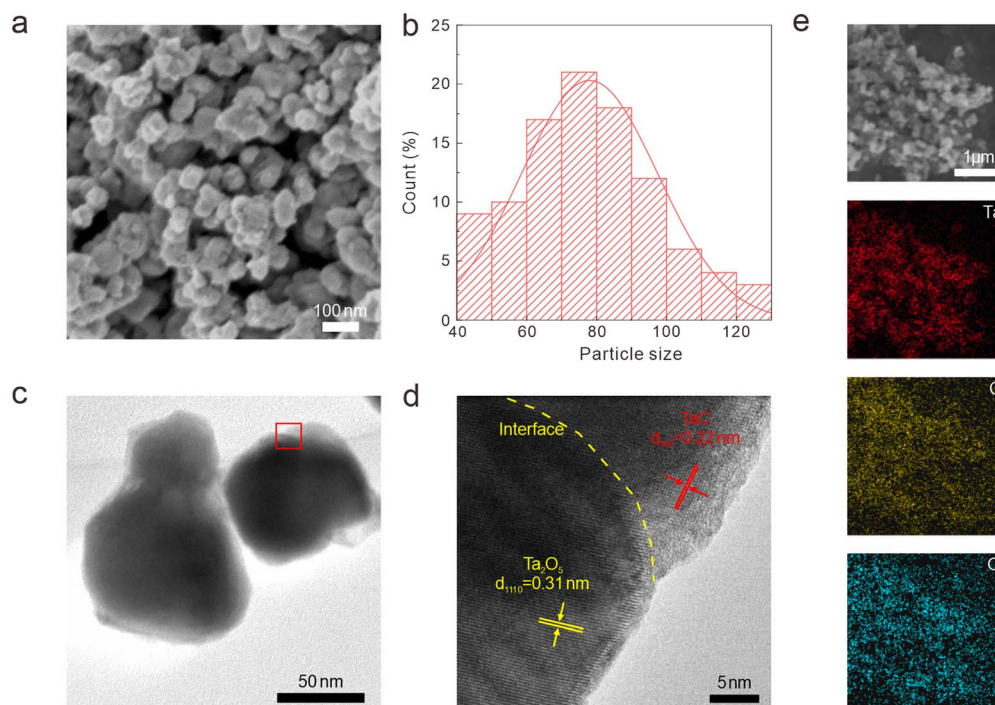

**Fig. 1** Morphology characterization of the Ta<sub>2</sub>O<sub>5</sub>/TaC nanoparticles. (a) FESEM images. (b) Particle size distribution. (c) TEM image. (d) HRTEM image. (e) EDS mapping images.

spectroscopy (XPS), as presented in Fig. 2c. Five distinct peaks were noted at 26.4, 230.7, 243.3, 285.1, and 531.3 eV, which belonged to Ta 4f, Ta 4d<sub>5/2</sub>, Ta 4d<sub>3/2</sub>, C 1s, and O 1s, respectively.

The high-resolution Ta 4f spectra of the three samples are shown in Fig. 2d. The Ta 4f spectrum of Ta<sub>2</sub>O<sub>5</sub> could only be fitted into the Ta–O 4f<sub>7/2</sub> (27.3 eV) and Ta–O 4f<sub>5/2</sub> (29.2 eV) states.

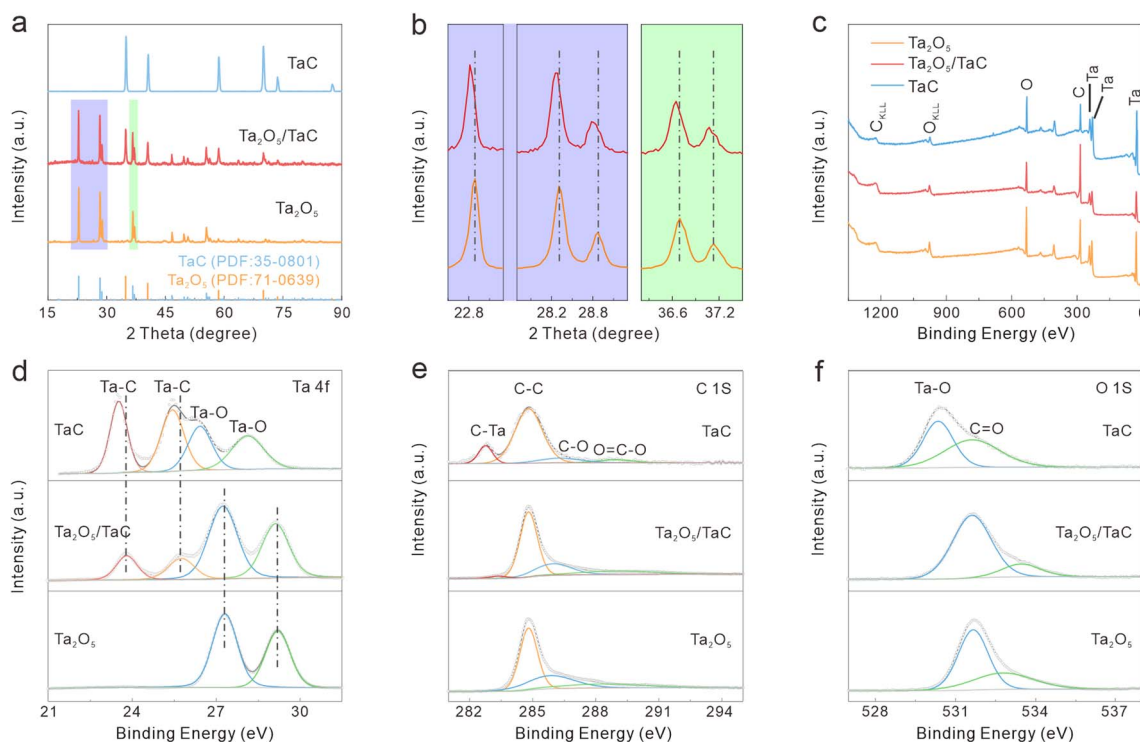

**Fig. 2** (a) XRD patterns of Ta<sub>2</sub>O<sub>5</sub>, Ta<sub>2</sub>O<sub>5</sub>/TaC, and TaC. (b) Corresponding zoom-in regions of the XRD patterns of Ta<sub>2</sub>O<sub>5</sub> and Ta<sub>2</sub>O<sub>5</sub>/TaC. (c) XPS survey spectra of Ta<sub>2</sub>O<sub>5</sub>, Ta<sub>2</sub>O<sub>5</sub>/TaC, and TaC. High-resolution XPS spectra of Ta<sub>2</sub>O<sub>5</sub>, Ta<sub>2</sub>O<sub>5</sub>/TaC, and TaC: (d) Ta 4f, (e) C 1s, (f) O 1s.

As for Ta<sub>2</sub>O<sub>5</sub>/TaC, there were four well-resolved peaks corresponding to the Ta–C bond in TaC (23.8 eV and 25.7 eV for Ta 4f<sub>7/2</sub> and Ta 4f<sub>5/2</sub>, respectively) and the Ta–O bond in Ta<sub>2</sub>O<sub>5</sub> (27.2 eV and 29.1 eV for 4f<sub>7/2</sub> and 4f<sub>5/2</sub>, respectively).<sup>26,31</sup> For the pure TaC, the peaks located at 26.4 and 28.1 eV could be ascribed to the Ta–O bond, resulting from the natural oxidation of carbide during air exposure. Also, another two peaks at 23.5 and 25.4 eV were associated with Ta 4f<sub>7/2</sub> and Ta 4f<sub>5/2</sub> for TaC. The Ta–C peaks in the Ta<sub>2</sub>O<sub>5</sub>/TaC composite were shifted to higher binding energy compared with TaC, indicating the strong electronic interactions between Ta<sub>2</sub>O<sub>5</sub> and TaC. In comparison with the pure Ta<sub>2</sub>O<sub>5</sub>, the Ta–O peak was shifted to a lower binding energy, further suggesting the existence of the Ta<sub>2</sub>O<sub>5</sub>/TaC heterostructure. The deconvolution peak located at 283.3 eV in the C 1s spectrum of Ta<sub>2</sub>O<sub>5</sub>/TaC was ascribed to the C–Ta bond and further confirmed the formation of TaC (Fig. 2e). Moreover, the peak intensity of C–Ta (282.7 eV) in the C 1s of TaC was higher and sharper than that of Ta<sub>2</sub>O<sub>5</sub>/TaC. The O 1s state of Ta<sub>2</sub>O<sub>5</sub>/TaC showed two typical peaks originating from the O=C and O–Ta bonds, located at 533.3 and 531.6 eV, respectively (Fig. 2f). In accordance with the XRD results, the XPS analysis indicated that the Ta<sub>2</sub>O<sub>5</sub>/TaC heterostructure was successfully synthesized.

Then, the electrochemical performances of these samples were evaluated for use as anode materials for LIBs. Fig. S4† shows the first five cyclic voltammogram of the Ta<sub>2</sub>O<sub>5</sub>, Ta<sub>2</sub>O<sub>5</sub>/TaC, and TaC anodes in the potential range from 3.0 to 0.005 V at a scan rate of 0.2 mV s<sup>-1</sup>. As shown in Fig. S4b,† the irreversible cathodic peaks of the Ta<sub>2</sub>O<sub>5</sub>/TaC anode appearing at 0.36 V and 0.67 V in the first cycle were derived from the side reactions with the electrolyte and the generation of a solid–electrolyte interphase layer (SEI),<sup>32</sup> which was not fully recovered in the subsequent anodic sweep. The following four cycles demonstrated a higher overlap ratio than that of Ta<sub>2</sub>O<sub>5</sub>, indicating the outstanding reversibility and cycle stability of Li<sup>+</sup> insertion/extraction in the Ta<sub>2</sub>O<sub>5</sub>/TaC anode. Additionally, a pair of broad peaks at ~0.75/0.8 V was noted, corresponding to the reversible phase transition of the Ta<sub>2</sub>O<sub>5</sub>/TaC anode. In the following four cycles, the intensity of the oxidation peaks continued to increase, indicating that more active components were involved in the delithiation reaction.<sup>33</sup> Note that the curves of the following four cycles of TaC basically overlapped, and showed the minimum potential difference ( $\phi_p$ ) of the redox process, indicating its better cycle stability than that of the Ta<sub>2</sub>O<sub>5</sub> anode.<sup>34</sup> The  $\phi_p$  value of Ta<sub>2</sub>O<sub>5</sub>/TaC was intermediate between Ta<sub>2</sub>O<sub>5</sub> and TaC, revealing that the introduction of zero-strain TaC facilitated the reversibility of the whole electrode. Fig. S5† presents the galvanostatic charge/discharge profiles of the Ta<sub>2</sub>O<sub>5</sub>/TaC anode in the 1st, 2nd, and 10th cycles at a current density of 0.5 A g<sup>-1</sup>. It could be seen in the first cycle that an irreversible capacity loss was mainly caused by the formation of SEI layers,<sup>23</sup> which was in accordance with the CV result. The plateaus of the discharge–charge characteristics matched well with the CV profiles.

Fig. 3a shows the rate performances of Ta<sub>2</sub>O<sub>5</sub>/TaC, Ta<sub>2</sub>O<sub>5</sub>, and TaC at varying current densities from 0.5 to 10 A g<sup>-1</sup>. The Ta<sub>2</sub>O<sub>5</sub>/TaC anode displayed higher discharge capacities of


328.6, 247, 212.2, 169.3, and 144.4 mA h g<sup>-1</sup> at differing current densities, higher than those of Ta<sub>2</sub>O<sub>5</sub> (124.9 mA h g<sup>-1</sup> at 5 A g<sup>-1</sup> and 86.1 mA h g<sup>-1</sup> at 10 A g<sup>-1</sup>). When the current density suddenly switched back to 0.5 A g<sup>-1</sup>, a discharge specific capacity of 301.3 mA h g<sup>-1</sup> could still be recovered in Ta<sub>2</sub>O<sub>5</sub>/TaC, indicating its high reversibility and excellent Li<sup>+</sup>-diffusion kinetics. Furthermore, both Ta<sub>2</sub>O<sub>5</sub>/TaC and TaC exhibited enhanced capacity retention rates at higher current rates. Compared with the rate performance at 0.5 A g<sup>-1</sup>, the capacity retention rates of Ta<sub>2</sub>O<sub>5</sub>/TaC and TaC at 10 A g<sup>-1</sup> were 43.9% and 78.8%, respectively, while the corresponding value for Ta<sub>2</sub>O<sub>5</sub> was only 29.3%. One can draw a conclusion that TaC was conducive to realizing the excellent rate capability of the Ta<sub>2</sub>O<sub>5</sub>/TaC anode. Fig. 3b shows the galvanostatic charge–discharge profiles at current densities from 0.5 to 10 A g<sup>-1</sup>. The absence of the plateau region in these curves suggested a capacitive Li<sup>+</sup>-storage behaviour of the Ta<sub>2</sub>O<sub>5</sub>/TaC anode.<sup>35</sup> To highlight the impressive lithium storage performance of Ta<sub>2</sub>O<sub>5</sub>/TaC, the performances of the reported Ta<sub>2</sub>O<sub>5</sub> anodes are listed in Fig. 3c.<sup>15,17–19,28,36</sup> As shown, the Ta<sub>2</sub>O<sub>5</sub>/TaC anode manifested superior electrochemical performance, especially at higher cycling rates.

We also evaluated the cycling performances of Ta<sub>2</sub>O<sub>5</sub>, Ta<sub>2</sub>O<sub>5</sub>/TaC, and TaC electrodes at a current density of 0.5 A g<sup>-1</sup> and the results are displayed in Fig. 3d. The reversible capacity of Ta<sub>2</sub>O<sub>5</sub>/TaC remained at 395.5 mA h g<sup>-1</sup> even after 500 cycles. In contrast, the Ta<sub>2</sub>O<sub>5</sub> and TaC anodes showed unsatisfactory capacities of 212.8 and 152.8 mA h g<sup>-1</sup>, respectively. This revealed that the Ta<sub>2</sub>O<sub>5</sub>/TaC anode had preferable cycling stability compared with the bare Ta<sub>2</sub>O<sub>5</sub> anode. The long-term stability of the Ta<sub>2</sub>O<sub>5</sub>/TaC electrode was first activated at 0.5 A g<sup>-1</sup> for 10 cycles and was further measured under an ultrahigh current density of 10 A g<sup>-1</sup> (Fig. 3e). The reversible capacity of Ta<sub>2</sub>O<sub>5</sub>/TaC remained as high as 127.8 mA h g<sup>-1</sup> even after 1000 cycles with a low-capacity decay rate of 0.08% per cycle.

To further study the kinetic process of the Ta<sub>2</sub>O<sub>5</sub>/TaC anode, the lithium-ion diffusivity was evaluated by the galvanostatic intermittent titration technique (GITT). Fig. 4a presents the GITT curves for Ta<sub>2</sub>O<sub>5</sub>, Ta<sub>2</sub>O<sub>5</sub>/TaC, and TaC, and the zoom-in regions are shown in Fig. 4b. The Ta<sub>2</sub>O<sub>5</sub>/TaC anode presented the lowest voltage difference of 8.3 mV during the Li<sup>+</sup> lithiation/delithiation process, while the values were 15.8 mV for Ta<sub>2</sub>O<sub>5</sub> and 13.4 mV for TaC. This indicated that lower polarization occurred in the Ta<sub>2</sub>O<sub>5</sub>/TaC anode.<sup>37</sup> The corresponding diffusion coefficient ( $D_{Li}$ ) could be calculated by Fick's second law with eqn (1),<sup>38</sup>

$$D_{Li} = \frac{4}{\pi} \left( \frac{m_B V_m}{M_B S} \right)^2 \left( \frac{\Delta E_s}{\tau d E_\tau / d\sqrt{\tau}} \right)^2 \left( \tau \ll \frac{L^2}{D_{Li}} \right) \quad (1)$$

where  $m_B$  is the mass weight of Ta<sub>2</sub>O<sub>5</sub>/TaC,  $V_m$  is the molar volume,  $M_B$  is the molar weight of Ta<sub>2</sub>O<sub>5</sub>/TaC,  $S$  is the real surface area,  $\Delta E_s$  is the variation in the equilibrium potential,  $\tau$  is the titration time, and  $\Delta E_\tau$  is the potential variation during the pulse. Since the potential was linearly proportional to  $\tau^{0.5}$

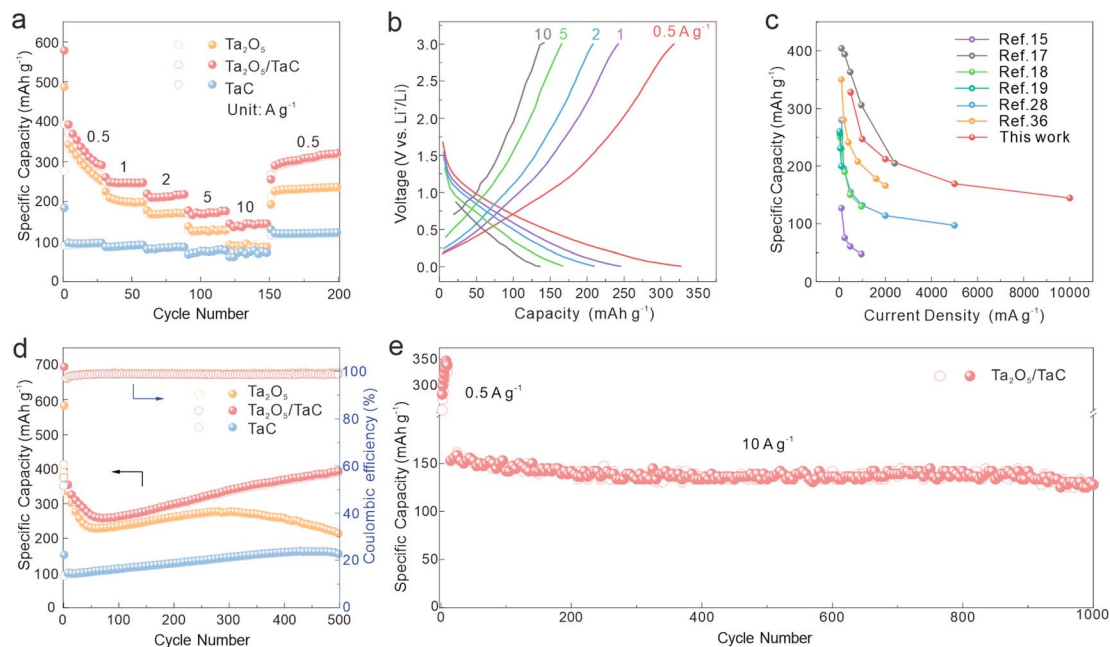

**Fig. 3**  $\text{Li}^+$ -storage performances. (a) Rate performances of the  $\text{Ta}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5/\text{TaC}$ , and  $\text{TaC}$  anodes. (b) Galvanostatic charge/discharge curves of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode at different current densities from 0.5 to  $10 \text{ A g}^{-1}$ . (c) Rate performance of  $\text{Ta}_2\text{O}_5/\text{TaC}$  compared with reported  $\text{Ta}_2\text{O}_5$  compounds for LIBs. (d) Cycling performance of the  $\text{Ta}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5/\text{TaC}$ , and  $\text{TaC}$  anodes at  $0.5 \text{ A g}^{-1}$ . (e) long cycling performance of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode at an ultrahigh current density of  $10 \text{ A g}^{-1}$ .

during the single titration, eqn (1) could be simplified as eqn (2):


$$D_{\text{Li}} = \frac{4}{\pi} \left( \frac{m_{\text{B}} V_{\text{m}}}{M_{\text{B}} S} \right)^2 \left( \frac{\Delta E_{\text{s}}}{\Delta E_{\text{t}}} \right)^2 \left( \tau \ll \frac{L^2}{D_{\text{Li}}} \right) \quad (2)$$

As exhibited in Fig. 4c, the average  $D_{\text{Li}}$  values of  $\text{Ta}_2\text{O}_5/\text{TaC}$  towards  $\text{Li}^+$  insertion and extraction were  $1.64 \times 10^{-11}$  and  $2.26 \times 10^{-11}$ , respectively (Table S1†). Both values were higher than those of  $\text{Ta}_2\text{O}_5$  ( $9.54 \times 10^{-12}$  and  $1.38 \times 10^{-11}$ ) and  $\text{TaC}$  ( $1.61 \times 10^{-11}$  and  $2.05 \times 10^{-11}$ ) in Table S1 and Fig. S6.† This indicated a faster interface kinetics and efficient lithium-ion insertion/desertion, further implying a higher rate capability of  $\text{Ta}_2\text{O}_5/\text{TaC}$  for LIBs.<sup>22</sup>

The electrochemical impedance spectra (EIS) were adapted to clearly understand the dynamic behaviour and further verify the synergistic effect between  $\text{Ta}_2\text{O}_5$  and  $\text{TaC}$ . The Nyquist profiles at an open-circuit potential before cycling are shown in Fig. 4d.  $\text{Ta}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5/\text{TaC}$ , and  $\text{TaC}$  possessed similar resistance profiles, with the semicircle in the high-frequency regions corresponding to the charge-transfer resistance ( $R_{\text{ct}}$ ), and the sloping line in the low-frequency region related to the solid-state  $\text{Li}$ -ion mass-transfer process.<sup>39</sup> The solution resistance ( $R_{\text{s}}$ ) and  $R_{\text{ct}}$  of  $\text{Ta}_2\text{O}_5/\text{TaC}$  were calculated to be 3.7 and  $351.8 \Omega$ , respectively, according to the simulated equivalent circuit model (Table S2†). The  $R_{\text{ct}}$  of  $\text{Ta}_2\text{O}_5/\text{TaC}$  was higher than that of the  $\text{TaC}$  anode ( $255.4 \Omega$ ). Meanwhile, the  $\text{Ta}_2\text{O}_5$  electrode presented the largest  $R_{\text{ct}}$  ( $400 \Omega$ ). This confirmed that the introduction of highly conductive  $\text{TaC}$  significantly improved the conductivity and led to a synergistic enhancement of the

interfacial kinetics, thus boosting the rate performance. After that, the  $D_{2\text{Li}}$  of all electrodes could be deduced *via* the linear relationship between the real part of the impedance ( $Z'$ ) and the reciprocal square root of the angular frequency ( $\omega^{-1/2}$ ) in the low-frequency region ( $Z' = \sigma \omega^{-1/2}$ , where  $\sigma$  is Warburg parameter),<sup>40</sup> as depicted in Fig. 4e. According to the equation  $D_{2\text{Li}} = R^2 T^2 / 2A^2 n^4 F^4 C^2 \sigma^2$ ,<sup>23</sup> the  $D_{2\text{Li}}$  of  $\text{Ta}_2\text{O}_5/\text{TaC}$  was calculated to be 54.7 and 9.3 times higher than that of  $\text{Ta}_2\text{O}_5$  and  $\text{TaC}$ , respectively. This is consistent with the GITT results described above. Therefore, we could conclude that the  $\text{Ta}_2\text{O}_5/\text{TaC}$  composite exhibited enhanced  $\text{Li}^+$ -diffusion kinetics due to the interaction between  $\text{Ta}_2\text{O}_5$  and the highly conductive  $\text{TaC}$ . Fig. S7† shows the Nyquist plots of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  composite before and after cycling. It could be observed that the impedance value gradually decreased with the increasing cycles, manifesting the reduction of electrode polarization and successive activation of  $\text{Ta}_2\text{O}_5/\text{TaC}$  in the cycling process.

The CV measurements of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  electrode under scanning speeds ranging from 0.2 to  $3 \text{ mV s}^{-1}$  were carried out and the results are shown in Fig. 4f. Both the cathodic and anodic peak currents ( $i$ ) increased with the elevated scan rates ( $\nu$ ), owing to the capacitive effect on the electrode materials under the fast  $\text{Li}^+$  charge/discharge process.<sup>37</sup> The contribution of the pseudocapacitive ( $k_1 \nu$ ) and diffusion-controlled ( $k_2 \nu^{1/2}$ ) process were analyzed based on the following equation:  $i = k_1 \nu + k_2 \nu^{1/2} = a \nu^b$  (where  $k_1$ ,  $k_2$ , and  $a$  are constants; and  $b$  is an adjustable parameter). The  $b$  value (anodic peak) of  $\text{Ta}_2\text{O}_5/\text{TaC}$  (Fig. 4g) was calculated to be 0.8166, demonstrating the superior  $\text{Li}^+$ -storage behaviour stemming from the combination of a diffusion-controlled and capacitive process.<sup>12,19</sup> In Fig. 4h, the

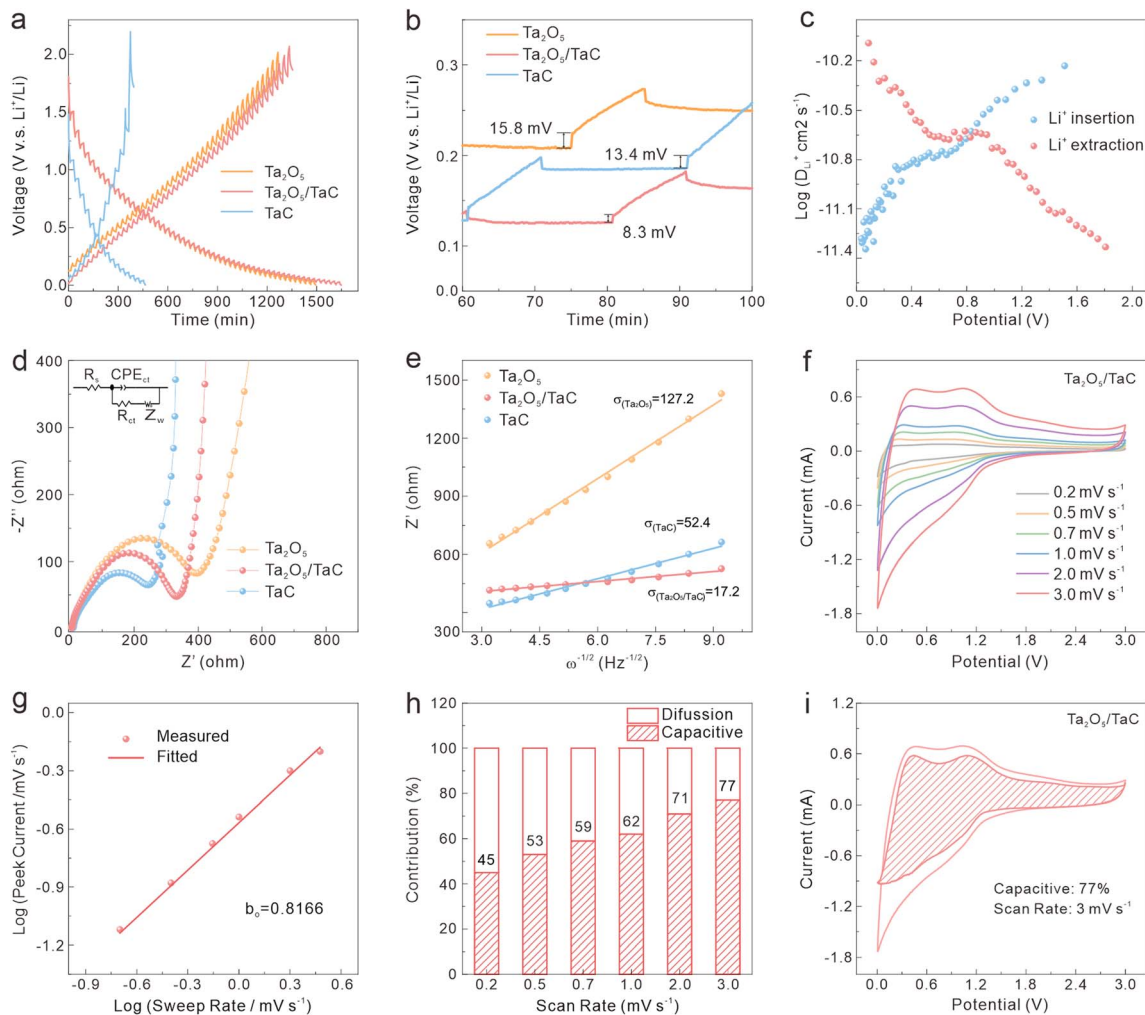

**Fig. 4** Kinetics analysis of  $\text{Li}^+$ -storage: (a) GITT curves and (b) corresponding zoom-in regions of the GITT curves for  $\text{Ta}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5/\text{TaC}$ , and TaC anodes. (c) Calculated  $D_{\text{Li}}$  of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode from the GITT curves. (d) Nyquist plots and (e) dependence of  $Z'$  on the reciprocal square root of  $\omega$  in the low-frequency region for the  $\text{Ta}_2\text{O}_5$ ,  $\text{Ta}_2\text{O}_5/\text{TaC}$ , and TaC anodes. (f) CV profiles collected at different scan rates, (g) corresponding relationship between the anode peak currents and scan rates (in common logarithm axis) and the corresponding linear fits, (h) contribution ratios of the pseudocapacitive to charge storage at different scan rates, (i) CV curve with the pseudocapacitive contribution at  $3 \text{ mV s}^{-1}$  of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  electrode.

pseudocapacitive contribution of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode increased with the sweep rate. This exhibits a pseudocapacitive capacity of 77% at a scanning rate of  $3 \text{ mV s}^{-1}$  (Fig. 4i). This pseudocapacitive behaviour enabled the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode to realize rapid charge transport and enhanced rate performance. The kinetics analysis demonstrated the synergistic effect between  $\text{Ta}_2\text{O}_5$  and TaC to ensure an outstanding rate performance of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode, by accelerating both electron and Li-ion transportation.

*In situ* XRD tests were conducted to explore the electrochemical reaction mechanism and the crystal-structure evolution of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode during cycling. The *in situ* XRD patterns and contour map related to the time–voltage profiles between 3 and 0.01 V during the first two cycles at  $50 \text{ mA g}^{-1}$  are shown in Fig. 5a and b. From the contour plots, we proposed a three-stage transition for the  $\text{Ta}_2\text{O}_5/\text{TaC}$  electrode during the

first discharging procedure. In the first stage (marked as  $I_1$ ), the potential dropped rapidly from an open-circuit voltage to 1.6 V. When initially discharged to 1 V, the (001), (110), (200), (111), and (201) crystallographic planes of  $\text{Ta}_2\text{O}_5$  gradually shifted to lower angles, due to the lattice expansion caused by  $\text{Li}^+$  intercalation.<sup>41</sup>

When further discharged to 0.88 V (the second stage,  $I_2$ ), the intensity of these two peaks of TaC gradually decreased and then recovered to the original intensity after being completely charged (Fig. 5d and S8a†). From the enlarged (111) peaks of the TaC electrode, no obvious intensity change could be observed during the cycle. As for TaC, neither the (111) nor (200) diffraction peaks showed evident shifts during the charge–discharge process. This indicated that the TaC stored the Li ions *via* a solid–solution reaction, with the crystal transformation highly reversible.<sup>42</sup> To further confirm this solid–solution



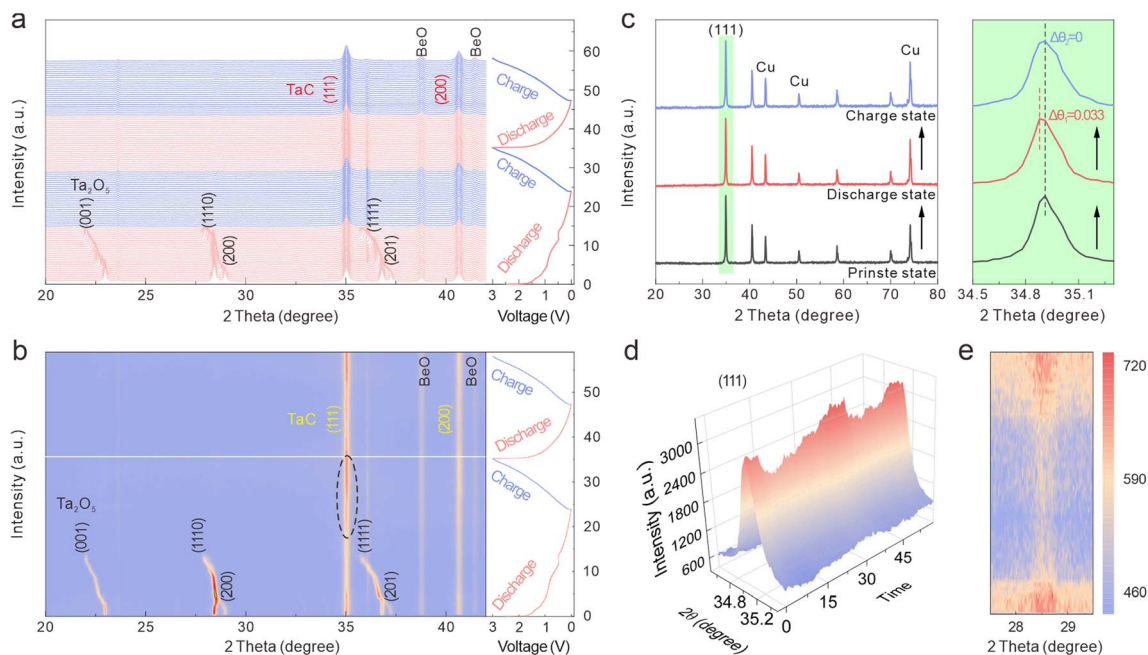


Fig. 5 *In situ* XRD patterns of Ta<sub>2</sub>O<sub>5</sub>/TaC during the initial two cycles, (a) pristine *in situ* XRD patterns with the corresponding discharge–charge profiles. (b) Contour plots with the corresponding charge/discharge curves. (c) *Ex situ* XRD patterns of TaC (left) and the corresponding zoom-in regions (right). 3D plot of selected *in situ* XRD patterns in the 2-theta range of (d) 34.5–35.5°. (e) Contour plot of Ta<sub>2</sub>O<sub>5</sub> in the 2-theta range of 27.5–29.5° during the second cycle.

transition characteristic of the TaC anode, *ex situ* XRD patterns were obtained and are shown in Fig. 5c. The XRD patterns of the TaC anode almost remained unchanged at different stages, with no advent of new peaks or vanishing of the original peaks. The solid-solution type TaC demonstrated negligible lattice distortion and strain during the charge/discharge process, thereby continuously enabling the Li<sup>+</sup> ions to realize the fast-charging application. Moreover, by virtue of Rietveld refining of the XRD patterns of TaC, the alterations of the lattice parameters and volume are presented in Fig. S8b.† The refinement results showed that the initial lattice parameters were  $a = b = c = 4.445$  Å (Fig. S9†). After the first full discharge process, the unit-cell volume of TaC varied from 88.41 to 88.62 Å<sup>3</sup>, with a total volume expansion of only 0.24%. This value was less than 1%, verifying that TaC was a zero-strain insertion material.<sup>43</sup> Significantly, the evolution of the lattice parameters and volume in the second cycle almost held constant, verifying the excellent structural stability and reversibility of TaC. Here, TaC with negligible lattice distortion could confine Ta<sub>2</sub>O<sub>5</sub> in a very limited region, thus giving rise to an enhanced cycling life of the whole anode. Furthermore, given the small volume change during cycling, the decomposition and structural damage of the SEI layer could be mitigated to some degree.


Subsequently, all the peak intensities of Ta<sub>2</sub>O<sub>5</sub> gradually reduced with decreasing the potential and then disappeared at ~0.34 V (the third stage, I<sub>3</sub>). This was likely due to the structural damage and reduced crystallinity of Ta<sub>2</sub>O<sub>5</sub>. In the contour plot in the range of 27.5–29.5° during the second cycle (Fig. 5e), when charging to 3 V, the Ta<sub>2</sub>O<sub>5</sub> phase appeared again. This phenomenon proved the reversible reaction of Ta<sub>2</sub>O<sub>5</sub> with Li<sup>+</sup>. As shown in Fig. 5b and d and S8a,† the peaks at 34.9° and 40.5°

belonged to the (111) and (200) planes of TaO (PDF: 89-4772), respectively. The intensity of these two peaks continuously increased when discharging to 0.34 V, then decreased in the subsequent charging process, due to the conversion of Ta<sub>2</sub>O<sub>5</sub> to TaO.<sup>18</sup> Therefore, the electrochemical Li<sup>+</sup> insertion/extraction mechanism of Ta<sub>2</sub>O<sub>5</sub>/TaC can be described by eqn (3) and (4):



The morphology evolution of the Ta<sub>2</sub>O<sub>5</sub>/TaC electrode was explored after cycling for 50 times at a current density of 0.5 A g<sup>-1</sup> is shown in Fig. S10a† and 6a. The electrode still showed an intact surface and the Ta<sub>2</sub>O<sub>5</sub>/TaC nanoparticles could be well preserved, verifying the structural stability induced by the zero-strain strategy. Besides, the TEM image also confirmed the structural stability of Ta<sub>2</sub>O<sub>5</sub>/TaC (Fig. S10b†). When the Ta<sub>2</sub>O<sub>5</sub>/TaC electrode returned to a fully charged state after 50 cycles, the lattice fringes for Ta<sub>2</sub>O<sub>5</sub> (1110) and TaC (200) could be observed in the HRTEM image (Fig. 6b). The HRTEM image also indicated that TaC robustly maintained a monocrystalline phase, while on the contrary, Ta<sub>2</sub>O<sub>5</sub> cracked into polycrystalline from the original single-crystal phase. The robust TaC structure allowed the volume expansion of the inner Ta<sub>2</sub>O<sub>5</sub>, thereby maintaining the integrity of the whole electrode. Additionally, the phase compositions of the Ta<sub>2</sub>O<sub>5</sub>/TaC electrode after being charged to 3 V were investigated by XPS (Fig. 6c, and S10c–f†). The high-resolution Ta 4f spectrum could be resolved into four distinguishable peaks, assigned to the Ta–C bond in TaC (23.6 and 25.6 eV) and Ta–O bond in Ta<sub>2</sub>O<sub>5</sub> (27.4



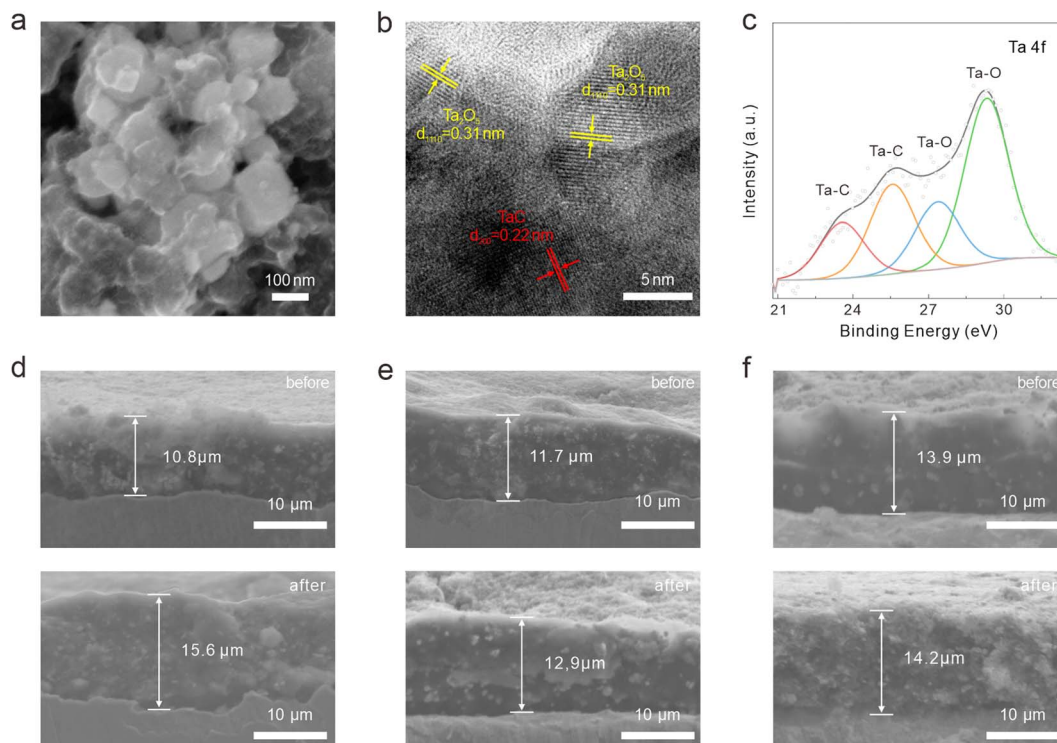

**Fig. 6** (a) High-magnification FESEM image, and (b) HRTEM image of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  electrode after 50 cycles. (c) High-resolution XPS spectrum of Ta 4f for  $\text{Ta}_2\text{O}_5/\text{TaC}$  electrode after being charged to 3 V. Cross-sectional view of SEM images of the three different electrodes before and after cycling, (c)  $\text{Ta}_2\text{O}_5$ , (d)  $\text{Ta}_2\text{O}_5/\text{TaC}$ , (e) TaC.

and 29.3 eV), respectively. In comparison with the high-resolution C 1s spectra of  $\text{Ta}_2\text{O}_5/\text{TaC}$  before and after cycling, the intensity of the O=C-O peak was stronger after cycling (Fig. S10c†). The Ta-O bond for  $\text{Ta}_2\text{O}_5$  (531.8 eV) could also be clearly observed in the spectrum of O 1s (Fig. S10d†). The only peak located at 55.4 eV was ascribed to the Li-O state of  $\text{Li}_2\text{O}$  (Fig. S10e†). The above results confirmed the reversibility of the reaction and the integrity of the electrode before and after cycling. To further demonstrate the structural effect of zero-strain TaC, the cross-sectional SEM was employed to compare the thickness of the electrodes before and after cycling, as shown in Fig. 6d-f. After 50 cycles, the increase in thickness of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  electrode (10%) was significantly reduced relative to the pure  $\text{Ta}_2\text{O}_5$  electrode (44%). Moreover, the TaC electrode exhibited minimal thickness variation of just 2%. These results demonstrated that the zero-strain TaC could reduce the electrode swelling.

Based on the above results, we can conclude that the enhanced electrochemical performance of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode originated from the synergistic effect between the TaC and  $\text{Ta}_2\text{O}_5$  during the charge/discharge process. First, the zero-strain and conductive TaC could boost the conductivity of the whole electrode, thereby reducing the diffusion barrier of  $\text{Li}^+$ . Also, the zero-strain capacity enabled TaC to remit the volume expansion of  $\text{Ta}_2\text{O}_5$  when cycling, which guaranteed the long-term cycling life of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode. Second, the construction of heterostructure led to the formation of an implanted electric field and more delocalized charge transport on the interface. Then, the

transport of charge carriers could be accelerated, ensuring the high-rate performance of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode.

## Conclusion

To sum up, a heterostructured  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode was fabricated as a novel fast-charging anode for LIBs. A reversible solid-solution process and conversion reaction mechanism of the  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode was revealed. The anode achieved a high rate and long-cycle performance. After 1000 cycles, the capacities of  $\text{Ta}_2\text{O}_5/\text{TaC}$  retained  $127.8 \text{ mA h g}^{-1}$  at an ultrahigh current density of  $10 \text{ A g}^{-1}$ , with a low-capacity decay rate of 0.08% per cycle. This could be attributed to the zero-strain and high conductivity of TaC, which enhanced the  $\text{Li}^+$  transport and relieved the volume expansion during charge/discharge. The heterostructure between  $\text{Ta}_2\text{O}_5$  and TaC accelerated the interfacial kinetics, and lowered the charge transfer energy barriers. Additionally, the intercalation-pseudocapacitive behaviour enabled  $\text{Ta}_2\text{O}_5/\text{TaC}$  anode to store additional energy and thus it delivered a high-rate capacity. We believe that these findings open a new avenue in the search for even better anode materials and will help speed up the development of high-rate capacity LIBs for large-scale energy-storage systems.

## Author contributions

Yinhong Gao: conceptualization, investigation, data curation and writing-original draft & editing. Xu Nan: formal analysis, resources and software. Bing Sun: supervision and formal

analysis. Wenli Xu: formal analysis. Qiang Huang: formal analysis. Ye Cong: conceptualization. Yanjun Li: conceptualization. Xuanke Li: project administration. Qin Zhang: validation, project administration and writing-review & editing.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The research was supported by the National Natural Science Foundation of China (No. 51902232). The authors moreover thank Haotang Li for data analysis.

## Notes and references

- 1 L. Zhai, W. Zhang, H. Gong, Y. Li, M. Gao, X. Zhang, D. Li, Y. Zhou, C. Dong, W. Liu, F. Jiang and J. Sun, *Surf. Interfaces*, 2022, **34**, 102299.
- 2 T. Li, J. Sun, S. Gao, B. Xiao, J. Cheng, Y. Zhou, X. Sun, F. Jiang, Z. Yan and S. Xiong, *Adv. Energy Mater.*, 2021, **11**, 2003699.
- 3 T. Kim, W. Song, D. Y. Son, L. K. Ono and Y. Qi, *J. Mater. Chem. A*, 2019, **7**, 2942–2964.
- 4 V. P. H. Huy, S. So, I. T. Kim and J. Hur, *Energy Storage Mater.*, 2021, **34**, 669–681.
- 5 Y. H. Gao, X. Nan, Y. Yang, B. Sun, W. L. Xu, D. L. D. Wandji, X. K. Li, Y. J. Li and Q. Zhang, *New Carbon Mater.*, 2021, **36**, 1–28.
- 6 S. Gao, P. Ju, Z. Liu, L. Zhai, W. Liu, X. Zhang, Y. Zhou, C. Dong, F. Jiang and J. Sun, *J. Energy Chem.*, 2022, **69**, 356–362.
- 7 J. W. Choi and D. Aurbach, *Nat. Rev. Mater.*, 2016, **1**, 1–16.
- 8 N. Mahmood, T. Tang and Y. Hou, *Adv. Energy Mater.*, 2016, **6**, 1600374.
- 9 J. Liu, D. Xie, X. Xu, L. Jiang, R. Si, W. Shi and P. Cheng, *Nat. Commun.*, 2021, **12**, 3131.
- 10 X. Zhang, L. Han, J. Li, T. Lu, J. Li, G. Zhu and L. Pan, *J. Mater. Sci. Technol.*, 2022, **97**, 156–164.
- 11 K. Xu, X. Shen, C. Song, H. Chen, Y. Chen, Z. Ji, A. Yuan, X. Yang and L. Kong, *Small*, 2021, **17**, 2101080.
- 12 X. Zhu, J. Xu, Y. Luo, Q. Fu, G. Liang, L. Luo, Y. Chen, C. Lin and X. Zhao, *J. Mater. Chem. A*, 2019, **7**, 6522–6532.
- 13 J. Ma, X. Guo, H. Xue, K. Pan, C. Liu and H. Pang, *Chem. Eng. J.*, 2020, **380**, 122428.
- 14 M. Sun, Y. Jiang, J. Ni and L. Li, *J. Mater. Sci. Technol.*, 2018, **34**, 1969–1976.
- 15 X. Geng, X. Huang, B. Zhong, Z. Liu, D. Wang and G. Wen, *J. Alloys Compd.*, 2021, **881**, 159920.
- 16 C. Choi, D. S. Ashby, D. M. Butts, R. H. DeBlock, Q. Wei, J. Lau and B. Dunn, *Nat. Rev. Mater.*, 2020, **5**, 5–19.
- 17 K. N. Manukumar, B. Kishore, R. Viswanatha and G. Nagaraju, *J. Solid State Electrochem.*, 2020, **24**, 1067–1074.
- 18 S. Xia, J. Ni, S. V. Savilov and L. Li, *Nano Energy*, 2018, **45**, 407–412.
- 19 L. Pan, H. Huang, T. Liu and M. Niederberger, *Electrochim. Acta*, 2019, **321**, 134645.
- 20 J. Wu, R. Zhao, H. Xiang, C. Yang, W. Zhong, C. Zhang, Q. Zhang, X. Li and N. Yang, *Appl. Catal., B*, 2021, **292**, 120200.
- 21 S. Chen, S. Huang, J. Hu, S. Fan, Y. Shang, M. E. Pam, X. Li, Y. Wang, T. Xu, Y. Shi and H. Y. Yang, *Nano-Micro Lett.*, 2019, **11**, 80.
- 22 S. Zhang, G. Wang, B. Wang, J. Wang, J. Bai and H. Wang, *Adv. Funct. Mater.*, 2020, **30**, 2001592.
- 23 C. Hou, J. Wang, W. Du, J. Wang, Y. Du, C. Liu, J. Zhang, H. Hou, F. Dang, L. Zhao and Z. Guo, *J. Mater. Chem. A*, 2019, **7**, 13460–13472.
- 24 S. Xiao, X. Li, T. Li, Y. Xiang and J. S. Chen, *J. Mater. Chem. A*, 2021, **9**, 7317–7335.
- 25 S. Xiao, X. Li, W. Zhang, Y. Xiang, T. Li, X. Niu, J. S. Chen and Q. Yan, *ACS Nano*, 2021, **15**, 13307–13318.
- 26 L. Wang, F. Zhang, W. Dai, Q. Cheng, L. Lu, K. Zhang, M. Lin, M. Shen and D. Wang, *J. Am. Ceram. Soc.*, 2019, **102**, 6455–6462.
- 27 J. Jiang, S. Wang, W. Li and Z. Chen, *Ceram. Int.*, 2016, **42**, 7118–7124.
- 28 K. N. Manukumar, B. Kishore, K. Manjunath and G. Nagaraju, *Int. J. Hydrogen Energy*, 2018, **43**, 18125–18135.
- 29 Z. W. Cui, X. K. Li, Y. Cong, Z. J. Dong, G. M. Yuan and J. Zhang, *New Carbon Mater.*, 2017, **32**, 205–212.
- 30 A. C. Larson and R. B. Von Dreele, *Report LAUR*, 1994, pp. 86–748.
- 31 C. Di, X. Yan, Y. Yang, W. Ye, M. Zhao and D. Li, *Ceram. Int.*, 2021, **47**, 32766–32774.
- 32 K. Manukumar, R. Viswanatha and G. Nagaraju, *Ionics*, 2020, **26**, 1197–1202.
- 33 M. C. Zhao, J. Zhang, W. Wang and Qi Zhang, *Nanotechnology*, 2021, **32**, 485404.
- 34 G. Luo, Y. Gu, Y. Liu, Z. Chen, Y. Huo, F. Wu, Y. Mai, X. Dai and Y. Deng, *Ceram. Int.*, 2021, **47**, 11332–11339.
- 35 J. Wu, X. Zhang, Z. Li, C. Yang, W. Zhong, W. Li, C. Zhang, N. Yang, Q. Zhang and X. Li, *Adv. Funct. Mater.*, 2020, **30**, 2004348.
- 36 S. Wang, T. Yao, B. Li, Y. Li and Y. Yang, *Mater. Lett.*, 2020, **267**, 127545.
- 37 Q. Wang, H. Yang, T. Meng, J. Yang, B. Huang, F. L. Gu, S. Zhang, C. Meng and Y. Tong, *Energy Storage Mater.*, 2021, **36**, 365–375.
- 38 K. Chang, Z. Wang, G. Huang, H. Li, W. Chen and J. Y. Lee, *J. Power Sources*, 2012, **201**, 259–266.
- 39 X. Li, Q. Xiao, H. Zhang, H. Xu and Y. Zhang, *J. Energy Chem.*, 2018, **27**, 940–948.
- 40 Y. You, X. L. Wu, Y. X. Yin and Y. G. Guo, *J. Mater. Chem. A*, 2013, **1**, 14061–14065.
- 41 K. Lee, S. Shin, T. Degen, W. Lee and Y. S. Yoon, *Nano Energy*, 2017, **32**, 397–407.
- 42 W. Zhang, D. H. Seo, T. Chen, L. Wu, M. Topsakal, Y. Zhu, D. Lu, G. Ceder and F. Wang, *Science*, 2020, **367**, 1030–1034.
- 43 Y. S. Kim, Y. Cho, P. M. Nogaes and S. K. Jeong, *Energies*, 2019, **12**, 2960.