


 Cite this: *RSC Adv.*, 2022, 12, 5245

Solar-driven aromatic aldehydes: green production from mandelic acid derivatives by a Co(II)/C₃N₄ combined catalyst in aqueous media†

 Mi Wu,^a Hongzhao Wang,^a Haifang Mao,^{*a} Chaoyang Wang,^a Zhenbiao Dong,^a Ting Tang,^{*b} Wei Zheng,^a Lehong Jin^a and Jibo Liu^{ib} ^{*a}

According to the requirements for sustainable development, reclaiming fine chemicals from wastewater under mild conditions is an extremely significant line of research. A low-cost and high-efficiency polydentate chelate- and polymeric Co(II)-based complex (Co-L)-loaded C₃N₄ photocatalyst (Co-L/C₃N₄) was constructed and used to convert aromatic mandelic acids in wastewater at room temperature. The BET specific surface area increased from 28 m² g⁻¹ to 68 m² g⁻¹, indicating its excellent absorptive character. The light absorption range of Co-L/C₃N₄ reached 650 nm, while the band energy reduced to 2.30 eV, which caused a significant enhancement in photocatalytic activity. The conversion of substituted mandelic acids was more than 90% due to the photoactivity of Co-L/C₃N₄. Time-resolved PL spectra indicated the remarkable separation of the photogenerated electron-hole pairs in Co-L/C₃N₄. Furthermore, the UV-vis and *in situ* FTIR spectra indicated the formation of aldehyde groups in the selective oxidation process, which provided support for the plausible catalytic mechanism.

Received 10th November 2021

Accepted 27th January 2022

DOI: 10.1039/d1ra08256f

rsc.li/rsc-advances

1 Introduction

In the last few decades, rapid industrial progress, especially in the fine chemicals industry, has dramatically increased the occurrence of chemical-induced water pollution. Mandelic acid and its derivatives (MADs) are such a series of chiral compounds that have attracted much attention due to their wide use in the synthesis of antibiotics, antiobesity and anti-tumor agents, biologically active compounds and enantiomer separation.^{1,2} Due to their superior water solubility, the concentration of MADs is substantial in relevant wastewater, causing serious environmental problems because of their strong negative environmental impact and high toxicity.³ Considering not only environmental pollution improvement but also resource re-utilization, converting MADs into useful chemicals, *i.e.* aromatic aldehydes, is a much more potent alternative to direct mineralization. Aromatic aldehydes, such as *p*-chlorobenzaldehyde, *p*-hydroxybenzaldehyde, 4-hydroxy-3-methoxybenzaldehyde, 4-hydroxy-3-ethoxybenzaldehyde, and

4-hydroxy-3-methoxy-5-methyl-benzaldehyde, have been used as pivotal intermediates in the pharmaceutical, printing and dyeing, pesticide, cosmetic, flame retardant and spice industries.⁴⁻⁷ Typically, *p*-hydroxybenzaldehyde is mainly used to synthesize the cardio-cerebrovascular medicine esmolol, the oral antibiotic amoxicillin, the antibacterial sulfa synergist trimethoxy benzylamine, the anti-hepatic fluke nitroiodophenol nitrile, among others.⁸⁻¹¹

However, due to the outstanding water solubility of MADs, their highly efficient conversion has always been the focus of attention, especially under low MAD concentration.¹² The conversion rate and aromatic aldehyde selectivity of MADs can reach 85% and 70–80%, respectively, when various nanoparticles, such as Bi(0), Co(II), and Cu(II), are employed to catalytically convert MADs in DMSO.¹³⁻¹⁷ During this process, the introduction of organic solvents causes potential environmental problems. Silica-encapsulated Cu–Al hydrotalcite (SECuAlHT) was developed as an efficient catalyst to catalytically oxidize 4-hydroxy-3-methoxymandelic acid in a.q. solution under mild conditions, which gave a 72% yield of 4-hydroxy-3-methoxybenzaldehyde.¹⁸ Without a doubt, the chemical oxidation efficiency towards the substrate was limited under low substrate concentration.

Considering that environmental pollution and the sustainable supply of green energy are the two main global challenges being faced in the current era, photocatalytic selective oxidation technology has become a focus of international attention as it has potential for development.¹⁹⁻²² Photocatalysis has been

^aSchool of Chemical and Environmental Engineering, Shanghai Institute of Technology, 100 Haiquan Road, Shanghai, 201418, China. E-mail: mhj@sit.edu.cn; jiboliu@sit.edu.cn; Tel: +86-21-60877281

^bHangzhou Normal University, College of Medicine, 2318 Yuhangtang Road, Hangzhou, Zhejiang, China. E-mail: tangtinghnu@163.com

† Electronic supplementary information (ESI) available: The SEM, TEM and UV-visible DRS of Co(II)/C₃N₄, the HOMO and LUMO information of the mandelic acid derivatives. See DOI: 10.1039/d1ra08256f



widely used in water splitting, the degradation of organic pollutants, CO₂ conversion, selective organic synthesis, and so on.^{23–26} In order to reclaim useful products from wastewater with low energy consumption and high efficiency, photocatalytic technology has attracted extensive attention due to its advantages of clean and environmentally friendly character derived from the use of solar energy.²⁷ Thanks to the advantageous non-polluting nature and low-energy consumption, heterogeneous photocatalysis has been widely used for the generation of clean energy and catalytic oxidation. Several aromatic aldehydes have been obtained from the corresponding alcohols by employing photocatalytic technology in the water medium at room temperature and atmospheric pressure.²⁸ It has been widely used for the detoxification of water and the air and has become a very promising fine chemical synthesis method in recent years.²⁹ Without a doubt, noble metal catalysts, such as Au, Ru, and Pd, can mediate efficient oxidation reactions due to the low-temperature or preferential oxidation of CO, alcohol oxidation and soot oxidation.³⁰ However, high cost is the dominating disadvantage of noble metal-based catalysts, limiting their large-scale use. Thus, low-cost catalyst construction has immense potential. In recent decades, metal-free semiconductor polymer carbon nitride (C₃N₄) has attracted attention due to its unique and interesting physical and chemical properties, such as high working efficiency under visible and ultraviolet light, strong stability, non-toxicity, non-polluting nature.^{31–34} For further improvement of the photocatalytic activity of C₃N₄, many strategies have been adopted, including doping with different metals, such as palladium, silver, and cobalt.^{35–38} Based on the principles of green sustainable chemistry and engineering, considerable efforts have been made to adjust the catalytic activity of C₃N₄ toward achieving excellent conversion and selectivity in aqueous solutions.³⁹ Simultaneously, metal–organic complexes have attracted the attention of scientists due to their excellent catalytic activity and tunable structure. Considering that C₃N₄ exhibits excellent electron-transition ability due to the π -conjugated system, supporting π -conjugated compounds on C₃N₄ has been used to develop hybrid photocatalysts for selective photocatalytic oxidation in the fields of water splitting and organic synthesis.^{40,41} Especially, the usage of industrial solid waste for organic ligand synthesis can further realize the resource utilization of industrial by-products. For example, 5-aldehyde vanillin (5-AV) is the typical by-product formed during the production of vanillin. The oxhydryl and aldehyde groups make it an abundantly tuneable structure (Scheme 1).

Herein, a polydentate chelate and polymeric metal–organic complex based on 5-AV, a by-product of vanillin, was constructed and doped on the surface of C₃N₄ (Co-L/C₃N₄) to achieve the selective conversion of a variety of substituted mandelic acids to aromatic aldehydes efficiently under mild photocatalytic conditions. The conversion of the substrate reached 96.3% with an 84% selectivity. More importantly, the plausible mechanism for aromatic aldehyde production was investigated by employing *in situ* IR and UV-vis spectroscopy.

2. Experimental details

2.1 Reagents and instruments

All materials were of AR grade. Melamine, CoCl₂·6H₂O, 1,3-diaminopropane, mandelic acid, 4-chloromandelic acid, 4-hydroxy-3-methoxymandelic acid, 4-hydroxy-3-ethoxymandelic acid, 4-hydroxy-3-methoxy-5-methylmandelic acid and ethanol were purchased from Sinopharm Chemical Reagent Co., Ltd., China. All the mentioned chemicals were directly used without additional purification. 5-Aldehyde vanillin was purchased from Jiaying Zhonghua Chemical Co., Ltd.


2.2 Experimental method

2.2.1 Preparation of Co-L/C₃N₄. The synthesis process of C₃N₄ was according to a previously reported method: melamine (0.1 mol, 12.6 g) was added to a ceramic crucible and heated to 550 °C at a ramping rate of 3 °C min⁻¹ and held at 550 °C for 4 h. After cooling it to room temperature, 220 mg C₃N₄ was collected as a light-yellow solid.

Then, 5-aldehyde vanillin (5.5 mmol, 1.0 g) and 1,3-diaminopropane (5.5 mmol, 0.41 g) were completely dissolved in ethanol (30 mL) under vigorous stirring at 75 °C and refluxed for 4 h. After it cooled down to room temperature, the solvent was evaporated to give ligand (L) as a white solid. The ligand (219 mg, 1 mmol) and CoCl₂·6H₂O (238 mg, 1 mmol) were added to EtOH (10 mL) and heated to 80 °C for 3 hours. After they cooled down to room temperature, the solvent was removed in a vacuum to get the Co(II) complex (Co-L). A certain amount of Co-L was mixed with C₃N₄ uniformly and calcined at 500 °C for 2 hours to obtain the Co/C₃N₄ catalyst (0.05 g Co-L mixed with 1 g C₃N₄ is denoted as Co-L/C₃N₄-5).

2.2.2 Photocatalytic conversion performance of by Co-L/C₃N₄. The typical procedure for testing the photocatalytic conversion performance was as follows: the freshly prepared catalyst (Co/C₃N₄ 0.1 g) was added to an aqueous solution of mandelic acid (100 mL, 1.0%). After the pH value was adjusted to 11 using aqueous NaOH (30%), the mixture was bubbled with O₂ under constant stirring at room temperature. Simultaneously, the mixture was irradiated with a 500 W Xe lamp for 5 hours, and the residual material was determined by HPLC. The pH value of the mixture was adjusted to 3.0–3.5 by using 6 M HCl. The mixture was washed with EtOAc (50 mL × 3). The combined organic layers were washed with brine, dried over MgSO₄, filtered and concentrated to give the crude product. The residue was purified by silica gel chromatography (petroleum ether/EtOAc = 10 : 1 to 1 : 1) to give the product as a white solid (0.563 g, yield 77.6%). ¹H-NMR (DMSO-d₆, 600 MHz) δ : 9.39 (s, 1H), 7.19 (d, *J* = 12.00 Hz, 2H), 6.72 (d, *J* = 12.00 Hz, 2H), 5.62 (s, 1H), 4.90 (s, 1H). The structure and ¹H NMR spectra of the products are shown in Fig. S1.†

2.2.3 Characterization of the C₃N₄ and Co-L/C₃N₄. X-ray data from suitable single crystals were collected at 293 K on a Focus D8 (Bruker, Germany) with Cu K α radiation (λ = 0.1542 nm). Fourier transform infrared spectroscopy (FT-IR) was performed by using a Thermo Nicolet IS5. The X-ray photoelectron spectroscopy (XPS) experiments were conducted on a Thermo

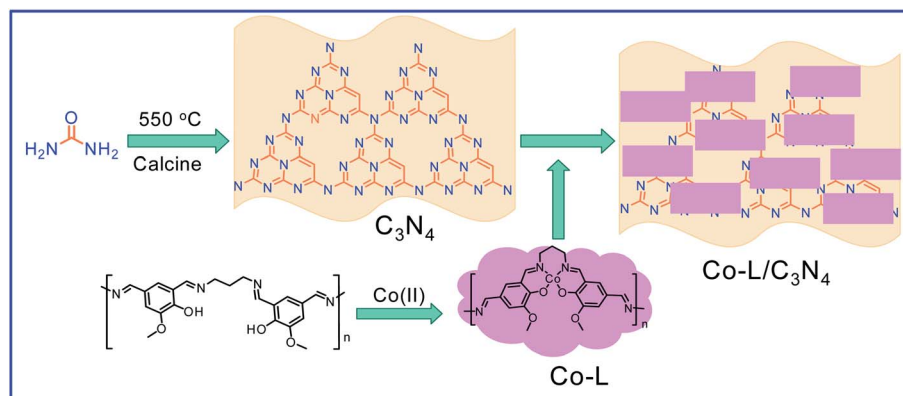

Scheme 1 The synthetic process of the Co-L/C₃N₄ composite catalyst.

Escalab 250 Xi system using Al-K α radiation ($h\nu = 1486.6$ eV). The Brunauer–Emmett–Teller (BET) specific surface areas of the typical products were obtained at 77 K on a Micromeritics ASAP 2020 system. The UV-vis spectra were recorded on a UV-3900 spectrophotometer. A high-pressure mercury lamp (PLS-LAM500) and high-performance liquid chromatography (HPLC-Ulti Mate 3000, Thermo Fisher Scientific) were employed to detect material conversion. *In situ* ATR-FTIR spectroscopy was carried out on a Mettler Toledo Reactir-15.

3 Results and discussion

3.1 Excellent catalytic performance of the Co-L/C₃N₄ combined catalyst

As a representative, 4-hydroxyphenylglycolic acid (HPA) was employed as the model material to investigate the catalytic activity of the catalyst. In order to investigate the reaction clearly, the factors affecting the reactivity were considered one by one. Firstly, the catalytic activity caused by different catalyst loads was examined under typical conditions. As shown in Fig. 1a, in the presence of pure C₃N₄, the conversion ratio of HPA and the yield of 4-hydroxybenzaldehyde (HBD) were only 46.7% and 38.9%, respectively, indicating the mediocre catalytic activity of C₃N₄. When Co was loaded on pure C₃N₄ by

employing an inorganic Co salt, such as CoCl₂·6H₂O, the conversion rate of HPA and the yield of HPB were 72.3% and 66.4%, respectively. This might be due to the agglomeration of the Co unit in the prepared catalyst. Co-L could be attached on the surface of C₃N₄ due to the π - π interactions, which avoided the agglomeration effectively. Furthermore, other types of Co sources were also introduced to be compared with Co-L-attached C₃N₄. As shown in Fig. S2,[†] the conversion of HPA ranged from 30% to 72% in the presence of other Co sources. With Co-L loaded on C₃N₄, the conversion of HPA and the yield of HBD increased rapidly, reflecting the excellent catalytic activity of Co-L/C₃N₄. The catalytic efficiency of Co-L/C₃N₄ was affected by the loading ratio of Co-L. As shown in Fig. 1a, HPA conversion increased from 87.8% to 94.0% when the Co-L loading amount increased from 5% to 20%. However, the highest yield of HBD reached was 77.6% in the presence of 10% Co-L/C₃N₄. This might be caused by the overoxidation of the obtained aldehyde in the presence of excess Co-L. Furthermore, the HPA conversion, HBD yield and selectivity corresponding to the repeated use of Co-L/C₃N₄-10 for 5 cycles are summarized in Fig. 1b. The photocatalytic activity of Co-L/C₃N₄-10 toward HBD formation hardly reduced after recycling over five runs, and the yield rate was maintained at 75%. Simultaneously, the catalyst was recovered after the reaction and characterized. The XRD

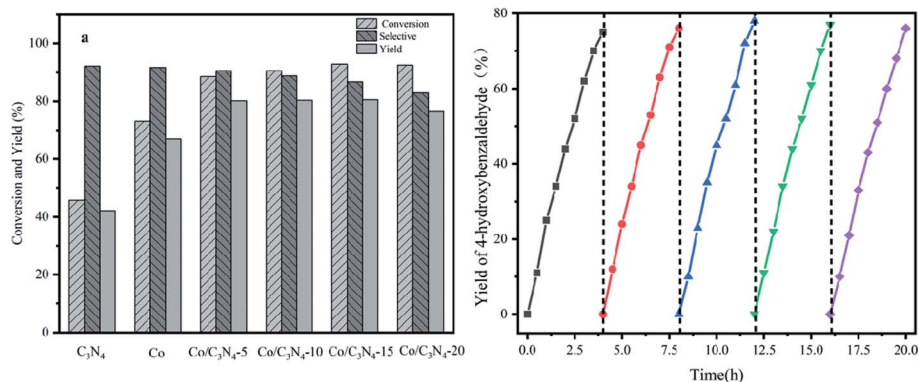


Fig. 1 (a) The catalytic activity of 4-hydroxybenzaldehyde conversion with different Co-L/C₃N₄ ratios. (b) The yields of 4-hydroxybenzaldehyde under the catalytic action of Co-L/C₃N₄-10 over 5 continuous cycles.

and FT-IR, spectra, as well as TEM and SEM images, suggested that the catalyst underwent no obvious change compared with the freshly prepared catalyst, which indicated the superior stability and good photocatalytic performance of Co-L/C₃N₄-10 during the degradation process, as shown in Fig. S3† (Table 1)

3.2 Characterization of the prepared Co-L/C₃N₄ composite catalyst

SEM and TEM were employed to investigate the morphology of the C₃N₄ catalyst. The obtained C₃N₄ presented a thin layered structure with folds that looked like a layer of tulle, confirming that it had a porous structure. Concurrently, the numerous mesopores on the surface of the Co-L/C₃N₄ composite catalyst displayed a structure with in-plane pores (as shown in Fig. S4†). As shown in Fig. S3c,† the chiffon-like structures with wrinkles and rippled edges were indexed to the C₃N₄ phase, and some large aggregates of irregular shape were evidently found in the field of vision, which suggested the possible coexistence of both phases and the coverage of C₃N₄ by the Co-L phase.

The crystalline structures of C₃N₄ and Co-L/C₃N₄ were examined by X-ray diffraction (XRD). As shown in Fig. 2a, the peaks at 13.5° and 27.2° were ascribed to the reflections of the (100) and (002) planes of C₃N₄, respectively.⁴² Interestingly, the peaks at 13.5° and 27.2° barely appeared in Co-L/C₃N₄, and these peaks became sharper and more obvious with the gradual increase in the Co-L ligand content, reflecting the enhanced crystallinity of the Co-L/C₃N₄ structure.^{36,43} The XRD results further confirmed the successful preparation and high stability of the Co-L/C₃N₄ heterostructure.⁴⁴ In addition, the FT-IR

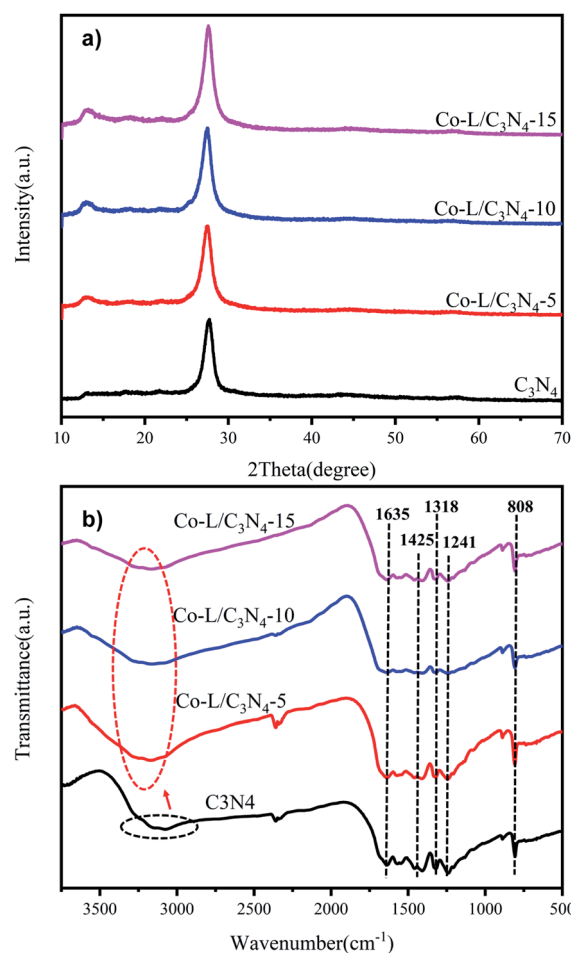












Fig. 2 (a) X-ray diffraction (XRD) patterns of C₃N₄ and Co-L/C₃N₄; (b) FT-IR spectra of C₃N₄ and Co-L/C₃N₄.

Table 1 Comparison of the conversion of different substrates to corresponding aromatic aldehydes by Co-L/C₃N₄-10

Entry	Substrate	Product	Conv. (%)	Sel. (%)	Yield (%)
1			93.1	83.4	77.6
2			92.2	84.6	78
3			90.7	84.4	76.6
4			85.4	84.8	72.4
5			68.5	62.6	42.9

spectra of the C₃N₄ and Co-L/C₃N₄ samples (Fig. 2b) exhibited some strong absorption peaks at 808 cm⁻¹, which was the characteristic vibration of the out-of-plane bending of the triazine rings. The peaks at 1200–1650 cm⁻¹ were attributed to the C–N and C=N heterocycles, and those between 3000–3500 cm⁻¹ could be assigned to the N–H/O–H groups. Interestingly, Co-L/C₃N₄ had a characteristic band similar to C₃N₄, indicating that the typical graphite structure of the carbonitride was not destroyed after Co-L doping. However, the peak at around 3100–3400 cm⁻¹ was much narrower than that in the C₃N₄ spectrum, while the intensity was much greater, which is completely consistent with the description in the literature.^{45–47}

To further investigate the surface microstructure of Co-L on the C₃N₄ nanoparticles, XPS (X-ray photoelectron spectroscopy) characterization was employed to investigate the constitution of the C₃N₄ and Co-L/C₃N₄-10 photocatalysts. As shown in Fig. 3a, both the C₃N₄ and Co-L/C₃N₄ samples consisted of C and N elements. Furthermore, a peak for Co appeared in the Co-L/C₃N₄ photocatalyst. In the high-resolution XPS analysis, the C 1s (Fig. 3b) deconvoluted peaks were centred at 284.5, 286.2 and 288.1 eV.^{48,49} The peak at 284.5 eV was ascribed to the physically adsorbed carbon species or the sp² C–C bonds, and the peak at

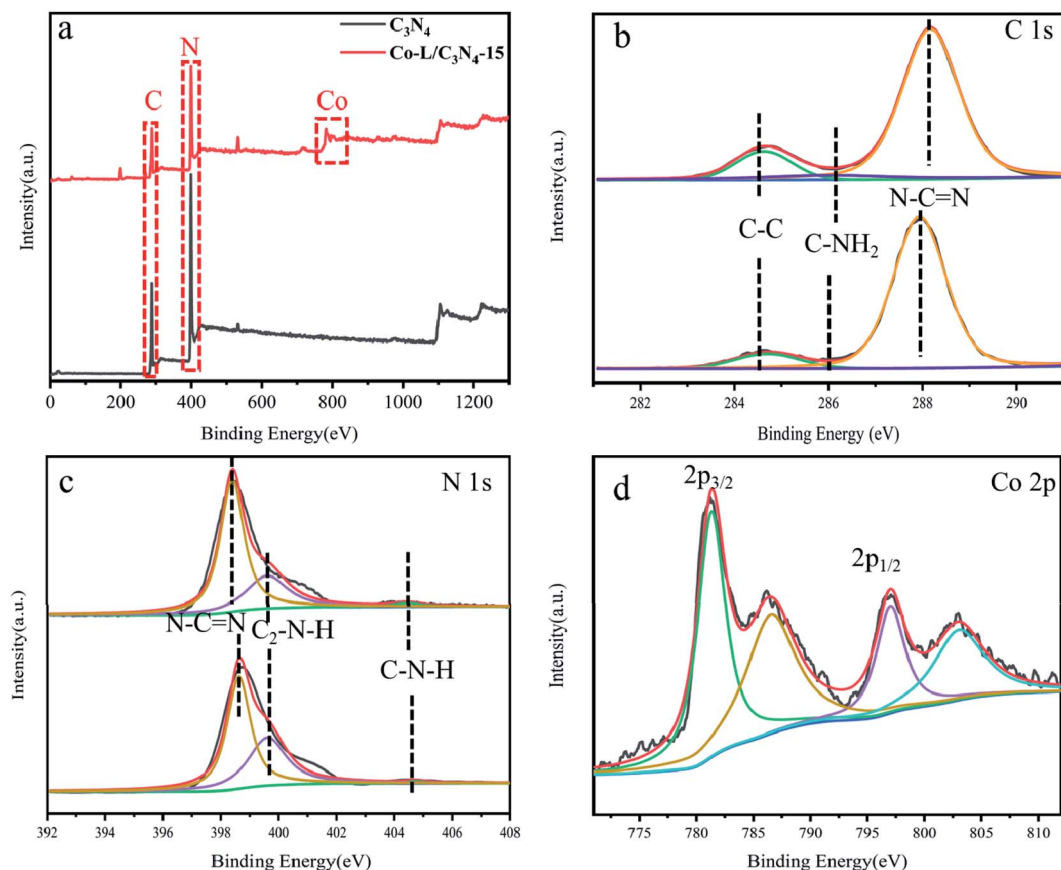


Fig. 3 (a) X-ray photoelectron spectroscopy (XPS) of C_3N_4 and Co-L/ C_3N_4 -15; (b–d) high-resolution XPS spectra of C 1s, N 1s and Co 2p.

286.2 eV was assigned to the C-NH₂ species, while the strong peak at 288.1 eV could be attributed to N-C=N. The three peaks at binding energies 398.6, 400.4 and 404.5 eV could be attributed to the triazine rings N-C=N, C₂-N-H and C-N-H, respectively (as shown in Fig. 3c), which belong to the typical N 1s peaks in C_3N_4 .^{50–53} In the high-resolution XPS analysis, the Co 2p peak at (Fig. 3d) the binding energy of 781.2 and 796.2 eV could be attributed to the Co(II) state in the form of Co-N. This indicated that the valence state of the Co ion in Co-L/ C_3N_4 was Co(II) rather than Co(III). As shown in Fig. S5,† the Co 2p spectrum could be divided into Co²⁺ and Co³⁺ fitting curves, and four shakeup satellites. The fitting peaks at 782.5 and 797.4 eV could be grouped to Co³⁺, whereas the peaks at 779.5 and 794.5 eV were assigned to Co²⁺.^{38,54–56}

The N₂ adsorption–desorption isotherms and pore size distribution curves of C_3N_4 and Co-L/ C_3N_4 -10 were recorded by the BET method, as shown in Fig. 4. All the prepared samples exhibited typical type IV isotherms and H3 hysteresis loops (Fig. 4a), implying the remarkable mesoporous properties of the materials.⁵⁷ As a typical porous material, the specific surface area of C_3N_4 was 28 m² g⁻¹. As expected, the specific surface area of all the catalysts increased from 28 m² g⁻¹ to 86 m² g⁻¹ following the addition of 15% Co-L. The increase in specific surface area after Co doping was mainly due to the rich pore structure. As shown in Fig. 4b, the pore size and pore volume of the Co-L/ C_3N_4 catalyst were larger than those of C_3N_4 .⁵⁸

The optical properties of the as-prepared photocatalysts were characterized by UV-vis diffuse reflectance spectroscopy (DRS). The DRS curves of the as-prepared C_3N_4 and Co-L/ C_3N_4 samples are shown in Fig. 5a; C_3N_4 showed an absorption edge at ~450 nm, suggesting its limited photo-response to visible light. More importantly, the absorption edge of Co-L/ C_3N_4 was obviously red-shifted in comparison with C_3N_4 .⁵⁹ The optical absorption intensity of Co-L/ C_3N_4 was significantly enhanced in the range of 550–650 nm. These results describe that Co doping facilitates secondary absorption in the visible light region, which would promote absorption in the wider range of visible light and the absorption efficiency of the system, resulting in higher photocatalytic activity.^{60,61} To further investigate the effect of Co doping on the optical bandgap energy of Co-L/ C_3N_4 , the Kubelka–Munk method was used to calculate the bandgap of the prepared samples.⁶² As shown in Fig. 5b, the presence of the Co-L ligand slightly reduced the energy band of C_3N_4 . The results show that the Co-L ligand presented a good optical response in the whole visible wavelength range (E_g of Co-L was about 1.85 eV, as shown in Fig. S6†). At the same time, the optical response intensity of the Co-L/ C_3N_4 hybrid material was significantly stronger than that of ordinary C_3N_4 . With an increase in Co-L ligand content, the fluorescence intensity increased gradually, especially in the range of 550–650 nm. This phenomenon showed that the introduction of Co-L effectively improved the light absorption ability of the C_3N_4 material.⁶³

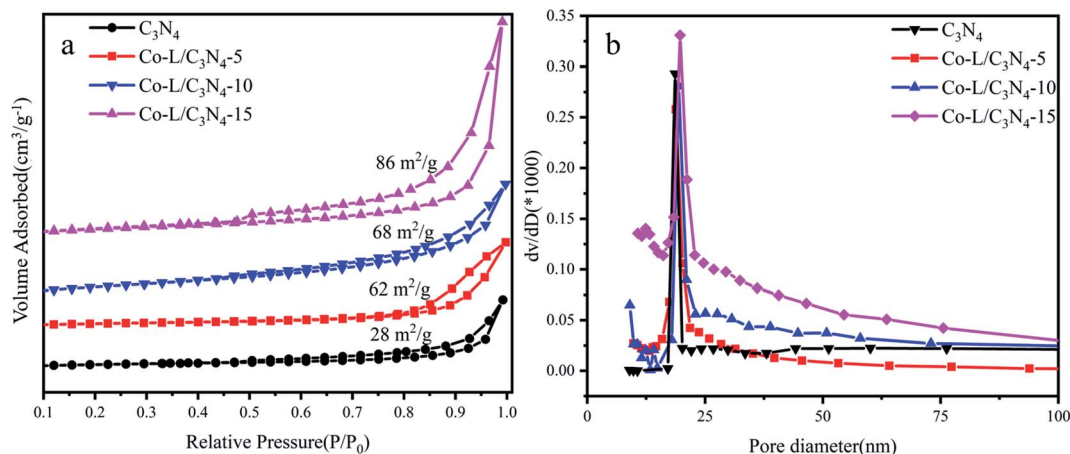


Fig. 4 (a) N_2 adsorption–desorption isotherms of C_3N_4 and Co-L/ C_3N_4 ; (b) the corresponding pore size distribution curves of C_3N_4 and Co-L/ C_3N_4 .

As shown in Fig. S7,[†] the Mott–Schottky plot was obtained in aqueous solutions containing 0.1 M KCl at pH = 7.0 to estimate the EFB of Co-L and C_3N_4 , respectively. The values of EFB were estimated to be -0.86 V and -0.97 (vs. NHE) for Co-L and C_3N_4 , respectively. Compared with C_3N_4 , a positive shift in the EFB of Co-L demonstrated a decrease in the bending of the band edge, thus facilitating electron transfer.⁶⁴ The reason for the improvement in the photocatalytic activity of the Co-L/ C_3N_4 nanocomposites was investigated by photochemical experiments. As shown in Fig. 6a, the photocurrent responses of C_3N_4 were much lower than that of Co-L combined C_3N_4 due to the rapid recombination of the photoexcited e^- and h^+ . However, the photocurrent intensity increased dramatically along with the introduction of Co-L, and the Co-L/ C_3N_4 -15 catalyst exhibited the highest photocurrent density, which is consistent with the steady-state PL results. The obvious changes in the current response of the Co-L/ C_3N_4 samples under irradiation indicated the good photo-harvesting capability of the prepared samples. Moreover, after several switching cycles, the photo-response was basically stable, further indicating the strong light

corrosion resistance of the nanocomposites.^{65,66} At the same time, it was observed that the transient current between the lamps decreased, which may be caused by the accumulation of charges before the lamp is turned on. The photoelectric response was closely related to the content of Co ions. The photocurrent of Co-L/ C_3N_4 -15 was 3 times that of C_3N_4 , which indicated the excellent photo-response of the composite nanomaterial. For nano-photocatalysts, reducing the interfacial resistance can promote charge transfer and thus improve photocatalytic performance.⁶⁷ The interfacial properties of semiconductors are usually studied by electrochemical impedance spectroscopy (EIS).⁶⁸ The interfacial resistance of the sample is expressed by the radius of the semicircle in the EIS.⁶⁹ As shown in Fig. 6b, the radius of the C_3N_4 curve is larger than those of the Co-L loaded catalysts, and the radius of the semicircle decreases obviously after the introduction of Co ions, indicating that the addition of Co-L clearly reduces the resistance at the C_3N_4 interface. The interface of the Co-L/ C_3N_4 -15 composite nanomaterials had minimum resistance, which is consistent with the results of the photocurrent.

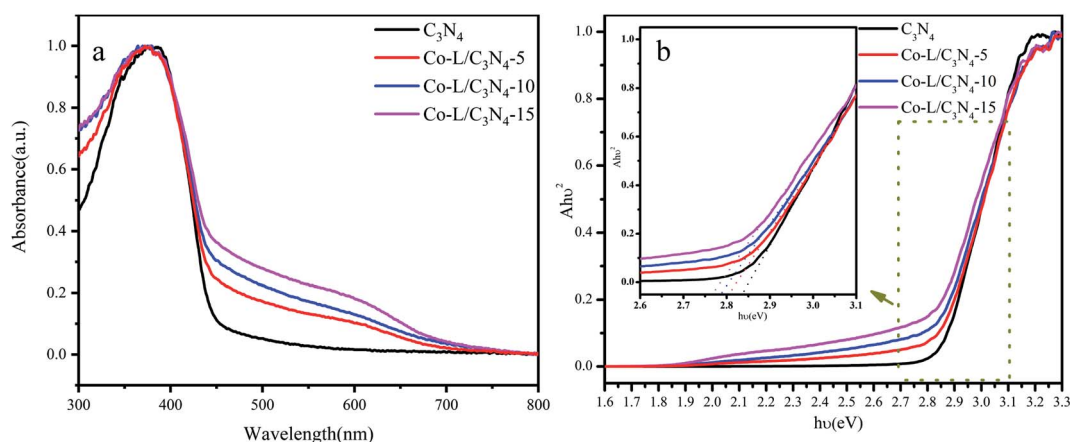


Fig. 5 (a) The UV-visible diffuse reflectance spectra of C_3N_4 and Co-L/ C_3N_4 ; (b) the bandgap energy of C_3N_4 and Co-L/ C_3N_4 .

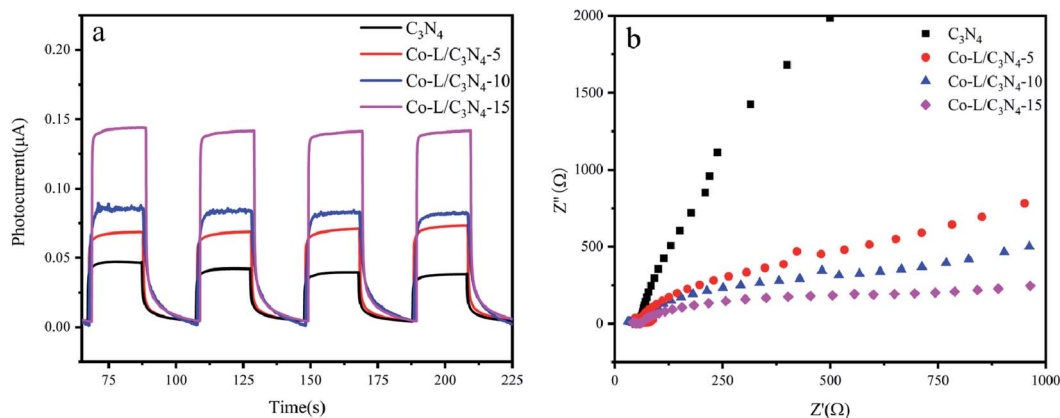


Fig. 6 (a) Transient photocurrent response of C_3N_4 and Co-L/ C_3N_4 ; (b) electrochemical impedance spectra of C_3N_4 and Co-L/ C_3N_4 .

Fluorescence spectroscopy is an effective method to investigate the efficiency of photogenerated electron–hole separation in semiconductors.⁷⁰ The fluorescence spectra of C_3N_4 and Co-L/ C_3N_4 were measured at the same excitation wavelength ($\lambda_{\text{ex}} = 390$ nm). As shown in Fig. 7a, C_3N_4 showed a strong fluorescence peak near 455 nm. After Co-L was loaded on C_3N_4 , the fluorescence peak intensity of Co-L/ C_3N_4 decreased significantly, indicating effectively suppressed recombination of the photogenerated charges. Furthermore, the photogenerated electron–hole recombination is also the critical factor to improving the photocatalytic oxidation efficiency. As shown in Fig. 7b, to further study the behaviour of the charge carriers in

the samples, the time-resolved PL spectra were recorded, and the results are shown in Fig. 7b. C_3N_4 afforded a shorter average fluorescence lifetime (3.07 ps) compared with the Co-L/ C_3N_4 (5.79 ps), which fully implied that the activated state in Co-L/ C_3N_4 was long-lived than that in C_3N_4 . The longer lifetime of electrons could be attributed to the remarkable separation of the photogenerated electron–hole pairs.^{71–73}

3.3 Probable mechanism of aromatic aldehyde production by Co-L/ C_3N_4

In order to investigate the mechanism of 4-hydroxyphenylglycolic acid oxidation, the probable reaction pathway was explored by employing *in situ* FTIR and UV absorption spectroscopy.

The IR spectra of 4-hydroxybenzaldehyde and 4-hydroxyphenylglycolic acid in water were collected from a series of undersaturated solutions with known solute concentrations. To exhibit the reaction clearly, the differential absorption (ΔA) data was collected and processed, as shown in Fig. 8a. Peaks pointing down indicated bands disappearing, while those pointing up corresponded to new bands appearing due to the catalytic reaction. The increased intensity of the ΔA value at 1650 cm^{-1} was vested to the band of C=O stretching vibration, which represents the generation of 4-hydroxybenzaldehyde by oxidation of benzyl alcohol in 4-hydroxyphenylglycolic acid.⁷⁴ At the same time, the increased ΔA peaks at 1245 and 1170 cm^{-1} (as shown in Fig. 8b) belonged to the C–C stretching vibration and the conjugation of aromatic ketones following the 4-hydroxybenzaldehyde ketonic acid generation.⁷⁵ The peaks at 1520 cm^{-1} and 1480 cm^{-1} were attributed to the intermediates of the conversion of 4-hydroxyphenylglycolic acid to ketonic acid. The peak at 1020 cm^{-1} was attributed to the C–C stretching vibration. The decline in the peaks was attributed to the probable fracture of C–C caused by the decarboxylation of the intermediate ketonic acid.⁷⁶ UV-visible spectroscopy was an important method to study the oxidation of 4-hydroxymandelic acid to 4-hydroxybenzaldehyde. As shown in Fig. S8,[†] the decrease in the strong absorption peak at 249 nm could be attributed to the π – π^* transition of the benzene ring. The

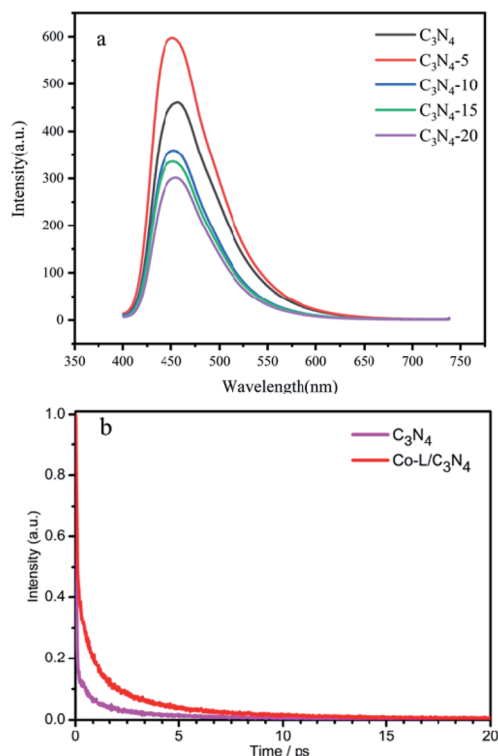


Fig. 7 (a) The PL spectra of C_3N_4 and different ratios of Co-L/ C_3N_4 . (b) The transient fluorescence spectra of C_3N_4 and Co-L/ C_3N_4 .

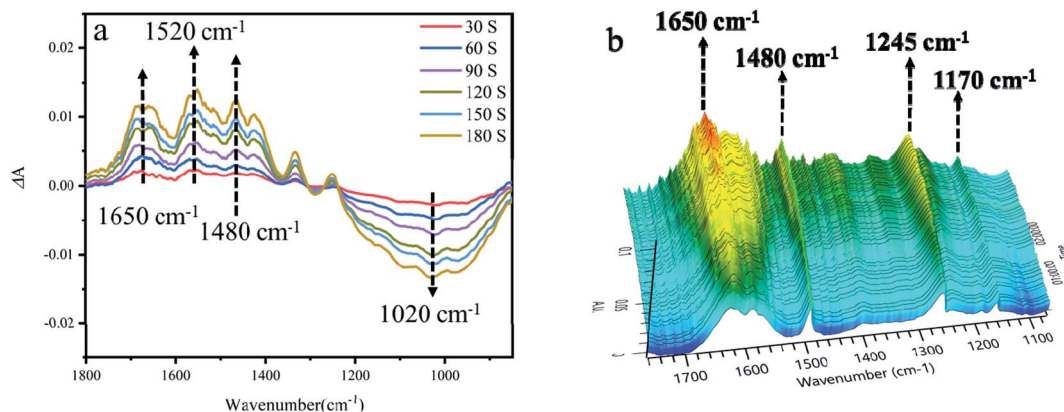


Fig. 8 (a) The 2D *in situ* FTIR spectra of 4-hydroxyphenylglycolic acid oxidation under irradiation. (b) The 3D *in situ* FTIR spectra of 4-hydroxyphenylglycolic acid oxidation under irradiation.

absorption peak at 332 nm was attributed to the $n-\pi^*$ transition of the aldehyde oxygen atom. The changes in the UV-visible spectrum indicated the transformation of 4-hydroxymandelic acid to 4-hydroxybenzaldehyde clearly under irradiation.

On the basis of the above results, a plausible mechanism for the catalytic process has been proposed, as shown in Fig. 9. The Co-L loaded to C_3N_4 significantly enhances the visible light absorption, which has been proven by the UV-Vis and PL valence band spectra analysis. Therefore, under visible light irradiation, electrons are excited to the conduction band from the valence band of C_3N_4 , with the holes staying on the valence band simultaneously.⁷⁷⁻⁷⁹ The electrons in the conduction band of Co-L/ C_3N_4 can be trapped by electrophilic O_2 to produce superoxide radical anions ($^{\cdot}O_2^-$).^{80,81} On the other hand, the transition of Co^{2+}/Co^{3+} ensures the generation of $^{\cdot}O_2^-$, which causes the substrate oxidation reaction. The high concentration of $^{\cdot}O_2^-$ is captured by *p*-hydroxymandelic acid and further experiences the hydroxylation process to give OH^- finally. The deprotonated *p*-hydroxymandelic acid forms the pivotal intermediate (α -keto carboxylate radical) to accomplish the oxidation process. Simultaneously, *p*-hydroxybenzaldehyde is generated following the decarboxylation of the pivotal intermediate. The continuously generated $^{\cdot}O_2^-$ radicals greatly

promote the conversion rate of *p*-hydroxymandelic acid in the photocatalytic process.

4 Conclusions

In conclusion, a Co-L/ C_3N_4 composite photocatalyst was designed and prepared for high-efficiency aromatic aldehyde generation under normal temperature and pressure, with oxygen as the oxidant. The Co-L-loaded C_3N_4 could accelerate the separation of the photogenerated carriers and significantly improve photocatalytic activity. Under ultraviolet light irradiation, the conversion of *p*-hydroxybenzaldehyde was 93.1%, which is 2 times higher than that achieved with pure C_3N_4 . The enhanced photocatalytic activity is attributed to the synergistic effect of Co-L and C_3N_4 , which promote the remarkable separation of the photogenerated electron-hole pairs and charge transfer. This work provides a useful strategy for aromatic aldehyde production in wastewater containing substituted mandelic acid derivatives, thus promoting the recycling of waste resources.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We acknowledge the financial support from the National Natural Science Foundation of China (No. 21906105), Collaborative Innovation Center of Fragrance Flavour and Cosmetics, Shanghai Chenguang Program (20CG66) and Shanghai Sailing Program (21YF1446600).

Notes and references

- 1 P. Intasian, K. Prakinee, A. Phintha, D. Trisrivirat, N. Weeranoppanant, T. Wongnate and P. Chaiyen, *Chem. Rev.*, 2021, **121**, 10367–10451.

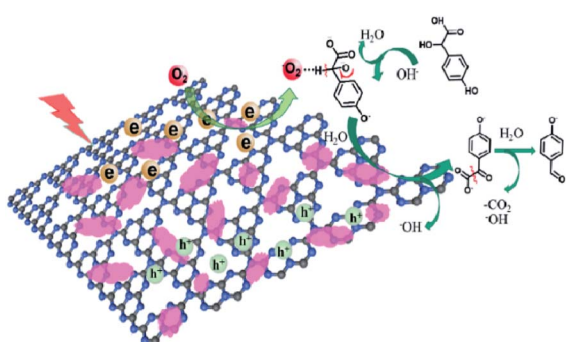


Fig. 9 Proposed mechanism for *p*-hydroxymandelic acid photo-oxidation by Co-L/ C_3N_4 .

- 2 Z. Tang, Z. Tong, Z. Xu, C. T. Au, R. Qiu and S. Yin, *Green Chem.*, 2019, **21**, 2015–2022.
- 3 Y. Hajizadeh, H. Teiri, S. Nazmara and I. Parseh, *Environ. Sci. Pollut. Res.*, 2018, **25**, 6656–6667.
- 4 G. Li, Y. Yan, P. Zhang, X. Xu and Z. Jin, *ACS Catal.*, 2021, **11**, 10460–10466.
- 5 H. Mao, H. Wang, T. Tang, Q. Shi, H. Yu, X. Hu, Z. Xiao, P. Zhang and J. Liu, *Sustainable Energy Fuels*, 2021, **5**, 1158–1170.
- 6 O. Negishi, K. Sugiura and Y. Negishi, *J. Agric. Food Chem.*, 2009, **57**, 9956–9961.
- 7 H. Pfukwa, C. Coetzee, J. Johani, A. Carstens, A. Lederer and H. Pasch, *ACS Appl. Polym. Mater.*, 2021, **3**, 3941–3952.
- 8 D. C. Waddell and J. Mack, *Green Chem.*, 2009, **11**, 79–82.
- 9 Q. Meng, J. Yan, R. Wu, H. Liu, Y. Sun, N. Wu, J. Xiang, L. Zheng, J. Zhang and B. Han, *Nat. Commun.*, 2021, **12**, 4534.
- 10 F. Wang, G. Y. Yang, W. Zhang, W. H. Wu and J. Xu, *Chem. Commun.*, 2003, **10**, 1172–1173.
- 11 H. Mao, H. Wang, X. Hu, P. Zhang, Z. Xiao and J. Liu, *ACS Omega*, 2020, **5**, 8794–8803.
- 12 X. Zhang, R. Dai, H. Sun, Y. Zhang, D. Liu, M. Wang, M. Sun and H. Yu, *Mater. Chem. Front.*, 2020, **4**, 222–230.
- 13 C. Xie, L. Lin, L. Huang, Z. Wang, Z. Jiang, Z. Zhang and B. Han, *Nat. Commun.*, 2021, **12**, 4823.
- 14 I. Favier and E. Duñach, *Tetrahedron*, 2003, **59**, 1823–1830.
- 15 I. Favier, F. Giulieri, E. Duñach, D. Hébrault and J. R. Desmurs, *Eur. J. Org. Chem.*, 2002, 1984–1988.
- 16 I. Favier, E. Duñach, D. Hébrault and J. R. Desmurs, *New J. Chem.*, 2004, **28**, 62–66.
- 17 J. A. Jiang, C. Chen, J. G. Huang, H. W. Liu, S. Cao and Y. F. Ji, *Green Chem.*, 2014, **16**, 1248–1254.
- 18 S. L. Bhanawase and G. D. Yadav, *Ind. Eng. Chem. Res.*, 2017, **56**, 12899–12908.
- 19 M. Fache, B. Boutevin and S. Caillol, *ACS Sustainable Chem. Eng.*, 2015, **4**, 35–46.
- 20 V. Augugliaro, G. Camera-Roda, V. Loddo, G. Palmisano, L. Palmisano, F. Parrino and M. A. Puma, *Appl. Catal., B*, 2012, **111**, 555–561.
- 21 H. Zhang, X. Yong, J. Zhou, J. Deng and Y. Wu, *ACS Appl. Mater. Interfaces*, 2016, **8**, 2753–2763.
- 22 A. W. Pacey, P. Ding, M. Garrett, G. Sheldrake and A. W. Nienow, *Ind. Eng. Chem. Res.*, 2013, **52**, 8361–8372.
- 23 Y. Nosaka and A. Y. Nosaka, *Chem. Rev.*, 2017, **117**, 11302–11336.
- 24 C. Gao, J. Wang, H. Xu and Y. Xiong, *Chem. Soc. Rev.*, 2017, **46**, 2799–2823.
- 25 X. Liu, X. Duan, W. Wei, S. Wang and B. J. Ni, *Green Chem.*, 2019, **21**, 4266–4289.
- 26 R. Ma, W. Chen, L. Wang, X. Yi, Y. Xiao, X. Gao, J. Zhang, X. Tang, C. Yang, X. Meng, A. Zheng and F. S. Xiao, *ACS Catal.*, 2019, **9**, 10448–10453.
- 27 S. Yurdakal, G. Palmisano, V. Loddo, V. Augugliaro and L. Palmisano, *J. Am. Chem. Soc.*, 2008, **130**, 1568–1569.
- 28 M. Zhang, Q. Wang, C. Chen, L. Zang, W. Ma and J. Zhao, *Angew. Chem., Int. Ed.*, 2009, **48**, 6081–6084.
- 29 X. Wu, N. Luo, S. Xie, H. Zhang, Q. Zhang, F. Wang and Y. Wang, *Chem. Soc. Rev.*, 2020, **49**, 6198–6223.
- 30 H. Huang, W. Ye, C. Song, Y. Liu, X. Zhang, Y. Shan, Y. Ge, S. Zhang and R. Lu, *J. Mater. Chem. A*, 2021, **9**, 14710–14721.
- 31 W. J. Ong, L. L. Tan, Y. H. Ng, S. T. Yong and S. P. Chai, *Chem. Rev.*, 2016, **116**, 7159–7329.
- 32 F. Guo, B. Hu, C. Yang, J. Zhang, Y. Hou and X. Wang, *Adv. Mater.*, 2021, 2101466.
- 33 H. Niu, W. Zhao, H. Lv, Y. Yang and Y. Cai, *Chem. Eng. J.*, 2021, **411**, 128400.
- 34 Y. Li, S. Wang, W. Chang, L. Zhang, Z. Wu, R. Jin and Y. Xing, *Appl. Catal., B*, 2020, **274**, 119116.
- 35 J. Shi, T. Yuan, R. Wang, M. Zheng and X. Wang, *Green Chem.*, 2021, **23**, 3945–3949.
- 36 Y. Li, S. Zhu, Y. Liang, Z. Li, S. Wu, C. Chang, S. Luo and Z. Cui, *Appl. Surf. Sci.*, 2021, **536**, 147743.
- 37 T. Yuan, M. Zheng, M. Antonietti and X. Wang, *Chem. Sci.*, 2021, **12**, 6323–6332.
- 38 B. C. He, C. Zhang, P. P. Luo, Y. Li and T. B. Lu, *Green Chem.*, 2020, **22**, 7552–7559.
- 39 C. Xiao, L. Zhang, H. Hao and W. Wang, *ACS Sustainable Chem. Eng.*, 2019, **7**, 7268–7276.
- 40 D. F. Niu, H. C. Li and X. S. Zhang, *Tetrahedron*, 2013, **69**, 8174–8177.
- 41 W. Fu, L. Yue, X. Duan, J. Li and G. Lu, *Green Chem.*, 2016, **18**, 6136–6142.
- 42 P. Sharma and Y. Sasson, *Green Chem.*, 2019, **21**, 261–268.
- 43 Z. Zhu, X. Tang, T. Wang, W. Fan, Z. Liu, C. Li, P. Huo and Y. Yan, *Appl. Catal., B*, 2019, **241**, 319–328.
- 44 X. Li, J. Hu, T. Yang, X. Yang, J. Qu and C. M. Li, *Nano Energy*, 2022, **92**, 107614.
- 45 L. Zhang, F. Mao, L. R. Zheng, H. F. Wang, X. H. Yang and H. G. Yang, *ACS Catal.*, 2018, **8**, 11035–11041.
- 46 F. Chang, J. Zheng, F. Wu, X. Wang and B. Deng, *Colloids Surf., A*, 2019, **563**, 11–21.
- 47 Y. T. Li, X. L. Zhang, Z. K. Peng, P. Liu and X. C. Zheng, *Fuel*, 2020, **277**, 118243.
- 48 W. Wang, Y. Tao, L. Du, Z. Wei, Z. Yan, W. K. Chan, Z. Lian, R. Zhu, D. L. Phillips and G. Li, *Appl. Catal., B*, 2021, **282**, 119568.
- 49 X. Wu, H. Ma, W. Zhong, J. Fan and H. Yu, *Appl. Catal., B*, 2020, **271**, 118899.
- 50 X. Xu, J. Luo, L. Li, D. Zhang, Y. Wang and G. Li, *Green Chem.*, 2018, **20**, 2038–2046.
- 51 Y. Du, L. Zhao, H. Chen, Z. Huang, X. He, W. Fang, W. Li, X. Zeng and F. Zhang, *J. Mater. Sci.*, 2020, **55**, 1973–1983.
- 52 Z. Jin, L. Zhang and J. Mate, *Sci. Technol.*, 2020, **49**, 144–156.
- 53 H. Ren, D. Yang, F. Ding, K. An, Z. Zhao, Y. Chen, Z. Zhou, W. Wang and Z. Jiang, *J. Photochem. Photobiol., A*, 2020, **400**, 112729.
- 54 J. Liu, H. Shi, Q. Shen, C. Guo and G. Zhao, *Green Chem.*, 2017, **19**, 5900–5910; P. Yang, R. Wang, H. Tao, Y. Zhang, M.-M. Titiricic and X. Wang, *Appl. Catal., B*, 2021, **280**, 119454.
- 55 S. Nie, J. Wang, X. Huang, X. Niu, L. Zhu and X. Yao, *ACS Appl. Nano Mater.*, 2018, **1**, 6567–6574.
- 56 T. Chen, D. Yin, F. Zhao, K. K. Kyu, B. Liu, D. Chen, K. Huang, L. Deng and L. Li, *New J. Chem.*, 2019, **43**, 463–473.

- 57 Q. Zhu, B. Qiu, M. Du, J. Ji, M. Nasir, M. Xing and J. Zhang, *ACS Sustainable Chem. Eng.*, 2020, **8**, 7497–7502.
- 58 M. Li, T. Qi, R. Yang, H. N. Xiao, Z. Fang, S. A. Hodge, T. D. James, L. Wang and B. Mao, *J. Mater. Chem. A*, 2018, **6**, 11296–11305.
- 59 M. Karimi-Nazarabad, E. K. Goharshadi and S. J. Mahdizadeh, *J. Phys. Chem. C*, 2019, **123**, 26106–26115.
- 60 H. Zhang, J. Yang, L. Guo, R. Wang, S. Peng, J. Wang, J. Wan and J. Xu, *Chem. Phys. Lett.*, 2021, **762**, 138143.
- 61 S. Zhang, Y. Liu, P. Gu, R. Ma, T. Wen, G. Zhao, L. Li, Y. Ai, C. Hu and X. Wang, *Appl. Catal., B*, 2019, **248**, 1–10.
- 62 Y. Xu, Y. Chen and W. F. Fu, *Appl. Catal., B*, 2018, **236**, 176–183.
- 63 C. Chen, J. Hu, X. Yang, T. Yang, J. Qu, C. Guo and C. M. Li, *ACS Appl. Mater. Interfaces*, 2021, **13**(17), 20162–20173.
- 64 Y. Zhang, G. Zhao, H. Shi, Y. Zhang, W. Huang, X. Huang and Z. Wu, *Electrochim. Acta*, 2015, **174**, 93–101.
- 65 J. Hu, C. Chen, T. Hu, J. Li, H. Lu, Y. Zheng, X. Yang, C. Guo and C. M. Li, *J. Mater. Chem. A*, 2020, **8**(37), 19484–19492.
- 66 Z. Zhu, Z. Lu, D. Wang, X. Tang, Y. Yan, W. Shi, Y. Wang, N. Gao, X. Yao and H. Dong, *Appl. Catal., B*, 2016, **182**, 115–122.
- 67 L. Ma, H. Fan, K. Fu, S. Lei, Q. Hu, H. Huang and G. He, *ACS Sustainable Chem. Eng.*, 2017, **5**, 7093–7103.
- 68 G. Liao, Y. Gong, L. Zhang, H. Gao, G. J. Yang and B. Fang, *Energy Environ. Sci.*, 2019, **12**, 2080–2147.
- 69 C. Zhao, G. Tan, J. Huang, W. Yang, H. Ren and A. Xia, *ACS Appl. Mater. Interfaces*, 2015, **7**, 23949–23957.
- 70 X. Wu, D. Gao, H. Yu and J. Yu, *Nanoscale*, 2019, **11**, 9608–9616.
- 71 J. Wen, J. Xie, H. Zhang, A. Zhang, Y. Liu, X. Chen and X. Li, *ACS Appl. Mater. Interfaces*, 2017, **9**, 14031–14042.
- 72 H. Hu, J. Hu, X. Wang, J. Gan, M. Su, W. Ye, W. Zhang, X. Mac and H. Wang, *Catal. Sci. Technol.*, 2020, **10**, 4712–4725.
- 73 J. Fu, C. Bie, B. Cheng, C. Jiang and J. Yu, *ACS Sustainable Chem. Eng.*, 2018, **6**, 2767–2779.
- 74 A. G. Young and A. J. McQuillan, *Langmuir*, 2009, **25**, 3538–3548.
- 75 A. J. Wain, M. A. O'Connell and G. A. Attard, *ACS Catal.*, 2018, **8**, 3561–3570.
- 76 M. Ma, P. Hou, J. Cao, H. Liu, X. Yan, X. Xu, H. Yue, G. Tian and S. Feng, *Green Chem.*, 2019, **21**, 5969–5979.
- 77 C. Xiao, L. Zhang, H. Hao and W. Wang, *ACS Sustainable Chem. Eng.*, 2019, **7**, 7268–7276.
- 78 W. Feng, G. Wu, L. Li and N. Guan, *Green Chem.*, 2011, **13**, 3265–3272.
- 79 S. Samanta, S. Khilari, D. Pradhan and R. Srivastava, *ACS Sustainable Chem. Eng.*, 2017, **5**, 2562–2577.
- 80 J. Hu, T. Yang, J. Chen, X. Yang, J. Qu and Y. Cai, *Chem. Eng. J.*, 2022, **430**, 133039.
- 81 X. Liu, H. Yu, J. Ji, Z. Chen, M. Ran, J. Zhang and M. Xing, *ACS ES&T Engg*, 2021, **1**, 1705–1714.