


 Cite this: *RSC Adv.*, 2022, 12, 26834

# High performance ozone decomposition over MnAl-based mixed oxide catalysts derived from layered double hydroxides†

 Mingpan Shao, Wei Hong, Tianle Zhu,  Xinxin Jiang, Ye Sun\* and Shiyu Hou

Mesoporous and dispersed MnAl-based mixed metal oxide catalysts ( $Mn_xAlO$ ) were fabricated *via* the calcination of layered double hydroxide (LDH) precursors prepared by the coprecipitation method. Their physiochemical properties were characterized and their catalytic activities for ozone decomposition were evaluated. The results indicate that the prepared  $Mn_xAlO$  catalysts have excellent catalytic activity owing to their large specific surface area, abundant surface oxygen vacancies and lower average Mn oxidation states. The Mn/Al atomic ratio and calcination temperature are found to significantly affect the textural properties and catalytic activity for ozone decomposition. The  $Mn_2AlO-400$  catalyst (Mn/Al = 2, calcined at 400 °C) exhibited 84.8% ozone conversion after 8 h reaction under an initial ozone concentration of  $45 \pm 2$  ppm,  $30 \pm 1$  °C, a relative humidity of  $50\% \pm 3\%$ , and a space velocity of  $550\,000\ h^{-1}$ . The results also show that the catalytic activity of  $Mn_2AlO-400$ , which was deactivated owing to the accumulation of oxygen-related intermediates, was recovered by calcination at 400 °C under a  $N_2$  atmosphere for 1 h. A possible reason for catalyst deactivation and regeneration is proposed. This work provides a facile method for fabricating  $Mn_xAlO$  catalysts with excellent characteristics to achieve better catalytic activity, which are promising candidates for practical ozone decomposition.

 Received 13th July 2022  
 Accepted 9th September 2022

DOI: 10.1039/d2ra04308d

[rsc.li/rsc-advances](https://rsc.li/rsc-advances)

## 1. Introduction

The ozone layer in the stratosphere protects against short-wavelength ultraviolet radiation from sunlight, but is also a source of air pollution in the troposphere. Ozone ( $O_3$ ) is a critical air pollutant in both indoor and outdoor environments. In outdoor environments, ozone is a secondary air pollutant that results from photochemical reactions among volatile organic compounds (VOCs) and nitrogen oxides ( $NO_x$ ) under sunlight irradiation.<sup>1</sup> In indoor environments ozone can be generated from electric appliances (*e.g.*, photocopiers, air purifiers, and laser printers), which may lead to considerable ozone emissions.<sup>2</sup> Additionally, natural or mechanical ventilation can introduce ozone to the indoor environment. Ozone participates in reactions with organic pollutants present in indoor environments and generates a series of oxidation products (*e.g.*, unsaturated hydrocarbons, VOCs, and secondary organic aerosols), which have a severely detrimental effect on the environment and human health over long-term exposure.<sup>3,4</sup> Ozone has a resonant structure that makes it highly stable, with a half-life of 160 h at room temperature and atmospheric pressure,<sup>5</sup> and its spontaneous decomposition at room

temperature is negligible. The development of effective ozone elimination techniques has thus become an urgent task to protect the environment and human health.

Several promising methods to eliminate ozone have been explored, including activated carbon adsorption, thermal decomposition, photocatalytic decomposition and catalytic decomposition.<sup>4</sup> As a cheap and conventional adsorbent, activated carbons are commonly used to remove ozone. The ozone removal efficiency depends on the strength of the chemical bonds and specific area.<sup>6,7</sup> However, activated carbon needs to be regenerated or replaced frequently because it is easily deactivated, and the removal efficiency is greatly affected by humidity. Thermal decomposition requires heating the gas to about 400 °C, which has good removal efficiency for high-concentration  $O_3$ .<sup>8</sup> For the photocatalytic decomposition, the removal efficiency is relatively low in the environment of natural light.<sup>9</sup> The conversion of ozone on bare  $TiO_2$  is low, needs adding noble metals (such as Ag, Pt, Pd, Au) or transition metals (such as Mn, Cu, Fe) to promote charge transfer.<sup>10–12</sup> Compared with above methods, catalytic decomposition is considered an effective technique to safely, economically, and efficiently remove gaseous ozone.<sup>13,14</sup> Catalysts mainly includes noble metal catalysts (*e.g.*, Ag, Au, Pt, Pd)<sup>15–18</sup> and transition metal catalysts (*e.g.*, Mn, Co, Ni, Fe).<sup>3,19–23</sup> Noble metal catalysts have excellent activity for  $O_3$  decomposition, as well as excellent moisture resistance, and have attracted the attention of many researchers, but the high cost limits their wide applications.<sup>24</sup>

School of Space and Environment, Beihang University, Beijing 100191, China. E-mail: [suny@buaa.edu.cn](mailto:suny@buaa.edu.cn)

† Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2ra04308d>



Manganese oxides ( $\text{MnO}_x$ ) are commonly used as the active components for ozone decomposition due to their economic and environmental benefits, diverse structures, simple preparation, and excellent physicochemical properties.<sup>20,24–27</sup> Several studies have shown that  $\text{Mn}^{3+}$  (oxygen vacancy) is the active site in  $\text{MnO}_x$  for the catalytic decomposition of ozone.

Recent studies have reported oxygen vacancies with different properties and effects on performance. Li *et al.*<sup>28</sup> reported two different kinds of structural oxygen vacancies ( $\text{sp}^2\text{-O}_{\text{vac}}$  and  $\text{sp}^3\text{-O}_{\text{vac}}$ ) in  $\alpha\text{-MnO}_2$ , its different adsorption energies for  $\text{O}_3$ ,  $\text{O}_2$ , and  $\text{H}_2\text{O}$ , resulted in different catalytic activities. These findings are indicative of the strong sensitivity of catalytic reactions to oxygen vacancy properties. Hong *et al.*<sup>14</sup> showed that  $\text{Li}^+$  ions on  $\alpha\text{-MnO}_2$  surface can influence oxygen vacancies by promoting the adsorption of  $\text{O}_3$  and desorption of  $\text{H}_2\text{O}$  and  $\text{O}_2$ , thus improving the ozone decomposition performance. The content and species of various ions in the channels of the  $\text{MnO}_x$  structure can be regulated to increase oxygen vacancy contents. High content of oxygen vacancies is beneficial to the ozone decomposition performance. Therefore, it is necessary to adjust the oxygen vacancies at the micro-scale of the manganese oxides. However, the low yield and low specific surface areas of  $\text{MnO}_x$  catalysts prepared by the hydrothermal method. Relatively low specific surface areas tend to limit the catalytic efficiency of  $\text{MnO}_x$  and supporters are required. The key challenge in the preparation of supported manganese oxides is the active phase  $\text{MnO}_x$  to uniformly dispersed to maximum extent, while simultaneously stabilizing it against thermal degradation resulting from sintering and solid state reactions with the support and within the active phase itself.<sup>29</sup> All these limits its practical applications.

Numerous recent reports have contributed to the synthesis, characterization, and catalytic applications of mixed metal oxides (MMO) produced by the thermal decomposition of layered double hydroxides (LDHs) (*e.g.*, Co–Al,<sup>30</sup> Co–Mn–Al,<sup>31,32</sup> Pd/Co–Mn–Al,<sup>33,34</sup> Cu–Co–Al<sup>35,36</sup>), which are two-dimensional layered materials with a general chemical formula of  $[\text{M}_{1-x}\text{M}_x^{2+}(\text{OH})_2]^{x+}[\text{A}_{x/n}]^{n-} \cdot m\text{H}_2\text{O}$ , where  $\text{M}^{2+}$  and  $\text{M}^{3+}$  are di- and trivalent metal cations, respectively,  $\text{A}^{n-}$  is a counter anion, and  $x = 0.17\text{--}0.33$ . With their adjustable cations, interlayer anions, and particular structure characteristics (*e.g.*, long-range order, topological transformation, confined effects), LDHs have been proven to have many potential applications as catalysts,<sup>37</sup> catalyst supports, or catalyst precursors.<sup>38,39</sup> Mixed metal oxides are formed by the calcination of LDHs, which possess unique properties such as high surface area and porosity, good thermal stability, homogeneously mixed oxides, and high metal cation dispersion. These features motivated this study to construct  $\text{MnO}_x$  catalysts derived from LDHs for ozone decomposition, which are expected to exhibit the following strengths. (1) A 2D lamellar structure with a large surface area can provides more active sites for ozone decomposition, and facilitates the adsorption and desorption of gas molecules. (2) Excellent thermal stability and high homogeneous dispersion of active components on the  $\text{Mn}_x\text{AlO}$  would accelerate the ozone decomposition performances. (3) The valence state of Mn can be tuned without changing the 2D structure and create more

redox couples, which would further improve the catalytic activity.

In this work, we report the fabrication of  $\text{Mn}_x\text{AlO}$  powdered catalysts derived from a  $\text{Mn}_x\text{Al-LDH}$  precursor, and investigate their catalytic activity for ozone decomposition. The results indicate that  $\text{Mn}_2\text{AlO-400}$  catalysts had the highest catalytic activity. Measurements of the BET,  $\text{H}_2\text{-TPR}$ ,  $\text{NH}_3\text{-TPD}$  and XPS demonstrate that the prepared  $\text{Mn}_2\text{AlO-400}$  possessed a large surface area, low temperature reducibility, stronger acid sites and the high  $\text{Mn}^{3+}/\text{Mn}^{4+}$  and  $\text{O}_{\text{II}}/\text{O}_{\text{I}}$  values, which account for its significantly enhanced activity. The  $\text{Mn}_2\text{AlO-400}$  catalyst was further investigated to the deactivation mechanism and regeneration method by *in situ* DFT-IR.

## 2. Materials and methods

### 2.1 Catalysts preparation

The  $\text{Mn}_x\text{Al-LDH}$  precursors were prepared by the coprecipitation method. A mixed solution of 0.5 M  $\text{Mn}(\text{NO}_3)_2$  and  $\text{Al}(\text{NO}_3)_3$  ( $\text{Mn}^{2+}/\text{Al}^{3+}$  molar ratio = 1, 2, 3, 4) was added dropwise to 0.5 M NaCl solution with stirring. The solution pH was adjusted to 9–10 by the dropwise addition of 2 M NaOH solution, and the temperature was held in a thermostat set at 313 K.  $\text{N}_2$  atmosphere and decarbonated water were applied throughout the procedure to prevent the over-oxidation of Mn and generation of  $\text{MnCO}_3$ . The resulting precipitate was aged for 1 h in the mother liquor solution and collected by filtration. The solid product was filtrated and washed completely with deionized water to pH = 7. The sample was also washed with ethanol several times and then filtered. The precipitate was dried in air at 60 °C.

$\text{Mn}_x\text{AlO}$  catalysts were obtained by calcinating the products of the  $\text{Mn}_x\text{Al-LDH}$  precursors in air at 400 °C for 4 h using a heating rate of 2 °C  $\text{min}^{-1}$  (denoted as  $\text{Mn}_x\text{AlO-400}$ ). The effect of calcination temperatures (300, 400, 500, 600, and 700 °C) on the catalyst performance was also investigated. The resulting samples are denoted as  $\text{Mn}_x\text{AlO-300}$ ,  $\text{Mn}_x\text{AlO-400}$ ,  $\text{Mn}_x\text{AlO-500}$ ,  $\text{Mn}_x\text{AlO-600}$ , and  $\text{Mn}_x\text{AlO-700}$ , respectively.

### 2.2 Catalysts characterization

Crystal structure analyses of the samples were systemically performed using X-ray powder diffraction (XRD, Bruker, USA) over a  $2\theta$  range of 5–80° and scanning speed of 4°  $\text{min}^{-1}$ . The pore size, pore volume, and surface area of the samples were measured on an ASAP 2020 instrument (BET, Micromeritics, USA) using  $\text{N}_2$  adsorption/desorption. The samples were pre-treated at 200 °C in a vacuum for 3 h prior to testing, and their microstructures were observed using a Zeiss Sigma 500 field emission scanning electron microscopic (SEM; Carl Zeiss AG, Oberkochen, Germany) at a voltage of 5 kV. The chemical compositions were measured by inductively coupled plasma-atomic emission spectrometry (ICP-OES, Agilent, USA). The surface chemical compositions and chemical states of Mn and O in the catalysts were obtained using an Escalab 250xi X-ray photoelectron spectrometer (Thermo Fisher Scientific Inc., USA), which was calibrated by referencing the C 1s signal at

284.8 eV. H<sub>2</sub>-TPR, NH<sub>3</sub>-TPD and CO<sub>2</sub>-TPD experiments were conducted on a Micromeritics AutoChem II 2920 chemisorption analyzer equipped with a TCD detector (Micromeritics Instrument Corp). The related reaction intermediates, which reduced the ozone decomposition activity, were investigated by *in situ* diffused Fourier transform infrared spectroscopy (*in situ* DFT-IR) using a Nicolet 6700 FTIR spectrometer (Nicolet Instrument Corp., USA).

### 2.3 Evaluation of ozone decomposition activity

The ozone decomposition activity was evaluated by dynamic testing at 30 ± 1 °C in a fixed-bed continuous flow quartz reactor (inner diameter = 5 mm) under atmospheric pressure conditions. In each run, 0.15 g of catalyst sample of 40–60 mesh was loaded into a quartz reactor and pretreated at a heating rate of 5 °C min<sup>-1</sup> to 120 °C for 1 h in a N<sub>2</sub> atmosphere to eliminate adsorbed water on the catalyst surfaces. Ozone was generated by flowing 1.0% O<sub>2</sub>/N<sub>2</sub> compressed gas through an HTU-500E ozone generator (Azco Industries Ltd., Canada). The relative humidity was adjusted from 0% to 99% with an accuracy of ±3% by passing compressed dry air (80% N<sub>2</sub> + 20% O<sub>2</sub>) through a water bath bubbler. The total gas flow rate passing through the quartz reactor was controlled at 2 L min<sup>-1</sup>, which contained 40 ± 2 ppm O<sub>3</sub>. The gas hour space velocity was maintained at 550 000 h<sup>-1</sup>. The ozone concentrations at the inlet and outlet were detected using a 106-L ozone online analyzer (2B Technologies, USA). The relative humidity was measured using a 7116-CP thermos hygrometer (Cole Parmer, USA). The ozone conversion was calculated according to:

$$\text{Ozone conversion (\%)} = \frac{C_{\text{in}} - C_{\text{out}}}{C_{\text{in}}} \times 100\% \quad (1)$$

where  $C_{\text{in}}$  and  $C_{\text{out}}$  are the inlet and outlet ozone concentrations, respectively.

## 3. Results and discussion

### 3.1 Structure and composition of catalysts

Fig. 1a shows that the XRD patterns of the prepared LDHs exhibit four typical (003), (006), (012), and (110) diffraction peaks,<sup>40,41</sup> which indicate the generation of a well-crystallized layered structure with  $R\bar{3}m$  symmetry.<sup>42</sup> The lattice parameter

Table 1 Lattice parameters and ICP-OES results for different Mn<sub>x</sub>Al-LDH samples

LDH	$a$ (Å)	$c$ (Å)	Mn/Al
MnAl-LDH	3.19	23.37	1.12
Mn <sub>2</sub> Al-LDH	3.19	23.40	2.09
Mn <sub>3</sub> Al-LDH	3.12	23.89	2.76
Mn <sub>4</sub> Al-LDH	3.06	23.99	4.11

$a = 2d(113)$  around  $2\theta = 59.4^\circ$  coincides with the closest M-M distance within the layers, whereas  $c = 3d(003)$  around  $2\theta = 11.3^\circ$  is as a function of the interlayer distance. These values are calculated and summarized in Table 1. The results suggest that the lattice parameter  $a$  decreases with increasing Mn/Al molar ratio, whereas  $c$  increases. It should be noted that Mn<sub>2</sub>Al-LDH had the best crystallinity, while Mn<sub>4</sub>Al-LDH had the worst. Diffraction peaks of Mn<sub>3</sub>O<sub>4</sub> were also observed in Mn<sub>4</sub>Al-LDH sample, because of the oxidation of the sample during preparation.<sup>41</sup> The color of the sample was found to change gradually from white to light yellow upon drying in air, showing that the Mn<sup>2+</sup> in the LDHs is partially oxidized.<sup>40</sup> The metal compositions of the LDHs were determined by ICP-OES (Table 1). The Mn contents are slightly higher than those in the feed materials, except for Mn<sub>3</sub>Al-LDH.

Fig. 1b shows the XRD patterns of the prepared Mn<sub>2</sub>AlO samples at different calcination temperatures. The LDH precursors are found to have been completely transformed into a mixture of oxide and spinel oxide phases. The peak intensities increase with increasing calcination temperature, and the lower-crystalline MnO<sub>x</sub> changed to a Mn<sub>3</sub>O<sub>4</sub> spinel phase. The strongest reflection ( $2\theta = 36.5^\circ$ ) corresponds to the (211) plane of the Mn<sub>3</sub>O<sub>4</sub> spinel phase (PDF card no. 80-0382). Other diffraction peaks located at 18.1°, 28.9°, 32.4°, and 60.4° are observed, which correspond to the (101), (112), (103), and (224) planes, respectively. The average crystallite sizes calculated using the Scherrer equation are listed in Table 2. The grain size of the crystallites significantly increased with increasing Mn/Al molar ratio. The size of the Mn<sub>2</sub>AlO-400 grains decreased to 16.8 nm with increasing calcination temperature, which is the smallest among all of the prepared samples. Small-sized particles will produce more crystal defects, which are beneficial to

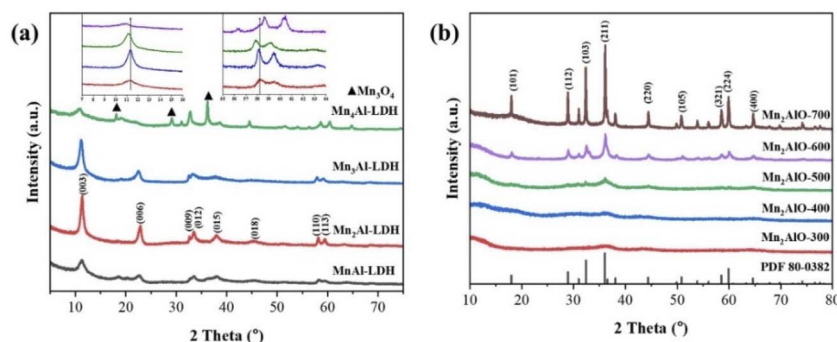


Fig. 1 (a) XRD patterns of Mn<sub>x</sub>Al-LDH; (b) XRD patterns of Mn<sub>2</sub>AlO calcined at different temperatures.

Table 2 Pore parameters of the catalysts

Samples	BET surface area ( $\text{m}^2 \text{g}^{-1}$ )	Total pore volume ( $\text{cm}^3 \text{g}^{-1}$ )	Pore diameter (nm)	Particle size (nm)
MnAlO-400	216.6	0.508	8.33	11.5
Mn <sub>2</sub> AlO-400	153.3	0.404	9.71	16.8
Mn <sub>3</sub> AlO-400	131.3	0.471	12.94	17.7
Mn <sub>4</sub> AlO-400	73.6	0.344	19.63	20.7
Mn <sub>2</sub> AlO-300	135.1	0.417	13.42	42.3
Mn <sub>2</sub> AlO-500	106.8	0.388	14.00	21.1
Mn <sub>2</sub> AlO-600	74.7	0.318	16.63	22.6
Mn <sub>2</sub> AlO-700	53.1	0.322	24.88	19.7

catalytic activity. The amorphous  $\text{Al}_2\text{O}_3$  matrix in mixed oxides can also play a supporting role in stabilizing and dispersing  $\text{MnO}_x$ , which is favorable to high catalytic activity.

### 3.2 Characterization of catalysts

Fig. 2 displays the  $\text{N}_2$  adsorption–desorption isotherm and corresponding pore size distribution curve for the  $\text{Mn}_x\text{AlO}$  catalysts. All of the samples exhibit a typical IV isotherm with a H2-type hysteresis loop ( $P/P_0 > 0.4$ ), which is associated with the occurrence of capillary condensation in the mesopores and confirmed by the pore size distribution shown in Fig. 2(c and d). This is commonly observed with aggregates of plate-like particles of LDH precursor materials that remain in the calcined mixture, giving rise to slit-shaped pores.<sup>43</sup> Table 2 lists the specific surface area, pore volume, and pore diameter of all samples. The specific surface area of  $\text{Mn}_x\text{AlO-400}$  catalysts

decreases with increasing Mn/Al ratio, from  $216.6 \text{ m}^2 \text{g}^{-1}$  for Mn/Al = 1 to  $73.6 \text{ m}^2 \text{g}^{-1}$  for Mn/Al = 4, and the average pore diameter increased from 8.33 to 19.63 nm over the same range.

The effect of calcination temperature on the  $\text{Mn}_2\text{AlO}$  samples was also examined. The specific surface area of the  $\text{Mn}_2\text{AlO}$  catalyst initially increased with calcination temperature, from  $135.1 \text{ m}^2 \text{g}^{-1}$  at 300 °C to  $153.3 \text{ m}^2 \text{g}^{-1}$  at 400 °C, and then decreased upon further increasing the calcination temperature to  $53.1 \text{ m}^2 \text{g}^{-1}$  at 700 °C (Table 2), together with increased pore size distribution.

SEM and TEM were employed to study the morphology and surface structure of the samples. Fig. 3a–d show SEM images of the obtained  $\text{Mn}_x\text{Al-LDH}$  particles. All of the LDHs indicate a uniform and randomly oriented, thin, hexagonal lamellar structure with dimensions ranging from 80 to 300 nm. The  $\text{Mn}_2\text{Al-LDH}$  samples are of higher quality in terms of

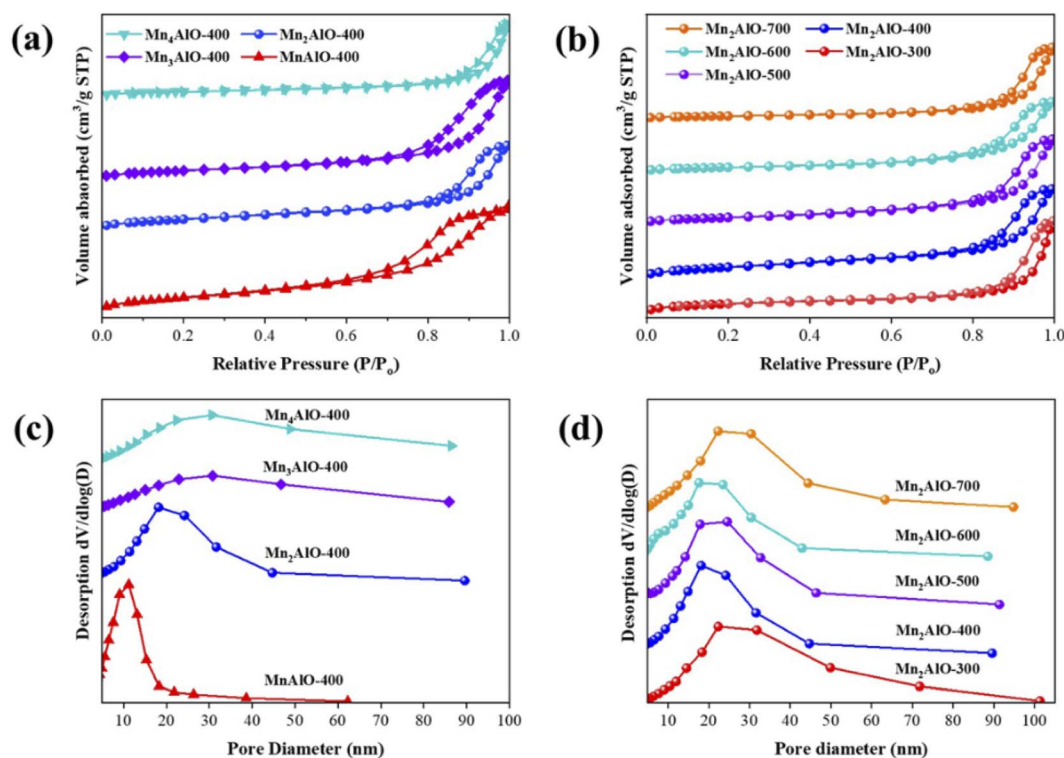


Fig. 2  $\text{N}_2$  adsorption–desorption isotherms and pore size distribution curves of catalysts.



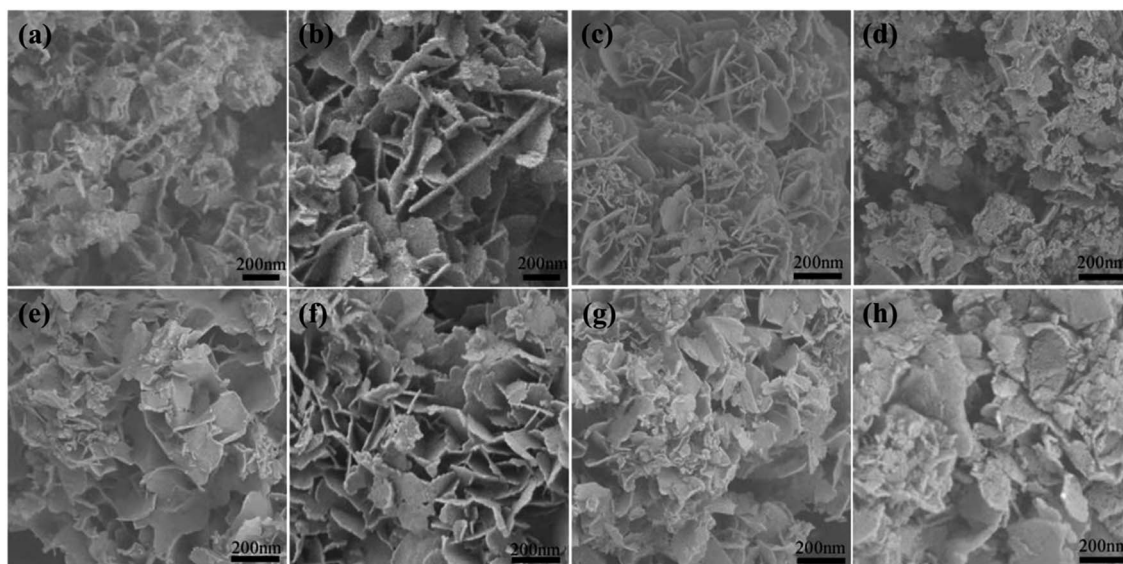


Fig. 3 SEM of (a) MnAl-LDH, (b) Mn<sub>2</sub>Al-LDH, (c) Mn<sub>3</sub>Al-LDH, (d) Mn<sub>4</sub>Al-LDH, (e) Mn<sub>2</sub>AlO-300, (f) Mn<sub>2</sub>AlO-400, (g) Mn<sub>2</sub>AlO-500, (h) Mn<sub>2</sub>AlO-700.

morphology, size, uniformity, and crystallinity, which are far superior to the other prepared Mn<sub>x</sub>Al-LDH samples. These results are consistent with the X-ray diffraction peak intensities among the Mn<sub>x</sub>Al-LDH samples. The SEM images of Mn<sub>2</sub>AlO after calcination in air at different temperatures are shown in Fig. 3e–g. The morphology of Mn<sub>2</sub>AlO can maintain a relatively complete shape after calcination in air at 300 °C to 500 °C, while the structures of the other higher-temperature samples (700 °C) decomposed to many fine particles.

Fig. 4(a1–d1) show the Mn<sub>x</sub>AlO show a hierarchical frizzy nanoflake shape composed of a randomly aggregated structure of numerous ultrathin platelet-like, which is well agreement with the SEM images in Fig. 3. In addition, many plates have been broken into smaller pieces. It also can be observed that the MnO<sub>x</sub> particles dispersed among plates, and the particles size

increase with increasing Mn/Al ratio and the calcination temperature which might be due to an increase of agglomeration and particularly to segregation of spinel phases Mn<sub>3</sub>O<sub>4</sub> observed by XRD. The particle sizes were 20–70 nm of Mn<sub>x</sub>AlO-400 and 100–450 nm of Mn<sub>2</sub>AlO-700, respectively. From high-resolution transmission electron microscopy (HRTEM) images (Fig. 4(a2–d2)) of Mn<sub>x</sub>AlO-400, the surface lattice spacing was measured to be 0.31 nm corresponding to the (112) crystal plane of Mn<sub>3</sub>O<sub>4</sub> spinel phase with poor crystallization. The HRTEM image (Fig. 4(d2)) of Mn<sub>2</sub>AlO-700 catalyst exposed the identified fringes with lattice spacings of about 0.28 nm, rather close to the (200) crystal phase of the Mn<sub>3</sub>O<sub>4</sub> phase with slightly good crystallization. The microstructures of Mn<sub>x</sub>AlO catalysts are in agreement with XRD results. Therefore, the calcination temperature has a great impact on the prepared catalysts.

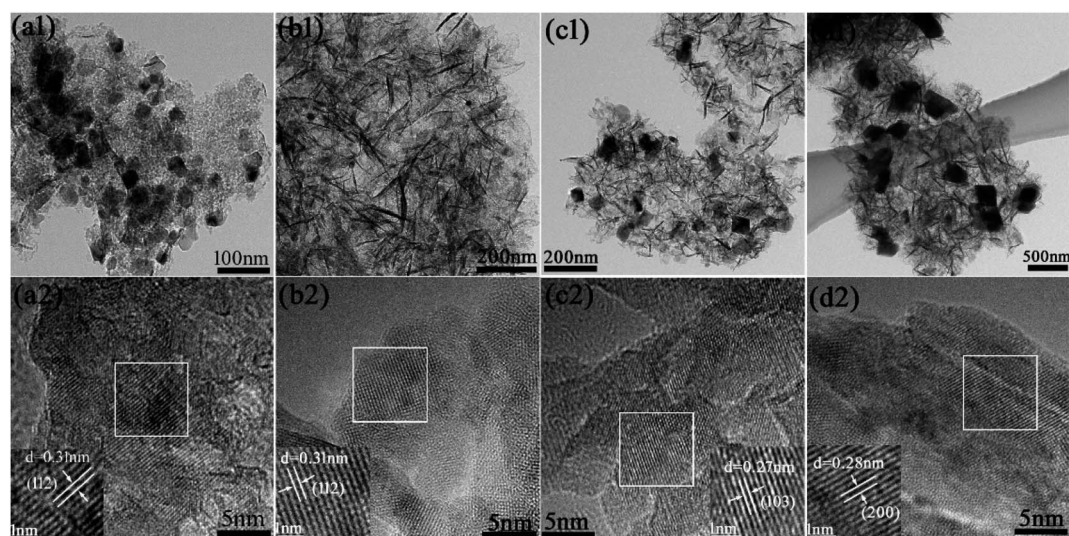


Fig. 4 TEM images and HRTEM images of (a) MnAlO-400; (b) Mn<sub>2</sub>AlO-400; (c) Mn<sub>3</sub>AlO-400; (d) Mn<sub>2</sub>AlO-700.

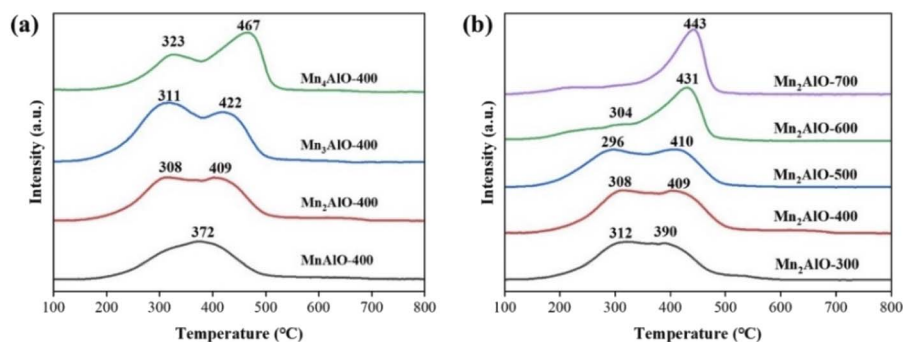


Fig. 5  $\text{H}_2$ -TPR results of the catalysts.

To assess the redox properties of the  $\text{Mn}_x\text{AlO}$  catalyst series,  $\text{H}_2$ -TPR analyses of all catalysts were carried out, as shown in Fig. 5. The  $\text{Mn}_x\text{AlO}$  samples were reduced in two main

temperature regions. The reduction of manganese oxides can be described by the successive reduction processes:  $\text{MnO}_2 \rightarrow \text{Mn}_2\text{O}_3 \rightarrow \text{Mn}_3\text{O}_4 \rightarrow \text{MnO}$ .<sup>19</sup> The first reduction peak (200–350

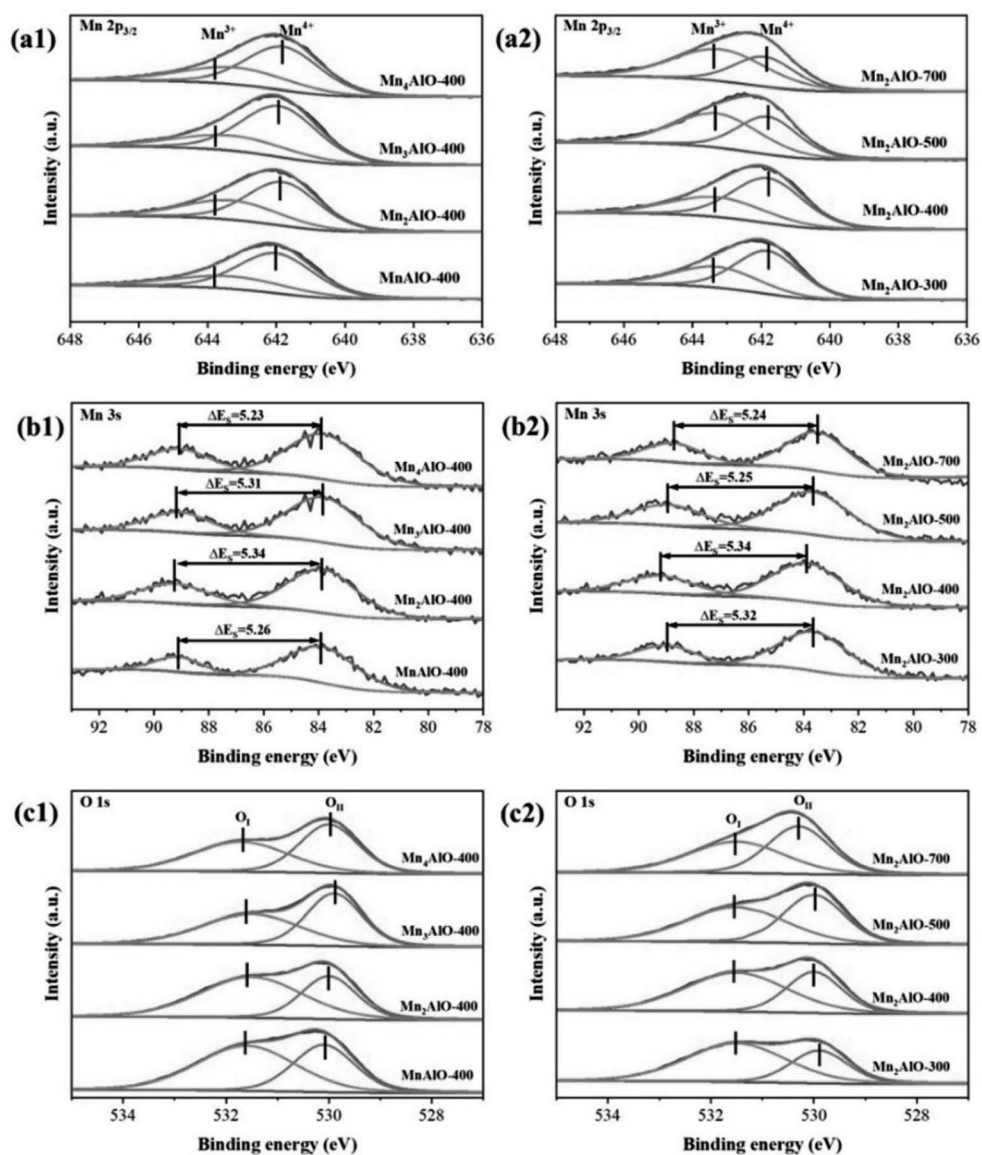


Fig. 6  $\text{Mn } 2p_{3/2}$ ,  $\text{Mn } 3s$  and  $\text{O } 1s$  XPS spectra of the prepared catalysts.

°C) is attributed to the reduction of MnO<sub>2</sub> to Mn<sub>3</sub>O<sub>4</sub>. The second reduction peak (350–500 °C) is ascribed to the reduction of Mn<sub>3</sub>O<sub>4</sub> to MnO. For the Mn<sub>2</sub>AlO-400 catalyst, the maximum H<sub>2</sub> consumption occurs at 308 °C and 409 °C. Increasing the Mn/Al molar ratio shifts the reduction peaks toward higher temperature. The reduction peak appears to widen and the intensity increases in Fig. 5a.

Fig. 5b shows the influence of calcination temperature on the catalyst reduction performance. For catalyst Mn<sub>2</sub>AlO-300, the first reduction peak occurred at 312 °C and the second peak appeared at 390 °C. The reduction pattern of Mn<sub>2</sub>AlO-500 was similar, but the first peak position shifted to lower temperature (296 °C) and the second peak position shifted to higher temperature (410 °C). In contrast, catalysts Mn<sub>2</sub>AlO-600 and Mn<sub>2</sub>AlO-700 only showed a single reduction peak at 431 °C and 443 °C, respectively. This supports that the reduction performance of the Mn<sub>2</sub>AlO catalysts is indeed sensitive to calcination temperature. The low-temperature reduction ability of Mn<sub>2</sub>AlO obtained at higher calcination temperature is poor, and low-temperature calcination is more beneficial to Mn<sub>2</sub>AlO reduction than high-temperature calcination.

The valence state of Mn also has a strong effect on catalytic ozone decomposition because the mechanism of ozone catalytic decomposition mainly consists of redox steps. The redox activity of Mn-based catalysts is associated with the presence of Mn<sup>2+</sup>, Mn<sup>3+</sup>, and Mn<sup>4+</sup> ions. Fig. 6 shows the XPS results, which

are used to characterize the chemical valence in the catalysts. As shown in Fig. 6a, the Mn 2p<sub>3/2</sub> spectra deconvoluted into two peaks with binding energies of 641.8 and 643.2 eV ascribed to Mn<sup>3+</sup> and Mn<sup>4+</sup>, respectively.<sup>26,44,45</sup> Previous studies have confirmed that high Mn<sup>3+</sup> (oxygen vacancies) content is the key factor to the excellent activity of manganese oxide catalysts.<sup>14,20,24,46</sup> When Mn<sup>3+</sup> forms on manganese dioxide, an oxygen vacancy will be generated to maintain charge balance, thus an oxygen vacancy and Mn<sup>3+</sup> are essentially the same.

A quantitative analysis of the molar ratios of surface Mn<sup>3+</sup>/Mn<sup>4+</sup> is summarized in Table 3. The Mn/Al molar ratios of the precursor and calcination temperature have a remarkable influence on the surface Mn<sup>3+</sup>/Mn<sup>4+</sup> molar ratio, which decreased in the following order: Mn<sub>2</sub>AlO-400 > Mn<sub>3</sub>AlO-400 > MnAlO-400 > Mn<sub>4</sub>AlO-400 and Mn<sub>2</sub>AlO-400 > Mn<sub>2</sub>AlO-300 > Mn<sub>2</sub>AlO-500 > Mn<sub>2</sub>AlO-700. The average oxidation state (AOS) of Mn was calculated according to:

$$\text{AOS} = 8.956 - 1.126 \times \Delta E_s \quad (2)$$

where  $\Delta E_s$  is the binding energy difference between the doublet Mn 3s peaks, as shown in Fig. 6b.<sup>26</sup> The results show that the AOS increases in the order of Mn<sub>2</sub>AlO-400 (2.94) < Mn<sub>3</sub>AlO-400 (2.98) < MnAlO-400 (3.03) < Mn<sub>4</sub>AlO-400 (3.07), Mn<sub>2</sub>AlO-400 (2.94) < Mn<sub>2</sub>AlO-300 (2.97) < Mn<sub>2</sub>AlO-500 (3.04) < Mn<sub>2</sub>AlO-700 (3.07), which suggests that Mn<sub>2</sub>AlO-400 has the highest Mn<sup>3+</sup> fraction.

Table 3 Surface compositions and oxidation states

Catalyst	H <sub>2</sub> -TPR H <sub>2</sub> consumption (mmol g <sup>-1</sup> )	XPS			AOS of Mn			
		Mn 2p <sub>3/2</sub> Mn <sup>3+</sup> (%)	Mn <sup>4+</sup> (%)	Mn <sup>3+</sup> /Mn <sup>4+</sup>	Mn 3s Mn	O 1s O <sub>I</sub> (%)	O <sub>II</sub> (%)	O <sub>II</sub> /O <sub>I</sub>
MnAlO-400	29.26	67.59	32.41	2.09	3.03	39.42	60.58	1.54
Mn <sub>2</sub> AlO-400	41.70	71.50	28.50	2.51	2.94	36.29	63.71	1.76
Mn <sub>3</sub> AlO-400	50.35	69.75	30.25	2.31	2.98	48.89	51.11	1.05
Mn <sub>4</sub> AlO-400	43.24	67.24	32.76	2.05	3.07	50.15	49.85	0.99
Mn <sub>2</sub> AlO-300	36.44	61.47	38.53	1.60	2.97	32.47	67.53	2.08
Mn <sub>2</sub> AlO-500	36.87	44.08	55.92	0.79	3.04	45.92	54.08	1.18
Mn <sub>2</sub> AlO-700	28.59	37.77	62.23	0.61	3.06	49.77	50.23	1.01

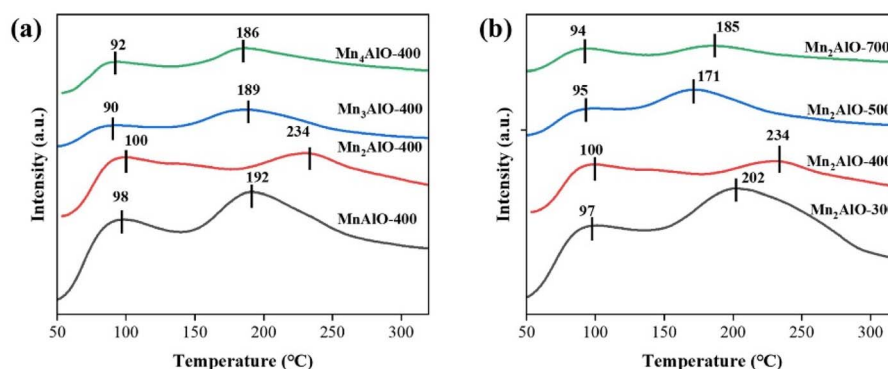


Fig. 7 NH<sub>3</sub>-TPD results of the catalysts.



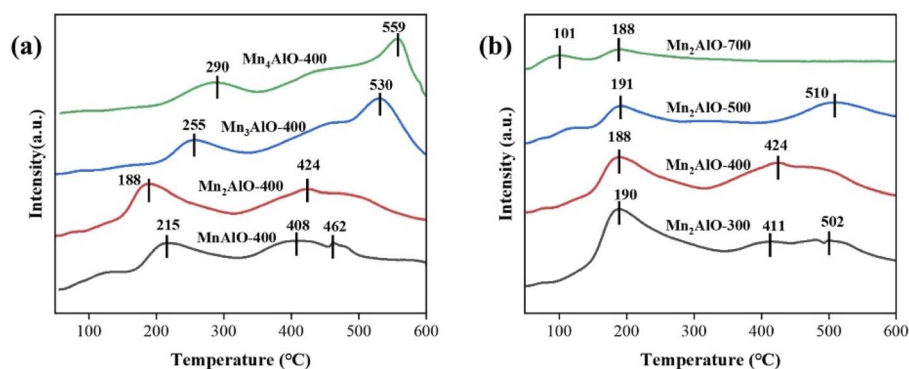


Fig. 8 CO<sub>2</sub>-TPD results of the catalysts.

The asymmetric O 1s peaks for the Mn<sub>x</sub>AlO samples can be deconvoluted into two contributions centered at 530 and 531.6 eV, which are attributed to the lattice oxygen (O<sub>I</sub>) and surface adsorbed oxygen (O<sub>II</sub>), respectively.<sup>46</sup> The surface molar percent of O<sub>I</sub> and O<sub>II</sub> and the O<sub>II</sub>/O<sub>I</sub> ratios are summarized in Table 3. The O<sub>II</sub>/O<sub>I</sub> ratio initially increases with increasing Mn/Al molar ratio, from 1.54 for MnAlO-400 to 1.74 for Mn<sub>2</sub>AlO-400, then drastically decreases to 1.05 for Mn<sub>3</sub>AlO-400 and 0.99 for Mn<sub>4</sub>AlO-400. This implies that the most abundant surface-adsorbed oxygen occurs when the Mn/Al molar ratio in the precursor is 2. This may be owing to the higher surface specific

area and narrower pore size, which create more vacancies and unsaturated chemical bonds, thus increasing the adsorbed oxygen ratio on the surface. The calcination temperature also affects the O<sub>II</sub>/O<sub>I</sub> molar ratios on the oxide surface. The O<sub>II</sub>/O<sub>I</sub> ratio is found to decrease with increasing calcination temperature, from 2.08 for Mn<sub>2</sub>AlO-300 to 1.01 for Mn<sub>2</sub>AlO-700. This may be due to the reduced amount of adsorbed oxygen species on the catalyst surface owing to the increased calcination temperature, increased crystallinity of the oxide, the reduction of the specific surface area, and surface defects.

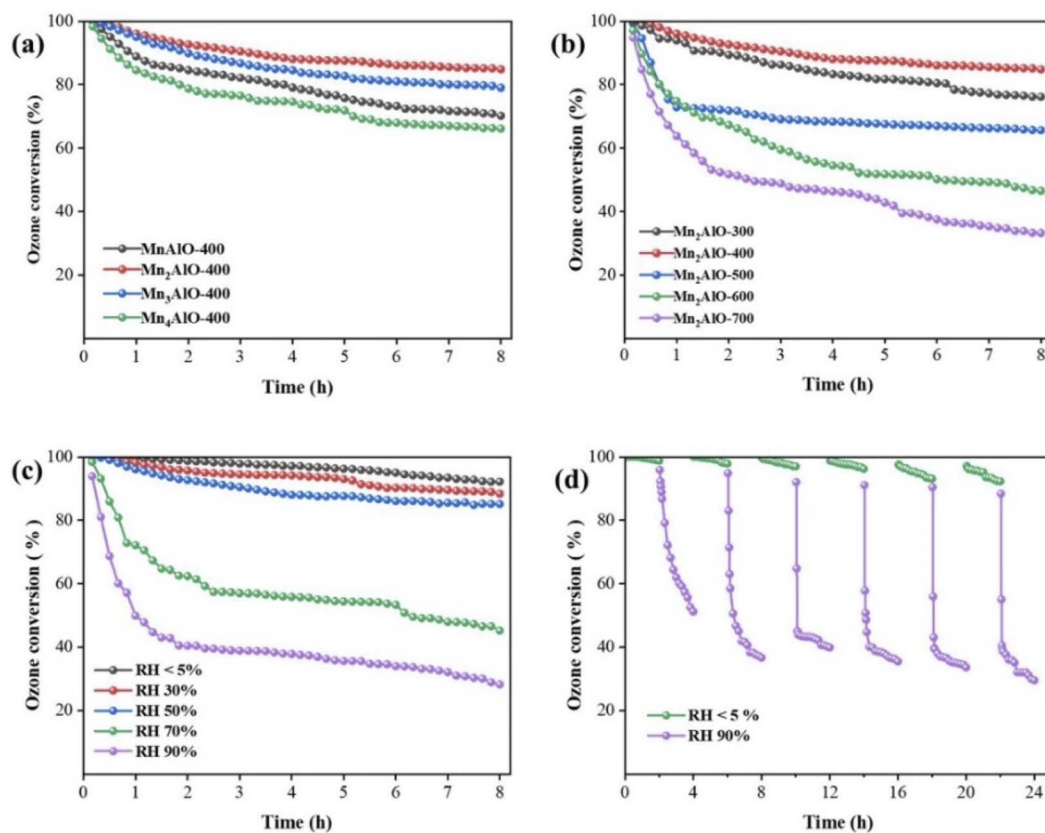


Fig. 9 Ozone conversion over the Mn<sub>x</sub>AlO catalysts. (a) Effects of Mn/Al molar ratios (b) effects of calcination temperatures (c) effects of relative humidity; (d) ozone conversion at alternate humidity conditions.



The surface acidity and basicity of  $Mn_xAlO$  were investigated by  $NH_3$ -TPD (Fig. 7) and  $CO_2$ -TPD (Fig. 8), respectively. The binding strength between acid sites and  $NH_3$  molecules or base sites and  $CO_2$  was positively correlated to the desorption temperature. Generally, the acid sites are classified into the weak ( $<150\text{ }^\circ\text{C}$ ), medium ( $150\text{--}350\text{ }^\circ\text{C}$ ) and strong ( $>350\text{ }^\circ\text{C}$ ) acid sites.<sup>47</sup> In Fig. 7, there are two  $NH_3$  desorption peaks near  $100\text{ }^\circ\text{C}$  and  $200\text{ }^\circ\text{C}$ , respectively. This indicates that the  $Mn_xAlO$  catalysts possess the weak and medium acid sites distributions on surface. The desorption peak  $<150\text{ }^\circ\text{C}$  is assigned to the physically adsorbed  $NH_3$ , and the peaks at  $150\text{--}300\text{ }^\circ\text{C}$  correspond to the desorption of  $NH_3$  on L-acid and B-acid sites, respectively. B-acid sites, which are weaker than L-acid ones, are attributed to surface protons, whereas L-acid sites are assigned to Al–O–Mn species and containing  $Al^{3+}$  cations predominantly in octahedral sites.<sup>48</sup> Fig. 7 shows the Mn/Al molar ratio and calcination temperature affecting on the catalyst surface medium acid sites. The most intensive peak was  $234\text{ }^\circ\text{C}$  of the  $Mn_2AlO$ -400 sample, significantly higher than other samples, so it has the strongest acid sites.

Fig. 8 was the  $CO_2$ -TPD profiles of catalysts. The desorption of  $CO_2$  from the all samples, which begins at  $150\text{ }^\circ\text{C}$ , after reaching maximum at  $400\text{--}550\text{ }^\circ\text{C}$ . The low-temperature desorption peak is assigned to the  $CO_2$  adsorbed on OH groups, the intermediate-temperature desorption peak corresponds to the  $CO_2$  adsorbed on Mn–O or Al–O pairs, and the

high-temperature desorption peak conforms to the desorption of  $CO_2$  on  $O^{2-}$  anions.<sup>48,49</sup> Fig. 8 shows the  $Mn_xAlO$  samples possess the medium and strong basic centers on surface. The strength of basicity increased with increasing Mn/Al molar ratio, and higher temperature calcination weakened the strong basic centers. Ozone was easy to be adsorbed on weak L-acid site and decomposes to form atom oxygen on strong L-acid site.<sup>50</sup> The strongest acid site and weaker base site on the surface of  $Mn_2AlO$ -400 are beneficial to ozone decompose catalytic activity.

### 3.3 Catalytic activity for ozone decomposition

The ozone decomposition activity was evaluated at  $30 \pm 1\text{ }^\circ\text{C}$ , a relative humidity (RH) of 50%, inlet ozone concentration of  $40 \pm 2\text{ ppm}$ , and space velocity of  $550\text{ }000\text{ h}^{-1}$ , the results are shown in Fig. 9. The initial catalytic activity of all prepared catalysts was 100% and the ozone conversion decreased as the reaction continued. The ozone catalytic decomposition performance of the oxides calcinated at  $400\text{ }^\circ\text{C}$  is demonstrated to be sensitive to Mn/Al molar ratios, as shown in Fig. 9a. The ozone conversion of  $Mn_2AlO$ -400 after 8 h is 84.8%, followed by  $Mn_3AlO$ -400 (79.0%),  $MnAlO$ -400 (70.2%), and  $Mn_4AlO$ -400 (66.2%). After calcination at different temperatures,  $Mn_2AlO$ -400 still has the best catalytic activity, as shown in Fig. 9b. This is related to larger specific surface area, abundant surface oxygen vacancy and adsorbed oxygen species.

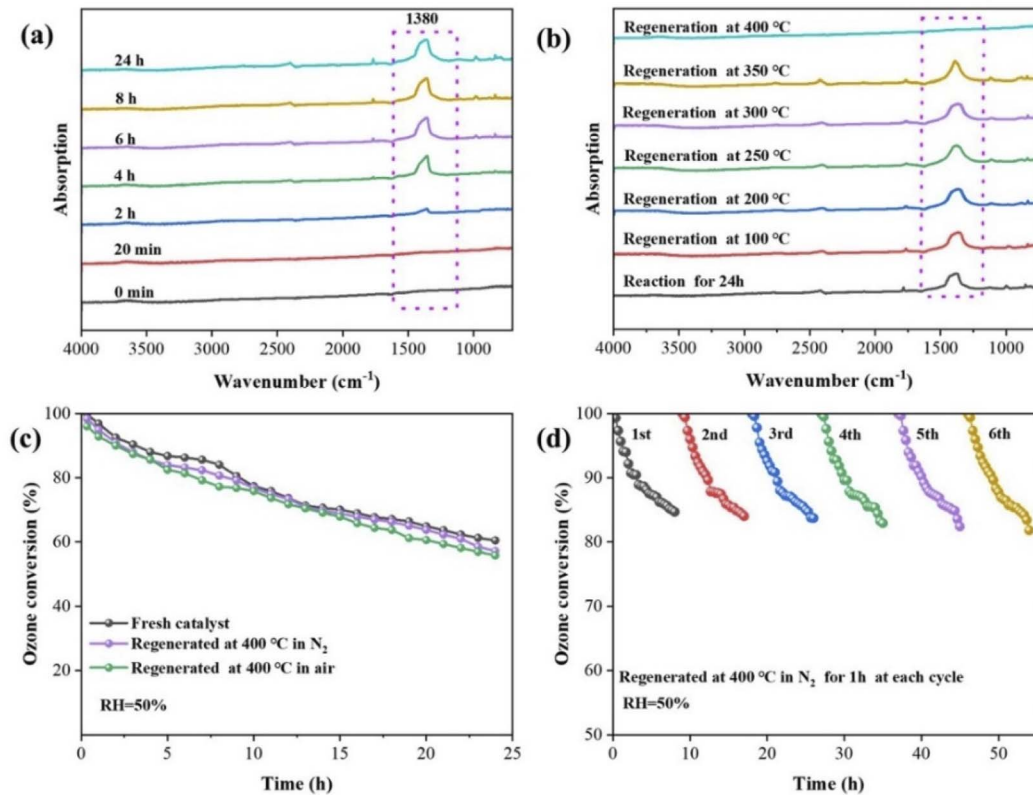


Fig. 10 (a) *In situ* DFT-IR spectra of  $Mn_2AlO$ -400 catalyst after reaction at different times; (b) *in situ* DFT-IR spectra of  $Mn_2AlO$ -400 catalyst after regeneration in  $N_2$  at different temperatures for 0.5 h; (c) ozone conversion of  $Mn_2AlO$ -400 before and after regeneration; (d) cycling performance of  $Mn_2AlO$ -400 catalyst.

We also investigated the ozone decomposition of Mn<sub>2</sub>AlO-400 under different RH, as shown in Fig. 9c. With increasing RH, the ozone conversion decreases from 92.2% for RH < 5% to 28.2% for RH = 90%. When RH ≤ 50%, the ozone conversion remains above 85% after 8 h. Water is known to inhibit the ozone decomposition of catalysts. To examine the stability and effect of water vapor on the catalytic performance of the Mn<sub>2</sub>AlO-400 catalyst, onstream reactions at 30 ± 1 °C were carried out in the absence and presence of RH = 90% water vapor, as shown in Fig. 9d. When RH = 90%, the water was introduced into the stream and the ozone conversion decreased sharply from 98.8% to 51.2% within 4 h. When the water vapor was cut off, the ozone conversion nearly recovered. The onstream reaction then continued. This operation cycle was repeated six times and the ozone conversion remained unchanged with or without water vapor. These findings demonstrate that the competitive adsorption of water molecules on the oxygen vacancies block ozone adsorption and decomposition during the reaction process, and that the effect of water on the active site is reversible.<sup>46,51</sup>

### 3.4 Catalyst deactivation and regeneration

Catalyst deactivation after a period of reaction time can affect practical engineering applications. To investigate the reason for catalyst deactivation and devise a method for catalyst regeneration, the intermediates depositing on the catalyst surface were

analyzed *via in situ* DFT-IR, as shown in Fig. 10. A new peak formed around 1380 cm<sup>-1</sup> and gradually increased with ongoing reaction time (Fig. 10a). Combined with previous studies,<sup>3,20,52</sup> this peak can be assigned to the generated oxygen-related intermediates (corresponding to peroxide species O<sub>2</sub><sup>2-</sup>) on oxygen vacancies, which are highly stable. The enrichment of O<sub>2</sub><sup>2-</sup> on oxygen vacancies is therefore the main reason for catalyst deactivation.

The regeneration of the deactivated Mn<sub>2</sub>AlO-400 catalyst was investigated by increasing the temperature in N<sub>2</sub> atmosphere (Fig. 10b). The peak at 1380 cm<sup>-1</sup> remained basically unchanged when the regeneration temperature was increased from 100 °C to 300 °C, but the peak area gradually decreased when the reaction temperature was increased from 300 °C to 400 °C, and completely disappeared at 400 °C, indicating that the intermediate was stable and desorption was not easy at low temperatures. The ozone conversion performance of the Mn<sub>2</sub>AlO-400 catalyst before and after regeneration at 400 °C in a N<sub>2</sub> and air atmosphere were also investigated, as shown in Fig. 10c. The findings show that the catalytic activity regenerated at 400 °C in N<sub>2</sub> could be nearly completely recovered, the catalytic activity is slightly lower in air.

A comparison of the XPS spectra of the Mn<sub>2</sub>AlO-400 catalysts before and after reaction with ozone, and after regeneration is shown in Fig. 11. After 24 h of reaction, the Mn<sup>3+</sup>/Mn<sup>4+</sup> molar ratio decreased from 2.51 to 1.21, accompanied by an increase

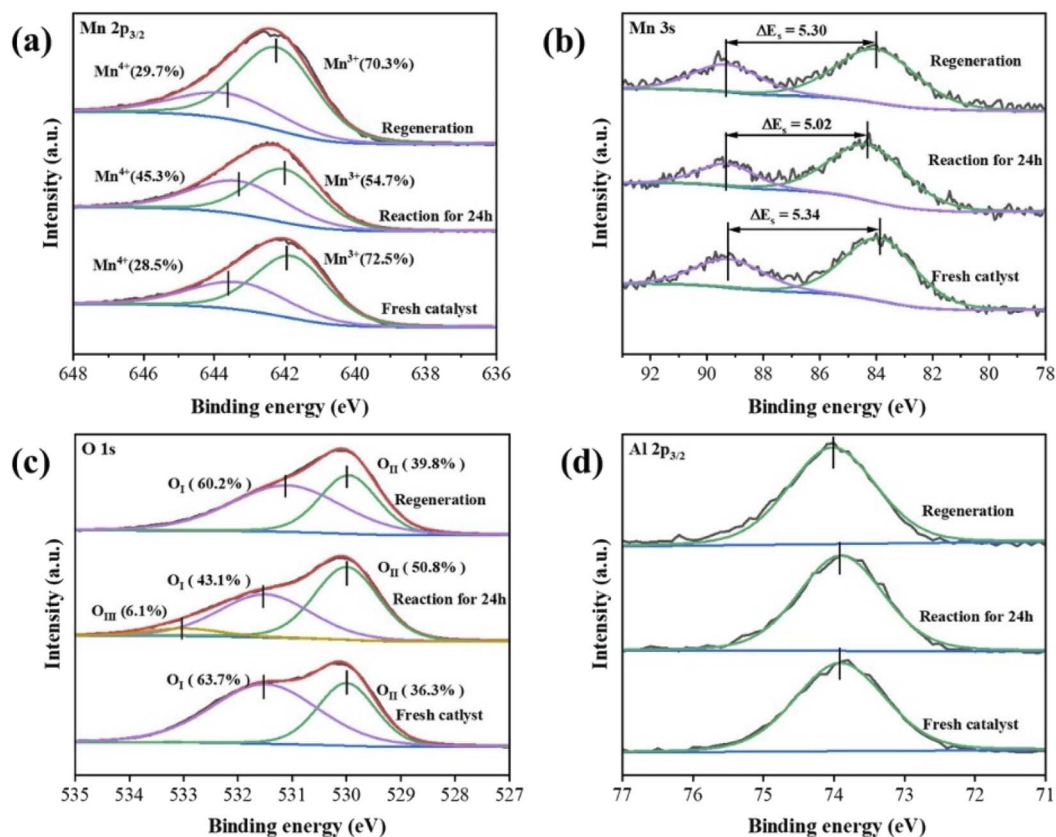


Fig. 11 Mn 2p<sub>3/2</sub> (a), Mn 3s (b), O 1s(c) and Al (2p<sub>3/2</sub>) (d) XPS spectra of the Mn<sub>2</sub>AlO-400 catalyst before and after reaction, and after regeneration at 400 °C under N<sub>2</sub> atmosphere for 2 h.

of the AOS of Mn from 2.94 to 3.31. In contrast, the  $O_{II}/O_I$  molar ratio decreased from 1.76 to 0.85, which indicates that the generated oxygen-related intermediates had accumulated on the catalyst surface during the reactions, and that the partial oxygen-related intermediates converted surface lattice oxygen over the oxygen vacancies, resulting in catalyst deactivation.<sup>3,20</sup>

$O_{III}$  appeared after 24 h of reaction, which is likely related to the hydroxyl species of surface-adsorbed water molecules because the reaction was carried out at RH = 50%. After thermal regeneration at 400 °C under  $N_2$  atmosphere for 2 h, the  $Mn^{3+}/Mn^{4+}$  molar ratio was 2.43, the AOS of Mn was 2.99, and the  $O_{II}/O_I$  molar ratio was 1.51. The catalyst was almost completely restored to its original state after regeneration at 400 °C, indicating that the generated oxygen intermediates accumulated on the catalyst surfaces were effectively removed. At the same time, a comparison of Al 2p<sub>3/2</sub> XPS spectra of  $Mn_2AlO_4$ -400 catalysts before and after reaction with ozone, and after regeneration is shown in Fig. 11d. The valence state of Al did not change after reaction 24 h, which indicates that the amorphous  $Al_2O_3$  has no ozone removal ability at room temperature. The amorphous  $Al_2O_3$  matrix in mixed oxides plays a supporting role in stabilizing and dispersing  $MnO_x$ , which is consistent with those reported in the literature.<sup>16,53</sup>

The cycling performances of  $Mn_2AlO_4$ -400 for ozone decomposition were further investigated to demonstrate its recoverability and stability. Fig. 11d shows that for  $Mn_2AlO_4$ -400, the ozone decomposition performance remained sustainable and similar to that of a fresh catalyst after six cycles. The ozone conversion of the  $Mn_2AlO_4$ -400 catalyst remained nearly 81% after six cycles with a total reaction time of 54 h, further suggesting that the catalyst has excellent chemical and structural stability. The promising reuse ability presented during the cycling experiments confirms the potential of the  $Mn_2AlO_4$ -400 catalyst for wide industrial applications.

## 4. Conclusions

A series of mesoporous and dispersed  $Mn_2AlO_4$  mixed metal oxide catalysts were successfully fabricated on LDH precursors. The morphology, textural properties, and surface chemistry of the as-prepared catalysts were characterized. The Mn/Al atomic ratios and calcination temperature were found to significantly affect the textural properties and catalytic activity for ozone decomposition. The  $Mn_2AlO_4$ -400 catalyst showed a substantially better performance than the other catalysts for ozone decomposition, which possibly benefited from a larger surface area, stronger acid sites, more abundant surface oxygen vacancies and surface-adsorbed oxygen species, lower Mn AOS, and temperature reducibility. The *in situ* DFT-IR and XPS spectra show that generated oxygen-related intermediates accumulate on the catalyst surface during the reactions, and partial oxygen-related intermediates convert surface lattice oxygen over oxygen vacancies, thus resulting in catalyst deactivation. Nevertheless, the deactivated catalyst can be regenerated at 400 °C in air atmosphere. These results provide a new perspective for catalysts applied for ozone decomposition.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This research was supported by the National Key R&D Program of China (No. 2017YFC0211800) and Natural Science Foundation of China (No. 52070010).

## References

- 1 L. Zhang, S. Wang, C. Ni, M. Wang and S. Wang, *Chem. Eng. Sci.*, 2021, **229**, 116011.
- 2 C. Guo, Z. Gao and J. Shen, *Build. Environ.*, 2019, **158**, 302–318.
- 3 X. Liang, L. Wang, T. Wen, H. Liu, J. Zhang, Z. Liu, C. Zhu and C. Long, *Sci. Total Environ.*, 2022, **804**, 150161.
- 4 M. Namdari, C.-S. Lee and F. Haghghat, *Build. Environ.*, 2021, **187**, 107370.
- 5 S. Oyama, *Catal. Rev.*, 2000, **42**, 279–322.
- 6 S. Yang, Z. Zhu, F. Wei and X. Yang, *Build. Environ.*, 2017, **125**, 60–66.
- 7 M. Ondarts, J. Outin, L. Reinert, E. Gonze and L. Duclaux, *Eur. Phys. J-Spec. Top.*, 2015, **224**, 1995–1999.
- 8 H. Helln, P. Kuronen and H. Hakola, *Atmos. Environ.*, 2012, **57**, 35–40.
- 9 W. Yang, J. Ren, J. Li, H. Zhang, K. Ma, Q. Wang, Z. Gao, C. Wu and I. D. Gates, *J. Hazard. Mater.*, 2022, **421**, 126639.
- 10 L. Wang, J. Guan, H. Han, M. Yao, J. Kang, M. Peng, D. Wang, J. Xu and J. Hao, *Appl. Catal., B*, 2022, **306**, 121130.
- 11 W. Smith, S. Mao, G. Lu, A. Catlett, J. Chen and Y. Zhao, *Chem. Phys. Lett.*, 2010, **485**, 171–175.
- 12 Y. Lin and C. Lin, *Environ. Prog.*, 2008, **27**, 496–502.
- 13 W. Hong, J. Ma, T. Zhu, H. He, H. Wang, Y. Sun, F. Shen and X. Li, *Appl. Catal., B*, 2021, **297**, 120466.
- 14 W. Hong, M. Shao, T. Zhu, H. Wang, Y. Sun, F. Shen and X. Li, *Appl. Catal., B*, 2020, **274**, 119088.
- 15 N. Kumar, P. Konova, A. Naydenov, T. Heikilla, T. Salmi and D. Murzin, *Catal. Lett.*, 2004, **98**, 57–60.
- 16 X. Shao, X. Li, J. Ma, R. Zhang and H. He, *ACS Omega*, 2021, **6**, 10715–10722.
- 17 L. Yang, J. Ma, X. Li, G. He, C. Zhang and H. He, *Catal. Sci. Technol.*, 2020, **10**, 7671–7680.
- 18 Z. Hao, D. Cheng, Y. Guo and Y. Liang, *Appl. Catal., B*, 2001, **33**, 217–222.
- 19 L. Zhang, J. Yang, A. Wang, S. Chai, J. Guan, L. Nie, G. Fan, N. Han and Y. Chen, *Appl. Catal., B*, 2022, **303**, 120927.
- 20 W. Hong, T. Zhu, Y. Sun, H. Wang, X. Li and F. Shen, *Environ. Sci. Technol.*, 2019, **53**, 13332–13343.
- 21 J. Jia, W. Yang, P. Zhang and J. Zhang, *Appl. Catal., A*, 2017, **546**, 79–86.
- 22 A. Wang, J. Guan, L. Zhang, H. Wang, G. Ma, G. Fan, W. Tang, N. Han and Y. Chen, *J. Phys. Chem. C*, 2022, **126**, 317–325.
- 23 S. Gong, A. Wang, Y. Wang, H. Liu, N. Han and Y. Chen, *ACS Appl. Nano Mater.*, 2020, **3**, 597–607.

- 24 X. Li, J. Ma and H. He, *J. Environ. Sci.*, 2020, **94**, 14–31.
- 25 Y. Liu and P. Zhang, *J. Phys. Chem. C*, 2017, **121**, 23488–23497.
- 26 J. Jia, P. Zhang and L. Chen, *Appl. Catal., B*, 2016, **189**, 210–218.
- 27 C. Wang, J. Ma, F. Liu, H. He and R. Zhang, *J. Phys. Chem. C*, 2015, **119**, 23119–23126.
- 28 X. Li, J. Ma, C. Zhang, R. Zhang and H. He, *J. Environ. Sci.*, 2020, **91**, 43–53.
- 29 B. Napruszewska, A. Michalik-Zym, R. Dula, E. Bielanska, W. Rojek, T. Machej, R. Socha, L. Litynska-Dobrzynska, K. Bahranowski and E. Serwicka, *Appl. Catal., B*, 2017, **211**, 46–56.
- 30 Q. Zhao, Q. Liu, C. Song, N. Ji, D. Ma and X. Lu, *Chemosphere*, 2019, **218**, 895–906.
- 31 S. Mo, Q. Zhang, Q. Ren, J. Xiong, M. Zhang, Z. Feng, D. Yan, M. Fu, J. Wu, L. Chen and D. Ye, *J. Hazard. Mater.*, 2019, **364**, 571–580.
- 32 M. Castano, R. Molina and S. Moreno, *Appl. Catal., A*, 2015, **492**, 48–59.
- 33 N. Li, J. Cheng, X. Xing, P. Li and Z. P. Hao, *Catal. Today*, 2019, **327**, 382–388.
- 34 S. Zhao, F. Hu and J. Li, *ACS Catal.*, 2016, **6**, 3433–3441.
- 35 S. Li, H. Wang, W. Li, X. Wu, W. Tang and Y. Chen, *Appl. Catal., B*, 2015, **166**, 260–269.
- 36 R. Xie, G. Fan, L. Yang and F. Li, *Chem. Eng. J.*, 2016, **288**, 169–178.
- 37 M. Sui, B. Duan, L. Sheng, S. Huang and L. She, *Chinese J. Catal.*, 2012, **33**, 1284–1289.
- 38 R. Dula, R. Janik, T. Machej, J. Stoch, R. Grabowski and E. M. Serwicka, *Catal. Today*, 2007, **119**, 327–331.
- 39 L. Li, L. Dou and H. Zhang, *Nanoscale*, 2014, **6**, 3753–3763.
- 40 S. Aisawa, H. Hirahara, H. Uchiyama, S. Takahashi and E. Narita, *J. Solid State Chem.*, 2002, **167**, 152–159.
- 41 J. Villegas, O. Giraldo, K. Laubernds and S. Suib, *Inorg. Chem.*, 2003, **42**, 5621–5631.
- 42 S. Mo, S. Li, W. Li, J. Li, J. Chen and Y. Chen, *J. Mater. Chem. A*, 2016, **4**, 8113–8122.
- 43 L. Zou, F. Li, X. Xiang, D. Evans and X. Duan, *Chem. Mater.*, 2006, **18**, 5852–5859.
- 44 R. Cao, L. Li and P. Zhang, *J. Hazard. Mater.*, 2021, **407**, 124793.
- 45 A. Ramirez, P. Hillebrand, D. Stellmach, M. May, P. Bogdanoff and S. Fiechter, *J. Phys. Chem. C*, 2014, **118**, 14073–14081.
- 46 G. Zhu, J. Zhu, W. Jiang, Z. Zhang, J. Wang, Y. Zhu and Q. Zhang, *Appl. Catal., B*, 2017, **209**, 729–737.
- 47 Y. Liu, W. J. Yang, P. Zhang and J. Zhang, *Appl. Surf. Sci.*, 2018, **442**, 640–649.
- 48 P. Kuśtrowski, L. Chmielarz and E. Bożek, *Mater. Res. Bull.*, 2004, **39**, 263–281.
- 49 J. Shen, M. Tu and C. Hu, *J. Solid State Chem.*, 1998, **137**, 295–301.
- 50 L. Wei, H. Chen, Y. Wei, J. Jia and R. Zhang, *J. Environ. Sci.*, 2021, **103**, 219–228.
- 51 Y. Yang, J. Jia, Y. Liu and P. Zhang, *Appl. Catal., A*, 2018, **562**, 132–141.
- 52 J. Roscoe and J. D. Abbatt, *J. Phys. Chem. A*, 2005, **109**, 9028–9034.
- 53 R. Radhakrishnan, S. Oyama, J. G. Chen and K. Asakura, *J. Phys. Chem. B*, 2001, **105**, 4245–4253.