



CrossMark  
click for updates

Cite this: *Chem. Sci.*, 2016, 7, 2331

# Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub> as a novel Lewis acid to trap abnormal N-heterocyclic carbenes: the unprecedented formation of a singly bonded [6,6]-adduct†

Muqing Chen,<sup>‡,ab</sup> Lipiao Bao,<sup>‡,a</sup> Min Ai,<sup>a</sup> Wangqiang Shen<sup>a</sup> and Xing Lu<sup>\*a</sup>

The reaction between an *N*-heterocyclic carbene (NHC), namely 1,3-bis(diisopropylphenyl)-imidazol-2-ylene (**1**), and Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub> successfully affords a Lewis acid–base pair (**2a**). Single crystal X-ray crystallographic results unambiguously reveal the unexpected structure of **2a** where the abnormal carbene center of the NHC is connected to a triple-hexagon-junction (THJ) carbon atom of Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub> *via* a single bond. Theoretical calculations reveal that selective entrapment of the abnormal carbene **1** is caused by the steric hindrance between the normal NHC moiety and the fullerene cage, which precludes the formation of normal carbene adducts. Furthermore, the analysis of the electronic density distribution on the cage of Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub> indicates that THJ carbons bear relatively low negative charge densities and, accordingly, are easily attacked by the electron-rich NHC **1** to form the singly bonded [6,6]-adduct **2a** instead of the corresponding [5,6]-adduct **2b**. It is thus confirmed that the regioselective formation of **2a** is a synergistic effect of both cage size and electron density distribution. Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub>, although with a highly charged cage, is proven to show excellent Lewis acidity, opening a wide avenue toward carbon-based Lewis acids taking into account the diversity of endohedral metallofullerenes.

Received 27th October 2015  
Accepted 1st December 2015

DOI: 10.1039/c5sc04070a

www.rsc.org/chemicalscience

## Introduction

“Frustrated Lewis pairs” are promising metal-free catalysts to activate small molecules such as H<sub>2</sub>, CO<sub>2</sub>, alkenes and alkynes.<sup>1–3</sup> Carbon-based Lewis bases are naturally diverse, such as ylides, isonitriles, enamines and *N*-heterocyclic carbenes (NHCs).<sup>4</sup> Among them, NHCs as stable carbene compounds featuring a neutral divalent carbon atom with two non-bonding electrons are considered as prototypical reactive intermediates and have attracted intensive interest.<sup>5</sup> Usually, NHCs use the normal carbene center (*e.g.* C2 of **1'** in Scheme 1) to form η<sub>1</sub> complexes.<sup>6</sup> However, recent experimental and theoretical results show that abnormal carbenes with C5 as the active center (*e.g.* **1** in Scheme 1) have a stronger electron-donating ability and, accordingly, their complexes show better catalytic properties than the normal ones.<sup>7,8</sup> As a direct result, great efforts have been devoted to the exploration of abnormal carbene compounds.<sup>9</sup>


In contrast, carbon-based Lewis acids are limited merely to trityl cations and some electron-poor allenes.<sup>4</sup> Recently, Bazan and coworkers reported that fullerenes such as C<sub>60</sub> and C<sub>70</sub> can behave as all-carbon Lewis acids to form the corresponding Lewis acid–base pairs with a normal NHC structure (**1'**).<sup>10</sup> This work opens a new perspective on the research of carbon-based Lewis acids. Meanwhile, as a novel class of metal–carbon hybrid molecules, endohedral metallofullerenes (EMFs) feature electron transfer from the internal metallic species to the carbon cage, forming zwitterionic compounds.<sup>11</sup> Accordingly, it is of

<sup>a</sup>State Key Laboratory of Materials Processing and Die & Mould Technology, School of Materials Science and Engineering, Huazhong University of Science and Technology, 1037 Luoyu Road, Wuhan, 430074 China. E-mail: lux@hust.edu.cn

<sup>b</sup>School of Physics and Mechanical & Electronical Engineering, Hubei University of Education, Wuhan 430205, China

† Electronic supplementary information (ESI) available. CCDC 1406974. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c5sc04070a

‡ These authors contributed equally to this work.

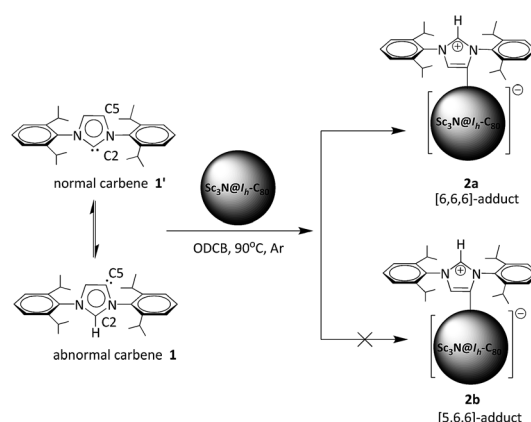

Scheme 1 The reaction between **1** and Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub>.



special interest to study whether the highly charged carbon cages of EMFs are willing to accept additional electrons to act as Lewis acids or not.

Herein, taking  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  as a representative, we show that EMFs also exhibit excellent Lewis acidity to form Lewis acid-base pairs with NHCs. Surprisingly, our unambiguous X-ray results reveal that the *abnormal* NHC **1** is bonded to  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$ , instead of the normal one **1'** (Scheme 1). More interestingly, a singly bonded [6,6,6]-adduct (**2a**) of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  is formed during the reaction, which has never been observed or even predicted, in contrast to the commonly observed [5,6,6]-adduct (**2b**). Our theoretical results reveal that the regioselective formation of the unprecedented [6,6,6]-adduct with an abnormal carbene moiety (**2a**) is synergistically affected by the cage size of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  and the electronic density distribution on the cage.

## Results and discussion

In a typical reaction, an *ortho*-dichlorobenzene (ODCB) solution of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  and an excess amount (*ca.* 50-fold) of 1,3-bis-(diisopropylphenyl)-imidazol-2-ylene (**1**) was heated to 90 °C under an argon atmosphere (Scheme 1). The reaction progress was monitored *via* high performance liquid chromatography (HPLC). After the solution was heated for 12 hours, a new peak appeared at 18.3 min, which is ascribed to the adduct **2a** as identified using mass spectrometry (Fig. 1). The reaction was

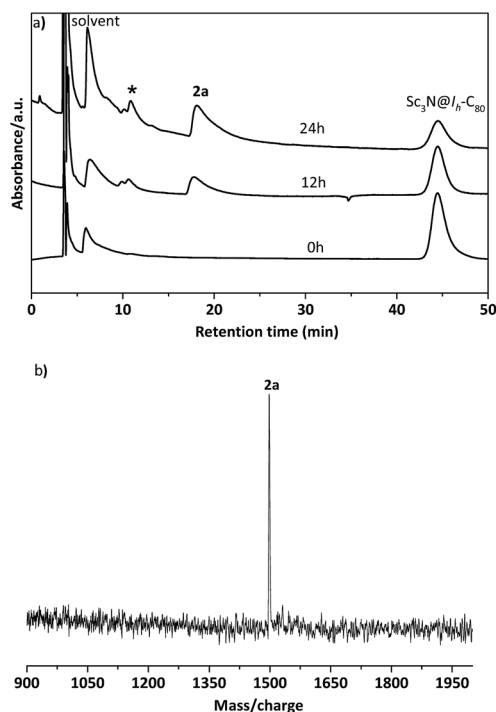


Fig. 1 (a) Monitoring the reaction between **1** and  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  *via* HPLC. Conditions: Buckyprep column ( $\varnothing$  4.6 mm  $\times$  250 mm), 0.8 mL  $\text{min}^{-1}$  toluene flow, and 330 nm detection wavelength. The peak marked with an asterisk represents an unidentified product. (b) MALDI-TOF mass spectrum of **2a**.

terminated after 24 hours, and **2a** was isolated with preparative HPLC in  $\sim$ 80% conversion yield based on consumed  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$ . The matrix assisted laser desorption/ionization time-of-flight (MALDI-TOF) mass spectrum of **2a** displays a single peak at  $m/z$  1498.2, firmly confirming the successful attachment of the NHC moiety onto the fullerene cage (Fig. 1b).

The electronic configuration of **2a** was investigated using UV-Vis-NIR spectroscopy in toluene (Fig. 2). Although the spectrum of **2a** resembles that of pristine  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  in the wavelength range between 540 nm and 1100 nm, their curves at 350–540 nm differ significantly from one another, confirming that the electronic structure of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  has been altered by the modification.

The structure of **2a** is unequivocally established *via* single-crystal X-ray crystallography. The entire system is fully ordered, including the functionalized cage, the internal cluster and even the three  $\text{CS}_2$  solvent molecules.<sup>12</sup> It is evident that a single bond is formed between the addend and the cage with a bond length of 1.515 Å (C5–C6), confirming unambiguously the formation of a Lewis acid–base complex (Fig. 3a).<sup>13,14</sup> More surprisingly, the addition site on the cage of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  involves a triple hexagon junction (THJ) which is generally less reactive than the carbon atoms of other kinds on a fullerene cage. Such an addition pattern has never been observed or even expected for  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  because previously reported singly bonded derivatives contained at least two substituents that are exclusively linked to the pentagon–hexagon–hexagon junction (PHHJ) carbon atoms unless the cage is severely functionalized.<sup>15–17</sup> Because of the substitution, the carbon atom at the site of addition (C6) is slightly pulled out from the cage sphere which causes a ‘Y-shaped’ displacement of the internal  $\text{Sc}_3\text{N}$  cluster with the  $\text{Sc}_3\text{-N1}$  bond nearly collinear with the new bond C5–C6, whereas the  $\text{Sc}_3\text{N}$ -plane is perpendicular to the *N*-heterocyclic ring of the addend (Fig. 3b).

Surprisingly, the NHC moiety is linked to the cage of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  with its abnormal carbene center C5 instead of the normal site C2, which is completely different from the corresponding Lewis pairs of  $\text{C}_{60}$  and  $\text{C}_{70}$ .<sup>10</sup> The bond length of C4–C5 (1.367 Å) falls into the range of a C=C double bond, confirming the existence of imidazol-2-ylene. The lengths of the

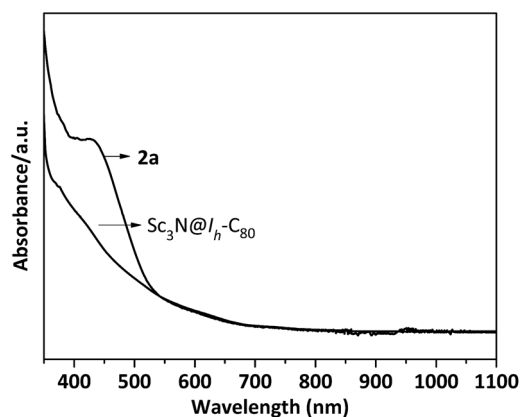


Fig. 2 UV-Vis-NIR spectra of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  and **2a**.



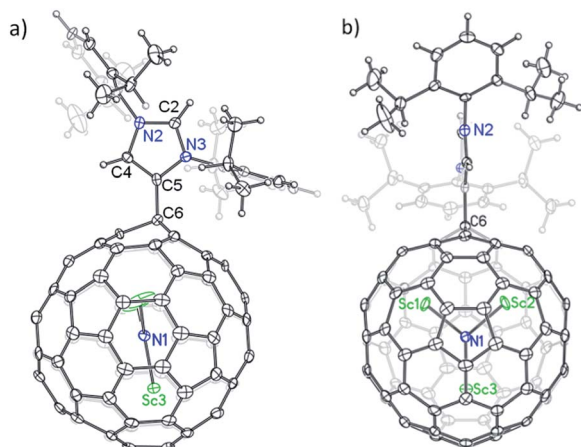


Fig. 3 Single-crystal X-ray structure of **2a**: (a) side view, and (b) front view. Thermal ellipsoids are shown at the 50% probability level. Solvent molecules are omitted for clarity.

other four C–N bonds forming the *N*-heterocyclic ring are similar: 1.384 Å (C4–N2), 1.326 Å (C2–N2), 1.333 Å (C2–N3) and 1.386 Å (C5–N3), excluding the existence of C=N double bonds.

The unprecedented structure of **2a** with an abnormal NHC moiety singly bonded to a THJ carbon atom is of great interest. First, we try to understand why a [6,6,6]-adduct (**2a**) is formed instead of the corresponding [5,6,6]-adduct (**2b**). It is well-known that THJ carbons are less pyramidal and accordingly are less reactive than the carbon atoms of other kinds of fullerenes.<sup>18</sup> Indeed, our theoretical results suggest that the [5,6,6]-adduct **2b**, if formed, is 0.49 kcal mol<sup>-1</sup> more stable than the [6,6,6]-adduct **2a** (Fig. 4a), indicating that the preferential formation of **2a** is not a thermodynamically controlled process. We then consider that the electron density distribution on the cage of Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub> should be a critical factor. It is widely accepted that pentagons are the sites of the negative charges of highly charged fulleride species such as EMFs.<sup>19</sup> Accordingly, [5,6,6]-junction carbon atoms always accumulate more negative charges than THJ carbons do. As a direct result, NHCs as electron-rich Lewis bases tend to attack the [6,6,6]-junction carbon atoms which have lower electron densities, revealing the Lewis acidic property of Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub>. In summary, the [6,6,6]-addition pattern of **2a** is a consequence of the electron density distribution on the cage of Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub>.

We then try to find a reasonable explanation for the unexpected formation of the abnormal carbene structure of **2a**. Usually NHCs use the normal carbene center (C2 in **1'**, Scheme 1) to bind metals. However, abnormal NHC carbene species (**1**, Scheme 1) can stably exist and can even be isolated.<sup>20</sup> Several examples of abnormal carbene complexes have been reported, which show enhanced catalytic properties for the activation of unreactive bonds.<sup>7,8</sup> Furthermore, Dagorne and coworkers reported that a normal but sterically congested NHC–AlMe<sub>3</sub> Lewis acid–base pair can isomerize to its abnormal NHC–AlMe<sub>3</sub> species.<sup>20</sup> This result inspires us to speculate that the abnormal carbene structure of **2a** is also caused by a steric effect. Our computational results showed that neither the normal [6,6,6]-


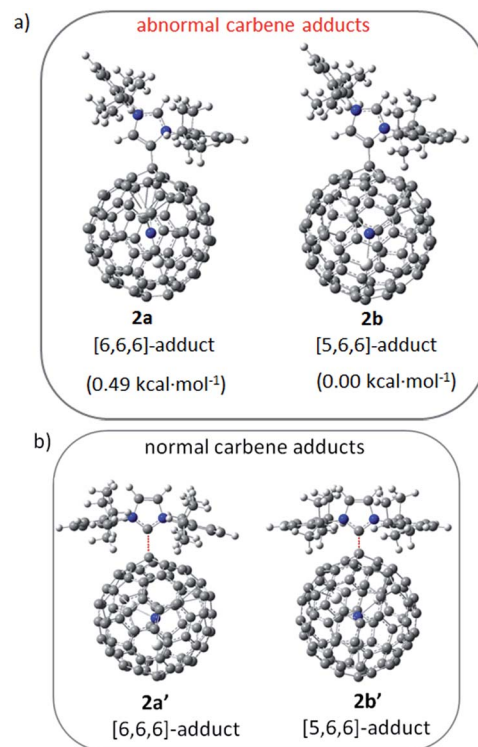


Fig. 4 Possible structures of NHC–Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub> complexes and their relative energies calculated at the B3LYP/6-31G\*/LANL2DZ (Sc) level.

adduct (**2a'**) nor the normal [5,6,6]-adduct (**2b'**) can exist as stable compounds: during the optimization processes the single bond connecting the normal NHC moiety and Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub> is broken (Fig. 4b), which can be attributed to the steric hindrance between the congested diisopropylphenyl groups of the normal NHC (**1'**) and the large cage of Sc<sub>3</sub>N@I<sub>h</sub>-C<sub>80</sub>.

Finally, we propose a plausible mechanism to rationalize the unexpected formation of **2a** (Scheme 2). According to the literature, the normal carbene **1'**, where C2 is the carbene center, can tautomerize into the abnormal one **1** with C5 as the active

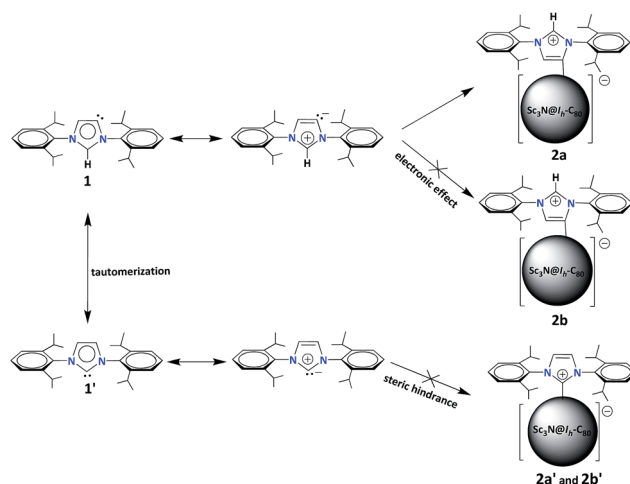

Scheme 2 Plausible formation mechanism of **2a**.



site.<sup>21</sup> Then, the tautomers (**1** and **1'**) turn into the corresponding mesoionic compounds.<sup>9</sup> Since the mesoionic species of **1'** can not form stable adducts (**2a'** and **2b'**) with  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  because of the high steric hindrance between the addend and the cage, only the abnormal carbene structure is possible. As discussed above, the electron-rich NHC **1** (or the corresponding mesoionic compound) tends to attack one of the THJ carbon atoms with low electron densities, forming the [6,6,6]-adduct **2a** in a highly regioselective manner.

## Conclusions

In summary,  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  is confirmed to be an excellent carbon-based Lewis acid although its cage is negatively charged, representing the first example of EMFs that readily undergo Lewis acid–base complexation reactions with NHCs. The regioselective formation of the unusual singly bonded [6,6,6]-adduct **2a** is reasonably interpreted by analyzing the charge density distribution on the cage because the electron-rich NHC is prone to attack one of the THJ carbons with low electron densities. More interestingly,  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$  here is found to selectively trap the rare abnormal NHC **1** as a consequence of the steric hindrance between the normal NHC moiety and  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$ . Hence, we conclude that the regioselective and unprecedented formation of **2a** is a synergistic effect of both the cage size and electron density distribution of  $\text{Sc}_3\text{N}@I_h\text{-C}_{80}$ . This synthetic strategy can be easily extended to create various EMF-based Lewis acid–base pairs with different metallic cores and/or cage structures, which may show unique catalytic properties in organic synthesis, taking into account their “frustrated” characteristics.

## Acknowledgements

Professors M. M. Olmstead and A. L. Balch in UC Davis are gratefully acknowledged for their assistance in single-crystal X-ray measurement. Financial support from the National Thousand Talents Program of China, NSFC (21171061, 51472095), Program for Changjiang Scholars and Innovative Research Team in University (IRT1014) and Key Laboratory of Functional Inorganic Material Chemistry (Heilongjiang University), Ministry of Education are gratefully acknowledged. We thank the Analytical and Testing Center in Huazhong University of Science and Technology for all related measurements.

## Notes and references

1 D. W. Stephan and G. Erker, *Angew. Chem., Int. Ed.*, 2010, **49**, 46.

- M. Légaré, M. Courtemanche, É. Rochette and F. Fontaine, *Science*, 2015, **349**, 513.
- S. K. Bose and T. B. Marder, *Science*, 2015, **349**, 473.
- J. Iglesias-Sigüenza and M. Alcarazo, *Angew. Chem., Int. Ed.*, 2012, **51**, 1523.
- F. E. Ahn and M. C. Jahnke, *Angew. Chem., Int. Ed.*, 2008, **47**, 3122.
- S. Díez-González, N. Marion and S. P. Nolan, *Chem. Rev.*, 2009, **109**, 3612.
- H. Lebel, M. K. Janes, A. B. Charette and S. P. Nolan, *J. Am. Chem. Soc.*, 2004, **126**, 5046.
- M. Heckenroth, E. Kluser, A. Neels and M. Albrecht, *Angew. Chem., Int. Ed.*, 2007, **46**, 6293.
- E. Aldeco-Perez, A. J. Rosenthal, B. Donnadiou, P. Parameswaran, G. Frenking and G. Bertrand, *Science*, 2009, **326**, 556.
- H. P. Li, C. Risko, J. H. Seo, C. Campbell, G. Wu, J. Bredas and G. C. Bazan, *J. Am. Chem. Soc.*, 2011, **133**, 12410.
- X. Lu, L. Echegoyen, A. L. Balch, S. Nagase and T. Akasaka, *Endohedral Metallofullerenes: Basics and Applications*, CRC Press, New York, 2015.
- Crystal data of **2a**. Black block, triclinic, space group  $P\bar{1}$ ,  $a = 10.9903(19) \text{ \AA}$ ,  $b = 17.558(3) \text{ \AA}$ ,  $c = 19.758(4) \text{ \AA}$ ,  $\alpha = 99.562(3)^\circ$ ,  $\beta = 90.938(3)^\circ$ ,  $\gamma = 107.217(3)^\circ$ ,  $V = 3376.2(10) \text{ \AA}^3$ ,  $Z = 1$ ,  $D_{\text{calc}} = 1.661 \text{ Mg m}^{-3}$ ,  $\mu = 0.514 \text{ mm}^{-1}$ ,  $T = 90(2) \text{ K}$ ,  $2\theta_{\text{max}} = 50.852^\circ$ ; 12355 reflections, 7675 with  $I > 2\sigma(I)$ ;  $R1 = 0.0784$  [ $I > 2\sigma(I)$ ],  $wR2 = 0.2401$  (all data). The maximum residual electron density is  $1.255 \text{ e\AA}^{-3}$ .
- C. Shu, W. Xu, C. Slebodnick, H. Champion, W. Fu, J. E. Reid, H. Azurmendi, C. Wang, K. Harich, H. C. Dorn and H. W. Gibson, *Org. Lett.*, 2009, **11**, 1753.
- M. Izquierdo, M. R. Cerón, M. M. Olmstead, A. L. Balch and L. Echegoyen, *Angew. Chem., Int. Ed.*, 2013, **125**, 12042.
- N. B. Shustova, A. A. Popov, M. A. Mackey, C. E. Coumbe, J. P. Phillips, S. Stevenson, S. H. Strauss and O. V. Boltalina, *J. Am. Chem. Soc.*, 2007, **129**, 11676.
- C. Shu, C. Slebodnick, L. Xu, H. Champion, T. Fuhrer, T. Cai, J. E. Reid, W. Fu, K. Harich, H. C. Dorn and H. W. Gibson, *J. Am. Chem. Soc.*, 2008, **130**, 17755.
- N. B. Shustova, Y. S. Chen, M. A. Mackey, C. E. Coumbe, J. P. Phillips, S. Stevenson, A. A. Popov, O. V. Boltalina and S. H. Strauss, *J. Am. Chem. Soc.*, 2009, **131**, 17630.
- Y. Z. Tan, S. Y. Xie, R. B. Huang and L. S. Zheng, *Nat. Chem.*, 2009, **1**, 450.
- A. Rodríguez-Forteza, N. Alegret, A. L. Balch and J. M. Poblet, *Nat. Chem.*, 2010, **2**, 955.
- A. Schmitt, G. Schnee, R. Welter and S. Dagorne, *Chem. Commun.*, 2010, **46**, 2480.
- M. Albrecht, *Chem. Commun.*, 2008, 3601.

